


BOSTON PUBLIC LIBRARY



3 9999 06317 239 7

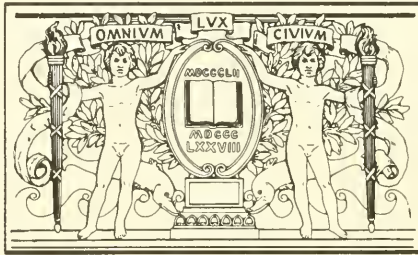

**BOSTON
PUBLIC
LIBRARY**





LIBRARY CATALOGUE SLIPS.

- | | |
|--------------------------|--|
| Series title. | <p>United States. <i>Department of the interior.</i> (<i>U. S. geological survey.</i>)
 Department of the interior United States geological survey
 J. W. Powell, director — Mineral resources of the United
 States — Calendar years 1889 and 1890 — David T. Day
 chief of division of mining statistics and technology [Vi-
 gnette]
 Washington government printing office 1892
 8°. viii, 671 pp.</p> |
| Author title. | <p>Day (David Talbot).
 Department of the interior United States geological survey
 J. W. Powell, director — Mineral resources of the United
 States — Calendar years 1889 and 1890 — David T. Day
 chief of division of mining statistics and technology [Vi-
 gnette]
 Washington government printing office 1892
 8°. viii, 671 pp.
 [UNITED STATES. <i>Department of the interior.</i> (<i>U. S. geological survey.</i>)]</p> |
| Title for subject entry. | <p>Department of the interior United States geological survey
 J. W. Powell, director — Mineral resources of the United
 States — Calendar years 1889 and 1890 — David T. Day
 chief of division of mining statistics and technology [Vi-
 gnette]
 Washington government printing office 1892
 8°. viii, 671 pp.
 [UNITED STATES. <i>Department of the interior.</i> (<i>U. S. geological survey.</i>)]</p> |

ADVERTISEMENT.

[Mineral Resources of the United States, 1889 and 1890.]

The publications of the United States Geological Survey are issued in accordance with the statute approved March 3, 1879, which declares that—

“The publications of the Geological Survey shall consist of the annual report of operations, geological and economic maps illustrating the resources and classification of the lands, and reports upon general and economic geology and paleontology. The annual report of operations of the Geological Survey shall accompany the annual report of the Secretary of the Interior. All special memoirs and reports of said Survey shall be issued in uniform quarto series if deemed necessary by the Director, but otherwise in ordinary octavos. Three thousand copies of each shall be published for scientific exchanges and for sale at the price of publication; and all literary and cartographic materials received in exchange shall be the property of the United States and form a part of the library of the organization; and the money resulting from the sale of such publications shall be covered into the Treasury of the United States.”

On July 7, 1882, the following joint resolution, referring to all Government publications, was passed by Congress:

“That whenever any document or report shall be ordered printed by Congress, there shall be printed, in addition to the number in each case stated, the ‘usual number’ (1,900) of copies for binding and distribution among those entitled to receive them.”

Except in those cases in which an extra number of any publication has been supplied to the Survey by special resolution of Congress or has been ordered by the Secretary of the Interior, this office has no copies for gratuitous distribution.

ANNUAL REPORTS.

I. First Annual Report of the United States Geological Survey, by Clarence King. 1880. 8°. 79 pp. 1 map.—A preliminary report describing plan of organization and publications.

II. Second Annual Report of the United States Geological Survey, 1880-'81, by J. W. Powell. 1882. 8°. 1v, 568 pp. 62 pl. 1 map.

III. Third Annual Report of the United States Geological Survey, 1881-'82, by J. W. Powell. 1883. 8°. xviii, 564 pp. 67 pl. and maps.

IV. Fourth Annual Report of the United States Geological Survey, 1882-'83, by J. W. Powell. 1884. 8°. xxxii, 473 pp. 85 pl. and maps.

V. Fifth Annual Report of the United States Geological Survey, 1883-'84, by J. W. Powell. 1885. 8°. xxxvi, 469 pp. 58 pl. and maps.

VI. Sixth Annual Report of the United States Geological Survey, 1884-'85, by J. W. Powell. 1885. 8°. xxix, 570 pp. 65 pl. and maps.

VII. Seventh Annual Report of the United States Geological Survey, 1885-'86, by J. W. Powell. 1888. 8°. xx, 656 pp. 71 pl. and maps.

VIII. Eighth Annual Report of the United States Geological Survey, 1886-'87, by J. W. Powell. 1889. 8°. 2 v. xix, 474, xii pp. 53 pl. and maps; 1 p. l. 475-1063 pp. 54-76 pl. and maps.

IX. Ninth Annual Report of the United States Geological Survey, 1887-'88, by J. W. Powell. 1889. 8°. xiii, 717 pp. 88 pl. and maps.

X. Tenth Annual Report of the United States Geological Survey, 1888-'89, by J. W. Powell. 1890. 8°. 2 v. xv, 774 pp. 98 pl. and maps; viii, 123 pp.

XI. Eleventh Annual Report of the United States Geological Survey, 1889-'90, by J. W. Powell. 1891. 8°. 2 v. xv, 757 pp. 66 pl. and maps; ix, 351 pp. 30 pl.

XII. Twelfth Annual Report of the United States Geological Survey, 1890-'91, by J. W. Powell. 1891. 8°. 2 v. xiii, 675 pp. 53 pl. and maps; xviii, 576 pp. 146 pl. and maps.

MONOGRAPHS.

I. Lake Bonneville, by Grove Karl Gilbert. 1890. 4°. xx, 438 pp. 51 pl. 1 map. Price \$1.50.

II. Tertiary History of the Grand Cañon District, with atlas, by Clarence E. Dutton, Capt. U. S. A. 1882. 4°. xiv, 264 pp. 42 pl. and atlas of 24 sheets folio. Price \$10.00.

III. Geology of the Comstock Lode and the Washoe District, with atlas, by George F. Becker. 1882. 4°. xv, 422 pp. 7 pl. and atlas of 21 sheets folio. Price \$11.00.

IV. Comstock Mining and Miners, by Eliot Lord. 1883. 4°. xiv, 451 pp. 3 pl. Price \$1.50.

V. The Copper-Bearing Rocks of Lake Superior, by Roland Duer Irving. 1883. 4°. xvi, 464 pp. 15 l. 29 pl. and maps. Price \$1.85.

VI. Contributions to the Knowledge of the Older Mesozoic Flora of Virginia, by William Morris Fontaine. 1883. 4°. xi, 144 pp. 54 l. 54 pl. Price \$1.05.

VII. Silver-Lead Deposits of Eureka, Nevada, by Joseph Story Curtis. 1884. 4°. xiii, 200 pp. 16 pl. Price \$1.20.

VIII. Paleontology of the Eureka District, by Charles Doolittle Walcott. 1884. 4°. xiii, 298 pp. 24 l. 24 pl. Price \$1.10.

IX. Brachiopoda and Lamellibranchiata of the Raritan Clays and Greensand Marls of New Jersey, by Robert P. Whitfield. 1885. 4°. xx, 338 pp. 35 pl. 1 map. Price \$1.15.

X. Dinocerata. A Monograph of an Extinct Order of Gigantic Mammals, by Othniel Charles Marsh. 1886. 4°. xviii, 243 pp. 56 l. 56 pl. Price \$2.70.

XI. Geological History of Lake Lahontan, a Quaternary Lake of Northwestern Nevada, by Israel Cook Russell. 1885. 4°. xiv, 288 pp. 46 pl. and maps. Price \$1.75.

XII. Geology and Mining Industry of Leadville, Colorado, with atlas, by Samuel Franklin Emmons. 1886. 4°. xxix, 770 pp. 45 pl. and atlas of 35 sheets folio. Price \$8.40.

XIII. Geology of the Quicksilver Deposits of the Pacific Slope, with atlas, by George F. Becker. 1888. 4°. xix, 486 pp. 7 pl. and atlas of 14 sheets folio. Price \$2.00.

XIV. Fossil Fishes and Fossil Plants of the Triassic Rocks of New Jersey and the Connecticut Valley, by John S. Newberry. 1888. 4°. xiv, 152 pp. 26 pl. Price \$1.00.

XV. The Potomac or Younger Mesozoic Flora, by William Morris Fontaine. 1889. 4°. xiv, 377 pp. 180 pl. Text and plates bound separately. Price \$2.50.

XVI. The Paleozoic Fishes of North America, by John Strong Newberry. 1889. 4°. 340 pp. 53 pl. Price \$1.00.

In press:

XVII. The Flora of the Dakota Group, a posthumous work, by Leo Lesquereux. Edited by F. H. Knowlton. 1891. 4°. 400 pp. 66 pl. Price \$1.10.

XVIII. Gasteropoda and Cephalopoda of the Raritan Clays and Greensand Marls of New Jersey, by Robert P. Whitfield. 1891. 4°. 402 pp. 50 pl. Price \$1.00.

In preparation:

XIX. The Penokee Iron-Bearing Series of Northern Wisconsin and Michigan, by Roland D. Irving and C. R. Van Hise.

XX. Geology of the Eureka District, Nevada, with atlas, by Arnold Hague.

XXI. The Tertiary Rhynchophorous Coleoptera of North America, by Samuel Hubbard Scudder.

XXII. Geology of the Green Mountains in Massachusetts, by Raphael Pumpelly, J. E. Wolf, T. Nelson Dal, and Bayard T. Putnam.

— Mollusca and Crustacea of the Miocene Formations of New Jersey, by R. P. Whitfield.

— Sauropoda, by O. C. Marsh.

— Stegosauria, by O. C. Marsh.

— Brontotheriidae, by O. C. Marsh.

— Report on the Denver Coal Basin, by S. F. Emmons.

— Report on Silver Cliff and Ten-Mile Mining Districts, Colorado, by S. F. Emmons.

— The Glacial Lake Agassiz, by Warren Upham.

BULLETINS.

1. On Hypersthene-Andesite and on Triclinic Pyroxene in Augitic Rocks, by Whitman Cross, with a Geological Sketch of Buffalo Peaks, Colorado, by S. F. Emmons. 1883. 8°. 42 pp. 2 pl. Price 10 cents.

2. Gold and Silver Conversion Tables, giving the coinage values of troy ounces of fine metal, etc., computed by Albert Williams, jr. 1883. 8°. 8 pp. Price 5 cents.

3. On the Fossil Faunas of the Upper Devonian, along the meridian of 76° 30', from Tompkins County, New York, to Bradford County, Pennsylvania, by Henry S. Williams. 1884. 8°. 36 pp. Price 5 cents.

4. On Mesozoic Fossils, by Charles A. White. 1884. 8°. 36 pp. 9 pl. Price 5 cents.

5. A Dictionary of Altitudes in the United States, compiled by Henry Gannett. 1884. 8°. 325 pp. Price 20 cents.

6. Elevations in the Dominion of Canada, by J. W. Spencer. 1884. 8°. 43 pp. Price 5 cents.

7. *Mapoteca Geologica Americana*. A Catalogue of Geological Maps of America (North and South), 1752-1881, in geographic and chronologic order, by Jules Marcou and John Belknap Marcou. 1884. 8°. 184 pp. Price 10 cents.

8. On Secondary Enlargements of Mineral Fragments in Certain Rocks, by R. D. Irving and C. R. Van Hise. 1884. 8°. 56 pp. 6 pl. Price 10 cents.

9. A report of work done in the Washington Laboratory during the fiscal year 1883-'84. F. W. Clarke, chief chemist. T. M. Chatard, assistant chemist. 1881. 8°. 40 pp. Price 5 cents.

10. On the Cambrian Faunas of North America. Preliminary studies, by Charles Doolittle Walcott. 1884. 8°. 74 pp. 10 pl. Price 5 cents.

11. On the Quaternary and Recent Mollusca of the Great Basin: with Descriptions of New Forms, by R. Ellsworth Call. Introduced by a sketch of the Quaternary Lakes of the Great Basin, by G. K. Gilbert. 1884. 8°. 66 pp. 6 pl. Price 5 cents.

12. A Crystallographic Study of the Thimolite of Lake Lahontan, by Edward S. Dana. 1884. 8°. 34 pp. 3 pl. Price 5 cents.
13. Boundaries of the United States and of the several States and Territories, with a Historical Sketch of the Territorial Changes, by Henry Gannett. 1885. 8°. 135 pp. Price 10 cents.
14. The Electrical and Magnetic Properties of the Iron-Carburets, by Carl Barus and Vincent Strouhal. 1885. 8°. 238 pp. Price 15 cents.
15. On the Mesozoic and Cenozoic Paleontology of California, by Charles A. White. 1885. 8°. 33 pp. Price 5 cents.
16. On the Higher Devonian Faunas of Ontario County, New York, by John M. Clarke. 1885. 8°. 86 pp. 3 pl. Price 5 cents.
17. On the Development of Crystallization in the Igneous Rocks of Washoe, Nevada, with Notes on the Geology of the District, by Arnold Hague and Joseph P. Iddings. 1885. 8°. 44 pp. Price 5 cents.
18. On Marine Eocene, Fresh-water Miocene, and other Fossil Mollusca of Western North America, by Charles A. White. 1885. 8°. 26 pp. 3 pl. Price 5 cents.
19. Notes on the Stratigraphy of California, by George F. Becker. 1885. 8°. 28 pp. Price 5 cents.
20. Contributions to the Mineralogy of the Rocky Mountains, by Whitman Cross and W. F. Hillebrand. 1885. 8°. 114 pp. 1 pl. Price 10 cents.
21. The Lignites of the Great Sioux Reservation. A Report on the Region between the Grand and Moreau Rivers, Dakota, by Bailey Willis. 1885. 8°. 16 pp. 5 pl. Price 5 cents.
22. On New Cretaceous Fossils from California, by Charles A. White. 1885. 8°. 25 pp. 5 pl. Price 5 cents.
23. Observations on the Junction between the Eastern Sandstone and the Keweenaw Series on Keweenaw Point, Lake Superior, by R. D. Irving and T. C. Chamberlin. 1885. 8°. 124 pp. 17 pl. Price 15 cents.
24. List of Marine Mollusca, comprising the Quaternary Fossils and recent forms from American Localities between Cape Hatteras and Cape Roque, including the Bermudas, by William Healey Dall. 1885. 8°. 336 pp. Price 25 cents.
25. The Present Technical Condition of the Steel Industry of the United States, by Phineas Barnes. 1885. 8°. 85 pp. Price 10 cents.
26. Copper Smelting, by Henry M. Howe. 1885. 8°. 107 pp. Price 10 cents.
27. Report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1884-'85. 1886. 8°. 80 pp. Price 10 cents.
28. The Gabbros and Associated Hornblende Rocks occurring in the Neighborhood of Baltimore, Maryland, by George Huntington Williams. 1886. 8°. 78 pp. 4 pl. Price 10 cents.
29. On the Fresh-water Invertebrates of the North American Jurassic, by Charles A. White. 1886. 8°. 41 pp. 4 pl. Price 5 cents.
30. Second Contribution to the Studies on the Cambrian Faunas of North America, by Charles Doolittle Walcott. 1886. 8°. 369 pp. 33 pl. Price 25 cents.
31. Systematic Review of our Present Knowledge of Fossil Insects, including Myriapods and Arachnids, by Samuel Hubbard Scudder. 1886. 8°. 128 pp. Price 15 cents.
32. Lists and Analyses of the Mineral Springs of the United States; a Preliminary Study, by Albert C. Peale. 1886. 8°. 235 pp. Price 20 cents.
33. Notes on the Geology of Northern California, by J. S. Diller. 1886. 8°. 23 pp. Price 5 cents.
34. On the relation of the Laramie Molluscan Fauna to that of the succeeding Fresh-water Eocene and other groups, by Charles A. White. 1886. 8°. 54 pp. 5 pl. Price 10 cents.
35. Physical Properties of the Iron-Carburets, by Carl Barus and Vincent Strouhal. 1886. 8°. 62 pp. Price 10 cents.
36. Subsidence of Fine Solid Particles in Liquids, by Carl Barus. 1886. 8°. 58 pp. Price 10 cents.
37. Types of the Laramie Flora, by Lester F. Ward. 1887. 8°. 354 pp. 57 pl. Price 25 cents.
38. Peridotite of Elliott County, Kentucky, by J. S. Diller. 1887. 8°. 31 pp. 1 pl. Price 5 cents.
39. The Upper Beaches and Deltas of the Glacial Lake Agassiz, by Warren Upham. 1887. 8°. 84 pp. 1 pl. Price 10 cents.
40. Changes in River Courses in Washington Territory due to Glaciation, by Bailey Willis. 1887. 8°. 10 pp. 4 pl. Price 5 cents.
41. On the Fossil Faunas of the Upper Devonian—the Genesee Section, New York, by Henry S. Williams. 1887. 8°. 121 pp. 4 pl. Price 15 cents.
42. Report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1885-'86. F. W. Clarke, chief chemist. 1887. 8°. 152 pp. 1 pl. Price 15 cents.
43. Tertiary and Cretaceous Strata of the Tuscaloosa, Tombigbee, and Alabama Rivers, by Eugene A. Smith and Lawrence C. Johnson. 1887. 8°. 189 pp. 21 pl. Price 15 cents.
44. Bibliography of North American Geology for 1886, by Nelson H. Darton. 1887. 8°. 35 pp. Price 5 cents.
45. The Present Condition of Knowledge of the Geology of Texas, by Robert T. Hill. 1887. 8°. 94 pp. Price 10 cents.
46. Nature and Origin of Deposits of Phosphate of Lime, by E. A. F. Penrose, jr., with an Introduction by N. S. Shaler. 1888. 8°. 143 pp. Price 15 cents.

47. Analyses of Waters of the Yellowstone National Park, with an Account of the Methods of Analysis employed, by Frank Austin Gooch and James Edward Whitfield. 1888. 8°. 84 pp. Price 10 cents.
48. On the Form and Position of the Sea Level, by Robert Simpson Woodward. 1888. 8°. 88 pp. Price 10 cents.
49. Latitudes and Longitudes of Certain Points in Missouri, Kansas, and New Mexico, by Robert Simpson Woodward. 1889. 8°. 133 pp. Price 15 cents.
50. Formulas and Tables to facilitate the Construction and Use of Maps, by Robert Simpson Woodward. 1889. 8°. 124 pp. Price 15 cents.
51. On Invertebrate Fossils from the Pacific Coast, by Charles Abiathar White. 1889. 8°. 102 pp. 14 pl. Price 15 cents.
52. Subaërial Decay of Rocks and Origin of the Red Color of Certain Formations, by Israel Cook Russell. 1889. 8°. 65 pp. 5 pl. Price 10 cents.
53. The Geology of Nantucket, by Nathaniel Southgate Shaler. 1889. 8°. 55 pp. 10 pl. Price 10 cents.
54. On the Thermo-Electric Measurement of High Temperatures, by Carl Barus. 1889. 8°. 313 pp. incl. 1 pl. 11 pl. Price 25 cents.
55. Report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1886-'87. Frank Wigglesworth Clarke, chief chemist. 1889. 8°. 96 pp. Price 10 cents.
56. Fossil Wood and Lignite of the Potomac Formation, by Frank Hall Knowlton. 1889. 8°. 72 pp. 7 pl. Price 10 cents.
57. A Geological Reconnaissance in Southwestern Kansas, by Robert Hay. 1890. 8°. 49 pp. 2 pl. Price 5 cents.
58. The Glacial Boundary in Western Pennsylvania, Ohio, Kentucky, Indiana, and Illinois, by George Frederick Wright, with an introduction by Thomas Chrowder Chamberlin. 1890. 8°. 112 pp. incl. 1 pl. 8 pl. Price 15 cents.
59. The Gabbros and Associated Rocks in Delaware, by Frederick D. Chester. 1890. 8°. 45 pp. 1 pl. Price 10 cents.
60. Report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1887-'88. F. W. Clarke, chief chemist. 1890. 8°. 174 pp. Price 15 cents.
61. Contributions to the Mineralogy of the Pacific Coast, by William Harlow Melville and Waldemar Lindgren. 1890. 8°. 40 pp. 3 pl. Price 5 cents.
62. The Greenstone Schist Areas of the Menominee and Marquette Regions of Michigan; a contribution to the subject of dynamic metamorphism in eruptive rocks, by George Huntington Williams; with an introduction by Roland Duer Irving. 1890. 8°. 241 pp. 16 pl. Price 30 cents.
63. A Bibliography of Paleozoic Crustacea from 1698 to 1889, including a list of North American species and a systematic arrangement of genera, by Anthony W. Vogdes. 1890. 8°. 177 pp. Price 15 cents.
64. A report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1888-'89. F. W. Clarke, chief chemist. 1890. 8°. 60 pp. Price 10 cents.
65. Stratigraphy of the Bituminous Coal Field of Pennsylvania, Ohio, and West Virginia, by Israel C. White. 1891. 8°. 212 pp. 11 pl. Price 20 cents.
66. On a Group of Volcanic Rocks from the Tewan Mountains, New Mexico, and on the occurrence of Primary Quartz in certain Basalts, by Joseph Paxson Iddings. 1890. 8°. 34 pp. Price 5 cents.
67. The relations of the Traps of the Newark System in the New Jersey Region, by Nelson Horatio Darton. 1890. 8°. 82 pp. Price 10 cents.
68. Earthquakes in California in 1889, by James Edward Keeler. 1890. 8°. 25 pp. Price 5 cents.
69. A Classified and Annotated Bibliography of Fossil Insects, by Samuel Hubbard Scudder. 1890. 8°. 101 pp. Price 15 cents.
70. Report on Astronomical Work of 1889 and 1890, by Robert Simpson Woodward. 1890. 8°. 79 pp. Price 10 cents.
71. Index to the Known Fossil Insects of the World, including Myriapods and Arachnids, by Samuel Hubbard Scudder. 1891. 8°. 744 pp. Price 50 cents.
72. Altitudes between Lake Superior and the Rocky Mountains, by Warren Upham. 1891. 8°. 229 pp. Price 20 cents.
73. The Viscosity of Solids, by Carl Barus. 1891. 8°. xii, 139 pp. 6 pl. Price 15 cents.
74. The Minerals of North Carolina, by Frederick Augustus Genth. 1891. 8°. 119 pp. Price 15 cents.
75. Record of North American Geology for 1887 to 1889, inclusive, by Nelson Horatio Darton. 1891. 8°. 173 pp. Price 15 cents.
76. A Dictionary of Altitudes in the United States (second edition), compiled by Henry Gannett, chief topographer. 1891. 8°. 393 pp. Price 25 cents.
77. The Texan Permian and its Mesozoic Types of Fossils, by Charles A. White. 1891. 8°. 51 pp. 4 pl. Price 10 cents.
78. A report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1889-'90. F. W. Clarke, chief chemist. 1891. 8°. 131 pp. Price 15 cents.

79. A Late Volcanic Eruption in Northern California and its Peculiar Lava, by J. S. Diller. 1891. 8°. 33 pp. 17 pl. Price 10 cents.
80. Correlation papers—Devonian and Carboniferous, by Henry Shaler Williams. 1891. 8°. 279 pp. Price 20 cents.
81. Correlation papers—Cambrian, by Charles Doolittle Walcott. 1891. 8°. 447 pp. 3 pl. Price 25 cents.
82. Correlation papers—Cretaceous, by Charles A. White. 1891. 8°. 273 pp. 3 pl. Price 20 cents.
83. Correlation papers—Eocene, by William Bullock Clark. 1891. 8°. 173 pp. 2 pl. Price 15 cents.
91. Record of North American Geology for 1890, by Nelson Horatio Darton. 1891. 8°. 88 pp. Price 10 cents.
- In press:
84. Correlation papers—Neocene, by W. H. Dall and G. D. Harris.
85. Correlation papers—The Newark System, by I. C. Russell.
86. Correlation papers—Archean and Algonkian, by C. R. Van Hise.
90. A report of work done in the Division of Chemistry and Physics, mainly during the fiscal year 1890-'91. F. W. Glarke, chief chemist.
92. The Compressibility of Liquids, by Carl Barus.
93. Some insects of special interest from Florissant, Colorado, by S. H. Scudder.
94. The Mechanism of Solid Viscosity, by Carl Barus.
95. Earthquakes in California during 1890-'91, by Edward S. Holden.
96. The Volume Thermodynamics of Liquids, by Carl Barus.
97. The Mesozoic Echinodermata of the United States, by W. B. Clark.
98. Carboniferous Flora—Outlying Coal Basins of Southwestern Missouri, by David White.
99. Record of North American Geology for 1891, by Nelson Horatio Darton.

In preparation:

87. Correlation papers—Pleistocene, by T. C. Chamberlin.
100. Bibliography and Index of the publications of the U. S. Geological Survey, 1879-1892, by P. C. Warman.
101. Insect fauna of the Rhode Island Coal Field, by Samuel Hubbard Scudder.
- The Eruptive and Sedimentary Rocks on Pigeon Point, Minnesota, and their contact phenomena, by W. S. Bayley.
- The Moraines of the Missonri Coteau, and their attendant deposits, by James Edward Todd.
- A Bibliography of Paleobotany, by David White.

STATISTICAL PAPERS.

- Mineral Resources of the United States, 1882, by Albert Williams, jr. 1883. 8°. xvii, 813 pp. Price 60 cents.
- Mineral Resources of the United States, 1883 and 1884, by Albert Williams, jr. 1885. 8°. xiv, 1016 pp. Price 60 cents.
- Mineral Resources of the United States, 1885. Division of Mining Statistics and Technology. 1886. 8°. vii, 576 pp. Price 40 cents.
- Mineral Resources of the United States, 1886, by David T. Day. 1887. 8°. viii, 813 pp. Price 50 cents.
- Mineral Resources of the United States, 1887, by David T. Day. 1888. 8°. vii, 832 pp. Price 50 cents.
- Mineral Resources of the United States, 1888, by David T. Day. 1890. 8°. vii, 652 pp. Price 50 cents.
- Mineral Resources of the United States, 1889 and 1890, by David T. Day, 1892. viii, 671 pp. Price 50 cents.

The money received from the sale of these publications is deposited in the Treasury, and the Secretary of the Treasury declines to receive bank checks, drafts, or postage stamps; all remittances, therefore, must be by POSTAL NOTE or MONEY ORDER, made payable to the Librarian of the U. S. Geological Survey, or in CURRENCY, for the exact amount. Correspondence relating to the publications of the Survey should be addressed

TO THE DIRECTOR OF THE
UNITED STATES GEOLOGICAL SURVEY,
WASHINGTON, D. C.

WASHINGTON, D. C., May, 1892.

NOTICE.

This volume, "Mineral Resources of the United States, 1889 and 1890," is the seventh of a series which began in 1882. Its price is 50 cents. In ordering the different volumes of this series care should be taken to designate them as:

1. Mineral Resources of the United States, 1882. Price 50 cents.
2. Mineral Resources of the United States, 1883-'84. Price 60 cents.
3. Mineral Resources of the United States, 1885. Price 40 cents.
4. Mineral Resources of the United States, 1886. Price 50 cents.
5. Mineral Resources of the United States, 1887. Price 50 cents.
6. Mineral Resources of the United States, 1888. Price 50 cents.
7. Mineral Resources of the United States, 1889 and 1890. Price 50 cents.

Remittances should be made by postal note (not stamps) and should be addressed to the Director United States Geological Survey, Washington, D. C.

Corrections, additions, or notice of important omissions, reports and maps of mines and mining districts, pamphlets on metallurgical processes, brief notes on new mineral localities, etc., will be highly appreciated, and should be addressed to David T. Day, U. S. Geological Survey, Washington, D. C. Duplicate copies of such reports, etc., are especially desired for extending the fine set of mining pamphlets in the library of the Survey, and will be thankfully acknowledged if sent to the

DIRECTOR UNITED STATES GEOLOGICAL SURVEY,
Washington, D. C.

5-57
DEPARTMENT OF THE INTERIOR
UNITED STATES GEOLOGICAL SURVEY

J. W. POWELL, DIRECTOR

WITHDRAWN
M. I. T.
LIBRARIES

MASS. INSTITUTE
OF
TECHNOLOGY
APR 18 1893
LIBRARY.

MINERAL RESOURCES

OF THE

UNITED STATES

CALENDAR YEARS

1889 AND 1890

DAVID T. DAY

CHIEF OF DIVISION OF MINING STATISTICS AND TECHNOLOGY



WASHINGTON
GOVERNMENT PRINTING OFFICE

1892 ✓

7862
- 61
1889 - 90

CONTENTS.

	Page.
Letter of transmittal.....	v
Introduction.....	vii
Summary.....	1
Iron:	
The iron and steel industries of the United States.....	10
Iron ores.....	22
Gold and silver.....	47
Copper.....	55
Lead.....	77
Zinc.....	87
Quicksilver.....	93
Aluminum.....	109
Tin.....	119
Nickel and cobalt.....	124
Manganese.....	127
Chromic iron ore.....	137
Antimony.....	141
Platinum.....	143
Coal.....	145
Petroleum.....	287
Natural gas.....	366
Stone:	
Limestone.....	373
Granite.....	374
Sandstone.....	374
Marble.....	375
Slate.....	376
Bluestone.....	376
Pottery.....	441
Precious stones.....	445
Fertilizers.....	449
Bulrstones.....	456
Corundum and emery.....	457
Grindstones.....	458
Infusorial earth.....	459
Oilstones, whetstones, etc.....	460
Cement.....	461
Gypsum.....	465
Fluorspar.....	468
Mica.....	474
Soapstone.....	476
Asphaltum.....	477
Salt.....	482

	Page.
Bromine.....	493
Borax.....	494
Graphite.....	507
Mineral paints.....	508
Barytes.....	513
Asbestos.....	514
Sulphur.....	515
Pyrites.....	518
Lithographic stone.....	519
Mineral waters.....	521
General index to series.....	537
Index to present volume.....	653

LETTER OF TRANSMITTAL.

UNITED STATES GEOLOGICAL SURVEY,
DIVISION OF MINING STATISTICS AND TECHNOLOGY,
Washington, January 23, 1892.

SIR: I have the honor to transmit herewith the seventh report of the series "Mineral Resources of the United States," this volume being entitled "Mineral Resources of the United States, 1889 and 1890." The first report of the series gave account of the mineral products of 1882 and part of 1883, and the subsequent volumes bring the statistics to December 31, 1888. The present volume carries the statistical data to December 31, 1890. A report covering the year 1891, which you have authorized, is in active preparation.

I beg to tender you my hearty appreciation for the consideration you have shown to my very considerable demands on your time and attention and for your untiring interest in this work.

Very respectfully, your obedient servant,

DAVID T. DAY,
Geologist in Charge.

Hon. J. W. POWELL,
Director, U. S. Geological Survey.

INTRODUCTION.

The present volume of the series "Mineral Resources of the United States" presents a review of the mineral industries during the calendar years 1889 and 1890. It is in continuation of the previous volume which covered the year 1888. During part of the years 1889, 1890, and 1891 the several contributors to this series were nearly all of them engaged in preparing the volume on the mineral industries for the Eleventh Census. The statistics here presented for 1889 are therefore those of the Census Office, with a few minor exceptions. These exceptions are the cases in which the mineral report for the Census Office did not consider certain industries which are usually included in the reports of this series. The statistical tables of former years have been carried forward, but the previous volumes should be consulted for all other information concerning the mineral industries prior to 1889.

The scope of the present volume has been lessened slightly in the effort to make the arduous work of complete statistics from all producers more accurate in the subjects of coal, iron ores, and other important subjects.

Units.—The different units adopted are those in common use for each mineral. Pounds are avoirdupois and tons are short tons of 2,000 pounds, unless long tons of 2,240 pounds are specified.

Imports and exports.—These are obtained from the records of the Bureau of Statistics of the Treasury Department. Recent years coincide with calendar years from January 1 to December 31, but earlier statistics of imports are for the Government fiscal year ending June 30.

Delay in publication.—It has already been shown in previous volumes that it is impossible to gather complete reports on so many subjects and publish the resultant volume without much delay, since one report can delay all the rest, and this is especially the case in proportion as the inquiries are extended to individual producers. Efforts have been made, however, to avail of the daily and technical press in giving information regarding each subject as promptly as possible.

Totals.—In preparing the statement of the total value of the mineral product, the usual commercial value has been taken. Following the rule adopted in the Census investigation, the value of a mineral is taken at that stage in its production where it first becomes a salable

article with a market value recognized in its trade. Thus, coal is valued on cars at the mine, while lead is given its value in New York City. Any valuations which might be adopted would involve inconsistencies, but this plan is best in accordance with ordinary usage.

The product indicated for 1890 is \$656,604,698, an increase far beyond any previous year. The year was a period of unexampled activity in mining, particularly so in iron, silver, copper, coal, and petroleum. This total is extraordinary, but the activity continued in 1891 until checked by the feeling of insecurity following the English depression. The year 1891 will show no marked contrast to 1890.

MINERAL RESOURCES OF THE UNITED STATES.

SUMMARY.

METALS.

Iron and steel.—The production of pig iron in the United States in the year 1889 was 7,603,642 long tons, or 8,516,079 short tons, valued at \$120,000,000, taking as the standard of valuation the price of No. 1 anthracite pig iron in Philadelphia. This was greater than the product of any previous year; but in 1890 the product increased greatly, reaching 10,307,028 short tons, valued at \$151,200,410, and in 1891, 9,273,455 short tons. The production of Bessemer steel in the United States in 1890 was 4,131,535 short tons, against 3,281,829 short tons in 1889, a gain of nearly 26 per cent. The consumption of limestone for flux in iron ore smelting was 5,521,622 long tons in 1890.

Gold and silver.—In 1889 the mines of the United States produced, according to the census returns, 1,590,869 fine ounces of gold, with a coinage value of \$32,886,744, and 51,354,851 ounces of silver, with a coinage value of \$66,396,988. In 1890 the product, according to the Director of the Mint, was: Gold, 1,588,880 ounces, valued at \$32,845,000, and silver, 54,500,000 ounces, with a coining value of \$70,464,645.

Copper.—The copper product remained nearly stationary in 1889, being 231,246,214 pounds, and in 1890 increasing to 265,115,133 pounds. It was worth, respectively, \$26,907,809 and \$30,848,797.

Lead.—The total product increased in 1889 to 182,967 short tons, worth \$16,137,689, compared with 180,555 short tons in 1888, worth \$15,924,951. In 1890 the product decreased to 161,754 short tons, worth \$14,266,703. The producers carried a stock of 10,389 short tons on January 1, 1891, as compared with 7,715 short tons on January 1, 1890. The lead content of the ores imported from Mexico was 26,570 tons in 1889, and 18,124 tons in 1890. The production of lead in the first half of 1891 increased to 95,121 short tons.

Zinc.—In 1888 the total product of spelter was 55,903 short tons, worth \$5,500,855. In 1889 it increased to 58,860 short tons, worth \$5,791,824, and in 1890 to 63,683 short tons, worth \$6,266,407. The stocks in

the hands of producers are small, considering the magnitude of the industry. On January 1, 1890, these stocks were 2,535 short tons, and on January 1, 1891, had decreased to 1,134 tons.

Quicksilver.—The industry continues to decline in spite of active prospecting for new supplies. In 1888 the product was 33,250 flasks of 76½ pounds net, valued in San Francisco at \$1,413,125. In 1889 this declined to 26,484 flasks, although the price was \$45 per flask, which was sufficient to cause strong inquiry for new supplies. In 1890 the product decreased to 22,926 flasks, the average price increasing to \$48.33 per flask. The product all came from California.

Nickel.—During the years 1889 and 1890 the condition of the industry changed completely, due to the development of extensive supplies in Canada. The inquiry for still other new deposits was nevertheless stimulated by the successful tests of steel containing a small percentage of nickel for armor plates. Previously the markets were regulated principally by the output of the New Caledonia mines. In 1888 the total product in the United States was 204,328 pounds. In 1889 this increased to 252,663 pounds and in 1890 to 223,488 pounds, worth \$134,093. The product from Canadian matte was 35,000 pounds in 1889 and 100,000 pounds in 1890.

Cobalt oxide.—The product has followed the nickel industry, except that proportionately more nickel has been produced than cobalt oxide, because the Canadian matte contains scarcely any cobalt. The New Caledonian producers have produced a greater proportion of cobalt by the aid of a mangiferous iron ore containing nickel and cobalt. The product in 1889 was 13,955 pounds and in 1890 6,788 pounds. The price remained at about \$2.50 per pound in 1889 and \$2.40 in 1890.

Chromic iron ore.—The industry remains unchanged. The supplies come from California, together with increasing importations from Turkey and Asia Minor. The output in California in 1889 was 2,000 long tons, and in 1890 3,599 long tons, worth \$53,985.

Manganese.—Product in 1889, 24,197 long tons, which includes a small shipment from Colorado. In 1890 the product was 25,684 long tons, worth \$219,050. The importations are increasing. In addition, mangiferous iron ores were produced to the amount of 83,434 tons in 1889 and 61,860 tons in 1890.

Aluminum.—The production of aluminum, including that in alloys, continued and increased from about 19,000 pounds in 1888 to 47,468 pounds in 1889, and 61,281 pounds in 1890. The price decreased from \$4.50 per pound in 1888 to \$1 per pound in 1890 for ingots. The manufacture of aluminum into musical instruments, thin sheets for ornamental purposes, and into various utensils is increasing.

Antimony.—In 1889, 115 short tons were produced, valued at \$28,000; in 1890 this increased to 129 short tons, valued at \$40,756. This included a slight product from a new source, Ketchum, Idaho.

FUELS.

Coal.—In 1889 the total product of coal of all kinds was 141,229,513 short tons, valued at the mines, before any expenses for shipment, at \$160,226,323. The product included 45,600,487 short tons of Pennsylvania and other anthracite, worth \$65,879,514, and 95,629,026 short tons of bituminous coal and lignite, valued at \$94,346,809.

In 1890 the total product increased to 157,788,657 short tons, a gain of over $4\frac{1}{2}$ per cent. over 1889. The total value at the mines was \$176,804,573. Of the above, 46,468,641 short tons were anthracite, worth \$66,383,772, and 111,320,016 short tons were bituminous coal and lignite, worth \$110,420,801.

Petroleum.—The product in 1889 was 35,163,513 barrels, valued at \$26,963,340. In 1890, the product was 45,822,672 barrels, worth \$35,365,105. The feature of the two years has been the successful refining of Lima (Ohio) oil, which now supplies a large share of the domestic trade, and the great increase in the Pennsylvania product in 1890, making this the year of greatest product.

Natural gas.—The product, measured in terms of the coal displaced, shows a decline from \$22,629,875 in 1888 to \$21,097,099 in 1889. The product declined again in 1890 to \$18,742,725.

STRUCTURAL MATERIALS.

Building stone.—The product in 1889 includes granite to the value of \$14,464,095, at the place where produced and in the condition in which it was first sold; marble, \$3,488,170; sandstone, \$10,816,057; blue-stone, \$1,689,606; limestone, \$19,095,179; and slate, \$3,482,513. In 1890 the total value of these products aggregates \$54,000,000. Even allowing for a considerable growth in the industry since 1888, these figures show that the statement then made was too small.

ABRASIVE MATERIALS.

Millstones.—The product continued to decrease. In 1889 the product was valued at \$35,155, and in 1890, at \$23,720.

Grindstones.—The supply still comes from Ohio and Michigan. The consumption has increased in grinding wood pulp. The product in 1889 was valued at \$439,587, and in 1890, at \$450,000.

Oilstones and whetstones.—This industry derives its supplies from well established quarries in Arkansas, Indiana, and New Hampshire. In 1889 the product amounted to 2,354,000 pounds, chiefly novaculite, and valued at \$32,980. In 1890 the value of the product was \$69,909 in the rough state.

MISCELLANEOUS.

Precious stones.—The product is small and with the exception of agatized wood, the tourmalines regularly produced in Maine, and a few gems from North Carolina, consists principally of tourists' jewelry. It was valued at \$188,807 in 1889 and \$118,833 in 1890.

Phosphate rock.—In 1889 the production of phosphate rock was established as a new industry in Florida and its importance is increasing. The total product from all sources amounted to 550,245 long tons in 1889, which was the greatest amount ever reported. In 1890 the product was 510,499 long tons, worth \$3,213,795.

Marls.—The product in 1889 was 139,522 short tons, worth \$63,956, and in 1890, 153,620 short tons, worth \$69,880. There is little change in the industry.

Salt.—Product in 1889, 8,005,565 barrels, worth \$4,195,412, and in 1890, 8,776,991 barrels, worth \$4,752,286.

Bromine.—The product in 1889 was 418,891 pounds, valued at \$125,667. In 1890 this decreased to 387,847 pounds on account of the accumulation of stock.

Borax.—In 1889 the product was 8,000,000 pounds worth \$500,000, increasing in 1890 to 9,500,000 pounds.

Sulphur.—In 1889 and 1890 the Utah works were closed by litigation. There was a small product from the Nevada mines in 1889, amounting to 1,150 short tons. Efforts are being made to open the Louisiana mines.

Pyrites.—The product from Virginia, Massachusetts, and Vermont amounted to 93,705 long tons, worth \$202,119 in 1889, and in 1890 to 111,836 long tons, worth \$273,745.

Barytes.—The use of this material is increasing. The main sources of supply are mines in Missouri, Virginia, and New York. The total product in 1889 was 19,161 long tons and in 1890, 21,911 long tons.

Gypsum.—In 1889 the product was 267,769 short tons of crude gypsum, worth \$764,118, and in 1890, 182,995 short tons, worth \$574,523.

Ozocerite.—Development work was continued in the regions near Soldier's Summit, Utah; 50,000 pounds were produced in 1889, and 350,000 pounds in 1890.

Asphaltum.—During the last two years the product on the Pacific coast has increased markedly and the price has declined. Product in 1889, 51,735 short tons, worth \$171,537, and in 1890, 40,841 short tons, worth \$190,416. The production of gilsonite in Utah continues and amounted to 492 short tons in 1889 and 1,105 tons in 1890.

Soapstone.—The use of this material in the form of slabs for various purposes increased. The total product of all kinds was 36,461 short tons in 1889 and 54,024 short tons in 1890. Of this 23,746 short tons and 41,354 short tons, respectively, consisted of fibrous talc from New York.

Mica.—The production decreased in 1889, but is now increasing again; product in 1889, 49,500 pounds, worth \$50,000, and in 1890, 60,000 pounds, worth \$75,000.

Mineral paints.—The product includes ocher, metallic paints, and some umber and sienna; it amounted to 32,307 long tons in 1889, and 45,732 long tons in 1890.

Graphite.—The principal product in 1889 was 400,000 pounds of refined graphite from Ticonderoga, New York, worth \$33,000. In 1890 this product was about stationary. Besides this, cheaper grades were obtained from several localities for use in making foundry facings, etc.

Fluorspar.—The supply from Rosiclare, Illinois, and Evansville, Indiana, is sufficient for the gradually increasing use as a flux in cupola furnaces and for chemical purposes. The product was 9,500 short tons in 1889, and 8,250 short tons in 1890. Some artificial fluorspar is made as a by-product in the decomposition of Greenland cryolite.

Infusorial earth.—From the usual sources the product was 3,466 short tons in 1889, and 2,532 short tons in 1890.

Mineral waters.—Total product in 1889, 12,780,471 gallons, worth \$1,748,458, and in 1890, 13,907,418 gallons, with a value of \$2,600,750.

Mineral products of the United States for

	Products.	1880.		1881.		
		Quantity.	Value.	Quantity.	Value.	
METALLIC.						
1	Pig iron, spot value	long tons	3, 375, 912	\$89, 315, 569	4, 144, 254	\$87, 029, 334
2	Silver, coining value,	troy ounces	30, 320, 000	39, 200, 000	33, 077, 000	43, 000, 000
3	Gold, coining value	do.	1, 741, 500	36, 000, 000	1, 676, 300	34, 700, 000
4	Copper, value at New York City ..	pounds	60, 480, 000	11, 491, 200	71, 680, 000	12, 175, 600
5	Lead, value at New York City	short tons	97, 825	9, 782, 500	117, 085	11, 240, 160
6	Zinc, value at New York City	do.	23, 239	2, 277, 432	26, 800	2, 680, 000
7	Quicksilver, value at San Francisco ..	flasks	59, 926	1, 797, 780	60, 851	1, 764, 679
8	Nickel, value at Philadelphia	pounds	329, 968	164, 984	265, 668	292, 235
9	Aluminum, value at Pittsburg	do.				
10	Antimony, value at San Francisco ..	short tons	50	10, 000	50	10, 000
11	Platinum, value (crude) at San Francisco ..	troy ounces	100	400	100	400
NONMETALLIC (SPOT VALUES).						
12	Bituminous coal	long tons	38, 242, 641	53, 443, 718	48, 179, 475	60, 224, 344
13	Pennsylvania anthracite	do.	25, 580, 189	42, 196, 678	28, 500, 016	64, 125, 036
14	Building stone	do.		18, 356, 055		20, 000, 000
15	Petroleum	barrels	26, 286, 123	24, 183, 233	27, 661, 238	25, 448, 339
16	Lime	do.	28, 000, 000	19, 000, 000	30, 000, 000	20, 000, 000
17	Natural gas	do.				
18	Cement	barrels	2, 072, 943	1, 852, 707	2, 500, 000	2, 000, 000
19	Salt	do.	5, 961, 000	4, 829, 566	6, 200, 000	4, 200, 000
20	Limestone for iron flux	long tons	4, 500, 000	3, 800, 000	6, 000, 000	4, 100, 000
21	Phosphate rock	do.	211, 377	1, 123, 823	266, 734	1, 980, 259
22	Mineral waters	gallons sold	2, 000, 000	500, 000	3, 000, 000	700, 000
23	Zinc white	short tons	10, 107	763, 738	10, 000	700, 000
24	Gypsum	do.	90, 000	400, 000	85, 000	350, 000
25	Borax	pounds	3, 692, 443	277, 233	4, 046, 000	304, 461
26	Mineral paints	long tons	3, 604	135, 840	6, 000	100, 000
27	Manganese ore	do.	5, 761	86, 415	4, 895	73, 425
28	Asphaltum	short tons	444	4, 440	2, 000	8, 000
29	Pyrites	long tons	2, 000	5, 000	10, 000	60, 000
30	Crude barytes	do.	20, 000	80, 000	20, 000	80, 000
31	Bromine	pounds	404, 690	114, 752	300, 000	75, 000
32	Corundum	short tons	1, 044	29, 280	500	80, 000
33	Marls	long tons	1, 000, 000	500, 000	1, 000, 000	500, 000
34	Precious stones	do.		50, 000		60, 000
35	Gold quartz, souvenirs, jewelry, etc.	do.		50, 000		50, 000
36	Flint	long tons	20, 000	80, 000	25, 000	100, 000
37	Fluorspar	short tons	4, 000	16, 000	4, 000	16, 000
38	Graphite	pounds		49, 800	400, 000	30, 000
39	Novaculite	do.	420, 000	8, 000	500, 000	8, 580
40	Feldspar	long tons	12, 500	60, 000	14, 000	70, 000
41	Chrome iron ore	do.	2, 288	27, 808	2, 000	30, 000
42	Mica	pounds	81, 669	127, 825	100, 000	250, 000
43	Slate ground as a pigment	long tons	1, 000	10, 000	1, 000	10, 000
44	Cobalt oxide	pounds	7, 251	24, 000	8, 280	25, 000
45	Sulphur	short tons	600	21, 000	600	21, 000
46	Rutile	pounds	100	400	200	700
47	Asbestos	do.	150	4, 312	200	7, 000
48	Potters' clay	long tons	25, 783	200, 457	25, 000	200, 000
49	Grindstones	do.		500, 000		500, 000
50	Millstones	do.		200, 000		150, 000
51	Ozocerite, refined	pounds				
52	Infusorial earth	short tons	1, 833	45, 660	1, 000	10, 000
53	Soapstone	do.	8, 441	66, 665	7, 000	75, 000
54	Fibrous talc	do.	4, 210	54, 730	5, 000	60, 000
55	Lithographic stone	do.			50	1, 000
Total value of metallic products				190, 039, 865		192, 892, 408
Total value of nonmetallic mineral products ..				173, 279, 135		206, 783, 144
Estimated value of mineral products un-				6, 000, 000		6, 500, 000
specified.						
Grand total				369, 319, 000		406, 175, 552

SUMMARY.

the calendar years 1880 to 1890, inclusive.

1882.		1883.		1884.		
Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
4 623, 323	\$106, 336, 420	4, 595, 510	\$91, 910, 200	4, 097, 868	\$73, 761, 624	1
36, 197, 695	46, 800, 000	35, 733, 622	46, 200, 000	37, 744, 605	48, 800, 000	2
1, 572, 186	32, 500, 000	1, 451, 249	30, 000, 000	1, 489, 949	30, 800, 000	3
91, 646, 232	16, 068, 091	117, 151, 795	18, 064, 807	145, 221, 934	17, 789, 687	4
132, 890	12, 624, 550	143, 957	12, 322, 719	139, 897	10, 537, 042	5
33, 765	3, 646, 620	36, 872	3, 311, 106	38, 544	3, 422, 707	6
52, 732	1, 487, 042	46, 725	1, 253, 632	31, 913	936, 327	7
281, 616	309, 777	58, 800	52, 920	64, 550	48, 412	8
		83	875	150	1, 350	9
60	12, 000	60	12, 000	60	12, 000	10
200	600	200	600	150	450	11
60, 861, 190	76, 076, 487	68, 531, 500	82, 297, 800	73, 730, 539	77, 417, 066	12
31, 358, 264	70, 556, 094	34, 336, 469	77, 257, 055	33, 175, 756	66, 351, 512	13
	21, 000, 000		20, 000, 000		19, 000, 000	14
30, 510, 830	24, 065, 988	23, 449, 633	25, 790, 252	24, 218, 438	20, 595, 966	15
31, 000, 000	21, 700, 000	32, 000, 000	19, 200, 000	37, 000, 000	18, 500, 000	16
	215, 000		475, 000		1, 460, 000	17
3, 250, 000	3, 672, 750	4, 190, 000	4, 293, 500	4, 000, 000	3, 720, 000	18
6, 412, 373	4, 320, 140	6, 192, 231	4, 211, 042	6, 514, 937	4, 197, 734	19
3, 850, 000	2, 310, 000	3, 814, 273	1, 907, 136	3, 401, 930	1, 700, 965	20
332, 077	1, 992, 462	378, 380	2, 270, 280	431, 779	2, 374, 784	21
5, 000, 000	800, 000	7, 529, 423	1, 119, 603	10, 215, 323	1, 459, 143	22
10, 000	700, 000	12, 000	840, 000	13, 000	910, 000	23
100, 000	450, 000	90, 000	420, 000	90, 000	390, 000	24
4, 236, 291	338, 903	6, 500, 000	585, 000	7, 000, 000	490, 000	25
7, 000	105, 000	7, 000	84, 000	7, 000	84, 000	26
4, 532	67, 980	6, 155	92, 325	10, 180	122, 160	27
3, 000	10, 500	3, 000	10, 500	3, 000	10, 500	28
12, 000	72, 000	25, 000	137, 500	35, 000	175, 000	29
20, 000	80, 000	27, 000	108, 000	25, 000	100, 000	30
250, 000	75, 000	301, 100	72, 264	281, 100	67, 464	31
500	80, 000	550	100, 000	600	108, 000	32
1, 080, 000	540, 000	972, 080	486, 000	875, 000	437, 500	33
	75, 000		74, 050		82, 975	34
	75, 000		133, 000		140, 000	35
25, 000	100, 000	25, 000	100, 000	30, 000	120, 000	36
4, 000	20, 000	4, 008	20, 000	4, 000	20, 000	37
425, 000	34, 000	575, 000	46, 000			38
600, 000	10, 000	600, 000	10, 000	800, 000	12, 000	39
14, 000	70, 000	14, 100	71, 112	10, 900	55, 112	40
2, 500	50, 000	3, 000	60, 000	2, 000	35, 000	41
100, 000	250, 000	114, 000	285, 000	147, 410	268, 525	42
2, 000	24, 000	2, 000	24, 000	2, 000	20, 000	43
11, 653	32, 046	1, 096	2, 795	2, 000	5, 100	44
600	21, 000	1, 000	27, 000	500	12, 000	45
500	1, 800	550	2, 000	600	2, 000	46
1, 200	36, 000	1, 000	30, 000	1, 000	30, 000	47
30, 000	240, 000	32, 000	250, 000	35, 000	270, 000	48
	700, 000		600, 000		570, 000	49
	200, 000		150, 000		150, 000	50
						51
1, 000	8, 000	1, 000	5, 000	1, 000	5, 000	52
6, 000	90, 000	8, 000	150, 000	10, 000	200, 000	53
6, 000	75, 000	6, 000	75, 000	10, 000	110, 000	54
						55
	219, 755, 109		203, 128, 850		186, 109, 599	
	231, 340, 150		243, 812, 214		221, 879, 506	
	6, 500, 000		6, 500, 000		5, 900, 000	
	457, 595, 259		453, 441, 073		412, 989, 105	

Mineral products of the United States for the

	Products.	1885.		1886.	
		Quantity.	Value.	Quantity.	Value.
METALLIC.					
1	Pig iron, spot value.....long tons..	4,044,525	\$64,712,400	5,683,329	\$95,195,760
2	Silver, coining value.....troy ounces..	39,910,279	51,600,000	39,445,312	51,000,000
3	Gold, coining value.....do.....	1,538,376	31,800,000	1,881,250	35,000,000
4	Copper, value at New York City.....pounds..	170,962,607	18,292,999	161,235,381	16,527,651
5	Lead, value at New York City.....short tons..	129,412	10,469,431	135,629	12,667,749
6	Zinc, value at New York City.....do.....	40,688	3,539,856	42,641	3,752,408
7	Quicksilver, value at San Francisco.....flasks..	32,073	979,189	29,981	1,060,000
8	Nickel, value at Philadelphia.....pounds..	277,904	179,975	214,992	127,157
9	Aluminum, value at Philadelphia.....do.....	283	2,550	3,000	27,000
10	Antimony, value at San Francisco.....short ton..	50	10,000	35	7,000
11	Platinum, value (crude) at San Francisco, troy ounces.	250	187	50	100
NONMETALLIC (SPOT VALUES).					
12	Bituminous coal.....long tons..	64,840,668	82,347,648	65,810,676	78,481,056
13	Pennsylvania anthracite.....do.....	34,228,548	76,671,948	34,853,077	76,119,120
14	Building stone.....do.....	19,000,000	19,000,000
15	Petroleum.....barrels.....	21,847,205	19,198,243	28,064,841	19,996,313
16	Lime.....do.....	40,000,000	20,000,000	42,500,000	21,250,000
17	Natural gas.....do.....	4,857,200	10,012,000
18	Cement.....barrels.....	4,150,000	3,492,500	4,500,000	3,990,000
19	Salt.....do.....	7,038,653	4,825,345	7,707,081	4,736,585
20	Limestone for iron flux.....long tons..	3,356,956	1,678,478	4,717,163	2,830,297
21	Phosphate rock.....do.....	437,856	2,846,064	430,549	1,872,936
22	Mineral waters, gallons sold.....	9,148,401	1,312,845	8,950,317	1,284,070
23	Zinc white.....short tons..	15,000	1,050,000	18,000	1,440,000
24	Gypsum.....do.....	90,465	405,000	95,250	428,625
25	Borax.....pounds.....	8,000,000	480,000	9,778,290	488,915
26	Mineral paints.....long tons..	3,950	43,575	15,800	285,000
27	Manganese ore.....long tons..	23,258	190,281	30,193	277,636
28	Asphaltum.....short tons..	3,000	10,500	3,500	14,000
29	Pyrites.....long tons..	49,000	220,500	55,000	220,000
30	Crude barytes.....do.....	15,000	75,000	10,000	50,000
31	Bromine.....pounds.....	310,000	89,900	428,334	141,350
32	Corundum.....short tons..	600	108,000	645	116,190
33	Marls.....do.....	875,000	437,500	800,000	400,000
34	Precious stones.....do.....	69,900	79,056
35	Gold quartz, souvenirs, jewelry, etc.....	140,000	40,000
36	Flint.....long tons..	30,000	120,000	30,000	120,000
37	Fluorspar.....short tons..	5,000	22,500	5,000	22,000
38	Graphite.....pounds.....	327,883	26,231	415,525	33,242
39	Novaculite.....do.....	1,000,000	15,000	1,160,000	15,000
40	Feldspar.....long tons..	13,600	68,000	14,900	74,500
41	Chrome iron ore.....do.....	2,700	40,000	2,000	30,000
42	Mica.....pounds.....	92,000	161,000	40,000	70,000
43	Slate ground as a pigment.....long tons..	1,975	24,687	3,000	30,000
44	Cobalt oxide.....pounds.....	68,723	65,373	35,000	36,878
45	Sulphur.....short tons..	715	17,875	2,500	75,000
46	Rutile.....pounds.....	600	2,000	600	2,000
47	Asbestos.....short tons..	300	9,000	200	6,000
48	Potters' clay.....long tons..	36,000	275,000	40,000	325,000
49	Grindstones.....do.....	500,000	250,000
50	Millstones.....do.....	100,000	140,000
51	Ozocerite, refined.....pounds.....
52	Infusorial earth.....short tons..	1,000	5,000	1,200	6,000
53	Soapstone.....do.....	10,000	200,000	12,000	225,000
54	Fibrous talc.....do.....	10,000	110,000	12,000	125,000
55	Lithographic stone.....do.....	40	700
Total value of metallic products.....		181,586,587	215,364,825
Total value of nonmetallic mineral products.....		241,312,093	245,139,469
Estimated value of mineral products unspecified.....		5,000,000	5,000,000
Grand total.....		427,898,680	465,504,294

SUMMARY.

calendar years 1880 to 1890, inclusive—Continued.

1887.		1888		1889.		1890.		
Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
6,417,148	\$121,925,800	6,489,738	\$107,000,000	7,603,642	\$120,000,000	9,202,703	\$151,200,410	1
41,269,240	53,350,000	45,783,632	59,195,000	51,354,851	66,396,988	54,500,000	70,464,645	2
1,596,500	33,000,000	1,604,927	33,175,000	1,590,869	32,886,744	1,588,880	32,845,000	3
185,227,331	21,115,916	231,270,622	33,833,954	231,246,214	26,907,809	265,115,133	30,848,797	4
160,700	14,463,000	180,555	15,924,951	182,967	16,137,689	161,754	14,266,703	5
50,340	4,782,300	55,903	5,500,855	58,860	5,791,824	63,683	6,266,407	6
33,825	1,429,000	33,250	1,413,125	26,484	1,190,500	22,926	1,203,615	7
205,566	133,200	204,328	127,632	252,663	151,598	223,488	134,093	8
18,000	59,000	19,000	65,000	47,468	97,335	61,281	61,281	9
75	15,000	100	20,000	115	28,000	129	40,756	10
448	1,838	500	2,000	500	2,000	600	2,500	11
78,470,857	98,004,656	91,106,998	101,860,529	85,383,059	94,346,809	99,392,871	110,420,801	12
37,578,747	84,552,181	41,624,611	89,020,483	40,714,721	65,879,514	41,489,858	66,383,772	13
	25,000,000		25,500,000		42,809,706		47,000,000	14
28,278,866	18,877,094	27,612,025	17,947,620	35,163,513	26,963,340	45,822,672	35,365,105	15
46,750,000	23,375,000	49,087,000	24,543,500	68,474,668	33,217,015	60,000,000	35,000,000	16
	15,817,500		22,629,875		21,097,089		18,742,725	17
6,692,744	5,674,377	6,503,295	5,021,139	7,000,000	5,000,000	8,000,000	6,000,000	18
7,831,962	4,093,846	8,055,881	4,374,203	8,005,565	4,195,412	8,776,991	4,752,286	19
5,377,000	3,226,200	5,438,000	2,719,000	6,318,000	3,159,000	5,521,622	2,760,811	20
480,558	1,836,818	448,567	2,018,552	550,245	2,937,776	510,499	3,213,795	21
8,259,609	1,261,473	9,578,648	1,679,302	12,780,471	1,748,458	13,907,418	2,600,750	22
18,000	1,440,000	20,000	1,600,000	16,970	1,357,600		1,600,000	23
95,000	425,000	110,000	550,000	267,769	764,118	182,995	574,523	24
11,000,000	550,000	7,589,000	455,340	8,000,000	500,000	9,500,000	617,500	25
20,000	310,000	24,000	380,000	32,307	463,766	45,732	661,992	26
34,524	333,844	29,198	279,571	24,197	240,559	25,684	219,050	27
4,000	16,000	53,800	331,500	51,735	171,537	40,841	190,416	28
52,000	210,000	54,331	167,658	93,705	202,119	111,836	273,745	29
15,000	75,000	20,000	110,000	19,161	106,313	21,911	86,505	30
199,087	61,717	307,386	95,290	418,891	125,667	387,847	104,719	31
600	108,000	589	91,620	2,245	105,565	1,970	89,395	32
600,000	300,000	300,000	150,000	139,522	63,956	153,620	69,880	33
	88,600		64,850					34
	75,000		75,000		188,807		118,833	35
32,000	185,000	30,000	175,000	11,113	49,137	13,000	57,400	36
5,000	20,000	6,000	30,000	9,500	45,835	8,250	55,328	37
416,000	34,000	400,000	33,000		72,662		77,500	38
1,200,000	16,000	1,500,000	18,000	5,982,300	32,980		69,909	39
10,200	56,100	8,700	50,000	6,970	39,370	8,000	45,200	40
3,000	40,000	1,500	20,000	2,000	30,000	3,599	53,985	41
70,500	142,250	48,000	70,000	49,500	50,000	60,000	75,000	42
2,000	20,000	2,500	25,000	2,000	20,000	2,000	20,000	43
18,340	18,774	8,491	15,782	13,955	31,092	6,788	16,291	44
3,000	100,000		1,150		7,850			45
1,000	3,000	1,000	3,000	1,000	3,000	400	1,000	46
150	4,500	100	3,000	30	1,800	71	4,560	47
43,000	340,000	36,750	300,000	294,344	635,578	350,000	756,000	48
	224,400		281,800		439,587		450,000	49
	100,000		81,000		35,155		23,720	50
		43,500	3,000	50,000	2,500	350,000	26,250	51
3,000	15,000	1,500	7,500	3,466	23,372	2,532	50,240	52
12,000	225,000	15,000	250,000	12,715	231,708	13,670	252,309	53
15,000	160,000	20,000	210,000	23,746	244,170	41,354	389,196	54
			210,000	18	243			55
	250,275,054		256,257,517		269,590,487		307,334,207	
	287,416,320		303,241,114		307,640,175		339,270,491	
	5,000,000		5,000,000		10,000,000		10,000,000	
	542,691,374		564,498,631		587,230,662		656,604,698	

IRON AND STEEL.

THE IRON AND STEEL INDUSTRIES OF THE UNITED STATES IN 1889, 1890, AND 1891.

COMPARED WITH THE IRON AND STEEL INDUSTRIES OF OTHER COUNTRIES.

BY JAMES M. SWANK,

General Manager of the American Iron and Steel Association.

Production of pig iron, by States, in 1889 and 1890.—The total production of pig iron in the United States in 1889 was 7,603,642 long tons, and in 1890 it was 9,202,703 long tons. In the following table is given, in short tons, the exact production of pig iron in each of the pig-iron producing States in 1889 and 1890, the States being given in the order of their prominence in 1890.

Production of pig iron, by States, in 1889 and 1890.

States.	1889.	1890.	States.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>		<i>Short tons.</i>	<i>Short tons.</i>
Pennsylvania.....	4,181,242	4,945,169	Kentucky.....	42,518	53,604
Ohio.....	1,215,572	1,389,170	Georgia.....	27,559	32,687
Alabama.....	791,425	914,940	Colorado.....	2,678	23,588
Illinois.....	601,035	785,239	Connecticut.....	24,143	22,552
New York.....	297,247	369,981	Indiana.....	9,839	16,398
Virginia.....	251,356	327,912	Oregon.....	9,426	12,305
Tennessee.....	294,655	299,741	Texas.....	4,544	10,865
Michigan.....	214,356	258,461	Massachusetts.....	7,751	5,531
Wisconsin.....	158,634	246,237	North Carolina.....	2,898	3,181
New Jersey.....	125,693	177,788	Maine.....	5,200	1,200
Maryland.....	33,847	165,559	Washington.....	10,371
West Virginia.....	117,900	144,970			
Missouri.....	86,190	100,550	Total.....	8,516,079	10,307,028

To show how great was the increase in the production of pig iron in the United States in 1889 and 1890 another table is subjoined, which gives in short tons the total production of pig iron in the United States in the eighty-one years from 1810 to 1890. From 1877 to 1881 we more than doubled our production of pig iron, and from 1885 to 1890 we again more than doubled our production.

Annual production of pig iron for eighty-one years.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
1810.....	60,377	1863.....	947,604	1877.....	2,314,585
1820.....	22,400	1864.....	1,135,996	1878.....	2,577,361
1830.....	184,800	1865.....	931,582	1879.....	3,070,875
1840.....	321,331	1866.....	1,350,343	1880.....	4,295,414
1850.....	632,526	1867.....	1,461,626	1881.....	4,641,564
1854.....	736,218	1868.....	1,603,000	1882.....	5,178,122
1855.....	784,178	1869.....	1,916,641	1883.....	5,146,972
1856.....	883,137	1870.....	1,865,000	1884.....	4,589,613
1857.....	798,157	1871.....	1,911,608	1885.....	4,529,869
1858.....	705,094	1872.....	2,854,558	1886.....	6,365,328
1859.....	840,627	1873.....	2,868,278	1887.....	7,187,206
1860.....	919,770	1874.....	2,689,413	1888.....	7,268,507
1861.....	731,544	1875.....	2,266,581	1889.....	8,516,079
1862.....	787,662	1876.....	2,093,236	1890.....	10,307,028

Our production of pig iron compared with that of Great Britain.—To show how rapidly we have in late years overtaken the production of pig iron by Great Britain a table in long tons is appended, giving the production of pig iron by both countries from 1882, when Great Britain reached its maximum, until 1890. The long ton is here used because it is the ton used by Great Britain.

Production of pig iron in the United States and Great Britain.

Years.	Great Britain.	United States.	Years.	Great Britain.	United States.
	<i>Long tons.</i>	<i>Long tons.</i>		<i>Long tons.</i>	<i>Long tons.</i>
1882.....	8,586,680	4,623,323	1887.....	7,559,518	6,417,148
1883.....	8,529,300	4,595,510	1888.....	7,998,969	6,489,738
1884.....	7,811,727	4,097,868	1889.....	8,322,824	7,603,642
1885.....	7,415,469	4,044,526	1890.....	7,904,214	9,202,703
1886.....	7,009,754	5,683,329			

Production of pig iron in the Southern States.—Since much attention still continues to be given to the rapid growth of the pig-iron industry in the Southern States a table in short tons is given below, showing the production of pig iron in that section of our country in the six years from 1885 to 1890.

Production of pig iron in the Southern States for six years.

States.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Alabama.....	227,438	283,859	292,762	449,492	791,425	914,940
Tennessee.....	161,199	199,166	250,344	267,931	294,655	299,741
Virginia.....	163,782	156,250	175,715	197,396	251,356	327,912
West Virginia.....	69,007	98,618	82,311	95,259	117,900	144,970
Kentucky.....	37,553	54,844	41,907	56,790	42,518	53,604
Georgia.....	32,924	46,490	40,947	39,397	27,559	32,687
Maryland.....	17,299	30,502	37,427	17,606	33,847	165,559
Texas.....	1,843	3,250	4,383	6,587	4,544	10,865
North Carolina.....	1,790	2,200	3,640	2,400	2,898	3,181
Total.....	712,835	875,179	929,436	1,132,858	1,566,702	1,953,459

Production of spiegeleisen.—The following table shows in short tons the production of spiegeleisen and ferro-manganese in the United States from 1875 to 1890. This production is included in that of pig iron already given.

Production of spiegeleisen and ferro-manganese.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
1875.....	7,832	1881.....	21,086	1887.....	47,598
1876.....	6,616	1882.....	21,963	1888.....	54,769
1877.....	8,845	1883.....	24,574	1889.....	85,823
1878.....	10,674	1884.....	33,893	1890.....	149,162
1879.....	13,931	1885.....	34,671		
1880.....	19,603	1886.....	47,982		

Production of crude steel.—The following table shows the production of all kinds of crude steel in the United States, in the form of ingots or

direct castings, in short tons. In the Bessemer column the figures include also the production of steel by the Clapp-Griffiths and Robert Bessemer modifications of the Bessemer process.

Production of crude steel of all kinds for six years.

Years.	Bessemer.	Open-hearth.	Crucible.	Miscellaneous.	Total.	
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Long tons.</i>
1885.....	1,701,762	149,381	64,511	1,696	1,917,350	1,711,920
1886.....	2,541,493	245,250	80,609	2,651	2,870,003	2,562,503
1887.....	3,288,357	360,717	84,421	6,265	3,739,760	3,339,071
1888.....	2,812,500	352,036	78,713	4,124	3,247,373	2,899,440
1889.....	3,281,829	419,488	84,969	5,734	3,792,020	3,385,732
1890.....	4,131,535	574,820	79,716	4,248	4,790,319	4,277,071

Production of all kinds of rolled iron, by States, in 1889 and 1890.—The following table gives the production of all kinds of rolled iron, by States, in short tons, in 1889 and 1890, rolled steel not included.

Production of rolled iron, by States, in 1889 and 1890.

States.	1889.	1890.	States.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>		<i>Short tons.</i>	<i>Short tons.</i>
Maine.....	10,248	10,588	Tennessee.....	24,792	22,067
New Hampshire.....	5,680	3,600	Georgia.....	1,000	1,500
Massachusetts.....	39,269	43,540	Ohio.....	475,120	504,216
Rhode Island.....	14,140	14,618	Indiana.....	37,534	67,734
Connecticut.....	17,451	18,231	Illinois.....	126,283	146,695
New York.....	96,279	93,971	Missouri.....	15,975	22,990
New Jersey.....	63,209	62,535	Iowa.....	3,020
Pennsylvania.....	1,353,076	1,479,318	Michigan.....	21,170	31,149
Delaware.....	47,584	50,812	Wisconsin.....	40,055	48,547
Maryland and District of Columbia.....	11,164	5,409	Minnesota.....	300	2,565
Virginia.....	51,783	55,224	Colorado.....	4,270	8,328
Alabama.....	50,111	42,691	Wyoming.....	6,002	10,287
West Virginia.....	6,043	7,046	California.....	35,061	37,663
Kentucky.....	27,766	29,053	Total.....	2,586,385	2,820,377

Production of rolled steel.—In the following table is presented the details of the production of rolled steel, by States, in short tons, in 1889 and 1890, excluding rails, which are given in another table.

Production of rolled steel in 1889 and 1890.

States.	Cut nails.	Plates and sheets.	Other rolled steel.	Total in 1890.	Total in 1889.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
New England States.....	5,550	5,261	106,618	117,429	97,831
New York.....	134	3,076	86,637	89,847	109,242
New Jersey.....					
Pennsylvania.....	39,532	288,131	673,919	1,001,582	872,246
Delaware and Maryland.....	2,735	8,835	11,570	2,188
Virginia.....	2,172	2,172	2,500
West Virginia and Kentucky.....	57,555	32,335	8,050	97,940	86,309
Ohio.....	68,614	66,962	197,832	333,408	295,971
Indiana.....	17,395	121,905	139,300	87,410
Illinois.....					
Missouri and Michigan.....	250	3,037	5,800	9,087	9,580
Wisconsin.....	38	24,138	24,176	13,583
California.....	500	2,236	2,736	7,444
Total.....	191,740	401,537	1,235,970	1,829,247	1,584,364

Production of steel rails.—The following table shows the production of Bessemer steel rails in 1889 and 1890, by States, in short tons.

Production of steel rails.

States.	1889.	1890.
Pennsylvania.....	<i>Short tons.</i> 1,141,350	<i>Short tons.</i> 1,470,490
Illinois.....	522,054	587,537
Other States.....	27,860	33,951
Total.....	1,691,264	2,091,978

Production of rolled steel compared with rolled iron.—The following table shows in short tons the total production of rolled steel in 1888, 1889, and 1890 in comparison with the total production of rolled iron in the same years.

Production of rolled steel compared with rolled iron.

Articles.	1888.		1889.		1890.	
	Iron.	Steel.	Iron.	Steel.	Iron.	Steel.
Rails.....	<i>Short tons.</i> 14,252	<i>Short tons.</i> 1,557,892	<i>Short tons.</i> 10,258	<i>Short tons.</i> 1,694,610	<i>Short tons.</i> 15,548	<i>Short tons.</i> 2,095,996
Cut nails.....	108,505	216,174	88,904	201,634	90,307	191,740
Plates and sheets.....	469,312	213,694	471,193	331,283	505,642	401,537
Wire rods.....	14,571	298,770	14,460	393,053	19,798	492,153
Other rolled products....	1,805,014	473,247	2,001,570	658,394	2,189,082	743,817
Total.....	2,411,654	2,759,777	2,586,385	3,278,974	2,820,377	3,925,243

Production of cut and wire nails.—The following table shows the production by States of iron and steel cut nails, respectively, in 1890, in kegs of 100 pounds, and the total production of that year compared with the total production of 1889, to which is added the total production of wire nails.

Production of cut nails in 1890 and 1889.

States.	1890.			Total 1889.
	Iron.	Steel.	Total.	
Pennsylvania.....	<i>Kegs.</i> 1,035,179	<i>Kegs.</i> 790,645	<i>Kegs.</i> 1,825,824	<i>Kegs.</i> 1,834,899
Ohio.....	46,351	1,372,270	1,418,621	1,546,928
West Virginia.....	1,252	956,442	957,694	960,346
Indiana.....	12,865	217,099	229,964	138,200
New Jersey.....	257,678	2,689	260,367	252,067
Illinois.....		130,806	130,806	204,438
Massachusetts.....	80,573	111,000	191,573	239,903
California.....	210,000	10,000	220,000	242,000
Virginia.....	159,114	43,446	202,560	194,998
Kentucky.....		194,654	194,654	165,000
Wisconsin.....	3,118	765	3,883	11,435
Missouri.....		5,000	5,000
Colorado.....				544
Total cut nails.....	1,806,130	3,834,816	5,640,946	5,810,758
Wire nails.....			3,135,911	2,435,000
Total nail production.....			8,776,857	8,245,758

The following table gives the production of wire nails, by States, in 1889 and 1890, in kegs of 100 pounds.

Production of wire nails in 1889 and 1890.

Wire nails—kegs.	New England, New York, and New Jersey.	Pennsylvania.	Ohio.	Other States.	Total.
1889	280,000	816,000	944,000	395,000	2,435,000
1890	335,595	1,061,639	1,115,320	623,357	3,135,911

Iron and steel vessels built in the United States.—The following table gives the number and gross tonnage of all iron and steel vessels, except those for the Navy, which have been built in the United States in the fiscal years from 1868 to 1891. Nearly all were steam vessels. Since 1883 we have built many vessels of steel, and the tendency now is to use steel in constantly increasing quantities in the construction of both merchant and naval vessels. This table has been compiled from the reports of the Bureau of Navigation of the Treasury Department.

Years.	No.	Tons.	Years.	No.	Tons.	Years.	No.	Tons.
1868.....		2,801	1876.....	25	21,346	1884.....	34	35,631
1869.....		4,584	1877.....	7	5,927	1885.....	48	44,028
1870.....		8,281	1878.....	32	26,960	1886.....	26	14,908
1871.....		15,479	1879.....	24	22,008	1887.....	29	34,354
1872.....	20	12,766	1880.....	31	25,582	1888.....	43	36,719
1873.....	26	26,548	1881.....	42	28,392	1889.....	48	53,513
1874.....	23	33,097	1882.....	43	40,097	1890.....	63	80,378
1875.....	20	21,632	1883.....	35	39,646	1891.....	76	105,618

Summary of production in 1889 and 1890.—In the following table are given the statistics of the production of all leading articles of iron and steel in 1889 and 1890. All products are given in short tons of 2,000 pounds, except nails, which are given in kegs of 100 pounds. (The short ton has been used by the United States Census Office in 1870, 1880, and 1890.)

Production of leading articles of iron and steel in 1889 and 1890.

Products.	1889.	1890.
Pig iron, including spiegeleisen, short tons.....	8,516,079	10,307,028
Spiegeleisen, short tons.....	85,823	149,162
Bessemer steel ingots, short tons.....	3,281,829	4,131,555
Bessemer steel rails, short tons.....	1,691,264	2,091,978
Open-hearth steel ingots, short tons.....	419,488	574,820
Open-hearth steel rails, short tons.....	3,346	4,018
Crucible steel ingots, short tons.....	84,969	79,716
Rolled iron, except rails, short tons.....	2,576,127	2,804,829
Rolled steel, except rails, short tons.....	1,584,364	1,829,247
Iron rails, short tons.....	10,258	15,548
Pig, scrap, and ore blooms, short tons.....	36,260	30,783
Kegs of iron cut nails, 100 pounds.....	1,778,082	1,806,130
Kegs of steel cut nails, 100 pounds.....	4,032,676	3,834,816
Kegs of wire nails, 100 pounds.....	2,435,000	3,135,911
Iron and steel wire rods, short tons.....	407,513	511,951

Average monthly prices of iron and steel in the United States in 1891.—In the following table we give the average monthly prices of ten leading articles of iron and steel in Eastern markets in 1891. The prices named are per long ton of 2,240 pounds, except for bar iron and nails, which are quoted by the hundred pounds and the keg, respectively. It will be noticed that prices were not only very low all through the year but that they did not greatly vary, the general tendency, however, being steadily downward from January to December. The monthly averages are obtained from weekly quotations.

1891.	Old iron T rails, at Philadelphia.	No. 1 anthracite foundry pig iron, at Philadelphia.	Gray forge pig iron, at Philadelphia.	Gray forge pig iron, Lake ore mixed, at Pittsburg.	Bessemer pig iron, at Pittsburg.	Steel rails, at mills in Pennsylvania.	Best refined bar iron from store, at Philadelphia.	All muck bar iron, at Pittsburg.	Cut nails, at Pittsburg (base price).	Cut nails, at Philadelphia, from store.
January	\$23.50	\$17.50	\$14.50	\$14.25	\$15.95	\$29.00	\$2.00	\$1.80	\$1.65	\$1.90
February	23.35	17.50	14.50	14.50	16.25	30.00	1.90	1.75	1.65	1.90
March	22.50	17.50	14.75	15.00	16.50	30.00	1.90	1.75	1.65	1.85
April	22.50	17.50	14.75	14.12	16.10	30.00	1.90	1.70	1.60	1.90
May	22.00	17.50	14.75	14.00	16.50	30.00	1.90	1.70	1.55	1.90
June	21.00	17.50	14.75	14.00	16.25	30.00	1.90	1.70	1.55	1.85
July	21.00	17.50	14.60	14.00	16.25	30.00	1.90	1.70	1.55	1.85
August	21.50	17.50	14.50	14.00	16.00	30.00	1.90	1.70	1.55	1.85
September	22.00	17.50	14.35	14.00	15.60	30.00	1.90	1.70	1.55	1.85
October	22.00	17.75	14.35	13.85	15.50	30.00	1.85	1.70	1.60	1.80
November	21.75	17.50	14.25	13.50	15.15	30.00	1.85	1.68	1.55	1.80
December	21.50	17.50	14.25	13.50	15.35	30.00	1.90	1.68	1.55	1.85

Average yearly prices of iron and steel from 1886 to 1891.—The following table gives the average yearly prices of the articles mentioned in the preceding table from 1886 to 1891, both years inclusive. The prices are per ton of 2,240 pounds, with the exceptions mentioned above. The yearly averages are obtained by averaging the monthly quotations.

Average yearly prices of iron and steel from 1886 to 1891.

Articles.	1886.	1887.	1888.	1889.	1890.	1891.
Old iron T rails, at Philadelphia	\$21.42	\$22.97	\$22.23	\$24.19	\$25.18	\$22.05
No. 1 anthracite foundry pig iron, at Philadelphia	18.71	20.92	18.88	17.75	18.40	17.52
Gray forge pig iron, at Philadelphia	16.40	17.79	16.21	15.48	15.82	14.52
Gray forge pig iron, Lake ore mixed, at Pittsburg	16.58	19.02	15.99	15.37	15.78	14.06
Bessemer pig iron, at Pittsburg	18.96	21.37	17.38	18.00	18.85	15.95
Steel rails, at mills in Pennsylvania	34.50	37.08	29.83	29.25	31.75	29.92
Best refined bar iron from store, at Philadelphia	1.92	2.20	2.01	1.94	2.05	1.90
All muck bar iron, at Pittsburg	1.70	1.95	1.77	1.71	1.85	1.71
Cut nails (base price), at Pittsburg	2.17	2.15	1.90	1.99	1.99	1.58
Cut nails at Philadelphia, from store	2.27	2.30	2.06	2.00	2.00	1.86

Our production of Bessemer steel compared with that of Great Britain.— Since 1879 the United States has annually produced more Bessemer steel rails than Great Britain, and since 1884 it has annually produced more Bessemer steel ingots. In the following table we give the production of Bessemer ingots and rails in each country from 1877 to 1890.

Production of Bessemer steel in the United States and Great Britain.

Years.	United States.		Great Britain.	
	Ingots.	Rails.	Ingots.	Rails.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
1877.....	500, 524	385, 865	750, 000	508, 400
1878.....	653, 773	491, 427	807, 527	622, 390
1879.....	829, 439	610, 682	834, 511	520, 231
1880.....	1, 074, 262	852, 196	1, 044, 382	732, 910
1881.....	1, 374, 247	1, 187, 770	1, 441, 719	1, 023, 740
1882.....	1, 514, 687	1, 284, 067	1, 673, 649	1, 235, 785
1883.....	1, 477, 345	1, 148, 709	1, 553, 380	1, 097, 174
1884.....	1, 375, 531	996, 983	1, 299, 676	784, 968
1885.....	1, 519, 430	959, 471	1, 304, 127	706, 583
1886.....	2, 269, 190	1, 574, 703	1, 570, 520	730, 343
1887.....	2, 936, 033	2, 101, 904	2, 089, 403	1, 021, 847
1888.....	2, 511, 161	1, 386, 277	2, 032, 794	979, 083
1889.....	2, 930, 204	1, 510, 057	2, 140, 791	943, 048
1890.....	3, 688, 871	1, 867, 837	2, 014, 843	1, 019, 606

Reaction in the American iron trade in 1891.—In the month of November, 1890, a serious financial panic occurred in London, growing out of wild speculation in the Argentine Republic and elsewhere. This panic was at once communicated to New York, and it also seriously affected financial operations in Paris, Berlin, and other financial centers. Since its occurrence there has ensued a sharp reaction in the productive activity of all manufacturing countries, their iron and steel industries sharing conspicuously in this reaction. How sharp this reaction has been in the iron and steel industries of the United States may be seen from the following summary of the production of pig iron, Bessemer steel, and Bessemer steel rails in the first six months of 1891, compared with the first six months of 1890.

Comparison of iron and steel activity in 1890 and 1891.

Products.	First six months of—	
	1890.	1891.
	<i>Short tons.</i>	<i>Short tons.</i>
Pig iron.....	5, 107, 775	3, 776, 556
Bessemer steel ingots.....	2, 041, 239	1, 599, 096
Bessemer steel rails.....	1, 032, 658	579, 929

In the months of July and August, 1891, an improved feeling was manifested in all trade circles in the United States, growing out of the large crops in our own country and the short crops in Europe. The domestic iron trade shared conspicuously in this turn in the tide, and during the second half of the year greater activity was noticeable in all lines of production than in the first half. The production of pig iron, which fell off so greatly in the first half of 1891, was actually larger in the second half of the year than in either the first or second half of

1890, as will appear from the following detailed statement. The production in each half of 1890 and 1891 was as follows, in long tons:

Years—long tons.	First half.	Second half.	Total.
1890	4,560,513	4,642,190	9,202,703
1891	3,368,107	4,911,763	8,279,870

Our production of pig iron in the second half of 1891 was 269,573 gross tons larger than in the second half of 1890, which was the half year of largest production in our history prior to 1891. Our production in the second half of 1891 was at the rate of 9,823,526 long tons per annum. It was larger than in any full year in our history down to and including 1885, and larger than Great Britain's production in any whole year down to and including 1867. Although our production of pig iron in the whole of the year 1891 declined as compared with the production in 1890, it was about 1,000,000 long tons larger than that of Great Britain in 1891. The exact figures of Great Britain's production are, however, not yet attainable.

The following table gives in short tons the production of pig iron in each State of the United States during 1891, compared with the production in each of the three preceding years.

Production of pig iron in 1888, 1889, 1890, and 1891.

States.	1888.	1889.	1890.	1891.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Maine	5,574	5,200	1,200	
Massachusetts	13,248	7,751	5,531	10,069
Connecticut	21,644	24,143	22,552	24,428
New York	257,180	297,247	369,381	352,925
New Jersey	101,882	125,693	177,788	103,589
Pennsylvania	3,589,186	4,181,242	4,945,169	4,426,673
Maryland	17,606	33,847	165,559	138,206
Virginia	197,396	251,356	327,912	330,727
North Carolina	2,400	2,898	3,181	3,603
Georgia	39,397	27,559	32,687	55,841
Alabama	449,492	791,425	914,940	891,154
Texas	6,587	4,514	10,865	20,902
West Virginia	95,259	117,900	144,970	96,637
Kentucky	56,790	42,518	53,604	50,225
Tennessee	267,931	294,655	299,741	326,747
Ohio	1,163,818	1,215,572	1,389,170	1,159,215
Indiana	15,260	9,839	16,398	8,657
Illinois	579,307	604,035	785,239	749,506
Michigan	213,251	214,356	258,461	238,722
Wisconsin	116,037	158,634	246,237	220,819
Missouri	91,783	86,190	100,550	32,736
Minnesota				1,373
Colorado	20,877	2,678	23,588	20,290
Oregon	2,509	9,426	12,305	10,411
Washington	4,093	10,371		
Total	7,268,507	8,516,079	10,307,028	9,273,455

The shrinkage in production in 1891 as compared with 1890 was shared by most of the pig-iron-producing States in the North and West, most notably by Pennsylvania, which lost over half a million short tons, all in the first half of the year. But the Southern States lost in the aggregate less than 40,000 short tons, while many of them actually

increased their production in 1891 over 1890, as will be seen from the following table.

States—net tons.	First half 1891.	Second half 1891.	Total 1891.	Total 1890.
Alabama.....	376,389	514,765	891,154	914,940
Tennessee.....	145,066	181,681	326,747	299,741
Virginia.....	141,908	188,819	330,727	327,912
West Virginia.....	20,977	75,660	96,637	144,970
Kentucky.....	18,779	31,446	50,225	53,604
Georgia.....	20,401	35,440	55,841	32,687
Maryland.....	49,992	88,214	138,206	165,559
Texas.....	8,465	12,437	20,902	10,865
North Carolina.....	1,003	2,600	3,603	3,181
Total.....	782,980	1,131,062	1,914,042	1,953,459

THREE GREAT IRON AND STEEL MAKING COUNTRIES.

The United States, Great Britain, and Germany are the three leading iron and steel making countries, as they long have been, but not in the order named. There was a time when Germany was first and Great Britain was second. For about 100 hundred years Great Britain has been first. For a number of years, however, as has been shown, the United States has been the leading producer of Bessemer steel, and in 1890, as has also been shown, it was the leading producer of pig iron. The reader will be interested in the authentic statistics of the production of pig iron by Great Britain and Germany for a long series of years, which will now be given.

Great Britain.—The following table shows the growth of the pig-iron industry of Great Britain from 1788 to 1890. For this valuable and accurate table we are indebted to the courtesy of Mr. Richard Meade, of the Mineral Statistics Branch of the Home Department of Her Majesty's Government. The table is compiled from the records of the department. It begins with the revival of the British iron industry which followed the general introduction of the use of coke in the blast furnace in the latter half of the last century.

Production of pig iron in Great Britain since 1788.

Years.	Long tons.	Years.	Long tons.	Years.	Long tons.
1788.....	68,300	1852.....	2,701,000	1872.....	6,741,929
1796.....	125,079	1854.....	3,069,838	1873.....	6,566,451
1806.....	243,851	1855.....	3,218,154	1874.....	5,991,408
1818.....	325,000	1856.....	3,586,377	1875.....	6,365,462
1820.....	400,000	1857.....	3,659,447	1876.....	6,555,997
1823.....	455,166	1858.....	3,456,064	1877.....	6,608,664
1825.....	581,367	1859.....	3,712,904	1878.....	6,381,051
1827.....	690,000	1860.....	3,826,752	1879.....	5,995,337
1828.....	703,184	1861.....	3,712,390	1880.....	7,749,233
1830.....	677,417	1862.....	3,943,469	1881.....	8,144,449
1833.....	700,000	1863.....	4,510,040	1882.....	8,586,680
1836.....	1,000,000	1864.....	4,767,951	1883.....	8,529,300
1839.....	1,248,781	1865.....	4,825,254	1884.....	7,811,727
1840.....	1,396,400	1866.....	4,523,897	1885.....	7,415,469
1842.....	1,099,138	1867.....	4,761,023	1886.....	7,009,754
1843.....	1,215,350	1868.....	4,970,206	1887.....	7,559,518
1844.....	1,999,608	1869.....	5,445,757	1888.....	7,998,969
1845.....	1,512,500	1870.....	5,963,515	1889.....	8,322,824
1847.....	1,999,508	1871.....	6,627,179	1890.....	7,904,214

Exactly one hundred and fifty-one years ago, in 1740, the production of pig iron in Great Britain was only 17,350 tons, the denudation of her forests, from which a supply of charcoal fuel had been obtained, having almost destroyed her pig-iron industry.

Great Britain has been a large importer in recent years of iron ore from Spain, Italy, and other countries, but chiefly from Spain. In 1887 the quantity imported amounted to 3,765,788 tons, in 1888 to 3,562,071 tons, in 1889 to 4,031,265 tons, and in 1890 to 4,471,790 tons. Great Britain also annually imports large quantities of cupreous iron pyrites, from which she obtains "purple ore" as a residuum for use in her blast furnaces. She obtained 447,580 tons of "purple ore" from this source in 1887, 464,207 tons in 1888, 483,257 tons in 1889, and 492,669 tons in 1890. The total quantity of iron ore mined in Great Britain in 1887 amounted to 13,098,041 tons, in 1888 to 14,590,713 tons, in 1889 to 14,546,105 tons, and in 1890 to 13,780,767 tons. Great Britain, therefore, now imports nearly one-fourth of her annual supply of iron ore. The sources of her supply of foreign ore in 1889 and 1890 and the quantities and values of the imports in these years were as follows:

Sources of the foreign iron-ore supply of Great Britain.

Countries from which imported.	1889.		1890.	
	Long tons.	Values.	Long tons.	Values.
Australasia.....	1,858	£8,026	3,475	£15,266
Greece.....	79,007	79,314	112,764	101,662
Algeria.....	205,670	153,836	237,609	190,940
Italy.....	79,312	68,542	46,517	43,411
Spain.....	3,627,646	2,608,856	4,028,672	3,129,656
Turkey.....	19,588	88,131	18,968	90,036
Other countries.....	18,184	17,900	23,785	25,085
Total.....	4,031,265	£3,024,605	4,471,790	£3,596,056

Great Britain's exports of iron ore are usually only nominal, but in 1886 and 1887 they attained respectable proportions. In 1886 they amounted to 70,527 tons, of which 69,639 tons were sent to the United States. In 1887 they amounted to 56,394 tons, of which 53,817 tons were sent to the United States. In 1888 the total exports amounted to 9,730 tons, in 1889 to 5,371 tons, and in 1890 to 7,567 tons.

As the prosperity of the British iron trade rests so completely upon the abundant supply of bituminous coal, which is found in many parts of England, Scotland, and Wales, the statistics of its production will properly find a place in these pages. The following table shows the annual production of coal in Great Britain from 1855 to 1890. This table has been carefully revised for this report by Mr. Meade.

Annual production of coal in Great Britain.

Years.	Long tons.	Years.	Long tons.	Years.	Long tons.
1855.....	64,453,079	1867.....	104,500,480	1879.....	133,720,393
1856.....	66,645,450	1868.....	103,141,157	1880.....	146,969,409
1857.....	65,394,707	1869.....	107,427,557	1881.....	154,184,300
1858.....	65,008,649	1870.....	110,431,192	1882.....	156,499,977
1859.....	71,979,765	1871.....	117,352,028	1883.....	163,737,327
1860.....	80,042,698	1872.....	123,497,316	1884.....	160,757,779
1861.....	84,013,941	1873.....	128,680,131	1885.....	159,351,418
1862.....	81,638,338	1874.....	126,590,108	1886.....	157,518,482
1863.....	86,292,215	1875.....	133,306,485	1887.....	162,119,812
1864.....	92,787,873	1876.....	134,125,166	1888.....	169,935,219
1865.....	98,150,587	1877.....	134,179,968	1889.....	176,916,724
1866.....	101,630,544	1878.....	132,612,063	1890.....	181,614,288

A steady decline in the production of coal in Great Britain from 1883 to 1886 will be noticed; but in 1887 the production increased, in 1888 and in 1889 it still further increased, and in 1890 the quantity of coal mined reached the astonishing total of 181,614,288 tons.

Germany.—The growth of the iron and steel industries of Germany in recent years has been very rapid. The following table, which has been carefully revised for these pages by Dr. Hermann Wedding, of Berlin, shows the production of pig iron in Germany and the Grand Duchy of Luxemburg, included in the Zollverein, from 1844 to 1890.

Pig iron production of Germany from 1844 to 1890.

Years.	Metric tons.	Years.	Metric tons.	Years.	Metric tons.
1844.....	171,000	1869.....	1,413,029	1880.....	2,729,038
1851.....	369,000	1870.....	1,391,124	1881.....	2,914,009
1860.....	529,087	1871.....	1,563,682	1882.....	3,380,806
1861.....	591,593	1872.....	1,988,394	1883.....	3,469,719
1862.....	696,350	1873.....	2,240,575	1884.....	3,600,612
1863.....	812,555	1874.....	1,906,263	1885.....	3,687,433
1864.....	904,658	1875.....	2,029,389	1886.....	3,528,658
1865.....	988,191	1876.....	1,846,345	1887.....	4,023,953
1866.....	1,046,954	1877.....	1,934,726	1888.....	4,337,421
1867.....	1,113,606	1878.....	2,147,641	1889.....	4,524,558
1868.....	1,264,347	1879.....	2,226,587	1890.....	4,658,151

In 1834, ten years earlier than the year first named in the table, the production of pig iron in Germany and Luxemburg was only 110,000 metric tons.

Germany and Luxemburg produced 10,664,307 tons of iron ore in 1888, 11,002,187 tons in 1889, and 11,406,132 tons in 1890. Of the iron ore produced in these commercially united countries more than one-half is now supplied by the "minette" of Lothringen and Luxemburg. The imports of iron ore into Germany and Luxemburg, chiefly from Spain, amounted to 1,163,373 tons in 1888, 1,234,789 tons in 1889, and 1,522,181 tons in 1890; and the exports, chiefly from Lothringen, amounted to 2,211,820 tons in 1888, 2,179,836 tons in 1889, and 2,208,120 tons in 1890. The exports are mainly to France and Belgium.

As the iron and steel industries of Germany owe their present prominence in large part to the possession by Germany of an abundant local

supply of mineral fuel, a table is given below, also verified for these pages by Dr. Wedding, showing the aggregate production of both coal and lignite in Germany from 1853 to 1890.

Production of coal and lignite in Germany from 1853 to 1890.

Years.	Metric tons.	Years.	Metric tons.	Years.	Metric tons.
1853	10, 714, 556	1869	34, 343, 913	1880	59, 118, 035
1857	14, 867, 121	1870	34, 003, 004	1881	61, 540, 485
1860	16, 730, 492	1871	37, 856, 110	1882	65, 378, 211
1861	18, 755, 361	1872	42, 324, 467	1883	70, 442, 648
1862	20, 660, 677	1873	46, 145, 194	1884	72, 113, 820
1863	22, 366, 203	1874	46, 658, 145	1885	73, 675, 515
1864	25, 612, 899	1875	47, 804, 054	1886	73, 682, 584
1865	28, 552, 762	1876	49, 550, 461	1887	76, 232, 618
1866	28, 162, 805	1877	48, 229, 882	1888	81, 960, 083
1867	30, 802, 889	1878	50, 519, 899	1889	84, 973, 230
1868	32, 879, 123	1879	53, 470, 716	1890	89, 290, 834

In 1848 the total production of coal and lignite in Germany was only 5,800,985 metric tons.

Results accomplished by the United States in the production of pig iron, steel, iron ore, and coal.—The position of the United States among iron and steel producing countries at the present time is correctly indicated in the following table of the world's production of pig iron and steel of all kinds, which has been compiled by the writer from the latest and most reliable statistics that are accessible. Most of the details are derived from official sources, while only those relating to "other countries" have been estimated. This table places the world's production of pig iron in 1890 at 26,937,113 tons and the world's production of steel in that year at 12,255,899 tons. The percentage of pig iron produced by the United States was 34.2 and its percentage of steel was 34.9. Tons of 2,240 pounds are used in giving the statistics of Great Britain, the United States, Canada, and "other countries," and metric tons of 2,204 pounds for all the continental countries of Europe. As the difference between the long ton and the metric ton is so trifling it is not necessary, as has been explained in previous references to foreign statistics, to change official figures.

World's production of pig iron and steel.

Countries.	Pig iron.		Steel.	
	Years.	Tons.	Years.	Tons.
United States	1890	9, 202, 703	1890	4, 277, 071
Great Britain	1890	7, 904, 214	1890	3, 679, 043
Germany and Luxemburg	1890	4, 658, 451	1890	2, 232, 099
France	1890	1, 970, 160	1890	704, 013
Belgium	1890	781, 958	1890	239, 266
Austria and Hungary	1890	925, 308	1890	440, 605
Russia (including Siberia)	1889	745, 872	1889	263, 719
Sweden	1890	456, 102	1890	169, 286
Spain	1890	179, 433	1890	63, 011
Italy	1889	13, 473	1889	157, 899
Canada	1890	19, 439	1889	24, 887
Other countries	1890	80, 000	1890	5, 000
Total		26, 937, 113		12, 255, 899
Percentage of the United States		34.2		34.9

In the following table we also give the latest accessible information concerning the production of coal and iron ore throughout the world. The percentage of production of coal by the United States is seen by this table to have been 27.9, and its percentage of production of iron ore is seen to have been 28.3.

The world's production of iron ore and coal.

Countries.	Iron ore.		Coal.	
	Years.	Tons.	Years.	Tons.
United States.....	1890	16,036,043	1890	140,882,729
Great Britain.....	1890	13,780,767	1890	181,614,288
Germany and Luxemburg.....	1890	11,406,132	1890	89,290,834
France.....	1887	2,579,465	1890	25,836,953
Belgium.....	1889	202,431	1890	20,343,495
Austria and Hungary.....	1890	2,200,000	1889	25,326,417
Russia (including Siberia).....	1888	1,433,513	1889	6,228,000
Sweden.....	1890	941,241	1890	258,000
Spain.....	1890	5,788,742	1891	1,314,147
Italy.....	1889	173,489	1889	390,320
Canada.....	1890	68,313	1890	2,783,626
Other countries (including Cuba).....	1890	2,000,000	1890	11,200,000
Total.....		56,610,137		505,468,809
Percentage of the United States.....		28.3		27.9

It is not pretended that all of the details in the above tables are absolutely accurate; at the present stage of statistical inquiry even in highly civilized countries this would be impossible. But they are substantially accurate.

To recapitulate: It is found by the foregoing tables that the United States now produces over 34 per cent. of the world's production of pig iron, over 35 per cent. of its production of steel, 28.3 per cent. of its production of iron ore, and nearly 28 per cent. of its production of coal. These are wonderful and even amazing results. Such industrial progress in a brief time as is here illustrated the world has never before known.

IRON ORES.

BY JOHN BIRKINBINE.

As the basis of iron manufacture is the natural raw material entering into the production of the metal, a consideration of the advances made in the exploitation of domestic iron ore mines and the quantities of the various kinds of iron ores produced and consumed in the United States appear to be proper starting points for statistical discussion of the iron and steel industries, and for this purpose the following information concerning the amount and character of iron ores mined in the various States, also the quantities of foreign iron ores imported, and of other materials used as iron ores in the United States, is presented:

The estimated quantity of iron ore produced in 1890 (16,036,043 long tons) and the foreign iron ore imported (1,246,830 long tons) does not represent all of the material used as iron ores. Many of the blast furnaces employ as part of the charge cinder from puddling and heating furnaces, which contains about 60 per cent. of iron, and a few "blue-billy," the residuum from burning pyrites in the production of sulphuric acid. A residuum cinder, containing iron and manganese, resulting from the treatment of the New Jersey franklinite, is also utilized in several blast furnaces to produce spiegeleisen. The quantities of such material used in 1890 is estimated at 850,000 long tons.

In several of the States the number of small operators prevent obtaining absolutely correct returns, but adding, say, $1\frac{1}{2}$ per cent. of the total output to cover these, to the importations of foreign ore and the quantities of other materials employed as iron ores, there was an apparent available supply in 1890 of 18,400,000 long tons.

The principal uses to which iron ores are put, are—

(1) The production of pig iron by smelting the ores in blast furnaces, and the production of wrought iron direct from the ore in forges or by other direct processes.

(2) Fix or fettling, lining for heating and puddling furnaces.

(3) Flux in smelting furnaces producing precious metals.

(4) The manufacture of paint. (The figures for this were not collected.)

In this report the iron ores are classed under the following heads:

Red hematite.—Those ores in which the iron is found as an anhydrous sesquioxide, including "specular," "fossil," "micaceous," "martite," "slate iron ores," etc. They range in color from light red to steel gray, and are recognized by a red streak on a test plate.

Brown hematite.—Includes all those ores in which the iron is found as a hydrated sesquioxide, the color ranging from yellow to dark brown and black. This class includes “bog ore,” “limonite,” “turgite,” “goethite,” etc., and is recognized by a brown streak on a test plate.

Magnetite.—Includes all those ores in which the iron occurs principally as magnetic oxide of iron, viz, Fe_3O_4 . These ores are magnetic and give a black streak.

Carbonate.—Comprises ores in which the protoxide of iron is associated with a large percentage of carbonic acid, and includes “black band,” “spathic,” “siderite,” and “clay iron stones.” They are generally light gray to brown, sometimes dark brownish red, according to the extent to which they are weathered.

Local names, or those indicating peculiarities of structure, are used to designate some special ores in the above classes. Thus, in the red hematite division there are “flaxseed” ore, “blue hematite,” “hard fossil,” “soft fossil,” etc. In the brown hematites, “pipe ore,” “grape ore,” and in carbonates, “kidney ore,” “limestone ore,” etc.

The division above adopted will correspond with the general method used in selling and purchasing iron ores in the United States.

The following table exhibits by States (except where but one or two firms or individuals were producers in a State) the quantities of each kind and the totals of all kinds of iron ore mined, as reported, together with the proportion of the total production of iron ore in the United States, which is represented by the output of each subdivision in the calendar year 1890.

Productions of various kinds of iron ore in 1890 by States.

States.	Red hematite.	Brown hematite.	Magnetite.	Carbonate.	Total of all kinds of iron ore.	Percentage.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	
Michigan	6,426,077	402,274	313,305	7,141,656	44.51
Alabama	1,538,297	359,518	1,897,815	11.83
Pennsylvania	143,745	415,779	765,318	36,780	1,361,622	8.50
New York	196,055	30,968	945,071	81,319	1,253,393	7.82
Wisconsin	784,257	164,708	948,965	5.92
Minnesota	861,910	891,910	5.56
Virginia	16,212	522,908	4,463	543,583	3.39
New Jersey	6,000	489,808	495,808	3.09
Tennessee	278,076	187,619	465,695	2.90
Georgia	69,271	174,817	244,088	1.52
Missouri	159,440	22,250	181,690	1.13
Ohio	169,088	169,088	1.05
Colorado	14,698	99,577	114,275	.71
Montana
Oregon
New Mexico	3,632	48,000	30,000	81,632	.51
Utah
Kentucky	15,685	62,000	77,685	.48
Maryland	23,343	12,314	35,657	.22
Massachusetts	32,934	32,934	.21
Connecticut	26,058	26,058	.16
West Virginia	9,000	16,116	25,116	.16
North Carolina	22,873	22,873	.14
Texas	22,000	22,000	.14
Maine	2,500	2,500	.02
Total	10,527,650	2,559,938	2,570,838	377,617	16,036,043	100.00
Percentage of total	65.65	15.96	16.03	2.36	100.00	

The above table shows that the estimated output of the iron-ore mines of the United States in 1890 was 16,036,043 long tons, an increase over the 1889 output (viz, 14,518,041 long tons) of 1,518,002 long tons, or 10.46 per cent. Most of this increase was in the red hematite mines, their total production for 1890 being 10,527,650 long tons against 9,056,288 tons in 1889, a gain of 1,471,362 long tons, or 16.25 per cent. The magnetite ores also show an increase of 64,423 long tons, or 2.57 per cent. over the output of 1889, the 1890 product being 2,570,838 long tons, while that of the year previous was 2,506,415 long tons. The brown hematite output in 1890 was 2,559,938 long tons and 2,523,087 tons were produced in 1889, the gain over 1889 being 36,851 long tons, or 1.46 per cent. The carbonate mines, on the other hand, show a decrease from 432,251 tons, the 1889 output, to 377,617 tons in 1890, a difference of 54,634 tons, or 12.64 per cent.

In the table the States are arranged in the order of their prominence as iron-ore producers, according to the tonnage of ore won, independently of its quality, and in the data following the larger producing States have been taken up in the same order. If the ore products of each State are compared in accordance with their pig-iron producing values, *i. e.*, with the relation to the contents of metallic iron, the amounts credited to the various States will be somewhat changed, and in several instances the relative rank will be affected.

In 1890 only twenty-three States and two Territories contributed to the output of the United States as against twenty-six States and two Territories in 1889. In the State of Washington the furnace which was in blast in 1889 was idle in the year following, and the new plants projected not having been completed the iron-ore mines of that State were not operated in 1890.

The mines in Idaho and Delaware were also reported inactive in 1890.

The neglect or refusal of some producers to supply the information asked for does not affect the totals materially, as in most cases it has been possible to approximate closely the amounts of iron ore mined when official figures were not obtained. The quantities mined and the distribution of the iron-ore output given below, while not absolutely exact, are, therefore, very close to the actual amounts.

No attempt has been made to subdivide the production further than by States, as this would complicate the data and necessitate separating the reported outputs of some mining companies. In several instances two or more States have been grouped so as not to make public the business of the only individuals or corporations operating in one of them, unless specific consent to such publication had been given.

The following memoranda concerning the iron ores of the various States are presented to supplement the data given in the table. In addition, other information as to the distribution of the different kinds of ore in the various States is also given.

PRODUCTION OF IRON ORE IN VARIOUS STATES IN 1890.

Michigan had the largest product, 7,141,656 long tons, or 44.54 per cent. of that of the entire country in 1890, and this State reported 77 producing mining operations, indicating an average annual output per property of 92,749 long tons. Of the total for the State, however, 88.25 per cent., or 6,302,729 long tons, were obtained from 32 mining operations, each contributing 50,000 long tons or over. These 32 mining operations represented 39 mines, some of which consisted of a number of openings, and if these are segregated, leaving out those under 50,000 tons, it will be found that in Michigan 35 mines together produced 6,225,900 long tons, an annual average of 177,883 tons per mine. Of the iron ores obtained from Michigan 89.98 per cent. was red hematite, 5.63 per cent. was brown hematite, and 4.39 per cent. was magnetite. Michigan contributed 61.04 per cent. of all the red hematite, 15.71 per cent. of all the brown hematite, and 12.19 per cent. of all the magnetite mined in the United States in 1890. The State therefore ranks first among the red hematite, third among the brown hematite, and fourth among the magnetite producers. All of the producing mines are embraced in the Lake Superior region, of which they form an important part. The whole of the Marquette range, most of the mines in the Menominee range, and the largest producers in the Gogebic range are in the State of Michigan. All of the blast furnaces of Michigan use charcoal as fuel, and the plants are therefore of comparatively small size. Basing the ore supply for these furnaces on the pig-iron output of 1890, the blast furnaces of Michigan would consume about 400,000 tons, which is but 5.60 per cent. of the total iron ore which the State produced; hence the ore must seek other markets, principally in New York, Pennsylvania, Ohio, and West Virginia. Chicago, Illinois, and Milwaukee, Wisconsin, are also large consuming points.

Although some ore had been taken out previously, the beginning of shipments from the Michigan mines may be said to have been in 1854, since which time there has been an almost constant growth, an output of 1,000,000 long tons per annum being first reached in 1873, 2,000,000 tons were supplied in 1881, 3,000,000 tons in 1886, 4,000,000 tons in 1888, 5,000,000 tons in 1889, and 7,000,000 long tons in 1890. The mines of Michigan were wrought until 1865 before an aggregate of 1,000,000 tons had been won, the outputs of the three succeeding years added more than another million tons, while the year following augmented the aggregate of iron ore won to over 3,000,000 tons in 1869. For the following ten years the annual output grew from one-half million to one and a quarter million tons, and up to 1878 the aggregate production of the Michigan mines reached a total of 11,892,273 long tons. By the close of the year 1880 the output had amounted to a total of 15,261,352 long tons. But in the last decade a total of nearly 36,000,000 tons has been added to the Michigan iron-ore production. In the year 1890 as much iron ore was won from the Michigan mines as from the earliest exploration to and

including the year 1873, and in the past four years as much iron ore has been mined as in the thirty preceding years.

In the table which follows the Michigan output of iron ore has been inserted, and also the prevailing freight rates for each year for ore shipped from Marquette or Escanaba to ports on the lower lakes, as reported by the State commissioner of mineral statistics. Other ports have been added since 1885, and the prevailing rates from these can be compared with those of the older shipping ports of Marquette and Escanaba, from which the bulk of Michigan iron ores was furnished:

Total iron ore shipments and lake freights from Michigan mines to date.

Years.	Iron ore shipments from Michigan.	Freight rate by lake vessel per long ton.		Years.	Iron ore shipments from Michigan.	Freight rate by lake vessel per long ton.	
		From Marquette.	From Escanaba.			From Marquette.	From Escanaba.
Previous to 1854.	<i>Long tons.</i> 75,083			1872	948,553	\$2.85 to 6.60	\$2.00 to 5.25
1854	3,000			1873	1,195,234	3.25 4.00	2.30 3.00
1855	1,449			1874	899,934	1.60 2.50	1.30 1.40
1856	6,790	\$3.00		1875	881,166	1.30 1.50	1.10 1.30
1857	25,646	3.00		1876	993,311	1.25 2.20	.70 1.40
1858	22,876	\$2.00 to 2.50		1877	1,025,129	1.25 2.00	.65 1.50
1859	68,832	2.00 2.50		1878	1,127,583	1.00 1.50	.60 1.15
1860	114,410	2.00 2.50		1879	1,420,745	1.25 3.00	.70 2.10
1861	49,909	2.00 3.00		1880	1,948,334	2.00 2.75	1.50 2.00
1862	124,169	2.25 4.50		1881	2,135,729	2.00 2.30	1.00 1.60
1863	203,053	3.00 4.00		1882	2,656,933	1.25 2.00	.90 1.40
1864	247,059	3.00 5.00		1883	2,518,048	1.30 1.75	.90 1.50
1865	193,758	2.05 5.00		1884	2,225,146		1.00 .65
1866	296,713	2.75 6.50	\$2.50 to 5.75	1885	2,205,190		1.40 1.00
1867	565,504	2.00 4.00	1.05 3.05	1886	3,179,511		1.75 1.35
1868	510,522	2.25 3.25	1.06 2.06	1887	3,934,339		2.15 1.75
1869	639,097	2.75 4.50	1.05 2.05	1888	4,113,803	1.10 1.15	.90 1.45
1870	859,507	2.05 3.25	1.65 2.50	1889 (a)	5,856,169	.90 1.25	.90 1.25
1871	813,984	2.05 4.00	1.50 2.50	1890 (b)	7,141,656	1.25 1.10	1.10 1.00

a Census report (production).

b U. S. Geological Survey (production).

Attention is called to the fact that the freight rates given in the preceding table and in two which follow are merely the charges for vessel carriage from the shipping docks on lakes Superior and Michigan to the receiving docks on Lake Erie. The figures given do not include the necessary railroad tolls from the mines to the shipping docks, the distance varying from 12 miles, the shortest in the Marquette range, to nearly 100 miles in the Vermilion range; in fact, some of the Gogebie ore loaded at Escanaba travels even a greater distance. Neither do the vessel freight rates include the dock charges. The figures of freight rates have been inserted as a matter of record and to illustrate the varying conditions which affect shipments in the Lake Superior region. While the rates show considerable fluctuation due to market conditions, the general tendency has been a decline in prices owing to the improved transportation facilities offered by larger and speedier vessels. Some of the important producers own or control a fleet of vessels for handling the products of their mines.

Alabama has risen to second place as a producer of iron ore, and is credited with 1,897,815 long tons, or 11.83 per cent. of the total output

for the United States for 1890. This State was given second rank in the Eleventh Census, but the absence of some specific information made its claim to this position uncertain. In 1890, however, the increased activity of the mines of this State places it unmistakably second to Michigan. Alabama's ore product was confined to red and brown hematite, 81.06 per cent. of the total being red hematite and 18.94 per cent. brown hematite. The State ranks second among the red hematite and fourth among the brown hematite producers, having contributed 14.61 per cent. of the total red hematite and 14.04 per cent. of the total brown hematite mined in the United States in 1890.

The geological formation, which has made the ore beds of Alabama unusually extensive and easily worked, has encouraged the erection of numerous large blast furnaces, requiring an output of iron ore for the State ten times larger than it was a decade ago. Alabama is practically a consumer of all the iron ore which it produces; for although some ore is sent from the State into Tennessee and some brought in from Georgia, Alabama is practically independent of other States in regard to its present iron ore supply. While the number and extent of the iron ore deposits in Alabama are remarkable, the rapid increase in blast furnace capacity, will, when all are in operation, have a tendency to deplete the ores which can now be cheaply obtained, and threaten a possible scarcity of cheap native ores for some of the furnaces now built.

Pennsylvania ranks third as a producer, and contributed each of the four kinds of iron ore. New York is the only other State which supplied more than three varieties as above classified.

The production of iron ore in Pennsylvania in 1890 was 1,361,622 long tons, which represents 8.50 per cent. of the total of the United States. The maximum output of any mine reporting was 686,302 long tons, from the Cornwall Ore Hills. No other mine in the State approached this amount; therefore, while Pennsylvania ranks first in the number of mines, these are as a rule small producers when compared with the mines of other States.

The output of Pennsylvania was divided among the different classes of ore in the following proportions: Magnetite, 56.21 per cent.; brown hematite, 30.53 per cent.; red hematite, 10.56 per cent.; carbonate, 2.70 per cent.

The State, on account of the large output of the Cornwall Ore Hills, ranks second as a producer of magnetite, and contributed 29.77 per cent. of the total magnetite mined in the United States in 1890. It also occupied second place in brown hematite production, having contributed from numerous mines 415,779 long tons, or 16.24 per cent. of the total of this class of ore. Its output of red hematite being 1.37 per cent. of the total for the United States, gives Pennsylvania eighth place in this class, while its smaller production of carbonate ore represented 9.74 per cent. of the total, and places it fourth in that class. Notwithstanding the high rank held by Pennsylvania, it produced but one-sixth of the iron ore which was consumed in that State in 1890. The growth of

the Bessemer steel industry requiring large amounts of pig iron low in phosphorus, the low cost of Lake Superior and foreign ores, carrying high percentages of iron, due to improved transportation facilities, consolidation of mines, etc., and the consequent lower fuel consumption per ton of iron possible, have led blast furnace managers to draw largely on these sources of supply, displacing the leaner or impure native ores. Some of the scattered workings have also been abandoned from various causes, and hence there has been a decline from former years in the iron ore output of the State.

The output of the Cornwall Ore Hills has been collected from records by Mr. J. Taylor Boyd, superintendent. It is shown in the following table and indicates that of the total output to date practically one-half was mined in the last ten years, the aggregate for 1881 to 1890, both inclusive, being 5,376,562 long tons; that is, in ten years nearly as much ore has been taken from the Cornwall Ore Hills as in the previous one hundred and forty years.

Production of iron ore at the Cornwall Ore Hills, Cornwall, Pennsylvania.

Years.	Quantity.	Years.	Quantity.
	<i>Long tons.</i>		<i>Long tons.</i>
From 1740 to February, 1864 . . .	2, 518, 910	1878	179, 299
1864 (11 months)	165, 915	1879	268 488
1865	114, 803	1880	231, 173
1866	216, 660	1881	249, 050
1867	202, 755	1882	309, 681
1868	165, 843	1883	363, 144
1869	173, 429	1884	412, 320
1870	174, 408	1885	508, 864
1871	176, 055	1886	688, 054
1872	193, 317	1887	667, 210
1873	166, 782	1888	722, 917
1874	112, 429	1889	769, 020
1875	98, 925	1890	686, 302
1876	137, 902		
1877	171, 589	Total	10, 845, 244

New York follows Pennsylvania with a total output of 1,253,393 long tons, or 7.82 per cent. of the total iron ore product for the United States. Of this amount 945,071 long tons, or 75.40 per cent., was magnetite, 196,035 long tons, or 15.64 per cent., was red hematite, 81,319 long tons, or 6.49 per cent., was carbonate, and 30,968 long tons, or 2.47 per cent., was brown hematite. This State headed the list of magnetite producers with 36.76 per cent. of the total for the United States. It occupied second position as to carbonates, with 21.53 per cent. of the total; ranked sixth as to red hematites, with 1.86 per cent. of the total for this class of ore, and also contributed 1.21 per cent. of the brown hematites, taking eleventh position in that class.

The magnetites of New York and some of the carbonates and red and brown hematites are liberally drawn upon to supplement the local supplies of Pennsylvania furnaces, as the former State produced more iron ore than it used. On the other hand, the ores from the Lake Superior region find convenient access to the State from the Great Lakes, which are its northern and western boundaries; in addition some

foreign ores are used in the blast furnaces to supplement local ores. A considerable increase in the output of magnetite iron ore is anticipated in the future, due to the operation of concentrating plants which have been or are being constructed. These are referred to under the head of concentration.

In "Mineral Resources of the United States, 1886," the output prior to that date from the mines in the Lake Champlain district appears, and the following table will bring these quantities up to date:

Total production of iron ore in the Lake Champlain district, New York.

Years.	Production.
	<i>Long tons.</i>
Output prior to 1886.....	(a)13,000,000
1886.....	588,829
1887.....	768,852
1888.....	669,553
1889.....	779,900
1890.....	821,994
Total.....	16,629,128

a. Estimated.

The extensive contract of removing the roof of the Tilly Foster magnetite mine in Putnam county, New York, has been completed, and ore is now taken from a great open cut 350 feet deep. Much of that removed having been left in pillars, or in the roof and floors of the older underground exploitations. At the Croton mine, also in Putnam county, arrangements are being perfected for removing a large body of lean magnetite by open cut, for the purpose of concentration.

Wisconsin occupies fifth place with a product in 1890 of 948,965 long tons, or 5.92 per cent. of the entire output of the country. The quantity of red hematite produced was 784,257 long tons, or 82.64 per cent. of the total amount of the iron ore won in this State, and 7.45 per cent. of the total of this kind of ore in the United States. Of the State's output 17.36 per cent., or 164,708 long tons, was brown hematite, being 6.43 per cent. of the country's total of this class of ore. Wisconsin is a larger producer than consumer of iron ores, its furnaces requiring about 45 per cent. of its total output of ores. Owing, however, to the ownership of mines, the character of material won, and the routes of transportation, a large amount of the iron ore used in the furnaces comes from Michigan, while Wisconsin ores seek markets at the lower lake ports. The total output of Wisconsin for a number of years can not be given, as some of the brown hematites in the central portion, and the fossil hematites in the eastern section of the State, are not regularly mentioned in shipping reports. Since 1885, when the Gogebic range made its first output, the following amounts of iron ore were shipped from the mines in Wisconsin, which may be considered as in the Lake Superior region. The freight rates on these ores are those for Ashland, Wisconsin, and Escanaba, Michigan, for the years named.

Total iron ore production and lake freights from Wisconsin mines in the Lake Superior region.

Years.	Iron ore production.	Freight rate by lake vessels per long ton.	
		From Escanaba, Michigan.	From Ashland, Wisconsin.
	<i>Long tons.</i>		
1880	14, 143	\$1.50 to 2.00	
1881	197, 911	1.00	1.60
1882	276, 020	.90	1.40
1883	62, 175	.90	1.50
1884	34, 612		.65
1885	55, 181	1.00	\$1.07 to 1.65
1886	150, 294	1.35	1.02 3.09
1887	400, 104	1.75	1.75 2.75
1888	381, 140	.90 1.45	1.02 1.08
1889	(a) 837, 399	.90 1.25	1.25 .90
1890	(a) 948, 965	1.10 1.00	1.35 1.00
Total	3, 357, 944		

a. Including all mines in the State.

Minnesota ranks sixth with a total of 891,910 tons, or 5.56 per cent. of the total iron ore for the country; all of the ore was of the red hematite variety, in which class the State occupied third place, producing 8.47 per cent. of the entire output.

The iron smelting industry of Minnesota has been dormant for a number of years, but a blast furnace has lately been constructed. It was not operated in 1890, and, therefore, no ore was used. The iron ores of Minnesota travel further to reach points of consumption than any other ores in the country. The ores being of the hard red hematite variety, and rich in iron, they stand shipment better than most ores because while in transit they absorb less moisture, which adds to the freight charges on the ore.

The first shipment of iron ore from the Vermilion range was in the year 1884, and since then each year has shown an increased output as will be seen from the accompanying table, which gives the product of the Vermilion range in Minnesota, up to and including 1890, as well as the freight rates from Two Harbors.

Total iron ore production and lake freights from Minnesota mines.

Years.	Production.	Freight rate by lake vessel per long ton, from Two Harbors, Minnesota.
	<i>Long tons.</i>	
1884	62, 122	
1885	227, 075	
1886	307, 948	
1887	394, 910	
1888	511, 953	\$1.02 to 1.66½
1889	(a) 864, 508	1.25 1.90
1890	891, 910	1.35 1.10
Total	3, 260, 426	

a Eleventh Census.

Virginia had an output of 543,583 long tons or 3.39 per cent. of the total product of iron ore in 1890. The major portion, viz, 522,908 long

tons, or 96.20 per cent., was brown hematite, this State heading the list of producers of that character of ore, its proportion being 20.43 per cent. The State held tenth position in the list of red hematite producers with 16,212 tons, or 2.98 per cent. of the State's product, or 0.15 per cent. of the entire red hematite product, and standing seventh as a producer of magnetite with a percentage of 0.17. Lately there has been an active development of blast furnace construction in Virginia, causing additional demands on the iron-ore mines. While ores have been sent from Virginia into other States, the bulk of what is mined, is, and will be, required and used in the State, and it is probable that other ores may be drawn into it from North Carolina and elsewhere.

New Jersey stands eighth, producing 495,808 tons, or 3.09 per cent. of the total iron ore for the United States, all of the ore being magnetite with the exception of 6,000 tons, or 1.21 per cent., which was red hematite. It produced 19.05 per cent. of the total magnetite mined, and 0.06 per cent. of the red hematites, ranking third and twelfth, respectively, in these classes. While the *New Jersey* blast furnaces use local magnetites, with the addition of some foreign ore, a large part of the output from the mines is sent to the *Pennsylvania* furnaces.

The table which follows gives the total production of iron ore in *New Jersey* up to and including 1890, and has been compiled from the reports of the *New Jersey* Geological Survey.

Total production of the iron-ore mines of New Jersey.

Years.	Long tons.	Years.	Long tons.
Prior to 1860.....	(x)6,000,000	1880.....	745,000
1860.....	164,900	1881.....	737,052
1864.....	226,000	1882.....	932,762
1867.....	275,067	1883.....	521,416
1870.....	362,636	1884.....	393,710
1871.....	450,000	1885.....	330,000
1872.....	600,000	1886.....	500,501
1873.....	665,000	1887.....	547,889
1874.....	525,000	1888.....	447,738
1875.....	390,000	1889.....	(b) 415,510
1876.....	285,000	1890.....	(c) 495,808
1877.....	315,000		
1878.....	409,674	Total.....	17,223,691
1879.....	486,028		

a Estimated.

b Eleventh Census.

c U. S. Geological Survey.

The output of iron ore in *Tennessee* was 465,695 long tons or 2.90 per cent. of the total for the country in 1890. Of this amount the red hematite mines contributed 278,076 tons, or 59.71 per cent., and the brown hematite 187,619 tons, or 40.29 per cent. This State occupied fifth place as a red hematite producer, its percentage being 2.64 and fifth place with 7.33 per cent. in the brown hematite class. Nearly all of the iron ore mined is consumed in the blast furnaces of the State, and in addition some iron ore is brought in from *Georgia*.

Georgia's product is 244,088 tons or 1.52 per cent. of the total iron ore for the country, the larger portion, 71.62 per cent., being brown hematite, in which class it takes sixth rank, with 6.83 per cent. of the

total of that class; the remainder of the State's output, 28.38 per cent., or 69,271 tons, is red hematite, which amount gives it ninth rank, with a percentage of the total of 0.66. Georgia made pig iron from about one-half of the ores mined in the State, the balance being shipped to Tennessee and Alabama.

Missouri's output of 181,690 tons of iron ore gives it eleventh position, its percentage being 1.13. Of this 87.75 per cent. or 159,440 tons, is red hematite, this amount giving it seventh position in that class of ore, with a percentage of the country's total of 1.51. The remainder, 22,250 tons, or 12.25 per cent. of the State's output, was brown hematite, in which class of ore it obtained fourteenth position, its percentage being 0.87 of the total mined.

The blast furnaces of Missouri use more than one-half of its iron-ore output. The remainder is sent to various States, some of it being employed in silver-smelting. The practical abandonment of one prominent ore-producer has had a depressing influence upon the possible future of other similar deposits, but later exploration of territory adjacent to this abandoned mine indicates large reserves of ore which can be depended upon when the demand shall encourage the exploitations being carried to sufficient depths.

In "Mineral Resources of the United States, 1887," the output of the Iron Mountain deposit up to 1887 was given as 2,736,445 tons; subsequent exploitations have increased this amount to 3,282,391 long tons.

On subsequent pages will be found an interesting summary of the chemical investigation of the Iron Mountain ores, covering one year of close examination.

Ohio ranks twelfth as a producer; it is the only other State producing over 1 per cent. of the total for the country, its proportion being 1.05, all of which is carbonate ore. It was the largest producer of this class of ore in the country, its percentage of the total output being 44.78. Nearly, if not all, of this ore is smelted in local blast furnaces, but it forms only a small proportion of the supply, the balance coming from the Lake Superior region, Missouri, Kentucky, and even from New York. In this respect Ohio is the opposite of Michigan, which consumes but a small percentage of its output, shipping the balance to other points. Ohio is a large user of Michigan ores and ranks next to Pennsylvania as a consumer of iron ores.

Production of carbonate iron ore in Ohio from 1886 to 1890.

Years.	Amount mined.
1886.....	<i>Long tons.</i> (a) 344,484
1887.....	(a) 377,465
1888.....	(a) 253,352
1889.....	254,294
1890.....	169,088
Total for five years.....	1,398,683

a Reports of the chief inspector of mines of the State of Ohio.

None of the remaining States produced a large amount of ore, their combined percentage being but 2.75. In the western States a majority of the ore won is brown hematite, which is used in smelting the precious metals, although there were active blast furnaces in Colorado and Oregon in 1890.

Kentucky uses some of her ores in local blast furnaces and also sends some to furnaces in Ohio.

Maryland uses the bulk of her own ores, carbonates, and brown hematites, although some were sent to Pennsylvania.

The brown hematites of Massachusetts, Connecticut, and New York, chiefly those from the Salisbury district, are sought after by local furnaces, but the output of the mines is comparatively small.

West Virginia uses all of the ore produced there and also obtains liberal supplies from the Lake Superior region and Missouri.

North Carolina magnetites are used in the local furnace, and also sent to other plants outside of the State. In addition to the magnetite, which is already developed, red and brown hematites exist and are being developed.

Texas as yet only mines bog ores for a limited home consumption.

The only blast furnace in the State of Maine suspended operations in 1890, and it is scarcely probable that the iron ore mines will be operated in the near future.

A deposit of bog ore occurs in Delaware, from which ore has been won for many years, and which will probably be again worked.

In Florida a deposit of carbonate ore has been explored with a view to working it, but the project has not been carried out.

Years ago South Carolina contributed to the iron-ore supply of the country and has some good deposits.

Mississippi, Louisiana, and Texas furnish some carbonates and brown hematites from surface strippings, but large areas must be exposed to win any considerable quantity of ore.

Wyoming is favored with unusually excellent deposits of iron ores; Indian Territory holds in reserve considerable bodies of ore; California, Washington, and most of the western States have supplies of excellent ores, which can be used in the future.

TOTAL PRODUCTION OF PROMINENT IRON ORE DISTRICTS.

The Lake Superior district is by far the most important producer of iron ores, and not only now supplies more iron ore than any other section of the country, but has up to the present time contributed more than any other section. In the following statement an effort has been made to give approximately the total output of various producing centers:

Total production of iron ore in prominent producing centers.

	Long tons.
Lake Superior region.....	57,000,000
Of which Marquette district supplied.....	32,700,000
Menominee district supplied.....	12,800,000
Gogebic district supplied.....	8,300,000
Vermilion district supplied.....	3,200,000
Lake Champlain region, New York.....	16,600,000
Of which Port Henry supplied.....	10,000,000
Crown Point supplied.....	1,800,000
Chateaugay supplied.....	2,550,000
Other mines supplied.....	2,250,000
New Jersey.....	17,200,000
Cornwall.....	10,850,000
Missouri.....	5,780,000
Of which Iron Mountain supplied.....	3,280,000
Pilot Knob and other Missouri mines supplied..	2,500,000

COMPARATIVE PRODUCTION OF IRON ORE IN 1880, 1889, AND 1890, IN PROMINENT STATES.

The tables which follow have been prepared to illustrate the changes which have taken place within the last decade, in the quantities of each class of ore, and of all kinds produced by each contributing State, and also the increase or decrease which has occurred in ten years and in one year, viz, 1889 to 1890. In these tables the published reports of the Tenth and Eleventh Censuses are used, and the figures from these are compared with those collected for 1890 for the present volume of Mineral Resources. The relative importance or rank of each State as a producer is given with the figures for each year.

Production of iron ores by States in 1890, 1889, and 1880, with percentages of increase or decrease.

States.	1890.			1889.		
	Rank.	Production.	Percent- age of total.	Rank.	Production.	Percent- age of total.
		<i>Long tons.</i>			<i>Long tons.</i>	
Michigan.....	1	7,141,656	44.54	1	5,856,169	40.34
Alabama.....	2	1,897,815	11.83	2	1,579,319	10.82
Pennsylvania.....	3	1,361,622	8.50	3	1,560,234	10.75
New York.....	4	1,253,393	7.82	4	1,247,537	8.59
Wisconsin.....	5	948,965	5.92	6	837,399	5.77
Minnesota.....	6	891,910	5.56	5	864,508	5.95
Virginia.....	7	543,583	3.29	7	498,154	3.43
New Jersey.....	8	495,808	3.09	9	415,510	2.86
Tennessee.....	9	465,695	2.90	8	473,294	3.26
Georgia.....	10	244,088	1.52	12	248,020	1.71
Missouri.....	11	181,690	1.13	10	265,718	1.83
Ohio.....	12	169,088	1.05	11	254,294	1.75
Colorado.....	13	114,275	0.71	13	109,136	0.75
Montana, Oregon, New Mexico, and Utah.....	14	81,632	0.51	14	(a) 86,405	0.60
Kentucky.....	15	77,685	0.48	15	77,487	0.53
Maryland.....	16	35,657	0.22	18	(b) 29,380	0.20
Massachusetts.....	17	32,934	0.21	16	46,242	0.32
Connecticut.....	18	20,058	0.16	17	29,690	0.20
West Virginia.....	19	25,116	0.16	19	13,101	0.09
North Carolina.....	20	22,873	0.14	22	10,125	0.07
Texas.....	21	22,000	0.14	20	13,000	0.09
Maine.....	22	2,500	0.02	21	12,319	0.09
Indiana and Vermont.....						
Total.....		16,036,043	100.00		14,518,041	100.00

a Including Idaho and Washington.

b Including Delaware.

Production of iron ores by States in 1890, 1889, and 1880, etc.—Continued.

States.	1880.			Increase or decrease in 1890 over 1889.	Percentage of increase or decrease in 1890 over 1889.	Increase or decrease in 1890 over 1880.	Percentage of increase or decrease in 1890 over 1880.
	Rank.	Production.	Percentage of total.				
		<i>Long tons.</i>		<i>Long tons.</i>		<i>Long tons.</i>	
Michigan	2	1,640,814	23.04	+1,285,487	+ 21.97	+5,500,842	+ 335.25
Alabama	8	171,139	2.40	+ 327,496	+ 20.86	+1,726,676	+1008.93
Pennsylvania	1	1,951,495	27.41	- 198,612	- 12.73	- 589,873	- 30.23
New York	3	1,126,899	15.53	+ 5,856	+ 0.47	+ 126,494	+ 11.22
Wisconsin	15	37,000	0.52	+ 111,566	+ 13.32	+ 911,965	+2404.77
Minnesota		None.		+ 27,402	+ 3.17	+ 891,910	
Virginia	7	162,791	2.29	+ 45,429	+ 9.12	+ 380,792	+ 233.91
New Jersey	4	676,225	9.50	+ 80,298	+ 19.33	+ 180,417	+ 26.68
Tennessee	10	93,272	1.31	- 7,599	- 1.61	+ 372,423	+ 399.29
Georgia	11	81,621	1.15	- 3,932	- 1.61	+ 162,467	+ 199.05
Missouri	6	344,819	4.84	- 84,028	- 31.62	- 163,129	- 47.31
Ohio	5	488,753	6.86	- 85,206	- 33.51	- 319,665	- 65.40
Colorado		None.		+ 5,139	+ 4.71	+ 114,275	
Montana, Oregon, New Mexico, and Utah	17	(a) 6,225	0.09	- 4,773	- 5.52	+ 75,407	+1211.36
Kentucky	12	57,865	0.81	+ 198	+ 0.26	+ 19,820	+ 34.25
Maryland	9	(b) 127,162	1.78	+ 6,277	+ 21.36	- 91,445	- 71.95
Massachusetts	13	55,926	0.79	- 13,308	- 28.78	- 22,992	- 41.11
Connecticut	16	31,267	0.44	- 3,632	- 12.23	- 5,209	- 16.66
West Virginia	14	54,657	0.77	+ 12,015	+ 91.71	- 29,541	- 54.05
North Carolina	20	2,963	0.04	+ 12,748	+125.91	+ 19,910	+ 671.95
Texas	19	3,214	0.05	+ 9,000	+ 69.23	+ 18,786	+ 584.51
Maine	18	5,357	0.07	- 9,819	- 79.71	- 2,857	- 53.33
Indiana and Vermont	21	958	0.01			- 958	- 100.00
Total		7,120,362	100.00	+1,518,002	+ 10.46	+8,915,681	+ 125.21

a Only Oregon.

b Including Delaware.

The above table treats of the aggregate of all kinds of ore mined, and indicates that the producing States in 1880 numbered twenty-three; in 1889, twenty-six States and two Territories, and in 1890, twenty-three States and two Territories. The total output of iron ore in ten years increased over 125 per cent, and the production of 1890 was over 10 per cent greater than that of 1889.

Pennsylvania was the largest contributor to the iron-ore supply of 1880, with 27.41 per cent of the total. In ten years its output has decreased over half a million tons, a decline of 30 per cent, and the State in 1889 and 1890 ranks third in importance, following Michigan and Alabama. As above stated, Pennsylvania local ores have been largely displaced by foreign ores, or by those from the Lake Superior region. Although a smaller producer of iron ores, Pennsylvania has been a growing consumer, and now requires a supply of iron ores which is equivalent to nearly 54 per cent of what the country produced in 1890.

Michigan, which held second rank in 1880, producing 23.04 per cent of the total, more than quadrupled its output in a decade, rising to first place and contributing in 1889 40.34 per cent, and in 1890 44.54 per cent of the total of the country. An increase of five and a half million tons in ten years is remarkable, but an augmented output exceeding one and a quarter million tons in one year is even more unusual, as shown by the production of Michigan for 1890 exceeding that for 1889 by almost 22 per cent. The number, the character, and the extent of the iron-ore deposits of the State, the improved mining appliances, and

the excellent transportation facilities established, give promise that Michigan will continue to lead other States as a producer of iron ores.

New York, which held third place in 1880, augmented its output so as to show an increase of 11.22 per cent in ten years, but the greater advance in other States forced New York to occupy fourth rank in 1889 and 1890. This State should be able to maintain its present position with the large deposits of good magnetite available and the possibilities of augmented output from these by ore which is beneficiated by magnetic separators. There was a decline in the amount of brown hematite produced in New York in 1890 and 1889 as compared with 1880.

New Jersey, for similar reasons, should in the future show an improvement, for although standing fourth in importance in 1880, and producing nearly one-tenth of the iron ore in that year, it fell to ninth place in 1889, recovering eighth position in 1890, and producing but 3 per cent of the country's total, showing a decline of production in a decade of 26.68 per cent. Some of the influences which affected the iron-ore output of Pennsylvania were active in New Jersey.

Ohio, even more than New Jersey, shows unfavorably in a comparison between the outputs for 1880, 1889, and 1890 occupying fifth place and producing nearly 7 per cent of the total in 1880, the State ranked eleventh in 1889 and twelfth in 1890, with an output of but 1 per cent of the country's total in the latter year, the decline in a decade being 65.4 per cent, owing to the displacement of local carbonate iron ores by richer ores from the Lake Superior region. Ohio, however, ranks second only to Pennsylvania as a consumer of iron ores.

Missouri is another instance of decreased production, more noted than New Jersey, but less than Ohio, except in the years 1889 and 1890. This State, whose output of iron ore in 1880 was nearly 5 per cent of the country's total, giving it sixth rank, contributed less than 2 per cent in 1889 and $1\frac{1}{2}$ per cent in 1890 of the totals in those years. The decline in ten years was 47.31 per cent, due to a contraction of the iron-smelting industry of the State and the practical exhaustion of one important iron-ore mine.

Virginia, which stood next to Missouri in 1880, and contributed 2.29 per cent of the total iron ore for the country in that year, has maintained the same relative rank (viz, seventh), although the production of 1880 was more than trebled in both 1889 and 1890, the proportions of the total iron-ore output which the State contributed in these years being 3.43 per cent and 3.39 per cent, respectively. The State did not quite keep pace with the entire country in the proportionate increased production of 1890 over 1889. The construction of numerous blast furnaces in Virginia offers indications for continued activity in its iron-ore mines.

Alabama shows more remarkable growth than Virginia, its output of 1880, which was 2.4 per cent of the country's production in that year, being increased nine and ten fold, respectively, in 1889 and 1890, when

the percentages of the total output represented by Alabama's contribution were 10.82 and 11.83 per cent. The rapid increase in the iron-producing industries of the State have encouraged an unusual development of iron-ore deposits; and Alabama, which was a comparatively unimportant producer of iron ore (ranking eighth in 1880), has risen to second place in 1889, maintaining this position with increased output in 1890.

Maryland shows a material decline in ten years, for, like Ohio, the abandonment of its local carbonate deposits has reduced its iron-ore output from 1.78 to 0.22 per cent of the country's total, driven it from ninth to sixteenth rank, and indicated a reduction of 71.95 per cent in production. A similar result is noticed in West Virginia, with a decline of 54 per cent in ten years. These two States, however, are important consumers of iron ore.

Tennessee, Georgia, and Kentucky, which held tenth, eleventh, and twelfth places in 1880, showed an increased production in 1890, fivefold, threefold, and one-third, respectively, giving the States named ninth, tenth, and fifteenth ranks.

On the other hand, Massachusetts, Connecticut, and Maine, which in 1880 combined supplied 1.3 per cent of the total for the country, each show a decided decline; and their combined output was but 0.61 per cent of the nation's production of iron ore in 1889, and 0.39 per cent in 1890.

The development of a large deposit of magnetite in North Carolina has caused an advance in that State, but it has not reached the important position it should command.

Texas has commenced the development of its bog ores, but it is not probable that it will reach a production equivalent to 1 per cent of the country's total for several years.

The most marked advances in the past decade appear in the States of Wisconsin, Minnesota, Colorado, and those States west of the Rocky Mountains.

Wisconsin, which ranked fifteenth in 1880, mining ores principally for local charcoal blast furnaces, increased its output in 1890 twenty-five fold, to nearly 1,000,000 tons, taking fifth rank as a producer. Only three States, Pennsylvania, Michigan, and New York, produced more iron ore in 1880 than Wisconsin did in 1890. This advance is chiefly due to the development, within six years, of the Gogebic iron range in Michigan and Wisconsin.

Minnesota, which did not appear in the record of 1880 as a producer of iron ore, followed Wisconsin closely in 1890 in sixth rank, with a production only excelled by three States a decade ago. The exploitation of the Vermilion iron range in Minnesota, contemporaneously with that of the Gogebic range, has brought this State into prominence as an iron-ore producer, a position which it will probably maintain in the future.

Colorado, which was not reported among the producers of iron ore in 1880, ranks thirteenth in 1890, with an output which was supplied to blast furnaces and silver smelters. This State would have ranked as a large producer ten years ago with the amount of iron ore which is credited to it in 1890, and the local developments will probably keep it as a contributor of a greater percentage than in 1890 (0.71) of the total output.

Oregon, the only far Western State which furnished iron ores in 1880, has been joined since by Washington, Utah, New Mexico, Montana, and Idaho. The combined outputs of these States and Territories in 1890 represented one-half of 1 per cent of the total production of the country. The amount was somewhat greater in 1889, for Idaho and Washington were producers in that year, but were not so reported in 1890.

Production of red hematite ores, by States, in 1890, 1889, and 1880, with percentages of increase or decrease.

States.	1890.			1889.		
	Rank.	Production.	Percentage of total.	Rank.	Production.	Percentage of total.
		<i>Long tons.</i>			<i>Long tons.</i>	
Michigan	1	6,426,077	61.04	1	5,272,915	58.22
Alabama	2	1,538,297	14.61	2	1,190,985	13.15
Minnesota	3	891,910	8.47	3	864,508	9.55
Wisconsin	4	784,257	7.45	4	735,429	8.12
Tennessee	5	278,076	2.64	5	299,102	3.30
New York	6	196,035	1.86	7	224,438	2.48
Missouri	7	159,440	1.51	6	265,318	2.93
Pennsylvania	8	143,745	1.37	8	162,957	1.80
Georgia	9	69,271	0.66	10	12,963	0.14
Virginia	10	16,212	0.15	11	8,746	0.10
Colorado	11	14,698	0.14	12	4,821	0.05
New Jersey	12	6,000	0.06			
Montana, Oregon, New Mexico, and Utah	13	3,632	0.04	9	14,106	0.16
Total		10,527,650	100.00		9,056,288	100.00

States.	1880.			Increase or decrease in 1890 over 1889.	Percentage of increase or decrease in 1890 over 1889.	Increase or decrease in 1890 over 1880.	Percentage of increase or decrease in 1890 over 1880.
	Rank.	Production.	Percentage of total.				
		<i>Long tons.</i>		<i>Long tons.</i>		<i>Long tons.</i>	
Michigan	1	1,213,479	54.09	+1,153,162	+ 21.87	+5,212,598	+ 429.56
Alabama	6	67,159	2.99	+ 347,312	+ 29.16	+1,471,138	+2,190.53
Minnesota				+ 27,402	+ 3.17	+ 891,910	
Wisconsin	9	35,000	1.55	+ 48,828	+ 6.64	+ 749,267	+2,140.73
Tennessee	5	68,358	3.04	- 21,026	- 7.03	+ 209,718	+ 306.79
New York	4	160,899	7.17	- 28,403	- 12.66	+ 35,136	+ 21.84
Missouri	2	344,719	15.36	- 105,878	- 39.91	- 185,279	- 53.75
Pennsylvania	3	267,572	11.93	- 19,212	- 11.79	- 123,827	- 46.28
Georgia	8	42,148	1.88	+ 56,308	+434.38	+ 27,123	+ 64.35
Virginia	7	37,000	1.65	+ 7,466	+ 85.36	+ 20,788	+ 56.18
Colorado				+ 9,877	+204.87	+ 14,698	
New Jersey				+ 6,000		+ 6,000	
Montana, Oregon, New Mexico, and Utah				- 10,474	- 74.25	+ 3,632	
West Virginia	10	6,250	0.28			+ 6,250	+ 100.00
Maryland	11	909	0.04			+ 909	+ 100.00
Vermont	12	500	0.02			+ 500	+ 100.00
Total		2,243,993	100.00	+1,471,362	+ 16.25	+8,283,657	+ 369.15

The table above illustrates the rank and comparative development of the various States in the production of red hematite ores, the class which in ten years has advanced most rapidly. The table shows that the increase has been chiefly in the rich red hematite of Michigan, Wisconsin, and Minnesota, and in the easily mined fossil ores of Alabama and Tennessee. New York and Georgia also show an advance, while Missouri and Pennsylvania exhibit a decline, due in the former State to depletion of available or easily wrought deposits, and in the latter to expensive mining of lean ores. The deposits of Maryland, West Virginia, and Vermont were not wrought in 1890.

Michigan, Wisconsin, Minnesota, and Alabama supplied over 90 per cent of all the red hematites mined in the country in 1890, whereas in 1880 the same territory contributed less than 60 per cent of the total of this class of ore. On the other hand, Pennsylvania and Missouri, which combined produced over 27 per cent of all of the red hematites in 1880, have in ten years declined in quantity more than one-half, and in 1890 these two States supplied less than 3 per cent of the red hematite mined in the United States.

Production of brown hematite ore, by States, in 1890, 1889, and 1880, with percentages of increase or decrease.

States.	1890.			1889.		
	Rank.	Production.	Percent- age of total.	Rank.	Production.	Percent- age of total.
		<i>Long tons.</i>			<i>Long tons.</i>	
Virginia	1	522,908	20.43	2	483,208	19.15
Pennsylvania	2	415,779	16.24	1	496,555	19.68
Michigan	3	402,274	15.71	4	332,257	13.17
Alabama	4	359,518	14.04	3	379,334	15.03
Tennessee	5	187,619	7.33	6	174,192	6.90
Georgia	6	174,817	6.83	5	235,057	9.32
Wisconsin	7	164,708	6.43	7	101,970	4.04
Colorado	8	99,577	3.89	8	100,421	3.93
Montana, Oregon, New Mexico, and Utah	9	48,000	1.88	10	37,763	1.50
Massachusetts	10	32,934	1.29	9	46,242	1.83
New York	11	30,968	1.21	11	80,374	1.20
Connecticut	12	26,058	1.02	12	29,690	1.18
Maryland	13	23,343	0.91	14	16,160	0.64
Missouri	14	22,250	0.87	21	400	0.02
Texas	15	22,000	0.86	15	13,000	0.51
Kentucky	16	15,685	0.61	13	25,212	1.00
West Virginia	17	9,000	0.35	17	4,000	0.16
Maine	18	2,500	0.10	16	12,319	0.49
Delaware				19	1,901	0.08
Idaho				20	1,104	0.04
Washington				18	1,923	0.08
Total		2,559,938	100.00		2,523,087	100.00

Production of brown hematite ore, by States, in 1890, 1889, and 1880, etc.—Continued.

States.	1880.			Increase or decrease in 1890 over 1889.	Percentage of increase or decrease in 1890 over 1889.	Increase or decrease in 1890 over 1880.	Percentage of increase or decrease in 1890 over 1880.
	Rank.	Production.	Percentage of total.				
		<i>Long tons.</i>		<i>Long tons.</i>		<i>Long tons.</i>	
Virginia.....	4	115,246	6.01	+99,700	+ 8.22	+407,662	+ 353.73
Pennsylvania.....	1	1,009,550	52.62	-80,776	- 16.27	-593,771	- 58.82
Michigan.....	2	294,551	15.35	+70,017	+ 21.07	+107,723	+ 36.57
Alabama.....	5	98,836	5.15	-19,816	- 5.22	+260,682	+ 263.75
Tennessee.....	10	24,914	1.30	+13,427	+ 7.71	+162,705	+ 653.07
Georgia.....	8	39,473	2.06	-60,240	- 25.63	+135,344	+ 342.88
Wisconsin.....	18	2,000	0.10	+62,738	+ 61.53	+162,708	+ 8,135.40
Colorado.....				- 844	- 0.84	+ 99,577
Montana, Oregon, New Mexico, and Utah.....	13	a 6,225	0.32	+10,237	+ 27.11	+ 41,775	+ 671.08
Massachusetts.....	7	55,926	2.92	-13,308	- 28.78	- 22,992	- 41.11
New York.....	3	138,275	7.21	+ 594	+ 1.96	-107,307	- 77.60
Connecticut.....	9	31,267	1.63	- 3,632	- 12.23	- 5,209	- 16.66
Maryland.....	6	57,821	3.01	+ 7,183	+ 44.45	- 34,478	- 59.80
Missouri.....	21	100	0.01	+21,850	+5,462.50	+ 22,150	+22,150.00
Texas.....	15	3,214	0.17	+ 9,000	+ 69.23	+ 18,786	+ 584.51
Kentucky.....	11	15,768	0.82	- 9,527	- 37.79	- 83	- 0.53
West Virginia.....	17	2,900	0.15	+ 5,000	+ 125.00	+ 6,100	+ 210.34
Maine.....	14	5,357	0.28	- 9,819	- 79.71	- 2,857	- 53.31
New Jersey.....	12	13,846	0.72	- 13,846	- 100.00
Delaware.....	16	2,434	0.13	- 1,901	- 100.00	- 2,434	- 100.00
Idaho.....				- 1,104	- 100.00
Washington.....				- 1,928	- 100.00
North Carolina.....	19	461	0.02	- 461	- 100.00
Indiana.....	20	458	0.02	- 458	- 100.00
Total.....		1,918,622	100.00	+36,851	+ 1.46	+641,316	+ 83.43

a Oregon only.

The table above exhibits the rank of various States as producers of brown hematite ores, showing a material decline in the amount produced in Pennsylvania and in all of the Eastern States, and a marked advance in Virginia, Alabama, and in all of the Southern States except Kentucky, also an increase in quantity in Michigan and Wisconsin, where some hydrated ores occur with red hematites, and where large deposits of limonites have lately been exploited. Brown hematites will not permit of such long hauls as most red hematites and magnetites, and hence depend more on local consumption.

The table which follows indicates an advance in the production of magnetite of but 20 per cent in ten years. Pennsylvania, however, increased its output over 70 per cent in 1889, and 53 per cent in 1890 over the returns for 1880, chiefly on account of the development of the Cornwall Ore Hills. New York shows a gradual increase, the output of 1890 exceeding that of 1880 by 14.18 per cent. The quantitative decline in New Jersey is offset by a nearly similar increase in Michigan. As in other tables the ranks of the various States in 1880, 1889, and 1890 are shown.

Production of magnetite by States in 1890, 1889, and 1880, with percentages of increase or decrease.

States.	1890.			1889.		
	Rank.	Production.	Percentage of total.	Rank.	Production.	Percentage of total.
		<i>Long tons.</i>			<i>Long tons.</i>	
New York	1	945,071	36.76	1	927,269	37.00
Pennsylvania	2	765,318	29.77	2	860,916	34.35
New Jersey	3	489,808	19.05	3	415,510	16.58
Michigan	4	313,305	12.19	4	250,997	10.01
Montana, Oregon, New Mexico, and Utah	5	30,000	1.17	5	31,504	1.26
North Carolina	6	22,873	0.89	6	10,125	0.40
Virginia	7	4,463	0.17	7	6,200	0.25
Colorado				8	3,894	0.15
Maryland						
Total		2,570,838	100.00		2,506,415	100.00

States.	1880.			Increase or decrease in 1890 over 1889.	Percentage of increase or decrease in 1890 over 1889.	Increase or decrease in 1890 over 1880.	Percentage of increase or decrease in 1890 over 1880.
	Rank.	Production.	Percentage of total.				
		<i>Long tons.</i>		<i>Long tons.</i>		<i>Long tons.</i>	
New York	1	827,725	38.78	+ 17,802	+ 1.92	+ 117,346	+ 14.18
Pennsylvania	3	498,146	23.34	- 95,598	- 11.10	+ 267,172	+ 53.63
New Jersey	2	662,379	31.04	+ 74,298	+ 17.88	- 172,571	- 26.05
Michigan	4	132,785	6.22	+ 62,308	+ 24.82	+ 180,520	+ 135.95
Montana, Oregon, New Mexico, and Utah				- 1,504	- 4.77	+ 30,000	
North Carolina	6	2,501	0.12	+ 12,748	+ 125.91	+ 20,372	+ 814.56
Virginia	5	10,545	0.49	- 1,737	- 28.02	- 6,082	- 57.68
Colorado				- 3,894	- 100.00		
Maryland	7	195	0.01			- 195	- 100.00
Total		2,134,276	100.00	+ 64,423	+ 2.57	+ 436,562	+ 20.45

The following table shows the disfavor which has been exhibited to the use of carbonate ores, the only increase being in New York, where a large deposit, opened since 1880, has contributed to the supply, and in Kentucky, where a local demand has encouraged exploitations. Ohio shows a decided decline, greater in quantity, but proportionately less, than is exhibited by Pennsylvania and Maryland.

Production of carbonate ore by States in 1890, 1889, and 1880, with percentages of increase or decrease.

States.	1890.			1889.		
	Rank.	Production.	Percentage of total.	Rank.	Production.	Percentage of total.
		<i>Long tons.</i>			<i>Long tons.</i>	
Ohio	1	169,088	44.78	1	254,294	58.83
New York	2	81,319	21.53	2	65,456	15.14
Kentucky	3	62,000	16.42	3	52,275	12.09
Pennsylvania	4	36,780	9.74	4	39,806	9.21
West Virginia	5	16,116	4.27	6	9,101	2.11
Maryland	6	12,314	3.26	5	11,319	2.62
Alabama						
Total		377,617	100.00		432,251	100.00

Production of carbonate ore by States in 1890, 1889, and 1880, etc.—Continued.

States.	1880.			Increase or decrease in 1890 over 1889.	Percentage of increase or decrease in 1890 over 1889.	Increase or decrease in 1890 over 1880.	Percentage of increase or decrease in 1890 over 1880.
	Rank.	Production.	Percentage of total.				
		<i>Long tons.</i>		<i>Long tons.</i>		<i>Long tons.</i>	
Ohio	1	488,753	59.35	-85,206	-33.51	-319,665	- 65.40
New York				+15,863	+24.23	+ 81,319
Kentucky	5	42,096	5.11	+ 9,725	+18.60	+ 19,904	+ 47.28
Pennsylvania	2	176,227	21.40	- 3,026	- 7.60	-139,447	- 79.13
West Virginia	4	45,507	5.53	+ 7,015	+77.08	- 29,391	- 64.59
Maryland	3	65,743	7.98	+ 995	+ 8.79	-53,429	- 81.27
Alabama	6	5,145	0.63	- 5,145	-100.00
Total		823,471	100.00	-54,634	-12.64	-445,854	- 54.14

As carbonates must be roasted before being charged into the blast furnace, and as their occurrence is generally in thin but continuous seams, or in scattered pockets, the large territory which must be uncovered to secure a comparatively small tonnage makes the cost of the ore per unit of iron excessive, and where richer ores are available they displace the carbonates.

IMPORTATIONS OF IRON ORES.

The table below gives the quantities of iron ore in long tons imported into the United States, the value of such importations during the years 1889 and 1890, also the countries from which the ore was forwarded. The point of shipment reported is not necessarily in the country where the ore was mined, but an examination of the table gives no reason to credit any of the ore elsewhere than to the countries named in the table. The unusual values given to some of the smaller importations are owing to the ore having some especially valuable constituent in addition to the iron. The amount of iron ore imported in 1890 was considerably in excess of that of 1889, and the quantity brought into the country in 1890 was greater than in any previous year. Spain and Cuba supplied the bulk of the foreign ore in each year.

Imports of iron ore in 1889 and 1890 by countries.

Countries.	1889.		1890.	
	Quantity.	Value.	Quantity.	Value.
	<i>Long tons.</i>		<i>Long tons.</i>	
Spain	298,568	\$621,481	512,933	\$1,099,031
Cuba	243,255	535,524	351,814	778,895
French Africa	97,583	180,697	96,428	188,360
Italy	87,410	228,164	134,399	393,280
England	54,496	111,638	51,857	155,275
Greece	23,955	32,880	48,807	87,397
Newfoundland and Labrador	14,450	43,100	6,320	18,960
British Columbia	13,670	27,860
Portugal	6,659	15,151	16,526	36,941
France	6,565	17,911	2,404	5,647
Quebec, Ontario, Manitoba, and Northwest Territory	4,091	10,697	22,211	57,667
Turkey in Asia	2,870	27,265	3,078	32,345
Germany	1	24
Brazil	52	300
Mexico	1	20
Total	853,573	1,852,392	1,246,830	2,854,118

The figures in the foregoing table indicate that none of the States except Michigan, Alabama, Pennsylvania and New York contributed as much iron ore in 1890 as was imported, and this amount was only slightly less than the production of the latter State; that Spain supplied more ore to this country than the State of New Jersey, and somewhat less than Virginia; that Cuba's contribution was in excess of that of Georgia, occupying a middle position between the outputs of Georgia and Tennessee; that from Italy more ore was brought to this country than was furnished by Colorado; that Africa was credited with four-fifths of Colorado's output, and three times that of Massachusetts. The exportations of iron ore from England to this country equaled the outputs of Connecticut and West Virginia combined, while that of Greece exceeded the total of North Carolina and Texas.

The following table is a companion to that above, the quantities and values being divided in accordance with the ports of the United States at which the foreign iron ores were received.

Imports of iron ore by ports of entry in 1889 and 1890.

Ports.	1889.		1890.	
	Quantity.	Value.	Quantity.	Value.
	<i>Long tons.</i>		<i>Long tons.</i>	
Philadelphia, Pennsylvania	525, 124	\$1, 192, 141	683, 665	\$1, 641, 654
Baltimore, Maryland	273, 050	519, 736	481, 250	1, 015, 093
New York, New York	25, 824	72, 297	38, 717	101, 908
Puget Sound, Washington	13, 670	27, 860
Perth Amboy, New Jersey (a)	11, 558	26, 075	25, 524	50, 984
Oswego, New York	2, 309	6, 353	12, 617	23, 446
Cuyahoga, Ohio	1, 224	3, 403	4, 675	15, 460
Vermont district	462	707	239	258
Pensacola, Florida	135	608
Buffalo Creek, New York	78	198	82	185
San Francisco, California	61	2, 525	60	5, 110
Boston, Massachusetts	50	283
Detroit, Michigan	18	36
Chicago, Illinois	5	58
Pittsburg, Pennsylvania	4	88
St. Louis, Missouri	1	24
San Diego, California	1	20
Total	853, 573	1, 852, 392	1, 246, 830	2, 854, 118

a This port may also be classed under the head of ports of New York Harbor.

The above table shows that one-half as much foreign iron ore was received at Philadelphia in 1890 as the State of Pennsylvania produced, and the imported ore received at Baltimore was nearly 80 per cent of the combined outputs of the mines of Maryland, West Virginia, and Virginia in the same year.

As a further illustration, a table is given showing a summary of the ports of entry by groups.

Receipts of foreign iron ore, by groups of ports.

Ports.	1889.		1890.	
	Quantity.	Value.	Quantity.	Value.
	<i>Long tons.</i>		<i>Long tons.</i>	
Atlantic	835,741	\$1,811,140	1,241,773	\$2,833,085
Lake	3,634	10,048	4,737	15,645
Pacific	13,731	30,385	61	5,130
Miscellaneous	467	819	239	258
Total	853,573	1,852,392	1,246,830	2,854,118

The above table emphasizes the fact that the amount of foreign iron ore received at Atlantic ports was very close to the output of domestic iron ores in New York State, and nearly 90 per cent of the quantity produced in all of the Atlantic States, excepting New York and Pennsylvania.

In "Mineral Resources of the United States, 1886," pp. 99 and 100, there appears a statement showing the quantities of pig iron produced in various prominent countries, in connection with the amounts of foreign iron ores consumed in these countries, to illustrate the apparent average consumption of foreign iron ores used per ton of pig iron made. This statement, as far as it relates to the United States, is here repeated and brought down to date.

Relation between the foreign iron ore imported into, and the pig iron made in, the United States.

Years.	Pig iron made.	Iron ore imported.	Average amount of ore imported per ton of iron produced.
	<i>Long tons.</i>	<i>Long tons.</i>	
1879	2,741,853	284,141	.104
1880	3,835,191	493,408	.129
1881	4,144,254	782,887	.189
1882	4,623,323	589,655	.128
1883	4,595,510	490,875	.107
1884	4,097,868	487,820	.109
1885	4,004,526	390,786	.086
1886	5,683,329	1,039,433	.183
1887	6,417,418	1,194,301	.183
1888	6,489,738	587,470	.091
1889	7,603,642	853,573	.112
1890	9,202,703	1,246,830	.135
Total	63,430,355	8,441,179
Average for twelve years	5,286,613	703,432	.133

CONCENTRATION OF IRON ORES.

Since the contribution upon the subject of iron ores was prepared for the 1887 volume of Mineral Resources, a lively interest has been exhibited in the concentration of magnetic iron ores by means of magnetic separators. That the process is not novel is evident from the numerous patents (some of them half a century old) which have been issued for magnetic separators and from the record of operations with

these appliances. The revival of interest in the concentration of lean magnetic iron ores is fortunately at a time when improvements in machinery for reducing in size and handling large quantities of material are supplemented by advanced knowledge of electro-magnetic appliances. The extent to which the process can be applied commercially to many ores can be decided only after a thorough investigation embracing the chemical and physical characteristics of the ore, the quantity accessible, the facilities for obtaining it, and the available market for the concentrated ore.

This method of beneficiating iron ores is confined to magnetite and such ores as can be made sufficiently magnetic to permit of their concentration by the appliances mentioned. No effort on a commercial scale has been made to treat any but ores which are naturally strongly magnetic, and most of the work done has been in enriching lean magnetite, although some ores carrying high percentages of iron have been fed to magnetic separators for the purpose of reducing the amount of phosphorus and sulphur. The predominance of magnetic iron ore in New York and New Jersey and the existence of large deposits of this class of ore in Pennsylvania and North Carolina have naturally attracted to these States most of the development in concentrating plants.

There is no question that the amounts of sulphur, phosphorus, silica, and in some cases titanium existing in magnetites can be considerably reduced if the material is sized and passed through magnetic separators, the degree of perfection reached being influenced by such reduction in size as will actually permit the mechanical separation of the pure magnetite from the other ingredients. In some of the titaniferous iron ores this element is so combined as to be magnetic also, and similarly the sulphur in other ores is in such combination as to make it partially magnetic. It may be possible, with improved machinery and greater knowledge, to separate various materials from each other, which differ but slightly in magnetism, but present practice is confined to separating magnetic from non-magnetic material, and the results achieved depend largely upon the comminution of the material, the rapidity with which it is fed on the separator, and the perfection of the machine.

COMPOSITION OF IRON ORE FROM IRON MOUNTAIN, MISSOURI.

Prof. W. B. Potter, of the Washington University, St. Louis, has contributed a complete suite of analyses of ore taken from the Iron Mountain mine, Missouri, during the year 1889. These determinations aggregate a total of 338, and from them the following statements of maxima, minima, and averages of the phosphorus, iron, and silica in the ore have been prepared for each class of ore described in the list by Prof. Potter as having been mined from the Iron Mountain deposit. The statements are offered as of special interest in showing the variations of composition of ores in one deposit.

Composition of iron ore from Iron Mountain, Missouri.

Kind of ore.	No. of samples.	Iron.		Phosphorus.			Silica.	
		Range.	Average.	Range.	Average.	Range.	Average.	
Surface:		<i>Per cent.</i>	<i>Per ct.</i>	<i>Per cent.</i>	<i>Per ct.</i>	<i>Per cent.</i>	<i>Per ct.</i>	
Lump	3	67.31 to 67.76	67.51	0.026 to 0.040	0.031	2.34 to 2.94	2.69	
Jigged	13	63.16 65.30	64.21	0.013 0.044	0.033	4.21 5.79	5.16	
Number 1 bluff:								
From Southern mine..	37	62.78 67.15	65.59	0.034 0.209	0.113	2.82 7.91	4.41	
From Shaft No. 11 (taken from dump)....	14	58.98 63.40	61.46	0.006 0.064	0.023	5.72 9.50	7.47	
Southeast mine.....	8	64.26 65.72	64.99	0.020 0.083	0.042	4.1 5.57	5.09	
From dump	3	65.14 65.55	65.31	0.033 0.068	0.048	4.98 5.26	5.13	
Select ore.....	2	67.16 67.47	67.31	0.015 0.020	0.017	2.58 2.95	2.76	
Special ore (a).....	20	62.76 64.82	63.74	0.010 0.055	0.018	4.80 7.12	5.96	
Furnace jigged ore.....	48	59.17 64.80	61.91	0.025 0.208	0.105	4.22 10.54	6.90	
Special from Little Mountain:								
Taken from mine (b)	4	63.39 64.63	63.81	0.013 0.018	0.016	4.83 6.69	5.45	
Taken from dump....	3	63.63 64.25	64.02	0.002 0.009	0.004	5.96 6.48	6.26	
Soft lump ore:								
From incline No. 1—								
Taken from dump	8	60.50 62.71	61.87	0.072 0.191	0.124	5.90 9.45	7.60	
From incline No. 2...	7	65.17 65.91	65.52	0.052 0.114	0.085	1.99 3.64	2.61	
Taken from dump	10	64.06 66.04	64.98	0.044 0.125	0.075	2.32 3.78	2.90	
From shaft No. 1 (c) ..	54	64.31 66.57	65.46	0.011 0.047	0.025	2.06 5.02	3.69	
Soft jigged ore:								
From incline No. 1—								
Taken from dump	12	60.88 63.47	61.92	0.054 0.093	0.077	4.98 7.68	5.86	
From incline No. 2 ...	22	62.23 64.70	63.31	0.044 0.148	0.065	3.76 5.63	4.78	
Taken from dump	17	60.87 64.23	62.71	0.023 0.104	0.057	4.06 6.23	5.08	
From separator No. 5 (d).....	52	55.32 63.99	61.37	0.019 0.065	0.040	4.27 13.59	6.62	

a One analysis of this ore showed 0.117 per cent. of manganese and another 1.02 per cent. of lime.

b This ore showed from 0.261 per cent. to 0.320 per cent. of manganese, with an average of 0.282 per cent.

c Two analyses of this ore show lime from 0.571 per cent. to 0.628 per cent., with an average of 0.599 per cent.; one shows sulphur 0.012 per cent.; one manganese 0.206 per cent.; and one 3.04 per cent. of alumina.

d Three samples of this ore show lime ranging from 0.685 per cent. to 0.838 per cent., with an average of 0.743 per cent.; two samples of this ore show alumina ranging from 3.03 per cent. to 3.11 per cent., with an average of 3.07 per cent.; one sample showed 0.023 per cent. of sulphur.

GOLD AND SILVER.

BY WILLIAM KENT.

Early in the year 1890 the annual report of the Director of the Mint was published on the production of the precious metals in the United States during the calendar year 1889, in which he gave, according to the usual custom in these annual reports, his estimates of the production of gold and silver in the several States and Territories. These estimates are based upon the figures reported to the Director by private refineries, upon deposits of refined and unrefined metal at the several mints and assay offices, upon returns from the custom-houses of the precious metals exported and imported, and to some extent upon the estimates made by mint officers and agents in the several producing States and Territories.

A direct investigation of the product of the gold and silver mines in 1889 was made in 1890 for the Eleventh Census of the United States by Mr. R. P. Rothwell, special agent of the Census Office, in charge of the statistics of gold and silver mines, with whom the writer was associated as principal assistant. The work was begun in the latter part of 1889 by obtaining from all available sources a directory of producing mines, and early in 1890 the collection of schedule statistics was undertaken, both by the use of the mails and by the efforts of numerous special agents in the field, several of whom were also agents of the mint.

The methods of collection and of compilation adopted by the Census Office are given in detail in the report of the special agent and need not be described here, but it is sufficient to say that the results reached are unquestionably more accurate, as might have been expected from the facilities availed of, than the figures of any previous census or mint report. The difference between the mint and census figures is but trifling in the case of gold, but it is considerable in the case of silver, both as regards the total product and as regards the distribution among the States and Territories. Thus the total product of silver according to the mint (United States coinage value) was \$64,646,000 and according to the census \$66,396,988. The product of Colorado according to the mint was \$20,686,868 and according to the census \$23,757,751, a difference of over \$3,000,000. For the reasons above given the figures of the census are adopted here for the production of gold and silver in 1889. For

the year 1890 the Annual Report of the Director of the Mint on the Production of the Precious Metals in the United States, published early in 1891, is taken as authoritative.

The following table shows the production of gold and silver in the years 1889 and 1890 by States. The production of silver is given both in ounces and in dollars, United States coining value \$1.2929 per ounce.

Production of gold and silver in the United States in 1889 and 1890.

States.	Gold.		Silver.			
	Eleventh Census.	U. S. Mint.	Fine ounces.		United States coining value.	
			1889.	1890.	1889.	1890.
Alabama.....	\$2, 539	77	\$100
Alaska.....	904, 650	\$762, 500	9, 219	7, 500	11, 918	\$9, 697
Arizona.....	910, 174	1, 000, 000	1, 812, 961	1, 000, 000	2, 343, 977	1, 292, 929
California.....	12, 586, 722	12, 500, 000	1, 062, 578	900, 000	1, 373, 807	1, 163, 636
Colorado.....	3, 883, 859	4, 150, 000	18, 375, 551	18, 800, 000	23, 757, 751	24, 307, 070
Georgia.....	107, 605	100, 000	359	400	464	517
Idaho.....	1, 984, 159	1, 850, 000	3, 137, 508	3, 700, 000	4, 056, 482	4, 783, 838
Maryland.....	10, 369
Michigan.....	87, 040	90, 000	14, 607	55, 000	18, 885	71, 111
Montana.....	3, 139, 327	3, 300, 000	13, 511, 455	15, 750, 000	17, 468, 960	20, 363, 636
Nevada.....	3, 506, 295	2, 800, 000	4, 696, 605	4, 450, 000	6, 072, 241	5, 753, 535
New Mexico.....	815, 655	850, 000	1, 251, 124	1, 300, 000	1, 617, 578	1, 680, 808
North Carolina.....	146, 795	118, 500	3, 000	6, 000	3, 879	7, 757
Oregon.....	964, 309	1, 100, 000	17, 851	75, 000	23, 382	96, 969
South Carolina.....	46, 853	100, 000	179	400	232	517
South Dakota.....	3, 091, 137	3, 200, 000	104, 672	100, 000	135, 331	129, 292
Texas.....	6, 823	323, 438	300, 000	413, 173	387, 878
Utah.....	487, 666	680, 000	7, 005, 193	8, 000, 000	9, 057, 014	10, 343, 434
Virginia.....	4, 100	10	13
Washington.....	186, 150	204, 000	28, 464	70, 000	36, 801	90, 505
Wyoming.....	14, 512
Other States.....	40, 000	2, 000	2, 585
Total.....	32, 886, 744	32, 845, 000	51, 354, 851	54, 516, 300	66, 396, 983	70, 485, 714

The number of mines from which statistics were obtained by the census and reported either as producing in 1889 or as doing development work, but not producing, or as temporarily stopped, but likely to produce in the near future, was 6,004. Besides this there were some thousands of small diggings, placers, washings, gulches, claims, locations, etc., which could not be classed as mines. The relative importance of the 6,004 mines is shown in the following table:

Relative importance of producing mines.

	Number.
Mines reported producing less than \$1,000 bullion.....	1, 610
From \$1,000 to \$10,000.....	1, 408
From \$10,000 to \$50,000.....	437
From \$50,000 to \$100,000.....	95
From \$100,000 to \$250,000.....	107
From \$250,000 to \$500,000.....	44
Over \$500,000.....	28
Total.....	3, 729
Mines reported working, but not producing bullion.....	1, 009
Mines reported idle.....	1, 266
Total number of mines reported.....	6, 004

The average earnings of all persons employed at the gold and silver mines from which returns were received or estimates made (57,635) was \$725 a year, while the average output per man amounted to \$1,723 a year.

The average daily rate of wages paid was as follows:

Rates of wages paid employés per day in gold and silver mines in 1889.

	Above ground.	Below ground.
Foremen.....	\$4. 21	\$4. 21
Mechanics.....	3. 57	3. 13
Miners.....		3. 13
Laborers.....	2. 65	2. 47

The production of gold in California continues to show a decrease. The production in 1870, according to the estimates of the Director of the Mint, was \$25,000,000 and in 1877 only \$15,000,000. It increased in the next four years to \$18,200,000 in 1881, and then decreased somewhat irregularly to \$12,586,722 in 1889, according to the census returns, and to \$12,500,000 in 1890, as estimated by the Director of the Mint. The prohibition of hydraulic mining in California is the chief cause of the decrease in recent years. California still, however, produces more than three times as much gold as any other State and about two-fifths of the total production of the country. The four other leading gold-producing States, Colorado, Nevada, South Dakota, and Montana, have remained in approximately the same relative positions during the past ten years, each producing between \$3,000,000 and \$4,000,000 in the census year. Idaho comes next in the order of producing States, with nearly \$2,000,000 in the census year. No other State produced in that year as much as \$1,000,000.

As to silver, remarkable variations in the production of the several States have taken place in the past ten years. Nevada, which in 1878, according to the Director of the Mint, produced over \$28,000,000 worth of silver, now produces less than \$6,000,000 (United States coining value), while Montana, which produced \$2,500,000 in 1880, produced over \$17,000,000 in 1889, according to the census, and over \$20,000,000 in 1890, according to the mint report. Colorado, whose production increased from \$4,500,000 in 1877 to \$17,000,000 in 1880, has still further increased its production to \$23,757,751 in the census year, and over \$24,000,000 in 1890, thus retaining the first place in silver production, which it has held since 1880. Utah has about doubled its production since 1880 reaching \$9,000,000 in 1889, according to the census, and over \$10,000,000 in 1890, according to the mint report. Idaho is fifth in the list of silver States, having increased in production from \$450,000 in 1880 to \$4,783,000 in 1890. Arizona appears to be rapidly decreasing in importance as a silver-producing State, its product being reported in 1882 as \$7,500,000 (which, however, is probably a gross exaggeration),

and only \$2,343,977 in 1889 by the census, and \$1,292,929 in 1890 by the Director of the Mint. New Mexico also is declining in importance, the product decreasing from \$3,000,000 in 1885 to \$1,680,000 in 1890. California also has decreased from \$3,000,000 in 1884 to \$1,373,807 in 1889, and to \$1,163,636 in 1890. The silver product of other States than those mentioned is comparatively insignificant.

The following table shows the latest estimates of the product of gold and silver in the United States since 1792:

Product of gold and silver in the United States from 1792.

[The estimate for 1792-1873 is by Dr. R. W. Raymond, United States Mining Commissioner, and since by the Director of the Mint.]

Years.	Total.	Gold.	Silver.
April 2, 1792-July 31, 1834	\$14,000,000	\$14,000,000	(a)
July 31, 1834-Dec. 31, 1844	7,750,000	7,500,000	\$250,000
1845	1,058,327	1,008,327	50,000
1846	1,189,357	1,139,357	50,000
1847	939,085	889,085	50,000
1848	10,050,000	10,000,000	50,000
1849	40,050,000	40,000,000	50,000
1850	50,050,000	50,000,000	50,000
1851	55,050,000	55,000,000	50,000
1852	60,050,000	60,000,000	50,000
1853	65,050,000	65,000,000	50,000
1854	60,050,000	60,000,000	50,000
1855	55,050,000	55,000,000	50,000
1856	55,050,000	55,000,000	50,000
1857	55,050,000	55,000,000	50,000
1858	50,500,000	50,000,000	500,000
1859	50,100,000	50,000,000	100,000
1860	46,150,000	46,000,000	150,000
1861	45,000,000	43,000,000	2,000,000
1862	43,700,000	39,200,000	4,500,000
1863	48,500,000	40,000,000	8,500,000
1864	57,100,000	46,100,000	11,000,000
1865	64,475,000	53,225,000	11,250,000
1866	63,500,000	53,500,000	10,000,000
1867	65,225,000	51,725,000	13,500,000
1868	60,000,000	48,000,000	12,000,000
1869	61,500,000	49,500,000	12,000,000
1870	66,000,000	50,000,000	16,000,000
1871	66,500,000	43,500,000	23,000,000
1872	64,750,000	36,000,000	28,750,000
1873	71,750,000	36,000,000	35,750,000
1874	70,800,000	33,500,000	37,300,000
1875	65,100,000	33,400,000	31,700,000
1876	78,700,000	39,900,000	38,800,000
1877	86,700,000	46,900,000	39,800,000
1878	96,400,000	51,200,000	45,200,000
1879	79,700,000	38,900,000	40,800,000
1880	75,200,000	36,000,000	39,200,000
1881	77,700,000	34,700,000	43,000,000
1882	79,300,000	32,500,000	46,800,000
1883	76,200,000	30,000,000	46,200,000
1884	79,600,000	30,800,000	48,800,000
1885	83,400,000	31,800,000	51,600,000
1886	86,000,000	35,000,000	51,000,000
1887	86,350,000	33,000,000	53,350,000
1888	92,370,000	35,175,000	59,195,000
1889 { mint.....	97,446,000	32,800,000	64,646,000
{ census.....	99,282,866	32,886,180	66,396,686
1890	103,330,714	32,845,000	70,485,714
Total (b)	2,869,483,483	1,871,706,769	997,776,714

a Insignificant.

b In the total the mint figures, and not the census, are included.

WORLD'S PRODUCTION OF GOLD AND SILVER.


The writer, in the course of his work on the Eleventh Census of gold and silver for the calendar year 1889, made a study of the various published statistics of the gold and silver production of the world from 1850 to 1889. The results of this study are published at length in the census report. A comparison of the various published figures showed that there is a probability that the best tables hitherto published are far from being accurate, and it is a matter of considerable difficulty to decide which of two conflicting sets of figures for any one year have the greater probability of an approach to accuracy. Dr. Soetbeer, the eminent German authority on statistics of the precious metals, writes as follows on this question:

“The longer and more zealously a conscientious investigator busies himself with the statistics of the production and employment of the precious metals, the more will he be convinced that, with some exceptions, the numerical results obtainable relating to such production and employment are of a very uncertain nature; that they possess only the character of a greater or less approach to the reality, and of greater or less probability that the round numbers laid before the student deserve confidence, because apparently most carefully calculated on positive data, and that a continual revision of the estimates seems desirable.”

WORLD'S PRODUCTION OF GOLD AND SILVER.

1849 — 1889.

According to different authorities.

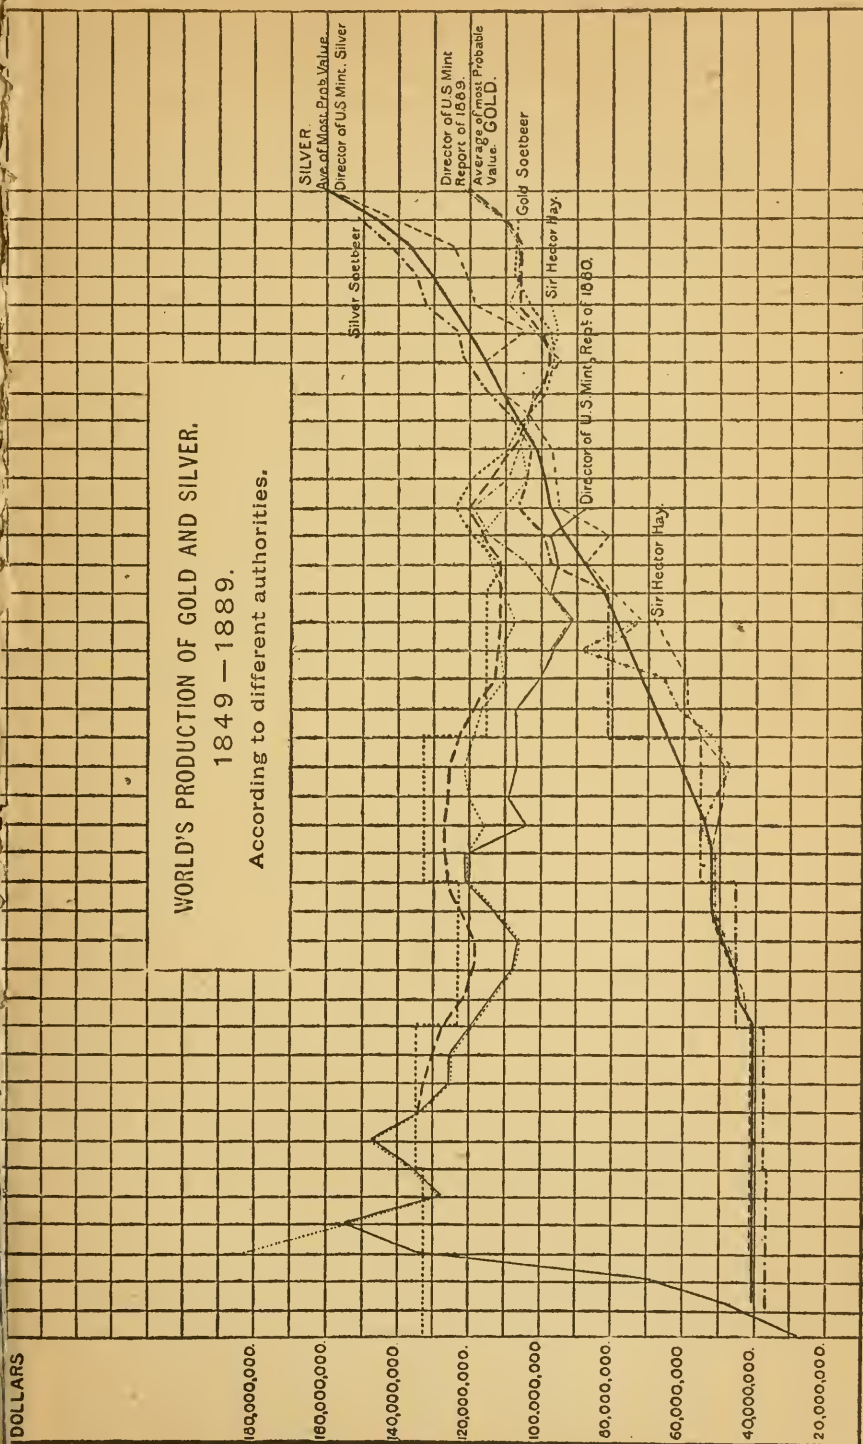

By taking the figures of the several authorities and plotting them in the form of a diagram, and studying with particular care those portions where the authorities showed a wide divergence in their figures, a curve of "most probable values" of production of gold and silver was obtained, from which the figures given in the following table were taken.

The bottom line in the table below is not in the census report, but is added from the figures given in the report of the Director of the Mint.

Most probable values of the world's production of gold and silver—price of silver, and ratio of gold to silver.

Years.	Production. (a) (Value in millions of dollars.)			Percentage of total.		Price of silver in London. (Pence per ounce standard.)	Value of silver per fine ounce.	Price ratio 1 ounce gold. (Ounces silver.)
	Total gold and silver.	United States coining value.		Gold.	Silver.			
		Gold.	Silver.					
1850 to 1855	172	132	40	76.7	23.3	61½	\$1.337	15.42
1856	174	134	40	77.0	23.0	61⅞	1.344	15.34
1857	174	134	40	77.0	23.0	61¾	1.353	15.27
1858	173	133	40	76.9	23.1	61⅞	1.344	15.36
1859	170	130	40	76.5	23.5	62⅞	1.360	15.21
1860	167	127	40	76.0	24.0	61½	1.352	15.30
1861	167	122	45	73.1	26.9	60⅞	1.333	15.48
1862	165	119	46	72.1	27.9	61⅞	1.346	15.36
1863	168	119	49	70.8	29.2	61⅞	1.345	15.38
1864	174	122	52	70.1	29.9	61⅞	1.345	15.39
1865	178	126	52	70.8	29.2	61⅞	1.338	15.43
1866	179	127	52	70.9	29.1	61⅞	1.339	15.44
1867	181	127	54	70.2	29.8	60⅞	1.328	15.57
1868	183	126	57	68.9	31.1	60½	1.326	15.61
1869	186	125	61	67.2	32.8	60⅞	1.325	15.60
1870	187	123	64	65.8	34.2	60⅞	1.328	15.60
1871	187	119	68	63.6	36.4	60½	1.326	15.58
1872	184	113	71	61.4	38.6	60⅞	1.322	15.64
1873	187	112	75	59.9	40.1	59½	1.298	15.93
1874	190	111	79	58.4	41.6	58⅞	1.278	16.16
1875	193	111	82	57.5	42.5	56½	1.246	16.63
1876	199	111	88	55.8	44.2	52½	1.156	17.80
1877	209	116	93	55.5	44.5	54½	1.201	17.19
1878	217	120	97	55.3	44.7	52⅞	1.152	17.96
1879	213	114	99	53.5	46.5	51½	1.123	18.39
1880	209	108	101	51.7	48.3	52½	1.145	18.06
1881	210	104	106	49.5	50.5	51⅞	1.138	18.24
1882	211	100	111	47.4	52.6	51⅞	1.136	18.27
1883	212	97	115	45.8	54.2	50½	1.110	18.65
1884	220	100	120	45.5	54.5	50½	1.113	18.63
1885	231	106	125	45.9	54.1	48⅞	1.065	19.39
1886	236	106	130	44.9	55.1	45⅞	C.995	20.78
1887	242	106	136	43.8	56.2	44⅞	0.978	21.13
1888	256	110	146	43.0	57.0	42⅞	0.939	21.99
1889	279	120	159	43.0	57.0	42⅞	0.935	22.09
1890	289	118	171	40.8	59.2	47½	1.053

a The figures of production are the "most probable values" arrived at from a comparison of the tables of Soetbeer, the Director of the Mint, and Sir Hector Hay. The price of silver is taken from the report of the Director of the Mint for 1889. The price ratio is from Soetbeer's tables down to 1885, and from 1886 to 1889 is calculated from the London price.

A study of the preceding table of the world's annual production of gold and silver, and the price of silver from 1850 to 1889, shows that the world's gold production from 1850 to 1857 remained nearly constant at about \$134,000,000; then decreased irregularly till 1883, reaching a minimum of \$97,000,000; then increased irregularly to 1889, when the product was \$120,000,000. The silver production remained nearly constant from 1850 to 1860 at above \$40,000,000, increasing slowly to 1866

to \$52,000,000; then increased steadily and rapidly to 1887, and still more rapidly in 1888 and 1889 to \$159,000,000.

The ratio of total value of silver product (at United States coining value) to that of the total of both gold and silver remained nearly constant, about 24 per cent, until 1860, increasing irregularly to 30 per cent in 1867, then steadily to 57 per cent in 1889, becoming equal to gold, or 50 per cent, in 1881. Thus both the production of silver and the ratio of silver production to total of silver and gold had a period of slow increase from 1860 to 1867, and then a rapid increase, beginning in 1867 and lasting to the present time. The price of silver remained nearly constant (at over 60 pence per ounce standard in London, equal to over \$1.32 per ounce fine) until 1872, being unaffected either by the decrease in the gold production or by the increase in silver production. In 1872 the rapid decrease in gold production, which had taken place for four years previously was arrested, and for the next four years the decrease was very slight, and in the ten years following a considerable increase took place. At this time (1872) no change took place in the rate of increase of silver production, this rate being nearly the same from 1867 to 1877; yet in 1873 began the decrease in price of silver, which has continued with but slight fluctuations to the present time. During the twenty-three years (1850 to 1872) the whole extent of the variation in price was only between \$1.36 and \$1.32 per ounce, or 3.8 cents, while in the seventeen years, 1872 to 1889, inclusive, it declined from \$1.322 to \$0.935, or 38.7 cents, or over 26 per cent.

The table does not reveal the cause of the decline in the price of silver, for if it be assumed that the ratio of the production of silver to that of gold controls the price of the former, then the decrease in the price should have begun in 1860, when the ratio of silver product began to increase, and the decrease would have been more pronounced in 1867, when the silver product increased more rapidly and the gold production decreased. There is nothing in the figures or in the diagram to explain why the decline began in 1873 instead of in 1860 or 1867. A study of Soetbeer's figures for 380 years, from 1493 to 1873, will also show no relation between the relative production of gold and silver, and from 1800 to 1870, although the value of the product of the two metals varied from 3.227 silver to 1 of gold down to 0.44 silver to 1 of gold, the relative price varied only between 15.41 and 15.83 to 1. From the year 1873 to the present time, however, there appears to be a very close agreement between the product ratio and the price ratio, as shown by the coincidence between the columns in the table representing "gold production, per cent of total gold and silver," and price of silver in pence in London. Thus, in 1873 the total value of the gold product, expressed as a percentage of the total of the gold and silver, was 59.9 per cent, and in 1889 it was 43 per cent; the price of silver in London in 1873 was 59 $\frac{1}{4}$ pence, and in 1889, 42 $\frac{1}{8}$ pence.

COPPER.

BY C. KIRCHHOFF.

The distrust and doubt following the collapse of the French syndicate in 1889 brought about a rapid and continuous decline until $10\frac{1}{2}$ cents a pound was touched for lake copper. It became evident, however, that consumers who had been starving themselves during the period of artificially high prices were liberal purchasers, and that the stock in the bankers' control was being handled cautiously and judiciously. Probably the most striking source of purchases of copper was that for electrical purposes, the development of electric lighting and traction having been phenomenal on both sides of the Atlantic. The metal began to recover in the fall of 1889, and maintained a level which made the year 1890 a profitable one. Considering the severe strain upon it during the progress and the collapse of the French syndicate, the American copper industry has developed well. During the two years under review no discoveries have been made of such magnitude as to influence the supply materially, nor has there been any permanent curtailment of product through the exhaustion of deposits which have been actively worked for some time past.

The publication of the report of the census, which covers the calendar year 1889, furnishes some interesting data, which may be referred to, since efforts have been made to deliberately misrepresent the figures and their teachings. The returns show that the cost of mining ore, which finally yielded 220,569,438 pounds fine, was \$12,062,180, or 5.47 cents per pound, the cost being \$3.63 per ton of copper ore. The following table deals with the mining cost in the three principal districts:

Mining cost of copper.

States.	Yield fine copper.	Cost per pound copper.	Cost per ton of ore.	Labor cost per pound copper.(a)
	<i>Per cent.</i>	<i>Cents.</i>		<i>Cents.</i>
Michigan	1.797	8.55	\$3.07	3.63
Montana	7.002	3.27	4.59	2.05
Arizona	10.079	3.66	7.37	2.32

a Exclusive of amounts paid office force and contractors.

This table seems to indicate a high cost of production on the part of the Lake Superior mines, but it must not be forgotten that the outlays for the separation of the copper vary very widely in the different regions. In Michigan cheap crushing and washing leads at once to a high-grade

product, yielding on the average 74.24 per cent. of ingot. The cost of crushing and washing during the census year averaged only 0.59 cent per pound. The cost of refining, of shipment to market, and of marketing is low. A guide to the magnitude of these expenditures is furnished by the annual report of a number of the companies. Mines whose total product was 42,977,065 pounds in the year 1889 gave expenditures aggregating \$686,663.48 for smelting, freight, brokerage, insurance, and taxes, the rate being 1.60 cents per pound. These data indicate that the cost of copper, delivered and sold, including outlays for betterments in the majority of cases, was 10.74 cents per pound.

For the Montana mines the cost of mining the copper rock is only a small part of the cost of production. The census report shows that the cost of concentrating and smelting was 6.16 cents per pound, nearly 90 per cent. of the product being in the form of matte, while the balance is blister copper. This must be shipped either to American or to foreign refiners, the cost of treatment being very considerably higher. The census investigation did not deal with the question of the cost of shipment of matte, nor could the cost of refining it be arrived at, since the reports of the refiners embrace the cost of treating other material. There must therefore be added to the cost of the fine copper in the matte or blister, on cars at the Montana smelting works, which averages 9.43 cents, the cost of shipment and of refining. It is probable that this carried the total to at least 11 cents per pound, from which must be deducted the value of the silver in the case of those companies which mine argentiferous ores, and the profit on the precious metal in the case of those works which purchase silver ores in the open market. Considering the advantage which the lake mines have as sellers of a higher grade of copper, even over the Montana producers who market their metal as electrolytic, the balance still rests in favor of the Michigan companies.

The Arizona mines produce at relatively low cost. According to the census report, the cost of concentrating and smelting the ores was 4.01 cents, which would carry the cost of copper in the blister and matte, at furnace in Arizona, to 7.67 cents. To this, too, the cost of transportation to the refinery, the cost of refining, and of marketing must be added, and allowance be made for silver in the case of one company. The quality of product is good, so that the Arizona mines possess the ability to meet a 10-cent copper market without loss.

On the cost of refining, the census report covers establishments producing a total of 159,693,252 pounds of refined copper. The average was 1.18 cents per pound. The report, however, segregates one group of refiners which treat exclusively high grade material like lake mineral, Arizona bars, and Montana blister copper. On a total product of 105,400,664 pounds, the average cost was 0.68 cent per pound. By deduction it appears that the 54,292,588 pounds produced from other grades of raw material cost 2.15 cents per pound.

The refining facilities are being largely increased in this country. The Baltimore works have nearly completed a new plant, the Calumet & Hecla Company is building works at Black Rock, New York, the Kansas City Smelting and Refining Company has started a new plant, and the Omaha & Grant Smelting and Refining Company has begun a copper refinery. In Colorado the Pueblo Smelting and Refining Company and the St. Helen's Smelting Company are handling cupriferous material. It is probable, therefore, that soon the American refiners will be in a position to handle all the copper produced in this country, so that our exports will consist more and more of ingot and less of matte.

DOMESTIC PRODUCTION.

The following table, showing the growth in the production of copper in the United States, is compiled, as far as the years previous to 1882 are concerned, from the best data available. Since that year the statistics are those collected by this office, with the exception of the year 1889, when the figures were gathered by the Census Office. It should be stated that the yield of copper from pyrites is not here included.

Product of copper in the United States from 1845 to 1890, inclusive.

Years.	Total production.	Lake Superior.	Calumet and Hecla.	Percentage of Lake Superior of total product.	Years.	Total production.	Lake Superior.	Calumet and Hecla.	Percentage of Lake Superior of total product.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>			<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	
1845...	100	12	12.0	1868...	11,600	9,346	2,276	80.6
1846...	150	26	17.3	1869...	12,500	11,886	5,497	95.1
1847...	300	213	71.0	1870...	12,600	10,992	6,277	87.2
1848...	500	461	92.2	1871...	13,000	11,942	7,242	91.9
1849...	700	672	96.0	1872...	12,500	10,961	7,215	87.7
1850...	650	572	88.0	1873...	15,500	13,433	8,414	86.7
1851...	900	779	86.6	1874...	17,500	15,327	8,984	87.0
1852...	1,100	792	72.0	1875...	18,000	16,089	9,586	89.4
1853...	2,000	1,297	64.9	1876...	19,000	17,085	9,683	89.9
1854...	2,250	1,819	80.8	1877...	21,000	17,422	10,075	83.0
1855...	3,000	2,593	86.4	1878...	21,500	17,719	11,272	82.4
1856...	4,000	3,666	91.7	1879...	23,000	19,129	11,728	83.2
1857...	4,800	4,255	88.6	1880...	27,000	22,204	14,140	82.2
1858...	5,500	4,088	74.3	1881...	32,000	24,363	14,000	76.1
1859...	6,300	3,985	63.3	1882...	40,467	25,439	14,209	62.9
1860...	7,200	5,388	74.8	1883...	51,574	20,653	14,788	51.6
1861...	7,500	6,713	89.5	1884...	64,708	30,961	18,069	47.8
1862...	9,000	6,065	67.4	1885...	74,052	32,209	21,093	45.5
1863...	8,500	5,797	68.2	1886...	70,430	36,124	22,553	51.3
1864...	8,000	5,576	69.7	1887...	81,017	33,941	20,543	41.9
1865...	8,500	6,410	75.4	1888...	101,054	38,604	22,453	38.2
1866...	8,900	6,138	69.0	1889...	100,918	39,043	21,727	38.7
1867...	10,000	7,824	003	78.2	1890...	115,669	44,976	26,727	38.9

It is a striking fact that the Lake Superior district in 1890 made more copper than was produced in the whole country in 1882. The returns for 1890 reflect the influence of good prices, but it may be stated in a general way that the output has now reached figures which are not likely to be much exceeded in the near future. While a number of the large mines are making preparations for working on a larger scale, others will find increasing difficulties in maintaining their best rate of

output. There have been no discoveries which give promise of suddenly flooding the markets, the only new district of promise being the "Seven Devils" district in Idaho. A noteworthy feature is the opening out of cupriferous bodies in the lower levels of some of the Leadville mines.

The following is, in detail, the output of the Lake Superior mines, as reported by the companies:

Product of Lake Superior copper mines, 1884 to 1890.

Mines.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>
Calumet and Hecla.....	40,473,585	47,247,990	50,518,222	46,016,123	50,295,720	48,668,296	59,868,106
Quincy.....	5,650,436	5,848,530	5,888,517	5,603,691	6,367,809	6,405,686	8,064,253
Osceola.....	4,247,630	1,945,208	3,560,786	3,574,972	4,134,320	4,534,127	5,294,792
Franklin.....	3,748,652	4,007,106	4,264,297	3,915,838	3,655,751	4,346,062	5,638,112
Allouez.....	1,928,174	2,170,476	1,725,463	885,010	314,198	1,762,816	1,407,828
Atlantic.....	3,163,585	3,582,633	3,503,670	3,641,865	3,974,972	3,698,837	3,619,972
Pewabic.....	227,834						
Central.....	1,446,747	2,157,408	2,512,886	2,199,133	1,817,023	1,270,592	1,413,391
Grand Portage.....	255,860						
Conglomerate.....	1,198,691						
Mass.....	481,396	363,500	247,179			58,349	62,187
Copper Falls.....	891,168	1,150,538	1,378,679	719,150	1,199,950	720,000	665,000
Phenix.....	631,004	344,355	1,101,804	11,000			
Hancock.....	562,636	203,037	150,000				
Huron.....	1,927,660	2,271,163	1,992,695	1,881,760	2,370,857	2,219,473	1,736,777
Ridge.....	74,030	63,390	158,272	84,902	50,924	28,000	21,569
Saint Clair.....	139,407						
Cliff.....	28,225		22,342				
Wolverine.....	751,763	328,610	3,125	2,300			
Nonesuch.....	23,867	28,484					
Isle Royale.....	16,074						
National.....	87,368	162,252	184,706	25,187		454,134	123,879
Minnesota.....	1,144	12,608					
Belt.....	130,851	27,433	7,300				
Sheldon and Colum- bia.....	9,828						
Adventure.....	4,333	4,000	1,000			692	15,485
Peninsula.....	1,225,981					736,507	1,108,660
Tamarack.....		181,669	3,646,517	7,396,529	11,411,325	10,605,451	10,106,741
Ogima.....	1,106	12,000					
Kearsarge.....				21,237	829,185	1,918,849	1,598,525
Evergreen Bluff.....	954	1,500	1,000			21,580	
Ash Bed.....	1,517						
Sundry companies— tributers.....	21,696	34,000	50,000	50,000	50,000	6,224	
Total.....	69,353,202	72,147,889	80,918,460	76,028,697	86,472,034	87,455,675	100,745,277

A somewhat different system has been adopted in the distribution of the product of the Western States outside of Montana, Arizona, and New Mexico, in which there is little copper mining proper, but in which considerable metal is raised as an incidental constituent of gold, silver and lead ores. This metal comes to lead and copper smelters often in small parcels, the source of which is not readily traced. In the above table the copper contents of matte produced by lead smelters has been credited to the States and Territories in which the works are located. The total quantity so distributed in 1890 was 1,906,913 pounds fine. The lead-refiners smelt large quantities of lead and dry ores containing copper and obtain some of the same metal from base bullion received. The product of Colorado copper smelters has been separately stated, deducting those quantities known to have come from other States and

Territories. This is notably the case with the product of a Montana works which goes to a Colorado establishment, which is often erroneously added to the product of that State, thus duplicating the amount. The Colorado copper smelters also treat large quantities of the matte made by Colorado lead works, thus again leading to duplication and causing an undue swelling of alleged Colorado output. It is probable, however, that by far the larger part of the quantity of copper enumerated under "copper-smelters" did originate in that State.

Total copper production in the United States, 1883 to 1890, inclusive.

Sources.	1883.	1884.	1885.	1886.
	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>
Lake Superior	59,702,404	69,353,202	72,147,889	80,918,460
Arizona	23,874,963	26,734,345	22,706,366	15,657,035
Montana	24,664,846	43,093,054	67,797,864	57,611,621
New Mexico	823,511	59,450	79,839	558,385
California	1,600,862	876,166	469,028	430,210
Utah	341,885	265,526	126,199	500,000
Colorado	1,152,652	2,013,125	1,146,460	409,306
Wyoming	962,468			
Nevada	288,077	100,000	8,871	50,000
Idaho		46,667	40,381	
Missouri	260,306	230,000		
Maine and New Hampshire	212,124	249,018		
Vermont	400,000	855,405	211,602	315,719
Southern States	395,175	317,711	40,199	29,811
Middle States	64,400	2,114	190,641	
Lead-desilverizers, etc	782,880	950,870	910,144	1,282,496
Copper-smelters (a)				
Total domestic copper	115,526,053	144,946,653	165,875,483	157,763,043
From imported pyrites and ores	1,625,742	2,858,754	5,086,841	4,500,000
Total (including copper from imported pyrites)	117,151,795	147,805,407	170,962,324	162,263,043

Sources.	1887.	1888.	1889.	1890.
	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>
Lake Superior	76,028,697	86,472,034	87,455,675	100,745,277
Arizona	17,720,462	31,797,300	31,586,185	34,796,659
Montana	78,699,677	97,897,968	98,222,444	112,980,896
New Mexico	283,664	1,631,271	3,686,137	850,034
California	1,600,000	1,570,021	151,505	23,347
Utah	2,500,000	2,131,047	65,467	1,006,656
Colorado	2,012,027	1,621,100	1,170,053	883,132
Wyoming		232,819	100,000	
Nevada		50,000	26,420	
Idaho		50,000	156,490	87,243
Missouri				
Maine and New Hampshire	} 200,000	271,631	72,000	} 378,840
Vermont				
Southern States		18,201	18,144	
Middle States				
Lead-desilverizers, etc	2,432,804	2,618,074	3,345,442	4,643,439
Copper-smelters (a)				2,702,559
Total domestic copper	181,477,331	226,361,466	226,055,962	259,098,092
From imported pyrites and ores	3,750,000	4,909,156	5,190,252	6,017,041
Total (including copper from imported pyrites)	185,227,331	231,270,622	231,246,214	265,115,133

a Copper smelters in Colorado, purchasing argentiferous copper ores and mattes in the open market, sources not known. The quantity of Montana matte which goes to one of these works has been deducted.

Lake Superior.—The Calumet and Hecla Company has progressed in the direction of a larger output and is still adding to its enormous

equipment. The report of Mr. Alexander Agassiz, the president, for the fiscal year ending April 30, 1891, records the fact that the openings are again gaining on the stoping, and adds: "At our present rate of production (30,000 tons of refined copper per annum) we must have from sixteen to seventeen years of ground opened."

Tamarack.—During its fiscal year ending June 30, 1891, the product of the Tamarack had risen to 14,076,957 pounds from 18,776,153 pounds of mineral, obtained from crushing 282,987 tons of rock, showing a percentage in stamp rock of 2.49 per cent of refined copper. The underground expense was \$522,834.07, and the outlays for stamping, transportation, etc., \$205,281.81; for smelting and marketing the copper the cost was \$213,921.24, making the total mining cost \$942,037.12. The sale of copper and interest receipts realized \$2,008,776.92, thus showing a mining profit of \$1,066,739.80, out of which dividends aggregating \$750,000 were paid. The balance of \$316,739.80 nearly paid for the construction account of \$340,430.71. This included \$182,253.31 expended in the equipment of mine and mill, including a large air-compressor, and leaves the future construction work of small proportions. Sinking is, however, progressing on shafts Nos. 3 and 4, which are being driven to reach another part of the tract and must go to much greater depth. The running cost is figured at 5.17 cents per pound, to which must be added 1.52 cents for smelting, freight, and all expenses of handling copper, making a total of 6.69 cents. The construction cost figures 2.42 cents per pound of copper produced, so that including it a total of 9.11 cents is reached. There were originally paid in \$13 per share, or \$650,000, and subsequently 10,000 shares were sold at \$100 per share, so that the capital investment, less \$13 per share credited to capital stock, reached \$1,520,000. The whole construction expense was \$1,362,279.18, and, after paying dividends aggregating \$2,070,000 and acquiring real estate of \$200,000, there remained a balance of quick assets of \$1,024,055.56. The total product of copper was 51,055,261 pounds, which realized \$6,589,611.86, or an average of 12.91 cents.

Quincy.—The Quincy is increasing its stamping facilities by the addition of two ball stamps and the necessary pumping machinery, which will bring its monthly products up to 1,000 or 1,100 tons. During the year 1889 there were mined 167,077 tons of rock, of which 123,998 tons were hoisted and 117,875 tons were stamped with a yield of 2.82 per cent. of mineral, or 6,641,785 pounds. There was also produced 1,178,225 pounds of masses, the total yield of refined copper being 6,405,686 pounds. Owing to the low price of copper, the net earnings were only \$182,601.14, and yet \$200,000 was paid in dividends. In 1890, however, the increased product (from 187,244 tons mined and 165,145 tons stamped, producing 7,262,485 pounds of stamp mineral and 2,740,365 of masses), 8,064,253 pounds of ingots, together with the much higher price and lessened construction account, ran the net income up to \$596,677.60, out of which dividends of \$400,000 were paid. The company has paid

\$5,770,000 in dividends on a total product of 114,691,387 pounds of copper, with an original capital of \$200,000 paid in, and had assets, after paying the last dividend, of \$542,045.15.

Franklin.—During 1889 and 1890 the Franklin showed a steady recovery in the grade of the rock, the copper contents of the material hoisted being 1.497 per cent. in 1890 against 1.164 per cent. in 1889, 1 per cent. in 1888, and 1.12 per cent. in 1887. The amount of rock hoisted rose from 186,740 tons in 1889 to 188,355 tons in 1890, while the quantity crushed increased from 141,579 tons to 144,393 tons, the yield of ingot copper rising from 4,346,062 pounds to 5,638,112 pounds. The cost per ton of rock hoisted rose from \$1.84 in 1889 to \$1.90 in 1890, which is, however, due to the fact that the stock of underground was largely increased. Owing to better prices, the net income jumped from \$139,577.52 in 1889 to \$373,612.49 in 1890.

Huron.—The Huron has continued a difficult struggle for existence, and experienced a heavy falling off in the product in 1890, which was only 1,736,777 pounds in that year against 2,219,473 pounds in 1889, and an assessment of \$200,000 was levied in 1890. The rock is apparently too lean to allow of profitable work. The rock stamped yielded only 0.86 per cent. of ingot in 1890, against 0.98 per cent. in 1889, and yet the quantity mined but rejected as too poor was enormous. Thus in 1890 not less than 45,501 tons, or nearly 31 per cent. of the whole taken out of the mine, was rejected. It seems that the productive ground is rapidly pitching toward the south, so that the lode in the bottom levels in the northern part of the mine is absolutely barren. In 1890 the cost per ton of rock hoisted was \$1.89 against \$1.69 in 1889.

Atlantic.—For close work, on a narrow margin, the Atlantic continues to be the most interesting mine in the Lake Superior district. The details of costs for a series of years are given in the following table:

Cost of copper at the Atlantic mine per ton of rock treated.

Items of cost.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Cents.</i>	<i>Cents.</i>	<i>Cents.</i>	<i>Cents.</i>	<i>Cents.</i>	<i>Cents.</i>
Mining, selecting, breaking, and all surface expenses, including taxes	78.62	80.88	87.23	83.73	87.87	104.14
Transportation to mill	4.80	3.48	3.80	3.47	3.88	3.46
Stamping and separating	30.36	26.53	27.31	26.89	27.78	27.78
Freight, smelting, marketing, and New York expenses.....	25.45	24.25	23.07	21.42	20.22	20.37
Total working expenses	139.23	135.14	141.41	135.51	139.75	155.75
Total expenditures	143.60	138.01	145.22	142.82	153.27	166.70
Net profit.....	22.05	15.29	30.53	54.36	6.23	27.71
Yield of copper, per cent.....	0.743	0.709	0.712	0.667	0.663	0.650

The figures for the year 1889 clearly show that, with copper at 12 cents, the closest economy will hardly permit of a profit. In that year, after paying \$37,669.56 for construction, the net profit was \$26,679.61, carrying the surplus up to \$323,020.93, out of which a dividend of

\$60,000 was paid. The better price realized in 1890 allowed a mining profit of \$112,064.29 to be obtained, out of which \$30,495.21 was paid for construction, and \$80,000 was paid in dividends. The mine is renewing its hoisting plant and preparing for deeper work, a high-speed direct-acting engine having been placed in 1889 with great success. The question of depositing the stamp-mill sands has been dealt with.

Central.—In 1889 and 1890 the Central mine was troubled with an irregularity in the vein, in depth, which proved to be due to a throw of 220 feet westward. In 1889 the production was lessened by the necessity of straightening the main shaft, and this, coupled with the low price of copper, created an apparent loss of \$26,575.59. The surplus was, however, drawn upon for a dividend of \$20,000. The better returns for 1890 left a profit of \$22,607.33, out of which a dividend of \$20,000 was distributed, leaving the surplus at \$109,993.88, exclusive of real estate or plant. The mine has paid a total of \$1,970,000 on a capital of \$100,000.

Allouez.—The Allouez Company has struggled with adversity. Low prices in 1889 caused a suspension of operations towards the end of October, and work was not resumed until May of the following year. In February, 1891, a fire destroyed the rock house. The company works a low-grade rock, the yield of refined copper per ton of rock mined having been only 0.67 per cent. in 1889 and 0.57 per cent. in 1890. In the former year the cost of the copper marketed, all expenses paid, was 12.80 cents, while in 1890 it was 14.65 cents. In 1889 the receipts, including an assessment of \$40,000, were \$253,177.76, and the outlays \$238,791.55. In 1890 the stockholders were again called upon for \$40,000, including which the receipts were \$247,428.28, the expenditures reaching \$257,830.40. Exploratory work for the Calumet and Hecla lode did not lead to favorable results.

Osceola.—In 1890 the Osceola had a prosperous year, since \$225,000 was paid in dividends, carrying the total up to January 1, 1891, to \$1,447,500 on a capital of \$1,250,000. Increased wages and extraordinary expenditures brought the mining cost per ton of stamp rock to \$2.39, against \$2.21 in 1889. On the other hand, however, the quality of the rock handled improved, the average being 1.44 per cent. in 1890, as compared with 1.291 per cent. in 1889. In 1890, 214,467 tons of rock were hoisted, of which 183,825 tons were sent to the mill. The cost of the copper at the mine was 8.31 cents, to which must be added 1.51 cents for smelting, freight, and handling, bringing the total to 9.82 cents. There were, however, construction costs footing up to \$75,156.19, which, added to the new cost, bring the total amount at which the metal was produced to 11.24 cents.

Kearsarge.—The Kearsarge mine continued during 1889 to draw upon its reserves in the upper levels without opening up much promising ground at greater depth. In 1890, however, the chances for developing a permanent mine were improved by better developments. Although

a larger amount of rock was treated (73,541 and 74,368 tons hoisted in 1889 and 1890, and 56,104 tons and 60,619 tons respectively stamped), the product was smaller, falling from 1,918,849 pounds to 1,598,525 pounds of ingot, since the percentage of copper in stamp rock declined from 1.71 to 1.32 per cent. Although the cost per ton of rock fell from \$2.49 to \$2.26, the cost of copper at the mine rose from 7.27 cents in 1889 to 8.64 cents in 1890. Adding the cost of smelting, the totals are 9.21 and 10.47 cents, and including cost of construction, 9.52 and 10.68 cents for the two years. After paying a dividend of \$80,000 on the 1st of January, 1890, the company closed the year with a balance of assets of \$144,757.31. Explorations on the Calumet conglomerate did not lead to any valuable discoveries.

MONTANA.

During the years 1889 and 1890, the State maintained its high rate of copper production. Aside from the Butte and Boston Company, no new producers of any consequence entered the lists. The older concerns have added more or less to their equipment.

The annual reports of the Boston and Montana Company are of particular interest, since it is the only mine concerning whose operations data reached the public, thus affording some insight into the costs of mining and producing copper in the great Butte district.

During the fiscal year ending June 1, 1890, the production of matte and ore was 22,740 short tons, which yielded 26,003,604 pounds, from which \$2,999,997.37 was realized, the corresponding figures for the fiscal year 1891 being 23,734 tons, with 26,693,842 pounds of copper, for which \$2,937,134.18 was obtained. The average price, therefore, was 11 cents in 1890-'91, against 11.54 cents in 1889-'90, 11.60 cents in 1888-'89, and 11.52 cents in 1887-'88. It must be noted, however, that the relatively high price obtained is due to the fact that the company was still delivering on contracts with the French syndicate. In addition to the copper, the company produced in the fiscal year 1889-'90, 284,553 ounces of silver, and in 1890-'91, 255,856 ounces. The total running cost in 1889-'90 was \$655,512.40 on 138,938 tons of ore, while in 1890-'91 it was \$612,211.57 on 144,705 tons. The principal mines are the Mountain View, which produced 59,779 and 60,243 tons, respectively, in 1889-'90 and 1890-'91, at a cost of \$3.31 and \$3.57; while 32,013 and 25,341 tons of Pennsylvania ore cost \$4.36 and \$4.12, and 49,476 and 46,679 tons of Colusa ore, \$4.76 and \$5.51 per ton. These figures do not include construction costs, which in 1889-'90 figured up \$106,046.94, and in 1890-'91, \$87,347.69, the latter including \$72,535.72 for the new Leonard shaft. The concentrating, calcining, and matte smelting cost \$742,244.86 in 1889-'90, and \$772,031.82 in 1890-'91, the other miscellaneous outlays for sacking, transportation, taxes, etc., being \$138,645.31 and \$139,588.75, respectively. Thus the total running expenses at the mine were \$1,536,402.57 in 1889-'90, and \$1,523,832.14 in 1890-'91, and adding construction

cost at the mines and smelter, \$1,663,638.07 and \$1,628,666.05. This makes the cost of fine copper in matte and shipping ore at the mine respectively 6.40 and 6.10 cents. To this must be added, however, the heavy outlay for freight on matte to the refinery, copper charges, commissions, refining, etc., which in 1889-'90 amounted to \$468,702.64, or 1.80 cents per pound, and in 1890-'91 to \$577,481.45, or 2.16 cents per pound of fine copper contents, the whole thus reaching a total of 8.20 and 8.26 cents, respectively. It should be noted, however, that in this computation the copper is charged with the entire cost of production, thus leaving the silver to swell profits. The company has expended heavy sums for a new smelting plant at Great Falls, Montana, where water power is available, and an electrolytic refining plant is to be established ultimately. Prior to July 1, 1890, the outlays at Great Falls were \$135,269.38. In the fiscal year 1890-'91 they were \$462,980.79, thus making a total of \$598,250.17, to which must be added the sums required for its completion early in 1892. The company has a capital stock of \$3,125,000, in \$25 shares; has issued \$1,500,000 7 per cent bonds, of which \$339,000 have been canceled, and has paid twelve dividends, aggregating \$1,825,000, closing the year with a balance of quick assets of \$621,715.60.

ARIZONA.

The history of the copper industry in Arizona has been uneventful during the past two years. Nearly the whole of the product came from the established mines, the Copper Queen and the Holbrook and Cave at Bisbee, the Arizona and the Detroit at Clifton, the Old Dominion at Globe, and the United Verde at Jerome.

COLORADO.

The most interesting development in this State has been the opening of large bodies of cupriferous ore in the lower levels of some of the Leadville mines. The Henriette and Maid has opened out a chute of ore 75 feet thick and from 100 to 150 feet wide of sulphide ore, with 40 to 60 ounces of silver, 5 to 8 per cent of copper, and about 5 per cent each of lead and of zinc.

IMPORTS.

The imports of fine copper contained in ores, and of regulus and black copper, and of ingot copper, old copper, plates not rolled, rolled plates, sheathing metal, and manufactures not otherwise specified, and of brass are given in the following tables:

Fine copper contained in ores, and regulus and black copper imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Calendar years ending December 31, from 1866 to 1890; previous years end June 30.	Fine copper contained in ores.		Regulus and black copper. (a)		Total value.
	Quantity.	Value.	Quantity.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>		
1867		\$936, 271			\$936, 271
1868	3, 496, 994	197, 203			197, 203
1869	24, 960, 604	448, 487			448, 487
1870	1, 936, 875	134, 736			134, 736
1871	411, 315	42, 453		499	\$60 42, 513
1872	584, 878	69, 017	4, 247	1, 083	70, 100
1873	702, 086	80, 132	1, 444, 239	279, 631	359, 763
1874	606, 266	70, 653		5, 397	76, 030
1875	1, 337, 104	161, 903		2, 076	163, 979
1876	538, 972	68, 922	8, 584	1, 613	70, 535
1877	76, 637	9, 756	1, 874	260	10, 016
1878	87, 039	11, 785			11, 785
1879	51, 959	6, 199			6, 199
1880	1, 165, 283	173, 712	2, 201, 394	337, 163	510, 875
1881	1, 077, 217	124, 477	402, 640	51, 633	176, 110
1882	1, 473, 109	147, 416	224, 052	30, 013	177, 429
1883	1, 115, 386	113, 349			113, 349
1884	2, 204, 070	219, 957	2, 036	204	220, 161
1885	3, 665, 739	343, 793	285, 322	20, 807	364, 600
1886	4, 530, 400	341, 558	1, 960	98	341, 656
1887	3, 886, 192	194, 785	27, 650	1, 366	196, 151
1888	4, 850, 812	381, 477	4, 971	324	381, 801
1889	3, 772, 838	274, 649	60, 525	4, 244	278, 893
1890	3, 448, 237	241, 732	221, 838	15, 688	257, 420

a Not enumerated until 1871.

Copper imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Calendar years ending December 31, from 1866 to 1890; previous years end June 30.	Bars, ingots, and pigs.		Old, fit only for remanufacture.		Old, taken from bottoms of American ships abroad. (a)		Plates not rolled.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>	
1867	1, 635, 953	\$287, 831	569, 732	\$81, 930				
1868	61, 394	6, 935	318, 705	42, 652				
1869	13, 212	2, 143	290, 780	34, 820				
1870	5, 157	418	255, 386	31, 931				
1871	3, 316	491	369, 634	45, 672			430	\$129
1872	2, 638, 589	578, 965	1, 144, 142	178, 536			148, 192	33, 770
1873	9, 697, 608	1, 984, 122	1, 413, 040	255, 711	32, 307	\$4, 913	550, 431	97, 888
1874	713, 935	134, 326	733, 326	137, 087	9, 500	930		
1875	58, 475	10, 741	396, 320	55, 564	11, 636	1, 124	8	4
1876	5, 281	788	239, 987	35, 545	10, 304	1, 981	5, 467	600
1877	230	30	219, 443	28, 608	41, 482	5, 136		
1878	1	1	198, 749	25, 585		6, 004		
1879	2, 515	352	112, 642	11, 997	11, 000	1, 107	27, 074	4, 496
1880	1, 242, 103	206, 121	695, 255	91, 234			120	11
1881	219, 802	36, 168	541, 074	63, 383	14, 680	1, 504	20	3
1882	6, 200	836	508, 901	59, 629	16, 075	1, 629		
1883			330, 495	36, 166	9, 415	666		
1884	(b) 542	107	149, 701	12, 099		554		
1885	914	172	81, 312	6, 658		1, 160		
1886	276	37	37, 149	2, 407		584		
1887	212	22	39, 957	2, 374		129		
1888	1, 787	299	37, 620	2, 535				
1889	3, 160	522	19, 912	1, 176				
1890	5, 189	830	284, 789	26, 473				

a Not enumerated until 1873.

b Includes "plates not rolled" since 1884.

Copper imported and entered for consumption in the United States, 1867 to 1890—Cont'd.

Calendar years ending December 31, from 1886 to 1890; previous years end June 30.	Plates rolled, sheets, pipes, etc.		Sheathing metal, in part copper. (a)		Manufac- tures not otherwise specified.	Total value.
	Quantity.	Value.	Quantity.	Value.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>			
1867.....		\$1, 101	220, 889	\$37, 717	\$15, 986	\$124, 565
1868.....		1	101, 488	18, 852	21, 492	89, 932
1869.....		39	43, 660	6, 592	43, 212	86, 506
1870.....		2, 039			485, 220	519, 608
1871.....		7, 487			668, 894	722, 673
1872.....		18, 895			1, 007, 744	1, 817, 910
1873.....		4, 514			869, 281	3, 216, 429
1874.....		27	282, 406	50, 174	125, 708	448, 252
1875.....		617	136, 055	28, 650	35, 572	127, 272
1876.....		326	18, 014	2, 903	29, 806	71, 949
1877.....		203	110	22	41, 762	75, 761
1878.....		1, 201	647	55	35, 473	68, 319
1879.....		786	300	20	39, 277	58, 035
1880.....		4, 134	6, 044	693	130, 329	432, 522
1881.....		82	39, 520	4, 669	284, 509	390, 318
1882.....	5, 855	1, 551			77, 727	141, 372
1883.....	2, 842	379	6, 791	1, 047	40, 343	78, 601
1884.....	6, 529	2, 330	19, 637	926	55, 274	71, 290
1885.....	470	120	86, 619	9, 894	61, 023	79, 027
1886.....	3, 770	339	21, 573	1, 017	31, 871	37, 155
1887.....	37, 925	5, 493	18, 189	1, 867	37, 289	47, 174
1888.....	5, 208	737	23, 622	2, 696	14, 567	20, 834
1889.....	13, 848	2, 082	23, 520	2, 572	13, 430	19, 782
1890.....	4, 209	917	37, 458	4, 467	24, 752	57, 468

a Does not include copper sheathing in 1867, 1868, and 1869.

Brass imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Calendar years ending December 31, from 1886 to 1890; previous years end June 30.	Bars and pigs.		Old, fit only for re- manufacture.		Not other- wise pro- vided for.	Total value.
	Quantity.	Value.	Quantity.	Value.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>			
1867.....		\$3, 099		\$26, 468	\$170, 873	\$200, 440
1868.....	31, 104	2, 071	120, 913	11, 699	181, 114	194, 884
1869.....	33, 179	2, 457	131, 640	10, 838	198, 310	211, 605
1870.....	54, 108	3, 791	98, 825	6, 918	49, 845	60, 554
1871.....	28, 453	2, 803	438, 085	37, 922	13, 659	54, 384
1872.....	17, 963	1, 664	829, 964	73, 098	23, 738	98, 500
1873.....	56, 656	7, 147	699, 478	71, 494	114, 767	193, 408
1874.....	253	19	682, 151	64, 848	350, 266	415, 133
1875.....	370, 273	38, 867	124, 285	12, 786	273, 873	325, 526
1876.....			618, 191	54, 771	232, 870	287, 641
1877.....			689, 633	59, 402	207, 642	267, 044
1878.....			713, 171	57, 551	205, 209	262, 760
1879.....	950	49	485, 354	32, 278	232, 030	264, 357
1880.....			958, 590	75, 093	339, 131	414, 224
1881.....	85, 370	11, 202	1, 615, 402	151, 541	331, 506	494, 249
1882.....	30, 769	3, 168	2, 954, 148	263, 891	400, 477	667, 536
1883.....	6, 380	559	1, 015, 345	84, 786	485, 321	570, 666
1884.....	1, 611	445	508, 923	40, 766	429, 224	470, 435
1885.....	2, 305	532	166, 317	15, 717	400, 175	416, 424
1886.....	6, 705	295	143, 121	30, 517	374, 364	405, 176
1887.....	2, 332	562	189, 157	30, 158	331, 800	362, 520
1888.....			257, 748	40, 373	156, 738	197, 111
1889.....	7, 667	1, 093	188, 467	37, 293	140, 193	178, 579
1890.....	7, 905	1, 261	285, 089	38, 938	175, 684	215, 883

EXPORTS.

In a very brief time the United States, with its exuberant production, has become one of the largest contributors to the supply of the world. The following tables show the quantities of copper, copper ore (including matte), and manufactured copper exported for a series of fiscal years;

Value of copper, brass, and manufactured copper exported from the United States, 1791 to 1863, inclusive.

Fiscal years ending September 30 until 1842, and June 30 since.	Value.	Fiscal years ending September 30 until 1842, and June 30 since.	Value.
1791	\$493	1833	\$203,880
1803	6,233	1834	198,273
1804	8,654	1835	69,791
1805	12,977	1836	72,991
1806	25,340	1837	91,724
1807	12,742	1838	81,363
1808	4,031	1839	81,334
1809	3,095	1840	86,954
1810	17,426	1841	72,932
1811	9,282	1842	97,021
1812	2,644	1843 (nine months)	79,234
1813		1844	91,446
1814		1845	94,736
1815	366	1846	62,088
1816	16,152	1847	64,980
1817	8,765	1848	61,468
1818	33,379	1849	66,203
1819	12,721	1850	105,060
1820	18,547	1851	91,871
1821	26,694	1852	103,039
1822	86,974	1853	108,205
1823	16,768	1854	91,984
1824	26,981	1855	690,766
1825	30,472	1856	534,846
1826	60,083	1857	607,054
1827	52,341	1858	1,985,223
1828	60,452	1859	1,048,246
1829	129,647	1860	1,664,122
1830	36,601	1861	2,375,029
1831	55,755	1862	1,098,546
1832	105,774	1863	1,026,038

Copper and copper ore of domestic production exported from the United States, 1864 to 1890, inclusive.

[Cwts. are long hundred-weights of 112 pounds.]

Calendar years ending December 31, from 1886 to 1890; previous years end June 30.	Ore.		Pigs, bars, sheets, and old.		Manufactured.	Total value.
	Quantity.	Value.	Quantity.	Value.	Value.	
	<i>Cwts.</i>		<i>Pounds.</i>			
1864	109,581	\$181,298	102,831	\$43,229	\$208,043	\$432,570
1865	225,197	553,124	1,572,382	709,106	282,640	1,544,870
1866	215,080	792,450	123,444	33,553	110,208	936,211
1867	87,731	317,791	(a)4,637,867	303,048	171,062	791,901
1868	92,612	442,921	1,350,896	327,287	152,201	922,409
1869	121,418	237,424	1,134,360	233,932	121,342	592,698
1870	(a)19,198	537,505	2,214,658	385,815	118,926	1,042,246
1871	(a)54,445	727,213	581,050	133,020	55,198	915,451
1872	35,564	101,752	267,868	64,844	121,139	287,735
1873	45,252	170,365	38,958	10,423	78,288	259,076
1874	13,326	110,450	503,160	123,457	233,301	467,208
1875	(a)51,305	729,578	5,123,470	1,042,536	43,152	1,815,266
1876	15,304	84,471	14,304,160	3,098,395	343,544	3,526,410
1877	21,432	109,451	13,461,553	2,718,213	195,730	3,023,394
1878	32,947	169,020	11,297,876	2,102,455	217,446	2,488,921
1879	23,070	102,152	17,200,739	2,751,153	79,900	2,933,205
1880	21,623	55,763	4,206,258	667,242	126,213	849,218
1881	9,958	51,499	4,865,407	786,860	38,036	876,395
1882	25,936	89,515	3,340,531	565,295	93,646	748,456
1883	112,923	943,771	8,221,363	1,293,947	110,286	2,348,004
1884	386,140	2,930,895	17,044,760	2,527,829	137,135	5,595,859
1885	432,300	4,739,601	44,731,858	5,339,887	107,536	10,187,024
1886	417,520	2,341,164	19,553,421	1,968,772	76,386	4,386,322
1887	501,280	2,774,464	12,471,393	1,247,928	92,064	4,114,456
1888	794,960	6,779,294	31,706,527	4,906,805	211,141	11,897,240
1889	818,500	8,226,206	16,813,410	1,896,752	86,764	10,209,722
1890	431,411	4,413,067	10,971,899	1,365,379	139,949	5,918,395

a Evidently errors in quantities.

Value of brass and its manufactures exported from the United States, 1867 to 1890, inclusive.

Fiscal years ending June 30—	Value.	Fiscal years ending June 30—	Value.	Calendar years ending December 31, from 1886 to 1890; previous years end June 30.	Value.
1867.....	\$12,864	1875.....	\$1,000,629	1883.....	\$287,847
1868.....	16,841	1876.....	256,974	1884.....	301,014
1869.....	40,063	1877.....	327,817	1885.....	538,118
1870.....	169,997	1878.....	589,451	1886.....	183,686
1871.....	210,816	1879.....	200,871	1887.....	275,019
1872.....	229,458	1880.....	183,468	1888.....	327,170
1873.....	494,575	1881.....	216,057	1889.....	366,739
1874.....	503,531	1882.....	322,439	1890.....	395,950

Exports of copper ore, matte, ingot, sheets, and manufactures of copper for the calendar years 1886, 1887, 1888, 1889, and 1890.

Articles.	1886.		1887.	
	Quantity.	Value.	Quantity.	Value.
Ore and matte.....long tons..	20,876	\$2,341,164	25,064	\$2,774,464
Ingots, bars, and old.....pounds..	19,504,087	1,960,189	12,347,507	1,223,260
Sheets.....do.....	49,334	8,583	123,886	24,668
All other manufactures of.....		76,386		92,064
Total.....		4,386,322		4,114,456

Articles.	1888.		1889.		1890.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
Ore and matte, long tons..	39,748	\$6,779,294	45,836	\$8,226,206	24,159	\$4,413,067
Ingots, bars and old, pounds.....	31,664,046	4,899,423	16,786,418	1,890,589	10,890,058	1,346,401
Sheets.....pound, ..	42,481	7,382	26,992	6,163	81,841	18,973
All other manufactures of.....		211,141		86,764		139,949
Total.....		11,897,340		10,209,722		5,918,395

THE COPPER MARKETS.

The following table summarizes the highest and lowest prices obtained for Lake copper monthly in the New York markets from 1860 to 1890, both inclusive:

Highest and lowest prices of Lake Superior ingot copper, by months, from 1860 to 1890.

[Cents per pound.]

Years.	January.		February.		March.		April.		May.		June.	
	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.
1860.....	24	23 $\frac{1}{2}$	24	23 $\frac{1}{2}$	23 $\frac{1}{2}$	23	23 $\frac{1}{2}$	23	23 $\frac{1}{2}$	22 $\frac{1}{2}$	22 $\frac{1}{2}$	21 $\frac{1}{2}$
1861.....	20	19	19	19	19 $\frac{1}{2}$	19 $\frac{1}{2}$	19	19	19 $\frac{1}{2}$	19 $\frac{1}{2}$	19	18
1862.....	28	27	28	25	25	23	23	21	21 $\frac{1}{2}$	20 $\frac{1}{2}$	23	20 $\frac{1}{2}$
1863.....	35	31	37	35	37	31	31	30	30 $\frac{1}{2}$	30	30 $\frac{1}{2}$	30
1864.....	41 $\frac{1}{2}$	39	42	41	42 $\frac{1}{2}$	41 $\frac{1}{2}$	44	42 $\frac{1}{2}$	44	43	49	44
1865.....	50 $\frac{1}{2}$	46	46	44	44 $\frac{1}{2}$	34 $\frac{1}{2}$	35	34	34	30	30 $\frac{1}{2}$	28 $\frac{1}{2}$
1866.....	42	38	38	35 $\frac{1}{2}$	35 $\frac{1}{2}$	29 $\frac{1}{2}$	30	28 $\frac{1}{2}$	31	29	33	31
1867.....	29 $\frac{1}{2}$	27	27	27	27 $\frac{1}{2}$	24	24	23 $\frac{1}{2}$	24 $\frac{1}{2}$	24	24	24
1868.....	23 $\frac{1}{2}$	21	24	22	24	23 $\frac{1}{2}$	24	24	24 $\frac{1}{2}$	24	24	24
1869.....	26 $\frac{1}{2}$	23	27	26	26 $\frac{1}{2}$	24	24	23 $\frac{1}{2}$	24 $\frac{1}{2}$	23 $\frac{1}{2}$	23	22 $\frac{1}{2}$
1870.....	22	21	21 $\frac{1}{2}$	20	20 $\frac{1}{2}$	19	19	19 $\frac{1}{2}$	19 $\frac{1}{2}$	19	20	19
1871.....	22 $\frac{1}{2}$	22	22	21	21 $\frac{1}{2}$	21	21	21 $\frac{1}{2}$	21 $\frac{1}{2}$	21	21	21 $\frac{1}{2}$
1872.....	22 $\frac{1}{2}$	22	22	22	30 $\frac{1}{2}$	30 $\frac{1}{2}$	34	30 $\frac{1}{2}$	42	36	34	33
1873.....	35	32	35	34	34	35	34 $\frac{1}{2}$	33 $\frac{1}{2}$	33 $\frac{1}{2}$	32	31	29
1874.....	25	24 $\frac{1}{2}$	25	24 $\frac{1}{2}$	24 $\frac{1}{2}$	24	25	24 $\frac{1}{2}$	25	24 $\frac{1}{2}$	24	24 $\frac{1}{2}$
1875.....	23 $\frac{1}{2}$	23	22 $\frac{1}{2}$	21	21 $\frac{1}{2}$	21 $\frac{1}{2}$	21	21 $\frac{1}{2}$	23 $\frac{1}{2}$	22 $\frac{1}{2}$	23	23
1876.....	23 $\frac{1}{2}$	23	22 $\frac{1}{2}$	22	22 $\frac{1}{2}$	22	22	22	22	21	21	19 $\frac{1}{2}$
1877.....	19 $\frac{1}{2}$	17	20 $\frac{1}{2}$	19	19 $\frac{1}{2}$	19	19	19 $\frac{1}{2}$	19 $\frac{1}{2}$	19	19	19
1878.....	17	17	17	17	16 $\frac{1}{2}$	16	17	16 $\frac{1}{2}$	16 $\frac{1}{2}$	16	16	16
1879.....	16	15 $\frac{1}{2}$	15 $\frac{1}{2}$	15 $\frac{1}{2}$	15 $\frac{1}{2}$	15	16	15	16	16	16	16
1880.....	25	21	24 $\frac{1}{2}$	24	24	22	22	24	24	21	18	18 $\frac{1}{2}$
1881.....	19 $\frac{1}{2}$	19	19 $\frac{1}{2}$	19	19 $\frac{1}{2}$	19	19	18 $\frac{1}{2}$	18 $\frac{1}{2}$	18 $\frac{1}{2}$	18 $\frac{1}{2}$	18 $\frac{1}{2}$
1882.....	20	20	20	19	19 $\frac{1}{2}$	18 $\frac{1}{2}$	18 $\frac{1}{2}$	18 $\frac{1}{2}$	18	18	18 $\frac{1}{2}$	18
1883.....	18	18	17 $\frac{1}{2}$	17 $\frac{1}{2}$	17 $\frac{1}{2}$	17	16	15	16	15	15	15
1884.....	15	14 $\frac{1}{2}$	15	14 $\frac{1}{2}$	15	14	15	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14	14	14
1885.....	11	10	11	10	11	10	11	10	11	10	10	10
1886.....	11	11	11	10	11	10	11	10	11	10	10	10
1887.....	12	11	11	10	10 $\frac{1}{2}$	10	10	10	10	10	10	10
1888.....	17 $\frac{1}{2}$	15	16	16	16	16	16	16	16	16	16	16
1889.....	17 $\frac{1}{2}$	16 $\frac{1}{2}$	16 $\frac{1}{2}$	16 $\frac{1}{2}$	16 $\frac{1}{2}$	15	15	16	16	16	16	16
1890.....	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14	14	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14 $\frac{1}{2}$	14	14

Years.	July.		August.		September.		October.		November.		December.	
	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.
1860.....	21 $\frac{1}{2}$	21 $\frac{1}{2}$	21 $\frac{1}{2}$	21 $\frac{1}{2}$	22	21 $\frac{1}{2}$	22	21 $\frac{1}{2}$	21 $\frac{1}{2}$	20 $\frac{1}{2}$	20 $\frac{1}{2}$	19 $\frac{1}{2}$
1861.....	18	17 $\frac{1}{2}$	19	17 $\frac{1}{2}$	20 $\frac{1}{2}$	19	20	20	22 $\frac{1}{2}$	20 $\frac{1}{2}$	27	29 $\frac{1}{2}$
1862.....	24 $\frac{1}{2}$	24 $\frac{1}{2}$	24	24	27	24	27	27	32 $\frac{1}{2}$	30 $\frac{1}{2}$	31	38 $\frac{1}{2}$
1863.....	32	29	31	29	32 $\frac{1}{2}$	31	34 $\frac{1}{2}$	32 $\frac{1}{2}$	38 $\frac{1}{2}$	34 $\frac{1}{2}$	38 $\frac{1}{2}$	39 $\frac{1}{2}$
1864.....	55	49	52 $\frac{1}{2}$	50	52 $\frac{1}{2}$	47	48	47	49	47	50	48 $\frac{1}{2}$
1865.....	30 $\frac{1}{2}$	28	32	30 $\frac{1}{2}$	32 $\frac{1}{2}$	31	33	32	45 $\frac{1}{2}$	33	45 $\frac{1}{2}$	45 $\frac{1}{2}$
1866.....	33 $\frac{1}{2}$	31	31	30	31 $\frac{1}{2}$	30	31	30	30 $\frac{1}{2}$	26 $\frac{1}{2}$	29	26 $\frac{1}{2}$
1867.....	26	24	26 $\frac{1}{2}$	25 $\frac{1}{2}$	27 $\frac{1}{2}$	26	26	26	29	23	23	21 $\frac{1}{2}$
1868.....	24 $\frac{1}{2}$	23	24 $\frac{1}{2}$	24	24	24	24	23	24	22 $\frac{1}{2}$	24 $\frac{1}{2}$	23 $\frac{1}{2}$
1869.....	24 $\frac{1}{2}$	23	23	21 $\frac{1}{2}$	23	22	22	22	22	22	22	21 $\frac{1}{2}$
1870.....	20 $\frac{1}{2}$	20 $\frac{1}{2}$	21	20 $\frac{1}{2}$	21 $\frac{1}{2}$	20 $\frac{1}{2}$	21 $\frac{1}{2}$	21 $\frac{1}{2}$	21 $\frac{1}{2}$	21 $\frac{1}{2}$	22	22 $\frac{1}{2}$
1871.....	22 $\frac{1}{2}$	22 $\frac{1}{2}$	22	22	22 $\frac{1}{2}$	22	22	22	23	23	23	24
1872.....	34	33	35	32 $\frac{1}{2}$	35 $\frac{1}{2}$	33	34	31	32	30 $\frac{1}{2}$	32 $\frac{1}{2}$	30 $\frac{1}{2}$
1873.....	29	26	27 $\frac{1}{2}$	27	27	25 $\frac{1}{2}$	27	25	24	21	25	23
1874.....	24 $\frac{1}{2}$	20	21	19	21	21	21	21	23	22	23	23
1875.....	23	22	23	23	23	23	23	23	23	23	23	23
1876.....	20	19 $\frac{1}{2}$	19	18 $\frac{1}{2}$	19	18	19	20	20	20	20	19
1877.....	19 $\frac{1}{2}$	19	19	17 $\frac{1}{2}$	18 $\frac{1}{2}$	17	18	17	17	17	17	17
1878.....	16 $\frac{1}{2}$	16	16	16	16	16	16	15	15	15	16	15
1879.....	16	16	16	16	17	16 $\frac{1}{2}$	17	18	18	18	18	18
1880.....	18 $\frac{1}{2}$	18	19	19	18 $\frac{1}{2}$	18	18	18	18	18	18	18
1881.....	16 $\frac{1}{2}$	16	16	16	18	16	16	18	18	19	18	19
1882.....	18 $\frac{1}{2}$	18	18	18	18	18	18	18	18	18	18	18
1883.....	15 $\frac{1}{2}$	15	15	15	15 $\frac{1}{2}$	15 $\frac{1}{2}$	15	15	15	14	15	14
1884.....	14	13 $\frac{1}{2}$	14	13 $\frac{1}{2}$	13	13	13	12	13	12	12	11
1885.....	11 $\frac{1}{2}$	10	11	11	11	10	11	10	11	11	11	11
1886.....	10	10	10	10	11	10	10	10	10	10	10	10
1887.....	10	10	10	10	10	10	10	10	10	10	10	10
1888.....	16 $\frac{1}{2}$	16 $\frac{1}{2}$	17	16 $\frac{1}{2}$	17	16	17	17	17	17	17	17
1889.....	12	12	12	12	12	11	11	11	11	11	11	11
1890.....	17 $\frac{1}{2}$	16 $\frac{1}{2}$	17 $\frac{1}{2}$	17	17	17	16 $\frac{1}{2}$	16 $\frac{1}{2}$	16 $\frac{1}{2}$	16 $\frac{1}{2}$	16	15

In some months, notably those immediately preceding and following the collapse of the syndicate, in 1889, the prices were merely nominal. A good illustration of the rates obtained for Lake copper is contained in the following table compiled from the reports of a number of the Lake companies:

Prices realized for Lake copper in 1888, 1889, and 1890.

[Cents per pound.]

Mines.	1888.		1889.		1890.	
	Sales.	Average price.	Sales.	Average price.	Sales.	Average price.
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>	
Allouez	314, 198	13. 71	1, 762, 816	12. 08	1, 407, 828	14. 73
Franklin	3, 655, 751	15. 07	3, 300, 667	12. 05	2, 529, 542	14. 80
Atlantic	3, 974, 972	14. 78	3, 698, 837	12. 09	2, 821, 616	15. 21
Central	1, 817, 023	14. 80	1, 270, 592	12. 57	1, 413, 391	14. 94
Huron	2, 414, 169	14. 92	1, 900, 081	12. 83	1, 375, 000	14. 86
Osceola	4, 134, 320	15. 03	4, 534, 127	11. 94	5, 294, 792	15. 51
Quincy	6, 367, 809	15. 93	6, 405, 686	11. 96	8, 064, 253	15. 36
Kearsarge	829, 185	16. 60	1, 918, 849	12. 58	1, 598, 525	15. 08
Tamarack (a)	11, 036, 469	12. 90	8, 928, 249	11. 99	14, 076, 957	14. 01

a Fiscal years ending June 30, 1889, 1890, and 1891.

The figures furnish the means for estimating fairly well the average prices obtained for the different years. They do not, however, cover the sales of the largest producer, but it may be stated that the average prices realized were 12 cents in 1889 and 15 cents in 1890.

As covering the longest period, the report of the yearly sales of the Osceola are the most interesting in showing the fluctuations in the price of Lake copper. Since 1874 the sales of this company have been as follows:

Sales of copper and average prices by the Osceola Mining Company, 1874 to 1890.

Years.	Sales.	Average price.	Years.	Sales.	Average price.
	<i>Pounds.</i>	<i>Cts. per lb.</i>		<i>Pounds.</i>	<i>Cts. per lb.</i>
1874	936, 002	23. 37	1883	4, 256, 409	14. 96
1875	1, 330, 313	22. 77	1884	4, 247, 630	12. 82
1876	1, 693, 737	20. 57	1885	1, 639, 169	10. 75
1877	2, 774, 777	18. 19	1886	3, 560, 786	10. 51
1878	2, 705, 998	15. 53	1887	3, 583, 723	11. 86
1879	3, 197, 387	17. 79	1888	4, 134, 320	15. 03
1880	3, 381, 061	19. 15	1889	4, 534, 127	11. 94
1881	4, 176, 976	17. 77	1890	5, 294, 792	15. 51
1882	4, 179, 782	17. 70			

The principal events in the copper market during 1890 were closely associated with the marketing of the syndicate metal controlled by the guaranteeing bankers. On the whole, the operations were conducted judiciously and were greatly aided by the rising tendency, created by the enormous demand on the part of the manufacturers. January opened with Lake copper at 14.25 cents, at which banker's copper was put on the market. A rising tendency developed during the month, aided by the attitude of the mining companies, who were holding at 15

cents. February was quieter, with a somewhat weaker market, largely created by the offering of copper by second hands. The market remained quiet in the early part of March at $14\frac{1}{2}$ to $14\frac{1}{4}$ cents, until the announcement was made that the mining companies had contracted with manufacturers for a large quantity for April, May, and June delivery at 14 cents, which was followed later in the month by the selling of about 2,000,000 pounds of banker's stock at $14\frac{1}{4}$ cents. The market fluctuated in the early part of April between $14\frac{1}{2}$ and $14\frac{1}{4}$ cents for Lake, casting brands being quoted at $12\frac{3}{4}$ to $12\frac{1}{2}$ cents. A further opportunity was offered during this month to the bankers to dispose of about 8,000,000 pounds, followed early in May by the placing of 2,000,000 pounds of Arizona copper. The market rose rapidly from $14\frac{1}{2}$ cents early in the month of May to 15 cents, near which figure additional banker's stock was placed on the market, the month closing with an active demand at $15\frac{1}{4}$ cents for prompt delivery of Lake copper and 13.35 cents for casting brands. June witnessed the closing out of all that part of the bankers' stock not tied up by litigation, about 5,000 tons of Lake copper, and large sales by the mining companies at rapidly advancing prices, the month closing with $16\frac{3}{4}$ cents asked for Lake and $14\frac{1}{2}$ cents for casting copper. During the same month very large quantities, about 20,000 tons, of matte were disposed of by the heirs of the syndicate. Although there were some offerings from second hands to realize profits on a rising market, the price of copper rose steadily in July until $17\frac{1}{4}$ cents was reached at its close for Lake copper and $14\frac{3}{4}$ cents for casting brands. Operations on a very large scale were carried through in England, the bankers disposing of close upon 25,000 tons of metal in the English and French markets. The demand became less urgent in August, and although the mining companies made large sales for September and October, delivery in September at 17 cents, followed by further purchases by the consumers at full prices in October, the market showed a weakening tendency, which was more pronounced in casting than in Lake copper, the market entering November with the former at 14 cents and the latter to $16\frac{3}{4}$. The financial crash in Europe and its serious effect upon business in all lines in this country told on copper, which declined slowly to $16\frac{1}{2}$ cents during the month, the Lake companies withholding from the market entirely. The weakness became more pronounced in December, and although producers sold at 17 cents considerable quantities for forward delivery, they undertook to protect consumers against a decline, which developed rapidly, the year closing with Lake copper offering at 15 cents, export sales at 14 cents, and casting brands seeking a market at 13 cents.

The fluctuations in the price of copper during the past decade in the English market are shown in the following table:

Average values of copper in England.

Years.	Chile bars, or G. O. B.	Ore, 25 per cent.	Precipitate.
	<i>Long ton.</i> £ s. d.	<i>Per unit.</i> £ s. d.	<i>Per unit.</i> £ s. d.
1880	62 10 0	0 12 9	0 12 11
1881	61 10 0	12 6	13 8 ³ / ₁₆
1882	66 17 0	13 6 ³ / ₄	13 10 ¹ / ₁₆
1883	63 5 16	12 4 ¹ / ₂	12 10 ¹ / ₁₆
1884	54 9 1	10 5 ¹ / ₂	11 1
1885	44 0 10	8 4	9 0 ¹ / ₂
1886	40 9 3	7 9	8 3 ³ / ₈
1887	43 16 11	8 6	8 11 ³ / ₄
1888	79 19 4 ¹ / ₂	14 3 ¹ / ₄	16 3
1889	49 10 5	9 0 ¹ / ₂	
1890	54 5 5	10 7	

THE PRINCIPAL FOREIGN PRODUCERS.

The copper production of the world, 1883 to 1890, inclusive.

Countries.	1890.	1889.	1888.	1887.	1886.	1885.	1884.	1883.
EUROPE.	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Great Britain.....	(a)1,000	905	(a)1,500	389	1,471	2,773	3,350	2,190
Spain and Portugal:								
Rio Tinto.....	30,000	29,500	(a)32,000	26,663	(a)24,700	23,484	21,564	20,472
Tharsis.....	(a)10,300	(a)11,000	(a)11,500	(a)11,000	(a)11,000	(a)11,500	(a)10,800	9,800
Mason & Barry.....	(a)5,600	(a)5,250	(a)7,000	(a)7,000	(a)7,000	(a)7,000	(a)7,500	8,000
Sevilla.....	870	1,700	1,700	2,300	2,135	1,800	2,000	2,026
Portuguesa.....	(a)1,200	1,200	(a)900	(a)856	1,258	1,665	(a)2,300	2,357
Poderosa and others.....	(a)4,225	(a)6,500	(a)7,200	4,050	3,560	2,424	2,251	1,000
Germany:								
Mansfeld.....	15,800	15,506	13,380	13,025	12,595	12,450	12,582	12,634
Other German.....	(a)2,000	(a)1,850	(a)1,850	(a)1,850	1,870	(a)2,800	(a)2,200	3,568
Austria.....	1,210	1,225	1,010	883	733	585	670	572
Hungary.....	(a)300	(a)300	858	531	366	504	614	661
Sweden.....	(a)800	830	(a)900	905	520	775	662	732
Norway.....	(a)1,375	1,357	1,570	1,450	2,220	2,560	2,706	2,630
Italy.....	3,000	3,500	(a)2,500	(a)2,500	900	835	1,325	1,600
Russia.....	4,800	4,070	4,700	5,000	4,875	(a)5,100	4,700	3,500
Total Europe..	82,480	84,843	88,568	78,402	75,203	76,255	75,224	72,172
NORTH AMERICA.								
United States.....	115,669	100,918	101,054	81,017	70,430	74,052	64,708	51,574
Canada.....	3,050	2,500	(a)2,250	1,400	1,440	2,500	236	1,055
Newfoundland.....	1,735	2,615	2,050	1,180	1,125	778	668	1,053
Mexico.....	4,325	3,780	2,766	2,050	850	375	291	489
Total North America....	124,779	109,813	108,120	85,647	73,845	77,705	65,903	54,171
SOUTH AMERICA.								
Chile.....	26,120	24,250	31,240	29,150	35,025	38,500	41,648	41,099
Bolivia:								
Corocoro.....	(a)500	(a)1,200	1,450	(a)1,300	1,100	(a)1,500	(a)1,500	1,680
Peru.....	150	275	250	50	75	229	362	395
Venezuela:								
New Quebrada.....	6,370	6,068	4,000	2,900	3,708	4,111	4,600	4,018
Argentine Republic	150	190	150	170	180	233	159	293
Total South America....	33,290	31,983	37,090	33,570	40,088	44,573	48,269	47,485
AFRICA.								
Algiers.....	120	160	50	150	110	250	260	600
Cape of Good Hope.....	6,450	(a)7,700	7,500	7,250	6,015	5,450	5,000	5,975
Total Africa..	6,570	7,860	7,550	7,400	6,125	5,700	5,260	6,575

a Estimated.

The copper production of the world, 1883 to 1890, inclusive—Continued.

Countries.	1890.	1889.	1888.	1887.	1886.	1885.	1884.	1883.
ASIA.	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Japan	15,000	15,000	(a)11,000	(a)11,000	10,000	(a)10,000	(a)10,000	7,600
Total Asia....	15,000	15,000	11,000	11,000	10,000	10,000	10,000	7,600
AUSTRALIA.								
Australia.....	7,500	8,300	7,550	7,700	9,700	11,400	14,100	12,271

a Estimated.

RECAPITULATION.

Countries.	1890.	1889.	1888.	1887.	1886.	1885.	1884.	1883.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Europe	82,480	84,843	88,568	78,402	75,203	76,255	75,224	72,172
North America	124,779	109,813	108,120	85,647	73,845	77,705	65,903	54,171
South America	33,290	31,983	37,090	33,570	40,088	44,573	48,269	47,485
Africa	6,570	7,860	7,550	7,400	6,125	5,700	5,260	6,575
Asia	15,000	15,000	11,000	11,000	10,000	10,000	10,000	7,600
Australia.....	7,500	8,300	7,550	7,700	9,700	11,400	14,100	12,271
Total	269,619	257,799	259,878	223,719	214,961	225,633	218,756	200,274

With the exception of the figures for the United States the data in the above table were taken from the annual statistics of Messrs. Henry R. Merton & Co., of London. In 1890 the United States produced 42.9 per cent. of the whole output of the world against 22.4 per cent. in the year 1882, when production statistics were first carefully collected.

British imports and exports of copper.

Years.	Imports of—		Total imports.	Exports.	Apparent English consumption.
	Bars, cakes, and ingots.	Copper in ores and furnace products.			
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
1860	13,142	13,715	26,857	26,117
1865	23,137	23,922	47,059	41,398
1870	30,724	27,025	57,749	53,006
1871	33,228	23,671	56,899	56,633
1872	49,000	21,702	70,702	53,195
1873	35,840	26,756	62,596	55,716
1874	39,906	27,894	67,800	59,742
1875	41,931	29,483	71,414	51,870
1876	39,145	36,191	75,336	52,468
1877	39,743	53,582	93,325	54,088
1878	39,360	48,212	87,572	55,001
1879	46,670	50,421	97,091	62,412	30,774
1880	36,509	56,225	92,734	59,482	32,879
1881	32,170	54,057	86,227	61,689	31,607
1882	35,509	58,366	93,875	55,683	42,877
1883	35,653	63,493	99,146	59,350	40,469
1884	39,767	69,622	109,390	64,691	51,263
1885	41,933	81,616	123,549	62,080	54,323
1886	42,969	65,046	108,015	60,511	41,158
1887	29,198	73,891	103,089	69,453	53,096
1888	44,603	90,867	135,470	(a)72,066	42,562
1889	(b)38,576	101,407	139,983	75,627	65,759
1890	(c)49,461	91,788	141,249	89,747	66,170

a Including 22,557 tons of Chile bars transferred to France.

b Including 1,166 tons of Chile bars transferred from France to England.

c Including 3,501 tons of Chile bars transferred from France to England.

The following figures from the Board of Trade returns for the past nine years show in detail the form in which the copper is brought into Great Britain and in what form it is exported:

Imports of copper into Great Britain from 1882 to 1890, inclusive.

Character.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Pure in pyrites	15,672	15,016	14,077	16,333	13,905	14,940	15,448	16,097	16,422
Pure in precipitate.....	17,935	23,645	19,688	21,398	19,323	21,819	26,366	25,110	25,563
Pure in ore	15,489	15,880	24,677	15,683	13,749	15,148	19,452	22,219	18,000
Pure in regulus	9,270	8,952	11,181	28,202	18,069	21,984	29,601	37,981	31,803
Bars, cakes, etc	35,509	35,653	39,767	41,933	42,969	29,198	44,603	(a)38,576	49,461
Total.....	93,875	99,146	109,390	123,549	108,015	103,089	135,470	139,983	141,249

a Including 1,166 tons of Chile bars transferred from France to England.

The following table gives the details relating to the British imports of precipitate and regulus:

Imports of precipitate and regulus into Great Britain from 1882 to 1890, inclusive.

Countries.	1882.	1883.	1884.	1885.	1886.	Fine copper.	1887.	Fine copper.	1888. Fine copper.	1889. Fine copper.	1890. Fine copper.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Portugal	7,301	8,873	7,161	8,283	6,657	24,032	\$10,758	24,754	30,119	28,157	28,018
Spain	21,398	28,962	27,621	38,267	38,666	737	37,892	718	734	1,919	2,122
Chile.....	10,882	6,384	10,699	5,255	1,637	10,853	24,229	15,039	20,752	26,581	18,897
United States	5,805	29,861	16,105	1,770	5,366	2,292	4,362	6,434	8,329
Other countries ..	9,716	13,509	11,124	6,000	5,240
Total.....	49,297	57,728	62,410	87,666	68,305	79,840
Fine copper	27,205	32,597	34,172	49,600	37,392	42,803	55,967	63,091	57,366

The notable feature is the heavy increase in receipts of fine copper in matte from the United States in 1889 and the falling off in 1890.

In detail, the imports of copper in the form of bars, cakes, etc., into Great Britain were as follows:

Imports of copper, wrought and unwrought, into Great Britain.

Countries.	1880.	1881.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Chile.....	24,258	21,019	22,585	22,799	22,843	24,832	24,748	17,516	21,534	17,631	19,716
Australia	9,406	9,150	8,152	9,531	9,329	8,564	9,933	5,412	5,398	5,567	5,355
America	1,773	3,584	3,375	2,110	1,469	4,680	3,799	1,269
Other countries.....	2,845	2,001	4,772	1,550	4,011	5,160	6,178	4,801	12,991	(a)11,575	23,121
Total.....	36,509	32,170	35,509	35,653	39,767	41,931	42,969	29,198	44,603	38,572	49,461

a Including 1,166 tons of Chile bars transferred from France to England.

Messrs. James Lewis & Son, of Liverpool, estimate as follows the imports of other than Chile copper into Liverpool, London, and Swansea during the years 1882, 1883, 1884, 1885, 1886, 1887, 1888. 1

1890, which represents the total imports, with the exception of precipitate, into Newcastle and Cardiff, reliable returns of which can not be obtained, but which is estimated to vary from 8,000 to 10,000 tons fine per annum:

Imports of copper product into Liverpool, Swansea, and London.

Countries.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Chile.....	30,112	27,504	31,298	28,985	27,191	20,008	24,479	22,070	22,909
United States.....	745	9,410	17,309	24,037	13,483	16,534	25,730	30,729	20,171
Spain and Portugal.....	464	2,788	2,359	4,655	5,721	5,178	5,915	5,189	5,202
Spain (precipitate).....	8,757	11,249	10,009	9,186	10,038	13,042	15,568	17,192	18,430
Spain (pyrites).....	15,673	15,017	14,077	16,333	13,905	14,940	15,448	16,097	16,422
Australia.....	9,847	9,694	9,685	8,951	10,096	6,047	6,746	6,285	6,561
Cape of Good Hope.....	5,298	5,670	6,042	5,405	7,073	8,271	8,829	11,507	9,927
New Quebrada.....	3,164	3,960	3,675	4,074	3,055	2,261	3,574	4,299	5,245
Japan.....			1,064	3,010	3,572	200	4,469	2,523	10,674
Italy.....	1,386	1,091	1,310	835	889	1,055	1,058	1,043	953
Norway.....	446	296	289	27			545	234	80
Canada.....	347	448	266		8	94	156	181	264
Newfoundland.....	1,362	1,185	224	723	891	359	465	631	1,552
Mexico.....	372	489	291	374	243	61	158	3,938	3,325
Peru.....	821	426	408	229	68	13	202	271	254
River Platte.....	260	319	131	233	179	167	135	184	143
Other countries.....	925	946	284	325	1,049	1,074	4,054	1,389	225
Total tons fine.....	79,979	90,492	98,721	107,382	97,461	89,304	117,531	123,762	122,337

In spite of a decline in 1890 of receipts from the United States to the extent of over 10,000 tons, the imports nearly reached the exceptionally high figure for 1889.

The following table, giving the details of the imports of copper from the United States into England and France, for a series of years in different forms, is particularly interesting as showing how closely this country is pushing Chile as a rival contributor to the world's markets:

Imports of copper from the United States in England and France.

	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
England:									
Ore.....	274	4,940	11,023	1,875	420	26	298	349	5
Matte.....	471	2,512	2,722	18,895	10,853	15,039	20,752	26,581	18,897
Bars and ingots.....		1,773	3,584	3,375	2,210	1,469	4,680	3,799	1,269
Total.....	745	9,225	17,329	24,145	13,483	16,534	25,730	30,729	20,171
France.....	1,072	4,513	7,205	9,235	4,107	3,910	6,496	1,058	1,733
United States into England and France.....	1,817	13,738	24,534	33,380	17,650	20,444	32,226	31,787	21,904
Chile into England and France.....	42,306	43,568	42,384	35,342	35,448	29,019	32,947	22,020	24,641

The exports of copper from Great Britain in different forms were as follows:

Exports of copper from Great Britain from 1882 to 1890, inclusive.

Character.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Raw English.....	12,776	16,777	17,943	18,766	19,036	40,700	32,058	48,189	58,571
Sheets.....	15,698	16,071	20,669	21,108	17,927				
Yellow metal, at 60 per cent.....	10,892	11,918	11,602	12,551	11,958	10,153	4,513	9,195	10,514
Brass, at 70 per cent.....	3,499	3,381	3,735	3,233	3,001	3,146	2,650	3,773	3,721
Total.....	42,865	48,147	53,949	55,658	51,922	53,999	39,221	61,157	72,806
Fine foreign.....	12,818	11,203	10,742	6,422	8,589	15,454	22,845	14,470	16,941
Total.....	55,683	59,350	64,691	62,080	60,511	69,453	72,066	75,627	89,747

a Including 22,557 tons Chile bars transferred to France.

FRANCE.

The direct imports of copper from different countries into France were as follows, for a series of years:

Direct imports into France, from 1883 to 1890, inclusive.

Countries.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Chile.....	16,064	11,086	6,357	8,257	9,011	8,468	2,470	2,803
United States.....	4,513	7,205	9,235	4,167	3,910	6,496	1,058	1,733
Mexico.....						2,700	738	
Other countries.....	317	392	995	1,600	1,048	6,905	1,715	975
Total.....	20,894	18,683	16,587	14,024	13,969	24,569	5,981	5,511

These statistics do not, of course, include the quantities, notably of Chile copper, transferred from English to French warehouses. The heavy decline in the imports of France during 1889 and 1890, is due to the fact that the accumulations of the syndicate are being drawn upon.

L E A D .

BY C. KIRCHHOFF.

The maximum production in the United States was reached in the year 1889, when the smelting works and refining establishments in the United States made 182,967 tons of lead. Making allowance for the lead contents in Mexican ores imported, the output of metal from American ores rose from about 145,000 tons in 1887 to 152,000 tons in 1888 and to 156,000 tons in 1889. In 1890 a marked decline took place, the gross product falling from 182,967 tons in 1889 to 161,754 tons in 1890; or, deducting the metal contents of the Mexican ores, from 156,397 to 143,630 tons. The gross production of refined lead since 1887 and the metal contents of Mexican ores has been as follows:

Production of lead in the past four years.

Years.	Gross production.	Lead contents of Mexican ores.	Net American product.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
1887	160,700	(a) 15,000	145,700
1888	180,555	28,636	151,919
1889	182,967	26,570	156,397
1890	161,754	18,124	143,630

a Estimated.

The following table presents the figures of production of lead in the United States from 1825. Up to the year 1882 the figures have been compiled from the best data available. Since 1882 the statistics are those collected by this office, with the exception of the year 1889, when they were gathered by the Census Office.

Production of lead in the United States from 1825 to 1890, both inclusive.

Years.	Total production. (Short tons.)	Desilverized lead. (Short tons.)	Non argentiferous lead. (Short tons.)	Percentage of desilverized lead.
1825.....	1,500
1830.....	8,000
1831.....	7,500
1832.....	10,000
1833.....	11,000
1834.....	12,000
1835.....	13,000
1836.....	15,000
1837.....	13,500
1838.....	15,000

Production of lead in the United States from 1825 to 1890, both inclusive—Continued.

Years.	Total production. (Short tons.)	Desilverized lead. (Short tons.)	Non-argentiferous lead. (Short tons.)	Percentage of desilverized lead.
1839.....	17,500			
1840.....	17,000			
1841.....	20,500			
1842.....	24,000			
1843.....	25,000			
1844.....	26,000			
1845.....	30,000			
1846.....	28,000			
1847.....	28,000			
1848.....	25,000			
1849.....	23,500			
1850.....	22,000			
1851.....	18,500			
1852.....	15,700			
1853.....	16,800			
1854.....	16,500			
1855.....	15,800			
1856.....	16,000			
1857.....	15,800			
1858.....	15,300			
1859.....	16,400			
1860.....	15,600			
1861.....	14,100			
1862.....	14,200			
1863.....	14,800			
1864.....	15,300			
1865.....	14,700			
1866.....	16,100			
1867.....	15,200			
1868.....	16,400			
1869.....	17,500			
1870.....	17,830			
1871.....	20,000			
1872.....	25,880			
1873.....	42,540	20,159	22,381	47.39
1874.....	52,080			
1875.....	59,640	34,909	24,731	58.53
1876.....	64,070	37,649	26,421	58.76
1877.....	81,900	50,748	31,152	61.96
1878.....	91,060	64,290	26,770	70.60
1879.....	92,780	64,650	28,130	69.68
1880.....	97,825	70,135	27,690	71.69
1881.....	117,085	86,315	30,770	73.72
1882.....	132,890	103,875	29,015	78.17
1883.....	143,957	122,157	21,800	84.86
1884.....	139,897	119,965	19,932	85.75
1885.....	129,412	107,437	21,975	83.02
1886.....	135,629	114,829	20,800	84.66
1887.....	160,700	135,552	25,148	84.35
1888.....	180,555	151,465	29,090	83.89
1889.....	182,967	153,709	29,258	84.01
1890.....	161,754	130,903	31,351	80.62
1891(a).....	95,121	79,301	15,820	83.37

a First half.

Producers carried on the 1st of January, 1891, a stock of 10,389 short tons, as compared with 7,715 short tons on the 1st of January, 1890. It must be considered, however, that practically the bankers' stock of about 8,000 tons went into consumers' hands.

The census report for the calendar year 1889 possesses particular interest because it gives the results of a comprehensive effort to ascer-

tain the sources, territorially, of the lead produced in the United States. Some statisticians have still clung to the hope, long abandoned by this office, of distributing the lead product territorially on the basis of the returns of lead smelters. How impossible this is may be inferred from the fact that the desilverizers and refiners at Omaha, Kansas City, Aurora, Chicago and St. Louis, at a great distance from the producing States and Territories, smelted Rocky Mountain and foreign ores which yielded 33,638 tons of base bullion. How little the product of smelters in a State reflect the lead contents of the ores mined in its territory is evidenced by the fact that the census returns show the lead contents of Idaho ores to have been 23,172 tons, while its smelters produced only 878 tons. Arizona shipped ore to other States containing 3,158 tons of lead and yet did not do any smelting. Montana is credited with an ore product carrying 10,183 tons of metal, and yet its smelters produced 19,404 tons of base bullion. Utah works some Nevada ores, but in spite of that fact it made only 12,908 tons of base bullion, while the lead contents of its ores was 16,675 tons. The following table presents the result of the investigation made by the Census Office to ascertain the lead contents of the ores mined in the mountain States and Territories:

Lead contents of ores mined in the Western States and Territories in 1889.

States.	Short tons.
Arizona	3,158
California	53
Colorado	70,788
Idaho	23,172
Montana	10,183
Nevada	1,994
New Mexico	4,764
South Dakota	116
Utah	16,675
Total	130,903

The following is a list of the counties which in the census year produced ore containing an aggregate of more than 1,000 tons:

States and counties.	Short tons.	States and counties.	Short tons.
Arizona:		Montana:	
Cochise	1,274	Beaverhead	3,453
Pima	1,152	Jefferson	5,081
Colorado:		Meagher	1,060
Challee	3,307	Nevada:	
Clear Creek	1,539	Eureka	1,489
Gilpin	1,013	New Mexico:	
Lake	50,492	Dona Ana	1,029
Ouray	1,333	Grant	1,613
Pitkin	7,132	Socorro	1,187
San Juan	1,787	Utah:	
Summit	1,596	Beaver	4,487
Idaho:		Salt Lake	4,794
Alturas	1,219	Summit	5,681
Logan	2,751	Tooele	1,483
Shoshone	18,564		

These figures well illustrate how widely scattered the sources of lead supply are, and how many of them, while individually unimportant, con

tribute a large aggregate. The lead industry is therefore losing more and more of the characteristics peculiar to it in its earlier days of development, when in turn Eureka, Utah, and Leadville swayed it, and when the markets for the metal often moved with the fortunes of individual mines. Since then the Coeur d'Alene has risen to eminence, Mexico has become an important factor, and new districts on both sides of the northwestern frontier promise to add to the sources of supply.

The soft lead product of Missouri, Kansas, and Wisconsin has remained fairly stationary. The Census report has shown that the output of lead ores from those districts in which it is associated with zinc ore is relatively unimportant. Wisconsin, with an output of 24,832 tons of zinc ore, reported only 1,678 tons of lead ore, equivalent to about 1,000 tons of lead. Kansas produced in 1889, 3,617 tons of lead ore, equal to about 2,200 tons of metal, while out of the total of 44,482 tons of lead ore mined in Missouri not less than 34,766 tons were taken from mines which did not yield any zinc. Thus roughly the total amount of lead obtained as a by-product in mining zinc ore in the three States named is 9,000 tons. This proves that so far as lead is concerned the metal is little influenced by prosperity or depression in zinc mining. It should be noted also that a part of the lead ore won as an incidental product in zinc mining is utilized in the production of sublimed lead, the quantity of the latter having been 1,250 tons during the census year. Practically the make of soft lead is controlled by the operations of the three great Missouri lead mining companies, the St. Joe, Doe Run, and Mine La Motte, which during the census year made 21,456 short tons out of total soft lead product of 29,258 tons at a direct outlay for mining and smelting of \$1,034,287. What expansion in the industry there is to be must therefore come chiefly from them, or from new concerns established to work some of the areas of the same deposits which they have so long and so successfully worked. Their ability to produce the metal under any contingencies likely to arise is generally unquestioned, so that a steady but slow development is looked forward to.

So many conditions influence the production of lead in the Rocky Mountain region that it is practically impossible to arrive at any conclusions on the question to what extent low prices will restrict and high prices stimulate the output of the metal. It is known that under favorable conditions lean lead ores, practically free from silver, may be worked when they serve as the basis for the treatment, at remunerative prices, of dry and refractory silver ores. The report of the census shows that Rocky Mountain smelters which treated 819,382 tons of ore produced 110,843 tons of base bullion, equal to a yield of the smelting mixture of between 13.50 and 14 per cent, and that, including the amount of ore treated by four refiners, the yield from 928,163 tons of ore was 144,481 tons, equal to a yield of between 15.50 and 16 per cent, making a rough allowance for the unknown silver contents and dross. The presence of the precious metals, the presence or absence of zinc, the character of the ore, whether a carbonate or a sulphide, the char-

acter of the gangue in relation to the preponderance of silica over bases, all influence the commercial value of the lead ore, aside from the cost of running, the proximity to railroad transportation and to fuel. All these considerations have their influence in determining the minimum lead contents which allow of profitable marketing of the ore. Under the circumstances, only very broad generalizations are possible, and no specific detailed examination is practicable. Past experience has taught, however, that an approach to 3 cents for refined lead at New York, with silver below \$1 per ounce, exerts a pressure upon producers which leads to a restriction of output in the principal Rocky Mountain lead-producing districts.

The St. Joseph Lead Company has built a narrow-gauge railroad 32 miles long between Herculaneum and Bonne Terre, and is extending to Doe Run, and will soon be in a position to transfer its smelting operations to Herculaneum.

Under the management of Mr. J. M. Desloge, the Desloge Consolidated Lead Company is prospecting a tract of 2,300 acres of magnesian limestone similar to the Bonne Terre formation. Drilling is progressing with two diamond drills, and a shaft has been sunk to a depth of 220 feet, from which drifts, upraises and stopes have been started.

THE LEAD MARKET.

The year 1890 opened dull at 3.85 cents, but under a large business soon developed some strength. With more moderate sales, a downward tendency again developed, which was only temporarily checked early in February, and finally led to heavier transactions during that month at 3.75 cents. March brought a reaction, and the market gradually advanced to 4 cents, from which, however, it again receded to 3.82½ cents towards the close of the month. April opened dull, but an improved feeling carried the metal up to 4.05 cents, at which sales were made. The weight upon the market was the lead held by bankers, who, it was estimated, were carrying a stock of 8,000 tons, upon which advances up to 4 cents had been originally made. The market fluctuated a little early in May, and then, under consumers' buying in anticipation of a decision on the Mexican ore duty, rose to 4.32½ cents, receding towards the close of the month to 4.25 cents. Under a heavy business the metal rose again to 4.55 cents in June, the bankers being heavy sellers until their holdings of Corwith lead had been reduced to about 4,000 tons lying in Western markets. July developed a weaker tone, with only little business transpiring, and it was only towards the early part of August that there was more activity coupled with rising values. This tendency gathered strength rapidly, and in September had so fully developed that the importing point was reached—above 5 cents—and several thousand tons of foreign lead were disposed of. In spite of this ^{but} market advanced very rapidly, small lots selling up to 6 cents in October, with further transactions on a large scale in foreign lead.

The reaction, however, proved as sharp and as violent as the advance, and the difference between prices for future delivery of foreign and spot domestic at one time reached nearly half a cent per pound. The drop continued in November, the month closing dull, with spot domestic lead at 4.70 cents; foreign, at 4.95 cents; and domestic, December delivery, at 4.60 cents. The financial troubles of the month had a very marked effect upon lead, so that the price declined in December from 4.60 cents down to 4.15 cents, under pretty large sales, the month and year closing with the metal back to 4.05 cents.

The following table, prepared from the annual reports of the daily price of lead, compiled by Mr. E. A. Caswell, of New York, shows the monthly average prices from 1884 to June, 1891, inclusive:

Average monthly prices of common pig lead in New York City.

(Cents per pound.)

Months.	1884.	1885.	1886.	1887.	1888.	1889.	1890.	1891.
January	4.09	3.65	4.57	4.27	4.80	3.82½	3.82½	4.34½
February	3.98	3.65	4.75	4.43	4.92	3.68	3.79½	4.28½
March	4.12	3.67	4.87	4.35	5.14	3.69	3.91½	4.32½
April	3.84	3.63	4.77	4.29	4.72½	3.64½	3.87½	4.20½
May	3.64	3.67	4.72	4.49	4.24	3.79½	4.13	4.25½
June	3.62	3.73	4.77	4.62	3.88	3.97½	4.37	4.41
July	3.58	4.06	4.88	4.50	3.96	3.88	4.43
August	3.58	4.25	4.75	4.55	4.43	3.82½	4.51
September	3.61	4.26	4.63	4.44	4.99	3.92½	4.86
October	3.69	4.10	4.23	4.30	4.45	3.82½	5.21½
November	3.46	4.12	4.32	4.35	3.67½	3.79	4.90
December	3.60	4.57	4.32	5.00	3.73	3.82	4.19
Yearly average ..	3.73½	3.94½	4.63	4.46½	4.41	3.80½	4.33½

The following table gives the highest and lowest prices monthly for a series of years:

Highest and lowest prices of lead at New York City, monthly, from 1870 to 1890, inclusive.

(Cents per pound.)

Years.	January.		February.		March.		April.		May.		June.	
	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.
1870.....	(a) 6.30	6.20	6.25	6.17	6.20	6.10	6.25	6.15	6.25	6.20	6.25	6.20
1871.....	(a) 6.30	6.15	6.25	6.20	6.20	6.15	6.20	6.10	6.18	6.10	6.15	6.12
1872.....	(a) 6.00	5.90	6.00	5.87	6.00	5.87	6.12	5.90	6.62	6.25	6.62	6.40
1873.....	(a) 6.37	6.25	6.50	6.40	6.50	6.25	6.50	6.25	6.62	6.35	6.55	6.12
1874.....	(a) 8.00	6.90	6.25	6.00	6.25	6.12	6.25	5.90	6.00	5.75	6.00	5.62
1875.....	(a) 6.20	5.00	5.90	5.85	5.75	5.62	5.87	5.80	5.95	5.95	5.90	5.75
1876.....	(a) 6.00	5.87	6.37	6.00	6.50	6.40	6.40	6.12	6.50	6.10	6.50	6.25
1877.....	(b) 6.15	6.12	6.40	6.20	6.75	6.50	6.50	6.25	6.00	5.55	5.70	5.60
1878.....	4.35	4.00	3.87	3.65	3.87	3.62	3.75	3.50	3.50	3.25	3.50	3.12
1879.....	4.50	4.00	4.50	4.50	4.50	3.25	3.25	2.87	3.12	2.87	3.80	3.12
1880.....	6.10	5.50	6.00	5.87	5.95	5.30	5.75	5.40	5.25	4.40	4.75	4.50
1881.....	5.00	4.30	5.10	4.80	4.85	4.62	4.85	4.37	4.70	4.25	4.50	4.25
1882.....	5.15	4.95	5.20	5.00	5.12	4.85	5.00	4.90	4.85	4.60	4.90	4.55
1883.....	4.70	4.60	4.60	4.50	4.65	4.50	4.62	4.40	4.55	4.40	4.45	4.40
1884.....	4.50	3.75	4.10	3.75	4.15	4.10	4.05	3.62½	3.75	3.52½	3.65	3.57½
1885.....	3.70	3.55	3.70	3.60	3.70	3.62½	3.70	3.62½	3.75	3.60	3.85	3.62½
1886.....	4.70	4.50	4.90	4.60	4.95	4.85	4.90	4.65	4.75	4.65	4.90	4.65
1887.....	4.45	4.15	4.50	4.25	4.45	4.25	4.32½	4.20	4.70	4.30	4.70	4.50
1888.....	4.90	4.50	5.15	4.60	5.25	5.00	5.05	4.55	4.62½	4.00	4.10	3.65
1889.....	3.90	3.75	3.75	3.60	3.75	3.65	3.67½	3.60	3.87½	3.60	4.05	3.90
1890.....	3.85	3.80	3.85	3.75	3.95	3.85	4.07½	3.85	4.35	4.00	4.50	4.25
1891.....	4.50	4.05	4.50	4.25	4.37½	4.25	4.32½	4.10	4.37½	4.20	4.50	4.35

Highest and lowest prices of lead at New York City, etc.—Continued.

Years.	July.		August.		September.		October.		November.		December.	
	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.
1870.....	6.30	6.20	6.37	6.32	6.37	6.30	6.37	6.25	6.35	6.25	6.35	6.25
1871.....	6.15	6.10	6.12	6.00	6.10	6.00	6.00	5.87	6.00	5.90	6.00	5.75
1872.....	6.62	6.40	6.50	6.40	6.50	6.30	6.62	6.40	6.60	6.50	6.60	6.42
1873.....	6.12	6.00	6.25	6.00	6.62	6.37	6.75	6.25	6.50	6.00	6.12	6.00
1874.....	5.80	5.62	5.80	5.65	6.10	5.65	6.35	6.10	6.50	6.25	6.40	6.12
1875.....	6.00	5.95	5.95	5.87	5.87	5.70	5.65	5.60	5.87	5.65	5.95	5.87
1876.....	6.35	6.20	6.37	6.25	6.25	6.00	6.00	5.80	5.80	5.70	5.70	5.65
1877.....	5.60	5.37	5.12	4.90	4.85	4.75	4.85	4.25	4.75	4.50	4.60	4.50
1878.....	3.62	3.25	3.50	3.20	3.45	3.25	3.60	3.37	3.95	3.60	4.00	3.90
1879.....	4.10	3.90	4.05	4.00	4.00	3.75	5.50	4.00	5.62	5.00	5.60	5.50
1880.....	4.75	4.25	5.00	4.30	4.90	4.80	4.87	4.65	4.85	4.75	4.75	4.25
1881.....	4.90	4.50	4.95	4.75	5.37	4.95	5.25	4.87	5.25	4.90	5.25	5.00
1882.....	5.15	4.90	5.10	4.95	5.15	4.95	5.15	4.85	4.90	4.50	4.75	4.50
1883.....	4.40	4.30	4.30	4.20	4.32	4.30	4.32	4.12	4.05	3.65	3.75	3.60
1884.....	3.70	3.55	3.70	3.52½	3.75	3.55	3.75	3.62	3.55	3.37½	3.75	3.50
1885.....	4.15	3.87½	4.25	4.12	4.25	4.00	4.25	4.00	4.60	4.00	4.67½	4.50
1886.....	4.90	4.75	4.80	4.75	4.70	4.45	4.30	4.00	4.40	4.10	4.35	4.25
1887.....	4.67½	4.40	4.62½	4.55	4.55	4.25	4.40	4.20	4.75	4.25	5.15	4.90
1888.....	4.07½	3.85	4.97½	4.15	5.12½	4.90	5.12½	3.62½	3.82½	3.60	3.82½	3.60
1889.....	4.05	3.80	3.95	3.75	4.00	3.85	3.90	3.75	3.90	3.75	3.90	3.75
1890.....	4.50	4.40	4.72½	4.35	5.00	4.67½	5.25	5.00	5.25	4.60	4.60	4.05

The following tables, compiled by Mr. E. A. Caswell, show the daily fluctuation in prices in 1889, 1890, and the first half of 1891:

Price of common pig lead in New York City in 1889.

Days.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.	Aug.	Sept.	Oct.	Nov.	Dec.
1.....	H.	3.75	3.70	3.65	3.60	3.90	4.05	3.95	S.	3.85	3.75	S.
2.....	3.77½	3.75	3.72½	3.65	3.67½	3.87½	4.05	3.90	H.	3.85	3.75	3.75
3.....	3.85	S.	S.	3.65	3.67½	3.92½	4.00	3.85	3.97½	3.90	S.	3.75
4.....	3.90	3.75	3.65	3.65	3.80	3.97½	H.	S.	4.00	3.90	3.75	3.75
5.....	3.90	3.75	3.72½	3.65	S.	4.00	3.95	3.85	4.00	3.90	H.	3.75
6.....	S.	3.75	3.72½	3.65	3.87½	4.00	3.90	3.85	4.00	S.	3.85	3.75
7.....	3.85	3.75	3.72½	S.	3.87½	3.97½	S.	3.85	4.00	3.90	3.90	3.75
8.....	3.85	3.70	3.72½	3.65	3.87½	3.97½	3.90	3.85	S.	3.90	3.90	S.
9.....	3.85	3.70	3.72½	3.65	3.87½	S.	3.90	3.80	4.00	3.90	3.90	3.75
10.....	3.85	S.	S.	3.67½	3.87½	3.97½	3.90	3.75	3.95	3.90	S.	3.75
11.....	3.85	3.70	3.72½	3.67½	3.87½	3.97½	3.90	S.	3.95	3.85	3.90	3.75
12.....	3.85	3.65	3.72½	3.67½	S.	3.90	3.85	3.75	3.90	3.85	3.80	3.75
13.....	S.	3.65	3.72½	3.67½	3.87½	3.90	3.85	3.75	3.90	S.	3.80	3.87½
14.....	3.85	3.65	3.75	S.	3.87½	3.92½	S.	3.80	3.90	3.85	3.80	3.87½
15.....	3.85	3.60	3.70	3.65	3.87½	3.92½	3.85	3.80	S.	3.85	3.80	S.
16.....	3.85	3.60	3.70	3.65	3.87½	S.	3.85	3.80	3.90	3.85	3.75	3.87½
17.....	3.85	S.	S.	3.65	3.70	4.00	3.85	3.80	3.90	3.85	S.	3.90
18.....	3.85	3.65	3.70	3.65	3.70	4.00	3.85	S.	3.90	3.85	3.75	3.90
19.....	3.85	3.65	3.70	3.65	S.	4.00	3.80	3.80	3.90	3.80	3.75	3.90
20.....	S.	3.65	3.70	3.65	3.75	4.00	3.80	3.80	3.90	S.	3.75	3.90
21.....	3.85	3.65	3.65	S.	3.70	4.00	S.	3.80	3.90	3.80	3.75	3.87½
22.....	3.80	H.	3.65	3.62½	2.70	3.95	3.82½	3.80	S.	3.75	3.75	S.
23.....	3.80	3.65	3.65	3.62½	3.70	S.	3.80	3.80	3.90	3.75	3.75	3.85
24.....	3.75	S.	S.	3.65	3.70	4.00	3.80	3.80	3.90	3.75	S.	3.85
25.....	3.75	3.65	3.65	3.65	3.85	4.00	3.80	S.	3.90	3.75	3.75	H.
26.....	3.80	3.65	3.65	3.62½	S.	4.00	3.80	3.80	3.90	3.75	3.75	3.85
27.....	S.	3.65	3.65	3.60	3.85	4.00	3.80	3.80	3.90	S.	3.75	3.80
28.....	3.80	3.65	3.65	S.	3.85	4.00	S.	3.85	3.85	3.75	H.	3.85
29.....	3.75	3.65	3.60	3.85	4.05	3.80	3.85	S.	3.75	3.75	S.
30.....	3.75	3.65	H.	H.	S.	3.97½	3.90	3.85	3.75	3.75	3.85
31.....	3.75	S.	3.85	3.97½	3.90	3.75	3.85
Average.	3.82½	3.68	3.69	3.64½	3.79½	3.97½	3.88	3.82½	3.92½	3.82½	3.79	3.82

Price of common pig lead in New York City in 1890.

Days.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.	Aug.	Sept.	Oct.	Nov.	Dec.
1.....	H.	3.80	3.85	3.85	4.07½	S.	4.42½	4.40	H.	5.00	5.25	4.60
2.....	3.85	S.	S.	3.85	4.05	4.25	4.42½	4.35	4.67½	5.00	S.	4.60
3.....	3.85	3.80	3.85	3.85	4.00	4.25	4.42½	S.	4.75	5.00	5.25	4.60
4.....	3.85	3.80	3.85	H.	S.	4.25	H.	4.35	4.75	5.00	H.	4.55
5.....	S.	3.85	3.85	3.85	4.00	4.25	4.42½	4.35	4.75	S.	5.25	4.50
6.....	3.85	3.85	3.95	S.	4.00	4.25	S.	4.35	4.75	5.25	5.10	4.40
7.....	3.85	3.80	3.95	3.85	4.05	4.25	4.42½	4.35	S.	5.25	5.10	S.
8.....	3.85	3.80	3.95	3.85	4.05	S.	4.42½	4.35	4.75	5.25	5.10	4.30
9.....	3.85	S.	S.	3.85	4.05	4.32½	4.42½	4.35	4.75	5.25	S.	4.20
10.....	3.85	3.80	3.95	3.85	4.05	4.32½	4.42½	S.	4.75	5.25	5.10	4.15
11.....	3.80	3.80	3.95	3.85	S.	4.35	4.42½	4.35	4.75	5.25	5.10	4.15
12.....	S.	3.80	3.95	3.85	4.05	4.35	4.42½	4.35	4.75	S.	5.10	4.10
13.....	3.80	3.80	3.95	S.	4.05	4.35	S.	4.50	4.75	5.25	5.00	4.10
14.....	3.80	3.75	3.95	3.85	4.05	4.35	4.42½	4.50	S.	5.25	5.00	S.
15.....	3.80	3.75	3.95	3.85	4.10	S.	4.42½	4.50	4.75	5.25	5.00	4.10
16.....	3.80	S.	S.	3.85	4.10	4.35	4.50	4.50	4.75	5.25	S.	4.05
17.....	3.80	3.75	3.95	3.85	4.12½	4.35	4.50	S.	4.95	5.25	5.00	1.05
18.....	3.80	3.75	3.95	3.85	S.	4.45	4.45	4.62½	4.95	5.25	4.75	4.05
19.....	S.	3.75	3.95	3.85	4.15	4.45	4.45	4.62½	4.95	S.	4.75	4.05
20.....	3.80	3.75	3.95	S.	4.17½	4.50	S.	4.62½	5.00	5.25	4.65	4.05
21.....	3.80	3.75	3.95	3.85	4.35	4.50	4.45	4.62½	S.	5.25	4.65	S.
22.....	3.85	H.	3.90	3.90	4.30	S.	4.45	4.60	5.00	5.25	4.60	4.05
23.....	3.85	S.	S.	3.90	4.20	4.50	4.45	4.60	5.00	5.25	S.	4.05
24.....	3.80	3.75	3.90	3.90	4.20	4.45	4.40	S.	5.00	5.25	4.60	4.05
25.....	3.80	3.85	3.90	3.90	S.	4.42½	4.40	4.60	5.00	5.25	4.60	H.
26.....	S.	3.85	3.90	3.90	4.20	4.42½	4.40	4.72½	5.00	S.	4.60	4.05
27.....	3.80	3.85	3.90	S.	4.30	4.42½	S.	4.67½	5.00	5.25	H.	4.05
28.....	3.80	3.85	3.85	3.90	4.25	4.42½	4.40	4.67½	S.	5.25	4.60	S.
29.....	3.80	3.85	3.90	4.25	S.	4.40	4.67½	5.00	5.25	4.60	4.05
30.....	3.85	S.	4.07½	4.42½	4.40	4.67½	5.00	5.25	S.	4.05
31.....	3.85	3.85	4.25	4.40	S.	5.25	4.05
Average.	3.82½	3.79½	3.91½	3.87½	4.13	4.37	4.43	4.51	4.86	5.21½	4.90	4.19

Price of common pig lead in New York City during six months ending June 30, 1891.

Days.	Jan.	Feb.	Mar.	Apr.	May.	June.	Days.	Jan.	Feb.	Mar.	Apr.	May.	June
1.....	H.	S.	S.	4.32½	4.20	4.42½	18.....	S.	4.25	4.30	4.15	4.20	4.35
2.....	4.05	4.35	4.25	4.32½	4.20	4.42½	19.....	4.50	4.25	4.30	S.	4.30	4.35
3.....	4.05	4.35	4.25	4.32½	S.	4.42½	20.....	4.40	4.25	4.30	4.10	4.25	4.35
4.....	S.	4.35	4.25	4.30	4.20	4.50	21.....	4.35	4.25	4.37½	4.10	4.25	S.
5.....	4.05	4.30	4.35	S.	4.20	4.50	22.....	4.30	S.	S.	4.12½	4.35	4.35
6.....	4.40	4.30	4.35	4.30	4.26	4.50	23.....	4.30	H.	4.35	4.12½	4.37½	4.35
7.....	4.40	4.50	4.35	4.32½	4.20	S.	24.....	4.25	4.25	4.35	4.12½	S.	4.40
8.....	4.40	S.	S.	4.30	4.20	4.45	25.....	S.	4.30	4.35	4.12½	4.37½	4.45
9.....	4.40	4.30	4.32½	4.25	4.20	4.40	26.....	4.25	4.25	4.35	S.	4.37½	4.50
10.....	4.40	4.30	4.32½	4.25	S.	4.40	27.....	4.25	4.25	4.35	4.12½	4.35	4.45
11.....	S.	4.25	4.32½	4.25	4.20	4.40	28.....	4.27½	4.25	4.35	4.20	4.35	S.
12.....	4.40	4.25	4.32½	S.	4.20	4.35	29.....	4.27½	S.	4.20	4.35	4.45
13.....	4.50	4.25	4.32½	4.25	4.20	4.35	30.....	4.37½	4.35	4.20	H.	4.45
14.....	4.50	4.25	4.32½	4.15	4.20	S.	31.....	4.35	4.32½	S.
15.....	4.50	S.	S.	4.15	4.20	4.35	Average.	4.34½	4.28½	4.32½	4.20½	4.25½	4.41
16.....	4.50	4.25	4.32½	4.15	4.20	4.35							
17.....	4.50	4.25	4.30	4.15	S.	4.35							

Lead imported and entered for consumption in the United States, 1867 to 1890, inclusive.

[Calendar years ending December 31 from 1886 to 1890; previous years end June 30.]

Years.	Ore and dross.		Pigs and bars.		Sheets, pipe, and shot.		Shot.		Not otherwise specified.	Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.		
	<i>Lbs.</i>		<i>Lbs.</i>		<i>Lbs.</i>		<i>Lbs.</i>			
1867...	611	\$25	65,322,923	\$2,812,668	185,825	\$9,560			\$6,222	\$2,828,475
1868...	6,945	239	63,254,677	2,668,915	142,137	7,229			6,604	2,682,987
1869...			87,865,471	3,653,481	307,424	15,531			18,885	3,687,897
1870...	5,973	176	85,895,724	3,530,837	141,681	6,879			10,444	3,548,336
1871...	316	10	91,496,715	3,721,096	86,712	4,209			8,730	3,734,045
1872...	32,331	1,425	73,086,657	2,929,623	15,518	859			20,191	2,952,098
1873...			72,423,641	3,233,011	105	12		420	21,593	3,254,576
1874...			46,205,154	2,231,817				1,349	36,484	2,269,650
1875...	13,206	320	32,770,712	1,539,017				58	4	1,585,115
1876...			14,329,366	682,132				20,007	1,204	710,442
1877...	1,000	20	14,583,845	671,482				16,502	1,041	673,785
1878...			6,717,052	294,233				15,829	963	295,309
1879...			1,216,500	42,983				3,748	209	930
1880...			6,723,706	246,015				1,120	54	371
1881...	5,981	97	4,322,068	159,129				900	65	1,443
1882...	21,698	500	6,079,304	202,603				1,469	99	2,449
1883...	600	17	4,037,867	130,108				1,510	79	8,030
1884...	419	13	3,072,738	85,395	15,040	630				1,992
1885...	4,218	57	5,862,474	143,103	971,951	22,217				1,372
1886...	715,588	9,699	17,582,298	491,310	27,357	1,218				964
1887...	153,731	21,487	7,716,783	219,770	27,941	1,286				302
1888...	88,870	2,468	2,582,236	69,891	23,103	1,252				977
1889...	328,315	7,468	2,773,622	76,243	35,859	1,417				1,297
1890...	493,463	12,947	19,336,233	593,671	68,314	3,338				1,133

Old and scrap lead imported and entered for consumption in the United States, 1867 to 1890, inclusive.

[Calendar years ending December 31 from 1886 to 1890; previous years end June 30.]

Years.	Quantity.	Value.	Years.	Quantity.	Value.
	<i>Pounds.</i>			<i>Pounds.</i>	
1867.....	1,255,233	\$53,202	1879.....	42,283	\$1,153
1868.....	2,465,575	101,586	1880.....	213,063	5,262
1869.....	2,983,272	123,068	1881.....	123,018	2,729
1870.....	3,756,785	150,379	1882.....	220,702	5,949
1871.....	2,289,688	94,467	1883.....	1,094,133	31,724
1872.....	4,257,778	171,324	1884.....	160,356	4,830
1873.....	3,545,098	151,756	1885.....	4,806	106
1874.....	395,516	13,897	1886.....	24,726	832
1875.....	382,150	13,964	1887.....	136,625	4,323
1876.....	265,860	9,534	1888.....	33,100	904
1877.....	249,645	8,383	1889.....	50,816	1,494
1878.....	106,342	3,756	1890.....	18,246,165	567,364

Lead and manufactures of lead, of domestic production, exported from the United States.

Fiscal years ending September 30 until 1842, fiscal years ending June 30 until 1885, and calendar years ending December 31 since.	Manufactures of—			Bars, shot, etc.		Total value.
	Lead.		Pewter and lead.	Quantity.	Value.	
	Quantity.	Value.	Value.			
	<i>Pounds.</i>			<i>Pounds.</i>		
1790.....	13,440	\$810				\$810
1803 (barrels).....	900					
1804.....	19,804					
1805.....	8,000					
1808.....	40,533					
1809.....	126,537					
1810.....	172,323					
1811.....	65,497					
1812.....	74,875					
1813.....	276,940					

Lead and manufactures of lead, of domestic production, etc.—Continued.

Fiscal years ending September 30 until 1842, fiscal years ending June 30 until 1885, and calendar years ending De- cember 31 since.	Manufactures of—			Bars, shot, etc.		Total value.
	Lead.		Pewter and lead.	Quantity.	Value.	
	Quantity.	Value.	Value.			
	<i>Pounds.</i>			<i>Pounds.</i>		
1814.....	43,600					
1815.....	40,245					
1816.....	35,844					
1817.....	111,034	\$9,993				\$9,993
1818.....	281,168	22,493				22,493
1819.....	94,362	7,549				7,549
1820.....	25,699	1,799				1,799
1821.....	56,192	3,512				3,512
1822.....	66,316	4,244				4,244
1823.....	51,549	3,098				3,098
1824.....	18,604	1,356				1,356
1825.....	189,930	12,697				12,697
1826.....	47,337	3,347	\$1,820			5,167
1827.....	50,160	3,761	6,183			9,944
1828.....	76,882	4,184	5,545			9,720
1829.....	179,952	8,417	5,185			13,602
1830.....	128,417	4,831	4,172			9,003
1831.....	152,578	7,068	6,422			13,490
1832.....	72,439	4,483	983			5,466
1833.....	119,407	5,685	2,010			7,695
1834.....	13,480	805	2,224			3,029
1835.....	50,418	2,741	433			3,174
1836.....	34,600	2,218	4,777			6,995
1837.....	297,488	17,015	3,132			20,147
1838.....	375,231	21,747	6,461			28,208
1839.....	81,377	6,003	12,637			18,640
1840.....	882,620	39,687	15,296			54,983
1841.....	2,177,164	96,748	20,546			117,294
1842.....	14,552,357	523,428	16,789			540,217
1843 (nine months).....	15,366,918	492,765	7,121			499,886
1844.....	18,420,407	595,238	10,018			605,256
1845.....	10,188,024	342,646	14,404			357,050
1846.....	16,823,766	614,518	10,278			624,796
1847.....	3,326,028	124,981	13,694			138,675
1848.....	1,994,704	84,278	7,739			92,017
1849.....	680,249	30,198	13,196			43,394
1850.....	261,123	12,797	22,682			35,479
1851.....		16,426	229,448		\$11,774	28,200
1852.....		18,469	747,930		32,725	51,194
1853.....		14,064	100,778		5,510	19,604
1854.....		16,478	401,247		26,874	43,352
1855.....		5,233	165,533		14,298	19,531
1856.....		5,628	310,029		27,512	33,140
1857.....		4,818	870,541		58,624	63,442
1858.....		27,327	900,607		48,119	75,446
1859.....		28,782	313,988		28,575	57,357
1860.....		56,081	903,468		50,446	106,527
1861.....		30,534	109,023		6,241	36,775
1862.....		28,832	79,231		7,334	36,166
1863.....		30,609	237,239		22,634	53,243
1864.....		30,411	223,752		18,718	49,129
1865.....		29,271	852,895		132,666	161,937
1866.....		44,483	25,278		2,323	46,806
1867.....		27,559	99,158		5,300	32,859
1868.....		37,111	438,040		34,218	71,329
1869.....			17,249			17,249
1870.....		28,315				28,315
1871.....		79,880				79,880
1872.....		48,132				48,132
1873.....		13,392				13,392
1874.....		302,044				302,044
1875.....		429,309				429,309
1876.....		102,726				102,726
1877.....		49,835				49,835
1878.....		314,904				314,904
1879.....		280,771				280,771
1880.....		49,899				49,899
1881.....		39,710				39,710
1882.....		178,779				178,779
1883.....		43,108				43,108
1884.....		135,156				135,156
1885.....		123,466				123,466
1886.....		136,666				136,666
1887.....		140,065				140,065
1888.....		194,216				194,216
1889.....		161,614				161,614
1890.....		181,030				181,030

ZINC.

BY C. KIRCHHOFF.

During the years 1889 and 1890 the zinc industry of the United States showed steady progress, the development in the production taking place particularly, however, in the West. The census report, which covered the calendar year 1889, for the first time revealed many facts relating to the industry which are of special interest. The production of zinc ore in the leading States and counties was as follows:

Production of zinc ore in the leading States in 1889.

States and counties.	Quantity.	Value.	States and counties.	Quantity.	Value.
Wisconsin:	<i>Short tons.</i>		Missouri—continued.		
Iowa county	16,996	\$237,463	St. Francois county	<i>Short tons.</i>	
Lafayette county	7,132	152,973	ty	2,310	\$23,100
Grant county	703	10,132	Total Missouri.	93,131	2,024,057
Total Wisconsin.	24,831	400,568	Iowa	450	3,600
Missouri:			Kansas	39,575	299,192
Barry county	180	2,340	Arkansas	130	3,250
Dade county	153	1,308	Eastern States	63,339	175,052
Greene county	677	17,139	Southern States	12,906	141,560
Jasper county	72,026	1,629,538	New Mexico	140	2,520
Lawrence county	9,463	158,665	Total United States	234,502	3,049,799
Morgan county	15	480			
Newton county	8,307	191,487			

It should be noted that a large part of the product credited to Kansas was crude, undressed ore, which makes its tonnage large, while the value is low.

The following is a summary of the census statistics relating to the spelter and zinc-oxide works of the United States:

Census statistics of spelter and zinc oxide.

Product:		Value of ore treated	\$4,154,403.98
Spelter short tons . .	58,860	Labor:	
Zinc oxide do	16,970	Foremen	82
Stock:		Mechanics	457
Spelter, January 1, 1889, short tons	2,781	Laborers	2,024
Spelter, January 1, 1890, short tons	2,492	Boys	127
Zinc oxide, January 1, 1889, short tons	1,425	Total wages	\$1,424,980.52
Zinc oxide, January 1, 1890, short tons	1,261	Office force	95
Ore treated short tons . .	196,309	Salaries	\$140,279.91
		Expenses:	
		Contractors	\$15,318.84
		Supplies	\$653,305.75
		All other	\$210,913.39

No direct deductions as to cost can be drawn from these figures, because they deal with two industries, which in some parts of the country are so closely associated that they are not separated in accounts and in other parts, notably in the West, are sharply separated. The outlays incidental to the rolling of 9,389 short tons of sheet zinc are also included. Reports from all the works in the United States show that the production of spelter has been as follows:

Production of spelter in the United States.

Years.	Short tons.	Years.	Short tons.
1873	7,343	1885	40,688
1875	15,833	1886	42,641
1880 (Census year ending May 31).	23,239	1887	50,340
1882	33,765	1888	55,903
1883	36,872	1889	58,860
1884	38,544	1890	63,683

Grouped by States, the product has been as follows:

Production of spelter in the United States, 1882 to 1890, inclusive, by States.

States.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Illinois	18,201	16,792	17,594	19,427	21,077	22,279	22,445	23,860	26,243
Kansas	7,366	9,010	7,859	8,502	8,932	11,955	10,432	13,658	15,199
Missouri	2,590	5,730	5,230	4,677	5,870	8,660	13,465	11,077	13,127
Eastern and Southern States.....	5,698	5,340	7,861	8,082	6,762	7,446	9,561	10,265	9,114
Total...	33,765	36,872	38,544	40,688	42,641	50,340	55,903	58,860	63,683

For the first time complete returns of stocks on hand have been received. The following are the aggregates:

Stocks of spelter.

States.	January 1—		
	1889.	1890.	1891.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Illinois.....	360	268	68
Kansas.....	800	1,075	233
Missouri.....		43	45
East and South.....	1,621	1,149	788
Total.....	2,781	2,535	1,134

The stock in the hands of producers is therefore small, considering the magnitude of the industry. The apparent consumption of domestic spelter increased, therefore, from 59,434 tons in 1889, to 69,084 tons in 1890.

Zinc imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Calendar years ending December 31 from 1886 to 1890; previous years end June 30.	Blocks or pigs.		Sheets.		Value of manufactures.	Total value.
	Quantity.	Value.	Quantity.	Value.		
	<i>Pounds.</i>		<i>Pounds.</i>			
1867.....	5,752,611	\$256,366	5,142,417	\$311,767	\$1,835	\$569,968
1868.....	9,327,968	417,273	3,557,448	203,883	1,623	622,779
1869.....	13,211,575	590,332	8,306,723	478,646	2,083	1,071,061
1870.....	9,221,121	415,497	9,542,687	509,860	21,696	947,053
1871.....	11,159,040	508,355	7,646,821	409,243	26,366	943,964
1872.....	11,802,247	522,524	10,704,944	593,885	58,668	1,175,077
1873.....	6,839,897	331,399	11,122,143	715,706	56,813	1,103,918
1874.....	3,593,570	203,479	6,016,835	424,504	48,304	676,287
1875.....	2,034,252	101,766	7,320,713	444,539	26,330	572,635
1876.....	947,322	56,082	4,611,360	298,308	18,427	372,817
1877.....	1,266,894	63,250	1,341,333	81,815	2,496	147,561
1878.....	1,270,184	57,753	1,255,620	69,381	4,892	132,026
1879.....	1,419,791	53,294	1,111,225	53,050	3,374	109,718
1880.....	8,092,620	371,920	4,069,310	210,230	3,571	585,721
1881.....	2,859,216	125,457	2,727,324	129,153	7,603	262,218
1882.....	18,408,391	736,964	4,413,042	207,032	4,940	948,936
1883.....	17,067,211	655,503	3,309,239	141,823	5,606	802,932
1884.....	5,869,738	208,852	952,253	36,120	4,795	249,767
1885.....	3,515,840	113,268	1,839,860	64,781	2,054	180,103
1886.....	4,300,830	136,138	1,092,400	40,320	9,162	185,620
1887.....	8,387,647	276,122	926,150	32,526	11,329	319,977
1888.....	3,825,947	146,156	295,287	12,558	12,080	170,794
1889.....	2,052,559	77,845	1,014,873	43,356	19,580	140,781
1890.....	1,997,524	101,335	781,266	43,495	9,740	154,570

Imports of zinc oxide in 1885, 1886, 1887, 1888, 1889, and 1890.

Calendar years ending December 31, from 1886 to 1890; previous years end June 30.	Dry.	In oil.
	<i>Pounds.</i>	<i>Pounds.</i>
1885.....	2,233,128	98,566
1886.....	2,526,389	79,788
1887.....	4,961,080	123,216
1888.....	1,401,342	51,985
1889.....	2,686,861	66,240
1890.....	2,631,458	102,298

Exports of zinc and zinc ore of domestic production, 1864 to 1890, inclusive.

Calendar years ending December 31, from 1886 to 1890; previous years end June 30.	Ore or oxide.		Plates, sheets, pigs, or bars.		Value of manufactures.	Total value.
	Quantity.	Value.	Quantity.	Value.		
	<i>Cwt.</i>		<i>Pounds.</i>			
1864.....	14,810	\$116,431	95,738	\$12,269	\$128,700
1865.....	99,371	114,149	184,183	22,740	136,889
1866.....	4,485	25,091	140,798	13,290	38,381
1867.....	3,676	32,041	312,227	30,587	62,628
1868.....	8,344	74,706	1,022,699	68,214	142,920
1869.....	65,411	65,411
1870.....	15,286	81,487	110,157	10,672	92,159
1871.....	9,621	48,292	76,380	7,823	56,115
1872.....	3,686	20,880	62,919	5,726	26,606
1873.....	234	2,304	73,953	4,656	6,960
1874.....	2,550	20,037	43,566	3,612	23,649
1875.....	3,083	20,659	38,090	4,245	\$1,000	25,904
1876.....	10,178	66,259	134,542	11,651	4,333	82,243
1877.....	6,428	34,468	1,419,922	115,122	1,118	150,708
1878.....	16,050	83,831	2,545,320	216,580	567	300,978
1879.....	10,660	40,399	2,132,949	170,654	211,053
1880.....	13,024	42,036	1,368,302	119,264	161,300
1881.....	11,390	16,405	1,491,786	132,805	168	149,378
1882.....	10,904	13,736	1,489,552	124,638	138,374
1883.....	3,045	11,509	852,333	70,981	734	83,224
1884.....	4,780	16,685	126,013	9,576	4,666	30,927
1885.....	6,840	22,824	101,685	7,270	4,991	35,685
1886.....	26,620	49,455	917,229	75,192	13,526	138,173
1887.....	4,700	17,286	136,670	9,017	16,789	43,092
1888.....	4,560	18,034	62,234	4,270	19,098	41,402
1889.....	26,760	73,802	879,785	44,049	35,732	153,583
1890.....	77,360	195,113	3,295,584	126,291	23,587	344,901

PRICES OF ZINC.

The following table summarizes the prices of spelter since 1875:

Prices of common western spelter in New York City, 1875 to 1890, inclusive.

[Cents per pound. Figures in parentheses are combination prices.]

Years.	January.		February.		March.		April.		May.		June.	
	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.
1875.....	6.75	6.37	6.67	6.25	6.50	6.20	(7.00)	6.50	(7.25)	7.15	(7.25)	7.15
1876.....	(7.60)	7.40	(7.75)	7.50	(7.75)	7.62	(8.00)	7.60	(8.00)	7.75	(8.00)	7.25
1877.....	6.50	6.25	6.62	6.50	6.50	6.37	6.37	6.25	6.25	6.00	6.12	5.87
1878.....	5.75	5.50	5.62	5.25	5.62	5.25	5.25	5.00	5.00	4.62	4.62	4.25
1879.....	4.50	4.25	4.62	4.40	4.62	4.37	4.75	4.25	4.50	4.25	4.37	4.12
1880.....	6.50	5.87	6.75	6.37	6.75	6.50	6.50	6.12	6.00	5.62	5.50	5.12
1881.....	5.25	4.87	5.25	5.12	5.00	4.87	5.12	4.75	5.00	4.87	5.00	4.75
1882.....	6.00	5.75	5.75	5.62	5.62	5.37	5.50	5.25	5.62	5.25	5.37	5.25
1883.....	4.62	4.50	4.62	4.50	4.75	4.62	4.75	4.60	4.75	4.50	4.62	4.37
1884.....	4.37	4.20	4.40	4.25	4.60	4.40	4.65	4.50	4.60	4.45	4.60	4.45
1885.....	4.50	4.12	4.30	4.25	4.30	4.12	4.30	4.12	4.25	4.10	4.10	4.00
1886.....	4.50	4.30	4.55	4.30	4.60	4.50	4.60	4.50	4.60	4.40	4.40	4.35
1887.....	4.63	4.50	4.60	4.40	4.60	4.40	4.65	4.45	4.65	4.45	4.65	4.40
1888.....	5.37	5.20	5.35	5.25	5.25	4.87	4.87	4.60	4.65	4.60	4.60	4.50
1889.....	5.00	5.00	5.00	4.90	4.87	4.70	4.65	4.65	4.85	4.62	5.00	5.00
1890.....	5.45	5.35	5.35	5.20	5.20	5.00	5.00	4.90	5.45	5.00	5.60	5.35

Years.	July.		August.		September.		October.		November.		December.	
	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.	Highest.	Lowest.
1875.....	(7.35)	7.25	(7.25)	7.10	(7.25)	7.10	(7.40)	7.15	(7.40)	7.15	(7.40)	7.15
1876.....	7.25	7.12	7.25	7.00	7.12	6.80	6.75	6.62	6.62	6.37	6.50	6.37
1877.....	5.87	5.62	5.90	5.80	5.87	5.75	5.90	5.70	5.87	5.62	5.75	5.50
1878.....	4.75	4.50	4.87	4.50	4.87	4.75	4.82	4.50	4.75	4.50	4.37	4.25
1879.....	4.75	4.37	5.62	4.80	6.00	5.62	6.37	6.00	6.25	5.87	6.25	6.00
1880.....	5.00	4.87	5.25	4.87	5.12	4.75	5.00	4.87	4.90	4.65	4.75	4.65
1881.....	5.00	4.75	5.12	5.00	5.25	5.00	5.37	5.25	5.87	5.50	6.00	5.87
1882.....	5.37	5.12	5.50	5.12	5.37	5.12	5.37	5.12	5.12	4.87	4.87	4.50
1883.....	4.50	4.30	4.40	4.30	4.50	4.40	4.45	4.35	4.40	4.37	4.37	4.35
1884.....	4.55	4.45	4.62	4.52	4.62	4.50	4.55	4.40	4.40	4.30	4.25	4.00
1885.....	4.40	4.10	4.60	4.40	4.62	4.50	4.62	4.50	4.60	4.45	4.60	4.45
1886.....	4.40	4.30	4.40	4.30	4.40	4.25	4.30	4.25	4.30	4.25	4.50	4.35
1887.....	4.50	4.50	4.60	4.55	4.65	4.60	4.65	4.50	4.80	4.52	5.87	5.00
1888.....	4.55	4.50	4.87	4.50	5.12	4.75	5.12	4.87	5.12	4.87	5.12	4.87
1889.....	5.10	5.00	5.20	5.15	5.15	5.10	5.15	5.10	5.25	5.05	5.35	5.30
1890.....	5.60	5.40	5.55	5.40	5.65	5.50	6.00	5.65	6.10	5.90	6.00	5.90

Opening the year 1890 with a steady market at 5.45 cents, a moderate business and freer offerings led to a decline to 5.35 cents, New York, toward the close of January. The falling market and general dullness continued during February and March, 5 cents being reached in that month. Good western spelter sold as low as 4.90 cents, New York, in April, but toward the close of that month developed a better feeling, rising to 5 cents. May brought a much better demand, and simultaneously a scarcity of ores told on the market, which went up to 5.45 cents. The rapid rise brought out some realizing to take profits on the part of second hands, which temporarily depressed the price to 5.35 cents in June, but when once these lots were disposed of the market rose to 5.60

cents under considerable purchases for consumption. The metal was steady during July and August, fluctuating in price between 5.40 cents and 5.55 cents as the extremes. The large consumption by brass-makers and galvanizers, and the general buoyancy of the whole metal trade, brought spelter up to 5.65 cents in September, and to 6.10 cents in October. The November financial troubles had their effect upon the market, as they did in all other metals, but in a much less marked degree, the price holding up to 5.90 cents toward the close of November and during December.

Messrs. Henry R. Merton & Co., of London, make the following report on the spelter production of Europe:

Estimate of the production of zinc in Europe.

Countries.	1890.	1889.	1888.	1887.	1886.	1885.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Rhine district and Belgium	137,630	134,648	133,245	130,995	129,020	129,754
Silesia	87,475	85,483	83,375	81,375	81,630	79,623
Great Britain	29,145	30,806	26,783	19,339	20,730	24,299
France and Spain ...	18,240	16,785	16,140	16,028	15,305	14,847
Poland	3,620	3,026	3,785	3,580	4,145	5,019
Austria	7,135	6,330	4,977	5,338	5,000	5,610
Total Europe ...	283,245	277,078	268,305	256,655	255,830	259,152

Countries.	1884.	1883.	1882.	1881.	1880.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Rhine district and Belgium ...	129,240	123,891	119,193	110,989	98,830
Silesia	76,116	70,405	68,811	66,497	64,459
Great Britain	29,259	28,661	25,581	24,419	(a) 22,000
France and Spain	15,341	14,671	18,075	(a) 18,358	15,000
Poland	4,164	3,733	4,400	(a) 4,000	(a) 4,000
Austria	6,170	6,267	6,709	5,825	5,970
Total Europe	260,290	247,628	242,769	230,088	210,259

a Estimated.

The output of the works in the different districts was as follows:

Production of zinc by principal foreign producers.

Districts.	1890.	1889.	1888.	1887.	1886.	1885.
Rhine district and Belgium:	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Vieille Montagne	52,865	52,016	51,670	51,517	50,790	50,687
Stolberg Co	14,855	14,634	14,036	14,070	14,065	14,452
Anstro-Belge	9,250	9,245	9,140	9,280	9,130	9,610
G. Dumont & Frères	8,350	8,863	8,759	8,368	8,000	7,072
Rhein-Nassau Co	7,960	7,470	7,586	7,588	7,730	7,676
L. de Laminne	6,760	6,693	6,597	6,745	6,550	7,039
Escombrera Bleyberg	5,630	5,560	4,930	4,925	5,315	5,835
Grillo	5,490	5,353	5,299	5,100	5,075	5,158
Märk. Westf., Bergw., Ver	5,485	5,805	5,537	5,553	4,950	4,429
Nonvelle Montagne	5,350	5,090	5,032	4,975	4,995	5,079
Berzelius	5,175	4,910	4,818	4,890	4,985	5,046
Eschger Ghesquière & Co	4,065	4,303	4,137	4,079	3,710	3,792
Société Prayon	4,100	3,956	3,906	3,905	3,725	3,879
Société de Boom	2,295	a750	1,798
	137,630	134,648	133,245	130,995	129,020	129,754
Silesia:						
Schlesische Actien-Gesellschaft	24,840	23,675	22,917	22,680	22,730	21,750
G. von Glesche's Erben	18,550	18,206	17,594	17,600	17,505	16,782
Herzog von Ujest	16,355	16,202	15,456	15,835	15,610	15,595
Graf H. Henckel von Donnersmarck	11,670	11,392	11,193	11,565	9,355	9,680
Graefin Schaffgotsch	6,265	6,405	6,402	6,430	6,505	6,091
Graf G. Henckel von Donnersmarck	4,090	3,943	4,114	1,565	1,670	1,682
Graf Lazy Henckel von Donnersmarck (included in Graf H. Henckel v. D.)	2,450	2,165
H. Roth	1,750	1,660	1,555	1,670	1,675	1,733
Wünsch	1,880	1,907	1,906	1,885	1,860	1,858
Vereinigte Königs & Laurahütte	1,020	1,130	1,166	1,065	1,185	1,305
Baron v. Horschitz'sche Erben	830	963	935	910	915	876
Fiscus	225	170	137	170	170	106
	87,475	85,653	83,375	81,375	81,630	79,623
Great Britain:						
Vivian & Sons	6,605	6,842	6,510	4,840	7,389	8,048
English Crown Spelter Co. (Limited)	4,945	4,981	4,980	4,007	3,248	3,500
Dillwyn & Co.	3,930	4,540	3,904	2,843	3,015	2,967
Swansea Vale Spelter Co	1,615	2,161	2,150	1,798	2,060	2,185
Villiers Spelter Co	1,890	2,180	1,993	1,810	1,880	1,985
Pascoe, Grentell & Sons	1,160	1,272	1,330	1,124	727	1,082
Neuthead & Tynedale Co	1,530	1,507	1,516	1,317	1,193	1,380
John Lysaght (Limited)	4,450	5,113	3,750	1,600	1,218	1,952
Staffordshire Knot	350	1,100	150	700
Minera Mines	2,170	610
H. Kenyon & Co.	500	500	500	500	500	500
	29,145	30,806	26,783	19,839	21,230	24,299
France and Spain:						
Asturienne	18,240	16,785	16,140	16,028	15,305	14,847
Austria:						
Sagor	1,430	1,210	1,087	866	1,000	970
Cilli	1,880	1,679	1,240	1,272	1,360	1,440
Siersza-Niedzieliska	3,825	3,450	2,650	3,200	2,640	3,200
	7,135	6,330	4,977	5,338	5,000	5,610
Poland	3,620	3,026	a3,785	3,580	4,145	5,019


a Estimated.

QUICKSILVER.

The quicksilver mines in California are becoming exhausted. The decline in production noted in 1888 continued in 1889 and 1890. The total product in 1888 was 33,250 flasks, in 1889, 26,484 flasks, including 20 flasks from Oregon, and in 1890, 22,926 flasks. The price per flask in 1888 ranged from \$36 to \$47; in 1889 the range was from \$40 to \$50, and in 1890 it increased to from \$47 to \$58 per flask. Using the averages of these figures the total value for 1890, \$1,203,615, is slightly greater than in 1889, and for a smaller amount of mining and smelting. The percentage yield of the ores decreased slightly, but not in proportion to the increased price. The above information, together with the table of production by mines, has been obtained from Mr. James B. Randol, of San Francisco. The information for 1889 was collected by him and published by the Census Office.

The product for 1889 includes 20 flasks from Oregon, but no product is reported from any State except California in 1890.

No new deposits have been found in the United States, although active search has been made, and many finds reported to be valuable have been carefully investigated in vain. Usually these finds have been clays stained with oxides of iron and bearing no resemblance to cinnabar, while in Arizona genuine ore was found, but of too poor quality to work even at high prices.

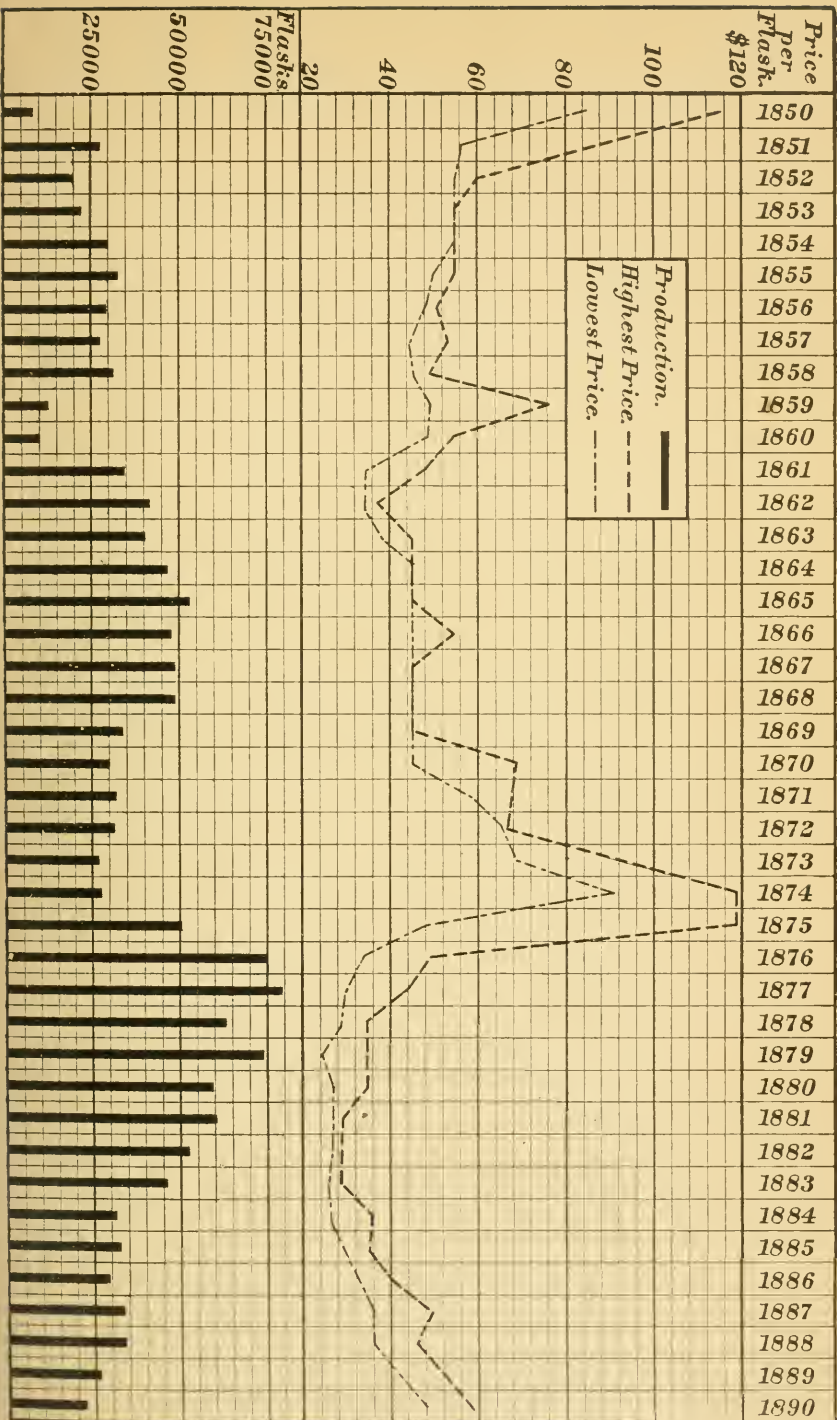

Production of quicksilver in the United States to the close of 1890. (Flasks of 7½ pounds.)

Years.	New Alma-den.	New Idria.	Red-ning-ton.	Sul-phur-Bank.	Gnada-lupe.	Great-West-ern.	Pope-Valley.	Napa-Consol-idated.	St. John.	Altoona.	Oce-anic-land.	Oak-land.	Calif.-orn.	Great-East-ern.	Sun-der-land.	Clo-ver-dale.	Ab-bot.	Brad-ford.	Vari-ous-mines.	Total yearly production of California mines.
1850.	7,723																			7,723
1851.	27,779																			27,779
1852.	15,901																			20,000
1853.	22,284																			22,284
1854.	30,004																			30,004
1855.	29,142																			33,000
1856.	27,133																			30,000
1857.	28,204																			28,204
1858.	25,761																			31,000
1859.	1,294																			13,000
1860.	7,061																			2,939
1861.	34,439																			11,706
1862.	33,671		444																	13,000
1863.	32,803		852																	10,000
1864.	42,489		1,914				800													35,000
1865.	47,194		3,545																	42,000
1866.	35,150		6,525																	1,885
1867.	24,461		11,493																	6,870
1868.	25,028		12,130																	2,286
1869.	16,898		10,686																	47,489
1870.	14,423		9,888																	2,261
1871.	18,568		8,180																	2,621
1872.	18,374		3,046																	46,550
1873.	11,042		7,735																	3,184
1874.	9,084		6,911																	112
1875.	13,643		8,432																	47,728
1876.	20,549		7,272																	33,811
1877.	23,996		9,316																	30,077
1878.	15,852		6,686																	81,686
1879.	20,514		4,425																	31,621
1880.	23,465		3,209																	27,642
1881.	26,080		2,775																	3,276
1882.	28,070		1,853																	27,756
1883.	29,000		1,600																	3,747
1884.	20,000		1,025																	50,250
1885.	21,400		1,144																	2,595
1886.	18,000		1,406																	75,074
1887.	20,800		1,890																	735
1888.	18,000		1,320																	2,911
1889.	13,100		980																	1,234
1890.	12,000		977																	1,151
Total.	916,359	131,296	99,753	84,683	55,910	60,722	18,097	63,833	3,598	7,527	7,391	6,831	5,653	16,000	2,777	2,061	2,272	8,555	68,961	1,567,855

^a Includes Etina.

^b Includes 65 flasks from Oregon.

^c Includes 20 flasks from Oregon.

Some was produced prior to 1875, but no record kept (estimated production previous to 1875, 1,000 flasks), included in production of various mines.

Yearly production previous to 1875 not obtainable (estimated at 20,000 flasks), included in production of various mines.

Production from 1858 to 1866, 17,453 flasks—no yearly details obtainable—included in production of various mines.

Production of quicksilver, in flasks, in California, from 1880 to 1890, by months.

Months.	New Almaden.	New Idria.	Redington.	Sulphur Bank.	Guatalupe.	Great Western.	Ætna. (a)	Napa. (a)	Great Eastern.	Bradford. (b)	Various mines.	Total.
1880.												
January	1,539	203	142	760	1,000	550	205	39	232	4,670
February	1,809	96	310	965	535	565	375	110	130	4,895
March	2,155	443	239	1,286	730	565	251	210	98	5,977
April	1,667	165	103	611	645	574	161	96	239	4,261
May	1,938	226	356	1,130	560	572	315	161	90	5,351
June	1,985	269	127	819	550	585	420	142	386	5,283
July	1,688	250	175	933	540	455	118	70	4,189
August	2,360	312	189	878	340	525	455	133	68	5,200
September	2,166	245	175	687	300	452	480	122	81	4,708
October	1,858	216	166	865	1,100	557	358	57	98	5,275
November	2,238	539	96	1,209	500	467	591	42	66	5,748
December	2,062	245	101	563	410	490	350	46	42	4,309
Total	23,465	3,209	2,139	10,706	6,670	6,442	4,416	1,279	1,600	59,926
1881.												
January	2,252	330	140	895	1,300	451	430	13	43	5,861
February	2,187	171	32	635	600	399	233	4	4,261
March	2,466	206	354	1,100	350	400	505	179	5,160
April	2,507	158	284	706	357	447	466	123	23	5,071
May	1,346	200	218	1,163	500	681	659	97	25	4,889
June	1,780	201	196	1,463	340	801	621	94	68	5,564
July	2,208	110	160	1,057	255	714	481	47	156	5,188
August	2,260	209	190	1,139	300	585	490	57	120	5,350
September	2,090	212	187	1,076	201	457	592	113	37	4,965
October	2,223	140	105	969	400	414	485	106	63	4,965
November	2,572	577	180	588	375	434	310	166	30	5,232
December	2,162	261	88	361	250	458	280	70	15	3,945
Total	26,060	2,775	2,194	11,152	5,228	6,241	5,552	1,065	584	60,851
1882.												
January	1,632	179	178	623	50	395	430	144	33	3,664
February	1,924	121	145	460	210	348	440	98	21	3,767
March	2,078	160	70	359	200	505	459	91	24	3,946
April	2,110	127	174	319	229	486	525	57	4,027
May	2,446	269	211	354	13	521	77	55	5	4,611
June	2,318	121	131	522	30	456	185	76	28	4,167
July	2,522	169	195	579	410	389	111	15	4,381
August	2,432	130	184	418	50	490	582	388	11	4,685
September	2,766	129	225	430	140	513	641	348	17	5,209
October	2,844	266	251	370	60	516	580	229	13	5,129
November	2,619	156	96	280	81	200	718	306	55	4,511
December	2,379	126	311	300	75	339	865	221	19	4,635
Total	28,070	1,953	2,171	5,014	1,138	5,179	6,812	2,124	241	52,732
1883.												
January	2,497	112	367	280	77	390	590	262	7	4,582
February	2,150	133	181	310	7	364	295	156	4	3,600
March	2,230	142	202	335	305	485	162	14	3,875
April	1,756	76	243	310	294	530	142	3	3,354
May	2,344	144	135	350	293	325	164	13	3,768
June	2,214	137	165	91	400	360	181	10	3,561
July	2,618	85	141	130	446	452	150	2	4,024
August	3,000	139	91	112	315	695	76	4	4,431
September	3,010	161	45	265	297	750	81	30	4,642
October	2,672	272	109	206	215	521	134	4,129
November	2,212	115	78	160	208	613	102	3,488
December	2,297	87	134	63	342	274	56	18	3,271
Total	29,000	1,666	1,894	2,612	84	3,869	5,890	1,669	101	46,725
1884.												
January	1,440	103	127	263	373	329	135	28	7	2,805
February	1,458	59	104	241	276	171	9	2,321
March	1,606	36	123	68	223	249	152	2	2,459
April	1,785	75	50	76	232	422	69	2,709
May	1,672	125	53	200	169	245	6	2,470
June	1,859	44	118	200	258	215	2,694

a Production of Ætna and Napa mines from 1880 to 1883 under heading of Napa mine.

b New mine.

Production of quicksilver, in flasks, in California, etc.—Continued.

Months.	New Almaden.	New Idria.	Redington.	Sulphur Bank.	Guadalupe.	Great Western.	Ætna. (a)	Napa. (a)	Great Eastern.	Bradford. (b)	Various mines.	Total.
1884.												
July	1,543	29	71	52	200	258	374	101				2,628
August	1,804	63	47	20	306	334	238	110				2,912
September	1,448	67	52	35	58	354	136	169	58			2,377
October	1,625	115	68	25	160	328	153	90	104			2,668
November	1,900	157	32	53	150	230	132	240	91			2,985
December	1,860	152	36	98	105	292	172	130	40			2,845
Total	20,000	1,025	881	890	1,179	3,292	2,981	1,376	332		7	31,913
1885.												
January	1,700	190	40	24		172	189	131	37			2,483
February	1,506	70	24	85	35	245	96	180	75			2,316
March	1,500	80		83		314	88	145	33		19	2,262
April	2,003	80		69		340	142	145	37			2,816
May	2,000	75		194		269	62	190			3	2,793
June	1,750	62	50	91		330	112	250	63		5	2,713
July	1,750	75	43	209		321	45	191	50		10	2,694
August	2,104	80	49	150		324	118	175			47	3,047
September	1,936	95	57	85		347	201	180			77	2,978
October	1,598	85	42	123		236	52	185	65		82	2,468
November	1,576	122	43	61		292	54	190	43		87	2,468
December	1,977	130	37	122		279	150	235	43		62	3,035
Total	21,400	1,144	385	1,296	35	3,469	1,309	2,197	446		392	32,073
1886.												
January	1,431	70	42	100		339	162	147	73		34	2,398
February	1,100	175	24	108		274	132	192	53		45	2,103
March	1,522	20	21	91		226	209	218	43		75	2,425
April	1,256	90	36	172		115	328	172	62		62	2,293
May	1,600	101	18	36		99	228	128	76		95	2,341
June	1,806	110	19	113		126	276	123	71		78	2,722
July	1,572	95	24	98		138	345	138	64		127	2,601
August	1,240	105	35	119		156	313	74	76		84	2,202
September	1,210	179	30	100		107	303	82	64		33	2,108
October	1,280	106	50	150		171	392	124	65		52	2,390
November	1,900	180	76	191		109	477	209	55		35	3,232
December	2,083	175	34	171		89	313	162	33		66	3,126
Total	18,000	1,406	409	1,449		1,949	3,478	1,769	735		786	29,981
1887.												
January	1,904	162	76	185		56	450	181	51		12	3,077
February	1,700	149	43	40		86	240	150				2,408
March	1,584	110	48	95		105	125	275	74		140	2,456
April	1,671	157	29	105		90	200	212	91		31	2,586
May	2,040	126	27	50		152	100	215	80		40	2,830
June	1,700	127	93	170		126	200	220	82		104	2,822
July	1,567	175	57	125		194	200	205	56	201	40	2,820
August	1,517	160	61	90		108	200	275	72	220	78	2,881
September	1,535	297	42	120		123	400	160	26	195	25	2,923
October	1,405	171	64	140		132	300	304	66	228	49	2,859
November	1,225	113	71	214		127	165	247	82	295	74	2,613
December	2,152	143	62	156		147	300	250	9	232	34	3,485
Total	20,000	1,890	673	1,490		1,446	2,880	2,694	689	1,371	627	33,760
1888.												
January	2,650	118		292		61	246	235	84	179	84	3,049
February	1,730	82		156		64	105	223	79	243	51	2,733
March	1,400	90		150		43	95	288	108	270	37	2,481
April	1,579	110		138		95	143	324	153	292	28	2,862
May	1,610	125		155		69	226	320	80	357	95	3,037
June	1,500	120		189		26	94	345	110	454	118	2,956
July	1,100	120		167		34	50	248	94	463	83	2,359
August	1,109	110		215		29		347	93	527	117	2,547
September	1,178	60		195		42		370	58	357	88	2,348
October	1,269	185	36	180		47		440	88	294	96	2,635
November	1,400	90	30	176		28		475	82	220	103	2,604
December	1,475	110	60	151		87		450	122	192	92	2,739
Total	18,000	1,320	126	2,164		625	959	4,065	1,151	3,848	992	33,250

^a Production of Ætna and Napa mines from 1880 to 1883 under heading of Napa mine. ^b Now mine.

Production of quicksilver, in flasks, in California, etc.—Continued.

Months.	New Almaden.	New Idria.	Redington.	Sulphur Bank.	Guadalupe.	Great Western.	Ætna. ^(a)	Napa. ^(a)	Great Eastern.	Bradford. ^(b)	Various mines.	Total.
1889.												
January	1,200	65	173	81	385	94	230	109	2,337
February	820	65	173	45	400	76	182	52	1,813
March	1,290	70	175	34	380	89	116	63	2,217
April	1,249	70	215	30	320	92	119	108	2,303
May	870	70	206	192	445	97	132	73	2,085
June	950	75	117	235	415	211	152	63	2,218
July	966	70	124	211	41	340	135	110	69	2,066
August	1,000	70	64	216	17	450	168	170	68	2,223
September	970	75	73	224	97	360	77	136	61	2,073
October	1,300	80	89	164	70	385	87	214	64	2,453
November	1,300	130	139	150	80	380	107	134	72	2,492
December	1,185	140	155	61	330	112	179	122	2,284
Total	13,100	980	812	2,283	556	4,590	1,345	1,874	924	26,464
1890.												
January	952	100	60	109	55	270	46	75	41	1,708
February	728	60	186	11	245	126	46	60	1,462
March	1,000	57	11	80	110	265	77	121	111	1,832
April	779	70	1	89	48	210	109	82	1,388
May	1,100	60	82	70	175	84	93	5	1,669
June	1,066	65	178	111	155	74	85	68	1,802
July	1,100	70	131	106	210	70	127	95	1,909
August	1,000	100	80	147	129	190	153	119	69	1,987
September	1,000	55	120	174	202	69	195	66	136	38	2,055
October	1,064	95	111	127	203	303	135	58	173	42	2,311
November	1,084	165	97	143	115	326	238	78	125	63	2,439
December	1,127	80	25	162	174	233	210	105	108	140	2,364
Total	12,000	977	505	1,608	1,334	931	2,493	1,046	1,290	737	22,926

^a Production of Ætna and Napa mines from 1880 to 1883 under heading of Napa mine. ^b New mine.

Prices.—The world's product of quicksilver was smaller than usual in 1889, and this, more than the local conditions in this country, made the price high in 1889 and higher in 1890 in London, where the rates are made practically for all markets. The product from Spain and Europe generally finds a market in London, and the first shipments from the mines all go there, except where orders from London specify the filling of contracts direct from the mines. The producers' stock accumulates in London. At the prices mentioned, this stock decreased from 47,000 flasks at the close of 1888 to 45,100 at the end of 1889, and this was further decreased in 1890. The following table continues the range in price for the period since quicksilver mining began in the United States:

Highest and lowest prices of quicksilver during the past forty-one years.

Years.	Price in San Francisco, per flask.		Price in London, per flask.	
	Highest.	Lowest.	Highest.	Lowest.
1850.....	\$114.75	\$84.15	£ 5 0 0	£ 13 2 6
1851.....	76.50	57.35	13 15 0	12 5 0
1852.....	61.20	55.45	11 10 0	9 7 6
1853.....	55.45	55.45	8 15 0	8 2 6
1854.....	55.45	55.45	7 15 0	7 5 0
1855.....	55.45	51.65	6 17 6	6 10 0
1856.....	51.65	51.65	6 10 0	6 10 0
1857.....	53.55	45.90	6 10 0	6 10 0
1858.....	49.75	45.90	7 10 0	7 5 0
1859.....	76.50	49.75	7 5 0	7 0 0
1860.....	57.35	49.75	7 0 0	7 0 0
1861.....	49.72	34.45	7 0 0	7 0 0
1862.....	38.25	34.45	7 0 0	7 0 0
1863.....	45.90	38.25	7 0 0	7 0 0
1864.....	45.90	45.90	9 0 0	7 10 0
1865.....	45.90	45.90	8 0 0	7 17 6
1866.....	57.35	45.90	8 0 0	6 17 0
1867.....	45.90	45.90	7 0 0	6 16 0
1868.....	45.90	45.90	6 17 0	6 16 0
1869.....	45.90	45.90	6 17 0	6 16 0
1870.....	68.85	45.90	10 0 0	6 16 0
1871.....	68.85	57.35	12 0 0	9 0 0
1872.....	66.95	65.00	13 0 0	10 0 0
1873.....	91.80	68.85	20 0 0	12 10 0
1874.....	118.55	91.80	26 0 0	19 0 0
1875.....	118.55	49.75	24 0 0	9 17 6
1876.....	53.55	34.45	12 0 0	7 17 6
1877.....	44.00	30.60	9 10 0	7 2 6
1878.....	35.95	29.85	7 5 0	6 7 6
1879.....	34.45	25.25	8 15 0	5 17 6
1880.....	34.45	27.55	7 15 0	6 7 6
1881.....	31.75	27.90	7 0 0	6 2 6
1882.....	29.10	27.35	6 5 0	5 15 0
1883.....	28.50	26.00	5 17 6	5 5 0
1884.....	35.00	26.00	6 15 0	5 2 6
1885.....	33.00	28.50	6 15 0	5 10 0
1886.....	39.00	32.00	7 10 0	5 16 3
1887.....	50.00	36.50	11 5 0	6 7 6
1888.....	47.00	36.00	10 0 0	6 12 6
1889.....	50.00	40.00	9 15 0	7 10 0
1890.....	58.00	47.00	10 10 0	9 1 0
Extreme range in forty-one years.	118.55	25.25	26 0 0	5 2 6

The detailed prices for the year 1889 were as follows:

Prices per flask obtained in New York for California quicksilver in 1889.

	Prices obtained in New York.		Netting in San Francisco freight and drayage \$1.30.		Rothschild's quotation and equivalent for quicksilver laid down in New York, duty added.				Laid down in New York, duty added.		Outsiders' price.	
	High-est.	Low-est.	High-est.	Low-est.	English money.		U. S. Money.		High-est.	Low-est.	High-est.	Low-est.
					High-est.	Low-est.	High-est.	Low-est.				
Jan....	\$44.00	\$43.00	\$42.70	\$41.70	9 10 0	9 10 0	\$50.50	\$50.50	\$46.60	\$43.55	8 15 0	8 3 6
Feb....	43.25	40.00	41.95	38.70	8 10 0	7 10 0	45.25	40.00	43.40	39.30	8 3 0	7 7 6
Mar....	40.50	39.00	39.20	37.70	7 15 0	7 10 0	41.25	40.00	41.40	39.30	7 15 6	7 7 6
April..	42.00	40.00	40.70	38.70	8 0 0	7 12 6	42.60	40.60	42.60	40.60	8 0 0	7 12 6
May....	45.25	42.75	43.95	41.45	8 10 0	8 5 0	45.25	44.00	44.35	41.85	8 6 6	7 17 0
June..	48.00	48.00	46.70	46.70	9 10 0	8 15 0	50.50	46.60	47.70	43.55	8 19 0	8 3 6
July...	49.00	46.00	47.70	44.70	9 15 0	9 10 0	51.75	50.50	50.20	46.60	9 8 6	8 15 0
Aug...	49.00	48.00	47.70	46.70	9 15 0	9 15 0	51.75	51.75	49.95	48.90	9 7 6	9 3 6
Sept...	49.50	48.50	48.20	47.20	9 15 0	9 15 0	51.75	51.75	49.15	48.75	9 4 6	9 3 0
Oct....	49.00	48.50	47.70	47.20	9 5 0	9 5 0	49.30	49.30	49.30	47.30	9 5 0	8 17 6
Nov....	50.00	49.00	48.70	47.70	9 15 0	9 10 0	51.75	50.50	50.90	49.95	9 11 0	9 7 6
Dec....	50.00	48.50	48.70	47.20	9 15 0	9 15 0	51.75	51.75	50.35	49.30	9 9 0	9 5 0

Movement of quicksilver from San Francisco in detail, from 1883 to 1888.

To—	1883.	1884.	1885.	1886.	1887.	1888.
By sea:	<i>Flasks.</i>	<i>Flasks.</i>	<i>Flasks.</i>	<i>Flasks.</i>	<i>Flasks.</i>	<i>Flasks.</i>
China.....	16,330	300	233	3,105	3,761
Japan.....	1,253	588	302	3
Mexico.....	10,764	5,404	5,884	5,530	6,397	4,766
South America.....	970	155	100
Australia.....	600	110
New Zealand.....	160	20	100	91	100	286
Central America.....	59	52	9	23	119	712
New York.....	3,100	8,350	9,055	600	8,370	2,320
Various.....	11	22	47	54	28	72
Total by sea.....	33,247	14,901	15,730	6,301	18,119	11,917
By rail:						
Central Pacific, Southern Pacific and Northern Pacific Railroads.....	4,620	(a) 7,000	(a) 10,000	10,000	4,000	7,833
Grand total.....	37,867	21,901	25,730	16,301	22,119	19,750

a Including about 3,500 flasks to Mexico by Southern Pacific Railroad.

Total exports and shipments of quicksilver in 1889 and 1890.

	1889.	1890.
BY SEA.		
Mexico.....	<i>Flasks.</i> 4,593	<i>Flasks.</i> 2,795
Central America.....	47	102
Chile and South America.....	10
New Zealand.....	112
Australia.....	10	127
British Columbia.....	11
China.....	300
Shipments to New York.....	4,783	3,324
Various.....	430	320
Various.....	6
Total by sea.....	5,213	3,650
BY RAILROAD.		
From San José:		
New York.....	5,100	1,800
Philadelphia.....	300
Texas.....	200
Montana.....	1,995	2,115
Nevada.....	4,520
Utah.....	118
Colorado.....	30
Idaho.....	100	130
Arizona.....	90	10
Mexico.....	95
	7,603	9,000
From San Francisco:		
New York.....	1,500
Mexico.....	819
Montana, Idaho, and Utah.....	2,311
Arizona.....	110
Colorado.....	61
Various points.....	2,548
	4,801	2,548
From San Francisco, via Portland and Northern Pacific Railroad:		
Montana.....	350
Add for shipments to Montana, Idaho, and Arizona, not included in above.....	533
Total by rail.....	13,287	11,548
Total shipments.....	18,500	15,198

Quicksilver imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Years ending—	Quantity.	Value.	Years ending—	Quantity.	Value.
June 30—	<i>Pounds.</i>		June 30—	<i>Pounds.</i>	
1867.....		\$15,248	1880.....	116,700	\$48,463
1868.....	152	68	1881.....	138,517	57,733
1869.....		11	1882.....	597,898	233,057
1870.....	239,223	107,646	1883.....	1,552,738	593,367
1871.....	304,965	137,332	1884.....	136,615	44,035
1872.....	370,353	189,943	1885.....	257,659	90,416
1873.....	99,898	74,146	December 31—		
1874.....	51,202	52,093	1886.....	629,888	249,411
1875.....	6,870	20,937	1887.....	419,934	171,431
1876.....	78,902	50,164	1888.....	132,850	56,997
1877.....	38,250	19,558	1889.....	341,514	162,064
1878.....	294,207	135,178	1890.....	802,871	445,807
1879.....	519,125	217,770			

Imports of quicksilver vermilion from 1867 to 1890.

Years ending—	Quantity.	Value.	Years ending—	Quantity.	Value.
June 30—	<i>Pounds.</i>		June 30—	<i>Pounds.</i>	
1867.....		\$123,506	1880.....	11,952	\$5,997
1868.....		90,648	1881.....	14,243	7,391
1869.....	247,382	145,665	1882.....	12,496	6,214
1870.....	104,523	57,262	1883.....	19,549	8,795
1871.....	79,195	43,935	1884.....		10,472
1872.....	120,067	49,237	1885.....		8,244
1873.....	87,008	65,796	December 31—		
1874.....	42,324	39,443	1886.....		11,016
1875.....	9,460	10,831	1887.....		16,542
1876.....	18,981	17,679	1888.....		9,342
1877.....	23,315	14,660	1889.....		3,263
1878.....	9,843	5,772	1890.....		6,916
1879.....	11,382	6,105			

Mercurial preparations imported and entered for consumption in the United States, 1867 to 1883, inclusive. (a)

Fiscal years ending June 30—	Blue-mass.		Calomel.		Mercurial preparations not otherwise specified.	Total value.
	Quantity.	Value.	Quantity.	Value.		
	<i>Pounds.</i>		<i>Pounds.</i>			
1867.....				\$4,242		\$4,242
1868.....				4,440		4,440
1869.....				4,516		4,516
1870.....				6,306		6,306
1871.....				3,147		3,147
1872.....	1,009	\$667	8,241	6,590	\$629	7,886
1873.....	919	660	5,520	5,240	699	6,599
1874.....	259	192	6,138	6,676	4,334	11,202
1875.....	125	109	2,424	2,817	52	2,978
1876.....	489	365	5,433	5,820	92	6,277
1877.....	455	327	4,649	4,305	90	4,722
1878.....	397	252	4,133	3,576	363	4,191
1879.....	485	266	5,875	4,335	6,453	11,354
1880.....	533	262	4,780	3,230	30	3,622
1881.....	395	236	8,177	5,640	116	5,992
1882.....	207	124	5,215	3,411	58	3,593
1883.....	188	79	8,732	5,503	190	5,772

a Not specified since 1883.

World's annual production.—The following table, by Mr. Randol, shows the product in various countries for the past ten years, and its relation to the consumption and the stock :

The world's production of quicksilver for ten years.

[Flasks of 34.5 kilograms, or 76.5 pounds avoirdupois.]

Years.	California.	Spain.		Austria-Hungary.		Italy. (c)	Russia.	Estimated consumption.	Estimated stock in London, England.	Total supply.
		Almaden.	Various. (a)	Idria.	Various. (b)					
1880.....	59,926	45,322	(d)	12,356	712	4,220	-----	95,600	68,500	122,536
1881.....	60,851	44,989	(d)	11,333	720	4,785	-----	106,300	84,899	122,678
1882.....	52,732	46,716	2,795	11,663	588	4,900	-----	116,200	88,000	119,394
1883.....	46,725	49,177	2,165	13,152	709	6,930	-----	124,800	82,014	118,858
1884.....	31,913	48,098	2,219	13,967	733	8,500	-----	111,300	76,105	105,430
1885.....	32,073	45,813	2,046	13,503	773	7,540	-----	108,300	69,467	101,748
1886.....	29,981	51,199	2,277	14,496	1,400	8,235	-----	123,050	54,000	107,588
1887.....	33,760	53,276	2,894	14,676	1,030	9,220	1,855	131,700	39,000	116,711
1888.....	33,250	51,872	1,877	14,962	1,018	10,200	4,777	109,900	47,000	117,956
1889.....	26,464	49,477	(d)	15,295	(e) 1,125	11,174	10,307	115,740	45,100	113,842
Total.	407,675	485,939	16,273	135,403	8,808	(c)75,704	16,939	1,142,890	-----	1,146,741

a Comprises mines in the provinces of Oviedo, Granada, and Ciudad Real.

b Comprises mines in Carniola and in Hungary.

c Figures taken from monograph on the quicksilver mines of Monte Amiata, by P. De Ferrari, M. E., 1889.

d Quantities unknown.

e Comprises mines in Carniola only, the production of Hungary not being known.

CENSUS STATISTICS.

The following data have been condensed from the very careful results of the census as taken by the expert special agent, Mr. Randol, in charge of that branch:

Location and number of all the quicksilver establishments—by States and counties.

States.	Counties.	Productive.		Nonproductive.	
		Mines.	Furnaces.	Mines.	Furnaces.
California.....	Lake.....	3	12	-----	-----
	Merced.....	1	(a)	-----	-----
	Napa.....	4	12	-----	-----
	San Benito.....	1	3	-----	-----
	Santa Clara.....	1	7	1	4
	Sonoma.....	1	2	-----	-----
	Siskiyou.....	-----	-----	1	(a)
Oregon.....	Trinity.....	-----	-----	1	-----
	Douglas.....	-----	-----	3	3
	Total.....	11	36	6	7

a One retort.

The productive mines and active furnaces employed 937 operatives, of whom 416 were engaged on surface work and 521 were employed underground. The other mines and furnaces employed 24 men, making a total of 961 employes, as shown in the following table:

Number of employes.

Employés.	Productive mines and furnaces.	Nonproductive mines and furnaces.	Total.
Men.....	932	24	956
Women.....	1		1
Boys.....	4		4
Total.....	937	24	961
Total on surface.....	416	18	434
Total underground.....	521	6	527
Total.....	937	24	961

Production statistics.—Of 95,714 tons (2,000 pounds each) of cinnabar ore mined, 92,964 tons were roasted, producing 26,484 flasks of quicksilver, each containing a standard quantity of $76\frac{1}{2}$ pounds advoirdupois. Of the eleven establishments working ore, one reported only 200 tons produced and worked in retorts, with an average yield of 2.295 per cent, the highest percentage returned. The lowest average yield was 0.286 per cent, and the average percentage yield in quicksilver for all the ore roasted was 1.088. The largest quantities of ore produced and roasted were respectively 28,007 and 28,887 tons, and the quantity of quicksilver produced at the several works ranged from 120 up to 13,100 flasks. The following table exhibits the quantity of ore produced and roasted in California in 1889, the number of flasks of quicksilver produced, and the percentage of yield:

Yield of quicksilver from California ores roasted in 1889.

Number of establishments.	Ore produced.	Ore roasted.	Quicksilver produced.	Yield.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Flasks.</i>	<i>Per cent.</i>
1	7,168	7,168	1,874	1.000
1	9,880	9,880	2,283	0.884
1	7,440	7,440	556	0.286
1	200	200	120	2.295
1	4,742	3,992	812	0.778
1	23,500	23,500	4,590	0.746
1	3,400	3,400	804	0.905
1	3,377	3,377	980	1.110
1	28,007	28,887	13,100	1.734
1	7,000	5,120	1,345	1.000
1	1,000			
11	95,714	92,964	(a) 26,464	1.088

a One mine in Oregon produced 20 flasks, the total product in that State. They are not included, being less than \$1,000 in value.

Expenditures.—The following table shows the value of supplies of all kinds consumed during the year 1889; “the aggregate of all wages paid;” total of all other expenditures for mines and works, including

rent, taxes, etc.; number of flasks of quicksilver produced, and average cost per flask:

Expenditures in the production of quicksilver in California in 1889.

Number of establishments.	Value of all supplies.	Aggregate of all wages.	Total of all other expenditures.	Number of flasks quicksilver produced.	Average cost per flask.
1	\$53,567	\$104,608	\$760	4,590	\$34.63
1	5,975	8,060	-----	-----	(b)
1	(a) 4,000	20,936	750	804	31.95
1	4,000	12,591	1,000	812	21.66
1	9,564	43,241	1,042	1,874	28.73
1	21,973	47,208	2,507	2,283	31.40
1	9,034	25,352	2,167	556	65.74
1	1,500	2,250	-----	120	31.25
1	3,114	27,546	79	980	31.37
1	86,428	304,341	26,826	13,100	31.88
1	20,467	30,156	359	1,345	37.90
11	219,622	626,289	35,490	26,464	32.71

a Estimated; correct amount unobtainable.

b Ore mined, but not roasted, and therefore omitted in average cost per flask.

From the above table it will be seen that at eleven active establishments there were expended \$219,622 for supplies, \$626,289 for wages, and \$35,490 for other expenses, embracing taxes, rent, interest, etc., making a total of \$881,401, showing that 71 per cent was paid for wages, 25 per cent for supplies, and 4 per cent for all other expenses. Of the amount paid for wages the office force absorbed \$34,966, and there were paid to foremen, mechanics, miners, furnace hands, and laborers \$591,323.

Prices.—The cost per flask of quicksilver produced ranged from \$65.74 to \$21.66, the average cost for all being \$32.71.

For the year the highest price was \$50 and the lowest \$40, giving an average of \$45, which for the year's production, 26,484 flasks, would make a total valuation of \$1,191,780. The difference between the cost, \$881,401, and value, \$1,191,780, is \$310,379, which may be regarded as the profit on the year's work, based on the returns collected. The difference between average cost and average sale price was \$11.69 per flask. The one establishment producing quicksilver at a cost of \$65.74 per flask, of course, met with a serious loss on its output.

Wages.—The wages in the table appended show considerable variations, depending largely upon the locality of the work, its importance, and the degree of skill required for its performance. On work at surface, foremen were reported to earn daily wages ranging from \$10.33 to \$2.66; mechanics, \$3.60 to \$2.05; laborers, \$2 to \$1.18, the last-named rate being for Chinamen. Boys under 16 years of age, of whom only four were employed, none underground, earned \$1 and 75 cents.

The following table gives the number and classification of employes on surface (excepting the office force), daily wages, and number of days' work for the year:

Wages of employes above ground in quicksilver mining.

Number of establishments.	Foremen.			Mechanics.			Number of establishments.	Laborers.			Boys under 16.		
	Average number employed daily.	Average wages per day.	Average number of days' work for year.	Average number employed daily.	Average wages per day.	Average number of days' work for year.		Average number employed daily.	Average wages per day.	Average number of days' work for year.	Average number employed daily.	Average wages per day.	Average number of days' work for year.
1	1	\$2.90	365	(a) 5	\$2.80	301	1	(e) 11	\$1.38	300	
1	2	10.33	360	5	2.50	360	1	15	1.75	360	
1	1	2.81	157	2 $\frac{1}{2}$	3.20	90	1	6	2.00	300	
1	1	1	3.60	300	1	17	1.73	265	
1	4	2.86	349	(b) 42 $\frac{1}{2}$	2.38	306	1	(f) 87	1.18	284	
1	1	2.75	340	5	3.00	340	1	(g) 98	1.94	281	3	\$0.75 187	
1	1	2	2.05	320	1	38	2.00	340	1	1.00 310	
1	2	2.66	365	1	(h) 12	1.30	300	
1	1	1	(i) 2	1.37	308	
8	11	(c) 10.33 (d) 2.66	(c) 365 (d) 157	63	(c) 3.60 (d) 2.05	(c) 360 (d) 90	9	286	(c) 2.00 (d) 1.18	(c) 360 (d) 265	4	(c) 1.00 (d) 0.75	(c) 310 (d) 187

- a Mechanics comprises engineers, \$2.90; blacksmiths, \$2.90; and furnace men, \$2.65 per day.
- b Mechanics comprise carpenters, \$3; masons, \$5; blacksmiths, \$2.10; helpers, \$1.03; engine-drivers \$2.39; machinists and helpers, \$3.67, as their average earnings per day.
- c Highest wages.
- d Lowest wages.
- e Laborers embrace men sorting ore, \$1.25; teamsters, \$1.65 per day.
- f Chinese.
- g Laborers comprise furnace hands earning \$2 to \$2.25 per day; ordinary laborers, earning \$2 per day; and ore cleaners, earning \$1.75 per day.

One establishment reported 42 men employed on surface and under-ground work without classification or number of days employed, miners at \$2.10 and laborers at \$1.75 per day. Another establishment reported 11 white men on surface without classification, at \$2.80 per day for 352 days. These establishments were not included in the tables.

The following tables exhibit the number and classification of workers underground, their daily wages, and the number of days' work for the year. For foremen at underground work the average wages ranged from \$4.68 to \$2.75 daily. Miners earned an average of \$2.67 to \$1.22, the lowest rate being for Chinamen, of whom a few were employed at small establishments.

Wages of foremen and miners underground.

Number of establishments.	FOREMEN.			MINERS.			LABORERS.		
	Average number employed daily.	Average wages per day.	Average number of days' work for year.	Average number employed daily.	Average wages per day.	Average number of days' work for year.	Average number employed daily.	Average wages per day.	Average number of days' work for year.
1	1	\$2.90	340	(a)6	\$2.40	300	(f)24	\$1.90	290
1	1	4.00	360	20	2.67	360	5	2.17	360
1	1	3.75	110	23	2.45	263	1	2.00	300
1	1	4.68	306	65	1.22	40	19	2.09	267
1	3	3.06	340	(c)233	2.66	279	(f)25	1.50	340
1	1	4.50	316	(b)80	1.25	340	3	1.65	315
1	1			6	2.05	284	4	1.35	336
1	1			6	1.50	336			
8	9	(d)4.68 (e)2.75	(d)360 (e)110	378	(d)2.67 (e)1.22	(d)360 (e)40	81	(d)2.17 (e)1.35	(d)360 (e)267

a Miners embrace timbermen and machine drill men.

b Chinese.

c Miners comprise tributars, \$2.41; drillers per foot on contract, \$2.33; drifting on contract, \$2.80; timbermen, \$3; blasters, \$2.75 per day.

d Highest.

e Lowest.

f Laborers embrace helpers and hand drillers at \$1.90 per day.

The following table gives the number of office force, total pay of same, total wages of all other employes, and the aggregate wages paid to all employes:

Total wages.

Number of establishments.	Number employed.	Total pay.	All other wages.	Total wages.
1			\$25,352	\$25,352
1			2,250	2,250
1			20,936	20,936
1	1	\$800	29,356	30,156
1	3	2,520	(b)40,721	43,241
1	2	3,900	23,646	27,546
1	2	3,366	43,842	47,208
1	7	17,560	(c)286,781	304,341
1	(a)3	5,200	99,408	104,608
1	1	1,200	(d)11,391	12,591
1	1	420	7,640	8,060
11	20	34,966	591,323	626,289

a Only one woman employed in all the establishments.

b \$300 paid to contractors included.

c \$10,606 paid to contractors included.

d \$375 paid to contractors included.

During the census decade, 1880-1889, there were no strikes or labor troubles of any kind in any of the mines and works.

POWER.—The active establishments employed 62 steam motors, with a capacity of 2,190 horse power, 54 boilers of 2,438 horse power, one electric dynamo and motor of 4 horse-power, and one water wheel of 3

horse power—a total of 2,197 horse power in motors. Two hundred and forty-seven animals were also reported as employed, but it is probable a greater number were in use. The details for the respective establishments are shown in the following table:

Power used in quicksilver mining and reduction.

Number of establishments.	Steam motors.		Boilers.		Other motors.		Number of animals.
	Number.	Horse power.	Number.	Horse power.	Number.	Horse power.	
1	2	50	2	30	-----	-----	4
1	5	230	5	140	-----	-----	4
1	3	90	2	125	-----	-----	4
1	2	150	5	155	-----	-----	12
1	2	50	4	100	-----	-----	12
1	7	185	5	400	-----	-----	15
1	29	1,000	23	1,088	2	(a) 7	114
1	5	170	3	200	-----	-----	52
1	7	265	5	200	-----	-----	20
1	-----	-----	-----	-----	-----	-----	10
10	62	2,190	54	2,438	2	7	247

a One water wheel of 3 horse power, and one dynamo and motor of 4 horse power.

The following statement gives an estimated valuation of the active mines and works as nearly as the same could be ascertained:

Value of quicksilver establishments.

Number of establishments.	Mines and real estate.	Furnaces, houses, and other surface improvements.	Machinery, supplies, tools, and live stock.	Quicksilver unsold.	Bills and accounts receivable.	Other assets.	Estimated total capital.
1	\$276,530	\$50,000	\$58,850	\$96,660	-----	\$108,513	\$590,553
1	30,000	13,300	2,000	4,700	-----	-----	50,000
1	65,000	25,000	10,000	6,460	-----	2,000	108,460
1	6,940	14,000	3,300	95	-----	-----	24,535
1	20,000	5,000	5,000	2,500	-----	-----	32,500
1	100,000	25,000	30,000	-----	-----	-----	155,000
1	12,000	5,000	10,000	-----	-----	-----	27,000
1	20,000	10,000	5,000	859	\$9,664	4,943	50,466
1	50,000	25,000	10,000	2,900	25,000	10,000	122,900
1	25,000	15,000	10,000	9,900	-----	-----	59,900
(a) 6	75,000	35,000	2,000	-----	-----	-----	112,000
16	680,470	222,300	146,150	124,074	34,664	125,456	1,333,114

a Nonproductive.

Some mine owners placed a higher valuation on their mines and improvements than is given in the foregoing statement; but it is preferred to take what may be considered a conservative opinion of the values as of December 31, 1889. Undoubtedly the original investments in the properties were many times the amounts of present estimates, but it must be remembered that mines are generally decreased in value by the extraction of ore for a long period of continuous work, which has been the case with the quicksilver establishments of the United States.

Exports of domestic quicksilver from the United States for the ten years ended December 31, 1889.

[Compiled from the returns sent in by the various collectors of customs.]

Ports.	1880.		1881.		1882.		1883.	
	Flasks.	Dollars.	Flasks.	Dollars.	Flasks.	Dollars.	Flasks.	Dollars.
Ports from which exported:								
San Francisco	34,359	1,028,826	33,935	985,927	33,728	983,977	29,928	804,077
New York	2,221	76,244	1,166	39,161	143	4,344	197	4,037
Philadelphia	630	14,882						
Boston			6	211	4	133	7	239
New Orleans								
Total	37,210	1,119,952	35,107	1,025,299	33,875	988,454	30,072	808,353
Exported to—								
Hongkong	19,610	577,019	17,031	493,171	18,965	560,353	16,356	438,689
Central American States	41	1,095	38	1,086	75	2,151	150	4,263
Chile	754	24,842	123	3,700	1,400	42,000	1,150	31,250
China	50	1,475						
Germany								
England	1,753	59,882						
British Columbia	7	211	5	141	16	472	4	110
British possessions in Australasia	1,535	47,874	1,330	37,249	1,831	52,997	786	20,766
Japan	105	3,050	314	9,213	621	17,601	1,297	32,151
Mexico	12,413	376,007	15,256	450,448	10,128	288,441	10,157	276,332
Peru	440	13,540	700	20,161	665	19,285	100	2,695
Cuba	356	10,270			1	33		
United States of Colombia	115	3,673	208	6,487	45	1,280	11	326
Venezuela	13	497	90	3,225	98	2,941	36	1,028
Dutch Guiana	1	26	12	418	4	133	5	175
Nova Scotia, New Brunswick, and Prince Edward Island							2	64
West Indies					18	552	18	504
All other ports	17	491			8	215		
Total	37,210	1,119,952	35,107	1,025,299	33,875	988,454	30,072	808,353

Exports of domestic quicksilver from the United States, etc.—Continued.

Ports.	1884.		1885.		1886.		1887.	
	Flasks.	Dollars.	Flasks.	Dollars.	Flasks.	Dollars.	Flasks.	Dollars.
Ports from which exported:								
San Francisco	7,037	189,420	6,547	200,739	5,845	196,384	10,401	396,316
New York	322	10,233	242	8,578	240	8,340	984	44,448
Philadelphia								
Boston			8	291	6	232	9	348
New Orleans	1	32	5	150				
Total	7,370	199,685	6,802	209,758	6,091	204,956	11,394	441,112
Exported to—								
Hongkong	220	6,750	233	8,990			3,323	141,237
Central American States	285	8,390	238	8,341	164	5,805	177	6,466
Chile			104	3,042				
China								
Germany								
England							800	36,200
British Columbia	15	406	40	1,088	59	1,902	31	1,104
British possessions in								
Australasia	130	3,768	75	2,257	90	2,295	100	3,965
Japan	669	16,032	300	9,100	3	108		
Mexico	5,830	157,758	5,777	175,828	5,678	190,461	6,920	250,514
Peru	50	1,550						
Cuba	11	351			5	180		
United States of Colombia	80	2,376	14	498	22	873	32	1,196
Venezuela	36	1,057			60	1,946		
Dutch Guiana			5	176				
Nova Scotia, New Brunswick and Prince Edward Island					2	77		
West Indies			2	76	6	232	7	261
All other ports	18	529			1	44		
Total	26	718	14	362	1	33	1	40
Total	7,370	199,685	6,802	209,758	6,091	204,956	11,394	441,112

Ports.	1888.		1889.		Total.	
	Flasks.	Dollars.	Flasks.	Dollars.	Flasks.	Dollars.
Ports from which exported:						
San Francisco	10,145	381,707	5,049	210,745	176,974	5,378,118
New York	539	24,692	62	2,972	6,066	223,049
Philadelphia					630	14,882
Boston					40	1,454
New Orleans					6	182
Total	10,684	406,399	5,111	213,717	183,716	5,617,685
Exported to—						
Hongkong	3,713	144,899			79,451	2,371,108
Central American States	1,333	52,586	93	4,111	2,594	94,294
Chile			12	475	3,543	105,309
China	37	1,386			87	2,861
Germany						
England					2,553	96,082
British Columbia	16	548	12	424	205	6,406
British possessions in Aus-						
tralasia	322	12,979	133	5,483	6,332	190,638
Japan	35	1,450			3,344	88,705
Mexico	5,172	190,013	4,841	202,228	82,172	2,558,030
Peru					1,955	57,231
Cuba	2	127	2	132	377	11,083
United States of Colombia	48	2,096	6	313	581	19,118
Venezuela					333	10,694
Dutch Guiana	5	265			37	1,399
Nova Scotia, New Brunswick, and Prince Edward Island						
West Indies			6	272	23	905
All other ports	1	50	6	284	55	1,629
Total	10,684	406,899	5,111	213,717	183,716	5,617,685

The final census volume on mining contains also an exhaustive treatise of very great value on the mining plant, etc., of New Almaden, which should be read entire, and will not bear further condensation.

ALUMINUM.

BY R. L. PACKARD.

The production of aluminum still remains small when compared with that of other metals used in the arts. The newspaper prophecies of the advent of the "age of aluminum," which were frequent a few years ago, are still unfulfilled, and the tone of the technical and trade journals is changing from that of expectancy to one of criticism. Enough has now been published of the methods of production of the metal and of its availability for different purposes to afford a basis for an estimate of its value and to place it upon a different footing from that which it occupied when its properties were less well known. The newspapers proper still occasionally herald a new process for extracting aluminum which is to be cheaper than its predecessors, but that part of the public which is interested in such matters is no longer eager to listen to statements of this character. Nevertheless, there is a real and very considerable advance in the production of this metal, both in Europe and the United States, and from a technological point of view it is a thing of great interest to witness the development of a laboratory experiment into an established commercial process, by which a metal formerly practically unknown has been introduced into the markets of the world, and this development has taken place in the case of aluminum within the last thirty years. It has been estimated that the total amount of the metal produced during this period (up to the close of 1889) was only about 116 tons, but the indications in 1889 were that this quantity would soon be exceeded by the annual production.

It is very likely that such is already the case, although figures are not at hand to show whether the prediction is actually verified or not, but the aluminum industry has received a new impetus in Europe within a short time and the American production has also been very largely increased. The total output of metallic aluminum in the United States in 1890 was 47,881 pounds, against 19,200 pounds in 1889. If to this is added the aluminum contained in alloys produced here in 1890, which was in round numbers 13,400 pounds, the total is 61,281 pounds of aluminum extracted in this country during the year.

From its first appearance aluminum has been used principally for articles which it is desired should be light and strong, such as parts of mathematical, astronomical, optical, and surveying instruments, light weights, fittings of various kinds, dental plates, surgical apparatus, and the like. The limited production of the metal and its high cost up to a

very recent date precluded its use in any large way. Its cost is now (1890) reduced to below \$2 a pound. The scope of its employment for articles of manufacture is still limited, as above indicated, while its production for such employment is very largely increased, and although the field of its possible uses is as wide as the imagination of newspaper writers can make it, these uses are as yet only unrealized suggestions. Its use in metallurgy, which is extending, is another matter. Instrument-makers now use aluminum more than formerly, especially where great rigidity is not required.

An illustration of this statement is afforded by a note read by Prof. William P. Blake before the American Institute of Mining Engineers in 1890. He described a double reflecting and repeating circle invented by Capt. Charles H. Townshend, of New Haven, Connecticut, and exhibited one of the instruments made by Messrs. Stackpole & Brothers, of New York. The circle, which was 9 inches in diameter, was cast in one piece. The aluminum was furnished by the Pittsburg Reduction Company. The instrument is intended to be used in a boat and is to be held in one hand like a sextant. Lightness, therefore, is of great importance. The instrument, exclusive of the eyepieces and handle, weighed only 1 pound. An inspection showed that in this case the metal worked well under the file, in the lathe, and under the graduating tool. The castings were homogeneous, free from blowholes, and dressed up clean and sharp. Messrs. Keuffel & Esser, of New York, have made sextants of aluminum which have proved satisfactory as far as the limited experience in their use has gone. The same manufacturers are also making a mining transit of aluminum, although some portions of the instrument are made of a harder and heavier metal. The great advantage of lightness in such instruments will be appreciated by those who have had to carry instruments of the usual construction through the devious passages of mines and up the side of high mountains, where every ounce of weight is a grievous burden. Moreover, since aluminum resists corrosion to a remarkable degree, instruments made of it are not liable to tarnish and do not require lacquer as brass instruments do, and their unprotected surfaces keep clean and bright where brass and ordinary bronze will become green and dirty.

Some instrument-makers are yet cautious in the use of unalloyed aluminum, preferring to employ it only in those parts of apparatus where lightness is important while great rigidity and hardness are not required, and which have careful handling. To increase the rigidity and hardness of the metal without materially increasing its weight, it has been proposed to alloy it with small quantities of other metals. For this purpose an alloy of aluminum, and silver, suggested by Tissier, has been made by Mr. Hunt, having the composition of 95 per cent aluminum and 5 per cent silver. This alloy is much harder and more rigid than aluminum, and works quite as well or better under tools. Its specific gravity is 3.2, so that it is a little heavier than aluminum (2.6). It is whiter than the pure metal, withstands corrosion nearly

as well, takes a good polish, and is better for graduation. In France, aluminum has also been alloyed with tin (nearly 10 per cent) for the same purpose. The specific gravity of this alloy is said to be 2.85, it is not easily corroded, can be worked more satisfactorily than aluminum, and has the great advantage of being as easily soldered as bronze. Aluminum wire has been substituted for lead as calking for steam pipes, on account of its resistance to the action of steam. It is made into steamers for evaporating fruit juices, to avoid the action of the fruit acids on galvanized and tinned ware. Trolley wheels on electric cars have been advantageously made of it, and new uses of this general character are frequently mentioned. This confirms the statement made at the outset that the scope of the employment of aluminum for articles of manufacture is yet limited to such as must be light and resist corrosion well. It has not yet (1890) begun to displace other metals to any noticeable extent in a large way.

Aluminum is used metallurgically in the manufacture of iron and steel, to which it is added before pouring, sometimes in the form of the alloy ferro aluminum and sometimes as metallic aluminum. A recent discussion of this subject will be noticed farther on. It is also used in this country in making alloys, especially aluminum bronze. No data are at hand to indicate what proportion of the total production is used in the arts to be drawn, rolled, cast, etc., into articles of manufacture, and what is used metallurgically and in the manufacture of alloys.

The following table showing the comparative physical properties of aluminum, iron, and copper is inserted here for convenience of reference. It must, however, be remembered that figures representing the tensile strength of aluminum given by different authorities are apt to disagree because the specimens which afforded the figures in the different cases did not have the same composition. The table is taken from an address delivered before the London Society of Chemical Industry by J. H. J. Dagher, F. I. C., F. C. S.:

Comparison of aluminum with iron and copper.

	Aluminum.		Iron.		Steel.	Copper.	
	Cast.	Rolled.	Cast.	Wrought.		Cast.	Rolled.
Color.....	Bluish white.		White.	Gray.	—	—	—
Density.....	2.5	2.7	7.5	7.1-7.8	7.7-7.2	8.96	
Weight per cubic foot in pounds.	162		450	485	490	555	
Melting point.....	1,300° F.		2,780° F.	above 4,000° F.	4,000° F.	1,990° F.	
Tensile strength in pounds per square inch.	20,000 to 25,000.	30-35,000	15,680 lb. (7 tons)	45-60,000 (19-27 tons)	60-90,000 (40-45 tons)	20,000 (does not cast as well as Al.)	30-40,000 lb.
Elongation per cent	14	3.0	7-22	5-15	20-40
Specific heat(a).....	0.21811380952
Electrical conductivity.	34.0	16	99
Thermal conductivity.(b)	33.7	11.9	75

a Higher than any metal except lithium and glucinium.

b Ag. = 100.

As mechanical difficulties are found in working aluminum, the following directions from an authentic source are given for the benefit of those who have occasion to work the metal. They are from a paper read at the Washington meeting of the American Institute of Mining Engineers, February, 1890, by Messrs. Alfred E. Hunt, John W. Langley, and Chas. M. Hall:

"Annealing.—A very low and even temperature should be maintained in the muffle. Aluminum melts at about 1,300 degrees Fahrenheit—a very dark red. The inexperienced, therefore, can not judge the proper annealing temperature by the eye alone without danger of fusing the metal. When the metal has been heated enough to char the end of a pine stick, thus leaving a black mark in the wake of the stick as it is drawn across the metal, it is sufficiently annealed. The metal should then be withdrawn from the furnace and allowed to cool slowly in the air. For some work, such as stamping and drawing, it is sometimes better not to heat the metal so hot as to leave a dead black mark with the stick, but just enough to show a dark brown mark instead. Very thin sheets or wire can be annealed sufficiently for some purposes in boiling water.

"Dipping and picking.—Remove the dirt and grease from the plates by dipping in benzine. To whiten the metal, leaving on the surface a beautiful white mat, the sheet should be first dipped in a strong solution of caustic potash. This solution should then be dipped in a mixture of concentrated acids, two parts nitric acid to one of sulphuric acid; then in a solution of undiluted nitric acid; then in a mixture of vinegar and water, equal parts; then washed thoroughly in water and dried as usual in hot sawdust.

"To polish.—Use a fine polishing composition, or rouge, or tripoli, and a sheepskin or chamois skin buff, although it is often polished with an ordinary rag buff. For fine work, to polish aluminum, use a mixture of equal parts, by weight, of olive oil and rum, made into an emulsion by being well shaken together in a bottle. The polishing stone is dipped in this liquid, and the metal is polished without using, however, too much pressure. Aluminum may be easily ground by using olive oil and pumice. The surface of aluminum, treated with varnish of four parts oil of turpentine to one of stearic acid, or with a mixture of olive oil and rum shaken into an emulsion, allows an engraving tool to work on aluminum as on pure copper.

"For burnishing.—Use a bloodstone or steel burnisher. For hand burnishing use either kerosene oil or a solution composed of 2 tablespoonsful of ground borax dissolved in about a quart of hot water with a few drops of ammonia added.

"For lathe work.—The burnisher should wear upon the fingers of his left hand a piece of Canton flannel, keeping it soaked with kerosene, and bringing it in contact with the metal, supplying a constant lubricant. Very fine effects can be produced by first burnishing or polishing

the metal and then stamping it in polished dies, showing unpolished figures in relief.

Scratch brushing.—Polish or burnish the surface and then use a fine steel scratch brush. A very fine finish is attained by rubbing with ground pumice stone and water. In spinning aluminum, plenty of oil should be used to prevent the clogging of the tool and to make it cut smooth in the turning and to assist in the spinning.

To solder aluminum.—Soldering the metal in large surfaces has not been successfully accomplished up to the present. Small surfaces of the metal can be readily soldered by the use of pure zinc and Venetian turpentine. Place the solder upon the metal with Venetian turpentine and heat gently with a blowpipe until the solder is melted. It will then be found to have fixed itself firmly to the aluminum. The trouble with this, as with other solders, is that it will not flow on the metal. Therefore large surfaces are not easily soldered. In cold-rolling aluminum, upon a roll designed for cold-rolling hard crucible steel, it has been found possible to reduce aluminum through the same sections as hard steel; the aluminum required, on the average, five annealings, where the steel required three to satisfactorily withstand the same work.

Sand castings.—Use open but very fine sand and bake the mold. Large feeding gates should be provided and the mold should be well vented. Pour the metal quickly at a temperature but little above the melting point. Use plumbago crucibles.”

The following translation from a German technical paper, the “*Neueste Erfindungen und Erfahrungen,*” has appeared in the papers here. It is reproduced on account of its possible practical value:

“Sheet aluminum may readily be soldered if previously given a light plating with copper. If aluminum so prepared is suddenly heated, there is considerable stripping of the copper, rendering the joint unreliable. Nevertheless, in many cases, the process is very satisfactory, and particularly so when the copper-plated edges are allowed to lap over each other.

“Aluminum bronze containing as much as 5 per cent. of aluminum may be readily soft soldered with ordinary tin solder. Increasing percentages of aluminum render the soldering more and more difficult, until with 10 per cent. of aluminum it becomes impossible. The method above referred to, of slightly plating with copper, will be found a help in such cases. When no tank is convenient for dipping the edges into the plating solution, very fair results may be obtained by using a number of pieces of blotting paper well soaked with solution of cupric sulphate. The paper is placed in contact with the article to be plated and with a piece of copper. The battery is then attached by wires with the positive pole to the copper and the negative pole to the casting or other object to be plated. A very short time is sufficient to give a plating heavy enough for soldering purposes. If for any reason a battery is

not attainable for plating, the bronze may be prepared with a mixture of resin, tallow, neutral chloride of zinc, and corrosive sublimate.

“Hard soldering offers no difficulties. A good solder for this purpose is made by smelting together 52 parts copper, 46 parts zinc, and 2 parts tin. Borax is used as the flux, and the process is the usual one. Tests of joints made with this solder were made at Neuhausen, and showed that aluminum bronze plates butted together gave a resistance to pulling strain of 26 to 28 kilograms per square millimeter; lapped joints (5 millimeter lap) required 39 kilograms per square millimeter to part them. Tubes made from sheets with this solder can be drawn down on a mandrel.

“Aluminum-bronze castings can be united by the process known to foundrymen as sweating or burning. The parts to be joined are placed in a sand mold and an excess of hot metal flowed over the joint. When carefully done the joint can not be seen, and shows as great strength as the body of the casting. Thin cylinders may be made in this way by bending sheets and sweating their edges together.”

Another formula for soldering, given by Mr. Dagger, which he found to give fairly good results, is, for ordinary work, an alloy of—aluminum, 6 parts; copper, 4; zinc, 90; but the zinc must be free from iron. For heavy soldering the proportions are—aluminum—12 parts; copper, 8, and zinc, 80.

Alloys.—In 1890 the Cowles Company produced 90,941 pounds of ferro-aluminum, containing about 12 per cent. of aluminum and 16,299 pounds of aluminum bronze.

In 1889 the total amount of aluminum alloys produced by this company was 171,759 pounds.

In recent experiments in Europe with aluminum bronze it is said that the alloy has shown itself well adapted for small arms using the new smokeless powders. Its use for ordnance was suggested in this country some three years ago by Mr. E. H. Cowles.

Experiments have recently been made at Calais, France, by the Department of Aërial Navigation with light aluminum alloys. A striking increase in tensile strength is noticeable on adding small quantities of copper to aluminum. The copper was added in the form of wire to the molten metal. As will be seen, the specific gravity of the alloy is not much greater than that of aluminum itself. The following table, from the London Engineer, gives the results of the experiments referred to:

Strength of alloys of aluminum and copper.

Composition.	Specific gravity.		Tons per square inch.
	Calculated.	Determined.	
Aluminum.....		2.67	12.0
Aluminum 98 per cent, copper 2 per cent.....	2.78	2.71	19.65
Aluminum 96 per cent, copper 4 per cent.....	2.90	2.77	19.9
Aluminum 94 per cent, copper 6 per cent.....	3.02	2.82	24.7
Aluminum 92 per cent, copper 8 per cent.....	3.14	2.86	22.7

The aluminum used was from the *Société de l'Aluminium*, and was very nearly pure.

The whole subject of aluminum alloys is being reopened by experiment. Since Deville's time there has been little occasion until recently to make and experiment with alloys of aluminum, or to determine the effect of alloying it with different proportions of a given metal. Aluminum bronze and, in a less degree, brass have become recognized as valuable alloys, but there is apparently a field for experiment which is now being cultivated in many directions.

Besides the alloy of aluminum with silver for use in instruments mentioned above, another alloy of the metal has been made in this country, which is noticeable from a metallurgical standpoint, as well as on account of the peculiar properties of the alloy itself. This is an alloy of aluminum with titanium, which is made in the following way: It will be remembered that aluminum is produced at the Pittsburg Reduction Company's works by forming a fused bath of the fluorides of aluminum, sodium, and calcium, adding alumina thereto, and passing the current from a dynamo through the bath, by which the alumina is decomposed and aluminum is liberated. The alloy under consideration is made in an analogous manner. The fluoride bath is prepared by fusion in a carbon crucible, and either before or after fusion a reducible oxide or salt of titanium is added to it. Titanic oxide is the substance employed in practice. After thorough mixing has taken place, the titanic oxide being dissolved by the fluoride, aluminum is introduced, either in the molten state or solid. The titanic oxide is reduced, and the titanium alloys with the aluminum. The alloy is harder than aluminum, nearly as incorrodible, and, on hammering or rolling, acquires a degree of elasticity comparable to that of spring brass. For commercial uses an alloy containing from about one-half of 1 per cent to 2 per cent of titanium is best. An alloy of aluminum, titanium, and chromium, made in the same way, containing preferably less than 5 per cent of chromium, is also described. The chromium is added to give rigidity.

Metallurgical use.—In 1885, when the beneficial action of aluminum upon molten iron was first attracting attention, the statement was made that the melting point of the iron was very much lowered by adding aluminum to the bath. This statement was subsequently questioned, and has recently been answered definitely by a direct experiment described in a paper on aluminum steel, read before the Iron and Steel Institute at the New York meeting in 1890, by Mr. R. A. Hadfield. (*Journal of the Iron and Steel Inst.*, No. II, 1890.)

A determination of the temperature of fusion, made with a Le Chatelier pyrometer by M. Osmond, of Paris, showed that the addition of 5 per cent of aluminum to steel does not lower the fusion point sensibly. Where there is an increase of fluidity in the metal after adding aluminum, Mr. Hadfield is inclined to attribute it to the evolution of heat due to the oxidation of the aluminum added, which takes oxygen

from the iron oxide and carbonic oxide contained in the steel, rather than to any lowering of the melting point. From many considerations, Mr. Hadfield concludes that the action of aluminum on steel is like that of silicon, but is more energetic. Experiments cited in the paper referred to and in the discussion show that at a very high temperature aluminum is a powerful reducing agent, and will even decompose carbonic oxide, setting carbon free. It is possible that this deoxidizing power of aluminum may account in part, at any rate, for the prevention of blow-holes, which is a remarkable effect attributed to the addition of small quantities of the metal to iron or steel shortly before pouring. If carbonic oxide is contained or formed in the molten metal, it would escape before solidification, and so form blow-holes. But since aluminum decomposes it by depriving it of its oxygen, the evolution and escape of the gas would be prevented in proportion to the amount of aluminum acted on by it.

The following table shows the comparative physical properties of forged silicon and aluminum steels, both materials having been annealed. It is given by Mr. Hadfield to illustrate the similarity of the action of aluminum on steel to that of silicon:

Physical tests of silicon and aluminum steels.

	Per cent.			Limit of elasticity, in tons per square inch.	Breaking load, in tons per square inch.	Extension, per cent on 2 inches.	Reduction of area, per cent.	Bending test of annealed forged bars.
	Carbon.	Aluminum.	Silicon.					
Silicon steel A14	.24	15.17	25	37.55	60.74	Bent double cold.
Aluminum steel A1538	20	26	40.35	60.74	Do.
Silicon steel B18	.73	19	29.50	34.02	52.66	Do.
Aluminum steel C1866	18	27	33	52.14	Do.
Silicon steel C19	1.60	25	33	35	54.52	Do.
Aluminum steel F21	1.60	13	26	36.35	67	Do.
Silicon steel D20	2.18	25.50	34	36.50	59.96	Do.
Aluminum steel H24	2.24	18.50	28.50	33	48.62	Do.
Silicon steel H26	5.53	29	39	.70	2	Would not bend.
Aluminum steel I22	5.60	27	36	6.45	6.16	16°; broken.

Mr. Hadfield's main objection to the use of aluminum instead of silicon as a "physic" is its cost. He says:

"Speaking generally of the application of aluminum to the manufacture of iron and steel, the usual amount stated to be requisite for producing good results is about 0.10 per cent, but in many cases, as already pointed out, this would be too little. Supposing, however, that an average percentage of 0.10 or 0.15 per cent was necessary, and assuming the aluminum to be sold at \$2 per pound, the expense of such addition would mean an extra cost of \$4.50 and \$7.25 per ton, respectively, whereas if as much as even 0.50 per cent of silicon is required to do the same work it does not cost more than \$1.12 per ton."

Mr. Hadfield does not wish to disparage the efforts of those who have devoted so much time to the manufacture of aluminum by offering the

above statement, but on the contrary expresses the hope that it may be an inducement to produce the metal more cheaply.

Aluminum imported and entered for consumption in the United States from 1870 to 1890.

Years.	Quantity.	Value.	Years.	Quantity.	Value.
	<i>Pounds.</i>			<i>Pounds.</i>	
Fiscal years ending June 30—			Fiscal years ending June 30—		
1870.....		\$98	1882.....	566.50	\$6,459
1871.....		341	1883.....	426.25	5,079
1873.....	2.00	2	1884.....	595.00	8,416
1874.....	683.00	2,125	1885.....	439.00	4,736
1875.....	434.00	1,355	Calendar years—		
1876.....	139.00	1,412	1886.....	452.10	5,369
1877.....	131.00	1,551	1887.....	1,260.00	12,119
1878.....	251.00	2,978	1888.....	1,348.53	14,086
1879.....	284.44	3,423	1889.....	998.00	4,840
1880.....	340.75	4,042	1890.....	2,051.00	7,062
1881.....	517.10	6,071			

T I N .

In 1890 the Temescal mine in California made active preparations to produce pig tin. Production was begun early in the following year, when the mine was active. In South Dakota additional interest was directed to the mines of the Harney Peak Company by a visit of the directors, who ordered the construction of a large concentrating plant at Hill City. They decided upon the plans, let the contract for the work, and actual construction was promptly under way. In Virginia important steps were taken towards testing the richness of the Cash and adjacent mines in Rockbridge county. It is evident that the attention which has been lavished upon this comparatively humble metal has been fully sustained in 1889 and 1890. It will require years to decide whether tin mining will pay, but the condition of an actual product has been reached. It has been somewhat a matter of surprise that this product should come from developments in California, which are new compared to the better known operations in South Dakota. But this is simply the outcome of a different policy with the managers of the two enterprises. The deliberate progress in South Dakota, but involving a large investment, is offered as evidence of the owners' confidence in the final outcome. The rapid progress in California on a small scale is interpreted as a practical working test of the richness of the vein which has received the principal development. By this the new purchasers wish to ascertain the worth of the mineral portion of their investment. This investment includes a large agricultural tract, comprising the whole San Jacinto estate, and in which the tin mine is the least known feature. It is entirely possible for South Dakota to reach the position of a large producer as soon as California. The experience as to whether the ore will pay a satisfactory profit can not be gained, however, for years to come.

CENSUS STATISTICS.

The most quantitative and exact account of progress in this industry is that just published by the Eleventh Census, although the account by its brevity indicates very accurately the few items which could be posted in a ledger.

Tin statistics in the United States for the year 1889.

States.	Total out-put of tin-bearing rock. (Short tons.)	Total capital.	Total amount paid for wages.	Other expenditures.
California.....	5,000	\$650,000	\$18,464	\$12,065
South Dakota.....	22,000	200,000	181,783	48,752
Virginia.....	1,000	48,000	1,800

Employés about tin mines in the United States in 1889.

States.	Number of openings.	Above ground.						Below ground.					
		Foremen.		Mechanics.		Laborers.		Foremen.		Miners.		Laborers.	
		Number.	Average wages.	Number.	Average wages.	Number.	Average wages.	Number.	Average wages.	Number.	Average wages.	Number.	Average wages.
California.....	6	2	\$4.66	34	\$3.30	31	\$2.80	1	\$6.46	9	\$2.81	2	\$2.14
South Dakota...	621	8	4.39	28	3.25	49	2.50	5	3.60	132	3.00	8	2.50
Virginia.....	40	1	4.17	1	1.25	11	1.00
Wyoming (a)....	11

a No work done in Wyoming in the census year.

This table shows that much substantial development work has been done on these various deposits. In all 6,000 feet of shafts and tunnels have been put in, besides 2,500 feet of open cuts. In the above statement of labor and wages no account is taken for the so-called assessment work done prior to patenting the claims, as this does not afford very definite employment, except to the few contractors for such work.

With regard to the present facilities for producing tin, it should be said that concentrating works are ready for operations at Glendale, South Dakota, and others have been ordered to be built at Hill City. At the Cash mine, in Virginia, a concentrator is to be built, and at the Temescal mines, in California, a small plant is in actual operation. There is a concentrator at the Etta mine, and the Tin Mountain Mining Company has a Cyclone pulverizer and other mining property.

RECENT DEVELOPMENTS.

South Dakota.—Since the report of 1888 the Burlington and Missouri River Railroad Company has extended its line through Custer, within a mile of Harney City, and directly through Hill City to Deadwood. At Hill City the concentrator of the Harney Peak Company is being erected. At this time (December, 1891) the frame work is nearly completed. In its arrangement the results of the Etta mill have been carefully studied. It is evident from these results that great care must be taken to save the finely-divided ore if the assay yields are to be approximated by the mill. The machinery will be placed as soon as the

railroad spurs to the mill are ready. The company is arranging development work on a larger scale, and will have sunk 500 feet on the Addie by the spring of 1892. Other mines, including the old Etta, will be deepened.

California.—The plant of the San Jacinto estate, limited, consists of a large number of located tin veins and one, the Cajalco, on which considerable developments have been made, produced about 2,000 tons of ore were mined in 1890 and 1891, and which yielded in 1891 120,000 pounds, or 60 tons of metallic tin. The ore was concentrated and then smelted in a small furnace capable of reducing about a ton of metallic tin per twenty-four hours. In the summer of 1890 the concentrating plant was increased by adding pneumatic stamps, so that the mill has 50-stamp capacity or can handle 40 tons of rock in a regular day's work. Steps were taken toward building a dam in Temescal Creek which will furnish plenty of water for the mill, and is also designed to irrigate the agricultural lands of the estate. But the great freshets of 1890 destroyed the dam, which was not built on bed rock. This is now being explored preparatory to rebuilding.

Virginia.—In 1889 Mr. Moses Joy, jr., obtained the control of the Cash mine in Rockbridge County for a company principally of Boston capitalists. The visit of a thoroughly reliable mining engineer to the property in the spring of 1890 gave a much better outlook for the property than it had ever had before, and steps were at once taken to erect a small concentrating plant, a Sturtevant mill, and a vanner. At the close of 1891 this mill is ready for operations near Vesuvius Station on the Shenandoah Valley Railroad, as soon as the bad roads to the ore piles have been improved. It is also the policy of the company not to concentrate any ore until full possession of the mine is secured. The development work has put more than 2,000 tons of ore on the dumps ready to be handled to the concentrator.

Foreign tin mines.—The foreign sources have contributed the usual proportions of the total supply, as follows:

World's supply of tin from 1880 to 1890.

Years.	English production.	Straits shipments to Europe and America.	Australian shipments to Europe and America.	Banca sales in Holland.	Billeteon sales in Java.	Total.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
1880.....	8,918	11,735	9,177	3,756	4,735	38,321
1881.....	8,615	11,400	10,100	4,548	4,740	39,403
1882.....	9,300	11,705	10,067	4,399	4,200	39,671
1883.....	9,307	16,958	11,121	4,203	4,157	45,746
1884.....	9,574	17,548	9,337	4,193	3,600	44,252
1885.....	9,331	17,320	9,088	4,200	3,760	43,699
1886.....	9,312	19,674	8,064	4,379	4,128	45,557
1887.....	9,252	23,977	7,750	4,384	4,978	50,371
1888.....	9,241	23,855	7,975	4,430	5,220	50,721
1889.....	8,912	28,295	6,800	4,114	4,857	52,978
1890.....	9,000	27,470	6,415	5,317	5,232	53,434

There have been few novel developments in the last two years. According to the official reports, the Australian tin placers have grown steadily poorer and the Straits Settlements, with Banca and Billeton, have kept steadily on, with an occasional addition of a new placer. The mines of Siak have been well described by Mr. Charles M. Rolker in a paper published in the Transactions of the American Institute of Mining Engineers and of which a résumé is also published in the Census report. The paper makes a valuable contribution to the meager literature of the tin deposits of the East and is very instructive, particularly as to the labor difficulties in that region.

Imports and exports.—The following tables show the tin and tin plates imported and entered for consumption from 1867 to 1890; also the value of the exports of the manufactures of tin from 1826 to 1890:

Tin and tin plates imported and entered for consumption in the United States, 1867 to 1890.

[Calendar years ending December 31, from 1886 to 1890; previous years ended June 30.]

Years.	In blocks, bars, or pigs, and grain tin.		Tin plates, sheets, etc.		Total value.
	Quantity.	Value.	Quantity.	Value.	
	<i>Cwts.</i>		<i>Cwts.</i>		
1867		\$1, 210, 354. 02		\$6, 276, 136. 78	\$7, 486, 490. 80
1868		1, 454, 327. 36		6, 893, 072. 07	8, 347, 399. 43
1869	80, 811	1, 709, 985. 00	1, 534, 324	8, 565, 432. 56	10, 274, 817. 56
1870	81, 702	2, 042, 887. 71	1, 333, 150	7, 628, 871. 51	9, 671, 759. 22
1871	106, 595	2, 938, 409. 82	1, 556, 023	9, 490, 778. 64	12, 429, 188. 46
1872	102, 006	2, 033, 857. 45	1, 617, 627	10, 736, 906. 59	13, 770, 744. 04
1873	130, 469	3, 938, 032. 25	1, 854, 956	15, 906, 446. 82	19, 844, 479. 07
1874	116, 442	3, 199, 807. 07	1, 553, 860	13, 322, 976. 14	16, 522, 783. 21
1875	102, 904	2, 329, 487. 96	1, 540, 600	12, 557, 630. 75	14, 887, 118. 71
1876	93, 176	1, 816, 506. 00	1, 767, 210	10, 226, 802. 87	12, 043, 308. 87
1877	98, 209	1, 783, 765. 00	1, 984, 893	9, 818, 069. 69	11, 601, 834. 69
1878	128, 849	2, 167, 350. 00	2, 166, 489	9, 893, 639. 61	12, 060, 989. 61
1879	142, 927	2, 301, 944. 00	2, 487, 007	10, 248, 720. 34	12, 550, 664. 34
1880	290, 007	6, 153, 005. 68	3, 298, 534	16, 524, 590. 19	22, 677, 595. 87
1881	171, 146	3, 971, 756. 67	3, 366, 720	14, 641, 057. 87	18, 612, 814. 54
1882	197, 544	5, 204, 251. 68	3, 926, 311	16, 550, 834. 64	21, 755, 086. 32
1883	237, 348	6, 106, 250. 37	4, 051, 108	16, 688, 276. 67	22, 794, 527. 04
1884	(a) 26, 081, 992	5, 429, 184. 01	(a) 527, 881, 321	18, 931, 072. 70	24, 360, 256. 71
1885	23, 947, 523	4, 263, 447. 00	505, 559, 076	16, 610, 104. 56	20, 873, 552. 00
1886	27, 960, 701	5, 873, 773. 00	574, 098, 405	17, 719, 957. 12	23, 593, 730. 12
1887	29, 645, 531	6, 927, 710. 00	570, 643, 389	16, 883, 813. 95	23, 811, 523. 95
1888	31, 740, 583	8, 758, 562. 00	632, 224, 296	19, 034, 821. 03	27, 793, 383. 03
1889	35, 177, 646	7, 045, 939. 00	734, 086, 964	20, 361, 564. 00	27, 407, 563. 00
1890	33, 800, 729	6, 869, 645. 00	688, 247, 657	21, 923, 754. 00	28, 793, 399. 00

a Pounds in 1884 and following years.

Value of tin manufactures exported from the United States (a).

[Fiscal years ending September 30 until 1843; ending June 30, from 1844 to 1886; calendar years since 1886.]

Years.	Value.	Years.	Value.	Years.	Value.
1826.....	\$4,515	1848.....	\$12,353	1870.....	\$46,007
1827.....	2,967	1849.....	13,143	1871.....	70,366
1828.....	5,049	1850.....	13,590	1872.....	67,244
1829.....	1,757	1851.....	27,823	1873.....	69,865
1830.....	4,497	1852.....	23,420	1874.....	62,973
1831.....	3,909	1853.....	22,988	1875.....	48,194
1832.....	3,157	1854.....	30,698	1876.....	48,144
1833.....	2,928	1855.....	14,279	1877.....	87,057
1834.....	2,230	1856.....	13,610	1878.....	116,274
1835.....	2,545	1857.....	5,622	1879.....	103,467
1836.....	5,604	1858.....	24,186	1880.....	144,185
1837.....	10,892	1859.....	39,289	1881.....	498,524
1838.....	10,179	1860.....	39,064	1882.....	198,608
1839.....	19,981	1861.....	30,229	1883.....	191,947
1840.....	7,501	1862.....	62,286	1884.....	166,819
1841.....	3,751	1863.....	41,558	1885.....	162,304
1842.....	5,682	1864.....	46,968	1886.....	157,724
1843 (nine months).....	5,026	1865.....	106,244	1887.....	137,551
1844.....	6,421	1866.....	79,461	1888.....	219,000
1845.....	10,114	1867.....	40,642	1889.....	255,100
1846.....	8,902	1868.....	27,110	1890.....	262,343
1847.....	6,363	1869.....	18,994		

a Classed as "tin, and manufactures of," from 1851.

Prices.—There have been no great fluctuations in prices in the past two years similar to those in 1888, due to the operations of the French copper syndicate. In 1889 the price was comparatively steady, fluctuating by fractions of a cent from 21 cents per pound. In 1890 the prices were not so steady, the principal feature being a rise in September to 25 cents per pound. This soon declined again to 21 cents, which was about the average for the year. The rise in price was due to a speculative movement, and the corner was aided by comparatively light stocks in New York and good consumptive demand. In 1891 the prices ruled slightly lower without great fluctuations, except a rise to 21½ cents in June. The prices for recent years are given below:

Prices of tin in New York by months from 1885 to 1891.

Years.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.	Aug.	Sept.	Oct.	Nov.	Dec.
1885....	16½	17.45	17½	17.80	18½	20½	22½	21½	20.95	20.95	20.65	21.00
1886....	20½	20.70	20.80	20.85	21.30	22½	22½	21½	22.20	22½	22.40	22½
1887....	20.30	22½	22.55	22½	22.95	23½	23.35	23.30	23½	25½	31.05	36½
1888....	36.95	36.95	36.70	32.95	21.95	18.05	19½	20½	22.95	23.35	22.70	22.10
1889....	21½	21½	21.30	20½	20½	20.30	19½	20.20	21.30	20.80	21½	21.30
1890....	20.95	20.87	20.39	20.13	21.52	21.53	21.17	21.62	24.00	22.60	21.07	21.21
1891....	20.20	19.90	19½	19½	20.00	21.00	20.20	20.10	20½	20.10	20.00	19.90

NICKEL AND COBALT.

During 1889 and 1890 nickel mining was depressed in the United States by the developments in Canada, but prospecting for nickel ores was active from the prominence which was given to the metal as an addition to steel. The product of the mines of the United States, together with the foreign ores smelted in the United States, was 252,663 pounds in 1889. In 1890 it was 223,488 pounds. The price did not vary markedly, hence the total values for the years were proportionate—\$151,598 in 1889 and \$134,092 in 1890. The United States' product in both years came from Lancaster Gap, Pennsylvania; Mine La Motte, Missouri, and Lovelock's, Nevada.

Early in 1891 the Lancaster Gap mine was shut down on account of Canadian competition.

Product of the United States, 1876 to 1890.

Years.	Metallic nickel.	Nickel in matte.	Nickel in ore.	Nickel in nickelammonium sulphate.	Total.	Value.
	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Ponnds.</i>	<i>Pounds.</i>	
1876.....					201,367	\$523,554
1877.....					188,211	301,138
1878.....					150,890	165,979
1879.....					145,120	162,584
1880.....					233,893	257,282
1881.....					265,668	292,235
1882.....	277,034	4,582			281,616	309,777
1883.....	6,500	52,300			58,800	52,920
1884.....		64,550			64,550	48,412
1885.....	245,504	14,400	18,000		277,904	179,975
1886.....	182,345	20,000	5,600	7,047	214,992	127,157
1887.....	183,125	10,846		11,595	205,566	133,200
1888.....	190,637		1,000	12,691	204,328	127,632
1889.....	209,763	42,900			252,663	151,598
1890.....	223,488				223,488	134,092

The product of cobalt oxide has been as follows: In 1889 it was 12,955 pounds, valued at \$32,388; and in 1890, 6,788 pounds, worth, at \$2.40 per pound, \$16,291.

The total product of cobalt oxide in late years is given in the following table:

Production of cobalt oxide in the United States.

Years.	Pounds.	Years.	Pounds.	Years.	Pounds.
1869.....	811	1877.....	7,328	1885.....	8,423
1870.....	3,854	1878.....	4,508	1886.....	8,689
1871.....	5,086	1879.....	4,376	1887.....	5,769
1872.....	5,749	1880.....	7,251	1888.....	7,491
1873.....	5,128	1881.....	8,280	1889.....	12,955
1874.....	4,145	1882.....	11,653	1890.....	6,788
1875.....	3,441	1883.....	1,096		
1876.....	5,162	1884.....	2,000		

The closure of the Gap nickel mine in 1891 will result in a smaller product in the future.

The importations have increased markedly in the last two years. They have been as follows:

Cobalt oxide imported and entered for consumption in the United States, 1868 to 1890

Years ending—	Oxide.		Years ending—	Oxide.	
	Quantity.	Value.		Quantity.	Value.
June 30—	<i>Pounds.</i>		June 30—	<i>Pounds.</i>	
1868.....		\$7, 208	1880.....	9, 819	\$18, 457
1869.....		2, 330	1881.....	21, 844	13, 837
1870.....		5, 019	1882.....	17, 758	12, 764
1871.....		2, 766	1883.....	13, 067	22, 323
1872.....		1, 920	1884.....	25, 963	43, 611
1873.....	1, 480	4, 714	1885.....	16, 162	28, 138
1874.....	1, 404	5, 500	1886.....	19, 366	29, 543
1875.....	678	2, 604	December 31—		
1876.....	4, 440	11, 180	1887.....	26, 882	39, 396
1877.....	19, 752	11, 056	1888.....	27, 446	46, 211
1878.....	2, 860	8, 693	1889.....	41, 455	82, 332
1879.....	7, 531	15, 208	1890.....	33, 338	63, 202

Census statistics.—The inquiry into the personnel of the nickel mining industry in 1889 shows that 187 persons are employed. The wages received by them averaged \$3.30 per day for the foreman underground and \$2.61 for foremen on the surface. Miners received \$2.45. Employment was comparatively steady during the year. The total paid in wages to the employes amounted to \$84,200. This included a large amount of unproductive prospecting and development work in Nevada, so that the total received for the 1,151 tons of matte showed a net loss. The mining inquiry of the Census Office did not include the smelting of this matte.

No new deposits of proved value have been found in the United States since the last report, although finds have been noted in North Carolina, the Black Hills of South Dakota, and in Idaho; the Gem mine in Fremont County, Colorado, was also developed slightly. The peculiar arsenide deposits of Nevada have been explored quite thoroughly, and a valuable description was published of these deposits in the census report.

The Canadian mines described in 1888 report continue as the chief factor in the supply in this part of the world. They are located near Sudbury along the Sault Ste. Marie branch of the Canadian Pacific Railway. Here the Canadian Copper Company has opened three mines, the Stobie, Evans, and Copper Cliff (with two water-jacketed furnaces); and the Dominion Copper Company has the Blezard, Worthington, and Crean; and Sir H. H. Vivian owns the Murray mine, 2½ miles northwest of Sudbury. This Vivian mine and the Dominion Company have each a water-jacketed furnace. The total yield of metallic nickel from these mines in 1889 was 2,500,000 pounds of nickel contained in the matte, which formed the article of export, and in 1890, 1,336,627 pounds.

The New Caledonia mines, which have been described frequently, still furnish a large proportion of the world's supply, although the deposits are pockets of uncertain extent. The output in 1890 included

about 5,000 tons of garnierite and 700 tons of manganiferous iron ore containing cobalt. The cost of mining is considerable, the labor uncertain, and the transportation facilities poor. Lately manganiferous iron ores, containing about 3 per cent. of cobalt oxide and perhaps 2 per cent. of nickel, have been sent to Rouen and there parted.

Imports.—The following table shows the imports of nickel into the United States from 1868 to 1890.

Nickel imported and entered for consumption in the United States, 1868 to 1890, inclusive.

Calendar years ending December 31 since 1866; previous years end June 30.	Nickel.		Oxide and alloy of nickel with copper.		Total value.
	Quantity.	Value.	Quantity.	Value.	
	Pounds.		Pounds.		
1868		\$118,058			\$118,058
1869		134,327			134,327
1870		99,111			99,111
1871	17,701	48,133	4,438	\$3,911	52,044
1872	26,140	27,144			27,144
1873	2,842	4,717			4,717
1874	3,172	5,883			5,883
1875	1,255	3,157	12	36	3,193
1876			156	10	10
1877	5,978	9,522	716	824	10,346
1878	7,486	8,837	8,518	7,847	16,684
1879	10,496	7,829	8,314	5,570	13,399
1880	38,276	25,758	61,869	40,311	66,069
1881	17,933	14,503	135,744	107,627	122,130
1882	22,906	17,924	177,822	125,736	143,660
1883	19,015	13,098	161,159	119,386	132,484
1884			(a) 194,711	129,733	129,733
1885			105,603	64,166	64,166
1886			277,112	141,546	(b) 141,546
1887			439,037	205,232	(c) 205,232
1888			316,895	138,290	(d) 138,290
1889			367,288	156,331	(e) 156,331
1890	(f) 566,571	260,665	247,299	115,614	376,279

a Including metallic nickel.

b Including \$465 worth of manufactured nickel.

c Including \$879 worth of manufactured nickel.

d Including \$2,281 worth of manufactured nickel.

e Including \$131 worth of manufactured nickel.

f Classified as nickel, nickel oxide, alloy of any kind in which nickel is the element or material of chief value.

Value of exports of nickel and nickel ore of domestic production from the United States.

Calendar years ending December 31 since 1866; previous years end June 30.	Manufactured nickel.	Nickel coin.	Nickel ore.
1864			\$25,494
1865			36,710
1869			11,350
1872			43,500
1873	\$19,780		19,891
1874	16,062		75,696
1875	26,000		72,020
1876	168,050		35,100
1877	8,200		
1878			2,452
1880	4,120		
1881	6,600	\$32,830	
1882	12,474	7,200	
1883	9,911		<i>a</i> 12,182
1884			<i>a</i> 22,249
1885	1,223		10,500
1886	45,653		5,700
1887	39,209		7,500
1888	38,951		625
1889	100		
1890	446		25

a Classified as "nickel and cobalt ore."

MANGANESE.

BY JOSEPH D. WEEKS.

The ores of manganese are divided into four general classes in the present report: (1) Manganese ores; (2) manganiferous iron ores; (3) manganiferous silver ores; and (4) manganiferous zinc ores. The dividing line between the first two grades is taken at 70 per cent. of manganese dioxide, or 44.252 per cent. of metallic manganese; those containing less manganese, containing also more or less iron, are classed as manganiferous iron ores. In the third class are included the argentiferous manganese ores of Colorado, which are utilized chiefly for the silver they contain, while the fourth class includes only the manganiferous residuum from New Jersey zinc ores.

The long ton of 2,240 pounds is used in this report.

Product of manganese ores.—In 1889 the product of manganese ores proper aggregated 24,197 tons, worth \$240,559. This was obtained as in previous years principally from Crimora, Virginia, Cartersville, Georgia, and Batesville, Arkansas. In 1890, however, 6,397 tons were obtained from Colorado.

Amount and value of manganese ores produced in the United States in 1889 and 1890.

States.	1889.			1890.		
	Production.	Total value.	Value per ton.	Production.	Total value.	Value per ton.
	<i>Long tons.</i>			<i>Long ton.</i>		
Arkansas	2,528	\$23,173	\$9.17	5,339	\$59,861	\$11.21
California	53	901	17.00	386	3,176	8.23
Colorado	6,397	25,588	4.00
Georgia	5,208	50,143	9.63	749	4,920	6.57
Nevada	15	83	5.53	100	300	3.00
North Carolina	47	470	10.00	14	84	6.00
South Carolina	124	744	6.00
Tennessee	30	120	4.00
Vermont	1,576	8,668	5.50
Virginia	14,616	156,257	10.69	12,699	125,121	9.85
Total	24,197	240,559	(a) 9.94	25,684	219,050	(a) 8.53

a Average.

In but four instances at the most is manganese ore mining prosecuted in the United States with anything like regularity, and in but two of the four is mining continuous. At the works producing the largest amount of manganese in Georgia the mines were operated but one hundred and ninety days in the year 1889, while at the Vermont mine during a large proportion of the year but little work was done. At one mine in Virginia and one in Arkansas the mining of manganese is fairly

continuous. At most of the other works the production reported has been from very irregular workings, and chiefly for the purpose of testing the character of the deposit. This is true of all the production of Tennessee, North Carolina, South Carolina, and Nevada, while the California production is from an old mine, worked occasionally to meet a small demand for manganese for the purpose of making chlorine gas in working sulphuret ores. The employés are in most cases men who were employed for a very brief time, and who were in most instances common laborers picked up from farm and other work, returning to their ordinary occupations as soon as their temporary service in stripping manganese ore deposits and in mining the small quantities of manganese reported were completed.

Production of manganese ores in the United States.

States.	1880.	1881.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
Virginia	3,661	3,295	2,982	5,355	8,980	18,745	20,567	19,835	17,646	14,616	12,699
Arkansas	100	175	400	800	1,483	3,316	5,651	4,312	2,528	5,339
Georgia	1,800	1,200	1,000	2,580	6,041	9,024	5,568	5,208	749
Other States...	300	300	375	400	400	450	269	14	1,672	1,845	6,897
Total	5,761	4,895	4,532	6,155	10,180	23,258	30,193	34,524	29,198	24,197	25,684

Product of manganese iron ores.—A large proportion of the hematite iron ores of the United States carry more or less manganese. While in most cases the amount of manganese in these ores does not increase their value over what the same ores would be worth as iron ores were the manganese absent, they, however, make the ore more desirable for certain purposes. No attempt has been made to collect the statistics of these manganese-bearing iron ores except in cases where the manganese in them has added somewhat to their value.

A product of 31,341 tons of ore, containing on an average 9 per cent. manganese, is reported from Michigan for 1889, and a further product of 50,018 tons of ore, containing 6.74 per cent. of manganese, is reported for the same State, making a total of 81,359 tons of iron ore produced in Michigan, containing sufficient manganese to make it desirable to be mined. The value of this ore is reported at \$4.54 a ton. In 1890 the total product was 61,863 tons, and the value \$231,655.

Product of manganese silver ores.—Returns of the production of 17,550 tons of manganese-bearing silver ores have been received for 1889 and 51,840 tons for 1890, all from Colorado. The manganese in these ores makes them desirable as fluxes.

Nearly all the argentiferous iron ores mined from the upper workings of the Leadville deposits carry manganese in varying quantities from 5 up to 25 per cent. and occasionally 30 to 35 per cent., with 5 to 20 ounces of silver, 0 to 4 per cent. of lead, 7 to 18 per cent. in silica, and 30 to 50 per cent. of iron. It has been estimated that from 300 to 500 tons of this ore are produced per day. On the basis of the lowest

figures—that is, 300 tons a day for 300 days in the year—the production of argentiferous manganese ore in the Leadville district would be 90,000 tons; but, as stated above, the total detailed reports received of this production are for only 17,550 tons.

These ores are sold to the smelters for fluxing the siliceous silver ores, and are usually paid for according to the silver contents—that is, so much per ounce of silver, without reference to the manganese contained therein. In some cases the value of this ore has been placed at \$3.50 a ton for its contents of iron and manganese.

Product of mangiferous silver ores in the United States in 1889 and 1890.

	1889.		1890.	
	Quantity.	Value.	Quantity.	Value.
Colorado, 20 per cent of manganese and over	<i>Long tons.</i> 9,987	} \$227,455	<i>Long tons.</i> 7,826	\$27,391
Colorado, less than 20 per cent of manganese	55,000		44,014	154,049
Total	64,987	227,455	51,840	181,440

Product of mangiferous zinc ores in the United States in 1889 and 1890.

Years.	Quantity.	Value.
1889.....	<i>Long tons.</i> 43,648	\$54,560
1890.....	48,560	60,700

Total product of all kinds of manganese ores in the United States in 1889 and 1890.

	1889.			1890.		
	Quantity.	Value.	Value per ton.	Quantity.	Value.	Value per ton.
Manganese ores.....	24,197	\$240,559	\$9.94	25,684	\$219,050	\$8.53
Manganiferous iron ores.....	83,434	271,680	3.26	51,863	231,655	3.74
Manganiferous silver ores.....	64,987	227,455	3.50	51,840	181,440	3.50
Manganiferous zinc ores.....	43,648	54,560	1.25	48,560	60,700	1.25
Total	216,266	794,254	3.67	187,947	692,845	3.69

Manganese imported and entered for consumption into the United States in 1889 and 1890.

Years.	Ore.		Oxide of.	
	Quantity.	Value.	Quantity.	Value.
1889	<i>Long tons.</i> 4,135	\$72,391	<i>Long tons.</i> 151	\$6,000
1890	33,998	509,704	156	7,196

THE WORLD'S PRODUCTION OF MANGANESE.

The following table exhibits an estimate of the world's product in 1888 and 1889. Where the figures are not obtainable for either of these

years the latest available statistics are given, and are regarded as approximately the annual product:

Total product of manganese in the world in 1888 and 1889.

Countries.	1888.	1889.	Countries.	1888.	1889.
	<i>Tons.</i>	<i>Tons.</i>		<i>Tons.</i>	<i>Tons.</i>
Caucasus (Russia).....	48,653	60,000	Greece.....	385	400
United States.....	29,198	24,197	Italy.....	1,652	400
Chile.....	24,746	5,000	Cuba.....	1,581	4,000
France (1886).....	7,676		Other countries.....	3,114	1,000
Sweden.....	6,089		Nova Scotia.....	106	200
Portugal.....	5,638	18,000	New Brunswick.....	1,094	1,000
Spain.....	2,830		Quebec.....	3	
Australia.....	1,572	9,000	Great Britain (1887).....	13,054	10,000
New Zealand.....	787		Bosnia.....	4,000	2,000
Turkey.....	669	8,000	Holland.....	1,107	800

ARKANSAS.

Manganese ores are found in two localities in Arkansas; one covering portions of Independence and Izard counties, in the northeastern part of the State, and known as the Batesville region; the other in the southwestern portion and extending from Pulaski county on the east to Polk county and the Indian Territory on the west. The Batesville region has produced all the ores mined commercially in the State. What little work has been done in the other district has been principally in the way of development.

The production of manganese in Arkansas since the beginning of shipments in 1850, as far as can be ascertained, is shown in the following table. The authorities for the figures are quoted in each instance. It has been estimated that the total production of manganese in Arkansas from 1850 to 1885 amounted to 5,000 tons, but this is probably exaggerated. The product from 1881 to 1884, inclusive, has been obtained from the railroad reports of shipments and may be considered fairly reliable. From 1885 to 1888 and for 1890 the statistics were collected for Mineral Resources of the United States, while those for 1889 are from the mineral volume of the Eleventh Census. The figures from 1885 to 1890 have been verified by statements of shipments kindly furnished by the officers of the St. Louis, Iron Mountain and Southern railroad.

Production of manganese in the Batesville district of Arkansas to December 31, 1890.

Years.	Authority.	Tons.
1850 to 1867.....	Estimated.....	400
1868.....	do.....	10
1881.....	Railroad reports of shipments.....	100
1882.....	do.....	175
1883.....	do.....	400
1884.....	do.....	800
1885.....	Mineral Resources of the United States.....	1,483
1886.....	do.....	3,316
1887.....	do.....	5,651
1888.....	do.....	4,312
1889.....	Census.....	2,528
1890.....	Mineral Resources of the United States.....	5,339

Product of manganese ores in Arkansas, from 1880 to 1890.

Years.	Quantity.	Years.	Quantity.
	<i>Long tons.</i>		<i>Long tons.</i>
1880		1886	3,316
1881	100	1887	5,651
1882	175	1888	4,312
1883	400	1889	2,528
1884	800	1890	5,339
1885	1,483		

CALIFORNIA.

The first mining of manganese in California is reported to have been done in 1867 by Mr. A. S. Ladd, at Corral Hollow, in Alameda county. This was carried on until 1874, the ore, which is said to have amounted in all to about .5,000 tons, being shipped to England for use in chemical manufacture. Since 1874 Spanish manganese has supplanted the California product in England, and this market for the latter being closed the production has been small. The Ladd mine was sold in 1874 to Mr. Justinian Caire, who produces a small amount each year, the product for 1889 being 53 tons, worth about \$17 per ton. The ore runs from 56 to 72 per cent. pyrolusite; and when fresh is a hard, black, massive variety, occurring in a lenticular bed, interstratified in red, yellow, and gray jasper. In 1890 the product increased to 386 tons, but decreased in the price per ton to \$8.23.

Regarding the total product of the State, little can be said and still less can be authoritatively stated regarding the annual product in each year. A prominent dealer on the coast reports, as published in the Mineral Resources of the United States, 1886, that the total amount used in California was from 100 to 150 tons annually. The price is said to have been \$3 to \$4 per ton at the mine for ore carrying from 50 to 60 per cent. manganese. The price quoted for the product in 1889 was for ore delivered in San Francisco. If, as is stated above, 5,000 tons of ore were mined in California up to 1874, it is possible that between 6,000 and 6,500 tons of manganese may have been produced in the State from the beginning of mining.

An analysis of the manganese from the Corral Hollow mine is as follows:

Analysis of manganese from Corral Hollow, California.

	Per cent.
Manganese protoxide (MnO)	75.26
Oxygen (O)	6.94
Ferric oxide (Fe ₂ O ₃)	3.26
Cobalt oxide (CoO)	Trace
Lime (CaO)	3.10
Baryta (BaO)	None
Magnesia (MgO)	0.56
Potash (K ₂ O)	0.19
Soda (Na ₂ O)	0.58
Water (H ₂ O)	8.46
Silica (SiO ₂)	1.98
Total	100.33

Other deposits of manganese are known to exist in California, but they are at present of no commercial importance.

COLORADO.

Colorado produces two classes of manganese-bearing ores, a manganese-bearing iron ore, used to some extent in the production of spiegeleisen, and a manganese-bearing silver ore, used as a flux in the smelting of silver-lead ores. The manganese-bearing iron ores carry, as a rule, but little silver, though in some cases the content of silver has been so high as to justify the working for silver of the slags produced at the blast furnaces at the time they were running on spiegeleisen.

These ores are all from the upper workings of the Leadville silver deposits, and carry manganese in varying quantities, from 5 up to 25 per cent., and occasionally 30 to 35 per cent., with 0 to 20 ounces of silver, 0 to 4 per cent. of lead, 7 to 18 per cent. in silica, and 30 to 50 per cent. of iron.

As stated above, those high in manganese and low in silver are sold to steel works for the manufacture of spiegeleisen, while those carrying silver and not too high in silica are sold to the silver smelters and paid for according to the content of silver. It is usual for the smelters to buy these ores according to their so-called "silica excess"—that is, the excess of iron and manganese over silica. This "silica excess" was placed in 1889 at 40 per cent.—that is, there must be an excess of 40 per cent of manganese and iron over the silica in the ore, and it is then accepted and paid for, not according to its iron and manganese contents, but its silver. When the "excess" is above 40 per cent. the excess is paid for at 10 cents a unit. Thus, an ore with the following composition: metallic manganese, 25 per cent.; metallic iron, 30 per cent.; silica, 2.5 per cent., and silver, 5 ounces, would have an excess of iron over silica of 52.5 per cent., or 12.5 per cent. above the 40 per cent. minimum excess. This, at 10 cents a unit, would be \$1.25; the 5 ounces of silver, at 45 cents an ounce, would be \$2.25, and the ore would be worth \$3.50. It will not pay to produce these ores at less than \$3.50, free on board at mines.

It has been estimated that from 300 to 500 tons of this ore are produced per day. On the basis of the lowest figures—that is, 300 tons a day for 300 days in the year—the production of manganese-bearing silver-iron ore in the Leadville district would be 90,000 tons.

The actual shipments to spiegel furnaces in 1889 were 2,075 long tons. It is estimated that in addition to this 9,987 tons, containing over 20 per cent of manganese, were sold as flux ores, and returns of the sales of some 55,000 tons of flux ores carrying less than 20 per cent of man-

gane have been received. This would make the production in 1889 as follows:

Production of manganese ores in Colorado in 1889.

	1889.	1890.
Manganiferous iron ores used for spiegeleisen.....	<i>Long tons.</i> 2,075	<i>Long tons.</i>
Manganiferous silver ores, with 20 per cent and over of manganese.....	9,987	7,826
Manganiferous silver ores, with less than 20 per cent of manganese.....	55,000	44,014
Total.....	67,062	51,840

As these ores were not produced as manganese ores, no returns of capital, employés, etc., can be given. Analyses of these ores carrying 20 per cent. and over of manganese are as follows:

Analyses of manganese iron ores in Colorado.

Component parts.	Catalpa.	Crescent No. 1.	Crescent No. 2.	Hull.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Iron.....	34.90	17.80	21.15	35.00
Silica.....	6.90	6.30	7.00	3.83
Manganese.....	21.30	34.00	31.00	19.30
Alumina.....	4.15	2.00
Lime.....	0.34	0.46
Magnesia.....	0.07	0.45
Sulphur.....	0.06	0.027
Phosphorus.....	0.04	0.056
Copper.....	Trace.	0.03
Oxide of lead.....	1.85
Volatile matter.....	9.36
Water.....	2.96

GEORGIA.

Near Cartersville, Georgia, is one of the oldest manganese ore-producing districts in the country. It is also one which has been most continuously worked. Mining was begun at this locality in 1866 by the Pyrolusite Mining Company, and 550 tons of ore were mined and sold in that year. The deposits are in the northwestern part of the State, in Bartow county, extending into Cherokee county. Other deposits have also been found in the extreme northwestern part of the State, in what is known as the Cave Spring district, but the product is almost entirely from the Cartersville region.

The production of manganese ore in Georgia has varied greatly, increasing nearly 100 per cent. from 1885 to 1886, or from 2,580 to 5,981 tons; nearly the same rate of increase is shown in the product for 1887, or to 9,024 tons. In 1888, it decreased to less than in 1886, and 360 tons more in 1889, the product for the two years being, respectively, 5,568 and 5,208 tons. In 1890 the product fell off to less than any year since 1866, being only 749 tons. The following table shows the annual production of manganese ores in Georgia so far as ascertained:

Production of manganese ore in Georgia from 1866 to 1890, inclusive.

Years.	Quantity.	Years.	Quantity.
	<i>Long tons.</i>		<i>Long tons.</i>
1866	550	1879	2,400
1867	5,000	1880	1,800
1868		1,200	
1869		1,000	
1870			
1871			
1872	2,400	1884	
1873			
1874			
1875			
1876			
1877		1885	2,580
1878		1886	5,981
		1887	9,024
		1888	5,568
		1889	8,208
		1890	749

NEVADA.

A small amount of manganese has been produced in Nevada, near Golconda, on the Central Pacific railroad. The product in 1889 was 15 tons, worth \$83. In 1890 the product increased to 100 tons, worth \$300.

NORTH CAROLINA.

Frequent reports are made of discoveries of manganese ore in North Carolina, but up to the present time it has not been found in paying quantities. The amounts reported as being mined in this State have been only for experimental purposes. In 1889 the product was 47 tons, valued at \$10 per ton, and in 1890, 14 tons, valued at \$6 per ton. The product since 1886 has been as follows:

Production of manganese in North Carolina from 1886 to 1890, inclusive.

Years.	Tons.
1886	15
1887	14
1888	50
1889	47
1890	14

SOUTH CAROLINA.

Very little manganese has been mined in South Carolina, though no doubt deposits exist here as they do in North Carolina. The only deposit that has been worked, so far as ascertained, is on the Dorn lands, near McCormick, and is owned by the Manganese Mining Company. Mining was begun in 1885 and continued until 1889. No product is reported for 1890.

The total production of manganese ore in South Carolina, so far as the same has been ascertained, is as follows:

Total production of manganese ore in South Carolina.

Years.	Tons.
1885 and 1886	300
1887	45
1888	50
1889	124

TENNESSEE.

So far as has been learned, the first manganese produced in the United States was in 1837, near Whitfield, Hickman county, Tennessee. It was for use in coloring earthenware, and it has been used for this purpose continuously ever since. The product, however, has been but a few hundred pounds each year. Exclusive of this small annual product in Hickman county, the product of Tennessee has amounted to 96 tons. This is since 1886, when the first is reported. No product is reported for 1887 or 1890.

Total production of manganese ore in Tennessee.

Years.	Tons.
1886	50
1887	
1888	16
1889	30
1890	

VERMONT.

According to Hitchcock's Geology of Vermont, manganese ore had been shipped from Brandon and Chittenden to England, but no reliable reports of actual production are obtainable for any year previous to 1888. The product for 1888 is given at 1,000 tons. Messrs. Carnegie Brothers & Co., limited, operated the Brandon deposits in 1889 and produced 1,576 tons, but abandoned them in 1890 and no ore was mined in that year.

VIRGINIA.

The production of manganese in Virginia in 1889 was 14,616 tons, valued at \$156,257. This was considerably more than half the product of the entire country. In 1890 the production decreased 1,917 tons, being 12,699 tons, worth \$125,121, and a little less than half the entire product reported for that year. The product in this State has shown a steady decrease since 1886, in which year it reached its maximum figure. The production of manganese in Virginia since 1880 has been as follows:

Production of manganese in Virginia from 1880 to 1890, inclusive.

Years.	Tons.
1880	3,661
1881	3,295
1882	2,982
1883	5,355
1884	8,980
1885	18,745
1886	20,567
1887	19,835
1888	17,646
1889	14,616
1890	12,699

So far as explorations have been made, manganese ores have been found over a much greater extent of territory in Virginia than in any other State. It is uncertain what future development may disclose in other States, but at present Virginia has more known deposits of this mineral. More localities have been worked and more manganese produced, and yet there were but two localities in 1889 and 1890 which produced any considerable amount. These are the Crimora and Houston mines. A small amount of high-grade pyrolusite, used in the manufacture of glass and bromine, was shipped from the Leets or Lerner mine, at Mount Athos. The three mines mentioned are the only ones producing regularly in the State. The Crimora and Houston are decreasing in production.

CHROMIC IRON ORE.

In 1889 and 1890 the same desultory mining of chrome iron ore which has been reported in previous volumes continued. Notices of deposits continue to be made in North Carolina and Georgia, but shipments came only from California. In 1889, 2,000 long tons, worth in San Francisco \$30,000, were produced, and 3,599 tons in 1890, worth \$53,985. The annual product since 1880 is as follows:

Production of chromic iron ore in the United States.

Years.	Quantity.	Value.	Years.	Quantity.	Value.
	<i>Long tons.</i>			<i>Long tons.</i>	
1880.....	2,288	\$27,808	1886.....	2,000	\$30,000
1881.....	2,000	30,000	1887.....	3,000	40,000
1882.....	2,500	50,000	1888.....	1,500	20,000
1882.....	3,000	60,000	1889.....	2,000	30,000
1884.....	2,000	35,000	1890.....	3,599	53,985
1885.....	2,700	40,000			

The production of chromic iron ore in California during 1890 and 1891 has been as follows:

Production of chromic iron ore in California in 1890 and 1891, by counties.

Counties.	1890.	1891.
	<i>Long tons.</i>	<i>Long tons.</i>
Alameda.....	355	229
San Luis Obispo.....	687	74
Tehama.....	2,207	1,069
Placer.....	150
Shasta.....	200
Total.....	3,599	1,372

Mr. C. C. Darwin, of the Geological Survey, while engaged in other work on the Pacific coast, has visited the scattered localities where chromic iron ore is produced, and states that there is no mining of the ore properly speaking and no company or combination of men operating in any one place. The ore is quarried out in dull times by land owners who have found pockets of it, reported it to interested parties, and been furnished by these parties with the capital needed to break it out and pile it up for transportation. In most cases the work is done only in the intervals of farming, and the owner gets only a royalty on every ton of sufficiently high grade ore. While there are outcroppings of the ore in the serpentine all along the foothills of the Sierras, most of

it contains less than 47.5 per cent. of Cr_2O_3 and has at present no commercial value, and the richer ore deposits are in localities so inaccessible that the cost of getting it to railroad station or seaport consumes all the profit that could be made upon it. The experience of the men handling the chromic ores on the Pacific coast shows that no ore grading less than 50 per cent. can be got to San Francisco, shipped even at ballast rates around the Horn to Philadelphia or Baltimore, and pay the cost of handling it in competition with the ores from the Mediterranean.

Wherever found it has been in pockets that are sooner or later exhausted, so that, even in the most promising finds, the policy of constructing roads over which to haul it can not be determined until the contents of the pocket have been broken out and estimated. There are many dumps in San Luis Obispo county and in Del Norte which have been owned for years by brokers who found the ore of good quality and purchased it, but have never marketed it because the quantity in any one place will not at present prices warrant the expense of building the roads necessary to haul it to transportation facilities.

The great falling off in the figures for 1891 as compared with those for 1890 is on account of the practical withdrawal from the business of one of the San Francisco firms handling the ore. The profit is so little that there is nothing to be made commensurate with the trouble involved. Another large broker in this ore has been experimenting with a view to increasing the purity of the marketed article or finding some commercial use for the impurities in the crude ore. He has discovered a process which gives him a purer article, but this purer article can not be shipped at ballast rates as can the crude ore. All the attempts so far made to free the weaker ores from their impurities have failed.

It is then easy to see why, with these hills full of pockets of the ore, but one-third of the quantity demanded by the Baltimore and Philadelphia manufactories has been supplied by California, while the other two-thirds has come from the Mediterranean. Under these discouraging conditions, however, there has been marketed from the Pacific coast the number of tons of chromic iron ore as set forth in the above table. Most of it has been sold by the small producers to two firms in San Francisco, namely, Messrs. N. R. Knight & Co. and Messrs. Kruse & Euler.

The Del Norte mines do not figure in the table of production, and will market no more chromic iron ore until other interests in that locality prompt capitalists to reconstruct roads and railways which were some time ago destroyed by an inundation that swept the valley clean, carrying to the sea, houses, men, roads, and everything. The profit on this ore alone will not justify the construction of the new ways and works.

There is one exception to the statement that there is no mining of

chromic iron ore properly speaking in California, to wit, the Pick and Shovel mine, near San Luis Obispo, which has been exploited quite systematically, and in which galleries are now being excavated from exhausted pockets along the line of thin seams of ore in search of contiguous deposits.

The fact that the two consuming firms, the Baltimore Chrome Works, in Baltimore, Maryland, and the Kalion Chemical Company, in Philadelphia, Pennsylvania, are independent of the domestic supply by reason of foreign imports from Turkey is the reason why greater efforts are not made to increase the California product.

Chromic iron ores, the quality ranging from 35 to 55 per cent, Cr₂ O₃, are to be found in practically unlimited quantities throughout the range of hills running through the States of California and Oregon west of the Sierra Nevada mountains. It is only the difficulties that surround the transportation of this mineral to a market that prevent those States from being the sole producers of ore for the use of the American factories. In due course these ores will find their way to a market in larger quantities than at present. The fact is that the United States is, under certain conditions, independent of the production of any foreign countries for its supply of this valuable mineral.

Imports.—The following table shows the imports of chromate and bichromate of potash and chromic acid imported and entered for consumption into the United States from 1867 to 1890:

Chromate and bichromate of potash and chromic acid imported and entered for consumption in the United States, 1867 to 1890, inclusive.

[Calendar years since 1886; previous years end June 30.]

Years.	Chromate and bichromate of potash.		Chromic acid.		Chrome ore.		Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Long tons.</i>		
1867	875,205	\$88,787					\$88,787
1868	777,855	68,634					68,634
1869	877,432	78,288		\$3			78,291
1870	1,235,946	127,333		8			127,341
1871	2,170,473	223,529		5			223,534
1872	1,174,274	220,111	514	49			220,160
1873	1,121,357	178,472	922	276			178,748
1874	1,387,051	218,517	44	13			218,530
1875	1,417,812	183,424	45	22			183,446
1876	1,665,011	175,795	120	45			175,840
1877	2,471,669	264,392	13	10			264,402
1878	1,929,670	211,136	32	35			211,171
1879	2,624,403	221,151					221,151
1880	3,505,740	350,279	5	3			350,282
1881	4,404,237	402,088	124	89			402,177
1882	2,449,875	261,006	52	42			261,048
1883	1,990,140	208,681	290	338			209,019
1884	2,593,115	210,677		120	2,677	\$73,586	284,383
1885	1,448,639	92,556		39	12	239	92,834
1886	1,985,809	139,117		101	3,356	43,721	182,949
1887	1,722,465	120,305		5,571	1,404	20,812	146,668
1888	1,755,489	143,312		281	4,440	46,735	190,328
1889	1,580,385	137,263		2,974	5,474	50,782	191,019
1890	1,304,185	113,613		634	4,353	57,111	171,358

Foreign sources.—The principal foreign supply comes from Turkish and Grecian deposits, which were described in the last report. The manufacturers in Glasgow obtain their supplies from the same sources, while the Germans obtain a supply from Spain. According to a British consular report, the mines at Dubostica, Austria-Hungary, produce from 2,000 to 3,000 tons of chromic iron ore annually, which goes to Hamburg and Glasgow. The Russian mines produced 9,000 long tons in 1888 and 5,000 long tons in 1889, all from Perm and Orenboorg.

Mr. Henry Bower has determined that the relative quantity of the bichromate of potash and soda produced and sold in the United States is in the proportion of three to one in favor of the potash salt. For many of the uses to which these substances are applied they are not interchangeable, hence bichromate of potash will always remain the more important of the two.

Two factories producing chromates are now in existence in the United States, with a joint capacity sufficient to fill the entire needs of the country. The quantity of bichromates of potash and soda manufactured at these establishments is not known, but it is believed that the consumption of these salts has materially decreased during the past ten years. This is owing to the introduction of dyestuffs requiring a lessened quantity of chromium to produce the same results that were formerly obtained from other dyeing materials. The works mentioned are the Baltimore Chrome Works, at Baltimore, Maryland, and the Kalion Chemical Company, of Philadelphia, Pennsylvania. The relative capacity of the two is not known, but is supposed to be as five is to three in favor of the former.

Prices.—The prices of bichromate of potash since 1845, when it was first manufactured in the United States, are given below:

Prices of bichromate of potash in the United States from 1845 to 1891.

Years.	Cents per pound.	Years.	Cents per pound.
1845	19 $\frac{7}{8}$	1869	16 $\frac{7}{8}$
1846	18 $\frac{3}{8}$	1870	14 $\frac{3}{8}$
1847	17 $\frac{3}{8}$	1871	16 $\frac{3}{8}$
1848	16 $\frac{3}{8}$	1872	20 $\frac{1}{8}$
1849	20 $\frac{3}{8}$	1873	20 $\frac{3}{8}$
1850	22 $\frac{3}{8}$	1874	18 $\frac{3}{8}$
1851	17	1875	18 $\frac{3}{8}$
1852	15 $\frac{3}{8}$	1876	15 $\frac{3}{8}$
1853	15	1877	13
1854	15 $\frac{1}{8}$	1878	12 $\frac{7}{8}$
1855	14 $\frac{1}{8}$	1879	12 $\frac{7}{8}$
1856	16 $\frac{1}{8}$	1880	13 $\frac{7}{8}$
1857	18 $\frac{1}{8}$	1881	15 $\frac{3}{8}$
1858	20 $\frac{3}{8}$	1882	15 $\frac{3}{8}$
1859	19	1883	14 $\frac{3}{8}$
1860	20 $\frac{3}{8}$	1884	11 $\frac{3}{8}$
1861	20 $\frac{3}{8}$	1885	10
1862	20 $\frac{3}{8}$	1886	9 $\frac{7}{8}$
1863	23 $\frac{1}{8}$	1887	10
1864	26 $\frac{1}{8}$	1888	10 $\frac{1}{8}$
1865	25 $\frac{1}{8}$	1889	11 $\frac{1}{8}$
1866	23 $\frac{7}{8}$	1890	10 $\frac{1}{8}$
1867	19 $\frac{3}{8}$	1891	9 $\frac{1}{8}$
1868	18 $\frac{3}{8}$		

ANTIMONY.

The amount of antimony produced in 1889 was 230,000 pounds, valued at \$28,000. In 1890 the product amounted to 257,768 pounds, valued at \$40,756. During 1889 the only States producing antimony ore, stibnite, were Arkansas and Nevada, the former having a product of 65 tons and the latter 200 tons. In 1890 Nevada produced 310 tons of ore, 250 tons of which were smelted in San Francisco, producing 190,000 pounds of star regulus. The United States Antimony Company of Philadelphia smelted 111 tons of ore, 81½ tons of which were mined from its own property in Arkansas, and 29½ tons were from the neighborhood of Thompson Falls, Montana. The Arkansas ore yielded in metallic antimony 54,188 pounds, and the Montana ore yielded 13,580 pounds. The total product of ore in Montana was 46 tons, but only 29½ tons of this was smelted. In addition to the 46 tons of "first-class" ore produced in Montana (ore yielding 35 per cent. or more of star regulus being considered first class) there were 200 tons of second-class ore mined, none of which was sold or treated. The amount of ore produced and treated and the amount and value of the antimony obtained in 1889 and 1890 are shown in the following table:

Production of antimony in 1889 and 1890.

Years.	Amount of ore produced.	Amount of ore treated.	Amount of antimony obtained.	Value of metallic antimony.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Pounds.</i>	
1889.....	265	265	230,000	\$28,000
1890.....	435	361	257,768	40,756

Production of antimony from 1882 to 1890.

Years.	Pounds.	Value.	Years.	Pounds.	Value.
1882.....	120,000	\$12,000	1887.....	150,000	\$15,000
1883.....	120,000	12,000	1888.....	200,000	20,000
1884.....	120,000	12,000	1889.....	230,000	28,000
1885.....	100,000	10,000	1890.....	257,768	40,756
1886.....	70,000	7,000			

Additional facilities for mining and reducing antimony ore were added to the industry in 1890. The United States Antimony Company has sunk about 200 feet of shafts at its mines in Arkansas, and extended several hundred feet of drifts, besides erecting three additional smelt-

ing furnaces for the reduction of its ores. Reduction works have also been completed at Lovelock's, Nevada, and the operators state they will hereafter produce metallic antimony at the mines instead of sending the ore to San Francisco for smelting. The demand for antimony was reported as fair during the most of the year, but notwithstanding a good demand the prices fell off from 22½ cents per pound in the early part of the year to 17 cents at the close. As will be seen from the following table the antimony produced in the United States is but a small portion of the amount consumed. The tariff bill passed in 1890 reduced the duty on antimony from 2 cents to $\frac{3}{4}$ of a cent per pound.

Antimony and antimony ore imported and entered for consumption in the United States, 1867 to 1890.

Years ended—	Crude and regulus.		Ore.		Total value.
	Quantity.	Value.	Quantity.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>		
June 30—					
1867		\$63,919			\$63,919
1868	1,033,336	83,822			83,822
1869	1,345,921	129,918			129,918
1870	1,227,429	164,179			164,179
1871	1,015,039	148,264		\$2,364	150,628
1872	1,933,306	237,536		3,031	240,567
1873	1,166,321	184,498		2,941	187,439
1874	1,253,814	148,409		203	148,612
1875	1,238,223	131,360	6,460	609	131,969
1876	946,809	119,441	8,321	700	120,141
1877	1,115,124	135,317	20,001	2,314	137,631
1878	1,256,624	130,950	20,351	1,259	132,209
1879	1,380,212	143,099	34,542	2,341	145,440
1880	2,019,389	265,773	25,150	2,349	268,122
1881	1,808,945	253,054	841,730	18,199	271,253
1882	2,525,838	294,234	1,114,699	18,019	312,253
1883	3,064,050	286,892	697,244	11,254	298,146
1884	1,779,337	150,435	231,360	6,489	156,924
December 31—					
1885	2,579,840	207,215	215,913	7,497	214,712
1886	2,997,985	202,563	218,366	9,761	212,324
1887	2,553,284	169,747	362,761	8,785	178,532
1888	2,814,044	248,015	68,040	2,178	250,193
1889	2,676,130	304,711	146,309	5,568	310,279
1890	3,315,659	411,960	611,140	29,878	441,838

P L A T I N U M .

The production of this substance is almost entirely confined to the western slope of the Ural mountains. Small amounts, however, are produced in South America and a trifling quantity of 600 ounces, worth \$2,500 in the crude state, was mined in the United States in 1890 and 500 ounces in 1889, valued at about the same rate.

The two principal platinum producing districts of Russia are situated on the slopes of the Ural mountains, on the Siberian side, and are called the Isa, or Goro-Blagodot district, and the Nisjne Tagilsk, or Demidoff district. They are situated about 100 miles apart, the former being the more northern. Each consists of dried but recent river beds, the Isa district being those forming a part of the Isa river drainage system and the Nisjne Tagilsk district being composed of similar dry tributaries to the Martin (Martian) river. These districts were probably originally gold placers, but there is nothing now to show this, as they are at present worked for platinum only. The platinum producing regions of Russia have been the subject of much speculation by outsiders as to their real nature and conditions on account of the meagerness of definite information obtainable in regard to them, owing to the characteristic secrecy of the Russian managers of these mines. But in the spring and summer of the present year (1891) Mr. George F. Kunz made a trip to these placers and has thrown much light on this hitherto dark subject. The Isa district is under the control of the Government, but the Nisjne Tagilsk district is worked as a business enterprise and is a part of the Demidoff estate, which was granted to the prince in order that these placers might be worked. For a further account of how these mines are worked, the cost of labor, etc., the reader is referred to the report of the Eleventh Census on the "Mineral Industries in the United States," where the results of Mr. Kunz's trip are given in detail. This report contains several illustrations of the deposits and the methods of washing the sand, etc., which will be found interesting and of much value.

The following table gives the production of platinum in Russia from 1880 to 1889, and is compiled from the best sources obtainable:

Product of platinum in Russia from 1880 to 1889.

Years.	Quantity.	Years.	Quantity.
	<i>Kilograms.</i>		<i>Kilograms.</i>
1880	2,947	1885	2,591
1881	2,986	1886	4,317
1882	4,081	1887	4,242
1883	3,537	1888	2,636
1884	2,237	1889	2,703

Price.—The price of platinum was phenomenally high during 1889 and 1890. It averaged above \$16 per ounce. The cause of this rise in price is generally attributed to a purchase of a large quantity of scrap platinum by Messrs. Johnson, Matheys & Co. and Des Moutis, Le Brun & Co. They purchased about 500,000 ounces. The consequent rise in price led to old platinum being brought from many unexpected places. The quantity was too large for the price to remain so high, and it declined again by the close of 1891 to \$9.50 per ounce. It is probable that the fluctuations in the near future will only be such as result from Russian finances. The price late in 1891 rose slightly at the mines on account of the change in the value of the Russian ruble. The high prices prevailing in 1889 and 1890 stimulated Russian production.

IMPORTS.

Platinum imported and entered for consumption in the United States, 1867 to 1890.

Calendar years ending December 31 since 1886; previous years end June 30.	Manufactured.	Unmanufactured.		Vases or retorts, etc.
		Quantity.	Value.	
		<i>Pounds.</i>		
1867	\$456			
1868	290	\$95,208	\$20,274	
1869	184	80,014	22,004	
1870	648	99,984	16,294	
1871	48	108,244	22,470	
1872	310	91,472	21,816	
1873	43	90,771	9	
1874	143	123,293	59,698	
1875	173	141,188	18,982	
1876	6	141,207	7,421	
1877	11	81,925	18,611	
1878	241	120,121	50,133	
1879	73	166,178	34,209	
1880	964	217,144	41,827	
1881	290	273,343	21,292	
1882	1,731	3,125.60	48,452	
1883	4	3,104.15	92,967	
1884		2,846.00	83,112	
1885	3	2,612.34	17,473	
1886		3,422.00	71,864	
1887		4,732.00	68,051	
1888		5,226.00	58,355	
1889	338	5,394.00	110,757	
1890		5,763.00	77,957	

Value of platinum exports.

Calendar years ending December 31 since 1886; previous years end June 30.	Unmanufactured.	Manufactured.	Old platinum.
1880			\$600
1881			4,222
1882		\$19,244	
1883	\$6,250	21,600	
1884		18,587	1,130
1885			7,000
1886		4,048	2,000
1887		2,200	17,500
1888			
1889			36,835
1890			14,500

COAL.

BY E. W. PARKER.

INTRODUCTION.

The present chapter on the coal production of the United States covers the calendar years 1889 and 1890. The statistics for 1889 were collected by the Census Office and those for 1890 have been compiled mainly from direct returns from operators. The section on anthracite coal has been prepared by Mr. John H. Jones, statistician of the Pennsylvania anthracite coal companies. The material for the Rocky Mountain section was collected by Mr. Frederick F. Chisolm, special agent at Denver, Colorado. The report on the product from Illinois is from that of Col. J. S. Lord, secretary of the bureau of labor statistics of the State of Illinois, while acknowledgments are due to Mr. Albert S. Bolles, chief of the bureau of industrial statistics of Pennsylvania, for valuable information obtained from his report on bituminous coal in that State. The data for the reports of all the bituminous coal-producing States have been collected by correspondence with individual operators. This method of conducting the investigation was rendered practicable by the work of the Census Office, through which a very complete directory of coal producers throughout the United States was obtained. Replies to the inquiries sent out from this office have been received from nearly all those addressed, leaving only a very small percentage of output on which it was necessary to make an estimate. It is believed that the present investigation has resulted in a more accurate statement of the coal product than has hitherto been possible, as no opportunity has been afforded in the compilation of previous volumes of Mineral Resources to obtain direct reports from all the mines. In the report for 1890 no attempt has been made to obtain the statistics from country banks where the output is used entirely for local consumption, an estimate of this small factor being all that was possible. The investigation has been limited to mines which are known as commercial properties. The output from small banks in 1889 was 2,889,286 short tons, or a little more than 2 per cent. of the total product.

THE COAL FIELDS OF THE UNITED STATES.

For convenience of description, the coal areas of the United States have been grouped into the Anthracite division and the Bituminous division.

The Anthracite division, in a commercial sense, may be said to in-

clude the anthracite districts of Pennsylvania alone, although small amounts of anthracite are mined in Colorado, Arkansas, and New Mexico. In the New England basin the original coal beds have been metamorphosed into graphite and graphitic coal, which have special uses, although not classified by the coal trade as anthracite.

The Bituminous division includes the following coal fields: (1) The Triassic field, embracing the coal beds of the Triassic or New Red sandstone formation in the Richmond basin in Virginia, and in the coal basins along the Deep and Dan rivers in North Carolina; (2) the Appalachian field, which extends from the State of New York on the north to the State of Alabama on the south, having a length northeast and southwest of over 900 miles and a width ranging from 30 to 180 miles; (3) the Northern field, which is confined exclusively to the central part of Michigan; (4) the Central field, embracing the coal areas in Indiana, Illinois, and western Kentucky; (5) the Western field, including the coal areas west of the Mississippi river, south of the forty-third parallel of north latitude and east of the Rocky mountains; (6) the Rocky mountain field, containing the coal areas in the States and Territories lying along the Rocky mountains; (7) the Pacific coast field, embracing the coal districts of Washington, Oregon, and California. (See Mineral Resources of the United States, 1886, for detailed descriptions.)

The following table contains the approximate areas of these coal fields, with the total product of each during 1887, 1888, 1889, and 1890:

Classification of the coal fields of the United States.

	Area.	Product in 1887.	Product in 1888.	Product in 1889.	Product in 1890.
<i>Anthracite.</i>					
New England (Rhode Island and Massachusetts)	<i>Sq. miles.</i> 500	<i>Short tons.</i> 6, 000	<i>Short tons.</i> 4, 000	<i>Short tons.</i> 2, 000
Pennsylvania	470	39, 506, 255	43, 922, 897	45, 544, 970	46, 468, 641
Colorado and New Mexico ..	15	36, 000	44, 791	53, 517	(b)
	985	39, 548, 255	43, 971, 688	45, 600, 487	46, 468, 641
<i>Bituminous (a).</i>					
<i>Triassic:</i>					
Virginia	180	30, 000	33, 000	49, 411	19, 346
North Carolina	2, 700	222	10, 262
<i>Appalachian:</i>					
Pennsylvania	9, 000	30, 886, 602	30, 796, 727	36, 174, 059	42, 302, 173
Ohio	10, 000	10, 301, 708	10, 910, 946	9, 976, 787	11, 494, 506
Maryland	550	3, 278, 023	3, 479, 470	2, 939, 715	3, 357, 813
Virginia	2, 000	795, 263	1, 040, 000	816, 375	764, 665
West Virginia	16, 000	4, 836, 820	5, 498, 800	6, 231, 880	7, 394, 494
Kentucky	10, 000	950, 903	1, 193, 000	1, 108, 770	1, 206, 120
Tennessee	5, 100	1, 900, 000	1, 967, 297	1, 925, 689	2, 169, 585
Georgia	200	313, 715	180, 000	225, 934	228, 337
Alabama	8, 660	1, 950, 000	2, 900, 000	3, 572, 963	4, 090, 409
	64, 395	55, 193, 034	60, 966, 240	62, 972, 222	73, 008, 102
<i>Northern:</i>					
Michigan	6, 700	71, 461	81, 407	67, 431	74, 977
<i>Central:</i>					
Indiana	6, 450	3, 217, 711	3, 140, 979	2, 845, 057	3, 305, 737
Kentucky	4, 000	982, 282	1, 577, 000	1, 290, 985	1, 495, 376
Illinois	36, 800	10, 278, 890	14, 655, 183	12, 104, 272	15, 292, 420
	47, 250	14, 478, 883	19, 173, 167	16, 240, 314	20, 093, 533

a Including lignite, brown coal, and scattering lots of anthracite.

b Included in bituminous product.

Classification of the coal fields of the United States—Continued.

	Area.	Product in 1887.	Product in 1888.	Product in 1889.	Product in 1890.
<i>Bituminous—Continued.</i>					
Western:	<i>Sq. miles.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Iowa	18,000	4,473,828	4,952,440	4,045,358	4,021,739
Missouri	26,700	3,209,916	3,909,967	2,557,823	2,735,221
Nebraska	3,200	1,500	1,500	} 2,222,443	2,259,922
Kansas	17,000	1,596,879	1,850,000		
Arkansas	9,100	150,000	276,871	279,584	399,888
Indian Territory	20,000	685,911	761,986	752,832	869,229
Texas	4,500	75,000	90,000	128,216	184,440
	98,700	10,193,034	11,842,764	10,036,256	10,470,439
Rocky Mountains, etc.:					
Dakota		21,470	34,000	28,907	30,000
Montana		10,202	41,467	363,301	517,477
Idaho		500	400		
Wyoming		1,170,318	1,481,540	1,388,947	1,870,366
Utah		180,021	258,961	236,651	318,159
Colorado		1,755,735	2,140,686	2,544,144	3,094,003
New Mexico		508,034	626,665	486,463	375,777
		3,646,280	4,583,719	5,048,413	6,205,782
Pacific coast:					
Washington		772,612	1,215,750	1,030,578	1,263,689
Oregon		31,696	75,000	64,359	61,514
California		50,000	95,000	119,820	110,711
		854,308	1,385,750	1,214,757	1,435,914
Total product sold ...		124,015,255	142,037,735		
Colliery consumption		5,960,303	6,621,667		
Total product, includ- ing colliery con- sumption		129,975,557	148,659,402	141,229,513	157,788,656

PRODUCT.

The total product of all kinds of coal in 1889, including colliery consumption, was, according to the census report, 141,229,513 short tons, (decrease from 1888 of 7,429,889 short tons), valued at \$160,226,323 (decrease \$51,292,404). In 1890 the product increased to 157,788,656 short tons, valued at \$176,804,573. The increase in tonnage in 1890 over that of 1889 was 16,559,143 short tons, and in value of \$16,578,250. The product of Pennsylvania anthracite in 1889 was 40,665,152 long tons, or 45,544,970 short tons, valued at \$65,721,578 (a decrease from 1888 of 959,459 long tons, or 1,074,594 short tons). In 1890 the product was 41,489,858 long tons, or 46,468,641 short tons (increase over 1889, 824,706 long tons, or 923,671 short tons), valued at \$66,383,772 (increase, \$662,184). The product of all other coals, including bituminous, semi-bituminous, brown, and lignite, and Arkansas and Colorado anthracite, in 1889, was 95,684,543 short tons, valued at \$94,504,745, and in 1890, 111,320,015 short tons, valued at \$110,420,801.

The colliery consumption varies considerably, according to the nature of the mines. The total amount so used in 1889 was reported to be 5,382,265 short tons, and in 1890, 4,457,456 short tons. The largest average consumption is reported from the anthracite mines of Pennsyl-

vania, and the smallest average in the bituminous region of the same State.

The total number of persons employed in and about the coal mines in 1889 was 299,559, and in 1890, 318,204. These figures include superintendents, mechanics, and clerical force at the mines, as well as miners, laborers, and others engaged in the actual working of the mines.

The total product, including colliery consumption, of each State and Territory during 1889 and 1890, with corresponding values, are shown in the following tables:

Product of coal in the United States in 1889, by States and Territories.

States and Territories.	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.	Total product of coal of all grades for year 1889.	Total amount received for coal sold in 1889.
<i>Bituminous.</i>							
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Alabama	2,327,209	38,835	21,110	79,515	1,106,314	3,572,983	\$3,961,491
Arkansas	268,518	5,020	1,800	4,246	-----	279,584	395,836
California and Oregon	173,611	3,854	608	6,106	-----	184,179	434,382
Colorado	2,059,848	70,595	18,453	87,187	308,061	2,544,144	3,843,992
Georgia and North Carolina	46,321	31	158	15,001	164,645	226,156	339,382
Illinois	9,884,883	1,699,478	111,224	395,787	12,900	12,104,272	11,755,203
Indiana	2,527,112	217,041	20,894	67,210	12,800	2,845,057	2,887,852
Indian Territory	699,122	1,173	5,922	33,997	12,618	752,832	1,323,807
Iowa	3,530,373	420,596	44,139	100,213	37	4,095,358	5,426,509
Kansas and Nebraska	1,891,000	267,047	34,560	29,246	500	2,222,443	3,301,788
Kentucky	2,111,010	225,234	21,072	23,981	18,458	2,399,755	2,374,339
Maryland	2,885,336	37,667	6,550	10,162	-----	2,939,715	2,517,474
Michigan	53,104	8,289	821	5,217	-----	67,431	115,011
Missouri	2,246,845	259,587	16,412	34,979	-----	2,557,823	3,479,057
Montana	314,372	10,755	2,162	5,436	30,576	363,301	880,773
New Mexico	466,127	5,371	2,582	6,383	6,000	486,463	870,468
North Dakota	18,610	9,792	505	-----	-----	28,907	41,431
Ohio	8,566,223	1,196,872	50,271	93,952	69,469	9,976,787	9,355,400
Pennsylvania	24,059,913	1,432,361	158,290	332,937	10,190,588	36,174,089	27,953,315
Tennessee	1,334,424	13,212	15,889	23,034	539,130	1,925,689	2,338,309
Texas	120,602	6,348	204	1,062	-----	128,216	340,620
Utah	216,969	15,050	2,012	412	2,217	236,651	377,456
Virginia	732,881	7,546	5,633	7,516	112,210	865,786	804,475
Washington	956,046	11,036	4,538	19,958	39,000	1,030,578	2,393,238
West Virginia	4,764,900	448,527	44,760	37,368	936,325	6,231,880	5,086,584
Wyoming	1,354,443	7,330	8,103	19,071	-----	1,388,947	1,748,617
Total	73,609,883	6,418,647	598,672	1,439,976	13,561,848	95,629,026	94,346,809
<i>Anthracite.</i>							
Pennsylvania	40,114,901	1,163,539	325,591	3,940,939	-----	45,544,970	65,721,578
Colorado and New Mexico	49,917	350	1,900	1,350	-----	53,517	151,936
Rhode Island	2,000	-----	-----	-----	-----	2,000	6,000
Total	40,166,818	1,163,889	327,491	3,942,289	-----	45,600,487	65,879,514
Grand total	113,776,701	7,582,536	926,163	5,382,265	13,561,848	141,229,513	160,226,323

Coal product of the United States in 1890, by States.

States.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.			
Pennsylvania, anthracite.....	41,011,087	2,000,891	3,456,663	46,468,641	\$66,383,772	200	126,000
Bituminous:								
Alabama.....	2,487,983	84,578	88,952	1,428,896	4,000,409	4,202,469	217	10,612
Arkansas.....	374,969	9,240	15,679	399,888	514,595	214	938
California.....	103,436	2,121	5,154	110,711	283,019	301	364
Colorado.....	2,636,939	65,432	48,451	343,181	3,094,003	4,344,196	220	5,827
Georgia.....	57,949	170,388	228,337	238,315	313	425
Illinois.....	12,539,784	2,130,539	606,497	15,600	15,292,420	14,171,230	204	28,574
Indiana.....	3,036,737	225,167	34,703	9,130	3,305,737	3,259,233	220	5,489
Indian Territory.....	828,102	6,211	11,292	23,624	869,229	1,579,188	238	2,571
Iowa.....	3,560,738	397,503	63,498	4,021,739	4,995,739	213	8,130
Kansas.....	2,028,100	224,839	6,983	2,259,922	2,947,517	210	4,523
Kentucky.....	2,357,989	291,666	29,568	22,273	2,701,496	2,472,119	219	5,259
Maryland.....	3,296,393	52,621	8,799	3,357,813	2,899,572	244	3,842
Michigan.....	57,100	12,885	4,992	74,977	149,195	229	180
Missouri.....	2,449,305	240,227	45,679	2,735,221	3,382,858	229	5,971
Montana.....	466,016	23,427	4,034	24,000	517,477	1,252,492	218	1,251
Nebraska.....	1,500	1,500	4,500
New Mexico.....	358,332	11,360	6,083	375,777	504,390	192	827
North Carolina.....	9,262	100	900	10,262	17,864	200	80
North Dakota.....	30,000	30,000	42,000
Ohio.....	10,161,887	1,164,876	143,984	23,759	11,494,506	10,783,171	201	20,576
Oregon.....	58,821	1,936	757	61,514	177,875	305	208
Pennsylvania, bituminous.....	29,288,923	1,473,317	395,837	11,144,096	42,302,173	35,376,916	232	61,333
Tennessee.....	1,482,357	41,932	23,583	621,713	2,169,585	2,395,746	263	5,082
Texas.....	180,800	1,840	1,800	184,440	465,900	241	674
Utah.....	279,336	13,749	1,015	24,059	318,159	552,390	239	429
Virginia.....	608,641	17,002	4,908	153,460	784,011	589,925	296	1,293
Washington.....	1,212,621	17,249	17,019	16,800	1,263,689	3,426,590	270	2,206
West Virginia.....	5,614,752	438,527	30,594	1,310,781	7,394,654	6,208,128	227	12,236
Wyoming.....	1,835,299	28,540	6,527	1,870,366	3,183,669	246	3,272
Total.....	128,383,658	9,009,285	5,063,953	15,331,760	157,788,656	176,804,573	216	318,204

IMPORTS AND EXPORTS.

The following tables have been compiled from official returns to the Bureau of Statistics of the Treasury Department and show the imports and exports of coal from 1867 to 1890 inclusive. The values given in both cases are considerably higher than the average "spot" rates by which the values of the domestic production have been computed.

The tariff from 1824 to 1843 was 6 cents per bushel, or \$1.68 per long ton; from 1843 to 1846, \$1.75 per ton; 1846, 30 per cent. ad valorem; 1847 to 1861, 24 per cent. ad valorem; 1862 to 1864, \$1 per ton; 1865, \$1.10 per ton; 1866 to 1872, \$1.25 per ton; since August, 1872, 75 cents per ton. During the period from June, 1854, to March, 1866, the reciprocity treaty was in force, and coal from the British possessions in North America was admitted into the United States duty free.

The exports consist both of anthracite and bituminous coal, the amount of anthracite being the greater. They are made principally by rail over the international bridges and by lake and sea to the Canadian provinces. Exports are also made by sea to the West Indies, to Central and South America, and elsewhere.

The imports are principally from Australia and British Columbia to

San Francisco, from Great Britain to the Atlantic and Pacific coasts, and from Nova Scotia to Atlantic coast points.

Coal imported and entered for consumption in the United States, 1867 to 1890.

Calendar years ending December 31 from 1886 to 1890; previous years end June 30.	Anthracite.		Bituminous and shale.	
	Quantity.	Value.	Quantity.	Value.
	<i>Long tons.</i>		<i>Long tons.</i>	
1867.....			509,802	\$1,412,597
1868.....			394,021	1,250,513
1869.....			437,228	1,222,119
1870.....			415,729	1,105,905
1871.....	973	\$4,177	430,508	1,121,914
1872.....	390	1,322	485,063	1,279,686
1873.....	2,221	10,764	460,028	1,548,208
1874.....	471	3,224	492,063	1,937,274
1875.....	138	963	436,714	1,791,601
1876.....	1,428	8,560	400,632	1,592,846
1877.....	630	2,220	495,816	1,782,941
1878.....	158	518	572,846	1,929,660
1879.....	488	721	486,501	1,716,209
1880.....	8	40	471,818	1,588,312
1881.....	1,207	2,628	652,963	1,988,199
1882.....	36	148	795,722	2,141,373
1883.....	507	1,172	645,924	2,013,555
1884.....	1,448	4,404	748,995	2,494,228
1885.....	4,976	15,848	768,477	2,548,432
1886.....	2,039	4,920	811,657	2,501,153
1887.....	14,181	42,983	819,242	2,609,311
1888.....	24,093	68,710	1,085,647	3,728,060
1889.....	20,652	117,434	1,001,374	3,425,347
1890.....	15,145	46,695	819,971	2,822,216

Coal of domestic production exported from the United States, 1867 to 1890.

Calendar years ending December 31 from 1886 to 1890; previous years end June 30.	Anthracite.		Bituminous and shale.	
	Quantity.	Value.	Quantity.	Value.
	<i>Long tons.</i>		<i>Long tons.</i>	
1867.....	192,912	\$1,333,457	92,189	\$512,742
1868.....	192,291	1,082,745	86,367	433,475
1869.....	283,783	1,553,115		
1870.....	121,098	803,135	106,820	503,223
1871.....	134,571	805,169	133,380	564,067
1872.....	259,567	1,375,342	141,311	586,264
1873.....	342,180	1,827,822	242,453	1,086,253
1874.....	401,912	2,236,084	361,490	1,587,666
1875.....	316,157	1,791,626	203,189	828,943
1876.....	337,934	1,869,434	230,144	850,711
1877.....	418,791	1,891,351	321,665	1,024,711
1878.....	319,477	1,006,843	340,661	1,352,624
1879.....	386,916	1,427,886	276,000	891,512
1880.....	392,626	1,362,901	222,634	695,179
1881.....	462,208	2,091,928	191,038	739,532
1882.....	553,742	2,589,887	314,320	1,102,898
1883.....	557,813	2,648,033	463,051	1,593,214
1884.....	649,040	3,053,550	646,265	1,977,959
1885.....	588,461	2,586,421	683,481	1,989,541
1886.....	667,076	2,718,143	544,768	1,440,631
1887.....	825,486	3,469,166	706,364	2,001,966
1888.....	969,542	4,325,126	860,462	2,529,472
1889.....	857,633	3,636,347	935,151	2,783,592
1890.....	794,335	3,272,697	1,280,930	4,004,995

COAL TRADE REVIEW.

Including the coal sold to local trade (*i. e.*, the portion of the product sold without shipment by rail or water), the amount made into coke, and that used at the mines for steam and heat, the total production for 1889 was 7,429,889 short tons less than that of 1888. The decrease in value

was \$51,292,404. The mild winter of 1889-'90 is a satisfactory reason for this decided decrease, though it is quite evident that the product for 1888 was over-estimated. The slackened demand during the season caused a drop in prices still more pronounced than the decrease in tonnage. Heavy stocks, accumulated during the impetus given to trade by the activity in 1888, had to be moved, and prices fell accordingly. The depression of 1889 was followed by a heavier production in 1890. The product increased 16,559,143 short tons, and the value, \$16,578,250.

The spot value of anthracite coal, inclusive of colliery consumption, in 1888 was estimated at \$1.95 per ton, which was 6 cents lower than the average price during 1887. The average price in 1889 was \$1.77, or 18 cents less than that of 1888. The average price in 1890 was \$1.78 per ton.

The condition of the market during 1890 may be seen from the following review, made up partly from market reports to the various trade journals, but more particularly from Mr. Frederic E. Seward's annual report, "The Coal Trade."

New York.—The mild winter of 1889-'90 had a particularly depressing effect upon the anthracite trade, and prices were very much at the option of buyers, with the exception of manufacturing sizes, which were in demand. The prices quoted in the early part of 1890 for coal, free on board at New York, were as follows: Stove, \$3.90 to \$4; egg, \$3.70 to \$3.80; chestnut, \$3.65 to \$3.75. Notwithstanding a general reduction in output during February (some collieries shutting down entirely) prices fell off early in the month to \$3.50, free on board, for stove and egg, and \$3.35 for chestnut. Pea and buckwheat were scarce, however, and commanded anywhere from \$2.85 to \$3.10 and \$2.25 to \$2.40. A better tone was given to the market in April and May. The prices on Reading white ash were as follows: Broken egg and stove advancing to \$3.75 and chestnut to \$3.50, free on board, at New York, with pea at \$2.65 and buckwheat at \$1.80 to \$2, though other coals were quoted at \$3.50 for broken stove and egg and \$3.25 for chestnut. The market continued to advance during the summer, operators having materially reduced stocks at the shipping points by reducing production. In September the prices at New York were quoted as follows: Stove, \$4.15; egg, \$3.90; chestnut, \$3.75, and broken, \$3.75. In October the prices advanced still further, being for stove, \$4.30; egg, \$4.05; chestnut, \$3.95; broken, \$3.74, pea; \$2.60 to \$2.75. In November an attempt was made to get another advance of 15 cents per ton on all sizes in anticipation of colder weather and an increasing demand, but the element of competition made itself felt, and this, in connection with the recurrence of mild winter weather, caused another decline in prices, and the year closed with schedules demoralized and actual selling prices ranging about the same as September.

Owing to the large consumption of bituminous coal for manufacturing purposes the industry is not so liable to be affected by the fluctuations

of the thermometer as is the anthracite trade. The year opened with a good demand and operators mining freely, but with trade somewhat hampered by inadequate transportation facilities. A plan for combination of the bituminous coal producers was formulated in 1889, and strenuous efforts were made during the early months of 1890 to perfect a scheme for controlling the market, but the matter fell through, the failure being due in some degree, probably, to the refusal of Norfolk, and Western, and Chesapeake and Ohio operators to enter the combination. The Pocohontas and Hawk's Nest districts were anxious to increase their output and were doubtless afraid that combination would mean restriction.

On March 1 quotations were made as follows: \$2.60, free on board, at Baltimore, Newport News, and Philadelphia, and \$3.25 in New York harbor. During the late spring and early summer the market was unstable, showing a sympathy with the anthracite trade. Prices were variable without much attention paid to schedules and quotations. A strike was threatened among the miners in the Hocking Valley and Pittsburg districts, but was averted by an agreement to pay an advance of 5 cents in the Hocking Valley district and of 6 cents in the Pittsburg district, the new scale being 70 cents and 79 cents, respectively. This was followed by threatened strikes in Indiana, Illinois, and West Virginia, but the companies succeeded in compromising with the men and averted the strike. Prices became firmer toward the first of June, and these schedule quotations were abided by: \$2.40 to \$2.50 at Baltimore and Newport News, \$2.50 to \$2.60 at Philadelphia, and \$3.25 at New York. A demand made by the Pennsylvania Railroad Company, in June, of \$1 demurrage on each car per day for cars not unloaded at delivery points caused a rapid increase of stocks, but prices remained without material change until about the last of August, when they were quoted as "nominal," and cutting from schedule figures became general. This state of affairs continued until October, when a scarcity of cars caused a diminution of stocks and a stiffening of prices to the schedule rates, which were \$2.40, free on board, at Baltimore, \$2.50 at Philadelphia, and \$3.15 at New York. During November the market improved and an advance of 10 cents was noted at Baltimore and Philadelphia, New York remaining at \$3.15. In December snow blockades and increased demands caused a scarcity at the distributing points, and it was with difficulty that the demand was met. Dealers were obliged to buy from other dealers in order to supply their customers, and prices were high, the closing quotations for the year being \$2.70 at Baltimore, \$2.80 at Philadelphia, and \$3.35 at New York.

Boston, Massachusetts.—The receipts of coal at the port of Boston for a series of years has been as follows:

Receipts of coal at Boston for eight years.

Years.	Anthracite.	Bituminous.	From Cape Breton.	Total.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
1883.....				2,273,068
1884.....				2,225,740
1885.....				2,221,220
1886.....				2,500,000
1887.....				2,400,000
1888.....	2,057,279	1,004,195		3,061,474
1889.....	1,647,348	914,966	5,538	2,567,852
1890.....	1,740,564	964,857	14,072	2,719,493

The amounts here given do not represent the consumption of coal in the city of Boston, as about three-fifths of the coal received at the port is shipped to interior points, but it is not possible to determine the exact quantity.

The hard coal business of Boston and vicinity in 1889 was an unsatisfactory one. The commencement of the year found both wholesale and retail dealers well supplied with coal. The previous year was a very quiet one on account of the warm weather, and as retail dealers had laid in a good supply of coal in anticipation of an average demand, which did not materialize, large stocks were carried over. Notwithstanding the slack demand, however, prices were held up by the producing companies until the summer months, when considerable cutting was done. Trade in bituminous coal, on the other hand, was quite the reverse of the anthracite. Business was brisk, and owing to delays at shipping points and lack of transportation facilities some difficulty was experienced at times in supplying the local demand. The circular price for the year was \$2.60, free on board, and as at times there were threatenings of a famine in bituminous circles the rate was pretty generally maintained.

The beginning of 1890 found the anthracite market well stocked and the first months of the year were about as unsatisfactory as the previous year. In fact, the only really satisfactory trading that was done during the year was in the few weeks of cold weather which prevailed in November and December. Freights during the year were very low, and vessels for transportation rather a drug. This condition of affairs drove many vessels out of the traffic, and naturally a rise in freights resulted toward the close of the year. Freight tariffs in the earlier months of the year had been from New York 50 cents, and from Philadelphia 75 cents. Following the withdrawal of vessels from the trade the rates rose to 75 and 85 cents from New York and to \$1 and over from Philadelphia and Baltimore.

Philadelphia, Pennsylvania.—Lack of competition among the coal transportation companies has made Philadelphia a sufferer. Freights

from the Schuylkill region are but 5 cents per ton less than to New York. From the Lehigh they are the same, and from the Wyoming they are 10 cents higher. The following rates ruled during 1889 and 1890 for coal from the mines to Philadelphia:

Freight rates from coal mines to Philadelphia.

	Anthracite.	Bituminous.
For local use.....	<i>Per ton.</i> 1.70	<i>Per ton.</i> 2.00
For shipment out of Delaware bay.....	1.40	1.50

The wholesale prices for anthracite coal, free on board, at Port Richmond, averaged as follows during the past two years:

Average prices of anthracite coal at Port Richmond in 1889 and 1890.

Kind of coal.	Broken.	Egg.	Stove.	Chestnut.	Pea.
1889.	<i>Per ton.</i>	<i>Per ton.</i>	<i>Per ton.</i>	<i>Per ton.</i>	<i>Per ton.</i>
Hard white ash.....	3.70	3.85	4.05	3.80	2.10
Free-burning white ash.....	3.50	3.75	3.95	3.75	2.10
1890.					
Hard white ash.....	3.65	3.90	4.05	3.70	2.25
Free-burning white ash.....	3.50	3.75	4.05	3.70	2.25

Director Wagner, on December 27, 1888, awarded contracts for supplying the city with gas coal during the year 1889. The following were the successful bidders. The prices paid for 1888 were \$3.79, \$3.83 and \$3.84.

Contracts for supplying gas coal to Philadelphia in 1889.

Companies.	Tons.	Price per ton.
Manor Gas Coal Co.....	5,000	\$3.81
Penn Gas Coal Co.....	57,720	3.82
Westmoreland Coal Co.....	57,720	3.82
Newburg Orrel Coal and Coke Co.....	15,000	3.76
James Boyce.....	15,000	3.76
Despard Coal Co.....	10,000	3.76
J. & W. Wood.....	10,000	3.76
Chesapeake and Ohio.....	25,000	3.80

For 1890 the coal supplied to the gas works was at \$3.80 per ton, and the bids for the 1891 supply were as follows:

Bids for supplying gas coal to Philadelphia for 1890.

Companies.	Price per ton.
Montana Coal and Coke Co.....	\$3.91
Gaston Coal Co.....	3.91
Despard Coal Co.....	3.91
Chesapeake and Ohio.....	3.94
Manor Gas Coal Co.....	3.98
Westmoreland Coal Co.....	3.99

Freight rates from Philadelphia at the close of 1890.

To—	Rate per ton.	To—	Rate per ton.
Boston and discharge	\$1.15	Providence and discharge	\$0.85
Portsmouth and discharge	1.00	Portland and discharge75
Newburyport and discharge	1.00	Savannah and discharge	1.00
New Bedford and discharge75	New York, alongside90
Lynn and discharge	1.00	Washington, alongside85
Fall River and discharge90	Norfolk70

Baltimore, Maryland.—The coal received at Locust Point for the Baltimore market includes Cumberland, Georges Creek, Myersdale, and the gas coal from the West Virginia mines on the line of the Baltimore and Ohio railroad, and that from the Youghiogheny mines in Pennsylvania on the line of the same road, for local use and for northern shipment, and it is estimated that 200,000 tons were received during 1890. Of anthracite coal received there were something like 250,000 tons by the Susquehanna canal, and other water routes, besides 300,000 tons by the Northern Central railroad.

Rates for anthracite coal in cars, at Baltimore, or via Canton pier at the close of 1890.

	Hard white ash.	Shamokin.	Lykens Valley	Bernice.
Broken.....	\$4.20			\$4.30
Egg.....	4.30	\$4.30	\$4.45	4.30
Stove.....	4.45	4.45	4.70	4.45
Chestnut.....	4.30	4.30	4.35	4.30
Pea.....	3.00	3.00	3.25	
Buckwheat.....				

Bituminous coal was quoted at \$2.60 per long ton free on board at Locust Point or Canton piers. Hampton Roads quotations were the same. The Baltimore and Ohio, Northern Central, and Baltimore and Potomac railroads carried the following to Baltimore:

Coal receipts at Baltimore.

Years.	Via Baltimore and Ohio Railroad.	Via Northern Central Railroad.	Via Baltimore and Potomac Railroad.
	Tons.	Tons.	Tons.
1883	1,618,416	693,494	
1884	2,510,389	767,381	
1885	2,238,097	850,303	
1886	2,313,783	818,863	
1887	2,167,007	765,082	15,338
1888	2,300,000	680,962	10,500
1889	2,000,000	666,972	7,139
1890	2,200,000	700,000	10,000

Foreign shipments of coal from Baltimore.

Years.	Tons.	Years.	Tons.
1883	63,526	1887	54,455
1884	50,289	1888	33,386
1885	71,527	1889	27,500
1886	64,477	1890	30,000

Freight rates for coal from Baltimore at the close of 1890.

To—	Rate per ton.	To—	Rate per ton.
Portland	\$1.00	Bridgeport	\$1.00
Boston	1.15	Providence	1.00
Portsmouth	1.25	Hoboken95
New Haven	1.00	Jersey City85
New York	1.00	New Bedford	1.00

Pittsburg, Pennsylvania.—The following prices were quoted at the close of 1890:

Pittsburg coal prices at the close of 1890.

	Per bushel.
River, on board	<i>Cents.</i>
Railroad	4½ to 5
	5 5½

The fluctuations in the price of Pittsburg coal at Cincinnati, Louisville, and New Orleans during 1889 and 1890 are indicated below:

Prices of Pittsburg coal at Cincinnati, Louisville, and New Orleans. (a)

Months.	Cincinnati.	Louisville.	New Orleans.
1889.			
January	<i>Cts. per bushel.</i> 5 to 6½	<i>Cts. per bushel.</i> 6½ to 7	<i>Cts. per barrel.</i> 27 to 29
March	5 6	6½ 7	27 29
April	5 6	6 7	25 27
September	5 7½	6 7½	25 27
October	6½ 8	6½ 8	25 27
November	5½ 8	5½ 8	24 27
December	5½ 6½	5½ 7	22 24
1890.			
January	5½ 6½	6 7	23 25
April	5 6	5 6	22 24
July	5½ 6½	5½ 6½	22 24
October	5½ 6½	6 6½	24 26
December	5½ 6½	6½ 7	26 28

a Rates at Cincinnati and Louisville are for bushels of 76 pounds; at New Orleans for barrels of 208 pounds.

Coal shipments by Ohio river for eight years.

Years.	Bushels.	Years.	Bushels.
1883	87,995,000	1887	56,743,000
1884	55,432,000	1888	109,572,000
1885	74,964,000	1889	79,578,100
1886	91,664,000	1890	116,302,600

The railroad coal operators report unsatisfactory and unprofitable business for both 1889 and 1890. The product of Allegheny county in 1889 was 858,074 short tons less than in 1888. The value of the product in 1889, according to the Census Office, was \$4,000,104, against which the total expenditures are given at \$3,739,439, leaving a profit of \$261,665. The annual report of the Monongahela Navigation Company

1890 shows the total receipts from coal tonnage to be \$204,000. An expense approximately the same for 1889, deducted from the gross profits above quoted, will enable one to judge how much there was in the business for operators.

Buffalo, New York.—The prices for anthracite coal, free on board, at the close of 1890, were as follows:

Prices for anthracite coal at Buffalo, New York.

Sizes.	Per long ton.	Sizes.	Per long ton.
Stove	4.24	Grate	4.01
Chestnut	4.24	Egg	4.01

The Buffalo Coal Exchange rules say that when coal is sold in the yard the price shall be 40 cents per ton less than delivered figures. Rates to steam yachts and canal boats shall be the same on deck per ton as the regularly established retail quotations. Further, all coal shall be sold at regularly established retail prices, and these prices are for coal delivered only during the month in which the order is taken.

Prices for bituminous coal at Buffalo, New York, on track (nominal).

	Reynolds-ville region.	Allegheny Valley Railroad and Mercer County region.	Pittsburg region.	Low grade division of Allegheny Valley Railroad.
	<i>Short ton.</i>	<i>Short ton.</i>	<i>Short ton.</i>	<i>Short ton.</i>
Screened lump	\$2.45	\$2.25	\$2.60	\$2.25
Lump and nut mixed	2.35	2.15	2.50	2.15
Run of mines	2.20	2.00	2.55	2.00
Screened nut	2.20	2.00	2.00
Nut and slack mixed	2.00	1.80	1.80
Slack	1.70	1.50	1.50
Ohio cannel	4.30
Connellsville coke	3.75
Reynoldsville coke

The close of 1890 found the coal trade of Buffalo in an unsettled and unsatisfactory condition. A general stagnation existed in the local anthracite trade, while bituminous coal was scarce and hard to get from the mines, owing to the operators inability to secure cars to haul it, and the further trouble of snow blockades on the railroads.

The following table exhibits the shipments of anthracite coal from Buffalo for the past eight years:

Lake shipments of anthracite coal from Buffalo.

Years.	Tons.	Years.	Tons.
1883	1,467,778	1887	1,894,060
1884	1,431,081	1888	2,514,906
1885	1,428,086	1889	2,151,670
1886	1,531,210	1890	2,157,810

The principal points to which coal was shipped from Buffalo by lake during the past five years are shown in the following table, together with the tonnage for each year:

Clearances of coal at Buffalo for five years.

Destination.	1886.	1887.	1888.	1889.	1890.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Chicago	642, 135	784, 462	1, 023, 649	988, 750	952, 280
Milwaukee	376, 615	376, 876	549, 831	497, 895	451, 550
Duluth	157, 420	165, 798	282, 106	160, 430	199, 230
Superior	65, 090	96, 746	120, 000	112, 450	127, 300
Toledo	55, 290	84, 563	83, 850	52, 725	96, 230
Gladstone			39, 575	36, 520	30, 215
Racine	25, 263	16, 565	29, 695	33, 410	29, 130
Detroit	31, 090	40, 203	35, 330	31, 890	40, 065
Green Bay	23, 870	29, 446	26, 345	25, 050	22, 380
Other places	156, 439	140, 020	179, 525	142, 216	131, 390
Total	1, 531, 212	1, 734, 479	2, 369, 906	2, 081, 336	2, 079, 770

The following statements regarding the local trade of Buffalo will be found of interest as showing the development of the business since 1842. The figures for years prior to 1886 were compiled by Mr. E. L. Hedstrom, of Buffalo; those for 1886, and subsequent years are furnished by Mr. William Thurston:

Coal receipts at Buffalo for several years.

Years.	Anthracite.	Bituminous.	Blossburg.	Total.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
1842				1, 800
1852				57, 560
1862				239, 873
1872				790, 876
1882				3, 021, 791
1886	2, 673, 778	1, 420, 956	30, 000	4, 124, 734
1887	3, 497, 203	1, 776, 217	25, 000	5, 298, 420
1888	4, 549, 015	1, 892, 823	22, 500	6, 464, 338
1889	4, 338, 570	2, 198, 327	22, 500	6, 559, 397
1890	4, 500, 000	2, 200, 000	22, 500	6, 722, 500

Erie, Pennsylvania.—The shipments of coal from the city of Erie, Pennsylvania, during the past six years are reported as follows:

Coal shipments from Erie, Pennsylvania.

Years.	Tons.	Years.	Tons.
1883	204, 755	1887	230, 845
1884	193, 969	1888	215, 000
1885	188, 860	1889	300, 000
1886	235, 255	1890	498, 958

Cleveland, Ohio.—The prices of anthracite and bituminous coals at the close of 1889 and 1890 were as follows:

Price of coal at Cleveland, Ohio.

Kinds of coal.	1889.	1890.	Kinds of coal.	1889.	1890.
Bituminous:	<i>Per ton.</i>	<i>Per ton.</i>	Bituminous—continued:	<i>Per ton.</i>	<i>Per ton.</i>
Massillon	\$2.40	\$2.40	Coshocton	\$2.00	\$2.20
Palmyra	2.75	2.75	Hocking	1.90	2.00
Pittsburg	2.10	2.10	Anthracite:		
Salineville	1.70	1.70	Grate	4.53	5.00
Kentucky cannel	4.90	4.50	Egg	4.53	5.25
Gosheu	1.90	1.75	Stove	4.78	5.25
Sherodsville	1.70	1.75	Chestnut	4.78	5.25
Osnaburg	1.80	1.85			

Coal and coke receipts and shipments at Cleveland, Ohio, for the past five years.

	1886.	1887.	1888.	1889.	1890.
Receipts:	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Bituminous	1,412,535	1,454,744	1,737,781	1,600,000	1,560,208
Anthracite	144,826	176,769	181,551	160,000	205,856
Coke	117,372	114,924	124,827	150,000	194,527
Total	1,674,733	1,746,437	2,044,159	1,910,000	1,960,591
Shipments:					
Anthracite by rail	20,000	20,296	29,735	25,000	29,056
Bituminous by rail	120,000	294,453	677,733	600,000	785,526
Bituminous by lake	660,000	703,506	1,000,000	1,100,000	1,200,000
Total	740,000	1,018,255	1,707,468	1,725,000	1,814,582

From the Cuyahoga customs district, which embraces Cleveland, Ashtabula, Fairport, and Lorain, the clearances during the past five years have been as follows:

Clearances from the Cuyahoga, Ohio, district for five years.

Years.	Tons.	Years.	Tons.
1886	1,079,784	1889	2,020,996
1887	1,433,035	1890	2,328,663
1888	1,855,200		

Toledo, Ohio.—The receipts of coal of all kinds in 1890 were 3,021,886 tons as against 2,838,314 tons in 1889, and 3,423,785 tons in 1888. Of the amount received in 1890, 133,813 tons, and of the 1889 receipts, 90,282 tons were anthracite, which came by lake.

Receipts of coal at Toledo, Ohio, for five years.

Received by—	1886.	1887.	1888.	1889.	1890.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Wabash Railway.....	12,598	9,634	10,375	7,586	3,620
Lake Shore and Michigan Southern Railroad.	165,382	206,099	101,064	35,693	20,592
Cincinnati, Hamilton and Dayton Railroad..	8,198	11,741	37,831	51,746	25,753
Pennsylvania Company's railroad.....	201,427	330,020	339,750	234,675	214,765
Michigan Central Railroad.....	9,594	13,864	16,504	19,935	3,152
Columbus, Hocking Valley and Toledo Rail- way.....	1,039,200	955,620	1,358,025	923,745	931,717
Toledo, Ann Arbor and North Michigan Rail- way.....	1,910	552	24,700	96	-----
Toledo, St. Louis and Kansas City Railroad..	3,828	-----	1,359	3,287	8,420
Toledo and Ohio Central Railway.....	404,684	590,000	637,000	706,950	826,049
Lake boats (a).....	87,120	117,921	140,963	90,282	133,813
Wheeling and Lake Erie Railway.....	391,086	454,813	755,155	763,055	853,940
Toledo, Columbus and Southern Railway....	15,832	5,446	1,014	1,210	-----
Cincinnati, Jackson and Mackinaw Railroad.	-----	-----	45	54	65
Total.....	2,340,859	2,695,710	3,423,785	2,838,314	3,020,886

a Anthracite.

Chicago, Illinois.—The following statistics exhibit the amount of coal and coke received at, shipped from, and consumed in, Chicago, Illinois, during seven years ending December 31, 1890:

Yearly receipts of coal at Chicago, Illinois.

Kinds of coal.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Anthracite by lake.....	820,002	741,886	768,164	853,158	1,242,044	1,283,811	1,228,358
Anthracite by rail.....	627,806	613,054	616,997	845,386	702,737	408,574	429,926
Eastern bituminous coal by lake.....	243,188	206,817	166,762	123,221	115,862	53,684	40,766
Eastern bituminous coal by rail.....	612,462	790,169	888,771	1,196,324	1,049,372	803,552	780,249
Illinois coal.....	1,467,989	1,287,995	1,175,001	1,375,759	1,809,210	1,797,096	1,801,817
Indiana coal.....	469,079	659,634	732,191	1,154,681	1,169,231	962,544	1,240,085
Coke.....	553,860	558,963	540,204	592,980	643,486	813,645	965,227
Total.....	4,794,386	4,858,518	4,888,090	6,141,509	6,731,942	6,122,906	6,486,428

The shipments, as shown in the following table, comprise coal and coke rebilled from this market or passing beyond Chicago on through billing.

Shipments of coal from Chicago, Illinois, for five years.

	1886.	1887.	1888.	1889.	1890.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Anthracite.....	451,869	559,560	598,707	502,865	576,665
Bituminous coal and coke.....	539,184	1,001,477	872,631	703,743	951,678
Total.....	991,053	1,561,037	1,471,338	1,206,608	1,528,343

The following statement shows for each year the receipts and consumption of anthracite coal at, and shipments from, Chicago since 1884:

Anthracite coal receipts and consumption at Chicago, Illinois, from 1884 to 1890.

Years.	Receipts.				Distribution.			
	On hand in docks and yards Jan. 1.	Jan. 1 to Dec. 31.		Total.	Jan. 1 to Dec. 31.			Total.
		By ves-sel.	By rail.		Ship-ments to the coun-try.	Local consump-tion.	Balance of stock carried over.	
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
1884.....	265, 645	820, 002	627, 806	1, 713, 453	585, 753	803, 411	324, 289	1, 713, 453
1885.....	324, 289	741, 866	613, 054	1, 679, 209	632, 274	823, 417	223, 518	1, 679, 209
1886.....	223, 518	768, 164	616, 997	1, 608, 679	451, 869	1, 038, 751	118, 059	1, 608, 679
1887.....	118, 059	853, 158	845, 386	1, 816, 603	559, 560	1, 079, 443	177, 600	1, 816, 603
1888.....	177, 600	1, 242, 044	702, 737	2, 122, 381	598, 707	1, 062, 315	461, 359	2, 122, 381
1889.....	461, 359	1, 283, 811	408, 574	2, 153, 744	502, 865	1, 206, 520	444, 359	2, 153, 744
1890.....	444, 359	1, 228, 358	429, 926	2, 102, 643	576, 665	1, 025, 978	500, 000	2, 102, 643

A review of the market conditions of 1889 shows that the anthracite trade was handicapped in the beginning by the largest stocks on hand ever known. In January the trade was practically lifeless, and, with the exception of a spurt or two occasioned by colder weather, this condition prevailed during the remainder of the winter and early spring. A more hopeful tone was apparent during April and May, but little actual improvement took place. The only real change for the better that occurred throughout the year was during the months of September, October, and November, which was followed by disappointment in December, the demand falling flat and the year closing with as unsatisfactory a record as has been known in the history of the trade.

Notwithstanding strikes among the miners in both Illinois and Indiana, prices of bituminous coal were reduced in January and continued to decline during the summer, but advanced again in the fall with trade active. During the prevalence of the strikes in some of the larger districts of Illinois and Indiana, which shut off a large source of Chicago's coal supply, the trade felt no particular inconvenience for the reason that other districts in the same States made up the loss, and shipments from other States, with the exception of West Virginia, instead of increasing during the mine troubles showed a decrease from former years.

The business of 1890, in both anthracite and bituminous circles, while not particularly profitable, was much more satisfactory than that of 1889. A general strike throughout the bituminous regions from the Alleghenies to the Mississippi was threatened during the spring, but after many conventions of operators and operatives the troubles were adjusted and a repetition of the disastrous difficulties of 1889 was averted. The districts of Indiana which suffered from the previous strike recovered the ground lost and shipped large quantities of coal.

The following statement shows the prices of different coals at Chicago at the close of 1890:

Prices of coal and coke at Chicago, Illinois, at the close of 1890.

Kinds of coal.	Per short ton.	Kinds of coal.	Per short ton.
Winifred, West Virginia.....	\$3. 75	Pana.....	\$2. 00
Raymond, West Virginia.....	3. 75	Streator.....	2. 00
Plymouth, West Virginia.....	3. 75	Girard.....	1. 90
Pittsburg.....	3. 30	Wilmington.....	2. 10
Youghiogheny.....	3. 40	Springfield.....	2. 00
Hocking Valley.....	3. 30	Decatur Erie big vein.....	2. 15
Shawnee.....	3. 30	Colfax lump.....	1. 80
Sunday Creek.....	3. 30	Elk Creek.....	2. 60
Little Muddy.....	2. 60	Chattaroi cannel.....	5. 00
Jackson Hill, Ohio.....	3. 45	Brush Creek cannel.....	4. 25
Brazil block.....	2. 50	Birdseye cannel.....	5. 00
Norton Creek.....	2. 10	Sonman smithing.....	3. 65
New Pittsburg.....	1. 90	Cumberland smithing.....	3. 75
Clinton.....	1. 90	Blossburg.....	3. 90
Erie and Brier Hill.....	4. 25	CConnellsville coke (foundry).....	5. 20
New Kentucky lump.....	2. 80	CConnellsville coke (crushed).....	5. 40
New Kentucky mine run.....	2. 40	Walston coke.....	5. 20
Mount Olive.....	2. 10		

ANTHRACITE (a).

Lehigh lump.....	\$6. 47	Grate.....	\$5. 50
Stove.....	5. 75	Egg.....	5. 75
Chestnut.....	5. 75		

a Free on board cars in Chicago.

Milwaukee, Wisconsin.—The following are the total receipts of coal at the port of Milwaukee for the season of navigation during 1890:

Coal receipts at Milwaukee in 1890.

	Anthracite.	Bituminous.	Totals.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Northwestern Fuel Co.....	120, 194	46, 757	166, 951
Coxe Brothers & Co.....	72, 771	28, 843	101, 614
H. M. Benjamin.....	89, 519	47, 811	137, 330
R. P. Elmore & Co.....	42, 928	6, 581	49, 509
Pennsylvania Coal Co.....	18, 967	1, 036	20, 003
Corrigan & Co.....	6, 802	3, 954	10, 756
Buell & Pynebon.....		9, 632	9, 632
F. R. Buell & Co.....	34, 563	1, 168	35, 731
The Hadfield Co.....	53, 366	1, 440	54, 806
L. Hencs, jr. & Co.....	10, 968	26, 930	37, 898
Silver Creek Coal Co.....	19, 760	27, 952	47, 712
B. Urigh & Son.....	12, 471	1, 861	14, 332
Gross & Sons.....	13, 400		13, 400
N. A. Nelson.....	7, 545		7, 545
Lehigh and Franklin Coal Co.....	24, 233	49, 268	73, 501
J. H. Pauly.....	9, 683	3, 721	13, 404
Daniel Orth & Son.....	7, 519	528	8, 047
Husse & Raloff.....	4, 578		4, 578
Callaway & Co.....	3, 296		3, 296
Whitnell & Rademaker.....	6, 334		6, 334
Joachim Christensen.....	4, 165		4, 165
John Hannan.....			
Milwaukee Gas Light Co.....		29, 171	29, 171
Kranse & Co., Milwaukee.....		3, 161	3, 161
Milwaukee Coal Co.....	4, 325		4, 325
Illinois Steel Co.....		13, 681	13, 681
Cudahay Brothers.....		4, 319	4, 319
Jupiter Mills.....		604	604
Sandersens' Mill.....		1, 915	1, 915
Schlitz Brewing Co.....		12, 027	12, 027
Miscellaneous.....	5, 905	8, 884	14, 789
	573, 292	331, 244	904, 536
Summary:			
Anthracite.....			573, 292
Bituminous.....			331, 244
Total.....			904, 536

The following tables have been compiled and reported to the Survey by Mr. William J. Langson, secretary of the chamber of commerce:

Receipts of coal at Milwaukee for six years.

	1885.	1886.	1887.	1888.	1889.	1890.
By lake from—	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Buffalo.....	392,003	395,971	461,972	631,263	542,167	510,508
Eric.....	50,915	41,847	61,222	74,610	47,862	46,378
Oswego.....	10,043	1,153	1,348	2,408
Cleveland.....	126,741	91,997	78,259	98,631	89,071	135,413
Ashtabula.....	35,360	11,096	38,881	23,105	48,599	24,671
Black River.....	5,549
Lorain.....	19,452	12,417	11,757	13,533	15,367	15,351
Sandusky.....	19,207	57,412	36,606	19,733	51,816	26,193
Toledo.....	31,875	69,079	14,115	38,452	71,516	59,305
Charlotte.....	19,491	31,744	2,781	14,292	22,526	6,120
Fairport.....	10,517	30,253	5,552	11,100
Ogdensburg.....	7,700	4,953	7,026
Huron, Ohio.....	8,244	7,726	9,720
Other ports.....	2,679	4,331	588	a 49,375
Total by lake.....	710,736	714,242	724,594	961,164	907,743	903,658
By railroad.....	65,014	45,439	118,385	161,079	72,935	92,999
Total receipts.....	775,750	759,681	842,979	1,122,243	980,678	996,657

a Including cargoes from all ports not reported at the custom-house.

Shipments of coal from Milwaukee for the past eight years.

Shipped by—	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
Chicago, Milwaukee and St. Paul Railway.....	<i>Tons.</i> 146,295	<i>Tons.</i> 140,630	<i>Tons.</i> 179,883	<i>Tons.</i> 177,286	<i>Tons.</i> 166,120	<i>Tons.</i> 283,269	<i>Tons.</i> 258,281	<i>Tons.</i> 378,090
Chicago and Northwestern Railway.....	41,746	37,314	56,591	70,420	79,258	107,193	97,207	103,279
Wisconsin Central Railroad.....	6,725	7,469	8,943	11,745	18,953	12,624	11,727	15,929
Milwaukee, Lake Shore and Western Railway.....	30,575	11,757	12,804	13,072	13,886	16,146	25,413	5,884
Milwaukee and Northern Railroad.....	10,075	7,556	10,872	12,011	15,627	34,480	20,556	19,386
Lake.....	355	335	184	269	1,595	125	224	59
Totals.....	235,771	205,061	269,277	284,803	295,439	453,837	413,408	522,618

Receipts of coal at Milwaukee, by lake and rail annually, for twenty-nine years, from 1862 to 1890, inclusive.

Years.	Tons.	Years.	Tons.
1862.....	21,860	1877.....	264,784
1863.....	43,215	1878.....	239,667
1864.....	44,503	1879.....	350,840
1865.....	36,369	1880.....	368,568
1866.....	66,616	1881.....	550,027
1867.....	74,568	1882.....	593,842
1868.....	92,992	1883.....	612,584
1869.....	87,690	1884.....	704,166
1870.....	122,865	1885.....	775,750
1871.....	175,526	1886.....	759,681
1872.....	210,194	1887.....	842,979
1873.....	229,784	1888.....	1,122,243
1874.....	177,655	1889.....	980,678
1875.....	228,674	1890.....	996,657
1876.....	188,444		

Duluth, Minnesota, and Superior, Wisconsin.—A marked spirit of rivalry exists between these cities, and it is somewhat difficult to get at the exact facts regarding business done at both places. During 1889 Superior increased its facilities by the addition of the Eastern Minnesota coal dock; and Duluth by the opening of the Wilmar and Sioux Falls road, was able to ship through to Iowa and South Dakota. In addition to this the railroads reaching points covered by Chicago and Milwaukee dealers made rates from Duluth which enabled that city to compete with the others for the lake coal trade. In spite of these favorable conditions, however, the aggregate receipts of coal at the two cities were 330,000 tons less than in 1888. But in the following year the benefits became evident, for the receipts increased 575,995 tons over 1889, and 245,995 tons over the best previous year, 1888.

It is interesting to note the development of the coal trade at the head of the lakes (1889 being the only exception to the steady increase of business), and the following figures give total receipts in tons each season for the past ten years. Every settler on the prairies of the Northwest makes a new customer for Duluth coal, and the increased traffic is evidence of the great development going on.

Coal receipts at Duluth, Minnesota.

Years.	Tons.	Years.	Tons.
1878	31,000	1886	736,000
1881	163,000	1887	912,000
1882	260,000	1888	1,535,000
1883	420,000	1889	1,205,000
1885	595,000	1890	1,780,995

St. Paul and Minneapolis, Minnesota.—Wholesale prices for coal were as follows in December, 1890:

Prices of coal at St. Paul and Minneapolis, Minnesota, in December, 1890.

	Free on board cars at Duluth.	To dealers at St. Paul and Minneapolis.
Anthracite:		
Grate	\$5.00 to \$5.50	\$6.75
Egg, stove, and nut	5.25 to 5.75	7.00
Pea	3.75 to 4.00	5.25
Bituminous:		
Pittsburg	3.75	4.75
Youghiogheny	3.75	4.75
Kincaid	3.50	4.50
Mansfield	3.75	4.75
Hocking	3.50	4.50
Wheeling Creek	3.50	4.50
Briar Hill	4.25	5.25
Smithing:		
Cumberland	4.25	5.25
Blossburg	4.25	5.25

Cincinnati, Ohio.—Col. S. D. Maxwell, superintendent of the Cincinnati Chamber of Commerce, in his annual report states that the coal trade of the city for 1889 and 1890 was generally unfavorable. The warm weather which prevailed throughout the winter of both years reduced local consumption, and the market was tormented during nearly the whole of the time by supplies in excess of demand. Col. Maxwell reports the following receipts of coal at Cincinnati for ten fiscal years ending August 31:

Coal receipts at Cincinnati, Ohio.

Years.	Tons.	Years.	Tons.
1881	1,492,817	1886	2,130,354
1882	2,197,407	1887	2,350,026
1883	2,025,859	1888	2,551,415
1884	2,092,551	1889	2,348,055
1885	2,008,850	1890	2,452,253

Prices of coal at Cincinnati, Ohio, at the close of 1890.

Anthracite coal.	Free on board car.	Delivered.	Bituminous coal.	Free on board car.	Afloat, per bushel.
	<i>Short tons.</i>	<i>Short tons.</i>		<i>Short tons.</i>	<i>Cents.</i>
Chestnut	\$5.75	\$6.50	Youghiogheny ...	\$2.25	6¼ to 7¼
Stove	5.75	6.50	Kanawha River...	2.25	6 to 6½
Grate	5.50	6.50	Nut and slack ...	1.40	4
Egg	5.50	6.50			

Louisville, Kentucky.—The following table shows the consumption of coal in the vicinity of Louisville during the past six years. The figures do not include coal used by railroads. The receipts of coke are partly estimated on account of incomplete returns.

Consumption of coal in the vicinity of Louisville, Kentucky, for six years.

	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>	<i>Tons.</i>
Pittsburg by river	539,628	575,000	646,000	750,000	800,000	640,000
Ohio and Kanawha rivers ..	86,348	90,000	72,800	95,000	100,000	120,000
Total coal by river ...	625,976	665,000	718,800	845,000	900,000	760,000
Bituminous by rail	305,960	200,671	232,107	341,427	298,118	304,399
Anthracite	9,300	4,341	4,241	13,377	6,740	2,846
Coke	40,306	50,000	49,688	65,000	50,000	50,000
Aggregate	981,542	920,012	1,004,836	1,264,804	1,254,858	1,117,245

Saint Louis, Missouri.—The following prices were quoted free board, East Saint Louis, at the close of 1890:

Prices of coal at Saint Louis, Missouri, at the close of 1890.

Bituminous.		Per short ton.
Big Muddy		\$1. 87½
Vulcan and Superior.....		1. 87½
Trenton		1. 62½
Brookside.....		1. 50
Troy and St. Barnard		1. 37½
Standard, Illinois		1. 18½
Piedmont, smithing.....		4. 10
Blossburg, smithing.....		3. 95
CConnellsville coke.....		5. 55
Anthracite (a).		Per long ton.
Large egg, for 2½ tons and upward		\$7. 50
Egg, stove and nut, for 2½ tons and upward.....		7. 75

a Retail, delivered in St. Louis.

The receipts of anthracite and bituminous coal and of coke for 1889 and 1890 are shown in the following table, together with the receipts for the three previous years. They show that the receipts of bituminous coal decreased 448,711 tons, or 19 per cent. in 1889, and that anthracite receipts fell off 14,760 tons, or about 11 per cent., from either of which there was only a slight recovery in 1890. The receipts of coke increased each year, but in neither reached the same amount quoted for 1887.

Receipts of coal at Saint Louis, Missouri, in 1886, 1887, 1888, 1889, and 1890.

Years.	Bituminous coal.	Anthracite coal.	Coke.
	Tons.	Tons.	Tons.
1886	2,082,019	96,640	104,036
1887	2,321,814	131,600	175,550
1888	2,357,938	136,290	134,660
1889	1,909,227	121,530	147,750
1890	1,915,960	124,335	162,940

Kansas City, Missouri.—Quotations for short tons on the cars, delivered here, were as follows:

Prices of coal at Kansas City, Missouri, at the close of 1890.

	Per ton.		Per ton.
Bituminous:		Bituminous—Continued.	
Farmers' lump	\$2. 50	Foster lump.....	\$2. 25
Weir City nut	2. 00	Wellington.....	2. 40
Oakdale nut	2. 50	Semi-anthracite.....	4. 50
Rich Hill nut	1. 75	Anthracite:	
Higginsville lump.....	2. 30	Nut size	8. 75
Clinton lump.....	2. 25	Egg size	8. 50
Deepwater lump	2. 25	Stove size	8. 75
Cannel	4. 75	Grate size.....	8. 50
Illinois	2. 50-3. 00	Smithing coal:	
Vernon.....	2. 37½	Piedmont	6. 25
Weir City lump.....	2. 50	Blossburg	6. 25
Oakdale lump	2. 50	Coke:	
Rich Hill lump.....	2. 37½	Gas house.....	4. 50
Lexington lump.....	2. 40	Native.....	4. 00
Excelsior lump.....	2. 50	CConnellsville.....	7. 00

The receipts and shipments for the last six years have been as follows:

Coal receipts and shipments at Kansas City for six years.

	Receipts.	Shipments.		Receipts.	Shipments.
	<i>Tons.</i>	<i>Tons.</i>		<i>Tons.</i>	<i>Tons.</i>
1885.....	533,262	199,476	1888.....	935,735	174,197
1886.....	562,540	160,233	1889.....	1,260,816	269,281
1887.....	752,354	134,559	1890.....	1,149,253	385,000

Mobile, Alabama.—With the exception of a small amount of anthracite, all of the coal received at Mobile comes from the Alabama mines, but high freight rates from the mines have as yet prevented the port becoming of much importance as a shipping point. Government improvements now being made in the Warrior and Coosa rivers are expected to make direct water routes to the mines, and effect a material reduction in freight rates. If these hopes are realized coal will be put down in Mobile at \$1 per ton less than at present; that is, from \$3 to \$2 per ton. Coal business is reported as having been in an unsatisfactory condition for three years. In December, 1890, when there was a better demand for coal than at any time during the period mentioned, the Alabama miners went out on a strike, and coal became very scarce.

Following will be found the amounts of coal received at Mobile for the past eight years. These figures do not include the coal consumed by the Louisville and Nashville and the Mobile and Ohio railroads, which amounts to about 25,000 tons annually.

Receipts of coal at Mobile, Alabama, for eight years.

Years.	Alabama coal.	Anthracite and English.	Years.	Alabama coal.	Anthracite and English.
1883.....	25,304	1,229	1887.....	39,232	910
1884.....	17,808	891	1888.....	38,785	648
1885.....	40,301	775	1889.....	40,000	500
1886.....	30,310	2,022	1890.....	45,000	500

New Orleans, Louisiana.—A comparative statement of consumption of Pittsburg coal is given below:

Consumption of Pittsburg coal at New Orleans, Louisiana, from 1883 to 1890.

Years.	Barrels.	Years.	Barrels.
1883.....	3,759,250	1887.....	5,100,000
1884.....	3,864,300	1888.....	4,500,000
1885.....	3,995,650	1889.....	4,846,500
1886.....	4,529,000	1890.....	4,750,000

The coal sent to planters below the city is included in the consumption. The returns for 1886 and following are for calendar years; the preceding years end November 30. The Pittsburg and Southern Coal Company ceased to exist at the close of 1889, owing to dissensions among the members. This organization was mentioned in the report for 1888 as having been effected by Pittsburg coal shippers for handling

their coal in New Orleans. The method of measuring coal by the barrel at New Orleans still continues, the barrel weighing 208 pounds and containing 2.6 bushels. Prices of Pittsburg coal ranged about 25 cents per barrel during 1890, which was less than for some years previous.

California.—The following table exhibits the various sources from which California has received its coal during 1888, 1889, and 1890, and the tons imported from each locality:

Imports of coal at San Francisco.

	1888.	1889.	1890.
British Columbia (Wellington, Nanaimo, and East Wellington).....	<i>Tons.</i> 304, 916	<i>Tons.</i> 381, 460	<i>Tons.</i> 345, 252
Australian.....	272, 336	303, 285	155, 306
English and Welsh.....	107, 387	} 43, 678	40, 829
Scotch.....	10, 510		
Eastern (Cumberland and anthracite).....	30, 120	21, 588	32, 684
Franklin, Green River, and Cedar River.....	322, 711	198, 853	195, 770
Carbon Hill and South Prairie.....	241, 437	191, 775	247, 720
Mount Diablo and Coos Bay.....	81, 194	49, 770	53, 991
Japan.....	15, 852	4, 540	13, 170
Rocky Mountains.....		1, 594	
Other sources.....			850
Total.....	1, 386, 463	1, 196, 543	1, 085, 572

The arrivals at San Pedro and San Diego are not included in the above table. The following table shows the receipts at San Diego from 1886 and at San Pedro from 1888:

Receipts of coal at San Diego and San Pedro, California.

	1886.	1887.	1888.	1889.	1890.
San Diego.....	20, 986	68, 996	101, 368	54, 800	52, 358
San Pedro.....			166, 214	66, 740	70, 954

Prices for all coals during 1889 were widely fluctuating, but ruled generally low. In 1890 the demand was generally greater than the supply and prices were high, the year proving a profitable one to all engaged in the trade and especially to operators of Pacific coast mines. The scarcity of coal during 1890 was due to the great strike in Australia, which cut off an important source of supply. The strike at the Wellington mine, British Columbia, also affected receipts. The coal from this mine is of the finest produced on the coast and has always been in high demand. The vein is from 7 to 8 feet thick and the mine has a daily capacity of 950 tons, which is being increased as rapidly as possible.

Total receipts of coal at San Francisco during the past eight years.

Years.	Tons.	Years.	Tons.
1883.....	869, 615	1887.....	1, 154, 993
1884.....	987, 151	1888.....	1, 386, 463
1885.....	959, 246	1889.....	1, 196, 543
1886.....	1, 011, 867	1890.....	1, 085, 572

The average wholesale price of Wellington coal at San Francisco is \$9 per ton, but the scarcity in December put the price up to \$12 per ton. Australian coal, which sold at \$6.75 per ton in January, 1890, rose to \$11.50 per ton in December. The closing prices for the year were as follows:

Prices of coal at San Francisco at the close of 1890.

To arrive.	Per ton.	Spot, from yard,	Per ton.
West Hartley	\$10.00	Wellington	\$10.50
Scotch splint	10.00	Seattle	11.00
Cardiff	13.00	Coos Bay	11.00
Lehigh, lump	19.00	Cannel	11.00
Cumberland, bulk	17.00	Egg, hard	19.00
Egg, hard	18.00	Cumberland, bulk	18.00

WAGES IN COAL MINING.

The rate of wages paid to employés in and about coal mines continues to be a matter of dispute between the employer and the employed, and appearances do not seem favorable to the formation of a coöperative system whereby the interests of operator and miner may be mutually subserved. Strikes are of almost constant occurrence in one part the country or another, and no annual report of the industry can be written without mentioning some section which has been seriously injured from this cause. The miners, led frequently by some agitator rather than by reason, will not submit to a reduction of wages when the state of the market renders a curtailment of mining expenses necessary, and go out on a strike, causing loss of trade to their employers and bringing want to their own doors.

The average scale of wages paid to miners and other employés about the mines varies considerably in different parts of the country, depending largely, as it does, on the law of supply and demand, and, to a considerable extent, on the distance from trade centers and the cost of living in the particular section. The census returns show that the average wages paid miners in 1889 varied from \$1.46 per day in North Carolina and Georgia to \$3.26 per day in Washington. In most of the more important coal-producing States the miners are paid by the ton, bushel, or miner's car, the latter being an irregular quantity, though containing usually about 1,500 or 1,600 pounds.

In compiling the census tables on miners' wages it was deemed advisable to make them as uniform as possible with the wages of other employés, that is, by the rate of their daily earnings instead of by the rate per ton paid for mining. The census tables are reproduced below. No attempt has been made to obtain statements of wages from operators for 1890.

Labor and wages at coal mines of the United

States and Territories.	Above ground.												
	Foremen or overseers.			Mechanics.			Laborers.			Boys under 16 years.			Total average number employed.
	Average number employed.	Average wages per day.	Average number of days worked.	Average number employed.	Average wages per day.	Average number of days worked.	Average number employed.	Average wages per day.	Average number of days worked.	Average number employed.	Average wages per day.	Average number of days worked.	
Alabama	57	\$2.52	276	123	\$2.12	231	797	\$1.25	218	41	\$0.62	212	
Arkansas	5	2.69	248	21	2.22	208	79	1.49	210	11	.76	159	116
California and Oregon	6	5.12	296	20	2.90	236	48	2.04	248	2	1.50	240	76
Colorado	53	3.50	278	161	2.98	229	571	2.21	234	22	1.25	221	807
Georgia and North Carolina	12	2.29	264	34	2.15	210	277	.96	255	6	.45	24	329
Illinois	217	2.34	262	625	2.03	266	1,678	1.52	201	64	.80	200	2,584
Indiana	74	2.36	255	160	1.84	256	426	1.47	192	6	.71	152	666
Indian Territory	11	2.55	291	63	2.50	170	145	1.90	164	1	1.00	250	220
Iowa	147	2.20	228	202	2.23	253	709	1.57	209	17	.78	169	1,075
Kansas and Nebraska	69	2.37	190	160	2.23	200	488	1.56	197	25	.77	156	742
Kentucky	76	2.44	270	152	1.81	242	627	1.30	204	38	.75	205	893
Maryland	15	3.04	266	65	2.03	264	225	1.59	196	16	.90	187	321
Michigan	7	2.11	199	11	1.92	213	28	1.93	249	46
Missouri	122	2.09	228	107	2.11	246	692	1.52	214	29	.80	181	950
Montana	9	5.28	251	38	3.58	252	123	2.50	240	1	2.00	300	171
New Mexico	13	3.27	208	26	2.88	231	112	2.37	213	6	1.07	188	157
North Dakota	7	2.29	115	3	2.67	88	3	1.50	100	13
Ohio	221	2.26	244	334	1.91	235	1,420	1.51	192	83	.77	187	2,058
Pennsylvania (anthracite)	564	2.71	291	4,720	1.92	257	23,779	1.29	198	17,091	.62	185	46,154
Pennsylvania (bituminous)	378	2.57	250	1,028	2.11	237	3,366	1.67	208	207	.86	200	4,979
Tennessee	48	2.46	249	101	1.86	244	393	1.21	222	27	.55	190	569
Texas	7	2.91	283	5	2.50	260	109	1.52	248	121
Utah	3	3.63	246	18	2.84	238	59	2.35	198	4	.97	252	84
Virginia	16	2.01	245	51	1.77	269	407	1.16	282	47	.47	210	521
Washington	21	3.76	293	94	3.04	255	396	2.29	242	29	1.41	214	540
West Virginia	117	2.48	270	244	1.90	246	1,135	1.36	211	62	.76	203	1,558
Wyoming	10	4.42	263	37	2.97	260	321	2.21	253	1	1.50	156	369
Total	2,285	8,603	38,413	17,836	67,137

States in 1889, by States and Territories.

Below ground.													Total employees about mine.	Total amount of wages paid during 1889.
Foremen or overseers.			Miners.			Laborers.			Boys under 16 years.			Total average number employed.		
Average number employed.	Average wages per day.	Average number of days worked.	Average number employed.	Average wages per day.	Average number of days worked.	Average number employed.	Average wages per day.	Average number of days worked.	Average number employed.	Average wages per day.	Average number of days worked.			
73	\$2.73	272	4,110	\$2.15	248	1,564	\$1.33	237	99	\$0.66	224	5,846	6,864	\$3,157,109
10	2.71	228	462	2.20	180	64	2.00	186	25	.72	199	561	677	248,899
9	3.17	271	235	2.58	224	85	2.32	268	8	1.47	239	337	413	241,249
46	3.36	287	3,390	2.67	212	564	2.65	214	97	1.18	220	4,097	4,904	2,734,895
13	1.64	210	271	1.46	291	120	.98	288	404	733	258,016
305	2.38	256	15,386	1.98	177	5,062	1.77	199	597	.90	176	21,350	23,934	8,429,553
135	2.36	170	4,738	1.89	175	820	1.70	182	89	.71	184	5,782	6,448	2,144,566
10	3.10	252	1,200	3.25	166	393	2.41	177	39	.88	198	1,642	1,862	915,567
139	2.46	251	6,588	2.23	196	1,191	1.89	217	254	.77	200	8,172	9,247	3,860,893
103	2.46	230	4,447	1.89	207	456	1.75	222	208	.88	219	5,244	5,956	2,258,485
59	2.33	255	3,406	1.75	193	674	1.56	219	112	.70	213	4,251	5,144	1,669,524
22	3.04	289	2,689	2.45	203	386	1.86	222	284	1.06	200	3,381	3,702	1,700,305
4	2.31	218	191	1.74	184	10	1.67	216	10	.87	300	215	261	90,124
103	2.33	230	4,780	2.10	201	656	1.81	206	142	.71	203	5,681	6,631	2,476,870
11	4.32	248	521	3.19	213	143	2.60	235	2	1.50	300	677	848	576,773
9	3.58	287	688	3.08	192	146	2.59	207	15	1.10	105	858	1,015	584,376
3	3.00	117	55	2.15	108	4	1.88	111	62	75	17,560
221	2.32	245	14,733	1.95	181	1,955	1.63	185	376	.73	181	17,285	19,343	6,730,778
737	3.05	291	30,739	2.40	179	35,376	1.63	184	4,770	.89	180	77,522	123,676	38,867,331
606	2.56	256	40,100	1.93	210	5,303	1.85	220	2,144	.78	217	48,153	53,132	20,327,805
55	2.13	245	2,538	1.98	227	696	1.26	228	173	.71	229	3,462	4,031	1,548,392
6	2.65	248	340	2.00	264	56	1.77	236	20	.75	40	422	543	252,470
5	3.47	260	332	3.21	163	101	2.51	169	29	1.00	168	467	551	258,601
12	2.44	265	712	1.53	285	253	1.59	269	25	1.14	274	1,002	1,523	604,796
31	3.97	286	1,549	3.26	197	509	2.46	222	28	1.06	222	2,117	2,657	1,696,293
118	2.46	269	6,367	1.86	223	1,504	1.47	224	231	.66	220	8,220	9,778	3,748,721
14	3.31	310	1,593	2.71	231	680	2.47	220	19	1.32	238	2,306	2,675	1,537,107
2,859	158,060	58,771	9,796	229,486	296,623	106,937,058

DETAILED STATISTICS, BY STATES.

ALABAMA.

Total product in 1889, 3,572,983 short tons; spot value, \$3,961,491. Total product in 1890, 4,090,409 short tons; spot value, \$4,202,469.

In no other State have such rapid strides been made in the production of coal as in Alabama during the past decade. At the time of the taking of the Ninth Census (1870) no coal was being mined in the State except for local consumption. During the next ten years the production increased to a limited extent, amounting in 1880 to 340,000 tons. During 1886 and 1887 Birmingham experienced the great development due to the discovery of valuable coal and iron deposits in the neighborhood, and in the latter year the production of coal was increased to 1,950,000 tons. Another million tons was added to the product in 1888. In 1889 the product was 3,572,983 short tons, worth \$3,961,491, and in 1890, 4,090,409 short tons, valued at \$4,202,469.

The following tables show, by counties, the production of coal in Alabama in 1889 and 1890, also the distribution of the product. In previous volumes of Mineral Resources tables have been published showing the returns from individual mines in Alabama. The individual returns for 1889 were collected by the Census Office under the stipulation that they would be held strictly confidential. The same plan has been adopted in collecting the statistics for 1890, hence no statements of individuals are given.

Coal product of Alabama in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Bibb	363,102	1,414	17,590	118,419	500,525	\$604,230
Blount		164			164	273
Cherokee		40			40	80
Cullman		300			300	600
Etowah		4,751			4,751	8,325
Jefferson	1,899,264	40,577	49,208	948,397	2,437,446	2,618,777
St. Clair	21,922	1,170	2,840	14,625	40,557	50,518
Shelby	54,361	327	5,272	24,873	84,833	152,166
Tuscaloosa	8,600	6,991	550		16,141	19,796
Walker	479,960	4,211	4,055		488,226	506,726
Total	2,327,209	59,945	79,515	1,106,314	3,572,983	3,961,491

Coal product of Alabama in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Bibb.....	365,742	1,440	24,141	130,488	521,811	\$574,419	250	1,340
Coosa.....	22,000	750	3,903	7,000	33,653	39,855	188	175
Jefferson.....	1,294,882	31,292	52,478	1,286,408	2,665,060	2,669,226	267	(a)6,209
Shelby.....	25,022	-----	-----	-----	25,022	62,550	200	150
Tuscaloosa.....	60,521	3,936	1,060	-----	65,517	68,795	157	268
Walker.....	719,816	35,160	7,370	5,000	767,346	768,624	210	1,500
Small mines.....	-----	12,000	-----	-----	12,000	19,000	-----	-----
Total.....	2,487,983	84,578	88,952	1,428,896	4,090,409	4,202,469	(b)217	10,642

a Includes 1,350 convicts leased by the State.

b Average for the State.

PRODUCTION, BY DISTRICTS.

The coal fields of Alabama are divided into three districts, namely: The Warrior, embracing the counties of Tuscaloosa, Walker, and a portion of Jefferson; the Cahaba, embracing the counties of Bibb, Shelby, and the remainder of Jefferson; and the Coosa, covering St. Clair county. The product in 1890, by districts, is shown in the following table:

Coal product of Alabama in 1890, by districts.

Districts.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Cahaba.....	561,764	10,440	34,141	480,488	1,086,833	\$1,068,969	2,190
Coosa.....	22,000	750	3,903	7,000	33,653	39,855	175
Warrior.....	1,904,219	61,388	50,908	941,408	2,957,923	3,074,645	8,277
Small mines.....	-----	12,000	-----	-----	12,000	19,000	-----
Total.....	2,487,983	84,578	88,952	1,428,896	4,090,409	4,202,469	10,642

LABOR AT ALABAMA COAL MINES.

During 1889 the average number of men employed at Alabama coal mines was 6,975. They worked an average of about 248 days. In 1890 10,642 men were employed, and the average number of days the collieries were active was 217. It is difficult to arrive at the average number of days worked per man, as accounts are not kept in a manner to admit of easily obtaining such a statement, and operators naturally object to taking the time and trouble necessary for such work. A company carrying 300 men upon its pay roll may be operating, say, 250 days in the year. Few miners, however, work more than five days a week, and it is probable that the average would be little more than four days per week per man. Hence, in the foregoing tables the average is given of the number of days the collieries were operating, which is larger than the number of days worked per man. The number of men employed includes superintendents, foremen, mechanics, and all others employed in and about the mines. Of the number of employes, 1,350 were convicts.

ARKANSAS. (*)

Total product in 1889, 279,584 short tons; spot value, \$395,836. Total product in 1890, 399,888 short tons; spot value, \$514,595.

Coal mining in Arkansas as an industry of commercial importance is of recent date. Practically no coal was mined in the State up to 1870, though it has been stated some coal was taken out in that year. The Tenth Census (1880) reported a product of 14,778 short tons, valued at the mines at \$33,535. At this time the coal mines gave employment to a total force of 130 persons. At the time of taking the Eleventh Census 677 persons were employed in the production of 279,584 short tons. In the year 1890, 938 men were employed.

The product of 1889 was 2,713 short tons more than that of 1888. The increase in 1890 over that of 1889 was 120,304 short tons. The increase in value was \$118,659, showing that the increase in the volume of production was attended by a decrease in the price received at the mines.

The coal product of Arkansas, by counties, for 1889 and 1890, with the distribution of the product, is shown in the following tables:

Coal product of Arkansas in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Franklin		1,688		1,688	\$4,125	
Johnson	103,018	1,080	1,900	105,998	156,067	} 172
Pope	4,214	1,200	600	6,014	11,491	
Sebastian	161,286	2,552	1,746	165,884	224,153	505
Total	268,518	6,820	4,246	279,584	395,836	677

Coal product of Arkansas in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Sebastian	285,268	1,290	14,330	300,888	\$363,668	214	683
Johnson	85,900	1,800	1,300	89,000	130,927	215	215
Pope	3,801	150	49	4,000	8,000	200	40
Small mines		6,000		6,000	12,000		
Total	374,969	9,240	15,679	399,888	514,595	(a)214	938

a Average for the State.

* In the 1888 volume of Mineral Resources was published a detailed description of the Arkansas coal fields, prepared by Mr. Arthur Winslow, assistant geologist in charge of coal regions.

The production of coal in Arkansas from 1882 to 1890 has been as follows:

Product of coal in Arkansas from 1882 to 1890.

Years.	Short tons.	Years.	Short tons.
1882	5,000	1887	129,600
1883	50,000	1888	276,871
1884	75,000	1889	279,584
1885	100,000	1890	399,888
1886	125,000		

In "Mineral Resources of the United States, 1887," the coal product of Arkansas for that year was estimated at 150,000 short tons. Later returns, however, showed that this estimate was entirely too high, and in the volume for 1888 the amount is given as 129,600 short tons. It is probable that estimates for previous years are also excessive, with the possible exception of 1882.

Transportation facilities.—The product of Sebastian county is shipped over the Saint Louis, Iron Mountain and Southern railroad from Jenny Lind, and over the Saint Louis and San Francisco railroad from Huntington. The colliery at Hackett, on the line of the Saint Louis and San Francisco railroad, shipped 17,643 tons in 1889, but was not in operation in 1890. The product of Johnson and Pope counties is shipped over the Little Rock and Fort Smith railroad from Coal Hill and Will Creek.

Markets.—The larger portion of the shipments from Huntington are made to Texas, though Kansas and Arkansas take a part of the supply. The Jenny Lind properties supply the neighboring cities and towns with coal for domestic use, and the Saint Louis, Iron Mountain and Southern railroad with fuel for locomotives. The Allister and Coal Hill slopes at Coal Hill supply fuel to the Missouri, Kansas and Texas railroad for its locomotives. The greater part, probably 80 per cent. of the total product, is used for steaming purposes, the remainder being used for domestic consumption in Hot Springs, Van Buren, and other points in the State. The coal from Will Creek is used almost entirely for domestic purposes. It is shipped to Little Rock, Van Buren, Russellville, Hot Springs and Memphis.

Composition.—The following analyses and descriptions of Arkansas coals, made in the geological survey of the State by Dr. R. N. Brackett and Mr. J. P. Smith, were published in Mineral Resources for 1888, and on account of the exhaustion of that volume are repeated here.

Analyses of Arkansas coals (a).

Names of mines.	Counties.	Thick- ness.	How sampled.	Specific gravity.
		<i>Ft. In.</i>		
Hackett City shaft ..	Sebastian	3 0	From 5 market cars	1.341
Huntington slope	do	6 6	From 2 market cars	1.293
Greenwood shaft	do	6 0	From pile of fresh coal on dump.	1.300
Gwyn drift	do	4 10	do	1.315
Western Coal and Mining Company, Petty slope.	do	5 0	do	1.384
Philpott shaft	Johnson	1 9	do	1.292
Felker slope	Franklin	1 8	From pile on dump, dug six months.	1.317
Ouita slope	Pope	2 6	From 1 market car	1.339
Eureka shaft	Johnson	3 0	do	1.345
Coal Hill shaft	do	3 10	do	1.333
Allister slope	do	3 7	From 2 market cars	1.320
Shinn slope	Pope	1 10	From fresh face of coal	1.346

Names of mines.	Counties.	Chemical composition.					Fuel ratio.
		Water.	Sulphur.	Ash.	Fixed carbon.	Vol. hydro- carbon.	C. V. H. C.
Hackett City shaft ..	Sebastian	0.853	1.324	9.038	73.869	14.916	4.95
Huntington slope	do	0.928	1.143	4.845	77.538	15.546	4.99
Greenwood shaft	do	0.818	2.522	5.973	75.821	14.866	5.10
Gwyn drift	do	0.892	1.193	6.245	77.092	14.577	5.29
Western Coal and Mining Company, Petty slope.	do	1.779	1.620	7.046	76.225	13.330	5.72
Philpott shaft	Johnson	0.869	0.993	3.090	80.915	14.133	5.73
Felker slope	Franklin	1.128	1.164	3.220	81.277	13.211	6.15
Ouita slope	Pope	0.980	1.829	8.174	76.817	12.200	6.29
Eureka shaft	Johnson	1.100	2.745	12.042	72.855	11.278	6.46
Coal Hill shaft	do	1.017	3.672	8.351	76.119	10.841	7.02
Allister slope	do	1.178	3.531	8.322	76.494	10.475	7.30
Shinn slope	Pope	1.058	3.346	11.750	75.434	8.410	8.96

Names of mines.	Counties.	Results of coking tests.	
		Appearance of product.	Per cent of product.
Hackett City shaft ..	Sebastian	Product well fused and roughly took the shape of the crucible.	82.3
Huntington slope	do	Product well fused and took the shape of the crucible.	80.6
Greenwood shaft	do	Product very well fused and took the shape of the crucible.	83.6
Gwyn drift	do	do	82.2
Western Coal and Mining Company, Petty slope.	do	Product well fused and took roughly the shape of the crucible.	83.0
Philpott shaft	Johnson	Product well fused and took the shape of the crucible.	84.6
Felker slope	Franklin	Fragments partially fused, but retain somewhat the original shapes.	85.0
Ouita slope	Pope	Product not at all fused; fragments retain their original shapes.	87.6
Eureka shaft	Johnson	do	89.2
Coal Hill shaft	do	Product partially fused; fragments retain somewhat their original shapes.	87.2
Allister slope	do	Product partially fused; fragments little changed.	86.5
Shinn slope	Pope	Product not at all fused; fragments retain their original shapes.	88.4

a Arranged in the order of their fuel ratios.

On the basis of their fuel ratios, it is seen that the above coals are mostly semi-bituminous. The term "semi-anthracite" is often somewhat carelessly applied to all Arkansas coals. The physical appearance of the different varieties is similar, which, together with the fact that in composition they merge into each other by almost insensible gradations, has rendered confusion in nomenclature excusable. To the eye they all present more or less the appearance of soft bituminous coal with a cuboidal fracture. There seems to be no approach in any to the hard, compact, glistening anthracite, with the semiconchoidal fracture. But despite these facts of proximate composition there are several coals of this list which from their mode of burning deserve to be classed as semi-anthracities. These are the coals from the Ouita, the Eureka, and the Shinn openings. The remaining coals are all of the nature of semi-bituminous coals. Even those termed bituminous in the table are so near the border line as not to have the characteristics of that coal at all pronounced; others, from the Coal Hill district—*i. e.*, from the Felker, Allister, and Coal Hill openings—approach nearer to being semi-anthracites.

Arkansas coals are all more or less soft and friable and not well adapted to long transportation. This characteristic is variable in different openings. Much of the coal shipped from Huntington during the past year has been stripped coal, which, being soft and stained, was calculated to injure the reputation of Arkansas coals.

Arkansas coals have all a high evaporating power, burn freely, and make little smoke or soot. For reaching the best results, however, a grate with small openings is necessary, as these coals are liable to decrepitate and to fall through the grate. Coal Hill coal makes an intensely hot fire, producing steam rapidly; but it clinkers and is severe in its action upon grate bars. It slacks a good deal on exposure, and in burning much fine coal is lost through ordinary grate bars. Sebastian county coal is easily ignited and quick burning, but does not produce quite so intense a heat as does the Coal Hill coal; it does not clinker, but leaves a loose ash. The Ouita and Eureka coals are not considered good for steaming purposes. The coking qualities of several of the coals have been tested on a commercial scale and these tests give little prospect that any will produce a merchantable coke. Arkansas coals are all suitable for domestic use, being more or less free burning, easily kindled, and burning with a slight draft. Those of Sebastian county swell and coke somewhat in the fire, but not objectionably so; they leave a loose pulverulent ash and do not burn out the grates. Coal Hill coal is not esteemed as a domestic fuel. In open grates it burns with an objectionably intense heat; with this the sulphur in the coal becomes very active, and, as a result, grates and stoves are corroded. Some cinder or loose clinker is also formed. The Philpott and Felker coals have a much better reputation. The Ouita and Eureka coals are among the best for domestic purposes, and seem to

satisfy all the chief requirements. They are especially adapted for use in self-feeding stoves and for kitchen use. They are easily kindled, burn slowly, and do not swell or coke. The Ouita coal leaves a loose reddish ash, but the Eureka coal forms a fusible clinker.

Arkansas coals have heretofore been sent to market without any preparation other than a rough sorting into slack, nut, and lump at the tipple. Operators are now looking toward crushing and screening the coal into various market sizes, and this will, without doubt, add much to the development of the trade.

CALIFORNIA.

Total product in 1889, 121,820 short tons; spot value, \$288,232. Total product in 1890, 110,711 short tons; spot value, \$283,019.

The total product of coal in California in 1888 was estimated at 95,000 short tons by Mr. William A. Goodyear, who made a special collection of the statistics. This shows an increase during the census year of 26,820 short tons. The returns for 1890 show a decrease from 1889 of 11,109 short tons in product and of \$5,213 in value.

The following tables exhibit the production in California in 1889 and 1890 by counties, with the distribution of the product:

Coal product of California in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Amador	39,500	550	850	40,900	\$75,075
Contra Costa	63,221	336	1,388	64,945	161,190
Fresno	5,000	50	5,050	10,100	35,359
Monterey	392	22	253	672	3,600
San Bernardino	3,015	2,188	5,203	13,008
Total	111,128	3,146	7,546	121,820	288,232

Coal product of California in 1890, by districts.

Districts.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Jone (Amador county).....	33,432	50	128	33,610	\$55,215	291	47
Mount Diablo (Contra Costa, Fresno, and San Bernardino counties).....	70,004	2,046	4,926	76,976	226,804	303	287
Livermore (Alameda County) (a)	25	100	125	1,000	30
South Mission (Monterey County) (b).....
Total.....	103,436	2,121	5,154	110,711	283,019	(c) 301	364

a Prospecting.

b Developing.

c Average for State.

Production in previous years.—Statistics of the coal production of California are available only since 1883. Since that date the annual production has been as follows:

Coal product of California from 1883 to 1890.

Years.	Short tons.	Years.	Short tons.
1883	76,162	1887	50,000
1884	77,485	1888	95,000
1885	71,615	1889	121,820
1886	100,000	1890	110,711

COLORADO.

Total product in 1889, 2,597,181 short tons; spot value, \$3,993,768. Total product in 1890, 3,094,003 short tons; spot value, \$4,344,196.

The total product of Colorado coal in 1889 exceeded the product of 1888 by 411,704 short tons, but the value fell off from \$2.20 to \$1.54 per short ton, showing a decrease in the total value of \$814,281. A further increase of 496,822 short tons is noted in the product of 1890. The total value is increased \$350,428, though the average price realized at the mines fell off about 25½ cents per ton.

Coal product of Colorado in 1889 by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Arapahoe	50	737	36		823	\$1,039	2
Boulder	298,074	11,325	13,697		323,096	494,569	717
Delta	11	1,346			1,357	2,391	2
Douglas		260			260	520	(a)
El Paso	49,450	3,784	978		54,212	69,116	124
Fremont	239,940	4,508	29,581		274,029	581,125	928
Garfield	200,607		150	38,535	239,292	393,260	366
Gunnison	177,303	3,279	5,295	66,565	252,442	574,746	489
Huerfano	309,617	1,640	22,460		333,717	457,982	657
Jefferson	1,885	7,905	1,000		10,790	27,425	16
La Plata	14,393	7,596	3	12,979	34,971	60,855	69
Larimer		100			100	150	(a)
Las Animas	756,064	36,901	10,587	189,982	993,534	1,157,022	1,354
Mesa		1,100			1,100	2,750	(a)
Montezuma		816			816	2,155	(a)
Park	37,873	300	3,650		41,823	104,223	132
Rio Blanco		2,900			2,900	5,700	(a)
Routt		1,491			1,491	2,246	(a)
San Miguel		1,800			1,800	7,200	(a)
Weld	24,068	3,460	1,100		28,628	43,294	48
Total	2,109,335	91,248	88,537	308,061	2,597,181	3,993,768	4,904

a The mines in Douglas, Larimer, Mesa, Montezuma, Rio Blanco, Routt and San Miguel counties were not considered commercial mines by the Census Office, and no statistics were obtained as to labor, wages and capital.

Coal product of Colorado in 1890 by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Arapahoe	519	169	12		700	\$1,297	4
Boulder	499,571	9,326	6,807		425,704	563,860	979
Delta	559	225			775	1,125	3
Dolores	800				800	4,000	6
Douglas		700			700	1,400	4
El Paso	24,019	400	1,198		25,617	28,206	54
Fremont	335,590	1,758	90		397,418	610,570	1,049
Garfield	163,884	11,500	8,700		183,884	268,218	334
Gunnison	153,875	2,063	5,669	67,605	229,212	446,196	389
Huerfano	410,722	3,646	13,464		427,832	558,374	907
Jefferson	10,921	63			10,984	32,842	79
La Plata	28,697	1,156	30	13,310	43,193	119,065	97
Larimer		1,500			1,500	3,000	2
Las Animas	930,254	10,917	7,231	206,266	1,154,668	1,335,366	1,531
Mesa	950	50			1,000	2,000	4
Montezuma	140	98			238	909	8
Park	49,160	434			49,594	148,783	150
Pitkin	14,912		2,500	56,000	74,362	107,825	96
Rio Blanco		200			200	400	2
Routt	250	455			705	1,338	7
San Miguel	1,500				1,500	3,000	4
Weld	40,625	3,042	2,750		46,417	63,982	118
Small mines		17,000			17,000	42,500	
Total	2,636,939	65,432	48,451	343,181	3,094,003	4,344,196	5,827

NORTHERN DIVISION.

WELD COUNTY.

Product of coal in Weld county, Colorado, from 1886 to 1890.

Years.	Short tons.
1886	20,450
1887	39,281
1888	28,054
1889	28,628
1890	46,417

Product of coal in Weld county in 1890, with its value.

	Short tons.	Value.
Sold for railway and commercial use	40,625	
Sold to local trade and used by employés	3,042	
Made into coke		
Used at mines for steam and heat	2,750	
Total	46,417	\$63,982

The Weld county mines are economically of small importance, only one mine being worked regularly. The coal is the characteristic northern Colorado lignite, and is largely used by the railway.

BOULDER COUNTY.

Product of coal in Boulder county, Colorado, from 1886 to 1890.

Years.	Short tons.
1886	220,287
1887	297,338
1888	315,155
1889	323,096
1890	425,704

Product of coal in Boulder county in 1890, and its value.

	Short tons.	Value.
Sold for railway and commercial use	409,571
Sold for local trade and used by employés	9,326
Made into coke
Used at mines for steam and heat	6,807
Total	425,704	\$563,860

Boulder county ranks third in the amount of coal produced in the State, a position it has held for several years. While the field is inferior to that in the southern and western portions of the State, its proximity to Denver and excellent railroad facilities cause a great demand for the coal. There are seven mines in the county, which produced each 30,000 short tons or over in 1890. From the coal of one of these, the Simpson, the following analysis has been made:

Analysis of coal from the Simpson mine, Boulder county, Colorado.

	Per cent.
Water	12.01
Volatile matter	35.19
Fixed carbon	46.24
Ash	6.56
Total	100.00
Sulphur	1.00

JEFFERSON COUNTY.

Product of coal in Jefferson county, Colorado, from 1886 to 1890, inclusive.

Years.	Short tons.
1886	9,928
1887	12,000
1888	9,000
1889	10,790
1890	10,984

Coal production of Jefferson county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use	10,921
Sold to local trade and used by employés	63
Made into coke
Used at mines for steam and heat.....	
Total production.....	10,984	\$32,842

The only mines operated in Jefferson county are at Golden. The coal vein is vertical and expensive to work, and practically the entire product is used to supply local demand and that of adjacent towns.

The following is an analysis made of Jefferson county coal:

Analysis of Jefferson county coal.

	Per cent.
Water	13.60
Volatile matter.....	39.90
Fixed carbon	42.43
Ash	4.07
Total.....	100.00

ARAPAHOE COUNTY.

Product of coal in Arapahoe county, Colorado, from 1886 to 1890, inclusive.

Years.	Short tons.
1886	11,000
1887	16,000
1888	1,700
1889	823
1890	700

Coal production of Arapahoe county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use	519
Sold to local trade and used by employés	169
Made into coke
Used at mines for steam and heat.....	12
Total production.....	700	\$1,297

No new mine has been opened in Arapahoe county since 1888, and the small production comes from the Scranton mine, operated by the Colorado Eastern Railroad Company.

ROUTT COUNTY.

Product of coal in Routt county, Colorado, in 1889 and 1890.

Years.	Short tons.
1889.....	1,491
1890.....	705

Coal production of Routt county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	250	
Sold to local trade at mine.....	455	
Made into coke.....		
Used by employes and for steam at mine.....		
Total production.....	705	\$1,338

Coal outcrops over a large portion of Routt county and varies in character from lignite to a hard dry anthracite. The county is without a railway and sparsely settled. Only enough coal is mined to supply fuel for ranchmen and miners. The Yampah Valley Stock Company operates a mine of their own, using the coal chiefly for irrigating pumps.

LARIMER COUNTY.

Product of coal in Larimer county, Colorado, in 1889 and 1890.

Years.	Short tons.
1889.....	100
1890.....	1,500

Coal production of Larimer county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....		
Sold to local trade.....	1,500	
Made into coke.....		
Total production.....	1,500	\$3,000

The coal produced in Larimer county comes from one small mine, the Little Grizzly at Pinkhamton, and is mined only to supply the little local trade. As, however, coal veins outcrop in various portions in the North Park there may be a trifling amount of coal dug at other points by ranchmen for their own use. No record of any such operations has been obtainable.

CENTRAL DIVISION.

DOUGLAS COUNTY.

Product of coal in Douglas county, Colorado, from 1887 to 1890, inclusive.

Years.	Short tons.
1887	3,500
1888	400
1889	260
1890	700

Coal production of Douglas county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....		
Sold to local trade and used by employes.....	700	
Made into coke.....		
Used at mines for steam and heat.....		
Total production.....	700	\$1,400

The Douglas mine was opened in 1886, and a spur track built from the Denver and Rio Grande railroad to the mine from Sedalia; but the operation of the mine was not a financial success, and mining is carried on only upon a very small scale. The coal is used in the immediate neighborhood.

EL PASO COUNTY.

Product of coal in El Paso county, Colorado, from 1886 to 1890, inclusive.

Years.	Short tons.
1886	53,000
1887	47,517
1888	44,114
1889	54,212
1890	25,617

Coal production of El Paso county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	24,019	
Sold to local trade and used by employes.....	400	
Made into coke.....		
Used at mines for steam and heat.....	1,198	
Total production.....	25,617	\$28,206

The coal of El Paso county is a lignite of rather low quality. The properties have been described in Mineral Resources of the United States for 1882, 1883-'84, 1885, and 1886.

PARK COUNTY.

Product of coal in Park county, Colorado, from 1886 to 1890, inclusive.

Years.	Short tons.
1886	23, 823
1887	23, 421
1888	46, 588
1889	41, 823
1890	49, 594

Coal production of Park county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use	49, 160
Sold to local trade and used by employes	434
Made into coke	(a)
Used at mines for steam and heat	(a)
Total production	a 49, 594	\$148, 783

a Nut coal and slack coal not included in total, and no account kept.

The only mine producing coal in Park county in 1890 was the Como No. 5, operated by the coal department of the Union Pacific Railway Company. Nos. 1, 2, 3, and 4 are abandoned, and a new opening, Como No. 6, begun late in 1890, was not productive in that year. This opening is made only for economically mining a block of the vein of limited extent.

FREMONT COUNTY.

Product of coal in Fremont county, Colorado, from 1886 to 1890.

Years.	Short tons.
1886	332, 024
1887	417, 326
1888	438, 789
1889	274, 029
1890	397, 418

Coal production of Fremont county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use	395, 590
Sold to local trade and used by employes	1, 738
Made into coke	90
Used at mines for steam and heat	90
Total production	397, 418	\$610, 570

Fremont county ranks fourth in the State in importance of coal production. The principal producing properties are owned by the Cañon City Coal and Coking Company and the Colorado Coal and Iron Company. Following are reports of analyses made of coal taken from the Cañon and Chandler mines:

Analyses of coal from Cañon and Chandler mines.

	Cañon mine.	Chandler mine. <i>a</i>
	<i>Per cent.</i>	<i>Per cent.</i>
Water	3.93	
Volatile matter	42.43	42.40
Fixed carbon	47.16	53.72
Ash	6.48	3.20
Total	100.00	99.32
Sulphur		0.68

a Made by Mr. E. E. Burlingame.

SOUTHERN DIVISION.

HUERFANO COUNTY.

Product of coal in Huerfano county, Colorado, from 1886 to 1890, inclusive.

Years.	Short tons.
1886	89,913
1887	131,810
1888	159,610
1889	333,717
1890	427,832

Coal production of Huerfano county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	410,722	
Sold to local trade and used by employes	3,646	
Made into coke		
Used at mines for steam and heat.....	13,464	
Total production	427,832	\$558,374

Huerfano county has been very actively developed since 1888. The completion of the Missouri Pacific and Chicago, Rock Island and Pacific railways to Pueblo and Denver, and the consequent opening of large and prosperous markets in Kansas and Nebraska, together caused the purchase and development of many mines which previously had been undeveloped. The largest new product came from the Colorado Fuel Company, which bought and opened the Rouse mine. The vein worked here is 6 feet in thickness, and the coal is one of the best which reaches the Denver market. It is semi-coking, contains a low percentage of water, and burns freely and with great heat.

At Loma, 3 miles from Walsenburg, the Southern Colorado Coal Company has opened the Loma mines, to be operated in connection with the Chicago, Rock Island and Pacific Railway. The vein worked is 7 feet in thickness, and in quality the coal very closely resembles that from the Rouse mine.

The following analyses have been made of coal from the Lenox, Maitland, and Rouse mines:

Analyses of coals from Huerfano county, Colorado.

	Lenox.	Maitland.	Rouse.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Water.....	2.92	3.10	2.66
Volatile matter.....	41.18	38.12	36.71
Fixed carbon.....	45.36	48.58	51.41
Ash.....	10.54	10.20	9.22
Total.....	100.00	100.00	100.00
Sulphur.....	1.39	2.04	1.373

LAS ANIMAS COUNTY.

Product of coal in Las Animas county, Colorado, from 1886 to 1890.

Years.	Short tons.
1886.....	429,706
1887.....	506,540
1888.....	706,455
1889.....	993,534
1890.....	1,154,668

Coal production of Las Animas county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	930,254
Sold to local trade and used by employes.....	10,917
Made into coke.....	206,266
Used at mines for steam and heat.....	7,231
Total production.....	1,154,668	\$1,335,366

Las Animas is by far the most important coal producing county in the State, and the increase in the annual production since 1887 has been phenomenal. The product of 1888 was 40 per cent. larger than that of 1887, and that of 1889, 40 per cent. more than that of 1888. The product of 1890 was 20 per cent. greater than that of 1889, and considerably more than twice that of 1887.

The mines of Las Animas county were described in Mineral Resources for 1888. Three of the more important ones are the Chicosa, Sopris, and Victor, of which the following analyses have been made.

Analyses of coals from Las Animas county, Colorado.

	Chicosa. (a)	Sopris.	Victor.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Water.....	0.20	0.61	1.26
Volatile matter.....	28.94	33.18	36.40
Fixed carbon.....	64.51	57.56	53.10
Ash.....	6.35	8.65	9.24
Total.....	100.00	100.00	100.00
Sulphur.....	0.27	.75	1.11

LA PLATA COUNTY.

Product of coal in La Plata county, Colorado, from 1886 to 1890.

Years.	Short tons.
1886	18, 166
1887	22, 880
1888	33, 625
1889	34, 971
1890	43, 193

Coal production of La Plata county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use	28, 697
Sold to local trade and used by employés	1, 156
Made into coke	13, 310
Used at mine for steam and heat	30
Total production	43, 193	\$119, 005

The coal mines of La Plata county are operated only for the local demand in Durango and Silverton, both small towns. Some of the coal is burned in locomotives on the Denver and Rio Grande railroad, and most of that from the Porter mine is coked for the use of the San Juan smelter at Durango.

Analyses of La Plata county coals.

	Fairmount vein.	Porter-La Plata vein.	Carbonana.	
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	
Water	1.25	1.11	1.16	
Volatile matter	39.71	36.54	34.33	
Fixed carbon	52.90	51.69	52.69	
Ash	6.14	10.66	11.82	
Total	100.00	100.00	100.00	
Sulphur		1.450	1.22	

	Porter vein.	Peacock vein.	Graden vein.	San Juan.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Water	0.63	2.49	2.94	1.12
Volatile matter	34.70	34.31	35.63	37.30
Fixed carbon	57.30	51.98	50.65	54.69
Ash	7.37	11.22	10.78	6.89
Total	100.06	100.00	100.00	100.00
Sulphur	0.737	1.68	1.53	0.864

DOLOROS COUNTY.

Product of coal in Dolores county, Colorado, from 1887 to 1890, inclusive.

Years.	Short tons.
1887	1,000
1888	200
1889	
1890	800

The one mine worked in Dolores county is to supply the Grand View smelter at Rico, 8 miles from the mine. The coke from the coal is said to be of poor quality and very expensive.

WESTERN DIVISION.

PITKIN COUNTY.

Product of coal in Pitkin county, Colorado, from 1887 to 1890.

Years.	Short tons.
1887	4,000
1888	28,113
1889	
1890	74,362

Coal production of Pitkin county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use	14,912
Sold to local trade and used by employes	950
Made into coke	56,000
Used at mines for steam and heat	2,500
Total production	74,362	\$107,825

The only mine in this county producing in 1890 was the Spring Gulch, operated by the Grand river Coal and Coking Company of Colorado. The coal yields an excellent coke, which gives the greatest satisfaction in blast-furnace use. The coking ovens are located at Cardiff, on the Roaring Fork of Grand river, and about 4 miles south of Glenwood Springs. The coal of this county varies from a high grade anthracite to a dry bituminous, and the completion of the railway being built up Rock creek from Carbondale, and connecting the mines with the Colorado Midland and Denver and Rio Grande railways, will largely increase the output.

GARFIELD COUNTY.

Product of coal in Garfield county, Colorado, from 1887 to 1890, inclusive.

Years.	Short tons.
1887	30,000
1888	115,000
1889	239,292
1890	183,884

Coal production of Garfield county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	163,884
Sold to local trade and used by employés	11,300
Made into coke
Used at mines for steam and heat	8,700
Total product.....	(a) 183,884	\$268,218

a Slack coal used for steam at three mines not included and no account kept.

The tonnage of coal from Garfield county is yet comparatively small, the distance from the principal markets in Colorado being great and the cost of transportation made high by adverse gradients. The completion of the standard gauge track past the principal mines and to Utah points will probably lead to increased production from these mines to supply Utah trade. None of the coal mined in this county is coked, the greater portion of the output being dry bituminous coal of good quality. The mines and coal of this county have been fully described in past volumes of this-series.

GUNNISON COUNTY.

Product of coal in Gunnison county, Colorado, from 1886 to 1890.

Years.	Short tons.
1886	159,951
1887	243,122
1888	258,374
1889	252,442
1890	229,212

Coal production of Gunnison county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	153,875
Sold to local trade and used by employés	2,063
Made into coke	67,605
Used at mines for steam and heat.....	5,669
Total production.....	(a) 229,212	\$446,196

a Of this total 52,707 short tons was anthracite coal.

MESA COUNTY.

Product of coal in Mesa county, Colorado, from 1888 to 1890.

Years.	Short tons.
1888	300
1889	1, 100
1890	1, 000

Coal production of Mesa county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	950
Sold to local trade and used by employés	50
Made into coke.....	
Used at mines for steam and heat.....	
Total production.....	1, 000	\$2, 000

SAN MIGUEL COUNTY.

Product of coal in San Miguel county, Colorado, in 1889 and 1890.

Years.	Short tons.
1889	1, 800
1890	1, 500

Coal production of San Miguel county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	1, 500
Sold to local trade and used by employés
Made into coke.....	
Used at mines for steam and heat.....	
Total production.....	1, 500	\$3, 000

Two small mines supplied fuel to Telluride and vicinity in 1890, but the completion of the Denver and Rio Grande Southern railroad from Dallas to Telluride early in 1891 will probably cause coal mining in this county to cease through the introduction of other coal.

DELTA COUNTY.

Product of coal in Delta county, Colorado, in 1889 and 1890.

Years.	Short tons.
1889	1, 357
1890	775

Coal production of Delta county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	550
Sold for local trade and used by employes	225
Total production	775	\$1,125

MONTEZUMA COUNTY.

Product of coal in Montezuma county, Colorado, in 1889 and 1890.

Years.	Short tons.
1889	816
1890	238

Coal production of Montezuma county in 1890 and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....	140
Sold to local trade at mine and used by employes	98
Made into coke.....
Used at mines for steam and heat.....
Total production.....	238	\$909

In the newly created county of Montezuma the La Plata coal beds outcrop at various points, and near the town of Cortez several small mines have been opened and a little coal produced in 1890 to supply the limited local demand for domestic use. The product is a non-coking bituminous coal, similar to that mined in La Plata county, Colorado.

RIO BLANCO COUNTY.

Product of coal in Rio Blanco county, Colorado, in 1889 and 1890.

Years.	Short tons.
1889	2,900
1890	200

Coal production of Rio Blanco county in 1890, and its value.

	Short tons.	Spot value.
Sold for railway and commercial use.....
Sold to local trade and used by employes	200
Made into coke.....
Used at mine for steam and heat.....
Total production	200	\$400

The coal production of Rio Blanco county is made from a few small mines, and only to supply the local trade at Meeker. The county has

not yet been entered by any railway line, and the population is small. The coal field is the extension northward of the important Glenwood field and has been described in previous volumes of the Mineral Resources.

Coal product of Colorado from 1864 to 1890, inclusive.

Years.	Localities.	Product.
		<i>Short tons.</i>
1864.....	Jefferson and Boulder counties	500
1865.....	do	1,200
1866.....	do	6,400
1867.....	do	17,000
1868.....	do	10,500
1869.....	do	8,000
1870.....	do	13,500
1871.....	do	15,600
1872.....	do	14,200
	Weld county	54,340
1873.....	Jefferson and Boulder counties	14,000
	Weld county	43,790
	Las Animas and Fremont counties	12,187
1874.....	Jefferson and Boulder counties	15,000
	Weld county	44,280
	Las Animas and Fremont counties	18,092
1875.....	Jefferson and Boulder counties	23,700
	Weld county	59,860
	Las Animas and Fremont counties	15,278
1876.....	Jefferson and Boulder counties	28,750
	Weld county	68,600
	Las Animas and Fremont counties	20,316
1877.....		117,666
1878.....	Northern division	87,825
	Central division	73,137
	Southern division	39,668
1879.....	Northern division	182,630
	Central division	70,647
	Southern division	69,455
1880.....	Northern division	123,518
	Central division	136,020
	Southern division	126,403
	Northwestern division	1,064
	Unreported mines	50,000
1881.....	Northern division	156,126
	Central division	174,882
	Southern division	269,045
	Northwestern division	6,691
	Unreported mines	100,000
1882.....	Northern division	300,000
	Central division	243,694
	Southern division	474,285
	Northwestern division	43,500
1883.....	Northern division	243,903
	Central division	396,401
	Southern division	501,307
	Northwestern division	87,982
1884.....	Northern division	253,282
	Central division	296,188
	Southern division	483,865
	Northwestern division	96,689
1885.....	Northern division	242,846
	Central division	416,373
	Southern division	571,684
	Southwestern division	125,159
1886.....	Northern division	260,145
	Central division	408,857
	Southern division	557,785
	Southwestern division	161,551

Coal product of Colorado from 1864 to 1890, inclusive—Continued.

Years.	Localities.	Product.
		<i>Short tons.</i>
1887.....	Northern division	364, 619
	Central division	491, 764
	Southern division	602, 230
	Western division	273, 122
		1, 791, 735
1888.....	Northern division	353, 909
	Central division	529, 891
	Southern division	899, 690
	Western division	401, 987
		2, 185, 477
1889.....	Northern division	364, 928
	Central division	370, 324
	Southern division	1, 362, 222
	Western division	499, 707
		2, 597, 181
1890.....	Northern division	486, 010
	Central division	473, 329
	Southern division	1, 626, 493
	Western division	491, 171
		3, 077, 003

GEORGIA.

Total product in 1889, 225,934 short tons; spot value, \$338,901. Total product in 1890, 228,337 short tons; spot value, \$238,315.

The coal-producing district of Georgia lies in the extreme north western portion of the State and along the eastern border of the Appalachian coal field. The production up to the close of 1890 has been limited to Dade county, but during that year active development work was carried on in Walker county, and the company controlling the property reports that it expects to be in operation in 1891.

The Dade county mines operate very steadily, reporting for 1890, three hundred and thirteen days mining, and employing 425 men. The following tables show the production of Georgia for 1889 and 1890 with the value and distribution of the product.

Coal product of Georgia in 1889 and 1890 by counties.

Years.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
1889.....	<i>Short tons.</i> 46, 131	<i>Short tons.</i> 158	<i>Short tons.</i> 15, 000	<i>Short tons.</i> 164, 645	<i>Short tons.</i> 225, 934	\$338, 901
1890.....	57, 949	170, 388	228, 337	238, 315	313	425

Coal product of Georgia from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	150, 000	1888	180, 000
1885	150, 000	1889	225, 934
1886	223, 000	1890	228, 337
1887	313, 715		

IDAHO.

In the 1888 volume of Mineral Resources, Idaho is credited with a coal product of 400 short tons, valued at \$1,800. The census investigation of 1889, however, failed to discover any producing mines in that year, and no product has been reported in 1890. There have been some coal discoveries in the State, but Mr. F. F. Chisolm, who has visited the localities to investigate the subject, reports the coal of so poor a quality that it will not bear competition with other coals brought into the State, nor with the wood which is plentiful in the same localities.

ILLINOIS. (a)

Total product in 1889, 12,104,272 short tons; spot value, \$11,755,203. Total product in 1890, 15,292,420 short tons; spot value, \$14,171,230.

According to the census report on the production of coal in Illinois for 1889, the number of tons produced was 12,104,272. Col. Lord, for the same period, gives the product as 11,597,963 short tons. The difference is but little more than 4 per cent., and serves to show the value and practically correct work of the state bureau of statistics. In the accompanying tables of production the figures for 1889 are taken from the published reports of the Census Office, while those for other years and in the comparative tables in which the product for 1889 is contained, Col. Lord's figures are adhered to. The following table shows the product for 1889, with the distribution and value:

Coal product of Illinois for 1889, by counties.

Counties.	Disposition of total product.					Total product of coal of all grades for 1889.	Total amount received for coal sold in 1889.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.		
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Adams		294				294	\$730
Bond	50,510	9,000	413	3,000		62,923	58,783
Brown		60				60	90
Bureau	270,535	44,103	790	27,145		342,573	441,360
Calhoun		967	14			981	1,226
Cass	33	3,114	40	186		3,373	5,702
Christian	109,361	19,452	1,150	6,686		136,658	106,745
Clinton	136,417	6,850	1,062	11,711		156,040	128,957
Crawford		100	10			110	220
Effingham		770	5			775	1,170
Franklin		700				700	1,050
Fulton	382,618	67,743	4,070	11,952		466,383	503,912
Gallatin	40,008	2,455	232	448	11,200	54,343	38,732
Greene	1,880	12,912	169	8		14,969	24,436
Grundy	524,412	23,083	6,148	952		554,595	778,752

a Statistics for 1890, compiled from the annual report of Col. J. S. Lord, secretary of the bureau of labor statistics of the State of Illinois.

Coal product of Illinois for 1889, by counties—Continued.

Counties.	Disposition of total product.					Total product of coal of all grades for 1889.	Total amount received for coalsold in 1889.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.		
	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.	
Hamilton.....		450				450	\$675
Hancock.....		5,170	79			5,249	8,025
Hardin.....		40				40	50
Henry.....	70,383	37,727	1,276	3,156		112,542	159,978
Jackson.....	453,176	37,496	5,939	17,023		513,634	474,933
Jasper.....		100				100	200
Jefferson.....		1,775	55	120		1,950	2,925
Jersey.....		1,086	17	1		1,104	1,669
Johnson.....	3,000	410	100			3,510	3,020
Kankakee.....	51,331	2,285	900	770		55,286	78,588
Knox.....		46,150	629	20		46,799	58,546
La Salle.....	749,782	176,603	15,563	30,184	1,700	973,832	1,118,631
Livingston.....	276,557	49,029	3,511	8,992		338,089	376,747
Logan.....	105,688	35,317	9,337	4,260		154,602	174,531
McDonough.....		26,603	1,197	1,876		96,336	154,549
McLean.....	117,897	40,157	3,530	7,550		169,134	216,535
Macon.....	103,420	92,365	390	375		196,550	229,131
Macoupin.....	1,237,656	51,164	6,072	44,220		1,339,112	973,487
Madison.....	468,689	75,900	3,924	28,483		576,996	438,361
Marion.....	198,582	10,995	2,967	8,275		220,819	176,982
Marshall.....	35,855	10,130	977	4,800		51,762	63,890
Menard.....	202,603	42,873	1,024	8,550		255,050	238,861
Mercer.....	232,969	19,955	2,861	6,383		262,173	295,132
Montgomery.....	19,078	12,930	40	1,200		33,248	33,479
Morgan.....		19,805	323	428		20,556	30,963
Peoria.....	446,371	128,709	4,482	9,238		588,800	597,449
Perry.....	436,288	22,983	6,144	27,140		492,555	400,126
Pike.....		85	17			102	198
Randolph.....	93,022	16,409	612	1,322		111,365	86,446
Richland.....		113	27			140	280
Rock Island.....	13,324	43,922	601	1,280		59,127	79,023
St. Clair.....	1,099,564	125,289	1,904	42,629		1,269,366	840,393
Saline.....	29,032	6,505	708	850		37,095	32,724
Sangamon.....	722,234	134,112	9,289	29,068		894,703	783,279
Schuyler.....	19,656	4,280	59	5,699		29,694	25,963
Scott.....	13,000	3,090	547	102		16,739	25,203
Shelby.....		11,703	47			11,750	20,155
Stark.....	200	21,203	159	6		21,568	31,310
Tazewell.....	50,906	14,806	582	1,725		68,019	74,173
Vermilion.....	494,915	88,917	2,185	7,191		593,208	606,598
Warren.....		15,992	101	11		16,104	30,378
Washington.....	26,183	7,031	136	1,567		34,917	32,538
Will.....	276,568	5,960	5,590	13,520		301,638	353,433
Williamson.....	175,139	12,253	1,087	4,680		193,159	138,797
Woodford.....	79,381	43,018	2,124	11,000		140,523	194,934
Total.....	9,884,883	1,699,478	111,224	395,787	12,900	12,104,272	11,755,203

The product of lump coal in Illinois in 1890 was 12,638,364 short tons, valued at \$12,882,936. Col. Lord estimates that in order to obtain the entire product of all grades of coal—which shall include nut, pea, and slack—the above tonnage should be increased about 21 per cent and the value about 10 per cent. Following this suggestion the total product of all grades for 1890 (corresponding with the statistics for 1889) is found to be 15,292,420 short tons valued at \$14,171,230.

The foregoing figures exhibit an increase in the product of 1890 over

1889 of 3,188,148 short tons, and in value of \$2,416,027. According to Colonel Lord's statements the value of lump coal per ton at the mines decreased from \$1.08 in 1889 to \$1.02 in 1890. The average value of the total product of all grades decreased from 97 cents per ton in 1889 to 93 cents per ton in 1890.

The number of employes reported by the census office in 1889 was 23,934; Colonel Lord's report for the year gives 30,076. This variance is readily accounted for by a corresponding difference in the number of days worked. The average number of days actually made by the 23,934 men reported by the census office was 214. Colonel Lord reports the average number of days the *collieries were active* as 211.5. The miners however will work only about four days in five, which would reduce this average to about 175 days per man, or an equivalent average, number of men considered, to that given by the Census Office.

Number and classification of mines.—The number of mines in Illinois reported by the census for 1889 was 1,072, of which 358 are given as commercial operations and 714 as local banks. The State report gives an aggregate of 854 openings in 1889, and 936 in 1890. Analyzing the character of these on the basis of their output for 1890 and by districts, the following results are obtained:

Classification of Illinois coal mines by output and districts.

Districts.	Number of mines producing—				Total number of mines of all kinds.
	Less than 1,000 tons.	From 1,000 to 10,000 tons.	From 10,000 to 50,000 tons.	Over 50,000 tons.	
First	18	20	22	19	79
Second	149	86	14	5	254
Third	115	108	37	13	273
Fourth	48	36	27	26	137
Fifth	68	51	55	19	193
Total.....	398	301	155	82	936

This illustrates the relative importance of the mines in the several districts as they have been found and reported for the past year. An opportunity to compare this with classifications of a similar kind made for a series of years, is presented in the following table:

Classification of Illinois coal mines by annual output for eight years.

Years.	Number of mines producing—				Total number of mines.
	Less than 1,000 tons.	From 1,000 to 10,000 tons.	From 10,000 to 50,000 tons.	Over 50,000 tons.	
1883	209	233	135	62	639
1884	262	273	146	60	741
1885	286	290	139	63	778
1886	316	280	136	57	789
1887	320	278	139	64	801
1888	327	271	152	72	822
1889	321	316	139	78	854
1890	398	301	155	82	936

The principal increase in the number of openings reported for 1890 is shown to have been in the least important class, though in the two higher classes there is a notable increase in the number of mines. The identity of these new mines, the place, character, and output of each may be established by reference to the subsequent county tables. The relative product of these groups of mines in short tons and for the past four years, as shown in the following table, will still further illustrate their relative importance:

Relative production by the several classes of mines for four years.

Years.	Mines producing more than 50,000 tons.		Mines producing from 10,000 to 50,000 tons.		Mines producing less than 10,000 tons.		Total.	
	Number.	Short tons.	Number.	Short tons.	Number.	Short tons.	Number.	Short tons.
1887.....	64	5,949,894	139	3,270,681	598	1,058,315	801	10,278,890
1888.....	72	7,188,507	152	3,666,324	598	1,000,357	822	11,855,188
1889.....	78	7,235,577	139	3,210,920	637	1,151,466	854	11,597,963
1890.....	82	8,011,787	155	3,488,601	699	1,137,976	936	12,638,364

The output for 1890.—Notwithstanding the strike which prevailed in the first and second districts during the earlier months of the year the aggregate product of the State has been considerably larger than ever before. The total for 1890 is 12,638,364 short tons of lump coal as against 11,597,963 short tons the preceding year. The absolute gain has been 1,040,401 short tons of lump coal, or 9 per cent. of the output of 1889. The following groups of totals show in what districts the gains and losses have been made:

Comparative coal product in Illinois in 1889 and 1890, by districts.

Districts.	1889.	1890.	Gain.	Loss.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
First	2,530,453	2,303,326	227,127
Second	1,087,848	1,002,600	85,248
Third	2,050,349	2,375,970	325,621
Fourth	3,164,835	3,716,464	551,629
Fifth	2,764,478	3,240,004	475,526
The State.....	11,597,963	12,638,364	1,040,401	312,375

From this it appears that the gain in the central and southern field has been greatly in excess of the losses sustained in the northern field by reason of the strike. This does not cover the whole case, however, as the same suspension also influenced the product of 1889. There was no work done in the disaffected districts during May or June of that year and but little for several months before; meanwhile there was no intermission of operations in other parts of the State. Thus the fiscal year of 1889 also showed a falling off in the tonnage of the northern field and an increase in that of the central and southern. The gains in one quarter, however, were not enough in that year to make up for the

losses in the other, and the net decline in product for the State was 257,225 tons. Taking the results of the two years in combination there was a falling off of product in the northern field of 694,452 tons in 1889 and of 312,375 tons in 1890, or 1,006,827 tons in all, while in the central and southern districts there was an increase of 437,227 tons in 1889 and of 1,352,776 tons in 1890, or of 1,790,003 tons in all. The difference between these totals, 783,176 tons, represents the net increase in the tonnage of the State during the last two years, or since 1888, notwithstanding the serious interruption of business and consequent impairment of output which resulted from the six months of controversy about wages. These facts afford rather strong evidence of the material progress of the industry and incidently point to a possible though gradual shifting of the center of greatest activity from the northern to the central coal field.

Total product of lump coal in Illinois for ten years.

Years.	Short tons.	Years.	Short tons.
1880	6, 115, 377	1886	9, 216, 435
1882	9, 115, 653	1887	10, 278, 890
1883	10, 030, 991	1888	11, 855, 188
1884	10, 101, 005	1889	11, 597, 963
1885	9, 791, 874	1890	12, 638, 364

For the year 1882 and for each subsequent year these statistics have been compiled by the Illinois State bureau; the figures given above for 1880 are those published by the Tenth United States Census. The results for 1881 are omitted from this table for the reason that no State report on this subject was made prior to 1882.

The conspicuous feature of this showing is the fact that the output of coal in this State has more than doubled during ten years. It is observable, however, that the increase has not been uniform from year to year, but that from 1883 to 1887 there was a decline in tonnage, followed by material gains in more recent years.

Although the mining of coal has been carried on to greater or less extent in fifty-seven counties in the State during the last year, the greater portion of the total product has been derived from comparatively few of them. The relative rank of the ten counties from which the greatest quantities have been mined is indicated as follows:

Product of coal in the ten principal counties of Illinois in 1890.

Rank.	Counties.	Short tons.	Rank.	Counties.	Short tons.
1	Macoupin	1, 369, 919	6	Grundy	654, 017
2	St. Clair	1, 332, 978	7	Madison	646, 228
3	La Salle	926, 214	8	Jackson	580, 521
4	Sangamon	879, 888	9	Perry	497, 768
5	Vermillion	704, 509	10	Peoria	482, 725

The amount of coal derived from these ten counties was 8,074,767 short tons, or about two-thirds of all the coal produced in the State.

Following is a statement of the output of each county for a series of four years, with the gain and loss in each county during 1890:

Comparative coal product of Illinois in 1887, 1888, 1889, and 1890.

Districts.	Output.				1890 compared with 1889.	
	1887.	1888.	1889.	1890.	Gain.	Loss.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
First district	2,686,829	2,877,794	2,530,453	2,303,326	227,127
Counties:						
Grundy	792,954	862,866	698,033	654,017	44,016
Kankakee	97,000	82,000	67,380	62,460	4,920
La Salle	1,125,235	1,090,435	1,039,703	926,214	113,489
Livingston	387,600	495,388	382,965	372,504	10,461
Will	284,040	347,105	342,372	288,131	54,241
Second district	1,069,027	1,293,187	1,087,848	1,002,600	71,059	156,307
Counties:						
Bureau	429,580	635,097	493,730	372,701	121,029
Hancock	6,203	6,515	6,028	6,948	920
Henry	117,533	108,831	101,716	98,734	2,982
Knox	64,324	57,043	57,588	51,653	5,935
Marshall	78,928	87,013	59,784	56,574	3,210
McDonough	110,102	104,274	98,386	83,401	14,985
Mercer	127,708	167,931	175,690	238,290	62,600
Rock Island	85,282	57,872	47,363	39,606	7,667
Schuyler	22,686	34,403	16,243	21,836	5,593
Stark	17,865	18,690	19,171	18,672	499
Warren	13,810	15,518	12,149	14,095	1,946
Third district	1,781,395	2,192,121	2,050,349	2,375,970	365,497	39,876
Counties:						
Cass	2,325	7,300	4,414	4,650	236
Fulton	337,215	461,589	366,577	404,417	37,840
Logan	159,000	174,330	138,700	164,650	25,950
McLean	141,700	117,110	129,322	173,492	44,170
Menard	155,621	181,075	181,621	230,662	49,041
Peoria	452,123	533,817	454,731	482,725	27,994
Tazewell	51,847	59,324	67,973	81,141	13,168
Vermilion	359,119	499,076	537,411	704,509	167,098
Woodford	122,445	158,500	169,600	129,724	39,876
Fourth district	2,568,291	2,854,540	3,164,835	3,716,464	613,222	61,593
Counties:						
Bond	36,076	38,200	59,724	66,746	7,022
Calhoun	1,036	1,078	1,468	390
Christian	149,973	147,030	249,774	439,451	189,677
Coles	34,612	27,210
Efingham	796	796
Greene	12,578	14,494	19,048	11,714	7,334
Jasper	152	152
Jersey	2,684	3,949	4,040	7,500	3,460
Macon	118,183	230,805	233,309	179,050	54,259
Macoupin	926,588	1,016,624	1,202,187	1,369,919	167,732
Madison	521,705	512,948	490,181	646,228	156,047
Montgomery	10,220	14,295	24,425	58,617	34,192
Morgan	6,669	12,545	13,019	16,601	3,582
Pike	135	135
Richland	154	154
Sangamon	730,391	764,970	846,012	879,888	33,876
Scott	9,802	12,491	15,028	20,022	4,994
Shelby	8,810	7,943	7,010	18,023	11,013
Fifth district	2,173,348	2,637,546	2,764,478	3,240,004	522,512	46,986
Counties:						
Clinton	55,238	66,463	121,557	170,416	48,859
Franklin	700	700
Gallatin	31,437	45,374	30,044	52,383	22,339
Hardin	40	40
Hamilton	450	450
Johnson	28,000	28,210	3,000	12,110	9,110
Jackson	375,718	445,575	477,474	580,521	103,047

Comparative coal product of Illinois in 1887, 1888, 1889, and 1890—Continued.

Districts.	Output.				1890 compared with 1889.	
	1887.	1888.	1889.	1890.	Gain.	Loss.
Counties—Continued:	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Jefferson				2,100	2,100	
Marion	98,915	156,975	180,777	218,499	37,722	
Perry	319,552	306,235	381,347	497,768	116,421	
Randolph.....	74,263	167,321	98,202	134,699	36,497	
Saline	19,518	32,350	35,496	45,845	10,349	
St. Clair	1,018,119	1,184,579	1,198,100	1,332,978	134,878	
Washington	40,220	43,600	36,220	25,160		11,060
Williamson	112,338	160,664	202,261	166,335		35,926
State totals	10,278,890	11,855,188	11,597,963	12,638,364	(a)1,040,401	

a Net increase.

Number of employes.—Contrary to all precedent the number of miners and others employed at coal mines, as reported for 1890, according to Colonel Lord's report, has not increased with the larger output of coal, but has materially fallen short of the number reported by him for 1889, but it does show an increase of 4,640 over the number of employes reported by the Census Office for 1889. The following figures show the number of employes reported by Colonel Lord for each of ten years:

Employes in Illinois coal mines for ten years.

Years.	Miners.	Others.	Total.
1880			16,301
1882			20,290
1883	20,839	3,100	23,939
1884	20,610	4,965	25,575
1885	20,772	5,174	25,946
1886	20,973	4,873	25,846
1887	21,153	5,646	26,804
1888	23,649	5,762	29,410
1889	23,583	6,493	30,076
1890	20,106	8,468	28,574

These totals are not the result of an enumeration of the employes at the several mines at any particular time, but are made up from the numbers reported to the inspector by each proprietor as the average number employed during the winter months. This is readily obtained from monthly pay rolls, and though the result is necessarily somewhat less than exact as to individuals, there is no reason to doubt the substantial correctness of the numbers thus reported.

It will be observed, however, that heretofore there has been a uniform increase in the number of employes corresponding in general with the increase in product; whereas for 1890, with an increase of 9 per cent. in tonnage, there is a decrease of 5 per cent. in the number of men employed. An examination of the returns by districts shows that this falling off is chiefly in the first and second districts, where the recent long strike prevailed, and from which there was a general exodus of miners at that time. In the third and fourth districts the working

force has remained about stationary, though the output has been larger than ever, while in the fifth district there has been an increase in product and a decrease of 7 per cent. in the number of men.

Days of active operations.—There has necessarily been some impairment of the time actually devoted to the product of 1890, owing to the entire suspension of operations for a portion of the year in one important field. The experience of the mines in the various districts for the present and two preceding years is given below.

Number of operating days in Illinois coal mines for 1888, 1889, and 1890.

Districts.	1888.	1889.	1890.
First	216	188	178
Second	219	198	182
Third	219	203	193
Fourth	230	240.3	243
Fifth	219	235	232
The State	220.6	211.5	203.5

The mines which are enumerated in this classification are those which are supposed to have operated continuously throughout the year, so far as the demand for coal justified it, and do not embrace those which are worked through the winter months only. The average running time of all mines is found to have been 203.5 days in 1890, as against 211.5 days in 1889, and 220.6 days in 1888. The falling off is observed to have taken place in the first three districts, while the average for the others has increased.

Average value of coal at the mines.—The customary computation of average worth of coal at the mine, based upon the figures given to the inspectors by the proprietors of mines, has been made for 1889 and 1890, and the results are presented herewith in comparison with similar results for a series of years:

Average value of Illinois coal per ton at the mines during eight years.

Districts.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
First	1.75	1.59	1.49	1.41	1.32	1.32	1.37	1.36	1.30
Second	1.87	1.97	1.79	1.71	1.57	1.50	1.47	1.43	1.48
Third	1.43	1.45	1.31	1.25	1.16	1.10	1.14	1.10	1.06
Fourth	1.33	1.32	1.09	.985	.97	.89	.95	.97	.87
Fifth	1.31	1.26	.96	.894	.86	.82	.86	.88	.81
The State	1.51	1.48	1.26	1.17	1.10	1.09	1.12	1.08	1.02

The fluctuations in the average value of coal are here shown for a series of years and for each district and the State. The averages as computed for the State present a uniform decline from year to year, save a slight exception in 1888, and the total falling off in value since 1882 is 50 cents a ton, or 33½ per cent. One-half of this depreciation, however, occurred in the first three years, and one-half of the remainder

in the two years following. The further decline from \$1.10 to \$1.02 has been more gradual and the result of four years depression of prices. Referring to the experience of the various districts it is noticeable that the average for the State has been depressed during the past year, almost wholly by the decline in prices in the fourth and fifth districts, in the former of which the average value has fallen off 9.2 cents, and the latter 5.6 cents a ton.

Prices paid for mining by hand.—An examination of the following table shows the movement in the rate of wages which has characterized coal mining in this State during a series of eight years:

Average prices paid per ton for hand-mining, from 1883 to 1890.

Districts.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
First.....	\$0.917	\$0.906	\$0.867	\$0.859	\$0.891	\$0.889	\$0.892	\$0.812
Second.....	.983	1.00	.941	.927	.927	.918	.924	.892
Third.....	.875	.873	.814	.729	.688	.706	.699	.680
Fourth.....	.71	.694	.62	.573	.576	.614	.599	.584
Fifth.....	.619	.60	.511	.501	.537	.554	.525	.511
The State.....	0.802	0.783	0.725	0.676	0.727	0.717	0.731	0.683

The foregoing averages have been computed every year for eight years by the proper combination of the number of tons mined at each specific rate, with the various rates paid and with due allowance for the difference, where any is found, between the rates paid in summer and in winter. They are, therefore, mathematically true as averages though not identical with the price paid at any particular place. The object of the table like that concerning the average value of product is to present an illustration of the tendency, both of values and wages, in specific terms, from year to year, for the various mining districts and the State as a whole.

The decline in the average rate of wages in this State during eight years is represented by the difference between 80.2 cents and 68.3 cents per ton, or 11.9 cents, or 14.8 per cent. It is observed, however, that during the years from 1885 to 1889, the variation from year to year was inconsiderable and without definite tendency, but that from 1883 to 1885 there was a drop of about 7 cents a ton, and during the last year an average decline of 5 cents. The latter is clearly due to the reduction of 7½ cents a ton, which was imposed in certain districts as a result of the strike of the past year. The average for the year following, or the current year (1891), during which the old rate of wages in the same field has been restored, should consequently be higher. The specific fluctuations in the various districts during the past year and seven preceding years may be observed in the table. The average decline in the first district is 7.96 cents, and in the second, only a part of which was affected by the strike, 3.24 cents, while in each of the other districts the variation is very small, though uniformly a decline.

Mining with machines.—The amount of coal undercut with machines during the year has been somewhat larger than in any previous year, and the number of machines in use has been greater than in the preceding year, though less than in the year 1888. The number of mines in which this method has been practiced has not increased, though the machines have been abandoned in some mines and introduced in others. The statistics for the last three years are as follows:

Statistics of machine mining in Illinois for three years.

Years.	Number of mines.	Number of machines.	Number of tons cut.	Per cent. of total product.	Number of men employed.	Per cent. of total men.
1888.....	39	272	2,243,810	18.9	3,088	10.5
1889.....	35	235	2,346,713	20.2	3,439	11.4
1890.....	34	266	2,881,983	22.8	3,141	10.9

The mines reported here are all those in which machines have been used at all, and is not confined to those in which they are used exclusively. The inference from these figures is that while the use of machines has not become more general, the number has been increased in mines where they have given satisfactory results.

The fields in which the machine process is most general are indicated by the following statement of the number of tons mined by this method in each of the several districts in 1890. With these figures are combined the number and the names of the machines used:

Product by machine mining and number and names of machines used.

Districts.	Total tons produced.	Number and kinds of machines used.							Total machines.	Number of men employed.
		Harri-son.	Chou-teau.	Inger-soll.	Kang-ley.	Legg.	Sperry.	Yock.		
First	89,414	14	5	4	4	27	224
Second.....	20,000	12	12	80
Third.....	55,854	6	6	50
Fourth	1,615,453	128	17	4	3	152	1,614
Fifth	1,101,262	54	9	6	69	1,173
Total	2,881,983	214	26	4	5	7	4	6	266	3,141

As compared with the preceding year, these figures show an increase of machine product of 241,580 tons in the fourth district and of 295,459 tons in the fifth district, with but slight changes in the others. Several new machines have made their appearance during the year, known severally as the Ingersoll, Kangley, and Sperry, and the number of Chouteau machines, which have recently been introduced, has increased from 14 to 26.

The rates of wages paid to men employed in operating machines have not materially changed during the last three years, as appears in the following group of average daily wages:

Wages paid machine operators for three years in Illinois.

Occupation.	1888.	1889.	1890.
Cutters.....	\$2.33	\$2.34	\$2.29
Helpers.....	1.70	1.78	1.77
Blasters.....	2.07	2.09	2.07
Loaders.....	1.79	1.80	1.78
Timberers.....	2.02	2.07	2.04
Laborers.....	1.61	1.66	1.73
Drillers.....	2.00	2.00

Casualties in 1890.—The number of accidents, fatal and otherwise, which have befallen employés about mines during 1890 was somewhat greater than in the year preceding. The increase in killed was 11, or from 42 to 53, and the increase in injured 93, or from 201 to 294. The statistics of the killed and hurt in the mines of the State for eight years are as follows:

Casualties in Illinois coal mines compared with annual production for eight years.

Years.	Number killed.	Number injured.	Total number of men employed.	Total number of tons of coal produced.	Total casualties.		Non-fatal casualties.	
					Number of employés to each life lost.	Number of tons of coal produced to each life lost.	Number of employés to each accident.	Number of tons of coal produced to each accident.
1883.....	134	231	23,939	10,030,991	179.6	74,858	103.6	43,424
1884.....	46	197	25,575	10,101,005	556	219,587	125.8	51,274
1885.....	39	176	25,446	9,791,874	652.4	251,074	144.6	55,634
1886.....	52	169	25,846	9,246,435	497	177,816	153.5	54,713
1887.....	41	180	26,804	10,278,890	654	244,735	149	57,105
1888.....	55	179	29,410	11,855,188	534.7	215,549	164.3	66,241
1889.....	42	201	30,076	11,597,963	716.1	276,142	149.6	57,701
1890.....	53	294	28,574	12,638,364	539.1	238,459	97.2	42,987
Totals....	462	1,627	215,670	85,540,710
Averages.	57.7	203.3	26,958	10,692,589	466.8	185,153	132.5	52,575

INDIANA.

Total product in 1889, 2,845,057 short tons; spot value, \$2,887,852. Total product in 1890, 3,305,737 short tons; spot value, \$3,259,233.

The coal product of Indiana in 1888 was 76,732 short tons less than 1887. This decrease was attributed principally to the increasing consumption of natural gas in Indianapolis and other cities of the State and to the consumption of oil as a fuel in Chicago. In Mineral Resources of 1888 it was stated that if the use of natural gas throughout the State, and of oil in Chicago materially increased, the production of Indiana coal would proportionately decrease. The prophecy seems to have been fulfilled, for in 1889 the production of Indiana coal decreased 295,922 tons from that of 1888, with a much greater difference in the value, namely, \$1,509,518. In other words, the average price per ton fell from \$1.40 in 1888 to \$1.02 in 1889. Whether this great difference

is altogether due to the above-mentioned causes may be doubted. It is probable that the market was considerably affected by the weather. Bituminous coal is the principal fuel in the State, and like the anthracite coal in the East, depends greatly on the ruling temperature.

In 1890 the coal operators of the State made a determined effort to restore production of Indiana coal to its former importance. This could only be accomplished by a reduction of wages and prices. The necessary reduction was made and the average price realized for coal during the year was less than \$1 per ton. The result, however, was satisfactory so far as increased output was concerned, for the product for the year was over 450,000 tons greater than the previous one and 88,826 tons more than in 1887, before the demoralizing effect of gas and oil had been felt.

The following tables exhibit the amount and value of the coal produced in Indiana in 1889 and 1890, by counties, with the distribution of the product:

Coal product of Indiana in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Clay	647, 442	31, 650	16, 357	695, 649	\$795, 140	2, 592
Daviess	176, 244	12, 419	2, 922	191, 585	195, 793	455
Dubois	5, 917	9, 531	400	15, 848	18, 500	41
Fountain	38, 485	2, 291	365	41, 141	53, 218	85
Gibson	128	1, 099	40	1, 267	1, 941	7
Greene	175, 753	3, 231	6, 865	185, 849	169, 595	296
Knox	7, 200	1, 840	9, 040	10, 405	22
Martin	710	710	887
Owen	225	3, 703	30	3, 958	4, 292	17
Parke	344, 658	6, 400	6, 376	357, 434	377, 324	591
Perry	27, 186	12, 284	580	40, 050	47, 175	109
Pike	138, 380	8, 487	2, 857	4, 800	154, 524	128, 867	340
Spencer	14, 934	3, 122	400	18, 456	21, 207	29
Sullivan	271, 977	21, 912	15, 363	8, 000	317, 252	299, 286	556
Vanderburg	89, 820	87, 594	6, 528	183, 942	212, 572	318
Vernillion	178, 925	6, 426	2, 300	187, 651	167, 590	276
Vigo	353, 685	13, 318	4, 900	371, 903	330, 205	629
Warren	2, 160	2, 160	3, 555
Warriek	56, 153	9, 758	727	66, 638	50, 300	85
Total	2, 527, 112	237, 935	67, 210	12, 800	2, 845, 057	2, 887, 852	6, 448

Coal product of Indiana in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Clay	1, 129, 638	25, 911	6, 181	1, 161, 730	\$1, 177, 666	218	2, 179
Daviess	188, 604	1, 092	189, 696	197, 696	231	280
Dubois	13, 494	300	200	13, 994	16, 056	216	40
Fountain	23, 300	100	600	24, 000	24, 000	260	48
Gibson (a)
Greene	174, 988	22, 000	350	197, 338	180, 294	218	250
Knox (a)
Owen (a)
Perry	33, 501	6, 100	600	40, 201	42, 201	250	100
Parke	343, 960	1, 500	345, 460	378, 033	254	558
Pike	109, 706	400	3, 600	2, 130	115, 836	113, 000	170	235
Spencer	11, 256	50	350	11, 656	11, 116	261	39
Sullivan	255, 466	11, 983	11, 874	7, 000	286, 323	268, 525	181	588
Vigo	423, 460	4, 488	1, 212	429, 160	341, 998	262	454
Vanderburgh	77, 633.	106, 071	8, 580	192, 284	197, 224	244	307
Vermillion	171, 500	1, 000	500	173, 000	203, 000	161	280
Warrick	80, 231	8, 172	656	89, 059	66, 424	222	131
Small mines	36, 000	36, 000	36, 000
Total	3, 036, 737	225, 167	34, 703	9, 130	3, 305, 737	3, 259, 233	(b) 220	5, 489

a The entire product of Gibson, Knox, and Owen counties is from country banks and is included in the total estimated product of small mines.

b Average for the State.

Product of coal in Indiana from 1873 to 1890.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
1873.....	1, 000, 000	1879.....	1, 196, 490	1885.....	2, 375, 000
1874.....	812, 000	1880.....	1, 500, 000	1886.....	3, 000, 000
1875.....	809, 000	1881.....	1, 771, 536	1887.....	3, 217, 711
1876.....	950, 000	1882.....	1, 976, 370	1888.....	3, 140, 979
1877.....	1, 000, 000	1883.....	2, 560, 000	1889.....	2, 845, 057
1878.....	1, 000, 000	1884.....	2, 260, 000	1890.....	3, 305, 737

INDIAN TERRITORY.

Total product in 1889, 752,832 short tons; spot value, \$1,323,807. Total product in 1890, 869,229 short tons; spot value, \$1,579,188.

All of the producing mines in the Indian Territory are in the Choctaw Nation Reservation. Until 1889 the Missouri, Kansas and Texas railroad was the only means of reaching a market, and all the mines were along the line of the road or reached by spurs built from it. In 1889, however, the Choctaw Coal and Railway Company, building through the Territory, secured valuable rights from the Indians for mining coal, and have made considerable progress in the development of mines at Hartshorne, about 18 miles from where the Choctaw Railroad crosses the Missouri, Kansas and Texas, at South McAlester. The following description of the Choctaw coal fields, by Mr. H. M. Chance, was read before the February (1890) meeting of the American Institute of Mining Engineers in Washington:

Geology of the Choctaw coal field.—“The Choctaw coal field is a direct westward extension of the Arkansas coal field, but its coals are not like Arkansas coals, except in the country immediately adjoining the Arkansas line.

“From the base of the coal-bearing rocks up to the top of the Coal Measures the writer finds a total thickness of at least 8,500 feet. This great mass of coal-bearing rocks consists of an alternation of slates, shales, sandstones, and coal beds, with their accompanying underbeds of fire clay. Only one small bed of limestone was observed. This occurs near the middle of the series; it is about 18 inches thick and quite arenaceous. The formation is naturally subdivided by seven or eight thick beds of sandstone, varying from 50 to 200 feet in thickness, the out-cropping edges of which form a series of more or less bold ‘hog-back’ ridges, the interbedded shales and slates forming the intervening valleys.

“The base of the coal series is a massive sandstone, ranging from 100 to 200 feet or more in thickness, lying immediately beneath the Grady coal bed, which is the lowest known coal. In the district embraced between the Missouri, Kansas and Texas railroad and the Arkansas State line, this sand rock usually forms a bold semi-mountainous ridge.

“This is the ridge through which the Saint Louis and San Francisco railroad passes at Bryan station, where the Grady coal bed is opened and worked, from which point it can be traced westward without difficulty, passing about 3 miles north of Le Flor on the same railroad, thence west to the Little Narrows (which is merely a gap in the ridge), and beyond to a point 2 miles west of the Thomson-McKinney place, where it swings abruptly north for a mile or more, only to resume immediately its westward course, forming for some miles the northern boundary of the valley known as the “Boiling Springs” prairie, beyond which it trends somewhat southwest, crossing Gaines’ creek, thence west to, and south of, the Simpson place (2 or 3 miles east of the mining town of Krebs), where it abruptly turns back, running in an easterly course about 7 miles to Brushy creek, which it crosses, maintaining its eastward course for a further distance of about 6 miles, here forming the southern boundary of the Boiling Spring prairie, and the northern boundary of the Grady coal basin. From the point last reached the ridge swings around in a curve to the southwest, a distance of about 9 or 10 miles, inclosing and forming the valley and coal basin which has been named by the writer, after its discoverer, the Grady coal basin.

“In tracing this ridge eastwardly from the Bryan mine it is followed without difficulty to and beyond the Poteau river to a point about 5 miles nearly due south from Cavanal station. Here it turns abruptly back to the southwest, and swinging in a horseshoe curve to the south and southeast, incloses a basin which the writer has called the Mitchell basin, naming it likewise after its discoverer.

"The discovery of this basin furnishes a good example of the results that can, at times, be reached by the structural geologist in predicting, in advance of the actual examination of a district, what may possibly be found. Having traced this ridge to the Poteau river, and from an elevated point being able to see that it was running straight toward the Poteau mountains, some 10 or 15 miles to the east, and knowing that these mountains were formed of rocks high in the Coal Measures the writer saw at once that either a great fault must cut off these lower rocks, or that they must turn back to the west or southwest, and then, resuming their easterly course, pass south of the Poteau mountains. The first hypothesis being deemed improbable, the second was assumed to be probably true, in which case a coal basin should be found a few miles south of our camp on the Poteau river. Just as the writer was about starting in search of this basin, a courier reached camp with a message requiring my immediate return to McAlester. Upon leaving camp I gave my chief prospector (Mitchell) directions how to proceed in search of this basin, which he afterward found, without trouble, located exactly as the writer had predicted.

"A survey line, started from the ridge at Bryan and running nearly north directly across the dip to the Kavanaugh mountains, north of Kennedy's store, a distance of about 7 miles, would have the data for a cross section, from which the thickness of the Coal Measures could be obtained with accuracy.

"At Bryan the dip is about 40 degrees; at 1 mile north, about 30 degrees; at 2 miles north, about 20 degrees; and for the next 2 miles, about 15 to 20 degrees. Still farther north it gradually decreases until, under the main ridge or backbone of the Kavanaugh mountains, the rocks are flat. A section, roughly constructed from odometer measurements, gives a minimum thickness of 8,500 feet, with a possibility of 10,000 feet of coal-bearing rocks in this basin.

"Should the entire series prove of Carboniferous age the thickness here present is about twice as great as has yet been found in any State of the Union. Probably about the same thickness will be found in Arkansas, but up to the time my Indian Territory work was finished Mr. Winslow's work for the Arkansas Geological Survey had not progressed to a position warranting any definite statements as to total thickness, hence we were not able to compare results, but he already evidently anticipated the existence of a thickness far in excess of that shown in other States, and was not surprised to hear of a similar occurrence in the Indian Territory.

"The coals worked in the McAlester, Savaunah, and Lehigh districts, on the Missouri, Kansas, and Texas railroad, and at Bryan, on the St. Louis and San Francisco railroad, belong to the lower portion of this 8,500 feet, being principally beds found within 1,500 feet of the basal sand rock.

"The coals of the Kavanaugh mountains, notably the big bed at

Mayberry's mine, and those in the mountain near Poteau switch, on the St. Louis and San Francisco railroad, belong high up in the series, being found in the uppermost 1,500 feet of rock. To this series, also, probably belong the coals opened and mined in the western part of Arkansas at Jenny Lind, Hackett City, and Huntington.

"The western Arkansas coals are dry semi-bituminous or semi-anthracite coals, mostly non-coking, or with quite feeble coking properties, ranging from 14 to 16 per cent. in volatile matter, the highest percentage yet found, according to Mr. Winslow's Arkansas report, being 17.655.

"In the Mitchell basin, about 10 miles west from the Arkansas line, coal recently opened shows 19 per cent. volatile matter; the Mayberry coal, about 8 miles farther west, contains 23 per cent. volatile matter, and the Bryan mine coal, about the same distance west, shows 26 per cent. volatile matter. About 30 miles farther west the coal shows from 38 to 41½ per cent. volatile matter, which is also about the percentage in coals of the McAlester and Lehigh districts.

"The Mitchell basin coal will coke; but whether it will make marketable coke has not yet been determined. From the Bryan mine west all the coals are strong coking coals; but they contain so much gas that the yield of coke will be small, except in the district between the Bryan mine and the Little Narrows. The coals best adapted for general use are found in the district lying at and west of the Little Narrows, in the Grady basin and in the McAlester field. The Mitchell basin coal, now being prospected, also promises coal of good quality, but of semi-bituminous character. A recent analysis, made by Prof. McCreath, gives the following result:

Analysis of coal from the Mitchell basin, Indian Territory.

	Per cent.
Water.....	1.058
Volatile matter.....	19.032
Fixed carbon.....	71.736
Sulphur.....	.649
Ash.....	7.525
Total.....	100.000

"The bed from which this sample was taken is supposed to be either the Grady or McAlester bed. The opening was made since my return, and I can not locate it.

"An average of seven analyses, made by Prof. McCreath, of coal from the Grady bed, in the Grady basin, shows:

Analysis of coal from the Grady basin, Indian Territory.

	Per cent.
Water.....	1.792
Volatile matter.....	40.207
Fixed carbon.....	51.785
Sulphur.....	1.333
Ash.....	4.883
Total.....	100.000

“Two analyses of coal from the Grady bed in the McKinney (Little Narrows) district, average:

Average analysis of coal from the McKinney district, Indian Territory.

	Per cent.
Water.....	1.709
Volatile matter.....	38.668
Fixed carbon.....	51.482
Sulphur.....	1.006
Ash.....	7.135
Total.....	100.000

“One analysis of coal from the McAlester bed at Krebs (near McAlester) gave:

Analysis of coal from the McAlester bed at Krebs, Indian Territory.

	Per cent.
Water.....	1.804
Volatile matter.....	37.171
Fixed carbon.....	53.404
Sulphur.....	.896
Ash.....	6.725
Total.....	100.000

“One analysis from Lehigh mines gave:

Analysis of coal from the Lehigh mines, Indian Territory.

	Per cent.
Water.....	4.323
Volatile matter.....	40.507
Fixed carbon.....	44.472
Sulphur.....	2.598
Ash.....	8.100
Total.....	100.000

“Both the Lehigh and Bryan mines produce coal objectionably high in sulphur; and the Lehigh coal has, moreover, the high percentage of moisture so common in the coals of Kansas and Missouri. The best coal now mined in the region is that from the McAlester bed, mined at

McAlester and Krebs by the Osage Mining Company, and at Alderson by the Choctaw Coal and Railway Company, and that from the Grady bed, just opened at Hartshorne by the latter company. These coals compare favorably with the best gas coals mined in the country (as comparison with standard Pittsburg coal will show), and they are by far the best coals now mined in the Southwest, if not indeed the best mined west of the Mississippi river. They are in every way vastly superior to Kansas, Missouri, and Iowa coals.

"Topographically and structurally the Choctaw coal fields represent in miniature many of the features of the anthracite region of Pennsylvania. The measures are flexed by a series of anticlinal and synclinal folds, not usually as sharp as those of the anthracite regions, but in many respects very similar. While all the anthracite basins are surrounded by a mountainous rim, of which the outcrop of the thick and massive conglomerate forms the core, the Choctaw basins are inclosed by a ridge, sharp and bold in places, but rarely mountainous, formed by the outcrop of the basal sandstone. Whether this rock is the equivalent of the conglomerate or not is as yet wholly conjectural.

"The writer has been enabled to compile the following generalized section of the Coal Measures from measurements rudely made and at points widely separated. In a general way it will be of service to the prospector or field geologist working in other portions of this coal field:

Columnar section of the Coal Measures of Indian Territory.

	Feet.
Shales and slates with two massive sandstone ledges. This group forms the backbone of the Kavanaugh Mountains north of Kennedy's store. Whether it contains coal beds is not now known. Its thickness is estimated at.....	1,200
Mayberry coal (this appears to be the Huntington-Jenny Lind coal)....	4 to 6
Slates, sandstones, and shales, with some coal beds; none, however, known of workable size and quality; This group contains four or five massive sandstones. Its thickness is estimated at about.....	3,500
Slates with two massive sandstones (these form the top rocks in the center of the basin 4 miles southwest from Frinks switch on the M. K. and T. R. R.).....	400
Sandstone.....	50
Slate.....	100
Secor coal.....	2 ¹ / ₂
Slate.....	30
Sandstone.....	50
Slates.....	320
Sandstone (forms ridge south of South McAlester).....	200
Slates with thin coal bed.....	220
Sandstone (ridge at South McAlester).....	100
Slates with sandstones.....	200
Sandstones (ridge between McAlester and South McAlester).....	50
Slates.....	130
Norman coal.....	3
Slates with sandstone bed near top and two or three thin coals.....	600
McAlester coal.....	4
Sandstone.....	50
Slates and shales with thin coal bed.....	500
Sandstone, massive, caps Round Top and Long Mountain in the Grady basin, forms bold ridge half mile north of Alderson stations on Choctaw Coal and Railway Company's railroad. "Flat-top sandstone".....	100
Slates and shales with two thin coals in upper part.....	600
Upper Grady coal, 1 to 3 feet.....	} Grady group of coals.....
Slates or sandstone, 50 feet.....	
Middle Grady coal, 1 to 3 feet.....	
Slates or sandstone, 50 feet.....	
Grady coal, 4 to 6 feet.....	
Sandstone, massive "Tobocksy sandstone".....	200

"Below this bottom sand rock we find shales and thin-bedded sandstones forming the Foureche valley, and including the 'Limestone ridge,' which is finely seen at Limestone Gap on the Missouri, Kansas and Texas railroad, and on the south side of the valley opposite the Little Narrows. These measures and the included limestone are probably of sub-Carboniferous age.

"The Grady coal basin is a beautiful little basin, inclosed on three sides by the ridge formed by the basal sand rock (Tobocksy sandstone) and on the fourth by the Adams ridge (formed by the 'Flat-top sandstone'), with but four narrow gaps through which entrance or egress may be had. A large part of the basin is flat or gently rolling, partly prairie and partly wooded. Near the center of this basin (exactly in its geological center) are three 'mountains' rising abruptly to a height of about 200 feet, almost perfectly flat on top and capped by a hard, massive sandstone, 30 feet or more in thickness, which outcrops in bold cliffs on all sides, making access to the top both difficult and dangerous.

"The maximum depth of the Grady coal bed in this basin is about 600 feet; but over three-fourths of the basin the bed can be reached at depths less than 450 feet, and over one-half of the basin the depth will probably not exceed 300 feet. The basin is about 6 miles long by 3 or 4 wide, and contains over 11,000 acres of the Grady bed. Throughout this area the coal is not always of workable thickness; but over a large portion of it the bed will range from $3\frac{1}{2}$ to 5 feet thick, yielding an average of 4 feet of clear coal.

"The axial line of the Kavanaugh mountains is a synclinal with a gentle anticlinal roll occupying the valley of Brazil creek, and another similar roll coinciding very nearly with the course of the Poteau river from Cavalal to and beyond Poteau station. These anticlinal rolls apparently have a general course of south forty degrees west, while the main synclinals run about south seventy degrees west to south eighty degrees west. The same feature was noticed in the McAlester and Grady basin districts, and seems to indicate two distinct types of disturbances, or, what is perhaps more probable, a single flexing force, giving rise to two series of rolls along the lines of two distinct resultants.

"Whatever the cause, the existence of two series of anticlinal and synclinal folds, not parallel, but forming an angle of thirty or forty degrees, is a fact that should not be overlooked, for it has a most important bearing upon the shape of the basins, and upon the location of those minor disturbances—roll and faulted areas—an intelligent anticipation of which may often avert the loss of large sums expended in attempting to open and operate collieries located in or near such a disturbed area.

"In a general way we may expect faulted coal, rolls, and swamps at and near the intersection of any two synclinal or anticlinal axes. Thus such an area is found along Brushy creek, immediately west southwest from the Grady basin. At the southwest corner of the Grady basin

the 'butt end' of an anticlinal axis is plainly shown by the indentation of the southern rim immediately west of Hartshorne station. This axis apparently runs about south twenty degrees or twenty-five degrees west.

"In prospecting for coal in this field, the first object is, of course, to find a bed of good quality, and thick enough for profitable mining. As in the McAlester and Lehigh districts coal averaging almost 4 feet in thickness is mined, and as from 4 to 6 feet of coal is worked in the Arkansas fields, a thickness of not less than 3 feet and 6 inches is needed to place a new establishment on anything like an equal footing with these older companies.

"Cheap mining, and the production of as large a percentage of lump coal as possible, require also that the dip of the coal shall be moderate, not exceeding a pitch of about 14 or 15 degrees, so that the mine cars may be taken directly to the face of the breasts or rooms. A pitch of 6 or 8 degrees is considered most advantageous, as on such a pitch slopes work well, and the cars are readily taken up to the working face.

"When the dip is less than 6 or 8 degrees, the best method of development is by shafts.

"Hence, in searching for coal in this field, the prospector rapidly passes, as undesirable, all territory in which the rocks show a strong angle of dip, and upon reaching an area of moderate dip his search may profitably be confined to the outcrops of the three beds above named.

"The Boiling Springs prairie, and the same valley farther east, where it is known as the Fourche Melane valley, or valley of the 'Big Fourche,' is not coal territory. It is occupied by the shales associated with the limestone of 'Limestone ridge,' which are possibly of sub-Carboniferous age."

Production.—The amount and value of coal produced in Indian Territory in 1889 and 1890, with the distribution of the product, is shown in the following table:

Coal product of Indian Territory in 1889 and 1890.

Years.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
1889	699, 122	7, 095	33, 997	12, 618	752, 832	\$1, 323, 807	1, 862
1890	828, 102	6, 211	11, 292	23, 624	869, 229	1, 579, 188	238	2, 571

No record of the production of the Indian Territory coal fields was made prior to 1885. Since that date the product has been as follows:

Product of coal in the Indian Territory from 1885 to 1890, inclusive.

Years.	Short tons.	Years.	Short tons.
1885	500, 000	1888	761, 986
1886	534, 580	1889	752, 832
1887	685, 911	1890	869, 229

IOWA.

Total product in 1889, 4,095,358 short tons; spot value, \$5,426,509. Total product in 1890, 4,021,739 short tons; spot value, \$4,995,739.

The production of coal in Iowa in 1889 was 857,082 short tons less than that of 1888, and showed a decrease in value of \$1,011,663. A further decrease is noted in 1890 of 73,619 short tons in amount and \$430,770 in value.

Owing to the large number of small mines in Iowa, considerable difficulty has been experienced in obtaining the statistics of production. Many of the small operators keep no systematic records, and the statements from these mines are necessarily estimated.

The following tables show the production in 1889 and 1890 by counties, with the distribution of the product.

Coal product of Iowa in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Adams	800	12,637	20	13,457	\$27,870
Appanoose	252,881	25,837	6,476	285,194	376,473	1,044
Boone	125,858	44,479	4,030	25	174,392	324,302	653
Cass	280	280	700
Dallas	60,309	5,576	1,170	67,055	111,472
Davis	3,820	5	3,825	5,409
Greene	41,429	6,772	3,237	51,438	89,704	175
Guthrie	12,275	12,275	30,852
Hardin	490	490	1,370
Jasper	171,120	17,853	10,179	199,152	282,081	464
Jefferson	3,341	4,728	54	8,123	12,609
Keokuk	417,751	18,765	18,046	455,162	569,190	890
Lucas	318,523	10,310	10,390	339,229	416,307	704
Mabaska	992,393	42,206	21,788	1,056,477	1,222,954	1,648
Marion	124,325	19,523	1,332	145,180	185,266	349
Monroe	244,306	8,589	5,506	258,401	300,786	690
Montgomery	1,040	1,040	2,280
Page	2,766	2	2,768	6,770
Polk	284,310	138,876	10,861	434,047	687,969	1,020
Scott	9,446	9,446	15,181
Taylor	3,800	5,936	9,736	20,122
Van Buren	34,891	3,906	461	39,258	54,617	89
Wapello	331,702	22,833	4,652	12	359,109	406,445	726
Warren	4,084	9,331	200	14,515	25,819
Wayne	7,489	9,811	180	17,480	25,751
Webster	110,161	26,554	1,024	137,739	224,210	414
Total.....	3,530,373	464,735	100,213	37	4,095,358	5,426,509	9,247

Coal product of Iowa in 1890, by counties,

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Appanoose.....	252,970	25,309	6,251	284,560	\$392,053	165	1,080
Boone.....	121,783	28,833	2,613	153,229	279,192	191	465
Dallas.....	26,439	3,927	3,100	33,466	57,059	207	130
Greene.....	45,031	161	-----	45,192	73,674	209	121
Jasper.....	165,240	5,760	2,044	173,044	191,775	246	335
Jefferson and Lucas.....	350,800	800	-----	351,600	439,900	298	324
Keokuk.....	328,435	11,811	9,072	349,318	458,608	184	1,018
Mahaska.....	1,072,688	12,993	18,150	1,103,831	1,165,861	258	1,673
Marion.....	147,013	6,213	280	153,506	192,714	265	269
Monroe.....	308,959	6,711	8,361	324,031	390,969	197	735
Polk.....	216,463	142,027	9,362	367,852	547,272	243	700
Van Buren.....	42,934	3,690	840	47,464	61,180	280	108
Wapello.....	336,284	2,448	3,200	341,932	376,928	159	773
Warren.....	5,790	2,640	40	8,470	14,306	204	38
Wayne.....	24,355	975	85	25,415	31,769	180	60
Webster.....	115,554	3,175	100	118,829	182,479	182	307
Small mines.....	-----	140,000	-----	140,000	140,000	-----	-----
Total.....	3,560,738	397,503	63,498	4,021,739	4,995,739	(a)213	8,130

a Average for the State.

The State is divided into three inspection districts, known respectively as the southern or first district, the northeastern or second district, and the northwestern or third district. In previous volumes of Mineral Resources the annual production of the State since 1883 has been given by districts and for the sake of comparison the tables are carried up to 1890.

Total production of coal in Iowa by districts from 1883 to 1890, inclusive.

Districts.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
First.....	1,099,503	1,040,895	1,156,224	1,264,433	1,426,841	1,528,967	1,497,685	1,536,978
Second.....	1,477,024	1,413,811	1,231,963	1,688,200	1,775,978	1,974,352	1,720,727	1,626,193
Third.....	1,403,419	1,447,585	1,194,469	900,741	791,671	918,503	876,946	718,568
Small mines.....	-----	-----	-----	-----	-----	-----	-----	140,000
Total....	3,979,946	3,902,291	3,582,656	3,853,374	3,994,490	4,421,822	4,095,358	4,021,739

Product of coal in the first inspection district of Iowa from 1883 to 1890, inclusive.

Counties.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Appanoose.....	128,896	158,956	245,896	150,000	160,351	210,263	285,194	284,560
Adams.....	3,891	3,981	3,896	9,581	19,851	18,817	13,457	(a)
Cass.....	-----	-----	-----	-----	-----	-----	280	(a)
Davis.....	527	1,207	33,655	1,000	1,800	1,800	3,825	(a)
Jefferson.....	38,887	8,172	1,116	1,083	10,397	9,387	8,123	} 351,600
Lucas.....	487,821	410,729	439,956	530,759	472,998	364,969	339,229	
Marion.....	90,985	97,085	100,011	141,694	212,695	230,652	145,180	153,506
Monroe.....	93,435	98,427	101,517	117,700	183,505	233,896	258,401	324,031
Montgomery.....	-----	-----	-----	-----	-----	-----	1,040	(a)
Page.....	748	1,009	1,819	1,550	1,780	3,430	2,768	(a)
Taylor.....	94	127	617	8,585	12,180	8,002	9,736	(a)
Van Buren.....	1,678	1,778	1,193	8,038	26,331	25,960	39,258	47,464
Wapello.....	237,821	240,720	187,911	237,111	272,073	380,395	359,199	341,932
Warren.....	12,828	13,727	12,825	23,332	24,796	17,103	14,515	8,470
Wayne.....	1,892	4,947	25,812	34,000	28,084	24,293	17,480	25,415
Total.....	1,099,503	1,040,895	1,156,224	1,264,433	1,426,841	1,528,967	1,497,685	1,536,978

a Included in product of small mines.

b Exclusive of product of small mines.

Product of coal in the second inspection district of Iowa from 1883 to 1890.

Counties.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Mahaska	927,387	932,714	762,785	851,362	1,025,548	835,981	1,056,477	1,103,831
Keokuk	500,040	430,940	372,816	545,304	599,007	541,966	455,162	349,318
Jasper	45,883	46,336	90,425	286,034	142,039	275,179	199,152	173,044
Scott	3,714	3,821	5,937	3,000	8,634	9,080	9,446	(a)
Marshall	400	200
Hardin	2,000	450	1,000	490	(a)
Muscataine	100	100
Total	1,477,024	1,413,811	1,231,963	1,688,200	1,775,978	1,663,206	1,720,727	1,626,193

a Included in product of small mines.

b Exclusive of product of small mines.

Product of coal in the third inspection district of Iowa from 1883 to 1890.

Counties.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Boone	466,981	473,073	458,191	294,970	167,068	140,142	174,392	153,229
Dallas	38,208	37,185	32,986	21,986	40,420	48,622	67,055	33,466
Greene	88,851	96,327	89,587	117,538	105,894	106,042	51,438	45,192
Guthrie	5,187	4,596	17,194	18,305	18,680	12,275	(a)
Hamilton	1,998	1,878	918	3,312	6,669	6,480
Pulk	558,821	619,921	462,895	337,964	305,094	300,669	434,047	367,852
Webster	248,560	214,014	145,296	107,777	146,221	159,715	137,739	118,829
Story	2,000	2,000
Total	1,403,419	1,447,585	1,194,469	900,741	791,671	735,350	876,946	1,118,568

a Included in product of small mines.

b Exclusive of product of small mines.

Résumé.—In the foregoing tables the product for the years previous to 1889 has been given in long tons, while that of 1889 and 1890 is given in short tons. In the following table the product for all the years from 1883 to 1890 is given in short tons:

Product of coal in Iowa from 1883 to 1890.

Years.	Short tons.	Years.	Short tons.
1883	4,457,540	1887	4,473,829
1884	4,370,566	1888	4,952,440
1885	4,012,575	1889	4,095,358
1886	4,315,781	1890	4,021,739

KANSAS.

Total product in 1889, 2,221,043 short tons; spot value, \$3,296,888. Total product in 1890, 2,259,922 short tons; spot value, \$2,947,517.

As shown in the following tables, the principal producing counties in the State are Cherokee, Crawford, Leavenworth, and Osage, the other producing counties having a combined total product of but little more than 35,000 short tons. In 1888 Cherokee county was the first in producing importance, Osage, Crawford, and Leavenworth following in the order named. In 1889 Crawford county took the lead with a prod-

uct of 827,159 short tons, Cherokee coming second with 549,073 short tons, Osage third with 446,018 short tons, and Leavenworth fourth with 245,616 short tons. In 1890 the order is again changed, Crawford county holding the lead and Cherokee the second place, Osage and Leavenworth changing places, the product for each being—Crawford, 900,464; Cherokee, 724,861; Leavenworth, 319,866; Osage, 179,012.

A description of the Kansas coal fields, by Mr. Braidwood, was published in Mineral Resources for 1888.

The following tables show the product of coal in Kansas in 1889 and 1890, with the value and distribution:

Coal product of Kansas in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Bourbon.....		19,150			19,150	\$32,092	
Chautauqua.....		4,274			4,274	12,451	
Cherokee.....	516,616	24,878	7,079	500	549,073	662,838	1,196
Cloud.....		8,454	21		8,475	21,496	
Coffey.....	1,602	16,679			18,272	35,488	25
Crawford.....	812,700	8,546	5,913		827,159	971,857	1,629
Ellsworth.....		5,390			5,390	17,026	
Franklin.....	10,666	27,105			37,771	82,499	(a) 75
Jewell.....		800			800	2,400	
Labette.....	80	2,461			2,541	5,773	(b)
Leavenworth.....	174,557	57,239	13,820		245,616	415,751	937
Lincoln.....		6,427			6,427	20,723	
Linn.....	12,401	12,864	80		25,345	33,665	62
Lyon.....		4,365			4,365	12,160	
Mitchell.....		960			960	3,840	
Nemaha.....		2,171			2,171	7,870	
Osage.....	362,468	81,217	2,333		446,018	903,602	2,032
Republic.....		986			986	2,710	
Russell.....		6,703			6,703	22,065	
Shawnee.....		9,547			9,547	30,562	
Total.....	1,891,090	300,207	29,246	500	2,221,043	3,296,888	5,956

a Including Labette county.

b Included in Franklin county.

Coal product of Kansas in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Cherokee.....	710,580	11,968	2,313	724,861	882,186	186	1,413
Coffey.....	200	12,000		12,200	17,000	187	22
Crawford.....	891,634	6,170	2,660	900,464	1,114,701	198	1,447
Labette.....		4,000		4,000	10,000	200	10
Franklin.....	5,400	3,610	35	9,045	18,130	224	47
Leavenworth.....	255,431	62,995	1,440	319,866	490,224	273	745
Osage.....	156,815	22,062	135	179,012	242,198	209	804
Linn.....	8,040	2,034	400	10,474	14,078	164	60
Small mines.....		100,000		100,000	150,000		
Total.....	2,028,100	224,839	6,983	2,259,922	2,947,517	(a) 210	4,523

a Average for the State.

KENTUCKY.

Total product in 1889, 2,399,755 short tons; spot value, \$2,374,339.
 Total product in 1890, 2,701,496 short tons; spot value, \$2,472,119.

The product of coal in 1889 was 170,245 short tons less than that of 1888. In 1890 the product was 301,741 short tons more than in 1889, and greater than that of any previous year. According to the census returns the number of country banks operated in Kentucky in 1889 was 1,762, which produced 170,862 short tons of coal—which amount is included in the product statement below. While the number of these small openings varies from year to year, some being abandoned in a very short time, and others started up, the amount of coal taken from them does not materially change except by reason of an exceptionally mild winter season, when little coal is needed, or when an unusually cold season produces the opposite effect. It is estimated that about 180,000 tons were obtained from these mines in 1890. The placing of a value upon this product is purely a matter of guesswork. Most of it is consumed by the man who digs it, who may or may not own the land, and who sometimes pays for it and as frequently does not.

The production of coal in Kentucky, by counties, for 1889 and 1890, with the value and distribution of the product, is shown in the following tables:

Coal product of Kentucky in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Bell.....	3,270	13,198	57	3,570	20,095	\$28,144
Boyd.....	161,030	2,094			163,124	179,385
Breathitt.....		353			353	324
Butler.....		6,489			6,489	8,054
Carter.....	167,301	3,777	1,698		172,776	196,892
Christian.....	23,154	1,127	3,000		27,281	34,348
Clay.....		5,170			5,170	6,207
Crittenden.....	3,976	1,310			5,286	5,604
Daviess.....		30,794	76		30,870	40,231
Edmonson.....		78			78	78
Elliott.....		1,100			1,100	1,247
Floyd.....		2,236			2,236	2,433
Grayson.....		492			492	615
Greenup.....		632			632	792
Hancock.....	16,110	5,478			21,588	34,087
Harlan.....		785			785	820
Henderson.....	39,473	24,651	1,558		65,682	82,457
Hopkins.....	508,927	23,328	7,976	14,888	555,119	434,606
Jackson.....		568			568	568
Johnson.....	24,544	7,555	248		32,347	54,178
Knott.....		1,158			1,158	1,052
Knox and Lee.....	47,503	1,200			48,703	42,200
Laurel.....	273,244	6,904	303		280,451	251,122
Lawrence.....	77,683	2,104			79,787	107,103
Leslie.....		1,271			1,271	1,271
Letcher.....		1,573			1,573	1,257
McLean.....	23,345	11,812	20		35,177	41,199
Madison.....		175			175	265
Magoffin.....		5,404			5,404	6,623
Martin.....		660			660	800
Menifee.....		1,160			1,160	1,450
Morgan.....		1,061			1,061	1,061
Muhlenberg.....	194,339	11,314	1,202		206,855	180,654
Ohio.....	221,385	22,607	2,201		246,253	200,497

Coal product of Kentucky in 1889, by counties—Continued.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Owsley		2,201			2,201	\$2,751
Perry		349			349	349
Pike		1,962			1,962	1,962
Powell		69			69	69
Pulaski	78,420	2,743	3,200		84,363	109,587
Rockcastle		1,432			1,432	1,790
Todd		530			530	663
Union	41,278	13,924	1,354		56,556	63,803
Wayne		1,457			1,457	1,821
Webster	26,776	5,947	6		32,729	26,379
Whitley	179,252	4,540	1,082		184,874	203,264
Wolfe		11,474			11,474	14,277
Total	2,111,010	246,306	23,981	18,458	2,399,755	2,374,339

Coal product of Kentucky in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Butler, Christian, Crittenden, and Daviess...	42,363	900	1,668		44,931	\$41,652	164	152
Boyd and Pulaski.....	188,027	3,473	100		191,600	163,176	275	312
Carter	175,670	960	2,749		179,379	197,027	237	459
Hancock, Henderson, and McLean	122,400	3,040	1,200		126,640	126,550	224	206
Hopkins	557,937	13,532	10,565	22,273	604,307	461,177	231	1,104
Johnson	20,822	400			21,222	45,234	267	110
Knox	89,200	800			90,000	69,600	240	200
Laurel	234,490	55,430	1,258		291,178	276,718	225	680
Muhlenberg	218,835	14,460	7,688		240,983	193,330	213	495
Ohio	262,720	3,700	1,316		267,736	208,072	236	520
Union	56,587	11,176			67,763	72,999	189	131
Webster and Lawrence.	129,723	2,069	1,424		133,216	149,860	264	265
Whitley	259,215	1,726	1,600		262,541	286,724	204	625
Small mines		180,000			180,000	180,000		
Total	2,357,989	291,666	29,568	22,273	2,701,496	2,472,119	(a) 219	5,259

a Average for the State.

Coal product of Kentucky in 1890, by districts.

Districts.	Loaded at mines for shipment.	Sold to local trade and used by employés.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Jellico	348,415	2,526	1,600		352,541	\$356,324	825
Laurel	231,490	55,430	1,258		291,178	276,718	680
Pine Hill and Coalton ..	363,697	4,433	2,849		370,979	360,203	771
Peach Orchard	118,822	1,400	1,200		121,422	170,234	310
Kentucky	1,292,565	47,877	22,661	22,273	1,385,376	1,128,640	2,643
Small mines		180,000			180,000	180,000	
Total	2,357,989	291,666	29,568	22,273	2,701,496	2,472,119	5,259

The following table shows the annual product of coal in Kentucky from 1873 to 1890:

Product of coal in Kentucky from 1873 to 1890.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
1873.....	300,000	1879.....	1,000,000	1885.....	1,600,000
1874.....	300,000	1880.....	1,000,000	1886.....	1,550,000
1875.....	500,000	1881.....	1,100,000	1887.....	1,933,185
1876.....	650,000	1882.....	1,300,000	1888.....	2,570,000
1877.....	850,000	1883.....	1,650,000	1889.....	2,399,755
1878.....	900,000	1884.....	1,550,000	1890.....	2,701,496

MARYLAND.

Total product in 1889, 2,939,715 short tons; spot value, \$2,517,474. Total product in 1890, 3,357,813 short tons; spot value, \$2,899,572.

Owing to the disastrous flood of 1889, which almost destroyed the Chesapeake and Ohio canal, one of the chief means of transportation for Maryland coal, was removed and the product for that year was 539,755 short tons less than in 1888. Additional railroad facilities—not by the construction of new roads but by an increase in the number of cars—enabled the trade to recover somewhat in 1890, and the rebuilding of the canal in 1891 will afford means of moving a still larger product in that year.

The production is limited to two counties in the State, Allegany and Garrett, the product of the latter being insignificant when compared with that of Allegany. The amount and value of coal produced in 1889 and 1890, with the distribution of the product is shown in the following tables:

Coal product of Maryland in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Average number employed
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Allegany	2,885,114	39,805	10,162	2,935,081	\$2,512,614	} 3,702
Garrett	222	4,412	4,634	4,860	
Total.....	2,885,336	44,217	10,162	2,939,715	2,517,474	3,702

Coal product of Maryland in 1890.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Number of days active.	Average number employed.
Allegany.....	<i>Short tons.</i> 3, 296, 393	<i>Short tons.</i> 44, 621	<i>Short tons.</i> 8, 799	<i>Short tons.</i> 3, 349, 813	\$2, 893, 172	244	3, 842
Small mines.....		8, 000	-----	8, 000	6, 400	-----	-----
Total.....	3, 296, 393	52, 621	8, 799	3, 357, 813	2, 899, 572	244	3, 842

In the 1888 volume of Mineral Resources a statement is made showing the product in long tons of the individual companies operating in Maryland from 1883 to 1888. The agreement made by the Census Office and in the collection of the statistics for 1890 precludes the publishing of the same reports for 1889 and 1890. The amounts are therefore summarized for the years in the following table, and for convenience of comparison are reduced to short tons:

Product of coal in Maryland from 1883 to 1890.

Years.	Short tons.	Years.	Short tons.
1883	2, 476, 075	1887	3, 278, 023
1884	2, 765, 617	1888	3, 479, 470
1885	2, 833, 337	1889	2, 939, 715
1890	2, 517, 577	1890	3, 357, 813

In the following table the statistics for 1889 and 1890 are taken from the report of the Cumberland coal trade, furnished by Mr. H. W. Shaidt, manager of the Cumberland Daily News. The product for 1890 is slightly in excess of the returns made to the survey:

Product of coal in Maryland for eight years.

Companies.	1883.	1884.	1885.	1886.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Consolidation Coal Company	456, 238	689, 212	710, 064	675, 652
New Central Coal Company.....	210, 850	210, 140	203, 814	149, 561
Georges Creek Coal and Iron Company	257, 490	266, 042	257, 343	265, 942
Maryland Union Coal Company.....	137, 105	117, 180	98, 095	116, 771
Borden Mining Company.....	151, 665	162, 057	179, 537	137, 747
Maryland Coal Company.....	235, 854	295, 736	365, 319	288, 742
American Coal Company.....	190, 055	194, 330	220, 339	211, 305
Potomac Coal Company.....	139, 723	169, 463	190, 280	156, 757
Hampshire and Baltimore Coal Company	194, 534	36, 416	-----	-----
Atlantic and Georges Creek Coal Company (Pekin mine)	69, 000	75, 467	64, 938	7, 321
Swanton Mining Company.....	34, 905	28, 620	52, 862	42, 688
Bløen Avon Coal Company.....	84, 721	100, 961	69, 192	65, 830
Piedmont Coal and Iron Company	4, 619	1, 250	32	1, 678
Union Mining Company.....	5, 024	5, 310	5, 641	6, 824
National Coal Company.....	38, 998	42, 680	48, 307	62, 637
Davis & Elkins mine.....	-----	74, 437	58, 002	58, 382
Total	2, 210, 781	2, 469, 301	2, 529, 765	2, 247, 837

Product of coal in Maryland for eight years—Continued.

Companies.	1887.	1888.	1889.	1890.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Consolidation Coal Company	936,799	1,023,349	871,463	956,031
New Central Coal Company	181,906	169,484	118,885	218,169
Georges Creek Coal and Iron Company	394,012	437,992	311,253	351,310
Maryland Union Coal Company	148,523	106,620
Borden Mining Company	192,636	212,520	206,549	290,055
Maryland Coal Company	316,518	340,866	268,438	366,839
American Coal Company	259,632	287,058	297,537	386,731
Potomac Coal Company	200,793	203,777	205,212	217,232
Atlantic and Georges Creek Coal Company (Pekin mine)	6,375	3,884	752
Swanton Mining Company	61,610	58,383	40,748	41,401
Blæon Avon Coal Company	11,934
Union Mining Company	7,500	6,396	3,734	17,933
National Coal Company	117,775	76,592	72,571	60,206
Davis & Elkins mine	82,667	98,443	18,089
James Ryan	3,608
George M. Hansel	1,989	3,559	113
Barton and Georges Creek Valley Company	69,857	123,429	175,838
Enterprise mine	399	288	11
Franklin Consolidated Coal Company	71,837	66,644
Big Vein Coal Company	21,310	52,917
Piedmont-Cumberland Coal Company	2,493	29,003
Anthony Mining Company	115
Total	2,926,902	3,106,670	2,637,838	3,231,187

Total shipments from the Cumberland coal field

Years.	Frostburg region.						
	Cumberland and Pennsylvania railroad.				Cumberland Coal and Iron Company's railroad.		
	By Baltimore and Ohio railroad.	By Chesapeake and Ohio canal.	By Pennsylvania railroad.	Total.	By Baltimore and Ohio railroad.	By Chesapeake and Ohio canal.	Total.
	Long tons.	Long tons.	Long tons.	Long tons.	Long tons.	Long tons.	Long tons.
1842	757			757	951		95
1843	3,661			3,661	6,421		6,42
1844	5,156			5,156	9,734		9,73
1845	13,738			13,738	10,915		10,91
1846	11,240			11,240	18,555		18,55
1847	20,615			20,615	32,325		32,32
1848	36,571			36,571	43,000		43,00
1849	63,676			63,676	78,773		78,77
1850	73,783	3,167		76,950	119,023	875	119,89
1851	70,893	51,438		122,331	103,808	31,540	135,34
1852	128,534	46,357		174,891	139,925	19,362	159,28
1853	150,381	84,060		234,441	155,278	70,535	225,81
1854	148,953	63,731		212,684	173,580	92,114	265,69
1855	93,691	77,095		170,786	97,710	100,691	198,40
1856	86,994	80,387		167,381	121,945	105,149	227,09
1857	80,743	55,174		135,917	88,573	54,000	142,57
1858	48,018	166,712		214,730	66,009	87,539	153,54
1859	48,415	211,639		260,054	72,423	86,203	158,62
1860	70,669	232,278		302,947	80,500	63,600	144,10
1861	23,878	68,303		92,181	25,983	29,296	55,27
1862	71,745	75,206		146,951	41,096	23,478	64,57
1863	117,796	173,269		291,065	111,087	43,523	154,61
1864	287,126	194,120		481,246	67,676	64,522	132,19
1865	384,297	285,295		669,592	104,651	57,907	162,55
1866	592,938	291,019		883,957	52,251	52,159	104,41
1867	623,031	385,249		1,008,280	40,106	72,904	113,01
1868	659,115	424,406		1,083,521	100,345	57,919	158,26
1869	1,016,777	573,243		1,590,020	130,017	78,908	208,92
					2,092,660	1,192,224	3,284,88
						Cumberland Branch.	
1870	909,511	520,196		1,429,707	114,404	83,941	198,34
1871	1,247,279	656,085		1,903,364	69,894	194,254	264,14
1872	1,283,956	612,537	22,021	1,918,514	26,586	203,666	230,25
1873	1,509,570	641,220	114,589	2,265,379	89,765	137,582	227,34
1874	1,295,804	631,882	67,671	1,995,357	113,670	135,182	248,85
1875	1,095,880	715,673	160,213	1,971,766	52,505	164,165	216,67
1876	939,262	443,435	131,866	1,514,563	15,285	189,005	204,29
1877	755,278	473,646	170,884	1,399,808	63,181	111,350	174,53
1878	823,801	486,038	145,864	1,455,703	99,455	123,166	222,62
1879	933,240	397,009	154,264	1,484,513	141,907	104,238	246,14
1880	1,055,491	471,800	213,446	1,740,737	197,525	131,925	328,85
1881	1,113,263	270,156	153,501	1,536,920	271,570	151,526	423,09
1882	576,701	115,344	91,574	783,619	199,183	76,140	275,32
1883	851,985	302,678	217,065	1,371,728	197,235	141,390	338,62
1884	1,193,780	150,471	199,138	1,543,389	289,884	124,718	414,60
1885	1,091,904	171,460	206,227	1,469,591	289,407	117,829	407,23
1886	1,131,949	115,531	141,520	1,389,000	243,321	113,791	357,11
1887	1,584,114	132,177	176,242	1,892,532	332,798	125,305	458,10
1888	1,660,406	155,216	193,046	2,208,668	374,888	95,191	470,07
1889	1,420,381	26,886	177,152	1,624,419	368,497	26,407	394,90
1890	1,511,418		291,704	1,803,122	(d)522,334		522,334
Total	28,926,454	11,051,588	3,027,976	42,985,998	4,073,264	2,550,071	6,623,335

a Of this amount 35,149 long tons were shipped to the Chesapeake and Ohio canal via Piedmont.

b Includes 73,945 long tons used on line of Cumberland and Pennsylvania railroad and its branches in locomotives, rolling mills, etc.

c The total shipments of the Cumberland coal field reported by the railroads is 63 long tons greater company.

d Of this amount 3,744 tons were shipped to the Pennsylvania railroad.

e Of this amount 307,750 tons were shipped to the Pennsylvania railroad.

f Includes 95,753 tons used on line of Cumberland and Pennsylvania railroad and its branches, and rolling mills, etc.

Maryland and West Virginia for forty-nine years.

Frostburg region.				Piedmont region.		Total.			Aggregate.		
Georges Creek and Cumberland railroad.				George's Creek railroad.	Hampshire railroad, by Baltimore and Ohio railroad.	Baltimore and Ohio railroad and local.	Chesapeake and Ohio canal.	Pennsylvania railroad.			
By Chesapeake and Ohio canal.	By Pennsylvania railroad.	Local and Baltimore and Ohio.	Total.						Long tons.	Long tons.	Long tons.
						1,708			1,708		
						10,082			10,082		
						14,890			14,890		
						24,653			24,653		
						29,795			29,795		
						52,940			52,940		
						79,571			79,571		
						142,449			142,449		
						192,806	4,042		196,848		
						174,701	82,978		257,679		
						268,459	65,719		334,178		
						376,219	157,760		533,979		
						503,836	155,845		659,681		
						478,486	183,786		662,272		
						502,330	204,120		706,450		
						465,912	116,574		582,486		
						395,405	254,251		649,656		
						426,512	297,842		724,354		
						493,031	295,878		788,909		
						172,075	97,599		269,674		
						218,950	98,684		317,634		
						531,553	216,792		748,345		
						399,354	258,642		657,996		
						560,293	343,202		903,495		
						736,153	343,178		1,079,331		
						735,669	458,153		1,193,822		
						848,118	482,325		1,330,443		
						83,724	1,230,518		1,882,669		
						(a) 2,190,673					
						<i>Empire and West Virginia mines.</i>					
						28,035	60,988	1,112,938	604,137	1,717,075	
						81,216	96,453	1,494,814	850,339	2,345,153	
						85,441	121,364	1,517,347	816,103	2,355,471	
						77,582	103,793	1,780,710	778,802	2,674,101	
						57,492	109,194	1,576,160	767,064	2,410,895	
						63,537	90,800	1,302,237	879,838	1,600,698	
						108,723	7,505	1,070,775	632,440	1,885,071	
								818,459	584,996	1,707,399	
								924,254	609,204	1,458,864	
								51	1,075,198	501,247	1,730,709
								66,573	1,319,589	603,125	2,136,160
								88,722	1,478,502	504,818	2,261,918
								277,929	1,085,249	269,782	1,540,406
								338,001	1,444,766	680,119	2,544,173
								466,228	2,233,928	344,984	3,566,097
								403,489	2,076,485	368,744	3,213,895
								346,308	(b) 2,069,774	282,802	2,399,891
								449,011	2,724,347	262,345	3,213,895
								564,397	2,669,216	286,700	3,671,067
								576,047	2,357,585	57,459	3,213,886
								(e) 774,904	(f) 2,723,341	1,282,748	4,006,091
584,876	2,373,668	2,268,135	5,226,679	4,854,339	1,475,969	44,922,144	15,454,539	6,267,202	66,643,885		

Baltimore and Ohio railroad, to Cumberland.
 by Cumberland and Piedmont; also 280,850 long tons used by the Baltimore and Ohio Railroad Com-

than the total shipments shown in the table already given exhibiting the shipments of each coal

at Cumberland and Piedmont; also, 440,268 tons used by the Baltimore and Ohio railroad in locomotives,

MICHIGAN.

Total product in 1889, 67,431 short tons; spot value, \$115,011.

Total product in 1890, 74,977 short tons; spot value, \$149,195.

Although the coal area of Michigan covers thirteen counties, in only two (Jackson and Shiawassee) has it been mined commercially. The amount taken out at country banks in 1889 was 1,947 short tons, and the estimated product from the same source in 1890 was 2,000 short tons. The coal beds in Jackson and Shiawassee counties are from 2½ to 3½ feet in thickness, and have been described in previous volumes of Mineral Resources.

Product of coal in Michigan in 1889 and 1890.

Distribution.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>
Loaded at the mines for shipment	53,104	57,100
Sold to local trade and used by employes	9,110	12,885
Used at the mines for steam	5,217	4,992
Total	67,431	74,977
Total value	\$115,011	\$149,195

a Includes product from country banks.

Following is the annual product of coal in Michigan from 1877 to 1890. It will be seen that the State reached its highest producing point in 1882. Subsequent to that year, two companies which had an aggregate annual output of about 50,000 tons have reported no product:

Product of coal in Michigan from 1877 to 1890.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
Previous to 1877	350,000	1881.....	130,130	1886.....	60,434
1877.....	69,197	1882.....	135,359	1887.....	71,461
1878.....	85,322	1883.....	71,296	1888.....	81,407
1879.....	82,015	1884.....	36,712	1889.....	67,431
1880.....	129,053	1885.....	45,178	1890.....	74,977

MISSOURI.

Total product in 1889, 2,557,823 short tons; spot value, \$3,479,057.

Total product in 1890, 2,735,221 short tons; spot value, \$3,382,858.

The product of coal in Missouri for 1889 was 1,352,144 short tons less than the amount reported for 1888. This remarkable difference (about 33 per cent.) leads to the belief that the amount reported for 1888 was largely in excess of the actual product, though the mild winter of 1889-'90 probably would account for a portion of the decrease. The product of 1890 shows but a slight increase over that of 1889, which adds color to the belief in an exaggerated report for 1888.

There are thirty-five coal producing counties in the State, twenty of which produced coal commercially in 1890. The estimated product from country banks, of which there were 356 in operation in the census year, was 140,000 short tons.

The following tables show the amount of coal produced in Missouri in 1889 and 1890, by counties, with the distribution and value of the product:

Coal product of Missouri in 1889, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Total product of coal of all grades for year 1889.	Total amount received for coal sold in year 1889.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Adair.....	14,729	3,553	190	120	18,592	\$30,860
Audrian.....	19,238	5,774	556	626	26,194	38,490
Barton.....	53,438	6,360	569	800	61,167	82,655
Bates.....	707,215	44,674	1,500	2,600	755,989	857,060
Boone.....	19,932	11,285	168	20	31,405	48,244
Caldwell.....	11,171	2,153	270	13,594	26,810
Callaway.....	2,004	13,242	728	79	16,053	28,727
Carroll.....	2,439	2,439	4,866
Cedar.....	2,070	2,070	4,137
Chariton.....	1,951	10	1,961	3,692
Cooper.....	670	326	996	2,574
Dade.....	6,708	52	6,760	11,385
Grundy.....	19,793	2,108	1,500	23,401	47,972
Henry.....	154,457	19,889	1,823	3,949	180,118	278,986
Howard.....	1,050	50	1,100	1,540
Jasper.....	720	720	1,340
Johnson.....	5,140	7,209	159	333	12,841	25,247
Lafayette.....	321,405	20,783	3,669	2,813	348,670	557,186
Linn.....	6,908	76	8	6,992	13,140
Livingstone.....	1,356	25	1,381	3,251
Macon.....	419,735	11,528	2,013	13,120	446,396	550,475
Montgomery.....	10,520	1,446	234	100	12,300	17,449
Monroe.....	222	222	345
Morgan.....	1,700	200	30	70	2,000	5,000
Nodaway.....	7,752	4	2	7,758	19,275
Putnam.....	74,913	6,741	2,120	83,774	112,089
Ralls.....	562	562	1,061
Randolph.....	162,365	53,287	2,002	3,809	221,463	285,019
Ray.....	210,635	5,786	1,929	2,180	220,530	351,153
St. Clair.....	4,085	2,570	125	100	6,880	14,885
Saline.....	2,225	2,225	4,861
Schuyler.....	770	770	1,013
Shelby.....	275	275	588
Sullivan.....	805	805	1,176
Vernon.....	32,650	5,910	500	360	39,420	46,506
Total.....	2,246,845	259,587	16,412	34,979	2,557,823	3,479,057

Coal product of Missouri in 1890 by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Audrian.....	12,800	7,161	300	20,261	\$32,688	205	70
Barton.....	28,000	450	50	28,500	30,200	231	90
Bates.....	732,622	8,980	10,100	751,702	767,542	215	1,315
Boone.....	12,000	5,000	17,000	25,500	290	46
Caldwell.....	18,273	2,756	570	21,599	42,706	294	77
Callaway.....	480	4,827	24	5,331	7,996	218	11
Grundy, Linn, Putnam, and Adair.....	158,322	4,265	4,615	167,202	219,165	236	524
Henry.....	104,368	4,295	1,105	109,768	161,995	207	311
Johnson.....	5,910	40	5,950	8,030	133	15
Lafayette.....	330,740	13,812	3,136	347,688	539,402	217	1,056
Macon.....	516,683	4,630	18,748	540,061	600,373	259	1,027
Montgomery.....	500	12,940	144	13,584	18,393	200	33
Morgan.....	400	200	50	650	1,300	75	3
Randolph.....	250,376	16,156	2,840	269,372	306,736	229	635
Ray.....	259,466	14,685	3,967	278,118	422,074	241	687
St. Clair.....	5,050	5,050	7,575	140	27
Vernon.....	13,315	40	30	13,385	16,183	118	44
Small mines.....	140,000	140,000	175,000
Total.....	2,449,305	240,237	45,679	2,735,221	3,382,858	(a) 229	5,971

a Average for the State.

Product of coal in Missouri from 1873 to 1890.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
1873.....	784,000	1879.....	1,008,000	1885.....	3,080,000
1874.....	799,680	1880.....	1,680,000	1886.....	1,800,000
1875.....	840,000	1881.....	1,960,000	1887.....	3,209,916
1876.....	1,008,000	1882.....	2,240,000	1888.....	3,909,967
1877.....	1,008,000	1883.....	2,520,000	1889.....	2,557,823
1878.....	1,008,000	1884.....	2,800,000	1890.....	2,735,221

MONTANA.

Total product in 1889, 363,301 short tons; spot value, \$880,773
 Total product in 1890, 517,477 short tons; spot value, \$1,252,492.

Coal mining in Montana seems to have experienced a remarkable impetus in the last two years, the product for 1889 being 321,834 short tons greater than, or nearly nine times as much as, in 1888. The product for 1890 shows a further increase of 154,176 short tons. The value however, is not so much in proportion, the price realized per ton falling from \$3.50 in 1888 to \$2.42 in 1889 and 1890. A full description of the coal mines of Montana and their operations was published in *Mineral Resources for 1888*, and a number of analyses of the Montana coals were given in the volume for 1885.

Coal product of Montana in 1889, by counties.

Counties.	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.	Total product of coal of all grades for year 1889.	Total amount received for coal sold in year 1889.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	
Cascade.....	161,687	4,723	70	50	166,480	\$339,226
Choteau.....	670	100	50	820	2,160
Custer.....	3,450	10	10	3,470	9,129
Dawson.....	733	733	1,900
Fergus.....	415	45	460	1,380
Gallatin.....	42,745	329	764	43,838	104,377
Lewis and Clarke.	50	50	200
Missoula.....	150	150	450
Park.....	109,940	564	1,608	4,612	30,576	147,300	421,950
Total.....	314,372	10,755	2,162	5,436	30,576	363,301	880,773

Coal product of Montana in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Cascade.....	193,919	6,516	200,435	\$406,748	379
Choteau.....	200	600	800	2,000	6
Custer.....	10,228	10,228	26,417	27
Dawson.....	100	350	450	1,350	3
Fergus.....	1,230	30	1,260	5,740	8
Gallatin.....	50,062	386	1,004	51,452	119,084	120
Lewis and Clarke.	10	105	115	283	3
Park.....	221,725	4,012	3,000	24,000	252,737	690,870	705
Total.....	466,016	23,427	4,034	24,000	517,477	1,252,492	1,251

Product of coal in Montana from 1883 to 1889.

Years.	Short tons.	Years.	Short tons.
1883	19, 795	1887	10, 202
1884	80, 376	1888	41, 467
1885	86, 440	1889	363, 301
1886	49, 846	1890	517, 477

The following notes and statements of the production by counties have been prepared by Mr. F. F. Chisolm, special agent of the Geological Survey at Denver.

Beaver Head county.—No mining was carried on in Beaver Head county in 1890. The coal, as stated in previous volumes of Mineral Resources, is found on Medicine Lodge and Horse Prairie creeks and is of an inferior lignite.

Cascade county.—There were seven mines producing coal in Cascade county in 1890 and four mines that were non-producers. The producing mines were the Castner, Sand Coulee, Cora M. Ross, Mann, Powell & Heerman, Paul and Dean. By far the most important producer in 1890 was the Sand Coulee, which had an output of 194,505 tons. The seven mines employed an aggregate of 379 men. At six of these the average wages paid miners was \$3.00 per day, while one reported \$3.50 as the average rate per day.

Analyses of coals and charcoal from the Sand Coulee, Montana.

	Coking coal.	Dry coal.	Charcoal.	Average.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Water	3.98	2.81	2.25	3.01
Volatile matter	33.15	29.43	25.10	30.23
Fixed carbon	57.05	56.50	65.60	59.71
Ash	5.83	11.27	7.05	7.05
"Total	100.01	100.01	100.00	100.00

Choteau county.—Only one productive mine reports from Choteau county in 1890, the two other mines in the county having no output. The producing mine, the O'Hanlon, employed 6 men, and paid an average of \$3 per day to miners.

Custer county.—Two mines in Custer county, produced an aggregate of 10,228 tons, all of which was consumed locally. The mines gave employment to 27 men.

Dawson county.—A small amount of coal (450 short tons) was mined in 1890, to supply the wants of ranchmen and the small local trade of the section.

Deer Lodge county.—Some coal has been discovered in Deer Lodge county, but the coal veins are very narrow and bony, and no attempt has been made to produce coal for market. So far no vein which could be profitably worked has been discovered.

Fergus county.—The product in 1890 was 1,260 short tons, all of which was sold to local trade and used about the mine. Two mines were not producing.

Gallatin county.—The Timberline mine produced 51,451 short tons in 1890. Analyses of this coal have been published in previous volumes.

Lewis and Clarke county.—In Lewis and Clarke county, from two small openings, one near Hogan and the other at Dearborn, a little coal was produced in 1890 for the local trade at these mines. In addition to this production a trifling amount of coal was probably dug by individuals for their own use from coal openings on Sun River, above Fort Shaw; around the base of the Haystack Butte, near Eagle Rock; and also a little north of the Mullan Pass.

Meagher county.—Lack of railway facilities has prevented the development of the coal veins outcropping at various points in Meagher county, and the value of the coal has not been fully determined. The coal field is the extension south of the Sand Coulee field and the coal is probably similar in character to that of Cascade county.

Park county.—The total product of Park county in 1890 was 252,437 short tons. The only coke made in the State is from the Cokedale mine, in this county. The amount of coal made into coke in 1890 is reported at 24,000 short tons. Three mines, the Rocky Fork, Bryan, and Cokedale, were producers in 1890 and employed 705 men, who received from \$3 to \$3.50 per day.

Analyses of coal from Rocky Fork and Bryan mines.

	Rocky Fork.	Bryan.
	<i>Per cent.</i>	<i>Per cent.</i>
Water	2.50	9.5
Volatile matter.....	46.12	34.0
Fixed carbon.....	46.20	54.0
Ash	6.01	2.5
Total	100.83	100.0

Silverbow county.—A number of coal openings have been made in Silverbow county, but there was no production in 1890. The principal developments are on the mines of the Mullan Pass Coal Company, at Blossburg, but the property has not been worked since 1886.

Yellowstone county.—While coal veins outcrop at a great number of points in Yellowstone county, no extensive mining has yet been carried on. The coal found in this county is almost all lignite, similar to that found in the eastern portion of Montana, and not desirable for locomotive use. The only coal mined in the county was to supply the local trade at various small points and for the use of ranchmen.

Montana coal mines not operated in 1890.

Counties.	Mines.	Location.	Counties.	Mines.	Location.
Beaverhead.....	Red Rock.....	Beaver Head.	Deerlodge.....	Taylor.....	Drummond.
Do.....	Horse Prairie.	Red Rock.	Do.....	Keith.....	Do.
Cascade.....	Largent.....	Sand Coulee.	Fergus.....	Viall.....	Wolf Creek.
Do.....	Great Falls...	Truly.	Do.....	Post Quarter-	Maginnis Res-
Do.....	Bickett.....	Smith River.		masters.	ervation.
Do.....	Brown.....	Belt.	Lewis and Clarke	Gillett mine..	Hogan.
Choteau.....	Swigerts.....	Birch Creek.	Do.....	Walker mine..	Do.
Do.....	Fort Assinni-	Fort Assinni-	Missoula.....	Missoula.....	Missoula.
	boine.	boine.	Park.....	Nevenhuisen..	Livingston.
Deerlodge.....	New Chicago..	Drummond.	Yellowstone...	Northern Pac-	North of Bil-
Do.....	Beiber.....	Do.		ific Coal Co.	lings.
Do.....	Mullan Pass..	Blossburg.	Do.....	F. Billings...	Do.
Do.....	Featherman..	Drummond.			

NEBRASKA.

Total product in 1889, 1,400 short tons; spot value, \$4,900. Total product in 1890, 1,500 short tons; spot value, \$4,500.

The small product of Nebraska comes from one mine in Pawnee county. The coal, which is all consumed locally, is mined irregularly by farmers in odd seasons. A description of the Nebraska coal seams, by Prof. L. E. Hicks, of the University of Nebraska, was published in Mineral Resources for 1887.

NEW MEXICO.

Total product in 1889, 486,943 short tons; spot value, \$872,628. Total product in 1890, 375,777 short tons; spot value, \$504,390.

The product of coal in New Mexico in 1889 was 139,722 short tons less than in 1888, while the value of the product decreased \$1,003,367, showing that the tonnage reported for 1888 was evidently not only excessive, but that the valuation placed upon it was far more than the amount actually realized. The product for 1890 shows a further decrease of 111,166 short tons in tonnage and of \$368,238 in value.

The following tables show the amount and value of the coal mined in New Mexico in 1889 and 1890, by counties, with the distribution of the product:

Coal product of New Mexico in 1889, by counties.

Counties.	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.	Total product of coal of all grades for year 1889.	Total amount received for coal sold in year 1889.	Average price of coal on cars at the mines.
Bernalillo.....	229,298	446	1,242	2,073	233,059	\$395,892	\$1.70	
Colfax.....	145,660	2,050	554	3,200	151,464	201,027	1.33	
Lincoln.....		1,255			1,255	3,138	2.50	
Rio Arriba.....	13,150		200	300	13,650	24,843	1.82	
Santa Fe.....		385	15		400	1,055	2.64	
Sierra.....	26,505	1,085	470	810	34,870	74,666	2.14	
Socorro.....	39		1		40	200	5.00	
	51,905	200	100		52,205	171,807	3.29	
Total.....	466,557	5,421	2,582	6,383	6,000	486,943	872,628	1.79

Coal product of New Mexico in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Average number employed
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Bernalillo	180, 162	480	1, 005	181, 647	\$207, 948	375
Colfax	145, 000	2, 400	4, 000	151, 400	198, 500	360
Lincoln		655	520	1, 175	5, 415	11
Rio Arriba	11, 900	75	200	12, 175	21, 000	20
San Juan		510		510	1, 137	4
Santa Fe	21, 270	1, 140	300	22, 770	52, 190	55
Sierra		100		100	200	2
Small mines		6, 000		6, 000	18, 000
Total	358, 332	11, 360	6, 085	375, 777	504, 390	827

Bernalillo county—The output of 181,647 short tons represents the product of five mines, which gave employment to 375 men. The average wages paid miners was \$2.62. Two mines in the county were not operated during the year.

Colfax county.—Two new mines, the Sproule and Willoughby, began production in 1890 to supply a small local demand in the vicinity of Raton, but the output was inconsiderable, and as in the past nearly the entire output comes from the Raton Coal and Coking Company's mines in Bloss cañon, which have been fully described in previous volumes of the "Mineral Resources." The county produced 151,400 tons and gave employment to 360 men.

Rio Arriba county.—The only production in Rio Arriba county is by the Monero Coal and Coke Company, operating the Monero and Grand Mesa mines, located at Monero, on the line of the Denver and Rio Grande railway. All of the product except that used at the mine is sold in Colorado, chiefly for fuel to the local railway.

Lincoln county.—The coal fields of Lincoln county occur near White Oaks and Nogal, far from railway transportation, and the production is limited to the demands of the local trade, nearly half of the total production being used for steam by the owners of the principal mine, the Parker, near White Oaks. The coal deposits of this section are more or less metamorphosed through the influence of the eruptive outflows common in this portion of New Mexico. The composition of the coal from the Parker mine and Cochran mine, both near White Oaks, is indicated by the following average analysis:

Average analysis of coal from the Parker and Cochran mines.

Water	<i>Per cent.</i>
Volatile matter	2.35
Fixed carbon	35.53
Ash	50.24
	11.88
Total	100.00
Sulphur	0.61

In thickness the seams vary from 2 to 5 feet.

During 1890 some twenty coal filings were made near Lincoln, and coal of good quality exposed in nearly every case.

San Juan and Sierra counties.—The total product of the two counties in 1890 was only 610 short tons, which was used locally.

Santa Fé county.—The product of six mines in 1890 was 22,770 short tons. These mines employed an average of 55 men, who received \$3 per day. The following analysis has been made of the coal from the Sterling mine in Santa Fé county:

Analysis of coal from the Sterling mine.

	Per cent.
Water.....	2.31
Volatile matter.....	50.45
Fixed carbon.....	41.55
Ash.....	5.69
Total.....	100.00
Sulphur.....	1.97

New Mexico coal mines not operated in 1890.

Counties.	Mines.	Location.
Bernalillo.....	Puecos Valley.....	Gallup.
Do.....	Cleveland.....	Tijeras Cañon.
Lincoln.....	Cochran.....	White Oaks.
Socorro.....	Bartlett.....	Magdalena.

Coal product of New Mexico from 1882 to 1890.

Years.	Short tons.	Years.	Short tons.
1882.....	157,092	1887.....	508,034
1883.....	211,347	1888.....	626,665
1884.....	220,557	1889.....	486,943
1885.....	306,202	1890.....	375,777
1886.....	271,285		

The various coal mines of the Territory have been more fully described in past volumes of Mineral Resources, and the following index will give the pages and volumes:

Description of New Mexico coal fields in previous reports.

[Years and pages of Mineral Resources.]

Localities.	1882.	1883-4.	1885.	1886.	1887.
	<i>Page.</i>	<i>Page.</i>	<i>Page.</i>	<i>Page.</i>	<i>Page.</i>
Raton.....	62	57-58	278
Cerrillos.....	63	279
Gallup.....	63	279
Monero.....	63	279
San Pedro.....	64	170	278

NORTH CAROLINA.

Total product in 1889, 192 short tons; spot value, \$451. Total product in 1890, 10,262 short tons; spot value, \$17,864.

Coal mining in North Carolina did not begin until 1889, and can hardly be said to have assumed commercial importance until the next year. The production is limited to Chatham county and but one company is operating. The coal areas of the State have been described in Mineral Resources for 1885 and 1887. The value and distribution of the product for 1889 and 1890 is shown in the following table:

Coal product of North Carolina in 1889 and 1890.

Distribution.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>
Loaded at mines for shipment	190	9,262
Sold to local trade and used by employés	1	100
Used for steam at the mine	1	900
Total	192	10,262
Total value.....	\$451	\$17,864

NORTH DAKOTA.

Total product in 1889, 28,907 short tons; spot value, \$41,431. Total product in 1890, 30,000 short tons; spot value, \$42,000.

The Eleventh Census gives the first report of coal mining in North Dakota, the product for that year being 28,907 short tons. There were five commercial mines operating in the census year whose total product was 24,982 short tons. The number of small banks was 337, whose entire output amounted to 3,925 short tons, or an average of a little less than 12 tons each. The coal-producing counties are Morton, Stark and Ward, the first two being in the southwestern and the last mentioned in the north central portion of the State. Previous to 1889 the product has been reported for the Territory of Dakota, but as the producing region of the Territory is contained in what is now the State of North Dakota, the product for previous years may be included in the following table:

Coal product of North Dakota from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	35,000	1888	34,000
1885	25,000	1889	28,907
1886	25,955	1890	30,000
1887	21,470		

The limited production of coal in North Dakota is due to the fact that it is an inferior quality of lignite, and not only is it a poor fuel, but the cost of mining is comparatively high, and consumers find it more economical to use coal brought from other States.

OHIO.

Total product in 1889, 9,976,787 short tons; spot value, \$9,355,400.
 Total product in 1890, 11,494,506 short tons; spot value, \$10,783,171.

The product of coal in Ohio in 1889 was nearly 1,000,000 tons less than that of the preceding year, showing the effect of the mild winter previously noted. In 1890 the production increased 1,517,719 short tons over that of 1889, and reached the highest point in the history of the State.

The following tables show the product for the two years, with the value and distribution:

Coal product in Ohio in 1889, by counties.

Counties.	Disposition of total product.					Total product of coal of all grades for 1889.	Total amount received for coal sold in 1889.	Total employés about mines.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employés.	Used for steam at mines.	Manufactured into coke.			
	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>		
Athens	1,102,670	70,933	4,273	7,288	39,022	1,224,186	\$994,344	2,228
Belmont	456,221	175,396	3,299	1,946	5,000	641,862	558,333	1,100
Carroll	337,393	14,101	88	290	351,782	261,813	565
Columbiana	542,665	49,388	2,492	2,279	596,824	471,945	955
Coshocton	112,130	53,691	446	332	166,599	163,659	290
Gallia	14,339	7,653	1,211	23,208	24,068	34
Guernsey	328,568	26,552	3,112	3,936	362,168	313,480	668
Harrison	800	31,817	1,107	33,724	41,028	8
Hocking	820,294	10,757	523	13,475	845,049	683,551	1,187
Holmes	9,272	146	5	9,423	13,037
Jackson	823,269	94,241	3,009	6,355	926,874	953,696	2,251
Jefferson	173,260	90,287	3,068	2,268	2,947	271,830	273,075	511
Lawrence	44,432	57,872	452	102,656	106,269	232
Mahoning	187,321	23,227	2,798	4,717	22,500	240,563	280,406	636
Medina	125,759	2,975	1,385	5,942	136,061	158,003	379
Meigs	103,301	111,698	3,132	2,146	220,277	223,614	567
Monroe	16,000	4,246	479	20,725	34,066	29
Morgan	7,662	398	8,060	10,502
Muskingum	133,589	79,254	554	608	214,005	212,873	304
Noble	10,200	26,250	1,950	38,400	44,039	43
Perry	1,506,282	51,313	3,754	4,437	1,565,786	1,317,963	3,056
Portage	73,728	2,641	598	1,150	78,117	99,213	179
Stark	782,466	41,541	5,502	22,485	851,994	1,073,703	1,975
Summit	36,152	11,645	857	2,072	50,726	92,723	170
Trumbull	101,270	4,193	1,417	1,240	108,120	176,934	388
Tuscarawas	562,060	113,886	2,468	5,091	683,505	544,524	1,061
Vinton	85,202	14,756	1,262	820	102,040	104,972	256
Washington	11,374	6,270	341	60	18,045	19,684	23
Wayne	75,478	3,350	250	5,100	84,178	103,883	248
Total	8,566,223	1,196,872	50,271	93,952	69,409	9,976,787	9,355,400	19,343

Coal product of Ohio in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Athens	1,152,825	29,551	6,499	16,580	1,205,455	\$999,003	198	2,122
Belmont	684,063	82,185	1,862	6,000	774,110	605,604	201	1,401
Carroll	328,467	400	100	328,967	278,704	188	642
Columbiana.....	545,014	17,818	4,763	567,595	518,136	219	987
Coshocton	172,500	5,000	200	177,700	159,150	237	327
Gallia	16,176	336	16,512	14,903	205	33
Guernsey	408,084	2,770	2,885	413,739	282,355	225	788
Jackson	882,243	77,947	10,688	970,878	974,892	180	2,654
Jefferson	373,012	114,429	2,552	1,179	491,172	409,654	203	944
Harrison	2,000	6,600	8,600	12,900	268	14
Hocking	1,258,722	8,500	52,205	1,319,427	1,084,057	240	1,625
Lawrence	75,989	1,015	77,004	83,265	198	242
Mahoning	235,474	18,615	2,230	256,319	306,633	220	537
Medina	130,359	5,683	3,700	139,742	167,538	219	310
Meigs	134,042	119,787	1,536	255,365	316,247	202	616
Monroe	1,000	1,000	1,000	100	3
Muskingum	197,113	32,406	200	229,719	197,640	250	366
Noble	5,640	1,210	6,850	7,350	102	25
Perry	1,880,502	39,176	1,739	1,921,417	1,642,967	188	2,977
Portage	68,338	1,328	1,000	70,666	112,475	236	155
Stark	767,703	28,174	40,572	836,449	1,088,978	182	1,930
Summit	101,602	5,614	5,781	112,997	169,171	173	389
Trumbull	46,652	362	700	47,714	57,713	243	102
Tuscarawas.....	576,413	12,015	1,447	589,875	499,685	196	1,082
Vinton	78,546	1,495	675	80,716	86,611	241	186
Washington	4,990	1,000	5,990	5,281	91	32
Wayne	35,418	460	2,650	38,528	41,259	178	87
Small mines.....	550,000	550,000	660,000
Total	10,161,887	1,164,876	143,984	23,759	11,494,506	10,783,171	(a)201	20,576

a Average for the State.

In collecting the statistics for 1889 and 1890 no attempt has been made to segregate the nut and slack coal from the lump, coal of all grades (except waste slack) being included in the total. From the State mine inspectors' reports the following statement has been compiled, showing the amount of lump and nut coal produced in 1886 and the lump, nut, pea, and slack produced in 1887 and 1888. The report for 1887 was prepared by Mr. Thomas B. Bancroft, and that for 1888 by Mr. R. M. Hazeltine, State mine inspector.

Counties.	1886.			1887.			1888.				
	Lump.	Nut.	Total.	Lump.	Nut.	Pea and slack.	Total.	Lump.	Nut.	Pea and slack.	Total.
Athens.....	Short tons. 766,411	Short tons. 132,635	Short tons. 899,046	Short tons. 141,900	Short tons. 57,021	Short tons. 198,921	Short tons. 1,083,543	Short tons. 1,081,559	Short tons. 167,181	Short tons. 87,958	Short tons. 1,336,698
Belmont.....	462,253	111,527	573,779	108,363	118,430	226,793	1,210,272	1,755,054	182,264	190,788	1,106,106
Columbiana.....	268,465	67,698	336,163	74,985	47,455	122,440	516,571	314,084	90,575	61,582	466,191
Coshocton.....	43,361	8,573	51,934	17,412	19,012	36,424	124,791	114,051	24,476	29,376	167,903
Carroll.....	184,095	32,535	216,630	186,624	39,137	225,761	283,328	217,341	74,538	62,988	355,097
Guernsey.....	349,063	84,297	433,360	360,340	100,475	460,815	553,613	259,552	64,984	59,192	383,728
Gallia.....	14,862	2,562	17,424	13,000	2,365	15,365	15,365	13,571	1,811	3,151	16,722
Holmes.....	10,491	2,179	12,670	7,407	836	8,243	10,526	5,500	1,562	1,059	8,121
Hocking.....	637,224	104,347	741,571	693,097	116,914	810,011	853,063	881,706	162,050	42,782	1,086,538
Harrison.....	5,132	877	6,009	3,643	4,032	7,675	4,032	2,465	200	200	2,865
Jackson.....	717,516	139,224	856,740	863,047	194,888	1,057,935	1,134,705	827,854	174,726	86,181	1,088,761
Jefferson.....	442,051	33,615	475,666	222,277	31,270	253,547	293,875	171,138	31,605	40,435	243,178
Lawrence.....	139,173	27,760	166,933	113,700	22,272	135,972	143,569	114,737	21,243	1,806	137,806
Madison.....	223,747	28,664	252,411	178,772	36,425	215,197	225,487	143,781	18,976	35,685	198,452
Meigs.....	165,627	26,636	192,263	153,444	23,051	176,495	185,268	170,280	48,773	23,430	242,483
Muskingum.....	85,011	11,590	96,601	127,353	9,442	136,795	171,928	148,782	17,890	45,189	211,861
Mahoning.....	251,515	61,525	313,040	210,294	18,999	229,293	272,349	177,477	11,775	41,783	231,035
Morgan.....	4,370	4,370	3,500	3,500	4,100	4,000	1,200	1,000	6,200
Noble.....	3,342	3,342	4,000	1,320	5,320	6,320	4,000	1,200	1,000	6,200
Perry.....	1,346,131	261,535	1,607,666	1,545,911	179,414	1,725,325	1,870,840	1,430,268	229,933	76,604	1,736,805
Portage.....	61,273	9,066	70,339	48,649	4,442	53,091	65,163	52,488	8,246	10,189	70,923
Scioto.....	519,992	73,430	593,422	586,014	81,973	667,987	784,164	590,009	74,782	128,436	798,227
Stark.....	70,221	12,004	82,225	76,110	5,700	81,810	95,815	90,050	4,373	17,601	112,024
Summit.....	212,362	55,304	267,666	363,094	81,554	444,648	506,466	180,375	112,314	14,943	546,117
Tuscarawas.....	162,331	26,200	188,531	132,829	27,058	160,887	167,989	120,875	12,707	24,744	137,826
Trumbull.....	49,392	10,621	60,013	69,043	11,702	80,745	89,727	84,706	11,288	11,888	108,695
Vinton.....	99,174	9,883	109,057	84,906	8,436	93,342	105,150	69,835	9,409	11,884	91,157
Wayne.....	4,000	1,500	5,500	1,480	400	1,880	1,880	1,462	115	115	2,432
Washington.....	7,299,024	1,336,187	8,635,211	7,900,304	1,342,945	9,243,249	10,300,807	8,241,145	1,558,707	1,111,099	10,910,951
Total.....	7,299,024	1,336,187	8,635,211	7,900,304	1,342,945	9,243,249	10,300,807	8,241,145	1,558,707	1,111,099	10,910,951

The following table shows the annual increase and decrease in production by counties from 1886 to 1890:

Comparative statistics by counties in Ohio from 1886 to 1890.

Counties.	1887 compared with 1886.		1888 compared with 1887.		1889 compared with 1888 (a).		1890 compared with 1889 (b).	
	Increase.	Decrease.	Increase.	Decrease.	Increase.	Decrease.	Increase.	Decrease.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Athens	184,497		253,155			112,512		18,731
Belmont	147,988		386,339			466,244	132,248	
Carroll	76,698		61,784			3,315		22,815
Columbiana	179,994			49,866	130,633			29,229
Coshocton	71,857		43,112			1,304	11,101	
Gallia		2,059	1,357		6,486			6,696
Guernsey	119,813			169,885		21,560	51,571	
Harrison		1,477		1,167	30,859			25,124
Hocking	111,492		233,475			241,469	474,378	
Holmes		2,144		2,405	1,302			(c)9,423
Jackson	278,865			45,944		161,887	44,004	
Jefferson	18,209			50,697	28,652		219,342	
Lawrence		23,374		5,753		35,150		25,652
Mahoning		40,691		41,514	9,528		15,756	
Medina		26,924		27,035		62,391	3,681	
Meigs		7,058	57,278			22,206	35,088	
Monroe					(d)20,725			19,725
Morgan		270		4,100	(d)8,060			(c)8,060
Muskingum	75,327		39,933		2,144		15,714	
Noble	2,978			120	32,200			31,550
Perry	263,175			134,035		171,019	355,631	
Portage		5,176	5,760		7,194			7,451
Stark	190,742		9,063		58,767			15,545
Summit	13,590		16,209			61,298	62,271	
Trumbull		20,542		10,163		49,706		60,406
Tuscarawas	238,800		39,651		137,388			173,630
Vinton	29,714		18,968			6,655		21,324
Washington		3,620	552		15,613			12,055
Wayne		3,907		13,933		6,979		45,650
Totals	2,003,739	137,242	1,166,636	556,477	489,551	1,423,715	1,420,785	533,066
Net increase or decrease	1,866,497		610,159			934,164	887,719	

a Includes product of small banks in 1889 and not in 1888.

b Includes product of small banks in 1889 and not in 1890.

c Product of small banks in 1889 not enumerated in 1890.

d Entire product of 1889; no product reported in 1888.

There are twenty-nine counties in the State which produced coal in 1889, though in two of them, Holmes and Morgan, the entire product was from small banks, and these are excluded from the tabulated statement for 1890. The total number of small banks in Ohio, as reported by the Census Office, is 1,745, which produced, in 1889, 506,049 short tons of coal. The counties showing increased production in 1889 over that of 1888 were Columbiana, Gallia, Harrison, Holmes, Jefferson, Mahoning, Monroe (*), Morgan (*), Muskingum, Noble, Portage, Stark, Tuscarawas, and Washington. The counties having a decreased product were Athens, Belmont, Carroll, Coshocton, Guernsey, Hocking, Jackson, Lawrence, Medina, Meigs, Perry, Summit, Trumbull, Vinton, and Wayne. The counties having an increased production in 1890 over 1889 were Belmont, Coshocton, Guernsey, Hocking, Jackson, Jefferson, Mahoning, Medina, Meigs, Muskingum, Perry, and Summit. The most notable increases were in Hocking and Perry counties, that in

* No product reported in 1888.

the former county being 474,378 short tons, and in the latter 355,631 short tons. The counties having a decreased production were Athens, Carroll, Columbiana, Gallia, Harrison, Lawrence, Monroe, Noble, Portage, Stark, Trumbull, Tuscarawas, Vinton, Washington, and Wayne.

The coal-producing portions of the State of Ohio are, for convenience of description, divided into twelve districts. The names of these districts, the counties or parts of counties embraced by them, and the amount of coal produced in each (exclusive of the product of small banks) for 1889 and 1890, are shown in the following table:

Coal product of Ohio in 1889 and 1890, by districts.

Names of districts.	Counties embraced in the districts.	Product in 1889.	Product in 1890.	Increase.	Decrease.
		<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Jackson	Jackson	922,631	970,878	48,247
Ohio Valley	Lawrence, Gallia, Meigs, Monroe, Belmont, Jefferson, and Medina.	1,292,469	1,754,905	462,436
Hocking Valley	Vinton, Hocking, Athens, and part of Perry.	3,089,525	3,705,464	615,939
Cambridge.....	Guernsey	336,840	413,739	76,899
Macksburg	Washington and Noble.....	23,982	12,840	11,142
Carrollton Valley...	Harrison	4,200	8,600	4,400
Muskingum Valley.	Part of Perry, and Muskin- gum.	756,859	1,051,270	294,411
Tuscarawas Valley .	Coshocton, Tuscarawas, Stark, Summit, and Wayne.	1,738,387	1,675,549	62,838
Salineville	Columbiana	562,230	567,595	5,365
Carrollton Valley...	Carroll	337,583	328,967	8,616
Mahoning Valley ...	Mahoning and Trumbull...	327,915	304,033	23,882
Palmyra	Portage	78,117	70,666	7,451
Total	9,470,738	10,864,506	1,507,697	113,929
Increase of product of commercial mines.	1,393,768	1,393,768

The Hocking Valley is the most important producing district in the State, the product for 1890 being nearly one-third the entire product of the State. The following table shows the annual output of the Hocking Valley district for the past nine years:

Product of the Hocking Valley district from 1882 to 1890.

Years.	Short tons.	Years.	Short tons.
1882	1,812,833	1887	3,348,547
1883	1,916,355	1888	3,484,354
1884	2,725,000	1889	3,089,525
1885	2,894,660	1890	3,705,464
1886	2,960,000		

Annual coal product of Ohio from 1872 to 1890.

Years.	Short tons.	Years.	Short tons.
1872	5,315,294	1882	9,450,000
1873	4,550,028	1883	8,229,429
1874	3,267,585	1884	7,640,062
1875	4,804,259	1885	7,816,179
1876	3,500,000	1886	8,435,211
1877	5,250,000	1887	10,301,708
1878	5,500,000	1888	10,147,180
1879	6,000,000	1889	9,470,738
1880	7,000,000	1890	11,414,506
1881	8,225,000		

The following tables, compiled by Mr. Sidney D. Maxwell, superintendent of the Cincinnati Chamber of Commerce, exhibit interesting statistics of the coal trade of southern Ohio for a number of years:

Receipts of coal at Cincinnati for nineteen years.

Years.	Pittsburg (Youghio- gheny).	Kanawha.	Ohio river.	Canal.	Anthracite.	Other kinds.	Total.
	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>
1871-'72	19,254,716		a10,359,906	1,104,003	72,171		30,790,796
1872-'73	24,962,373		a11,075,072	1,162,052	75,000		37,274,497
1873-'74	24,014,681		a10,398,153	710,000	112,000		35,234,834
1874-'75	24,225,002	4,476,619	4,277,327	565,352	248,750	1,597,260	35,390,810
1875-'76	27,017,592	6,004,675	4,400,792	409,358	282,578	2,068,322	40,183,317
1876-'77	28,237,572	3,631,823	5,141,150	322,171	376,125	1,913,793	39,622,634
1877-'78	26,743,055	6,386,623	3,288,008	380,768	439,350	1,654,425	38,892,229
1878-'79	20,769,027	6,134,039	4,068,452	333,549	768,750	2,136,850	34,210,667
1879-'80	31,750,968	8,912,801	4,268,214	202,489	712,075	2,351,699	48,198,246
1880-'81	23,202,084	10,715,459	3,151,934	67,684	770,525	2,336,752	40,244,438
1881-'82	37,807,961	13,950,802	3,560,881	77,336	779,925	3,090,715	59,267,620
1882-'83	33,895,064	13,260,347	3,309,534	180,621	977,250	2,997,216	54,620,032
1883-'84	32,239,473	15,926,743	2,956,688	293,010	1,085,350	3,910,795	56,412,059
1884-'85	32,286,133	14,588,573	3,007,078	314,774	1,257,900	2,683,864	54,138,322
1885-'86	34,933,542	17,329,349	939,746	205,717	1,287,925	2,720,250	57,416,529
1886-'87	37,701,094	20,167,875	338,435	129,503	1,314,775	3,693,850	63,345,532
1887-'88	41,180,713	20,926,596	1,533,358	26,098	1,328,225	5,710,649	70,705,639
1888-'89	36,677,974	23,761,853	544,940	12,129	1,020,523	3,075,000	65,092,421
1889-'90	42,601,615	19,221,196	454,385	1,001,175	4,709,775	67,988,146

a Including Kanawha coal.

OREGON.

Total product in 1889, 64,359 short tons; spot value, \$163,650. Total product in 1890, 61,514 short tons; spot value, \$177,875.

The product of coal in Oregon continues to come principally from one mine, the output from other sources in 1889 being only 56 tons, and no account of this small factor has been taken in the product reported for 1890. The one commercial property is located at Marchfield, in Coos county, and the bulk of the product is shipped to San Francisco. The average price received for coal in 1888 was \$3 per ton. In 1889 the price fell to \$2.60 per ton, and rose again in 1890 to \$2.89. The number of men employed in 1888 and 1889 was 160. The number reported for 1890 was 208, the increase probably being due to extended development work, looking to an increased production in the near future.

Amount, value, and distribution of the coal product of Oregon in 1889 and 1890.

Distribution.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>
Loaded at mines for shipment	62,483	58,821
Sold to local trade and used by employés	1,316	1,936
Used at mines for steam and heat.....	560	757
Total	64,359	61,514
Total value.....	\$163,650	\$177,875

The coal is classed as a lignite, but is said to be similar in appearance to the bituminous coals of the Mississippi Valley. It will not coke, but serves very well for domestic purposes, and is also good for black-smithing use. No authentic statistics of coal mining in Oregon have been obtained prior to 1886. In 1885 it was stated that the product probably did not exceed 50,000 short tons, and though that figure is undoubtedly excessive, it is quoted as the product for that year in the following table:

Coal product of Oregon from 1885 to 1890.

Years.	Short tons.	Years.	Short tons.
1885	50,000	1888	75,000
1886	45,000	1889	64,359
1887	31,696	1890	61,514

PENNSYLVANIA.

The total product in 1889, including coal shipped, the output of small banks, the coal sold by regular establishments to local trade and employés, and the amount consumed at the collieries for steam and heat was 81,719,059 short tons; spot value, \$93,671,480. Total product in 1890, 88,770,814 short tons; spot value, \$101,760,688.

Anthracite: Total product in 1889, 40,665,152 long tons, or 45,544,970 short tons; spot value, \$65,718,165. Total product in 1890, 41,489,858 long tons, or 46,468,641 short tons; spot value, \$66,383,772.

Bituminous: Total product in 1889, 36,174,089 short tons; spot value, \$27,953,315. Total product in 1890, 42,302,173 short tons; spot value, \$35,376,916.

ANTHRACITE.

[BY JOHN H. JONES.]

Total product in 1889, 40,665,152 long tons (equivalent to 45,544,970 short tons); spot value, \$65,718,165. Total product in 1890, 41,489,858 long tons (equivalent to 46,468,641 short tons); spot value, \$66,383,772.

The total production of anthracite coal in Pennsylvania during the calendar year 1889 was 40,665,152 tons of 2,240 pounds (equal to 45,544,970 tons of 2,000 pounds). The marketable product, that is, the amount of coal shipped and sold to local trade and employés, was 37,146,456 long tons (or 41,604,031 short tons), valued at the mines at \$65,718,165, or an average of \$1.76 $\frac{9}{10}$ per long ton. The quantity reported by the transportation companies as actually carried to market, which is the usual basis for statistics of shipments, was 35,407,710 tons during the year 1889; 1,329,580 tons were used by employés and sold to local trade in the vicinity of the mines, and 3,518,696 tons were reported as consumed for steam and heating purposes in and about the mines. For reasons stated below the item of colliery consumption is excluded from the valuation of the product.

The total production of anthracite coal in Pennsylvania during the calendar year 1890 was 41,489,858 long tons (or 46,468,641 short tons), of which the marketed amount was 38,403,552 long tons (or 43,011,978 short tons), valued at the mines at \$66,383,772, or an average of \$1.72 $\frac{9}{10}$ per long ton. The total quantity loaded on cars and sent to market was 36,617,042 tons during the year 1890; 1,786,510 tons were used by employés and sold to local trade in the vicinity of the mines, and 3,086,306 tons were consumed for steam and heat in and about the mines. The item of colliery consumption is, however, somewhat indefinite, the coal being taken either from the current mining or from screenings, and used where needed, often without preparation, and rarely included in the accounts of the operator, being reported in most instances as "approximated." For these reasons it has been excluded from the basis of valuation of the product at the mines. The average number of days worked during the year 1890 was 200. The number of persons employed during the year, including superintendents, engineers, and clerical force, was 126,000. The total number of regular establishments or breakers equipped for the preparation and shipment of coal was 350, exclusive of small diggings and washeries supplying local trade.

The average number of days worked during the year 1889 by all collieries was 194. The suspension of mining, during periods aggregating

about one-third of the year, was caused mainly by the inability of the market to absorb a larger product. The number of persons employed during the year, including superintendents, engineers, and clerical force, was 125,229. The total amount paid in wages to all classes during the year was \$39,152,124. The total number of regular establishments or breakers equipped for the preparation and shipment of coal was 342, 19 of which were idle during the year. Besides these, there were 49 small diggings and washeries, supplying local trade. There were also 18 new establishments in course of construction.

Comparing the statistics of anthracite coal production in 1889 and 1890, it will be seen that there was a gain in product during the latter year of 824,706 long tons (equal to 923,671 short tons) and an increase in value of \$665,607, the average price per ton realized at the mines during each year being \$1.76 $\frac{9}{10}$ and \$1.72 $\frac{9}{10}$, respectively. The average number of days worked during 1890 was 200, as against 194 days in 1889. The total number of employés at anthracite mines in 1889 was 125,229 and in 1890, 126,000. The number of regular establishments increased from 342 in 1889 to 350 in 1890.

The anthracite coal fields of Pennsylvania are situated in the eastern part of the State, and extend about equal distances north and south of a line drawn through the middle of the State from east to west, in the counties of Carbon, Columbia, Dauphin, Lackawanna, Luzerne, Northumberland, Schuylkill, Sullivan, and Susquehanna, and known under three general divisions, viz: Wyoming, Lehigh and Schuylkill regions. Geologically they are divided into five well-defined fields or basins, which are again subdivided, for convenience of identification, into districts, as follows:

<i>Geological fields or basins.</i>	<i>Local districts.</i>	<i>Trade regions.</i>
Northern	{ Carbondale	}
	{ Scranton	
	{ Pittston	
	{ Wilkesbarre	
	{ Plymouth	
Western Northern	{ Kingston	} Wyoming
	{ Bernice	
Eastern Middle	{ Green Mountain	}
	{ Black Creek	
	{ Hazleton	
	{ Beaver Meadow	
	{ Panther Creek	
Southern	{ East Schuylkill	} Lehigh
	{ West Schuylkill	
	{ Lorberry	
Western Middle	{ Lykens Valley	} Schuylkill
	{ East Mahanoy	
	{ West Mahanoy	
	{ Shamokin	

The following table shows the annual shipments of anthracite coal from the Pennsylvania fields since 1820, with the percentages from each region:

Annual shipments of anthracite coal in Pennsylvania since 1820, with the number of tons and percentage shipped from each region.

Years.	Schuylkill region.		Lehigh region.		Wyoming region.		Total. Long tons.
	Long tons.	Per ct.	Long tons.	Per ct.	Long tons.	Per ct.	
1820			365				365
1821			1,073				1,073
1822	1,480	39.79	2,240	60.21			3,720
1823	1,128	16.23	5,823	83.77			6,951
1824	1,567	14.10	9,541	85.90			11,108
1825	6,500	18.60	28,393	81.40			34,893
1826	16,767	34.90	31,280	65.10			48,047
1827	31,360	49.44	32,074	50.56			63,434
1828	47,284	61.00	30,232	39.00			77,516
1829	79,973	71.35	25,110	22.40	7,000	6.25	112,083
1830	89,984	51.50	41,750	23.90	43,000	24.60	174,734
1831	81,854	46.29	40,966	23.17	54,000	30.54	176,820
1832	209,271	57.61	70,000	19.27	84,000	23.12	363,271
1833	252,971	51.87	123,001	25.22	111,777	22.91	487,749
1834	226,692	60.19	106,244	28.21	43,700	11.60	376,636
1835	339,508	60.54	131,250	23.41	90,000	16.05	560,758
1836	432,045	63.16	148,211	21.66	103,861	15.18	684,117
1837	530,152	60.68	223,902	25.75	115,387	13.27	869,441
1838	446,875	60.49	213,615	28.92	78,207	10.59	738,697
1839	475,077	58.05	221,025	27.01	122,300	14.94	818,402
1840	490,596	56.75	225,313	26.07	148,470	17.18	864,379
1841	624,466	65.07	143,037	14.90	192,270	20.03	959,773
1842	583,273	52.62	272,540	24.59	252,599	22.79	1,108,412
1843	710,200	56.21	267,793	21.19	285,605	22.60	1,263,598
1844	887,937	54.45	377,002	23.12	365,911	22.43	1,630,850
1845	1,131,724	56.22	429,453	21.33	451,836	22.45	2,013,013
1846	1,308,500	55.82	517,116	22.07	518,389	22.11	2,344,005
1847	1,605,735	57.79	633,507	21.98	533,067	20.23	2,672,309
1848	1,733,721	56.12	670,321	21.70	685,196	22.18	3,089,238
1849	1,728,500	53.30	781,556	24.10	732,910	22.60	3,242,966
1850	1,840,620	54.80	690,456	20.56	827,823	24.64	3,358,899
1851	2,328,525	52.34	964,224	21.68	1,156,167	25.98	4,448,916
1852	2,636,835	52.81	1,072,136	21.47	1,284,500	25.72	4,993,471
1853	2,665,110	51.30	1,054,309	20.29	1,475,732	28.41	5,195,151
1854	3,191,670	53.14	1,207,186	20.13	1,603,478	26.73	6,002,334
1855	3,552,943	53.77	1,284,113	19.43	1,771,511	26.80	6,608,567
1856	3,603,029	52.91	1,351,970	19.52	1,972,581	28.47	6,927,580
1857	3,373,797	50.77	1,318,541	19.84	1,952,603	29.59	6,644,941
1858	3,273,245	47.86	1,380,030	20.18	2,186,094	31.96	6,839,369
1859	3,448,708	44.16	1,628,311	20.86	2,731,236	34.98	7,808,255
1860	3,749,632	44.04	1,821,674	21.40	2,941,817	34.56	8,513,123
1861	3,160,747	39.74	1,738,377	21.85	3,055,140	38.41	7,954,264
1862	3,372,583	42.86	1,351,054	17.17	3,145,770	39.97	7,869,407
1863	3,911,683	40.90	1,894,713	19.80	3,759,610	39.30	9,566,006
1864	4,161,970	40.89	2,054,669	20.19	3,960,836	38.92	10,177,475
1865	4,356,959	45.14	2,040,913	21.14	3,254,519	33.72	9,652,391
1866	5,787,902	45.56	2,179,364	17.15	4,736,616	37.29	12,703,882
1867	5,161,671	39.74	2,502,054	19.27	5,325,000	40.99	12,988,725
1868	5,330,737	38.52	2,502,582	18.13	5,968,146	43.25	13,801,465
1869	5,775,138	41.66	1,949,673	14.06	6,141,369	44.28	13,866,180
1870	4,968,157	30.70	3,239,374	20.02	7,974,660	49.28	16,182,191
1871	6,552,772	41.74	2,235,707	14.24	6,911,242	44.02	15,699,721
1872	6,694,890	34.03	3,873,339	19.70	9,101,549	46.27	19,669,778
1873	7,212,601	33.97	3,705,596	17.46	10,309,755	48.57	21,227,952
1874	6,866,877	34.09	3,773,836	18.73	9,504,408	47.18	20,145,121
1875	6,281,712	31.87	2,834,605	14.38	10,596,155	53.75	19,712,472
1876	6,221,934	33.63	3,854,919	20.84	8,424,158	45.53	18,501,011
1877	8,195,042	39.35	4,332,760	20.80	8,300,377	39.85	20,828,179
1878	6,282,226	35.68	3,237,449	18.40	8,085,587	45.92	17,605,262
1879	8,960,829	34.28	4,595,567	17.58	12,586,293	48.14	26,142,689
1880	7,554,742	32.23	4,463,221	19.05	11,419,279	48.72	23,437,242
1881	9,253,958	32.46	5,294,676	18.58	13,951,383	48.96	28,500,017
1882	9,459,288	32.48	5,689,437	19.54	13,971,371	47.98	29,120,096
1883	10,074,726	31.69	6,113,809	19.23	15,604,492	49.08	31,793,027
1884	9,478,314	30.85	5,562,226	18.11	(a)15,677,753	51.04	30,718,293
1885	9,488,426	30.01	5,898,634	18.65	(a)16,236,470	51.34	31,623,530
1886	9,381,407	29.19	5,723,129	17.89	(a)17,031,826	52.82	32,136,362
1887	10,609,028	30.63	4,347,061	12.55	(a)19,684,929	56.82	34,641,018
1888	10,654,116	27.93	5,639,236	14.78	(a)21,852,366	57.29	38,145,718
1889	10,486,185	29.28	6,294,073	17.57	(a)19,036,835	53.15	35,817,093
1890	10,867,822	29.68	6,329,658	17.28	(a)19,417,979	53.04	36,615,459
Total...	264,363,696	35.76	134,828,394	18.24	339,998,900	46.00	739,190,990

a Includes Loyalsock field.

The figures shown in the above table represent the actual shipments to market by rail and water, including the coal shipped to tidewater

and other storage docks for further transportation. The colliery consumption and the local sales at mines (not transported) are not included.

The quantity of coal produced in each of the counties comprising the anthracite fields of Pennsylvania, during the years 1889 and 1890, is shown in the following tables:

Production of Pennsylvania anthracite coal of all grades, by counties, in 1889.

Counties.	Total product of coal of all grades for year 1889.	Disposition of total product.		
		Loaded at mines for shipment on railroad cars.	Used by employés and sold to local trade at mines.	Used for heat and steam at mines.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Susquehanna and Sullivan.....	351,842	319,126	5,820	26,896
Lackawanna.....	8,939,621	7,823,694	588,535	527,392
Luzerne.....	16,607,177	14,892,324	446,036	1,268,817
Carbon.....	1,210,973	1,080,544	19,592	110,837
Schuylkill.....	9,052,619	7,837,369	181,893	1,033,357
Columbia.....	628,695	539,273	15,663	73,759
Northumberland.....	3,176,740	2,770,914	57,857	347,969
Dauphin.....	697,485	553,632	14,184	129,669
Total.....	40,665,152	35,816,876	1,329,580	3,518,696

Production of anthracite coal, of all grades, in 1890, by counties.

Counties.	Total product of coal of all grades for year 1890.	Disposition of total product.		
		Loaded at mines for shipment on railroad cars.	Used by employés and sold to local trade at mines.	Used for steam and heat at mines.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
Susquehanna and Sullivan.....	419,839	399,315	4,569	15,955
Lackawanna.....	9,109,330	7,978,765	791,716	338,849
Luzerne.....	16,892,099	15,189,715	599,968	1,102,416
Carbon.....	1,252,636	1,101,018	26,195	125,423
Schuylkill.....	9,238,434	7,996,874	246,086	985,474
Columbia.....	640,692	550,510	21,026	69,156
Northumberland.....	3,234,900	2,851,769	66,242	316,889
Dauphin.....	711,928	549,076	30,708	132,144
Total.....	41,489,858	36,617,042	1,786,510	3,086,306

The largest actual shipment during any year in the history of the trade was made in 1888, being 38,145,178 tons of 2,240 pounds. The largest actual shipment for any one month was 4,187,527 tons, in October, 1888. The largest actual shipments ever made in each of the months of any year to December, 1890, inclusive, are given in the table below, and show that, if the mines should be operated as actively in each month of the year as they ever have been in that month, the product for the year would be a little less than 40,000,000 long tons.

Largest shipments of anthracite for each month of any year.

Years.	Months.	Tonnage.
1889	January	2,622,529
1887	February	2,551,003
1887	March	2,911,272
1888	April	2,856,593
1889	May	3,016,531
1889	June	3,038,216
1889	July	3,627,522
1888	August	4,097,563
1888	September	3,916,326
1888	October	4,187,527
1888	November	3,718,652
1887	December	3,068,079
	Maximum shipment practicable	39,611,813

Average monthly tonnage based upon the largest shipments ever made..... 3,300,984

Average annual shipments during ten years ending with 1889..... 31,551,301

Average annual shipments during five years ending with 1889..... 34,390,868

The initial lines of transportation from the anthracite coal fields are operated by the following companies:

- Delaware, Lackawanna and Western Railroad Company.
- New York, Susquehanna and Western Railroad Company.
- New York, Ontario and Western Railroad Company.
- Delaware and Hudson Canal Company.
- Erie and Wyoming Valley Railroad Company.
- Central Railroad Company of New Jersey.
- Lehigh Valley Railroad Company.
- Pennsylvania Railroad Company.
- Philadelphia and Reading Railroad Company.
- New York, Lake Erie and Western Railroad Company.

The reports formerly made showing the shipments of coal by the respective initial railroad lines traversing the anthracite fields of Pennsylvania were discontinued at the close of 1888, owing to the confusion arising from the liability to duplicate certain tonnages originating upon one line and delivered to another near the mines for transportation to market. It is therefore impracticable to continue the comparative tables of such shipments which have hitherto appeared in this volume.

The tables below show the general distribution of the anthracite coal for 1889 and 1890, shipped as above stated, based upon the most reliable data available. The Survey has not been able to obtain reports for 1890 sufficiently complete from the transportation lines of the country to insure the degree of accuracy desired, and has therefore been compelled to approximate in many cases.

Distribution of anthracite coal for 1889.

Sections.	Long tons.	Per cent.
Pennsylvania, New York, and New Jersey.....	22,314,331	63.02
New England States.....	5,407,357	15.27
Western States.....	4,922,076	13.90
Southern States.....	1,613,120	4.56
Pacific Coast.....	20,900	0.06
Canada.....	1,094,736	3.09
Foreign.....	35,190	0.10
Total.....	35,407,710	100.00

Distribution of anthracite coal for 1890.

Sections.	Long tons.	Per cent.
Pennsylvania, New York, and New Jersey.....	22, 719, 221	62. 05
New England States.....	5, 442, 556	14. 86
Western States.....	5, 459, 320	14. 91
Southern States.....	1, 742, 521	4. 76
Pacific Coast.....	11, 100	0. 03
Canada.....	1, 196, 738	3. 27
Foreign.....	45, 536	0. 12
Total.....	36, 617, 042	100. 00

The cost of mining anthracite coal and preparing it for shipment is governed by so many conditions, which vary greatly in different localities, and in the diversity of practice, that no compilation would be of value which comprehended any large number of operations. A valuable and interesting statement, however, upon this subject, from data compiled from the books of a single establishment, was prepared by the late Dr. Charles A. Ashburner, and was published in the volume of Mineral Resources for 1888, pp. 329, 330, to which attention is directed.

During the past year much interest has been developed upon the subject of the utilization of the anthracite coal waste, i. e., the screenings resulting in the preparation of the coal into regular sizes at the breakers. This waste, aside from the fact that it constitutes a large per cent of the product which brings no return to the operator and is therefore a loss in the mining account, has become a source of additional expense owing to the difficulty of disposing of it in the vicinity of the breaker. Millions of tons of pure coal are at this moment lying in unsightly pyramids throughout the entire region. The governor of the State has appointed a commission consisting of Hon. Eckley B. Coxe, Mr. P. W. Sheaffer, and Mr. J. A. Price, to consider this subject and report upon the same to the next session of the legislature. This commission composed of gentlemen of eminent ability, has collected a vast amount of information to be presented in their forthcoming report, which is awaited with great interest. Mr. Coxe, in an address delivered before the Wilkesbarre Board of Trade, makes this reference to the subject:

“The future prosperity of the (Wyoming) Valley depends in a great measure upon the utilization of the waste coal product. This can not be done, however, by sending it away to other points, but by bringing here such enterprises as can use this waste fuel with profit. If instead of shipping the smaller sizes of coal to distant points and selling it for 30 or 40 cents a ton, we had industries here that would use it in the employment of labor, the result would be much more satisfactory to the people of this region. Wherever we travel in the anthracite region we see vast piles of culm blazing, almost priceless fuel going up in smoke—wasted. Every pound of that culm produces heat that might be used to advantage in scores of industries were it only utilized as it

should be. This gives us something to think about. Wherever such waste is seen, we know that somewhere in this country people are going without shoes who might be clothed and fed were the waste stopped and the waste material utilized."

Various schemes for utilizing this waste, by the manufacture of compressed fuel, in combination with combustible volatile substances, have been attempted, but none as yet have attained commercial importance in competition with the natural product.

Much confusion and inconvenience in the marketing of anthracite coal has been, in times past, occasioned by the want of uniformity in the sizes of the coal produced. At a meeting held for the purpose in Wilkesbarre this subject was considered, and the following sizes of meshes were adopted, to take effect January 1, 1891:

- Egg, through $2\frac{1}{4}$ inches and over 2 inches.
- Stove, through 2 inches and over $1\frac{1}{4}$ inches.
- Chestnut, through $1\frac{1}{4}$ inches and over $\frac{3}{4}$ inch.
- Pea, through $\frac{3}{4}$ inch and over $\frac{1}{2}$ inch.
- Buckwheat, through $\frac{1}{2}$ inch and over $\frac{1}{4}$ inch.
- No. 2 buckwheat, through $\frac{1}{4}$ inch and over $\frac{1}{8}$ inch.

It will be observed that the size known as "small stove" has been omitted. The meeting at which the above action was taken was composed of operators from every part of the anthracite fields, and represented over 90 per cent. of the entire production. Apropos of the classification of anthracite coal by sizes, the following interesting statement has been prepared by Mr. F. E. Saward, of the *Coal Trade Journal*, relating to the changes taking place in the proportions of the several sizes required by the markets:

"It is an interesting fact that while the output of anthracite has increased in the past ten years, there has been a radical change in the proportions of each size of coal made at the breakers. Why this is so is known to those who are more familiar with the course of events, but the average reader may have lost sight of the fact that the furnace trade has dropped off, while the steam coal trade has changed from one size to another.

"New markets have been opened for the increased quantity of the domestic sizes that have been made, but the making of so great a quantity has caused a lessening of the price, and it has also caused a larger percentage of the smaller coals (now largely used for steam) to be made; these have been disposed of for steam purposes as against soft or bituminous coals. It is doubtful if the gross result in dollars and cents is much beyond the result for the quantity marketed ten years ago.

"We have been led to these conclusions by the perusal of the figures showing the percentages made by one of the larger producers of Lehigh coal in the years 1879 and in 1889.

Percentage output of various sizes of anthracite made by a producer in the Lehigh region.

Sizes.	1879.	1889.
Lump and steamer	15.8	8.91
Broken	19.4	16.69
Egg	15.9	13.13
Stove	15.8	13.35
Chestnut	17.4	15.58
Pea	15.2	14.27
Buckwheat and small coals.....	0.5	18.07

“The percentages made at all the collieries in the Lehigh district in 1879 were as follows:

Percentages of sizes of anthracite in the Lehigh district in 1879.

Sizes.	Per cent.	Sizes.	Per cent.
Lump	24.6	Stove.....	18.2
Steamer	2.3	Chestnut.....	16.7
Broken	14.5	Pea	7.9
Egg	15.5	Buckwheat.....	0.3

“It is doubted if the result would show them to be very far away from those figures recorded above as for one of the principal concerns. That shows a very great increase in the small coals below chestnut, at any rate.

“One of the larger producers in the Wyoming district, whence so much free-burning coal is had, makes the following comparative showing of percentages for the years 1879 and 1889:

Percentage of various sizes of anthracite made by a producer in the Wyoming region.

Sizes.	1879.	1889.
Lump and steamer.....	11.13	11.00
Broken	16.11	11.00
Egg	14.06	15.00
Stove	30.64	25.00
Chestnut	20.32	21.00
Pea	7.47	9.00
Buckwheat and small.....	0.27	8.00

“This shows a loss in broken (or former steamer size) and in the stove, to the increase of the smaller sizes, such as pea, buckwheat, etc.

“The percentages of Schuylkill coal have also changed, as the following will show; the figures are the average of all grades of coal, both hard and free burning:

Percentage of various sizes of anthracite produced in the Schuylkill region.

Sizes.	1883.	1889.
Lump and steamer.....	14.3	9.4
Broken	14.7	14.5
Egg	15.5	13.6
Stove	19.0	14.8
Small stove.....	5.1	8.4
Chestnut	11.6	12.8
Pea	14.8	18.3
Buckwheat.....	5.0	8.2

"The changes do not appear so radical in this last statement, for the figures are not at hand for the earlier year named in the other comparative statements, but it is sufficient to show that the growth of the anthracite trade has been mainly on the small coals.

Recapitulation.

	1879.			1889.		
	Lump and steamer.	Domestic.	Smalls.	Lump and steamer.	Domestic.	Smalls.
Lehigh	15.80	68.50	15.70	8.91	58.75	32.34
Wyoming	11.13	81.13	7.74	11.00	72.00	17.00
Schuylkill.....	14.30	65.90	19.80	9.40	64.10	26.50
Average	13.74	71.84	14.42	9.77	64.95	25.28

"In 1879 the total product was 26,142,689 tons. The percentages were as follows:

Percentages of sizes of anthracite from the Schuylkill region in 1879.

Sizes.	Per cent.	Tons.
Lump and steamer.....	13.74	3,592,005
Domestic.....	71.84	18,780,908
Smalls.....	14.42	3,769,775

"In 1889 the total product was 35,407,710 tons. The percentages were as follows:

Percentages of sizes of anthracite from the Schuylkill region in 1889.

Sizes.	Per cent.	Tons.
Lump and steamer.....	9.77	3,459,333
Domestic.....	64.95	23,997,307
Smalls.....	25.28	8,951,069

"In the item classed as 'domestic' is included all sizes from broken to chestnut—both included—though, as is well known, not all this coal goes for domestic or house use, but the proportion now is infinitely greater than it was ten years ago, for broken and chestnut were then largely used as steam raisers.

"The loss is great in the Schuylkill and Lehigh lump, as these districts supply the furnace trade, which now takes coke; the Wyoming lump is mainly for steam, and that trade appears to have been held."

During the year 1890 extensive developments have been in progress in all parts of the anthracite coal fields. In the southern field, between Tremont and Minersville, new collieries are being constructed by the Lehigh Valley Coal Company, Mr. Calvin Pardee, Messrs. J. P. &

J. H. Hosie, and the Philadelphia and Reading Coal and Iron Company. The latter company has completed the North Brookside and Good Spring collieries in the Lykens district. Silver Creek colliery in the East Schuylkill district, and Maple Hill colliery in the East Mahanoy district. The Midvalley colliery of Messrs. Righter, Leisenring & Co. will begin shipments early in 1891. Oneida colliery of Messrs. Coxé Brothers & Co. is nearly ready for operation.

In the northern field shipments have begun from the following recently completed collieries: Clinton tunnel, Ontario, Washington, Wm. A., Babylon, Pettibone, and Mount Lookout.

The Schuylkill and Lehigh Valley railroad has been opened between Minersville and Lizard Creek Junction, where it connects with the Lehigh Valley system.

The New York, Ontario and Western railroad extension, from Hancock, New York, to Scranton, Pennsylvania, has been opened for traffic, and is receiving coal from several collieries located between Forest City and Scranton.

The large breaker attached to the Neilson colliery of Messrs. J. Langdon & Co., near Shamokin, Pennsylvania, was destroyed by fire May 16, 1890. The central breaker of the Delaware, Lackawanna and Western Railroad Company, near Hyde Park, was destroyed by fire August 18, 1890.

On August 17, several large breakers in the vicinity of Wilkesbarre, Pennsylvania, were damaged by a windstorm. All of them, however, were restored and put in operation before the close of the year.

Extensive storage yards have been constructed at Landingville and at Mahanoy Plane by the Philadelphia and Reading Railroad Company; at South Plainfield by the Lehigh Valley Railroad Company; and at Hampton Junction by the Central Railroad of New Jersey. These, together with the increased storage and dock facilities recently completed by the Lehigh Valley, the Philadelphia and Reading, the Delaware, Lackawanna and Western, and the New York, Lake Erie and Western interests at Buffalo and other lake ports, will enable the companies to conduct mining operations with more regularity, and facilitate the movement of coal during periods of slack trade, thus insuring not only more steady work for the employes at the mines, but will enable the companies to meet demands for particular sizes on short notice. Not the least of the advantages gained by the establishments of these storage yards is the increased expedition in the handling of cars.

The continued mild weather in the early part of the year, coupled with the constant tendency to overproduction caused a weakening of prices in the Eastern markets which had its effect also upon the Western rates, and before the close of the first half of the year prices had reached a point lower than at the corresponding period in 1889. Many retailers and consumers, taking advantage of this condition of affairs, increased their orders and secured sufficient coal to meet their require-

ments until far into the autumn and early winter months. Efforts were made to advance prices during the latter half of the year, and the advances were announced by the usual circulars, but to what extent these prices were obtained it is difficult to say. The product was not controlled, during the year, as contemplated by the action of the producers to meet the actual demands of the markets; nevertheless, the conditions at the close of the year were not discouraging. The stocks at tide water shipping points at the close of the year were only about one-half what they were at the beginning, while the shipments were half a million tons greater during the year 1890 than the previous year. The regular increase in the consumption of anthracite coal goes on from year to year, though it is difficult to determine the exact ratio. The tables show, approximately, the percentage in general distribution, but it is well understood that all this is subject to modification, owing to the large and varying quantities of coal in stock at the interior points of storage, all of which has been counted in the tonnage statement.

Bituminous coal has not made the inroads upon the anthracite markets predicted by those interested in the former fuel. The small sizes of anthracite, pea, buckwheat, etc., being supplied in larger quantities and with more certainty of steady supply, have not only held their own but have found new demands at fairly remunerative prices. The rates of transportation, of course, must be low, and this has been recognized by the railroad companies who provide special tariffs for the small sizes.

PENNSYLVANIA BITUMINOUS COAL.

Total product in 1889, 36,174,089 short tons; spot value, \$27,953,315.
Total product in 1890, 42,302,173 short tons; spot value, \$35,376,916.

The bituminous coal fields of Pennsylvania form the northeastern end of the Appalachian field. The total area underlaid by workable coal beds is about 900 square miles. The coal mines of the State are confined to twenty-seven counties, later enumerated. The largest coal area is contained in the western and southwestern parts of the State, extending west from the crest of the Allegheny mountains to the Ohio line, and southwest of a line drawn from New Castle, in Lawrence county, northeast to Kane, in McKean county, and thence southeast in the direction of Bellefonte, in Center county. Ragged edges of broken Coal Measures extend beyond these lines. In addition, isolated areas are found in the Wellersburg Basin, in Somerset county; in the Broad Top coal field, in Huntingdon, Blair, and Fulton counties; in the Tipton field, west of Altoona, in Blair county, and in the fields in Bradford and Tioga counties. The characteristics of the Coal Measures in which these beds occur have been described in former reports.

Notwithstanding the fact that the total product of bituminous coal in the United States for 1889 was 2,485,812 short tons less than in 1888, the production of Pennsylvania increased 2,377,362 short tons, a gain nearly as great as the total decrease, and shows the loss sustained by

other States to have been 4,863,174 short tons. The increase in the product of bituminous coal in Pennsylvania in 1888 was 2,279,871 short tons. This was in a year of general increase and represented only about 17 per cent. of the total gain. The increase, from a comparative standpoint, in 1889 is a remarkable one. The returns for 1890 show an increase in the product of Pennsylvania bituminous coal of 6,128,084 short tons. The details of the respective increases and decreases in the production, by counties, for the two years is shown in the following table, together with a statement of the production in 1886, 1887, and 1888:

Comparative statistics of the Pennsylvania bituminous mines, by counties.

Counties.	1886.				1887.				1888.				1889.				1890.			
	Short tons.				Short tons.				Short tons.				Short tons.				Short tons.			
	Total product.	Increase over 1885.	Decrease from 1885.	Total product.	Total product.	Increase over 1888.	Decrease from 1888.	Total product.	Total product.	Increase over 1889.	Decrease from 1889.	Total product.	Total product.	Increase over 1889.	Decrease from 1889.	Total product.	Total product.	Increase over 1889.	Decrease from 1889.	
Allegheny.....	4,202,086	4,680,324	5,375,505	4,717,431	4,717,431	5,375,505	5,375,505	4,717,431	4,894,372	176,941	4,894,372	4,894,372	
Armstrong.....	210,856	235,221	226,093	289,218	289,218	226,093	226,093	289,218	380,554	91,336	380,554	380,554	
Beaver.....	208,820	197,863	63,900	93,461	93,461	63,900	63,900	93,461	139,117	45,656	139,117	139,117	
Bedford.....	173,372	311,452	248,159	257,455	257,455	248,159	248,159	257,455	445,192	187,739	445,192	445,192	
Blair.....	305,695	287,367	314,013	215,410	215,410	314,013	314,013	215,410	298,196	82,786	298,196	298,196	
Bradford.....	296,908	167,416	163,851	129,141	129,141	163,851	163,851	129,141	126,687	2,454	126,687	126,687	
Butler.....	162,306	161,764	194,715	288,591	288,591	194,715	194,715	288,591	167,578	121,013	167,578	167,578	
Cambria.....	1,222,028	1,421,980	1,540,400	1,751,654	1,751,654	1,540,400	1,540,400	1,751,654	2,790,954	1,039,290	2,790,954	2,790,954	
Cameron.....	3,200	3,000	3,000	2,300	2,300	3,000	3,000	2,300	
Center.....	313,383	508,255	382,770	395,127	395,127	382,770	382,770	395,127	452,114	56,987	452,114	452,114	
Clarion.....	429,544	593,758	535,192	596,589	596,589	535,192	535,192	596,589	512,387	512,387	512,387	
Clearfield.....	3,753,986	5,180,311	5,398,981	5,224,506	5,224,506	5,398,981	5,398,981	5,224,506	6,651,587	1,427,081	6,651,587	6,651,587	
Cleintown.....	32,000	106,000	106,000	32,000	32,000	106,000	159,000	53,000	159,000	159,000	
Elk.....	526,036	609,757	555,960	614,113	614,113	555,960	555,960	614,113	1,121,534	507,421	1,121,534	1,121,534	
Fayette.....	4,434,613	4,540,322	5,208,993	5,897,254	5,897,254	5,208,993	5,208,993	5,897,254	6,413,081	515,827	6,413,081	6,413,081	
Greene.....	5,600	3,002	5,323	53,714	53,714	5,323	5,323	53,714	(b)	(d)	(b)	(b)	
Huntington.....	313,581	265,479	281,823	280,133	280,133	281,823	281,823	280,133	322,630	42,497	322,630	322,630	
Indiana.....	103,615	207,507	157,255	153,698	153,698	157,255	157,255	153,698	357,580	203,882	357,580	357,580	
Jefferson.....	1,023,186	1,693,482	2,275,349	2,896,487	2,896,487	2,275,349	2,275,349	2,896,487	2,850,799	2,850,799	2,850,799	
Lawrence.....	101,154	135,361	106,921	143,410	143,410	106,921	106,921	143,410	140,528	140,528	140,528	
McKean.....	617	9,214	10,443	11,500	11,500	10,443	10,443	11,500	(c)	(c)	(c)	
Mercer.....	537,712	539,721	487,122	575,751	575,751	487,122	487,122	575,751	524,319	524,319	524,319	
Somerset.....	349,926	416,240	370,228	442,027	442,027	370,228	370,228	442,027	522,796	80,769	522,796	522,796	
Tioga.....	1,384,800	1,328,963	1,106,146	1,036,175	1,036,175	1,106,146	1,106,146	1,036,175	903,997	903,997	903,997	
Venango.....	2,500	2,296	2,000	6,911	6,911	2,000	2,000	6,911	(d)	(d)	(d)	
Washington.....	1,612,407	1,751,615	1,793,022	2,364,901	2,364,901	1,793,022	1,793,022	2,364,901	2,826,687	471,766	2,826,687	2,826,687	
Westmoreland.....	5,446,480	6,074,486	6,519,773	7,631,124	7,631,124	6,519,773	6,519,773	7,631,124	8,290,504	659,380	8,290,504	8,290,504	
Unreported mines and country banks employing less than 10 miners (estimated).....	200,000	240,000	(a)	(a)	240,000	240,000	(a)	(c)1,000,000	925,575	(c)1,000,000	(c)1,000,000	
Total.....	27,094,501	31,516,856	33,796,727	36,174,089	36,174,089	33,796,727	33,796,727	36,174,089	42,302,173	6,567,933	42,302,173	42,302,173	
Net increase.....	4,422,355	2,279,871	2,377,362	2,377,362	2,279,871	2,279,871	2,377,362	6,128,084	6,128,084	6,128,084	6,128,084	

a Included in county distribution. b Included in product of country banks. c Estimate based on the census returns for small banks, which for 1889 were, approximately 800,000 short tons, showing that previous estimates of the product from this source were too small. d All product from country banks and decrease deducted from total estimated production.

It will be seen from the foregoing table that in 1889 Allegheny county suffered the greatest loss in tonnage, having over 66 per cent. of the loss sustained in all the counties in which decreases in product occurred. Westmoreland county showed a remarkable increase, being nearly one-half of the total net increase of the State, and exceeding by 8,058 short tons the aggregate increase of the county from 1886 to 1888. Fayette county came second in increased tonnage, with a gain of 688,261 short tons; Jefferson third, with an increase of 621,138 short tons, and Washington, fourth, shows 571,879 short tons in excess of the preceding year's product. In remarking upon the decrease of product in Allegheny county it may be well to call attention to the statement made under the coal trade review of Pittsburg, that the shipments had fallen off 29,993,900 bushels (of 76 pounds), or something over 1,000,000 short tons. Allowing for a production based upon an expectation of a demand which did not materialize, it will be seen that the two statements are compatible, and the fact that the decrease in production was not so great as the decrease of shipments will in part account for the comparatively small increased production in 1890.

In 1890 the county showing the greatest gain on the preceding year was Clearfield, whose product in 1890 was 1,427,081 short tons greater than in 1889. Cambria county increased 1,039,290 short tons, and the other notable increases were in Westmoreland county, 659,380 short tons; Fayette county, 515,827 short tons; Elk county, 507,421 short tons, and Washington county, 471,766 short tons. The counties having an increased production in 1889 and an apparent decreased product in 1890 were Butler, Clarion, Jefferson, Lawrence, and Mercer. But against this must be set the fact that the product of small mines is included in the county distribution in 1889 and not accounted for in 1890, except in a total estimate for the State.

The following tables show the bituminous coal product of Pennsylvania in 1889 and 1890, by counties, with the distribution and value:

Bituminous coal product of Pennsylvania in 1889, by counties.

Counties.	Disposition of total product.				Total product.	Value of total product at mines.	Average number of persons employed.
	Loaded at mines for shipment on railroad cars and boats.	Used by employes and sold to local trade.	Used for steam and heat at mines.	Made into coke.			
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Allegheny	4,464,376	204,282	25,103	23,670	4,717,431	\$4,000,104	9,386
Armstrong	229,402	59,460	356	289,218	210,067	459
Beaver	44,932	48,180	249	100	93,461	110,604	162
Bedford	237,554	6,932	3,889	9,078	257,453	205,672	560
Blair	80,777	4,188	2,918	127,527	215,410	210,466	466
Bradford	121,976	6,365	800	129,141	171,387	321
Butler	183,477	94,064	2,162	8,888	288,591	270,394	451
Cambria	1,174,508	179,525	7,296	390,335	1,751,664	1,348,484	2,791
Center	389,331	4,964	115	9,717	395,127	311,544	750
Clarion	535,251	57,500	3,370	468	596,589	430,850	940
Clearfield	4,937,506	89,580	19,651	177,769	5,224,506	4,403,551	7,703
Elk	596,014	7,549	4,789	5,761	614,113	498,728	1,185
Fayette	593,149	111,714	101,272	5,091,119	5,897,254	3,702,548	6,567
Greene	53,714	53,714	57,307
Huntingdon	185,799	9,111	3,129	82,094	280,133	211,597	538
Indiana	53,498	80,200	20,000	153,698	124,088	139
Jefferson	2,371,703	53,684	11,403	459,697	2,896,487	2,117,531	3,738
Lawrence	117,091	25,696	620	143,410	150,537	267
Mercer	509,737	51,231	14,783	575,751	511,202	1,094
Somerset	370,791	50,909	586	19,741	442,027	308,400	525
Tioga	1,010,544	12,572	8,543	4,516	1,036,175	1,264,889	2,400
Washington	2,261,040	64,847	11,972	27,042	2,364,901	1,557,486	4,005
Westmoreland	2,488,873	299,874	109,597	3,732,780	7,631,124	5,674,493	9,109
Cameron, Clinton, Lycoming, McKean and Venango.....	111,581	14,510	334	286	126,711	101,386	224
The State.....	24,059,913	1,590,651	332,937	10,190,588	36,174,089	27,953,315	53,780

Bituminous coal product of Pennsylvania in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Allegheny	4,643,050	174,870	37,496	38,956	4,894,372	\$4,534,708	198	9,036
Armstrong	341,447	11,064	2,480	25,563	380,554	275,011	251	661
Beaver	119,216	18,355	1,286	260	139,117	145,946	251	205
Bedford	305,282	10,279	1,400	128,231	445,192	356,005	288	662
Blair	163,399	1,852	506	132,439	298,196	241,678	284	595
Bradford	121,359	1,355	3,973	126,687	161,751	196	292
Butler	147,935	9,372	2,471	7,800	167,578	146,162	237	314
Cambria	2,487,414	26,348	15,186	262,006	2,790,954	2,332,997	361	4,140
Center	378,384	5,684	200	67,846	452,114	356,121	230	623
Clarion	501,563	8,425	2,399	512,397	386,617	237	938
Clearfield	6,351,454	9,629	61,715	228,789	6,651,587	5,642,098	236	9,324
Clinton	159,000	159,000	123,362	265	200
Elk	1,064,372	11,788	374	45,000	1,121,534	942,081	255	1,871
Fayette	996,469	12,044	128,264	5,281,304	6,413,081	4,931,015	247	6,503
Huntingdon	229,855	8,486	3,222	81,067	322,630	247,364	237	611
Indiana	283,102	2,184	112	72,182	357,580	294,389	245	668
Jefferson	2,678,522	7,805	6,820	157,662	2,860,799	2,421,960	245	3,971
Lawrence	94,908	45,108	511	140,528	142,682	232	307
Mercer	488,205	25,313	10,801	524,319	446,392	231	1,023
Somerset	486,322	10,041	593	25,840	522,796	341,518	225	646
Tioga	852,621	19,986	11,405	19,985	903,997	995,936	192	2,019
Washington	2,775,610	8,253	12,454	40,350	2,836,607	2,649,627	227	4,644
Westmoreland	3,619,434	45,075	97,169	4,528,826	8,290,504	6,691,532	228	12,080
Small mines	1,000,000	1,000,000	750,000
Total ...	29,288,923	1,473,317	395,837	11,144,096	42,302,173	35,376,916	(a)232	61,333

a Average for the State.

ALLEGHENY COUNTY.

(Coal produced in 1889, 4,717,431 short tons; 1890, 4,894,372 short tons.)

The coal product of Allegheny in 1888 was 894,581 short tons in excess of the product of the preceding year, and this gain was greater than that of any other county with the exception of Westmoreland. This was followed by a revulsion of trade in 1889, for the product decreased 858,074 short tons, falling back to within 36,507 short tons of the product of 1887. In 1890 the product was 176,941 short tons more than in 1889; it was 681,133 short tons less than 1888, and 213,448 short tons more than in 1887.

The following table exhibits the product of Allegheny county since 1884:

Coal product of Allegheny county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	2,863,631	1888	5,575,505
1885	3,588,244	1889	4,717,431
1886	4,202,086	1890	4,894,372
1887	4,680,924		

The following table shows the shipments from the Pittsburg district by slack-water navigation down the Monongahela and Ohio rivers since 1860:

Shipments of Pittsburg coal by slack-water navigation since 1860.

Years.	Quantity.	Years.	Quantity.
	<i>Short tons.</i>		<i>Short tons.</i>
1860	1,517,909	1876	2,495,800
1861	834,630	1877	2,677,460
1862	743,358	1878	2,797,530
1863	1,134,150	1879	2,623,232
1864	1,402,828	1880	3,361,934
1865	1,580,791	1881	3,450,186
1866	1,704,212	1882	4,057,384
1867	1,202,908	1883	4,339,492
1868	1,812,040	1884	3,170,900
1869	2,100,504	1885	3,298,200
1870	2,303,856	1886	4,123,945
1871	1,944,852	1887	3,065,240
1872	2,291,220	1888	4,498,430
1873	2,094,312	1889	4,250,000
1874	2,503,504	1890	4,400,000
1875	2,275,265		

ARMSTRONG COUNTY.

(Coal produced in 1889, 289,218 short tons; 1890, 380,554 short tons.)

This county produced 9,128 tons less in 1888 than in 1887. The product in 1889 was 63,125 tons more than in 1888, and an increase of 91,336 tons over 1889 is noted in the product of 1890. The annual production of Armstrong county for seven years has been as follows:

Coal product of Armstrong county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	170, 826	1888	226, 093
1885	139, 327	1889	289, 218
1886	210, 856	1890	380, 554
1887	235, 221		

BEAVER COUNTY.

(Coal produced in 1889, 93,461 short tons; 1890, 139,117 short tons.)

The product of coal in Beaver county in 1889 was 29,561 short tons more than in 1888, in which year the product fell off two-thirds from 1887. In 1890 a further gain of 45,656 tons was made, but the loss of 1888 was not made up, the product of 1890 being still 58,746 tons short of the yield in 1887.

Coal product of Beaver county, Pennsylvania, for seven years.

Years.	Short tons.	Years.	Short tons.
1884	156, 695	1888	63, 900
1885	184, 631	1889	93, 461
1886	208, 820	1890	139, 117
1887	197, 863		

BEDFORD COUNTY.

(Coal produced in 1889, 257,453 short tons; 1890, 445,192 short tons.)

The coal mines of this county, together with those of Huntington and the greater portion of those of Blair, are located in the broad top semi-bituminous coal basin. There was an increased production in 1889 over 1888 of 9,294 short tons, followed by a large increase in 1890 of 187,739 tons.

The coal beds of this county belong to the Lower Productive Coal Measures. The names which have been adopted for these coal beds have been local, since it has only been within the last few years that the geological survey of the State has established the identity of these coal beds with those of the Freeport, Kittanning, and Clarion beds of the western Pennsylvania bituminous coal fields.

The annual production of Bedford county for seven years has been as follows:

Coal product of Bedford county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	69, 770	1888	248, 159
1885	107, 694	1889	257, 453
1886	173, 372	1890	445, 192
1887	311, 452		

BLAIR COUNTY.

(Coal produced in 1889, 215,410 short tons; 1890, 298,196 short tons.)

The total product in this county in 1889 was 98,603 tons less than in 1888. In 1890 the product increased 82,786 tons over 1889. The falling off in 1889 was due, not to the suspension of any one or more mines, but to a decreased output at each one of the seven important mines of the county. The reaction in 1890 was also participated in by all the producing companies with one exception.

Coal product of Blair county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	208,541	1888	314,013
1885	205,075	1889	215,410
1886	305,095	1890	298,196
1887	287,307		

BRADFORD COUNTY.

(Coal produced in 1889, 129,141 short tons; 1890, 126,687 short tons.)

The annual coal product of this county shows a steady decrease in amount since 1884. The decrease in 1889 from 1888 was 34,710 short tons. The succeeding decrease in 1890 was 2,454 short tons. Only two companies are operating in the county on a commercial scale, the Towanda Coal Company and the Long Valley Coal Company, the former having been producing coal continuously since 1856. The following table exhibits the total product of the county since 1884:

Coal product of Bradford county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	313,575	1888	163,851
1885	249,920	1889	129,141
1886	206,998	1890	126,687
1887	167,416		

BUTLER COUNTY.

(Coal produced in 1889, 288,591 short tons; 1890, 167,578 short tons.)

The total product of this county for 1888 was reported at 194,715 short tons. The seemingly large increase in 1889, and as notable a decrease in 1890, are due simply to the numerous small mines in the county, whose product, included in the returns for 1889, was 91,615 short tons. Deducting this factor from the total product in 1889 and comparing with the statistics for the preceding and succeeding years, it shows an increase over the product of 1889 of 2,261 short tons and a decrease in 1890 of 29,398 tons.

Coal product of Butler county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	151,355	1888	194,715
1885	85,429	1889	288,591
1886	162,306	1890	167,578
1887	161,764		

CAMBRIA COUNTY.

(Coal produced in 1889, 1,751,664 short tons; 1890, 2,790,954 short tons.)

The coal product of Cambria county has increased each year since 1884. The increase in 1889 over the preceding year was 211,204 short tons, or nearly 14 per cent., while that in 1890 was 1,039,290 short tons, or within a fraction of 60 per cent. greater than the output of 1889. With the exception of Clearfield, the gain in the product of Cambria county was the largest in the State during the year, being 379,910 tons more than the gain of Westmoreland county, which comes third in increased production.

The following table exhibits the annual output of the coal mines of Cambria county since 1884:

Coal product of Cambria county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	659,843	1888	1,540,460
1885	1,037,000	1889	1,751,664
1886	1,222,028	1890	2,790,954
1887	1,421,980		

CAMERON COUNTY.

The product of coal in Cameron county in 1889 was 2,300 short tons, the output of one mine which went into the hands of a receiver in 1890, and no production was reported for that year.

CENTER COUNTY.

(Coal produced in 1889, 395,127 short tons; 1890, 452,114 short tons.)

The total product of this county for 1889 was 12,357 tons greater than during the previous year. In 1890 a further increase of 56,987 short tons was made.

Although the coal mined in the Snow Shoe basin in Center county has long been favorably known by the coal trade as a superior coal, yet the limited areas which are underlaid by coal beds, and the cost of mining as compared to more favorable conditions which exist in Clear-

field county, immediately to the west, have had a direct influence in diminishing the product of Center county. The large increase in the product of Clearfield county in 1890 and comparatively small gain in Center afford abundant proof of the advantages possessed by the former.

Coal product of Center county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	216,422	1888	382,770
1885	373,504	1889	395,127
1886	313,383	1890	452,114
1887	508,255		

CLARION COUNTY.

(Coal produced in 1889, 596,589 short tons; 1890, 512,387 short tons.)

Clarion county is one of the five bituminous coal producers which had an increased product in 1889, and a falling off in 1890 when the general tendency was toward increased business. The total product of this county in 1889 was 61,397 tons greater than during the previous year, and in 1890 84,202 tons less than during 1889. The annual production of the county for seven years has been as follows:

Coal product of Clarion county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	329,973	1888	535,192
1885	299,216	1889	596,589
1886	429,544	1890	512,387
1887	593,758		

CLEARFIELD COUNTY.

(Coal produced in 1889, 5,224,506 short tons; 1890, 6,651,587 short tons.)

The general depression in the coal trade in 1889 is exemplified by the product of Clearfield county, which from having a steady annual increase for five years, fell off in 1889, 174,475 short tons and increased 1,427,081 tons in 1890. The average yearly increase from 1884 to 1888 was 805,359 short tons, and from 1884 to 1890, 745,507 short tons, indicating that an ordinary business in 1889 would have given Clearfield county a practically steady annual increase in product.

The rapid development of the mines of Clearfield county is sufficiently shown in the coal tonnages of the Tyrone and Clearfield branch of the Pennsylvania railroad during the last twenty-nine years, and also in the tonnages of the Beech Creek railroad, which are given below:

Coal carried over the Tyrone and Clearfield branch railroad during the last twenty-seven years.

Years.	Short tons.	Years.	Short tons.
1862	7, 239	1877	1, 374, 927
1863	24, 330	1878	1, 295, 201
1864	65, 380	1879	1, 631, 120
1865	60, 629	1880	1, 739, 873
1866	107, 878	1881	2, 401, 987
1867	166, 364	1882	2, 838, 970
1868	170, 335	1883	2, 857, 710
1869	259, 994	1884	3, 173, 303
1870	379, 863	1885	2, 901, 613
1871	542, 896	1886	2, 273, 147
1872	431, 915	1887	3, 256, 328
1873	592, 860	1888	3, 389, 864
1874	639, 630	1889	3, 215, 630
1875	928, 297	1890	3, 389, 450
1876	1, 281, 861		

Beech Creek railroad tonnage.

Years.	Short tons.	Years.	Short tons.
1884	234, 751	1888	1, 694, 495
1885	774, 055	1889	1, 556, 930
1886	1, 050, 238	1890	2, 081, 173
1887	1, 351, 579		

Coal product of Clearfield county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	2, 177, 543	1888	5, 398, 981
1885	3, 363, 671	1889	5, 224, 506
1886	3, 753, 986	1890	6, 651, 587
1887	5, 180, 311		

CLINTON COUNTY.

(Coal produced in 1889, 106,000 short tons; 1890, 159,000 short tons.)

There are many isolated areas of the top lands of this county which are underlaid by the lower beds of the Lower Productive Coal Measures. These beds have been prospected and worked on a commercial scale at various times during the past twenty-seven years. The thinness of many of the beds, the poor character of the coal as compared with that in other counties, and their height in the hilltops above the grade of railroad lines have all militated against the extensive development of the coal, although it is estimated that there are between 15,000 and 20,000 acres of land in the county underlaid by workable coal beds, which have an aggregate available tonnage of about 60,000,000 tons. Since 1884, and up to 1888, no product from this county has been reported. In the latter year the product was 32,000 short tons.

ELK COUNTY.

(Coal produced in 1889, 614,113 short tons; 1890, 1,121,534 short tons.)

The total product of this county in 1889 was 58,153 short tons greater than during the previous year, and in 1890 took a remarkable jump, gaining 507,421 short tons over 1889. The largest producer in the county is the Northwestern Mining and Exchange Company, operating both in Elk and Jefferson counties. The annual product of the county for seven years is exhibited in the following table:

Coal product of Elk county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	413, 243	1888	555, 960
1885	537, 826	1889	614, 113
1886	526, 036	1890	1, 121, 534
1887	609, 757		

FAYETTE COUNTY.

(Coal produced in 1889, 5,897,254 short tons; 1890, 6,413,081 short tons.)

The total product of Fayette county has increased very regularly since 1887. The increase in 1888 over the previous year was 668,671 short tons. In 1889 the increase was 688,261 tons, and in 1890 515,827 tons. The largest operator for a number of years has been the H. C. Frick Coke Company, whose total product in this county in 1890 was 3,543,826 tons, of which 3,456,336 tons were made into coke, the remainder, 87,490 tons, being consumed at the mines. Of the total product of the county in 1889, 5,091,119 tons were made into coke, and 5,281,304 tons were so consumed in 1890. The annual product of the county since 1884 has been as follows:

Coal product of Fayette county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	4, 041, 643	1888	5, 208, 993
1885	3, 192, 172	1889	5, 897, 254
1886	4, 494, 613	1890	6, 413, 081
1887	4, 540, 322		

GREENE COUNTY.

The total product of Greene county in 1889 was 53,714 short tons, all of which was from mines not considered of commercial importance and not accounted in the returns for 1890, except in the total estimate for the State. The entire county is underlaid with valuable coal beds, but they are at such depth that the cost of production is too great to admit of competition with more favorable localities.

HUNTINGDON COUNTY.

(Coal produced in 1889, 280,133 short tons; 1890, 322,630 short tons.)

The total product of this county in 1889 was 1,690 tons less than during the previous year. The product in 1890 was 42,497 tons greater than during 1889.

This coal fields of the county are contained exclusively in the Broad Top semi-bituminous field. The mines are opened on both sides of what is known as the Broad Top Mountain field, on both sides of the mountain, being known respectively as the east and west fields.

On account of the superior character of the coal it is much sought for by the trade to supply special consumers. Although a very small area of the southwestern corner of the county is underlaid by coal beds, yet the amount of available coal is very considerable, and there are no facts to warrant the popular impression that the coal beds will be early exhausted, since the amount of available tonnage contained is such as to make it impracticable at the present time to enter into any speculation on this question.

Coal product of Huntingdon county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	212, 587	1888	281, 823
1885	247, 424	1889	280, 133
1886	313, 581	1890	322, 630
1887	265, 479		

Coal carried by the Huntingdon and Broad Top railroad to the Pennsylvania railroad at Huntingdon.

Years.	Short tons.	Years.	Short tons.
1873	350, 245	1882	271, 216
1874	226, 693	1883	196, 534
1875	204, 921	1884	192, 706
1876	159, 779	1885	176, 075
1877	140, 143	1886	385, 796
1878	150, 204	1887	357, 438
1879	141, 594	1888	375, 958
1880	174, 736	1889	376, 801
1881	204, 819	1890	515, 309

Coal carried by the East Broad Top railroad to the Pennsylvania railroad at Mount Union.

Years.	Short tons.	Years.	Short tons.
1875	43, 567	1883	44, 737
1876	66, 104	1884	43, 514
1877	54, 738	1885	51, 878
1878	63, 068	1886	51, 050
1879	67, 929	1887	48, 551
1880	72, 450	1888	55, 795
1881	91, 745	1889	72, 253
1882	99, 095	1890	70, 764

Coal product of Huntingdon county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	212,527	1888	281,823
1885	247,424	1889	280,133
1886	313,581	1890	322,630
1887	265,479		

INDIANA COUNTY.

(Coal produced in 1889, 153,698 short tons; 1890, 357,580 short tons.)

The total product for this county for 1889 was 3,587 tons less than in 1888, and 53,899 tons less than during 1887. The falling off in 1888 and 1889, was due largely to the decreased output of the Saltsburg Coal Company, which fell from 160,000 tons in 1887 to 7,000 in 1889. The product in 1890 increased 203,882 short tons. This gain was due partly to a general increase in the product of all the old producers, and particularly of the Saltsburg Coal Company and the Glenwood Coal Company, which increased from 7,000 and 7,836 tons respectively in 1889 to 87,600 and 69,596 tons in 1890. Five new mines, not reported in 1889, had an aggregate output of 125,152 short tons. The difference in the increase apparent from this statement and that given as the actual increase in the county is due to the exclusion from the returns of 1890 of the product of small mines, which in 1889 amounted to 80,110 short tons. The product of the county for the past seven years has been as follows:

Coal product of Indiana county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	30,758	1888	157,285
1885	82,750	1889	153,698
1886	103,615	1890	357,580
1887	207,597		

JEFFERSON COUNTY.

(Coal produced in 1889, 2,896,487 short tons; 1890, 2,850,799 short tons.)

Jefferson county produced 621,138 more tons in 1889 than in the previous year. The product for 1890 was in reality about the same as in 1889, but the omission of the product of small mines from the total makes an apparent decrease of 45,688 tons. The following table shows the remarkable increases in the amount of coal produced since 1884. The most notable increases occurred in 1886, 1887, and 1888, being approximately 600,000 tons each year and averaging within a fraction of that figure.

Coal product of Jefferson county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	450,079	1888	2,275,349
1885	479,675	1889	2,896,487
1886	1,023,186	1890	2,850,799
1887	1,693,492		

LAWRENCE COUNTY.

(Coal produced in 1889, 143,410 short tons; 1890, 140,528 short tons.)

The total product of this county for 1889 was 36,489 tons greater than during 1888, and (owing to the omission of small mines) 2,882 tons less in 1890 than in 1889. The product of the commercial mines in 1890 was 19,388 greater than the preceding year. Following is the product of the county as reported for seven years:

Coal product of Lawrence county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	42,818	1888	106,921
1885	42,137	1889	143,410
1886	101,154	1890	140,528
1887	125,361		

M^cKEAN COUNTY.

Including the coal taken out by small operators the product of McKean county in 1889 was 11,500 tons. The Buffalo Coal Company, which had been operating in the county on a commercial scale, but almost exclusively for locomotive use, ceased work in 1889, and the only production in 1890 was by individual diggers. The coal beds of the county are thin and the quality of the coal inferior, and these and other disadvantages prevent large operations.

MERCER COUNTY.

(Coal produced in 1889, 575,751 short tons; 1890, 524,319 short tons.)

Mercer county is one of the five in the State which had an increased product in 1889 and a decreased one in 1890, but in this county the falling off is not entirely attributable to the omission of country banks from the product of the latter year. The decrease in the product of commercial mines amounted to 19,935 short tons. Including the product of small mines in 1889, the decrease is shown to be 51,432 tons. The increase in product from 1888 to 1889 was 83,629 tons.

Coal product of Mercer county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884.....	276,350	1888.....	487,122
1885.....	378,508	1889.....	675,751
1886.....	537,712	1890.....	524,319
1887.....	539,721		

SOMERSET COUNTY.

(Coal produced in 1889, 442,027 short tons; 1890, 522,796 short tons.)

From a decreased product of 46,012 short tons in 1888, as compared with that of 1887, the output of the county shows a gain in 1889 of 71,799 short tons, and another gain in 1890 of 80,769 tons. The falling off in 1888 was due largely to decreased production by the principal operating company. With the exception of the depression in 1888 the production of the county has increased steadily since 1884, as shown in the following table:

Coal product of Somerset county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884.....	269,930	1888.....	370,238
1885.....	302,715	1889.....	442,027
1886.....	349,926	1890.....	522,796
1887.....	416,240		

TIOGA COUNTY.

(Coal produced in 1889, 1,036,175 short tons; 1890, 903,997 short tons.)

In Mineral Resources for 1888 it was stated that it was more than probable that the annual production of this county had already passed its maximum limit. The statement seems to have been borne out, for since 1886, when the largest yearly product is reported, the output has decreased annually. The product for 1889 was 69,971 tons less than during 1888, and in 1890, 132,178 tons less than in 1889. Owing to the unfavorable situation of the coal areas, and their scattered condition, the cost of mining is too great to admit of profitable competition with the more western counties of the State, where conditions are more favorable for economical mining. The production of Tioga county since 1884 is shown in the following table:

Coal product of Tioga county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884.....	931,922	1888.....	1,106,146
1885.....	1,067,081	1889.....	1,036,175
1886.....	1,384,800	1890.....	903,997
1887.....	1,328,963		

The product of the Blossburg district since 1872 has been as follows:

Product of coal in Blossburg region since 1872.

Years.	Short tons.	Years.	Short tons.
1872	849, 262	1882	1, 165, 604
1873	991, 057	1883	1, 217, 870
1874	796, 388	1884	1, 018, 342
1875	581, 782	1885	1, 074, 581
1876	616, 984	1886	1, 388, 611
1877	602, 245	1887	1, 329, 239
1878	652, 597	1888	1, 106, 959
1879	874, 010	1889	1, 035, 926
1880	921, 555	1890	888, 771
1881	1, 178, 581		

VENANGO COUNTY.

There are only a few scattered areas in the southeastern part of Venango county, principally in the townships of Irwin, Clinton, Scrubgrass, Dotters, and Potterfield, which are underlaid by coal beds.

All the coal is mined to supply a local trade. This amounted in 1889 to 6,911 short tons.

WASHINGTON COUNTY.

(Coal produced in 1889, 2,364,901 short tons; 1890, 2,836,667 short tons.)

The total amount of coal produced in this county during 1889 was 571,879 tons greater than during 1888, and in 1890, 471,766 tons greater than in 1889. The product of commercial mines in 1890 was 521,697 short tons greater than in 1889, the output of country banks in 1889 being 49,931 short tons. Washington is destined to be one of the greatest coal-producing counties in the State; but on account of the fact that most of the workable coal beds are situated below water level, and will have to be mined from shafts, the large amount of capital which is required to develop these beds and the cost of operation would necessarily be greater than that in the more northern counties, where the coal beds can be mined above water level. These facts will make the development of the coal beds of the county a slow one. At the present time the Pittsburg coal bed supplies almost the entire product of the county, which is shipped by rail to Chicago, Cleveland, Columbus, and intermediate points, and by boat down the Monongahela river to Ohio and Mississippi river points.

Coal product of Washington county from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	707, 262	1888	1, 793, 022
1885	836, 633	1889	2, 364, 901
1886	1, 612, 407	1890	2, 836, 667
1887	1, 751, 615		

WESTMORELAND COUNTY.

(Coal produced in 1889, 7,631,124 short tons; 1890, 8,290,504 short tons.)

Westmoreland continues to be the queen county of the State in the amount of bituminous coal produced. It has for the past seven years produced more coal than any other county in the Pennsylvania bituminous field. In 1889 the total product was 1,733,870 tons greater than that of Fayette county, which came second. In 1890 the product of Westmoreland county was 1,638,917 tons greater than that of Clearfield, which changed places with Fayette in rank of producing importance. The product of Westmoreland county in 1889 was 1,111,351 tons greater than in 1888, and 659,380 tons greater in 1890 than in 1889. The product in 1890 was 754,715 tons greater than the product of commercial mines in 1889. The steady increase in the annual product of the county since 1884 may be seen from the following table:

Coal product of Westmoreland county, Pennsylvania, from 1884 to 1890.

Years.	Short tons.	Years.	Short tons.
1884	3,282,733	1888	6,519,773
1885	3,774,072	1889	7,631,124
1886	5,446,480	1890	8,290,504
1887	6,074,486		

TENNESSEE.

Total product in 1889, 1,925,689 short tons; spot value, \$2,338,309. Total product in 1890, 2,169,585 short tons; spot value, \$2,395,746. The coal product of Tennessee decreased 41,608 short tons in 1889, as compared with that of 1888, but showed an increase in value of \$174,283. In 1890 the output increased 243,886 short tons, and the total value \$57,437.

The following tables show the amount of coal produced in Tennessee in 1889 and 1890, with the value and distribution of the product:

Coal product of Tennessee in 1889, by counties.

Counties.	Disposition of total product.					Total product of coal of all grades for 1889.	Total amount received for coal sold in 1889.	Total number of employes.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.			
	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.		
Anderson.....	442,319		9,700	5,050		457,069	\$531,920	986
Bledsoe.....		225				225	280	
Campbell.....	117,017	691	2,985	1,410	1,000	123,103	146,610	393
Claiborne (a).....								
Cumberland.....		124				124	155	
Fentress.....		25				25	30	
Franklin, Roane, and White.....	53,608	1,401	2,118	10,796	106,628	174,551	318,686	390
Grundy.....	253,891	280	700	2,100	143,136	400,107	395,767	501
Hamilton.....	212,845	893	60	2,110	25,159	241,067	313,991	625
Marion.....	103,288	2,663	11	633	97,328	203,923	230,116	423
Morgan.....	64,037	3,452	100	640		68,229	91,511	135
Overton and Putnam.....		10				10	10	
Rhea.....	2,000	1,505	50		145,639	149,194	164,118	475
Scott.....	85,419	1,908	165	295	20,240	108,027	145,075	180
Van Buren.....		10				10	10	
Warren.....		25				25	30	
Total.....	1,334,424	13,212	15,889	23,034	539,130	1,925,689	2,338,309	4,108

a Prospecting.

Coal product of Tennessee in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.			
Anderson.....	574,053	5,700	2,650		582,403	\$680,249	291	1,325
Campbell.....	119,467	3,100	3,800		126,367	153,790	212	251
Claiborne (a).....								
Franklin, Roane, and White.....	12,000	4,554	7,692	100,356	124,602	141,714	209	315
Grundy.....	176,755	2,849	2,469	167,394	349,467	326,827	310	880
Hamilton.....	231,464	1,000	1,500	43,952	277,896	318,328	285	500
Marion.....	129,440	12,700	800	70,262	213,202	225,403	226	523
Morgan.....	138,633	4,345	540		143,518	158,243	258	5363
Rhea.....		3,170	4,032	204,263	211,465	211,465	200	450
Scott.....	100,545	214	100	35,506	136,365	175,327	241	475
Small mines.....		4,300			4,300	4,400		
Total.....	1,482,357	41,932	23,583	621,713	2,169,585	2,395,746	(c)263	5,082

a Prospecting.

b One hundred and seventy-five convicts.

c Average for the State.

Extended descriptions of the Tennessee coal fields have been published in previous reports with numerous analyses of the coals and cokes. The coal-producing regions are divided into three State inspection districts, the first including the counties of Franklin, Grundy, Marion, and White; the second the counties of Hamilton, Morgan, Rhea, Roane, and Scott; and the third the counties of Anderson, Campbell, and Claiborne. The product of these districts in 1888, 1889, and 1890 (exclusive of small banks) was as follows:

Coal product of Tennessee in 1888, 1889, and 1890, by districts.

Districts.	1888.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
First	637, 415	630, 333	616, 819
Second	683, 973	681, 962	839, 696
Third	645, 909	579, 542	708, 770
Total	1, 967, 297	1, 921, 837	2, 165, 285

The product of coal in Tennessee from 1873 to 1890 is shown in the following table:

Coal product of Tennessee from 1873 to 1890.

Years.	Short tons.	Years.	Short tons.	Years.	Short tons.
1873	350, 000	1879	450, 000	1885	1, 440, 957
1874	350, 000	1880	641, 042	1886	1, 714, 290
1875	360, 000	1881	750, 000	1887	1, 900, 000
1876	550, 000	1882	850, 000	1888	1, 967, 297
1877	450, 000	1883	1, 000, 000	1889	1, 925, 689
1878	375, 000	1884	1, 200, 000	1890	2, 169, 585

The number of men employed at Tennessee coal mines in 1890 was 4,767, against 4,108 in 1889. Of the number employed in 1890, 175 were convicts.

TEXAS.

Total product in 1889, 128,216 short tons; spot value, \$340,617. Total product in 1890, 184,440 short tons; spot value, \$465,900.

Although nine counties are reported by the Census Office as producing coal in 1889, in only four of them—Erath, Maverick, Medina, and Webb—is it mined commercially. The other five—Coleman, Jack, McCullough, Rains, and Wise—produced an aggregate of little more than 1,000 short tons. There is nothing to report on the development of coal mines in the State except the increased production of those previously described; the product in 1889 being 38,216 short tons greater than that of the year before and the product of 1890, 55,824 short tons greater than that of 1889. The amount of coal produced in the two years is shown in the following table, together with the distribution and value of the product:

Coal product of Texas in 1889 and 1890.

Distribution.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>
Loaded at mines for shipment	120, 602	180, 800
Sold to local trade and used by employes	6, 552	1, 840
Used for steam at mines	1, 062	1, 800
Total	128, 216	184, 440
Total value	\$340, 617	\$465, 900

UTAH.

Total product in 1889, 236,651 short tons; spot value, \$377,456. Total product in 1890, 318,159 short tons; spot value, \$552,390.

Coal mining in Utah has been carried on since 1864, but no record of the amount produced was made until 1885, when the product was 213,120 short tons. As yet no thorough geological survey has been made of the coal fields of the Territory, and therefore any reliable estimate of the possibilities of the Territory in the way of future coal production is not practicable. Mr. Ellsworth Daggett contributed an interesting article on the coal fields of Utah to Mineral Resources for 1882, which contains practically all that is known on the subject. During 1888 there was considerable activity in coal mining in Utah, the production increasing 78,940 short tons over the previous year. In 1889 the product decreased 22,310 short tons, but reacted again in 1890 with an increase of 81,508 short tons over 1889.

The most important recent advance in coal mining in Utah has been caused by the opening of the Pleasant Valley No. 1 mine, located at Scofield, Emery county, and operated by the coal department of the Union Pacific Railway Company. The property embraces 1,800 acres of land, on which three coal seams have been opened; the upper 7 feet in thickness, the middle 12 feet, and the lower 28 feet. The mine opened is on the lower seam, and the entire thickness of coal, 28 feet, is taken out, the vein being all clean coal without bone or slate.

The amount, value, and distribution of the coal product of Utah in 1889 and 1890 was as follows:

Coal product of Utah in 1889 and 1890.

Distribution.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>
Loaded at mines for shipment	216,960	279,336
Sold to local trade and used by employé's	17,062	13,749
Used for steam at mines.....	412	1,015
Made into coke	2,217	24,059
Total	236,651	318,159
Total value.....	\$377,456	\$552,390

Coal product of Utah from 1885 to 1890.

Years.	Short tons.	Years.	Short tons.
1885	213,120	1888	258,961
1886	200,000	1889	236,651
1887	180,021	1890	318,159

VIRGINIA.

Total product in 1889, 865,786 short tons; spot value, \$804,475. Total product in 1890, 784,011 short tons; spot value, \$589,925.

The total coal product of Virginia in 1889 was 207,214 short tons less

than in 1888. In 1890 it decreased 81,775 tons from 1889. The falling off in 1889 was due partly to the suspension of operations at the Winterpock mines in Chesterfield county. These mines were flooded in 1890 and could not be worked. The Southwest Virginia Improvement Company, the largest operator in the State, also curtailed its output during the year. The following tables exhibit the amount of coal produced in the State during 1889, and 1890 by counties, with the value and distribution of the product:

Coal product of Virginia in 1889, by counties.

Counties.	Disposition of total product.					Total product of coal of all grades for 1889.	Total amount received for coal sold in 1889.	Total number of employes.
	Loaded at mines for shipment on rail-road cars.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.			
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Buchanan		89	80			169	\$345	
Chesterfield and Henrico	44,648	798	45	3,920		49,411	77,692	257
Dickenson		23	12			35	106	
Lee and Wythe		370				370	703	
Montgomery	3,062	4,642	226	235		8,165	19,644	56
Pulaski and Tazewell..	685,171	1,062	5,242	3,361	112,210	807,046	705,121	1,242
Russell		398	4			402	603	
Wise		164	24			188	261	
Total	732,881	7,546	5,633	7,516	112,210	865,786	804,475	1,555

Coal product of Virginia in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Henrico	19,346				19,346	\$24,183	300	24
Chesterfield (a)	2,349	3,140	138		5,627	11,400	205	36
Montgomery								
Pulaski and Tazewell	586,946	13,862	4,770	153,460	759,038	554,342	298	1,235
Total	608,641	17,002	4,908	153,460	784,011	589,925	(b) 296	1,295

a Mines flooded.

b Average for the State.

All but a very small portion of the coal product of the State comes from the Flat Top region, which has been fully described in previous volumes of Mineral Resources. The "Iron Belt" has added some valuable literature to the subject in a history of the development of this remarkable field, from which the following is abstracted:

"The development in the Flat Top coal field started in the fall of 1881, but only surface work on the side of the mountain was done. In January, 1882, about 20 miners were landed at the point in Tazewell county, Virginia, where now stands the town of Poalontas, then a howling wilderness, having taken nine days to make the trip from New York, the greater part of this time being consumed in making their way

across the mountains from Wytheville. A place was cleared away and a shanty was erected, in which the men cooked their meals and had their sleeping apartments.

“The wet season in the spring of 1882 retarded the progress of the work, which was all out of doors, but in March of that year the first blast was put in the East mine, and on April 1, Mr. Thomas C. Blair, now a successful capitalist of Roanoke, Virginia, closed a contract with the Southwest Virginia Improvement Company to run the No. 1 East mine 1 mile; also the air course and the No. 1 West mine. The work was then pushed with vigor till fall, when it was stopped for a time on account of the inability of the railroad to reach the mines, and in consequence of which all the coal taken from the mine was dumped in front of the opening.

“The New River division of the Norfolk and Western railroad was completed in 1883, and the first carload of the product of the new coal field was shipped through to Norfolk and distributed among the poor. When the car left Pocahontas it was decorated with branches of laurel, and as it passed through the various towns along the route the people, realizing that the completion of the Norfolk and Western branch road to the coal mines would mark the beginning of a new era in the history of our development, in their enthusiasm draped the car with bunting and flags, and when it arrived at Norfolk it was one mass of red, white, and blue.

“When the mines were first opened a shipment of 200 and 300 tons per day was considered a great output, but when the big explosion took place in the year 1884 the daily output was many times greater than this. This explosion was beneficial to the new coal fields, inasmuch as it attracted the attention of the public to it. At that time there were thousands of people in the State who did not know there was such a place as Pocahontas, or had not heard of the wonderful developments going on there.

“In the beginning of 1885 the Norfolk and Western Railroad Company built a branch road from Bluestone Junction which tapped the north side of the Flat Top field. The first to enter this side of the field was the firm of John Cooper & Co. and Messrs. Freeman & Jones. Since the opening of this road the development has been phenomenally rapid.

“The Pocahontas Flat Top coal measures are above the water level, in veins ranging from 5 to 13 feet in thickness, extending through an area estimated to contain not less than 300 square miles. Pocahontas coal is from the Lower Coal Measures and is semibituminous, containing but 18 per cent. of volatile matter. The veins dip to the north and west, and the extension of the Ohio division of the Norfolk and Western railroad north to the Ohio river and the road west to the Cumberland mountains pass through the Middle and Upper measures, thus opening up coal of greater volatile matter, bituminous, splint, and cannel.”

Total shipments over the Norfolk and Western Railroad from 1883 to 1890.

Years.	Short tons.	Years.	Short tons.
1883 (from month of June)	105, 805	1887	1, 169, 700
1884	272, 173	1888	1, 563, 343
1885	651, 987	1889	1, 783, 527
1886	924, 361	1890	1, 814, 568

Part of the above shipments are from the portion of the Pocahontas field which extends into Mercer and McDowell counties, West Virginia. The amounts for the two States are combined in order to show the business of the Flat Top region.

WASHINGTON.

Total product in 1889, 1,030,578 short tons; spot value, \$2,393,239. Total product in 1890, 1,263,689 short tons; spot value, \$3,426,590.

The production of coal in Washington in 1889 shows a decrease in the amount produced of 185,172 short tons, and in value of \$1,254,011 from 1888, which was a year of exceptional activity in the coal-mining industry in Washington. In 1890 the product increased 233,111 short tons in amount over 1889, and \$1,133,351 in value.

The following tables show the amount and value of coal produced in Washington in 1889 and 1890, with the distribution of the product:

Coal product of Washington in 1889, by counties.

Counties.	Disposition of total product.					Total product of coal of all grades for year 1889.	Total amount received for coal sold in year 1889.	Total employes about mine.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.			
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
King	398, 657	3, 121	2, 410	11, 591	415, 779	415, 779	\$954, 295	1, 220
Kittitas	289, 300	1, 643	625	3, 758	294, 701	294, 701	777, 450	759
Pierce	228, 889	672	1, 008	4, 049	39, 000	273, 618	578, 493	
Thurston	39, 200	5, 600	1, 120	560		46, 480	83, 000	
Total	956, 046	11, 036	4, 538	19, 958	39, 000	1, 030, 578	2, 393, 238	a2, 657

a Including 678 employes in Kittitas and Thurston counties.

Coal product of Washington in 1890, by counties.

Counties.	Loaded at mine for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>	<i>Short tons</i>			
King	507, 003	4, 032	12, 086	445, 311	517, 492	\$1, 352, 920	292	1, 098
Kittitas	436, 539	2, 518	625	16, 800	445, 311	1, 229, 330	259	489
Pierce	254, 079	10, 699	4, 308		285, 886	814, 340	257	589
Thurston	a 15, 000				15, 000	30, 000	240	30
Total	1, 212, 621	17, 249	17, 019	16, 800	1, 263, 689	3, 426, 590	(b) 270	2, 206

a Prepared coal from lignite.

b Average for the State.

The number of men employed at coal mines in Washington in 1890 was 2,206, against 2,657 the previous year, showing that during 1889 a considerable number were employed in development work, which resulted in an increased product in 1890 while employing less labor. The Census Office reports show that the average wages paid in the State were as follows: Foremen, above ground, \$3.76; below ground, \$3.97; mechanics, \$3.04; laborers, above ground, \$2.29; below ground, \$2.46; miners, \$3.26; boys, from \$1 to \$1.50.

The following table shows the product of the State for 1887, 1888, 1889, and 1890, by counties:

Product of coal in Washington for four years, by counties.

Counties.	1887.	1888.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
King	339,961	546,535	415,779	517,492
Kittitas	104,782	220,000	294,701	445,311
Pierce	229,785	276,956	273,618	285,886
Thurston	15,295	42,000	46,480	15,000
Not specified	82,778	130,250		
Total	772,601	1,215,750	1,030,578	1,263,689

The first discovery of coal in Washington was made in 1852, and the first mine was opened on Bellingham bay in 1854. The coal from this mine was shipped to San Francisco and was the only coal shipped out of the Territory until 1870, when exportation commenced at Seattle, from the Seattle, Renton, and Talbot mines in the vicinity. In 1874 the product from the Seattle mines was 50,000 tons; from July 1, 1878, to July 1, 1879, the product was 155,900 tons. In the year ended December 31, 1879, the product was 137,207 short tons. The Renton mine, opened in 1874, produced, in 1875 and 1876, 50,000, short tons. The Talbot mine, opened in 1875, produced, in 1879, 18,000 short tons of coal. Records of the operations of Washington coal mines are incomplete, and entirely wanting from 1879 to 1884. The mining during this time was confined to King and Pierce counties. During the fiscal year ended June 30, 1885, the total product of the Territory is given at 380,250 short tons, of which King county is credited with 204,480 short tons and Pierce county with 175,770 short tons. The annual product since that time has been as follows:

Product of coal in Washington from 1886 to 1890.

Years.	Short tons.	Years.	Short tons.
1886	423,525	1889	1,030,578
1887	772,601	1890	1,263,689
1888	1,215,750		

WEST VIRGINIA.

Total product in 1889, 6,231,880 short tons; spot value, \$5,086,484. Total product in 1890, 7,266,494 short tons; spot value, \$6,086,678.

With the exception of a small decrease in 1876, coal mining in West Virginia has shown a continuous growth since 1873, the rate of increase during the last five years being exceptionally rapid. The most notable increase is that in Mercer county, which is a part of the great Flat Top coking coal region, the central point of which is Pocahontas, Virginia, and which embraces the mines at Elkhorn, Simmons, Maybeury, and Goodwill in Mercer and McDowell counties, West Virginia. The product in the West Virginia part of the Flat Top region in 1886 was 328,733 short tons, and in 1890 1,962,092 short tons, showing an increase of 1,633,359 short tons, or nearly 500 per cent. in five years.

The coal fields of West Virginia have been extensively described in previous volumes of Mineral Resources, particularly in the number covering the years 1883-'84.

The following tables show the product for 1889 and 1890 by counties, together with the value and distribution:

Coal product of West Virginia in 1889, by counties.

Counties.	Disposition of total product.					Total product of coal of all grades for 1889.	Total amount received for coal sold in 1889.	Total number of employes.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.	Manufactured into coke.			
	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.	Short tons.		
Barbour		1,600				1,600	\$1,200
Boone		2,888				2,888	2,293
Braxton		160				160	120
Brooke	14,035	16,831	103	150		31,119	22,828	50
Cabell		505				505	485
Calhoun		220				220	165
Clay		256				256	192
Fayette	1,074,409	12,211	11,468	7,150	345,542	1,450,780	1,302,438	2,644
Gilmer		820				820	615
Harrison	141,343	26,328	1,200	11	5,233	174,115	114,427	233
Kanawha	1,168,024	31,393	10,614	3,529	4,676	1,218,236	1,166,038	2,484
Lewis		60				60	30
Lincoln		284				284	213
Logan		3,456				3,456	2,592
McDowell	309,489	56,620	4,788	3,265	212,367	586,529	390,232	764
Marion	157,975	24,066	974	1,932	97,520	282,467	199,692	333
Marshall	33,000	14,106		600		47,706	35,956	72
Mason	83,116	96,844	3,613	1,457		185,030	167,783	363
Mercer	750,507	13	4,302	1,858	165,061	921,741	594,885	1,121
Mineral	487,622	3,862	1,924	56		493,464	394,827	608
Monongalia	64,927	7,177	438	1,489		74,031	53,318	61
Monroe		30				30	23
Nicholas		1,408				1,408	1,056
Ohio	28,121	113,615	1,020	414		143,170	126,909	204
Pocahontas		240				240	180
Preston	41,807	3,893	2,156	5,124	76,952	129,932	86,024	239
Putnam	210,214	6,140	1,384	1,014		218,752	244,203	451
Raleigh		1,480				1,480	1,110
Ritchie		1,528	36	63		1,627	998
Taylor	68,318	16,685	337	21	7,651	83,012	52,725	96
Tucker	141,993	538	403	9,235	21,323	173,492	120,574	229
Tyler		12				12	9
Upshur		2,114				2,114	1,586
Wayne		880				880	660
Wetzel		264				264	198
Total.....	4,704,900	448,527	44,760	37,368	926,325	6,231,880	5,086,584	9,952

Coal product of West Virginia in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.	Total amount produced.	Total value.	Number of days active.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>			
Brooke	16, 494	20, 130	170	36, 794	\$28, 520	202	50
Fayette.....	1, 181, 369	28, 176	2, 839	428, 914	1, 591, 298	1, 438, 612	225	2, 824
Harrison	130, 215	9, 522	212	4, 454	144, 403	100, 818	194	305
Kanawha	1, 380, 131	31, 001	5, 004	4, 960	1, 421, 116	1, 365, 585	230	2, 756
McDowell	595, 515	7, 414	4, 518	348, 775	956, 222	678, 305	183	1, 315
Marion	317, 931	2, 427	4, 236	131, 134	455, 728	313, 505	218	866
Marshall.....	71, 631	52, 038	123, 669	100, 846	265	175
Mason	77, 052	(a) 66, 562	1, 700	145, 314	134, 643	229	480
Mercer	793, 841	2, 447	1, 232	208, 350	1, 005, 870	755, 014	217	1, 465
Mineral.....	532, 813	40, 793	75	573, 681	501, 391	279	620
Monongalia.....	12, 040	10, 080	56	9, 184	31, 360	20, 000	260	55
Ohio	650, 960	(b) 52, 514	112	103, 586	100, 017	268	153
Preston.....	80, 521	2, 107	9, 400	86, 411	178, 439	127, 893	282	337
Putnam.....	203, 300	838	1, 040	205, 178	198, 269	194	375
Taylor.....	68, 841	1, 509	6, 268	76, 618	58, 159	256	108
Tucker.....	152, 098	10, 969	82, 311	245, 378	180, 641	309	353
Small mines	100, 000	100, 000	100, 000
Total	5, 614, 752	438, 527	30, 594	1, 310, 781	7, 394, 654	6, 208, 128	(c) 227	12, 236

a Of this amount 55,265 tons were consumed at the mines for evaporating salt brine.

b Of this amount 65,364 tons were used by iron works at or in the vicinity of the mines.

c Average for the State.

The coal-producing regions of West Virginia may be said to lie in two nearly parallel lines, one stretching along the northern border of the State from Mineral county on the east to Marion and Monongalia counties on the west, the other following the course of the New and Kanawha rivers through the southwestern portion of the State from its boundaries; the two exceptions to the lines being in the "Panhandle" or extreme northwestern point of the State and in McDowell county in the extreme southern point, a portion of the great Flat Top region. The northern strip embraces the counties of Mineral, Tucker, Preston, Taylor, Harrison, Marion, and Monongalia; the "Panhandle" contains the counties of Ohio, Marshall, and Brooke; and Mason, Putnam, Kanawha, Fayette, and Mercer counties fill out the southern strip. For convenience of description the coal belts are divided into ten districts or regions, as follows: Elk Garden (Mineral county), Upper Potomac (Tucker county), Cheat River (Preston county), Clarksburg (Harrison and Taylor counties), Upper Monongalia (Marion and Monongalia counties), Panhandle (Ohio, Marshall, and Brooke counties), Point Pleasant (Mason county), Kanawha (Putnam and McDowell counties, and part of Fayette), New River (part of Fayette county), Flat Top (McDowell and Mercer counties). The product of West Virginia in 1890, by districts, was as follows:

Coal product of West Virginia in 1890, by districts.

Districts.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Made into coke.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Cheat River	80,521	2,107	9,400	86,411
Clarksburg	199,056	11,031	212	10,722
Elk Garden	532,813	40,793	75
Flat Top	1,389,356	9,861	5,750	557,125
Kanawha	1,897,178	35,103	6,492	136,091
New River	817,622	24,912	2,391	297,803
Pan Handle	(a)139,085	(a)124,682	282
Point Pleasant	77,052	(b)66,562	1,700
Upper Monongalia	329,971	12,507	4,292	140,318
Upper Potomac	152,098	10,969	82,311
Small mines	100,000
Total	5,614,752	438,527	30,594	1,310,781

Districts.	Total amount produced.	Total value.	Average number of days worked.	Average number employed.	Counties embraced in the districts.
	<i>Short tons.</i>				
Cheat River	178,439	\$127,803	282	337	Preston.
Clarksburg	221,021	158,977	210	413	Harrison and Taylor.
Elk Garden	573,681	501,391	279	620	Mineral.
Flat Top	1,962,092	1,433,319	201	2,780	McDowell and Mercer.
Kanawha	2,074,864	1,922,357	229	3,909	Putnam, Kanawha, and part of Fayette.
New River	1,142,728	1,080,109	220	2,046	Part of Fayette.
Pan Handle	264,049	229,383	253	378	Ohio, Marshall, and Brooke.
Point Pleasant	145,314	134,643	229	480	Mason.
Upper Monongalia	487,088	333,505	221	920	Marion and Monongalia.
Upper Potomac	245,378	186,641	309	353	Tucker.
Small mines	100,000	100,000	
Total	7,394,654	6,208,128	(c) 227	12,236	

a Of the Ohio county product 65,364 tons were used by iron works at or in the vicinity of the mines.
 b Of this amount 55,265 tons were consumed at the mines for evaporating salt brine.
 c Average for the State.

The following table shows the tendency of coal production in West Virginia, by counties, from 1886 to 1890:

Coal production in West Virginia from 1886 to 1890, by counties.

Counties.	1886.	1887.	1888.	1889.	1890.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
Brooke	22,880	40,366	11,568	31,119	36,794
Fayette	1,413,778	1,126,839	863,600	1,450,780	1,591,298
Harrison	234,597	154,220	109,515	174,115	144,403
Kanawha	876,785	1,126,839	863,600	1,218,236	1,421,116
McDowell	575,885	961,395	586,529	956,222
Marion	172,379	365,844	363,974	282,467	455,728
Marshall	251,333	92,368	47,702	47,706	123,669
Mason	150,878	140,968	72,410	185,030	145,314
Mercer	328,733	1,252,427	1,977,030	921,741	1,005,870
Mineral	361,312	478,636	456,361	493,404	573,081
Monongalia	74,031	31,360
Ohio	(a)	131,936	140,019	143,170	103,586
Preston	170,721	276,224	231,540	129,932	178,439
Putnam	(b)	53,200	145,440	218,752	205,178
Taylor	(c)	168,000	55,729	83,012	76,618
Tucker	22,400	24,707	62,517	173,492	245,378
Other counties and small mines	18,304	100,000
Total	4,005,796	4,881,620	5,498,800	6,231,880	7,394,654

a Included in product of Marshall county.
 b Included in product of Mason county.

c Included in product of Harrison county.

The annual increase in the production of coal in West Virginia (with the exception previously noted) may be seen from the following statement:

Coal product of West Virginia from 1873 to 1890.

Years.	Short tons.	Years.	Short tons.
1873	672, 000	1882	2, 240, 000
1874	1, 120, 000	1883	2, 335, 833
1875	1, 120, 000	1884	3, 360, 000
1876	896, 000	1885	3, 369, 062
1877	1, 120, 000	1886	4, 005, 796
1878	1, 120, 000	1887	4, 881, 620
1879	1, 400, 000	1888	5, 498, 800
1880	1, 568, 000	1889	6, 231, 880
1881	1, 680, 000	1890	7, 266, 494

WYOMING.

Total product in 1889, 1,388,947 short tons; spot value, \$1,748,617.
Total product in 1890, 1,870,366 short tons; spot value, \$3,183,669.

The product of coal in Wyoming in 1889 was 92,593 short tons less than in 1888. The output in 1890 was 481,419 short tons more than in 1889. The following tables show the amount produced in the State in 1889 and 1890, by counties, with the value and distribution of the product:

Coal product of Wyoming in 1889, by counties.

Counties.	Disposition of total product.				Total product of coal of all grades for year 1889.	Total amount received for coal sold in year 1889.	Total employes about mines.
	Loaded at mines for shipment on railroad cars and boats.	Sold to local trade at mines.	Used by employes.	Used for steam at mines.			
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Carbon	193, 402	1, 501	1, 073	3, 300	199, 276	\$194, 817	488
Converse	16, 285	553	305	250	17, 393	30, 955
Crook		200	200	600
Johnson	2, 300	2, 742	50	5, 092	13, 257
Sheridan		510	45	555	840
Sweetwater	843, 668	3, 368	10, 177	857, 213	1, 025, 067	1, 441
Uinta	298, 788	1, 824	3, 262	5, 344	309, 218	483, 081
Total	1, 354, 443	7, 330	8, 103	19, 071	1, 388, 947	1, 748, 617	(a)2, 675

a Including 746 employes in Converse, Crook, Johnson, and Uinta counties.

Coal product of Wyoming in 1890, by counties.

Counties.	Loaded at mines for shipment.	Sold to local trade and used by employes.	Used at mines for steam and heat.	Total amount produced.	Total value.	Average number employed.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>		
Carbon	302, 106	1, 785	2, 078	305, 969	\$535, 460	714
Converso	23, 345	1, 603	800	25, 748	44, 696	30
Fremont	900	500	1, 400	5, 750	4
Johnson	7, 275	195	7, 470	16, 984	12
Sheridan	400	250	650	975	2
Sweetwater	974, 533	3, 994	300	978, 827	1, 666, 068	(a)1, 672
Uinta	341, 710	5, 213	3, 349	350, 278	623, 806	422
Weston	185, 024	15, 000	200, 024	289, 930	416
Total	1, 835, 299	28, 540	6, 527	1, 870, 366	3, 183, 669	3, 272

a Including 250 Chinese.

The following information regarding the production of coal in Wyoming in 1890 by counties, and the comparative tables in connection therewith, have been compiled by Mr. F. F. Chisolm, special agent for the Rocky Mountain region:

CARBON COUNTY.

Total product in 1890, 305,969 short tons; spot value, \$535,460. This does not include nut coal and slack coal from Union Pacific mines, as no account is kept.

Although all the various openings made at the Carbon mines have been abandoned, except No. 2 and No. 5, and the output smaller in 1890 than in any year since 1882, except 1889, nearly two-thirds of the production in 1890 came from Carbon, the combined output from the New Hanna No. 1 and No. 2 mines and the Dana No. 1 mine being less than half that from the Carbon mines.

The Carbon mines have been fully described in previous volumes of the Mineral Resources. The product of coal from these mines to date has been:

Product of the Carbon mines, Wyoming.

Years.	Short tons.	Years.	Short tons.
1863	6,560	1880	100,433
1869	30,482	1881	156,820
1870	54,915	1882	200,123
1871	31,748	1883	248,380
1872	59,237	1884	319,883
1873	61,164	1885	226,863
1874	55,880	1886	214,233
1875	61,750	1887	288,358
1876	69,060	1888	338,947
1877	74,343	1889	178,832
1878	62,418	1890	201,191
1879	75,424		

The newly opened Hanna No. 1 and Hanna No. 2 mines of the Union Pacific railway at Hanna, on the Carbon cut-off, practically began production in 1890, the output for the year being 74,757 short tons. These two mines will probably be steady and large producers, in part supplying the increasing demands of the Union Pacific for locomotive use and also for commercial purposes in Nebraska and Kansas. The coal is very similar in character to the Carbon coal. The machinery and equipment of these mines is excellent, but coal-cutting machines are not used.

The Dana No. 1 mine, at Dana Station, began commercial production in 1889, and is described on page 329 of the Mineral Resources for 1888. The output in 1890 was 29,886 short tons. It is commonly reported that the coal from this mine has not equaled the expectations of the Union Pacific Railway Company, to which may be due the small production in 1890. It should be specially noted that the stated product of all mines operated by the coal department of the Union Pacific does not

include the nut or slack produced, these sizes being practically unsalable, and no satisfactory statement of the amounts produced being obtainable.

Near Rawlins two new coal mines are growing in importance as coal producers, the Dillon mine operated by the Dillon Coal Company, and the Merrill mine operated by the Rawlins Coal Company. At various points in Carbon county the small local trade is supplied by individual operators from the Bessemer, Clyde, Fly, Reeder, Gumerson, Cronkhite, and Savory mines. The coal of the Seminoe district is yet without a railway, though the building of the Carbon cut-off from Carbon to Hanna has brought it within 25 miles of railroad transportation.

Analyses of coals from Seminoe, Wyoming.

	No. 1.	No. 2.	No. 3.	No. 4.	Average.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Water.....	10.70	9.10	9.40	8.52	9.43
Volatile matter.....	45.15	45.23	39.60	49.30	44.82
Fixed carbon.....	35.05	37.06	47.40	38.97	39.62
Ash.....	9.10	8.61	3.60	3.21	6.13
Total.....	100.00	100.00	100.00	100.00	100.00
Total fuel.....	88.20	82.29	87.00	88.27	84.69
Sulphur.....	0.93	0.66	0.52	0.37	0.62

The following analyses, made by Prof. L. D. Ricketts, show the composition of the coals from the Dana Nos. 1 and 2, the Hanna 1 and 2, the Dillon, Merrill, and Cronkhite mines in Carbon County:

Analyses of some Carbon county coals, Wyoming.

	Dana No. 1.	Dana No. 2.	Hanna No. 1.	Hanna No. 2.	Cronkhite.	Dillon.	Dillon.	Merrill.
	<i>Per ct.</i>	<i>Per ct.</i>	<i>Per ct.</i>	<i>Per ct.</i>	<i>Per ct.</i>	<i>Per ct.</i>	<i>Per ct.</i>	<i>Per ct.</i>
Water.....	11.70	11.30	8.67	9.52	9.20	7.47	5.19	19.16
Volatile matter.....	41.41	42.01	45.05	41.85	34.40	36.05	37.05	33.11
Fixed carbon.....	39.85	39.69	41.91	44.68	52.40	51.56	48.50	41.07
Ash.....	7.24	7.00	4.71	3.92	2.80	4.32	9.25	3.64
Total.....	100.00	100.00	100.44	99.97	98.80	99.40	99.99	96.98

CONVERSE COUNTY.

Total product in 1890, 25,748 short tons; spot value, \$44,696.

The coal output of Converse county in 1890 came from the Douglas mine, at Douglas; the Fetterman mine, at Inez, and the Deer Creek mine at Glenrock. At the latter mine the Deer Creek Coal Company has put in Harrison coal-mining machines.

FREMONT COUNTY.

The total product in 1890 amounted to 1,400 short tons, valued at \$5,750, which came from the Lone Star and Gillis mines. This is the first product of coal reported from Fremont county.

JOHNSON COUNTY.

Total product in 1890, 7,470 short tons; spot value, \$16,984. The coal mined in Johnson county was taken from four mines, the Buffalo and Vulcan, of the Buffalo Fuel Company, the Diamond, of the Diamond Coal Company, and the Holland, operated by Mr. W. H. Holland. These mines supply the local trade at and near Buffalo. The Buffalo mine shows a 7-foot vein of good lignite, and the Diamond a 6-foot vein. At various points in this county veins of coal varying from 3 to 4 feet in thickness outcrop and some small amount is taken from them by ranchmen for their own use as fuel, but no estimate of the total mined in this way is included in the statement of production. The prospects for railway connection with Buffalo, the only town in the county, are bright, and with transportation facilities the growth of coal production in Johnson county will be rapid.

SHERIDAN COUNTY.

The total product of Sheridan county in 1890 was 650 short tons, valued at \$975, against 550 short tons, valued at \$840, in 1889. There were no developments of any interest during the two years.

SWEETWATER COUNTY.

Total product in 1890, 978,827 short tons; spot value, \$1,666,068. (a) The mines worked by the Coal Department of the Union Pacific Railway Company, the Van Dyke Coal Company, the Rock Spring Coal Company, and the Hopkins Coal Company have been fully described in previous volumes of the Mineral Resources.

There were in 1890 no developments of note among the coal mines, and only one new coal mining corporation of importance has been organized since the Mineral Resources for 1888 was issued. This corporation, the Sweetwater Coal Mining Company, owns a very large body of coal and lying near Rock Spring and south of the Union Pacific railway and began production practically in 1890.

The Coal Department of the Union Pacific Railway Company has mined from the Rock Spring field the tonnage given in the following table:

Product of the Rock Spring mines, Wyoming.

Years.	Short tons.	Years.	Short tons.
1868	365	1880	244,460
1869	16,933	1881	270,425
1870	20,945	1882	287,510
1871	40,566	1883	304,495
1872	34,677	1884	318,197
1873	44,700	1885	328,601
1874	58,476	1886	359,234
1875	104,664	1887	465,444
1876	134,952	1888	662,277
1877	146,494	1889	777,213
1878	154,282	1890	652,408
1879	193,252		

a Not including nut coal and slack coal from Union Pacific mines, of which no account is kept.

Following are some analyses of Sweetwater county coals, made by Prof. Ricketts:

Analyses of Sweetwater county, Wyoming, coals.

	Van Dyke.	Number 4.	Blair No. 1.	Hopkins.	Blair No. 2.	Number 7.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Water	8.86	9.05	7.51	6.70	7.08	9.22
Volatile matter	39.15	40.00	39.06	39.30	38.54	38.78
Fixed carbon	49.13	48.87	50.22	51.27	52.63	49.52
Ash	2.86	2.08	2.59	2.72	1.75	2.48

UINTA COUNTY.

Total product in 1890, 350,278 short tons; spot value, \$623,806. This does not include nut coal and slack coal from Union Pacific mines, as no account is kept.

The coal output of Uinta county is made by but two corporations, the Coal Department of the Union Pacific Railway Company and the Rocky Mountain Coal and Iron Company. There are in all ten openings made by these two companies, eight of which are on the east of Bear river and contiguous. Of these the Union Pacific owns the Almy Nos. 1, 2, 3, 5, and 8, all of which have been abandoned except No. 8, while the Rocky Mountain Company own the Almy Nos. 6 and 7, and also a little further north two new mines, the Red Cañon No. 1 and No. 2.

The product of the Union Pacific mines to January 1, 1891, has been as follows:

Product of the Union Pacific mines at Almy, Wyoming.

Years.	Short tons.	Years.	Short tons.
1869	1,967	1880	100,234
1870	12,454	1881	110,157
1871	21,171	1882	117,211
1872	22,713	1883	111,713
1873	22,847	1884	150,880
1874	23,006	1885	164,441
1875	41,805	1886	155,547
1876	60,756	1887	196,913
1877	54,643	1888	160,035
1878	59,096	1889	118,629
1879	71,576	1890	176,130

Since the date of opening, the Rocky Mountain Coal and Iron Company has produced up to January 1, 1891, the following tonnage of coal:

Product of the Rocky Mountain Coal and Iron Company's mines at Almy, Wyoming.

Years.	Short tons.	Years.	Short tons.
1870	16,961	1881	90,779
1871	53,843	1882	94,065
1872	105,118	1883	78,450
1873	130,989	1884	68,471
1874	181,699	1885	70,216
1875	92,589	1886	100,341
1876	69,782	1887	164,510
1877	67,373	1888	209,298
1878	57,404	1889	190,589
1879	60,739	1890	170,798
1880	82,684		

Both properties have been fully described in previous volumes of the Mineral Resources.

WESTON COUNTY.

Total product in 1890, 200,024 short tons; spot value, \$289,930.

The most remarkable developments in the history of coal mining in Wyoming were made at Newcastle mines, the Antelope and Jumbo, located at Cambria, six miles north of Newcastle, Weston county, and operated by the coal department of Kilpatrick Brothers and Collins.

The coal found here probably occurs in the lowest portion of the Dakota measures of the Colorado Cretaceous and almost upon the topmost rocks of the Jurassic, but not, as often stated, within the Jurassic rocks. The influence of the eruptive upthrust of the Black Hills is shown by the local dip of the stratification, which averages about 22 degrees, the direction of the dip being nearly parallel to a line drawn from Harney Peak to Cambria, or about northeast by southwest, but this inclination of the sedimentary rocks is not constant in degree or direction, but varied by the eruptive outflow, not connected with the Harney Peak mass, such as the Inyan Kara butte to the north.

The vein of coal worked at Cambria is from 6½ to 7½ feet in thickness, with good roof and floor.

Regarding the character of the coal, there is a considerable diversity of opinion, and it has been classed from lignite to a high-grade coking bituminous coal. This difference may be due, in part, to actual variations caused by partial metamorphism by heat. It is sufficient to say that under the test of actual use it gives satisfaction, and that it is claimed by the operators to be a good coking coal. The coke produced is apparently of a good quality, quite dense, and capable of sustaining any weight ordinarily required of coke. The coke, however, as at present produced, runs a trifle too high in ash to be valuable for all uses.

The two mines worked are separated by a narrow cañon, through which the railway spur track to the mines is built, the main entries being on opposite sides and from 60 to 70 feet above the railway tracks.

The tipples and chutes are connected with the entries by short tres-

ties substantially built. The daily capacity of the mines is about 2,000 tons, and the product is sold largely to the railroad company.

All of the openings are made with a view to large and regular production, and their entries and rooms are lighted by electricity. The machinery and appliances are of the best modern type and the entire equipment admirable.

Several coal mines in this section have been slightly developed by other corporations and individuals, but as yet the production from these has been small.

The production of coal from the beginning of coal mining to January 1, 1891, is given in the following table:

Total product of coal in Wyoming, by counties.

Years.	Carbon county.	Sweetwater county.	Uinta county.	Weston county.	Converse county.	Other counties.	Total.
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>
1868.....	6,560	365					6,925
1869.....	20,422	16,933	1,967				49,382
1870.....	54,915	20,945	29,435				105,295
1871.....	31,748	40,566	75,014				147,328
1872.....	59,237	34,677	127,831				221,745
1873.....	61,164	44,700	153,836				259,700
1874.....	55,880	58,476	104,705				219,061
1875.....	61,750	104,664	134,394				300,808
1876.....	69,060	134,952	130,538				334,550
1877.....	74,343	146,494	122,016				342,853
1878.....	62,418	154,282	116,500				333,200
1879.....	75,424	193,252	132,315				400,991
1880.....	100,433	244,460	182,918				527,811
1881.....	156,820	270,425	200,936				628,181
1882.....	200,123	287,510	211,276			8,855	707,764
1883.....	248,380	304,495	190,163			36,651	779,689
1884.....	319,883	318,197	219,351			45,189	902,620
1885.....	226,863	328,601	234,657			17,207	807,328
1886.....	214,233	359,234	255,868				829,355
1887.....	288,358	465,444	361,423			55,093	1,170,318
1888.....	338,947	732,327	369,333		29,933	11,000	1,481,540
1889.....	199,276	857,213	309,218		17,393	5,847	1,388,276
1890.....	305,969	978,827	350,278	200,024	25,748	9,520	1,870,366
Total....	3,242,266	6,097,039	4,013,992	200,024	73,074	189,362	13,825,086

PETROLEUM.

BY JOSEPH D. WEEKS.

LOCALITIES IN THE UNITED STATES IN WHICH PETROLEUM IS FOUND.

While petroleum has been found in nearly every State and Territory, the localities in which it is produced in quantity are but few. These are the well-known oil regions of western Pennsylvania and New York, the Turkey Foot and other districts of West Virginia, the Macksburg and Lima fields in Ohio, the Florence district of Colorado, and the oil fields of southern California. Practically, all the petroleum produced in the United States is from the districts named, though a few thousand barrels were produced in Indiana, Kentucky, Illinois, Kansas and Texas in 1889 and 1890.

Not only are the localities named above the chief petroleum producing districts in the United States, but the indications are that, with the possible exception of Wyoming, they will continue so to be. The Indiana field has some promise, and may be a producer of some importance in the future. The Kentucky and other southern oil fields, which at one time it was supposed would be factors of some importance in the oil production of the United States, give at the present time no such indication. The Illinois field is an exceedingly small one, with but little promise for the future, while the Kansas and Texas fields will at the best probably produce only a few thousand barrels each year of a high-grade lubricating oil. However, there have been so many surprises in petroleum that these statements must be regarded as only setting forth the present indications.

A notable feature of the production in the United States in 1890 was the great increase in production which is manifest in nearly all of the districts. The production of the United States increased from 35,163,513 barrels in 1889 to 45,822,672 barrels in 1890.

The production of Pennsylvania and New York increased from 21,487,435 barrels to 28,458,208 barrels. This increased production was chiefly in what is known as the Southwest district, including Allegheny, Washington, Beaver and Greene counties. The McDonald production had not yet begun in 1890.

The production of Ohio increased from 12,471,466 barrels to 16,124,656 barrels in 1890. This increase was in both the Lima and Macksburg districts.

The production of West Virginia decreased slightly. Indiana very nearly doubled its production. There was a slight increase in both Colorado and California, while the other States about maintained their position.

Character and composition of American petroleum.—While the petroleum from different wells in the same district usually differs but little in character, there is a marked variation in many cases in the oils from different districts. The most notable distinction is in the solid constituents of the oil. The “basis” of all the petroleum in the United States, except a portion of those found in the southern part of California, is paraffin; of those of southern California, in most cases, asphalt.

In most of the oils a varying quantity of the lighter hydrocarbons, known in a general way as naphtha, is found. In others these lighter products are almost entirely wanting, or at least in refining all of the distillate is sold as illuminating oil. The composition of certain oils is also such that a large amount of lubricating oil, or heavy oils adapted to lubricating, is produced. For example, the Kansas and Texas oils are natural lubricating oils and can be used without any preparation except straining to remove any grit, while other so-called natural lubricating oils have to be prepared by a process of distillation, the various grades of density being used for various kinds of lubrication.

It may be said in a general way that the products of petroleum are naphthas or the lighter hydrocarbons, illuminating oils, heavy oils or lubricants, residuum, paraffin or asphalt, and water.

Regarding the oils of western Pennsylvania, New York, West Virginia and the Macksburg district of Ohio, which are chiefly used for the production of illuminating oil, it may be said that the petroleum of these districts as they come from the ground are clear, semitransparent oils, generally of an amber color, but varying somewhat in this regard with their density. When allowed to stand, however, a thick emulsion, reported in the tables of stocks, as “B. S.” or sediment, separates itself from the oil. The amount of this sediment varies greatly, the longer the oil is allowed to stand the greater being the proportion of “B. S.,” and the less the proportion of the lighter hydrocarbons. It is for this reason that fresh oil, or oil just produced, commands a premium over old oil, or that which had been allowed to stand in tanks, its yield of the lighter hydrocarbons, and of the better grades of illuminating oil, being greater when fresh than after having been stored.

The percentages of the products of fresh oil in refining will depend largely upon the methods of refining. This can be carried on so as to make the product of heavy oils almost nothing. From a refinery in western Pennsylvania the following statement as the result of their operations for two years has been received:

Percentage of products from Pennsylvania petroleum.

Products.	Per cent.	Per cent.
Naphthas.....	10.34	10.89
Illuminating oils.....	75.00	78.20
Heavy oils.....	2.00 to 6.00	2.00 to 4.00
Residuum.....	4.05	2.86
Water and loss.....	5.00 to 8.00	5.00 to 8.00

But little Lima or, better, Trenton limestone oil produced in western Ohio and eastern central Indiana had been refined in a commercial way prior to 1889. The chief obstacle to this use of the oil was the difficulty of removing the sulphur compounds present in it and the small percentage of illuminating oil which could be produced from the crude. At least two refineries succeeded in overcoming the difficulties in the way of the sulphur compounds during 1889, and American Trenton limestone oil became a factor in the market to some extent and promises to be a much more important one in the future. The actual facts, however, as to the yield of different products from this oil have been very difficult to obtain. In a general way it may be said to yield a comparatively large percentage of the lighter products and a small percentage of illuminating oil. In general conversation it is customary to assume a yield of 22 per cent. in illuminating oils and 15 per cent. of naphtha.

In a recent number of the Journal of the American Chemical Society appeared an analysis of Lima petroleum, made in the laboratory, however, which shows a yield as follows:

Products from Lima, Ohio, petroleum.

	Per cent.
Naphtha, at 70° Baume.....	16
Burning oil.....	68
Paraffin oils.....	6
Solid residuum.....	10
Total.....	100

These results are never reached in actual practice. Another sample of Lima petroleum gave the following results:

Products from Lima, Ohio, petroleum.

	Per cent.
Distillate at 59° Baume.....	13.75
Distillate at 75° Baume.....	35.11
Distillate at 39° Baume.....	7.93
Distillate at 36.5° Baume.....	13.40
Distillate at 36° Baume.....	18.60
Residuum.....	9.65
Water.....	0.70
Total.....	99.14

The foregoing would indicate a production of oils approximately as follows:

Products from Lima, Ohio, petroleum.

	Per cent.
Naphtha and burning oil.....	56.80
Heavy oils.....	32.00
Residuum.....	9.60
Water.....	0.70
Sulphur, first determination.....	0.63
Sulphur, duplicate.....	0.68
Sulphur, average.....	0.65
Total.....	99.75

The petroleum from the Florence oil fields in Colorado seems to be lacking in the lighter hydrocarbons or naphthas, or at least in refining it all of the distillate is sold as illuminating oil, the whole product of refining being divided only into two classes, illuminating oil and residuum. It yields in refining from 34 to 44 per cent. of this illuminating oil of about 125° fire test. This oil contains no "B. S."

As has already been pointed out, most of the oil of southern California differs from that of all other sections of the country in having asphaltum as its base instead of paraffin. The oils from the different fields of this section also differ greatly in their character, some being practically liquid bitumens, yielding a very small amount of illuminating oils on distillation, while others have less asphaltum, producing larger percentages of illuminating oil. Here, also, the results of distillation are only two, one illuminating oil, of which about 35 per cent. is produced from the crude charge, the other residuum, which is sold for fuel.

The approximate classification of the distillates of California oil, as given by Mr. Durand Woodman in the Journal of the American Chemical Society, is as follows:

Products from California petroleum.

	Per cent.
Naptha under 0.73 specific gravity	10 +
Illuminating oils.....	40 ±
Lubricating oils	40 ±
Residuum.....	10 +
Sulphur.....	0.18
Water.....	0.27
Paraffin	None separable.

TOTAL PRODUCTION OF CRUDE PETROLEUM IN THE UNITED STATES.

In the following table will be found a statement of the total production of crude petroleum of all grades in the United States in 1889 and 1890. It should be stated here, once for all, that the statistics and much of the text concerning the year 1889 are taken from the report made by the writer to the Eleventh Census:

Production of petroleum in the United States in 1889 and 1890.

States.	1889.	1890.
	<i>Barrels. (a)</i>	<i>Barrels. (a)</i>
Pennsylvania and New York.....	21,487,435	28,458,208
Ohio.....	12,471,466	16,124,656
West Virginia.....	544,113	492,578
Colorado.....	316,476	368,842
California.....	303,220	307,360
Indiana.....	33,375	63,496
Kentucky.....	5,400	6,000
Illinois.....	1,460
Kansas.....	500	1,200
Texas.....	48	54
Missouri.....	20	278
Total.....	35,163,513	45,822,672

In this table the production of Pennsylvania and New York is united. The Bradford (Pennsylvania) field extends into Cattaraugus county, New York, and is so closely connected with the Allegany county (New York) field as to cause them to be regarded as one in most reports. It will probably be approximately correct to estimate that 26.5 per cent. of this was produced in New York, 8.5 per cent. being from Cattaraugus county, and 18 per cent. from Allegany county; this would make the production in 1889 of New York 1,896,966 barrels, and of the Pennsylvania portion of this district 5,261,397 barrels. The production of Cattaraugus county, New York, assuming this estimate to be correct, was 608,461 barrels, and of Allegany county, New York, 1,288,505 barrels.

In the following table will be found consolidated the statistics of the production of petroleum in the United States from the beginning of operations in these fields, so far as the same could be ascertained:

Product of crude petroleum in the United States from 1859 to 1890. (a)

[Barrels of 42 gallons.]

Years.	Pennsylvania and New York.	Ohio.	West Virginia.	Colorado.	California.	Indiana.	Kentucky and Tennessee.	Illinois.	Kansas.	Texas.	Missouri.	Total United States.
1859..	2,000											2,000
1860..	500,000											500,000
1861..	2,113,609											2,113,609
1862..	3,056,690											3,056,690
1863..	2,611,309											2,611,309
1864..	2,116,109											2,116,109
1865..	2,497,700											2,497,700
1866..	3,597,700											3,597,700
1867..	3,347,300											3,347,300
1868..	3,646,117											3,646,117
1869..	4,215,000											4,215,000
1870..	5,260,745											5,260,745
1871..	5,205,234											5,205,234
1872..	6,293,194											6,293,194
1873..	9,893,786											9,893,786
1874..	10,926,945											10,926,945
1875..	8,787,514	d 200,000	d 3,000,000		d 175,000							c 12,162,514
1876..	8,968,906	31,763	120,000		12,000							9,132,669
1877..	13,135,475	29,888	172,000		13,000							13,350,363
1878..	15,163,462	38,179	180,000		15,227							15,396,868
1879..	19,685,176	29,112	180,000		19,858							19,914,146
1880..	26,027,631	38,940	179,000		40,552							26,286,123
1881..	27,376,509	33,867	151,000		99,862							27,661,238
1882..	30,053,500	39,761	128,000		128,636		e 160,933					e 30,510,830
1883..	23,123,389	47,632	126,000		142,857		4,755					23,449,633
1884..	23,772,209	90,081	90,000		262,000		4,148					24,218,438
1885..	20,776,041	650,000	91,000		325,000		5,164					21,847,205
1886..	25,798,000	1,782,970	102,000		377,145		4,726					28,064,841
1887..	22,356,193	5,018,015	145,000		76,295	678,572	4,791					28,278,866
1888..	16,488,668	10,010,868	119,448		297,612	690,333	5,096					27,612,025
1889..	21,487,435	12,471,466	544,113	316,476	303,220	33,375	5,400	1,460	500	48	20	35,163,513
1890..	28,458,208	16,124,656	492,578	368,842	307,360	63,496	6,000		1,200	54	278	45,822,672
Total	396,746,754	46,637,198	5,820,139	1,059,225	3,590,622	96,871	201,013	1,460	1,700	102	298	454,153,382

a Some oil was produced in other States, but no record has been secured other than that contained in note b.

b In addition to this amount, it is estimated that for want of a market some 10,000,000 barrels ran to waste in and prior to 1862 from the Pennsylvania fields; also a large amount from West Virginia and Tennessee.

c Including all production prior to 1876 in Ohio, West Virginia, and California.

d Includes all production prior to 1876.

e This includes all the petroleum produced in Kentucky and Tennessee prior to 1883.

PRODUCTION AND VALUE OF CRUDE PETROLEUM IN THE UNITED STATES IN 1889, ACCORDING TO USES.

In the following table are shown, by States, the production, total value, and value per barrel of the petroleum produced in the United States in 1889 according to uses, as compiled for the Census Office:

Production, value, etc., of crude petroleum in 1889, by States.

States.	Illuminating.			Lubricating.		
	Production.	Value.	Average per barrel.	Production.	Value.	Average per barrel.
	<i>Barrels.</i>			<i>Barrels.</i>		
Pennsylvania and New York	21,393,159	\$23,225,453	\$1.08 $\frac{3}{8}$	94,276	\$249,710	\$2.64 $\frac{7}{8}$
Ohio	317,037	340,683	1.07 $\frac{1}{2}$	1,240	10,334	8.33 $\frac{3}{8}$
West Virginia	520,511	595,730	1.14 $\frac{1}{2}$	23,602	58,097	2.46 $\frac{1}{8}$
Colorado	316,476	280,240	0.88 $\frac{3}{8}$			
California	97,264	121,684	1.25 $\frac{5}{8}$			
Indiana						
Kentucky	5,400	5,400	1.00			
Illinois				1,460	4,906	3.36
Kansas				500	2,500	5.00
Texas				48	340	7.08 $\frac{3}{8}$
Missouri				20	40	2.00
Total	22,649,847	24,569,190	1.08 $\frac{1}{2}$	121,146	325,927	2.69

States.	Fuel.			Total.		
	Production.	Value.	Average per barrel.	Production.	Value.	Average per barrel.
	<i>Barrels.</i>			<i>Barrels.</i>		
Pennsylvania and New York				21,487,435	\$23,475,163	\$1.09 $\frac{1}{2}$
Ohio	12,153,189	\$1,822,978	\$0.15	12,471,466	2,173,995	0.17 $\frac{1}{2}$
West Virginia				544,113	653,827	1.20 $\frac{1}{2}$
Colorado				316,476	280,240	0.88 $\frac{3}{8}$
California	205,956	234,364	1.13 $\frac{3}{8}$	303,220	356,048	1.17 $\frac{1}{8}$
Indiana	33,375	10,881	0.32 $\frac{3}{8}$	33,375	10,881	0.32 $\frac{3}{8}$
Kentucky				5,400	5,400	1.00
Illinois				1,460	4,906	3.36
Kansas				500	2,500	5.00
Texas				48	340	7.08 $\frac{3}{8}$
Missouri				20	40	2.00
Total	12,392,520	2,068,223	0.16 $\frac{3}{8}$	35,163,513	26,963,340	0.76 $\frac{3}{8}$

It should be said, in explanation of the preceding table, that the classification is according to uses for which the oil was intended. That classified as illuminating oil includes that production usually sold and delivered to refineries for making into illuminating oil, but in connection with this manufacture there is a certain amount of lighter products, such as benzine, as well as, when it is so desired, a certain amount of lubricating oil, and also of residuum, which may be used as fuel. Under the head of "Fuel" is included the production from those districts the oil of which is used chiefly for fuel purposes, though a small portion of this oil was used in 1889 for the manufacture of illuminating oil, and much larger amounts since. Under the head of "Lubricating" are included only what are known as the natural lubricating oils, which are used only as lubricators, either without any preparation or with slight

refining. From this table it will be noticed that the total production of what is classed as illuminating oil in the United States in 1889 was 22,649,847 barrels, valued at \$24,569,190, an average value of \$1.08½ per barrel. The product of lubricating oil was 121,146 barrels, valued at \$325,927, or \$2.69 per barrel. The production of what is classed as fuel oil was 12,392,520 barrels, valued at \$2,068,223, or 16¾ cents per barrel. With the exception of 205,956 barrels produced in California, all of the fuel oils, so called, produced in the United States were from the Trenton limestone oil fields in Ohio and Indiana. The total production of all grades of oil in the United States was 35,163,513 barrels, valued at \$26,963,340, or 76½ cents per barrel.

STOCKS OF CRUDE PETROLEUM.

The stocks of crude petroleum held in tanks at the wells in the United States on December 31, 1888 and 1889, as well as the total production for December, 1888, and December, 1889, are given in the following table. In the States other than Pennsylvania, Ohio and West Virginia these stocks at the wells represent all the stocks of crude petroleum held by producers or for them. In Pennsylvania, Ohio and West Virginia to these stocks at the wells should be added the stocks held by the pipe-line companies. Even this total will not represent the amount of crude petroleum in the country, but only that held by the producer or the party who has purchased the oil from him which is still carried in the tanks of the pipe-line companies. The crude petroleum held by the refiners is not included in the statement.

The table of stocks on hand December 31, 1888 and 1889, is as follows:

Production and well stocks of crude petroleum in 1888 and 1889, by States.

States.	1888.			1889.		
	Production, December.	Stock on hand at wells December 31.	Per cent. of stock at wells, production.	Production, December.	Stock on hand at wells December 31.	Per cent. of stock at wells, production.
	<i>Barrels.</i>	<i>Barrels.</i>		<i>Barrels.</i>	<i>Barrels.</i>	
Pennsylvania and New York	1,582,741	339,187	21.43	2,055,247	423,336	20.60
Ohio	1,070,746	81,224	7.59	971,538	470,125	48.39
West Virginia	19,060	6,104	32.03	81,453	6,835	8.39
Colorado	25,769	13,092	50.81	34,570	51,034	147.63
California	28,671	7,547	26.32	25,737	3,440	13.37
Indiana				a2,730	12,250	448.72
Kentucky				a450		
Illinois	a120	110	91.67	a120	100	83.33
Kansas	a42	100	238.10	a42	100	238.10
Texas	a4	6	150.00	a4	48	1,200.00
Missouri	a1			a2		
Total	2,727,154	447,370	16.40	3,171,893	967,268	30.49

a Average per month for the year.

From this table it appears that out of a total production in the United States of 2,727,154 barrels in December, 1888, 447,370 barrels, or 16.40 per cent. was carried in stock at the wells on December 31, 1888, while

of a production of 3,171,893 barrels in December, 1889, 967,268 barrels, or 30.49 per cent. was carried in stock at the wells. It will be noted that at the close of December, 1888, stocks carried at the wells of Pennsylvania amounted to 21.43 per cent. of the total production, and at the close of December, 1889, 423,336 barrels, or 20.60 per cent. was carried in stock at the wells. In Ohio but 7.59 per cent. of the production of December, 1888, was carried at the wells at the close of that month, while 48.39 per cent. of the production of December, 1889, was so carried. The other figures are of but little importance.

The stock of crude petroleum carried by the pipe lines in Pennsylvania and New York at the close of December, 1888, was 18,995,814 barrels. On December 31, 1889, this had decreased to 11,562,593 barrels. The stock held by the pipe lines in Ohio at the close of December, 1888, was 10,161,842 barrels. At the close of December, 1889, this had increased to 14,415,997 barrels, making a total stock held by the pipe lines at the close of December, 1888, of 29,157,656 barrels, and at the close of December, 1889, of 25,978,590 barrels. Adding these amounts to the stocks carried at the wells, there would be a total of 29,605,026 barrels in stock December 31, 1888, and 26,945,858 barrels on December 31, 1889.

CENSUS STATISTICS OF WAGES.

Concerning the different rates of wages paid foremen, pumpers or engineers, and drillers, shown in the various tables of classified wages that will appear through this report, it should be noted that a pumper or engineer may operate a number of wells and the lowest rate given may be for one well and highest rate for a group of wells. A similar remark will apply to the wages of foremen.

The statistics of labor and wages in the production of crude petroleum in the United States in 1889, by States, are as follows:

Total number of employes and number of each class and wages paid.

States.	Number of employes.	Total wages.	Foremen.		Mechanics.	
			Number.	Wages.	Number.	Wages.
Pennsylvania and New York	19,832	\$7,423,781	1,230	\$744,674	10,049	\$3,742,416
Ohio	2,123	836,377	94	71,613	724	235,607
West Virginia	339	160,974	17	14,520	213	108,298
Colorado	90	31,632	5	4,950	56	19,138
California	95	75,056	5	8,000	25	18,147
Indiana	34	6,080	1	1,200	7	725
Kentucky	14	3,050	2	1,248	8	660
Illinois	1	600				
Kansas	10	6,000			2	1,000
Missouri	1	350				
Total	22,539	8,546,900	1,354	846,205	11,084	4,125,991

Total number of employes and number of each class and wages paid—Continued.

States.	Laborers.		Boys under 16.		Office force.			
	Num-ber.	Wages.	Num-ber.	Wages.	Males.		Females.	
					Num-ber.	Wages.	Num-ber.	Wages.
Pennsylvania and New York	8,256	\$2,748,453	156	\$53,193	134	\$133,741	7	\$1,304
Ohio	1,282	509,421			23	19,736		
West Virginia	107	36,756			2	1,400		
Colorado	28	8,744			1	1,800		
California	62	46,284			3	2,625		
Indiana	25	4,105			1	50		
Kentucky	4	1,142						
Illinois	1	600						
Kansas	6	2,500			2	2,500		
Missouri	1	350						
Total	9,772	3,358,355	156	53,193	166	161,852	7	1,304

Total wages paid and wages paid for the several classes of work.

States.	Total.	Wages paid in—						
		Building rigs.	Drilling wells.	Operating and caring for wells.	Tor-pedoing wells.	Building and re-pairing tankage.	Building and re-pairing pipe lines.	Office.
Pennsylvania and New York	\$7,423,781	\$478,214	\$2,780,795	\$3,773,139	\$105,626	\$110,268	\$40,694	\$135,045
Ohio	836,377	30,254	174,299	595,518	3,728	9,440	3,402	19,736
West Virginia	160,974	19,869	82,312	55,903	30	1,460		1,400
Colorado	34,632	2,703	8,099	21,494			536	1,800
California	75,056	3,195	20,131	49,055		50		2,625
Indiana	6,080	125	600	5,305				50
Kentucky	3,050	200	1,650	1,200				
Illinois	600			600				
Kansas	6,000	300		3,000		100	100	2,500
Missouri	350			350				
Total	8,546,900	534,860	3,067,886	4,505,564	109,384	121,318	44,732	163,156

PENNSYLVANIA.

Owing to their intimate connection in a commercial way, it is almost impossible to make an exact separation between the oil produced in New York and Pennsylvania. The basis of all information regarding the production of oil in Pennsylvania and New York is the pipe-line report, and in these reports of the Bradford district no distinction is made between the oil produced in Pennsylvania and that in New York, the Bradford district including portions of McKean county, Pennsylvania, and Cattaraugus county, New York. The returns from the northern field, as it is called, include not only the Bradford district, and, consequently, the production of the wells in Cattaraugus county, New York, but also of the wells of Allegany county, in the same State. An attempt has been made to separate the oil produced in New York from that in Pennsylvania, but at best the result must be regarded only as an approximation. In this report Pennsylvania is divided into eleven districts, as follows: (1) The Bradford district, (2) Forest county,

(3) Warren county, (4) Butler, Clarion, and Elk counties, etc., (5) Tidoute and Titusville, (6) Allegheny (Pennsylvania) county, (7) Beaver county, (8) Washington county, (9) Greene county, (10) the Franklin lubricating-oil district, and (11) Smith's Ferry district. These may be classified in a general way into the Bradford, Middle Lower and Washington or Southwestern districts.

The Bradford district lies chiefly in Pennsylvania, in McKean county, but the main field extends some 5 or 6 miles into New York. An outlying basin of oil rock, which properly belongs to the Bradford basin, is situated for the greater part in Carrollton township, Cattaraugus county, New York. This field also includes the small outlying district of Kinzua, which lies southwest from the main district and contains large and long-lived wells, and the Windfall Run field, lying in Pennsylvania, near Eldred, which has only small wells. The sand from which the oil in the Allegany (New York) and Bradford districts is obtained is a gray, black, dark brown, or chocolate brown sand of about the coarseness of the ordinary beach sand of the New Jersey coast. The oil obtained is dark amber green, and occasionally black. Its gravity is generally slightly greater than that of the oil usually obtained from the Venango and Butler districts.

The Middle field, the Warren and Forest, is located in the counties from which it takes its name. It includes such pools as Cherry Grove, Balltown and Cooper, Stoneham, Clarendon, Tiona, Kane, Grand Valley, and others in these two counties. The oil in this district comes from sands of varying geological horizons, having somewhat the general appearance of the Bradford and Allegany sand, but frequently coarser grained. The late Dr. Ashburner was of the opinion that the Allegany (New York), Bradford, Warren, and Forest district oil sands were of the Chemung (Devonian) age. The oils from the several Warren and Forest pools differ very greatly in color and gravity, but they are generally spoken of as amber oils.

The Lower field begins with a few pools in the southwestern corner of Warren county and the western end of Forest county and embraces all the oil-producing territory southward, including the fields of Venango, Clarion, and Butler counties, the field on the Ohio river in Beaver county, and the fields in Lawrence county. The oil of the Venango subdivision of the Lower district is obtained from three principal sand beds, known, respectively, as the first, second, and third oil sands, contained within an interval of about 350 feet. These sands are believed to belong to the Catskill (Devonian) formation. These sands were the first discovered in Pennsylvania, and drillers from this field operating in other districts designated the sands which were found in the new districts as the first, second, and third sands, irrespective of their geological position. The Venango sands generally consist of white, gray, or yellow pebble rock. The oils vary, though generally they are green in color, sometimes black, and in a few instances amber. The gravity varies

from 30° to 51°, 48° being about the average of the oil obtained from the third sand, which is the greatest producer. The Butler subdivision of the Lower district includes oil pools in Butler, Clarion, southeastern Venango, and Armstrong counties. The character of the sands and oils are very much the same as the Venango district. The Beaver subdivision of the Lower district includes chiefly the Slippery Rock and Smith's Ferry fields. In both of these pools heavy oil is obtained from the representative of the Pottsville conglomerate and amber oil from the Berea grit, in the sub-Carboniferous series.

The Washington or Southwestern district includes the wells in Allegheny, Washington, and Greene counties, in southwestern Pennsylvania. The general character of the sands and oil is similar to that of the Lower district.

Production in Pennsylvania and New York.—In the table below is given the actual production of crude petroleum in the States of Pennsylvania and New York in 1889, by months and districts. The total production for these States was 21,487,435 barrels in 1889, and 28,458,208 barrels in 1890. These totals differ somewhat from the totals of the pipe-line runs, which are the receipts from the wells by the pipe lines as published from month to month. These runs include all the production of Pennsylvania and New York and a portion of the production of West Virginia. After making due allowance for the West Virginia runs, the totals as given in the table of production and the pipe-line totals do not differ greatly. In fact, so far as it can be ascertained, the pipe-line runs in 1889 approximated very closely to the actual production.

The production of crude petroleum in Pennsylvania and New York in 1889, by districts and months, is as follows:

Production of crude petroleum in Pennsylvania and New York in 1889, by districts and months.

[Barrels of 42 gallons.]

Districts.	Jan.	Feb.	Mar.	Apr.	May.	June.
Bradford district, Pennsylvania and New York, and Alleghany county, New York.....	603,946	490,878	607,804	548,903	595,371	614,286
Forest county.....	19,537	16,737	21,689	19,393	23,699	22,647
Warren county.....	174,437	162,844	190,188	201,159	209,474	202,385
Butler and Clarion counties, etc.....	412,733	352,432	405,950	406,797	432,769	413,407
Tidioute and Titusville ..	66,569	61,135	70,321	67,122	83,560	72,476
Allegheny county.....	20,495	22,599	28,996	32,625	50,598	55,214
Beaver county.....	27,361	23,230	28,159	28,092	45,796	41,071
Washington county.....	185,516	171,165	244,474	301,799	349,192	357,033
Greene county.....	24,707	23,873	22,383	21,836	23,527	24,792
Franklin district.....	5,088	5,172	6,280	5,790	5,373	5,757
Smith's Ferry district (a).....	2,417	2,417	2,417	2,417	2,417	2,417
Pennsylvania and New York.....	1,542,806	1,332,482	1,628,661	1,635,933	1,821,776	1,811,485

a. Smith's Ferry production, which was very regular, is averaged at 2,416.67 barrels per month.

Production of crude petroleum in Pennsylvania and New York, etc.—Continued.

[Barrels of 42 gallons.]

Districts.	July.	Aug.	Sept.	Oct.	Nov.	Dec.	Total.
Bradford district, Penn- sylvania and New York, and Allegany county, New York	638, 763	628, 792	586, 686	618, 286	598, 952	625, 696	7, 158, 363
Forest county	23, 673	22, 336	21, 823	22, 432	23, 132	21, 857	258, 955
Warren county	211, 600	201, 766	191, 843	206, 944	195, 290	199, 504	2, 347, 434
Butler and Clarion coun- ties, etc.	451, 064	490, 873	475, 925	502, 541	484, 772	529, 140	5, 358, 403
Tidonts and Titusville ..	77, 392	75, 450	68, 728	78, 365	80, 920	83, 081	885, 119
Allegheny county	56, 529	54, 387	49, 942	59, 086	49, 606	61, 015	541, 092
Beaver county	51, 675	49, 354	49, 545	57, 670	78, 007	122, 776	602, 736
Washington county	401, 325	397, 093	376, 007	363, 830	351, 509	349, 262	3, 848, 145
Greene county	33, 819	36, 767	38, 768	42, 719	44, 176	55, 545	392, 912
Franklin district	5, 911	4, 992	5, 927	4, 880	5, 091	5, 015	65, 276
Smith's Ferry district (a) ..	2, 417	2, 417	2, 416	2, 416	2, 416	2, 416	29, 000
Pennsylvania and New York	1, 954, 168	1, 964, 227	1, 867, 610	1, 950, 169	1, 913, 871	2, 055, 247	21, 487, 435

a Smith's Ferry production, which was very regular, is averaged at 2,416.67 barrels per month.

The total production of crude petroleum in the Pennsylvania and New York oil fields from 1871 to 1889, by months and years, is as follows:

Total product of crude petroleum in the Pennsylvania and New York oil fields from 1871 to 1890, by months and years.

[Barrels.]

Years.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.
1871	418, 407	372, 568	400, 334	385, 980	408, 797	410, 340	456, 475
1872	583, 575	462, 985	461, 590	462, 090	537, 106	491, 130	517, 762
1873	632, 617	608, 300	665, 291	641, 520	776, 364	793, 470	867, 473
1874	1, 167, 243	835, 492	883, 438	778, 740	895, 745	921, 750	1, 033, 447
1875	852, 159	719, 824	789, 539	675, 000	696, 508	696, 210	788, 361
1876	712, 225	668, 885	718, 177	701, 490	735, 351	723, 600	763, 623
1877	842, 890	783, 216	901, 697	972, 810	1, 127, 594	1, 130, 790	1, 189, 005
1878	1, 203, 296	1, 094, 856	1, 208, 380	1, 195, 890	1, 264, 862	1, 217, 250	1, 283, 865
1879	1, 369, 921	1, 261, 935	1, 499, 315	1, 530, 450	1, 644, 922	1, 675, 650	1, 637, 767
1880	1, 904, 113	1, 870, 008	2, 015, 992	2, 015, 700	2, 228, 931	2, 158, 440	2, 248, 430
1881	2, 244, 090	1, 913, 128	2, 274, 532	2, 205, 780	2, 393, 293	2, 377, 860	2, 372, 678
1882	2, 353, 551	2, 131, 332	2, 482, 170	2, 402, 790	2, 486, 572	2, 825, 940	3, 258, 162
1883	1, 948, 319	1, 756, 188	1, 830, 674	1, 816, 530	1, 962, 052	1, 977, 900	2, 020, 394
1884	1, 825, 838	1, 880, 650	2, 052, 262	2, 065, 860	2, 381, 854	1, 862, 190	2, 059, 950
1885	1, 632, 176	1, 437, 884	1, 638, 133	1, 780, 290	1, 771, 371	1, 707, 210	1, 775, 804
1886	1, 748, 958	1, 604, 848	1, 928, 448	1, 938, 300	2, 178, 773	2, 335, 380	2, 418, 961
1887	1, 990, 851	1, 827, 924	2, 007, 196	1, 960, 860	1, 993, 517	1, 912, 860	2, 199, 525
1888	1, 155, 937	1, 290, 718	1, 338, 877	1, 349, 403	1, 473, 362	1, 450, 703	1, 394, 847
1889	1, 542, 806	1, 332, 482	1, 628, 661	1, 635, 933	1, 821, 776	1, 811, 485	1, 954, 168
1890	2, 108, 248	2, 055, 424	2, 313, 189	2, 328, 870	2, 378, 382	2, 370, 001	2, 524, 266

Years.	Aug.	Sept.	Oct.	Nov.	Dec.	Total.
1871	462, 582	461, 940	485, 243	464, 610	477, 958	5, 265, 234
1872	549, 909	500, 430	442, 432	638, 610	645, 575	6, 293, 194
1873	936, 138	954, 270	942, 493	991, 470	1, 084, 380	9, 893, 786
1874	931, 519	840, 630	919, 739	861, 060	858, 142	10, 926, 945
1875	718, 766	698, 910	731, 079	700, 200	720, 874	8, 787, 514
1876	782, 223	780, 600	809, 162	786, 480	787, 090	8, 968, 906
1877	1, 273, 759	1, 214, 910	1, 269, 326	1, 173, 420	1, 256, 058	13, 135, 475
1878	1, 341, 928	1, 315, 710	1, 369, 797	1, 348, 950	1, 138, 678	15, 163, 462
1879	1, 892, 302	1, 856, 700	1, 836, 378	1, 710, 450	1, 769, 356	19, 685, 176
1880	2, 341, 027	2, 346, 300	2, 385, 636	2, 274, 420	2, 238, 634	26, 027, 631
1881	2, 331, 727	2, 193, 420	2, 323, 171	2, 266, 830	2, 480, 000	27, 376, 509
1882	3, 104, 445	2, 620, 380	2, 297, 658	2, 192, 940	1, 897, 510	30, 053, 500
1883	1, 879, 437	1, 913, 370	2, 076, 659	1, 958, 340	1, 988, 526	23, 128, 389
1884	2, 099, 165	1, 948, 260	1, 961, 806	1, 811, 700	1, 822, 614	23, 772, 209
1885	1, 705, 961	1, 712, 790	1, 874, 105	1, 761, 660	1, 898, 657	20, 776, 041
1886	2, 413, 206	2, 418, 540	2, 408, 111	2, 222, 790	2, 181, 625	25, 798, 000
1887	1, 848, 877	1, 779, 930	1, 843, 291	1, 125, 450	1, 288, 602	21, 478, 883
1888	1, 382, 077	1, 273, 080	1, 354, 518	1, 442, 405	1, 582, 741	16, 488, 668
1889	1, 964, 227	1, 867, 610	1, 959, 169	1, 913, 871	2, 055, 247	21, 487, 435
1890	2, 514, 968	2, 584, 949	2, 750, 698	2, 575, 941	2, 626, 035	229, 130, 910

a Not including 877,310 barrels dump oil and oil shipped by private lines.

b Pipe line runs.

For some years previous to and including 1887 the total production given is simply the total of the pipe-line runs. The statistics in the early years, as indeed all of the figures up to the close of 1888, are those published in Stowell's Petroleum Reporter. As the pipe-line runs for 1888 and 1889 differ from the totals of production as given in the above table, and as these runs are of sufficient importance to those interested in the production of petroleum to become a matter of record, the runs for these two years are given below.

The runs of the several pipe lines for 1889, as reported from month to month in Pennsylvania and New York and that portion of West Virginia tributary to the southwestern Pennsylvania field, are as follows, by months and lines:

Pipe-line runs in Pennsylvania and New York in 1889, by lines and months.

[Barrels.]

Months.	National.	Tide water.	Octave.	Miller.	Western Atlantic.	South-west.	Franklin.	Total.
January	1,071,087	128,904	1,847	16,734	110,718	178,720	5,002	1,513,012
February	901,549	104,962	2,034	14,564	105,060	174,397	5,080	1,307,652
March	1,102,188	111,387	2,179	17,020	142,150	227,657	6,194	1,608,755
April	1,071,665	89,900	2,079	17,277	176,699	265,879	5,704	1,629,203
May	1,119,920	126,692	2,908	16,497	207,896	314,929	5,237	1,794,129
June	1,104,625	133,160	2,421	15,877	209,506	333,410	5,671	1,804,671
July	1,181,200	132,106	2,719	17,348	232,940	373,530	5,825	1,945,668
August	1,174,489	130,835	3,186	15,399	277,143	355,468	4,906	1,961,426
September	1,103,009	125,908	3,863	14,813	277,662	329,044	5,841	1,860,140
October	1,185,362	133,965	3,318	14,362	263,834	362,878	4,794	1,968,513
November	1,118,210	146,226	2,668	14,086	243,813	368,618	5,005	1,898,626
December	1,542,491	229,894	3,314	14,136	254,405	449,989	4,929	2,499,158
Total	13,675,776	1,593,939	32,536	188,113	2,501,826	3,734,519	64,244	21,790,953

The total runs by months for 1888 and 1889 are given below. It should be borne in mind, as stated above, that the runs for 1889 include a portion of the production of West Virginia as well as all of the production of Pennsylvania and New York.

Pipe-line runs in Pennsylvania and New York in 1888 and 1889, by months.

[Barrels.]

Months.	1888.	1889.	Months.	1888.	1889.
January	1,126,035	1,513,012	August	1,365,962	1,961,426
February	1,240,092	1,307,652	September	1,253,149	1,860,140
March	1,211,086	1,608,755	October	1,311,643	1,968,513
April	1,320,936	1,629,203	November	1,416,448	1,898,626
May	1,433,469	1,794,129	December	1,550,902	2,499,158
June	1,422,960	1,804,671			
July	1,370,080	1,945,668	Total	16,022,792	21,790,953

Monthly and yearly average price of pipe-line certificates or crude petroleum at the well for the years 1882 to 1890.

Months.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
January.....	\$0.83 $\frac{1}{2}$	\$0.93 $\frac{3}{4}$	\$1.11	\$0.70 $\frac{7}{8}$	\$0.8- $\frac{1}{2}$	\$0.70	\$0.91 $\frac{1}{2}$	\$0.80 $\frac{1}{2}$	\$1.05 $\frac{1}{2}$
February.....	.84 $\frac{1}{2}$	1.01	1.04 $\frac{3}{4}$.72 $\frac{3}{4}$.79 $\frac{1}{2}$.64 $\frac{5}{8}$.91 $\frac{3}{8}$.89 $\frac{1}{2}$	1.05 $\frac{1}{2}$
March.....	.81 $\frac{3}{4}$.97	.98 $\frac{3}{4}$.80 $\frac{1}{2}$.77 $\frac{1}{4}$.63 $\frac{3}{8}$.93 $\frac{3}{8}$.90 $\frac{7}{8}$.90
April.....	.78 $\frac{3}{4}$.92	.94	.78 $\frac{1}{2}$.74 $\frac{1}{2}$.64 $\frac{7}{8}$.82 $\frac{3}{8}$.88	.82 $\frac{5}{8}$
May.....	.71 $\frac{1}{2}$	1.00 $\frac{1}{2}$.85 $\frac{5}{8}$.79	.70	.64 $\frac{1}{2}$.86 $\frac{1}{2}$.83 $\frac{1}{2}$.88 $\frac{7}{8}$
June.....	.54 $\frac{3}{4}$	1.16	.68 $\frac{1}{2}$.82	.66 $\frac{1}{2}$.62 $\frac{1}{2}$.75 $\frac{7}{8}$.83 $\frac{1}{2}$.89 $\frac{1}{2}$
July.....	.57 $\frac{1}{2}$	1.05	.63 $\frac{1}{2}$.92 $\frac{1}{2}$.66	.59 $\frac{1}{2}$.80 $\frac{3}{8}$.95 $\frac{1}{2}$.89 $\frac{1}{2}$
August.....	.58 $\frac{3}{4}$	1.08 $\frac{1}{2}$.81 $\frac{1}{2}$	1.00 $\frac{1}{2}$.62 $\frac{1}{2}$.60	.90 $\frac{3}{8}$.99 $\frac{1}{2}$.89 $\frac{1}{2}$
September.....	.72 $\frac{3}{4}$	1.12 $\frac{1}{2}$.78	1.00 $\frac{3}{4}$.63 $\frac{1}{2}$.67	.93 $\frac{3}{8}$.99 $\frac{1}{2}$.81 $\frac{1}{2}$
October.....	.92 $\frac{3}{4}$	1.11	.71 $\frac{1}{2}$	1.05 $\frac{1}{2}$.65 $\frac{1}{2}$.70 $\frac{7}{8}$.90 $\frac{3}{8}$	1.01	.80 $\frac{1}{2}$
November.....	1.14	1.14 $\frac{1}{2}$.72 $\frac{1}{2}$	1.04 $\frac{3}{4}$.71 $\frac{1}{2}$.73	.85 $\frac{3}{4}$	1.08 $\frac{1}{2}$.72 $\frac{3}{4}$
December.....	.96	1.14 $\frac{3}{4}$.74 $\frac{3}{4}$.89 $\frac{7}{8}$.70 $\frac{5}{8}$.80 $\frac{1}{2}$.89 $\frac{1}{4}$	1.04	.67 $\frac{1}{2}$
Average....	.78 $\frac{2}{3}$	1.05 $\frac{3}{4}$.83 $\frac{1}{2}$.88	.71 $\frac{1}{4}$.66 $\frac{2}{3}$.87 $\frac{2}{3}$.94 $\frac{1}{2}$.80 $\frac{3}{4}$

Quantity of crude petroleum produced in, and the quantity and value of petroleum products exported from, the United States during the fiscal years 1864 to 1884, and calendar years 1885 to 1890.

Years ended—	Production (a).		Mineral, crude (including all natural oils without regard to gravity).				Naphthas, benzine, gasoline, etc.		Illuminating.		Lubricating (heavy paraffin, etc.).		Residuum (tar, pitch, and all other from which the light bodies have been distilled).	Total.
	Barrels (of 42 gallons) produced.	Gallons produced.	Gallons.	Value.	Gallons.	Value.	Gallons.	Value.	Gallons.	Value.	Gallons (b).	Value.		
June 30, 1864..	2, 478, 709	104, 105, 778	82, 864, 187	438, 197	12, 791, 518	86, 764, 411	12, 791, 518	86, 764, 411	23, 210, 368	810, 782, 689
1865..	2, 424, 905	101, 846, 010	6, 868, 513	480, 947	173, 943	1, 722, 005	9, 520, 957	25, 496, 849	16, 563, 413
1866..	3, 168, 700	132, 959, 400	6, 013, 921	673, 477	188, 825	34, 255, 621	18, 626, 141	50, 987, 341	24, 630, 887
1867..	3, 591, 400	136, 559, 800	1, 864, 903	224, 248	34, 175	62, 680, 657	22, 509, 466	70, 255, 881	24, 407, 672
1868..	3, 613, 709	131, 775, 778	1, 864, 903	1, 517, 208	267, 873	67, 909, 961	19, 977, 870	79, 456, 888	21, 810, 676
1869..	4, 046, 558	169, 965, 436	2, 994, 404	2, 673, 094	445, 770	84, 403, 492	27, 636, 137	100, 636, 684	31, 127, 433
1870..	4, 411, 016	185, 265, 672	2, 537, 292	5, 422, 604	564, 864	97, 902, 505	29, 864, 193	113, 735, 294	32, 668, 960
1871..	5, 558, 775	233, 468, 550	1, 971, 847	7, 209, 592	746, 797	132, 608, 953	34, 138, 736	110, 636, 684	31, 127, 433
1872..	5, 842, 497	245, 384, 874	2, 307, 111	8, 092, 635	932, 160	122, 539, 575	30, 566, 108	149, 892, 691	36, 894, 810
1873..	7, 242, 343	304, 178, 406	3, 010, 050	9, 743, 593	1, 487, 439	158, 102, 414	37, 195, 735	145, 171, 583	34, 058, 390
1874..	11, 188, 741	469, 927, 122	2, 099, 696	9, 737, 457	1, 038, 622	217, 220, 514	37, 560, 995	187, 456, 187	42, 050, 756
1875..	10, 083, 828	423, 520, 776	1, 406, 018	11, 758, 940	1, 442, 440	191, 551, 933	27, 030, 363	247, 806, 483	41, 245, 815
1876..	8, 829, 142	370, 571, 964	2, 220, 268	14, 780, 236	1, 442, 440	191, 551, 933	27, 030, 363	221, 955, 308	30, 073, 568
1877..	10, 822, 871	454, 560, 582	3, 756, 729	15, 140, 183	1, 816, 682	262, 441, 874	35, 401, 133	233, 060, 152	32, 815, 766
1878..	14, 738, 262	619, 007, 004	2, 694, 018	16, 416, 621	1, 411, 812	289, 214, 541	41, 513, 676	309, 198, 914	61, 789, 438
1879..	16, 917, 006	710, 539, 452	2, 180, 413	15, 084, 361	1, 258, 780	331, 586, 442	35, 999, 862	338, 841, 303	46, 374, 974
1880..	22, 382, 509	940, 065, 378	1, 927, 207	18, 411, 044	1, 192, 229	367, 325, 823	31, 783, 575	378, 310, 010	40, 360, 249
1881..	25, 805, 363	1, 083, 825, 246	3, 065, 464	17, 292, 311	1, 693, 275	332, 283, 043	34, 317, 695	423, 984, 699	36, 218, 625
1882..	28, 662, 181	1, 203, 307, 602	3, 129, 511	20, 213, 098	1, 809, 143	488, 213, 031	36, 588, 854	439, 662, 240	315, 000
1883..	26, 662, 808	1, 119, 837, 936	5, 302, 974	17, 070, 537	1, 302, 236	419, 821, 081	36, 574, 574	511, 232, 706	40, 315, 000
1884..	23, 744, 924	997, 286, 802	6, 040, 685	15, 045, 411	1, 072, 631	415, 615, 693	38, 195, 934	559, 954, 590	51, 232, 706
1885..	20, 776, 041	872, 583, 722	5, 068, 039	14, 739, 469	1, 160, 909	445, 531, 860	39, 439, 934	505, 981, 622	47, 913, 079
1886..	25, 708, 000	1, 083, 516, 000	5, 068, 039	14, 739, 469	1, 264, 736	485, 120, 680	39, 012, 922	513, 600, 092	47, 913, 079
1887..	21, 478, 883	902, 113, 088	5, 461, 363	13, 324, 260	1, 049, 043	455, 242, 107	37, 007, 336	591, 856, 302	48, 155, 204
1888..	16, 491, 084	692, 628, 528	5, 461, 363	13, 324, 260	1, 083, 429	454, 985, 784	37, 229, 551	601, 846, 307	46, 898, 842
1889..	21, 487, 435	692, 472, 270	6, 134, 002	13, 984, 407	1, 208, 116	551, 769, 660	41, 215, 192	572, 457, 975	48, 105, 743
1890..	28, 453, 208	1, 195, 244, 736	6, 744, 225	12, 937, 433	1, 134, 799	523, 285, 960	38, 640, 638	680, 705, 456	53, 293, 299

a As a given number of refined petroleum represents the product of a larger number of gallons of crude petroleum, it is necessary to reduce the exports of petroleum to their equivalent in crude oil, in order to arrive at a knowledge of the percentage of the total product of mineral oil exported. It has been ascertained, as the result of careful computation, that the quantity of petroleum and its distilled products exported during the year ended June 30, 1878, was equivalent to 407,482,175 gallons of crude oil; or, in other words, that the exports of petroleum constituted about 66 per cent. of the production. A larger percentage of the mineral oil product of the country is exported than of any other product, except cotton.

b Barrels reduced to gallons, at the rate of 42 gallons to the barrel.

c Estimated.

The values of the illuminating oils in Pennsylvania are based on the average value of pipe-line certificates. These averages for 1889, 12 months, were as follows:

Monthly average price of pipe-line certificates in 1889.

January	\$0.86 $\frac{5}{8}$	July	\$0.88 $\frac{1}{2}$
February	0.89 $\frac{1}{2}$	August	0.88 $\frac{1}{2}$
March	0.90 $\frac{5}{8}$	September	0.88 $\frac{1}{2}$
April	0.88	October	1.00
May	0.83 $\frac{1}{2}$	November	1.00
June	0.83 $\frac{7}{8}$	December	1.00
Average			\$0.88 $\frac{1}{2}$

These averages it is to be understood are not true averages, that is, the average which considers both price and quantity sold at that price, but they are the averages of the prices obtained in the different primary markets from day to day, which are the bases of the prices paid by the larger consumer, the Standard Oil Company, for all oil bought by them on that day. It is probable that the true average prices are slightly under the averages usually obtained. These, however, under the circumstances, are the only averages that can be ascertained, and do not vary greatly from the average of the prices.

The only oil that sold at the average in 1889 was that from the Bradford-Allegany district. The oil from each of the other districts commanded a premium above the price of pipe-line certificates, owing to its being better adapted to the production of light products and water-white oil. The average premium, as it was called, in the Forest, Warren, Butler, Clarion-Venango, and Allegheny (Pennsylvania) district was 20 cents; in the other districts, 25 cents.

The total production, total value, and average value of all of the oil produced in the Pennsylvania and New York district in 1889, by districts, were as follows:

Total production, total value, and average value of crude petroleum produced in the Pennsylvania and New York districts in 1889, by districts.

Districts.	Illuminating.			Lubricating.		
	Production.	Value.	Price per barrel.	Production.	Value.	Price per barrel.
	<i>Barrels.</i>			<i>Barrels.</i>		
Bradford-Allegany	7, 158, 363	\$6, 737, 809	\$0.94 $\frac{1}{2}$			
Forest	258, 955	295, 532	1.14 $\frac{1}{2}$			
Warren	2, 347, 434	2, 679, 010	1.14 $\frac{1}{2}$			
Butler-Clarion-Venango ^(a)	6, 243, 522	7, 125, 421	1.14 $\frac{1}{2}$			
Allegheny, Pennsylvania	541, 092	617, 512	1.14 $\frac{1}{2}$			
Beaver	602, 736	718, 010	1.19 $\frac{1}{2}$	b29, 000	\$34, 546	\$1.19 $\frac{1}{2}$
Washington	3, 848, 145	4, 584, 103	1.19 $\frac{1}{2}$			
Greene	392, 912	468, 056	1.19 $\frac{1}{2}$			
Franklin				65, 276	215, 164	3.30
Total	21, 393, 159	23, 225, 453	1.08 $\frac{5}{8}$	94, 276	249, 710	2.64 $\frac{7}{8}$

^a Including Tidioute and Titusville district.

^b Smith's Ferry district.

In the table from Stowell's Petroleum Reporter, given on the following page, will be found the monthly and yearly average of pipe-line certificates or the prices at primary markets of crude petroleum per barrel of 42 gallons from 1865 to 1890, inclusive. The remarks made

above regarding the value of these averages should be noted in examining this table; that is, that these are not true average prices, but the average of the prices obtained daily.

Monthly and yearly average prices of pipe-line certificates of crude petroleum at wells from 1865 to 1890.

Years.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.	Aug.	Sept.	Oct.	Nov.	Dec.	Yearly.
1865	\$8.25	\$7.50	\$6.00	\$6.00	\$7.37½	\$5.62½	\$5.12½	\$4.62½	\$6.75	\$8.12½	\$7.25	\$6.50	\$6.59
1866	4.50	4.40	3.75	3.95	4.50	3.87½	3.00	3.75	4.50	3.39	3.10	2.12½	3.74
1867	1.87½	1.85	1.75	2.07½	2.35	1.90	2.62½	3.15	3.40	3.55	2.50	1.87½	2.41
1868	1.95	2.00	2.55	2.82½	3.75	4.50	5.12½	4.57½	4.00	4.12½	3.75	4.35	3.62½
1869	5.75	6.95	6.00	6.70	5.35	4.95	5.37½	5.57½	5.50	5.50	5.80	5.12½	5.63½
1870	4.52½	4.52½	4.45	4.22½	4.40	4.17½	3.77½	3.15	3.25	3.27½	3.22	3.40	3.84
1871	3.82½	4.38	4.25	4.51	4.60	3.82½	4.79	4.66	4.65	4.82	4.25	4.00	4.34
1872	4.02½	3.80	3.72½	3.52½	3.80	3.85	3.80	3.58½	3.25	3.15	3.89½	3.32½	3.63
1873	2.60	2.20	2.12½	2.30	2.47½	2.22½	2.00	1.42½	1.15	1.20	1.25	1.00	1.87
1874	1.20	1.40	1.60	1.90	1.62½	1.32½	1.02½	0.95	0.95	0.85	0.55	0.61½	1.15
1875	1.03	1.52½	1.75	1.36½	1.40	1.26½	1.00	1.13	1.33	1.32½	1.44	1.55	1.36
1876	1.80	2.60	2.01	2.02½	1.90½	2.01½	2.24	2.71½	3.81	3.37½	3.11	3.73	2.56½
1877	3.53½	2.70	2.67½	2.58	2.24	1.94½	2.07	2.51	2.38	2.56	1.91	1.80	2.42
1878	1.43	1.65½	1.59	1.37½	1.35½	1.14	0.98½	1.01	0.86½	0.82	0.89½	1.16	1.19
1879	1.03	0.98	0.86½	0.78½	0.76	0.68½	0.69½	0.67½	0.69	0.88	1.05	1.18	0.85½
1880	1.10½	1.03	0.88½	0.78	0.80	1.00	1.06	0.91	0.96	0.96	0.91	0.91	0.94½
1881	0.95½	0.90	0.83½	0.86½	0.817	0.811	0.76	0.78½	0.971	0.91	0.85	0.84	0.85½
1882	0.87½	0.84	0.81	0.78	0.71	0.54	0.57	0.58½	0.72	0.93	1.14	0.96	0.78½
1883	0.93½	1.01	0.97½	0.94	1.00	1.16½	1.05	1.08	1.12	1.11	1.14	1.14	1.05½
1884	1.11	1.04	0.98½	0.94	0.85	0.68	0.63	0.81½	0.78	0.71	0.72	0.74	0.83½
1885	0.70½	0.72	0.80½	0.78½	0.79	0.82	0.92	1.00½	1.00	1.05	1.04	0.89	0.87½
1886	0.88½	0.79	0.77½	0.74	0.70	0.66½	0.66	0.62½	0.63	0.65	0.71	0.70	0.71½
1887	0.70	0.64	0.63½	0.64	0.64½	0.62	0.59	0.60½	0.67	0.70	0.73½	0.80	0.66½
1888	0.91½	0.91	0.93½	0.82	0.86½	0.75	0.80	0.90½	0.93	0.90	0.85	0.89½	0.87½
1889	0.86½	0.89½	0.90½	0.88	0.83½	0.83	0.95	0.99½	0.99	1.01	1.01	1.04	0.94½
1890	1.05½	1.03	0.90	0.82½	0.88½	0.89½	0.89	0.89½	0.81	0.80	0.72	0.67½	0.86½

Shipments of petroleum from Pennsylvania and New York.—In the following table will be found a statement of the number of barrels of crude petroleum and of refined petroleum reduced to its equivalent shipped out of the Pennsylvania and New York oil regions either by pipe line or railroad from 1871 to 1890, inclusive. In some years, especially in the earlier ones covered by this table, a considerable portion of the oil was shipped as refined. In this table that is reduced to its equivalent in crude, a barrel of refined being regarded as being produced from 1½ barrels of crude.

Shipments of crude petroleum and refined petroleum, reduced to crude equivalent, out of the Pennsylvania and New York oil fields for the years 1871-90, by months and years.

[Barrels.]

Year.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.
1871	437,691	347,718	389,890	389,147	587,375	501,754	541,137
1872	476,966	407,606	276,220	428,512	510,417	529,228	591,238
1873	573,124	527,440	668,374	708,191	768,176	696,414	814,449
1874	843,663	501,220	518,246	803,409	899,027	815,413	940,281
1875	453,995	327,776	693,918	729,581	681,679	745,986	904,537
1876	677,289	519,193	623,762	603,037	646,150	921,862	1,228,539
1877	743,461	484,904	913,919	903,526	1,234,324	1,391,124	1,096,951
1878	775,791	774,234	741,512	846,632	960,894	1,135,119	1,330,454
1879	663,998	702,729	973,879	1,136,188	1,331,469	1,369,314	1,625,035
1880	1,650,409	1,395,151	1,613,371	1,095,259	975,083	975,083	1,231,611
1881	1,061,617	915,028	1,276,746	1,348,398	1,563,436	1,729,697	1,925,532
1882	1,657,067	1,787,909	1,718,956	1,678,134	1,827,356	2,172,685	2,402,970
1883	1,357,815	1,250,824	1,641,899	1,908,379	1,995,634	1,747,789	1,634,407
1884	1,686,961	1,723,261	1,873,890	1,643,336	1,899,329	1,827,553	1,740,021
1885	1,804,028	1,895,021	1,887,034	1,823,726	2,097,099	2,034,025	1,961,152
1886	1,991,561	2,032,794	2,055,750	2,070,468	2,032,672	2,117,489	2,418,961
1887	2,312,067	1,995,757	2,332,324	1,938,278	2,328,564	2,165,439	2,000,173
1888	2,265,109	2,163,957	1,979,753	1,928,435	1,773,994	1,954,115	2,098,531
1889	2,388,609	2,272,060	2,263,009	2,236,004	2,256,120	2,402,280	2,949,597
1890	2,637,339	2,146,108	2,148,977	2,317,410	2,474,966	2,486,205	2,640,668

Shipments of crude petroleum and refined petroleum, etc.—Continued.

[Barrels.]

Year.	Aug.	Sept.	Oct.	Nov.	Dec.	Total.
1871.....	528, 134	551, 075	505, 071	480, 977	410, 822	5, 664, 7
1872.....	621, 954	541, 607	607, 468	477, 945	430, 786	5, 899, 9
1873.....	864, 768	952, 955	1, 010, 832	959, 589	955, 443	9, 499, 7
1874.....	793, 865	1, 014, 570	543, 341	546, 117	602, 348	8, 821, 50
1875.....	882, 089	1, 109, 392	871, 917	671, 066	871, 902	8, 942, 9
1876.....	1, 203, 402	1, 154, 549	524, 190	871, 496	1, 190, 983	10, 164, 4
1877.....	1, 425, 943	1, 563, 797	1, 268, 971	1, 205, 634	600, 019	12, 832, 57
1878.....	1, 655, 651	1, 434, 225	1, 747, 390	1, 281, 410	992, 688	13, 676, 0
1879.....	1, 808, 239	1, 627, 120	1, 662, 269	1, 453, 645	1, 532, 585	15, 886, 47
1880.....	1, 394, 129	1, 252, 635	1, 665, 933	1, 226, 030	1, 335, 613	15, 677, 49
1881.....	2, 214, 877	2, 131, 950	2, 080, 467	2, 066, 906	1, 969, 581	20, 284, 23
1882.....	2, 047, 545	1, 992, 171	2, 089, 428	1, 404, 640	1, 121, 453	21, 900, 31
1883.....	2, 086, 478	2, 325, 574	2, 215, 421	2, 065, 602	1, 749, 547	21, 979, 36
1884.....	2, 000, 371	2, 292, 087	2, 510, 283	2, 078, 261	2, 382, 244	23, 657, 59
1885.....	2, 049, 099	2, 116, 659	2, 050, 150	1, 857, 080	2, 138, 253	23, 713, 32
1886.....	2, 059, 299	2, 157, 323	2, 441, 848	2, 724, 796	2, 550, 891	26, 653, 85
1887.....	2, 220, 768	2, 342, 227	2, 573, 008	2, 462, 082	2, 608, 341	27, 279, 02
1888.....	2, 223, 263	2, 289, 486	1, 558, 115	2, 503, 491	2, 397, 782	25, 138, 03
1889.....	2, 625, 825	2, 567, 459	2, 747, 284	2, 393, 131	2, 671, 518	29, 638, 89
1890.....	2, 538, 224	2, 648, 418	2, 725, 341	2, 662, 898	2, 889, 525	30, 116, 07

These shipments are, for the latter years, chiefly what are known as pipe-line deliveries. It will be seen that the shipments for 1889 were the largest in the history of the trade, being 2,359,870 barrels greater than in 1887, the year of the largest previous shipment, when the total shipments were 27,279,028 barrels. It will also be noted that the shipments were over 8,000,000 barrels in excess of the production. This increased shipment makes itself very manifest in the statement of stocks held in the Pennsylvania and New York oil regions at the close of 1889, which are given below.

These figures of shipments must not be taken as showing the actual consumption of oil. To them must be added, in order to ascertain what becomes of the oil produced in the oil regions, all of the sediment, the dump oil, or oil that does not pass through the pipe line, as well as the amount of oil destroyed by fire and disposed of in other ways than by refining or direct consumption. There is also a certain amount of loss by evaporation and otherwise. This is provided for by the pipe lines in receiving the oil from the producers, a certain number of gallons per barrel being allowed for such loss. Forty-four gallons are generally delivered by the producer to the pipe line as a barrel, but certificates are issued for barrels of 42 gallons only.

Stocks of crude petroleum in the Pennsylvania and New York oil fields.—The reduction in stocks of petroleum held by the pipe lines in 1889 was most notable. The stocks at the close of that year, as will be seen in the following table, were less than at any time since 1879, being on December 31, 1889, 11,562,593 barrels, compared with 8,470,490 barrels at the close of 1879. Between 1879 and 1889 the stocks had risen to 37,366,126 barrels at the close of December, 1884. From this there was a gradual reduction until 1887, when the stocks stood 28,006,211 barrels on December 31 of that year, from which they dropped a little more than 9,000,000 barrels, or to 18,995,814, at the close of 1888, and to

11,562,593 at the close of 1889, notwithstanding, as has already been pointed out, the greatly increased production in 1889 over 1888. This increase, as above stated, in the Pennsylvania and New York oil fields was 4,998,767 barrels, yet the decrease in stocks was 7,433,221 barrels.

The following table shows the total stocks of crude petroleum in the Pennsylvania and New York oil fields from 1871 to 1890, by months and years:

Total stocks of crude petroleum in the Pennsylvania and New York oil fields for the years 1871-'90, by months and years.

[Barrels.]

Years.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.
1871	537,751	587,021	642,000	771,000	605,000	554,000	511,220
1872	532,971	579,793	662,497	877,832	950,803	1,010,302	990,229
1873	1,183,728	1,265,373	1,244,657	1,178,643	1,192,541	1,324,493	1,433,620
1874	1,948,919	2,283,032	2,648,210	2,623,534	2,594,286	2,701,625	2,279,479
1875	4,011,703	4,546,188	4,592,364	4,537,843	4,552,672	4,502,896	4,386,726
1876	3,585,143	3,734,835	3,829,250	3,900,793	3,989,904	3,791,642	3,326,726
1877	2,604,128	2,860,636	3,210,454	3,279,731	3,173,008	2,912,674	3,004,728
1878	3,555,342	3,875,964	4,342,832	4,692,090	4,996,058	5,078,189	5,031,600
1879	5,321,222	5,813,663	6,318,099	6,689,111	6,980,064	7,263,150	7,353,382
1880	8,724,194	9,004,062	9,606,683	10,780,153	11,916,577	13,099,964	14,116,753
1881	20,110,903	21,108,003	22,105,789	22,963,171	23,793,028	24,441,191	24,888,337
1882	26,716,188	27,059,611	27,822,825	28,547,481	29,206,697	29,859,952	30,715,144
1883	35,187,116	35,692,480	35,881,255	37,789,406	35,753,824	35,965,935	36,371,922
1884	35,884,509	36,041,898	36,220,270	36,642,794	38,631,203	38,665,838	38,985,767
1885	37,214,274	36,757,137	36,508,236	36,464,800	36,139,072	35,872,257	35,686,909
1886	34,186,238	34,082,775	33,954,493	33,823,385	33,969,486	34,187,377	34,428,490
1887	33,835,359	33,288,630	32,932,502	32,955,034	32,642,330	32,389,750	32,289,269
1888	26,927,634	26,084,574	25,404,276	24,893,223	24,653,043	24,219,496	23,586,951
1889	18,165,607	17,240,428	16,634,437	16,076,501	15,668,331	15,258,863	14,541,696
1890	11,060,220	10,990,417	11,170,997	11,178,990	11,062,100	10,866,587	10,663,497

Years.	Aug.	Sept.	Oct.	Nov.	Dec.	Averages.
1871	530,146	541,330	495,102	502,960	532,000	567,458
1872	997,166	951,410	914,423	886,909	1,084,423	869,897
1873	1,513,890	1,521,185	1,452,777	1,493,875	1,625,157	1,369,162
1874	2,932,444	2,758,504	3,134,902	3,449,845	3,705,639	2,755,035
1875	4,223,397	3,812,945	3,672,101	3,701,235	3,550,207	4,174,189
1876	3,304,405	2,930,456	3,040,108	2,955,092	2,551,199	3,411,622
1877	2,852,544	2,503,657	2,504,012	2,471,798	3,127,837	2,775,434
1878	4,717,877	4,509,362	4,221,769	4,289,309	4,615,299	4,501,308
1879	7,114,195	7,620,525	7,794,634	8,051,469	8,470,490	7,063,834
1880	15,063,651	16,157,316	16,877,019	18,025,409	18,928,430	13,525,015
1881	25,005,187	25,066,657	25,309,361	25,509,285	26,019,704	23,860,051
1882	31,772,094	32,400,303	32,608,533	33,728,555	34,596,612	30,419,500
1883	36,164,881	35,752,677	35,613,915	35,506,653	35,745,632	35,953,975
1884	39,084,561	38,740,734	38,192,317	37,925,756	37,366,126	37,698,481
1885	35,343,771	34,939,902	34,763,857	34,668,437	34,428,841	35,732,291
1886	34,800,397	35,061,614	35,027,877	34,525,871	34,156,605	34,350,384
1887	32,003,536	31,340,939	30,662,583	29,325,951	28,006,211	31,806,015
1888	22,825,298	21,876,681	20,722,024	19,734,132	18,995,814	23,426,929
1889	13,859,267	13,198,452	12,468,969	12,021,924	11,562,593	14,724,756
1890	10,526,613	10,346,878	10,263,258	10,080,538	9,993,600	10,682,807

For the last two years the total stocks of petroleum as given in the foregoing table are in excess of those held by the pipe lines. The stocks given in the table include, in addition to those held by the pipe lines, all that are held at wells, but not those of crude held at refineries.

Well records in the Pennsylvania and New York oil fields.—In the tables following are given what are known as the well records; that is, the statistics of the drilling of new wells and the number of producing wells in Pennsylvania and New York. New York is included in this

well report for reasons previously given, namely, that in the pipe line reports it is so difficult to arrive at the exact statistics of production in the oil territory in New York contiguous to Pennsylvania, the oil pools running from one State into the other and the oil being run through pipe lines to a common receptacle, often without any opportunity of measuring the oil from different wells in the different States belonging to the same parties.

In the following table is shown the number of rigs building, preparatory to drilling wells, at the close of each month of 1889, by districts and by totals:

Number of rigs building in the Pennsylvania and New York oil fields at the close of each month during 1889, by districts.

Months.	Bradford-Allegany.	Forest.	Warren	Butler-Clarion-Venango.	Washington.	Allegheny.	Beaver.	Greene.	Total.
January.....	26	3	18	108	37	19	1	7	219
February.....	27	12	1	132	34	18	5	229
March.....	55	2	23	153	43	18	7	311
April.....	52	1	16	134	33	17	7	7	267
May.....	46	2	14	122	50	34	12	279
June.....	55	1	13	126	36	33	7	7	278
July.....	53	6	13	107	34	29	4	246
August.....	81	6	34	144	46	22	18	351
September.....	58	3	34	179	18	27	13	15	347
October.....	102	9	46	191	42	12	15	10	427
November.....	120	11	27	199	64	6	14	12	453
December.....	96	2	27	213	60	5	5	14	422
Total.....	770	58	276	1,808	497	240	62	118	3,829

From this it will be seen that the number of rigs building increased from January to March, was stationary to the close of June, declined a little in July, increased rapidly from August to November, when the number was 453, the largest number during the year.

In the following table is given the number of wells actually drilling at the close of each month in 1889, by districts. This includes only drilling wells, excluding rigs building and wells actually completed during or at the close of the month.

Number of wells drilling at the close of each month in 1889, by districts.

Months.	Bradford-Allegany.	Forest.	Warren.	Butler-Clarion-Venango.	Washington.	Allegheny.	Beaver.	Greene.	Total.
January.....	45	3	19	174	56	22	2	20	341
February.....	50	17	5	151	92	13	22	350
March.....	63	3	44	186	113	25	19	453
April.....	79	3	16	179	143	41	7	19	487
May.....	93	2	43	206	132	79	19	574
June.....	76	5	34	205	170	105	1	16	612
July.....	97	4	36	193	148	113	5	2	598
August.....	113	6	49	194	148	61	27	598
September.....	85	9	43	230	142	59	10	22	600
October.....	166	14	35	273	150	28	13	19	698
November.....	139	9	37	275	124	35	12	28	659
December.....	148	10	45	231	132	19	4	21	610
Total.....	1,154	85	406	2,497	1,550	600	54	234	6,580

About the same remarks may be made on this table as were made in regard to that showing the number of rigs building, except that the

increase was a gradual one from the beginning of the year to the last of June, and was then stationary until the last of September, 1889, increasing over 16 per cent. in October, making the total number of wells drilling at the close of October 698, the largest number of wells drilling at the close of any one month during the period covered by the table given below, or from 1871 to 1890.

Number of drilling wells in the Pennsylvania and New York oil fields at the close of each month for the years 1871-1890, by months and years.

Years.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.	Aug.	Sept.	Oct.	Nov.	Dec.	Aver-ages.
1871	140	173	240	279	356	303	329	330	439	486	477	394	329
1872	363	369	313	302	386	391	359	392	301	311	354	318	347
1873	361	349	227	177	238	395	340	267	197	163	137	60	242
1874	37	55	99	213	235	210	180	128	107	82	57	54	121
1875	40	40	45	64	127	162	118	96	132	170	179	168	112
1876	142	151	230	267	307	340	353	374	511	565	618	493	363
1877	457	463	395	448	512	395	365	417	535	573	565	426	463
1878	334	326	379	409	376	266	188	185	240	282	297	218	292
1879	265	323	406	468	460	384	329	258	270	313	372	440	357
1880	540	595	577	580	460	440	452	515	491	469	475	408	495
1881	383	420	437	446	470	408	379	352	388	445	475	468	423
1882	422	438	408	405	381	226	240	194	177	184	154	138	281
1883	126	151	205	199	216	228	262	315	314	341	301	263	243
1884	270	273	260	284	244	123	123	91	79	100	86	78	168
1885	97	109	139	190	228	209	242	308	382	355	359	277	241
1886	320	337	356	318	358	403	349	290	322	272	285	238	321
1887	201	177	155	155	157	142	135	137	107	104	114	88	139
1888	64	72	65	59	82	106	124	106	166	187	327	273	136
1889	341	350	453	487	574	612	598	598	600	698	659	610	548
1890	597	608	645	603	585	617	643	683	632	644	542	445	604

The effect of the increased demand for petroleum and the decrease in stocks, shown in previous tables, and the reduction of production, owing to the shut-down in 1888, will be seen by comparing the figures of wells drilling in 1888 and 1889, as shown in the above table. It will be remembered that the shut-in began in November, 1887, and lasted until November, 1888. In January, 1888, there were but 64 wells drilling, as compared with 341 in the same month of 1889. The average for 1888 was 136 wells, as compared with 548 for 1889.

In the following table is given a statement of the number of wells completed in each district in the Pennsylvania and New York oil fields during each month of 1889, by months and districts:

Number of wells completed in the Pennsylvania and New York oil fields in 1889, by months and districts.

Months.	Bradford-Allegany.	Forest.	Warren.	Butler-Clarion-Venango.	Washing-ington.	Allegheny.	Beaver.	Greene.	Total.
January	39	4	32	180	16	7		6	284
February	34	1	16	207	10	14		6	288
March	52	2	38	196	49	8		8	353
April	59	1	52	224	51	6	3	5	401
May	82	4	46	207	47	34		11	431
June	83	4	71	275	54	34	4	12	537
July	107	9	62	228	60	69		14	549
August	104	7	65	233	71	23		5	508
September	97	2	70	222	50	5	26	6	478
October	143	7	62	250	59	18	8	12	559
November	121	9	72	253	56	5	15	10	540
December	113	5	50	211	54	8	27	3	471
Total	1,034	55	636	2,685	577	231	83	98	(a) 5,435

a Including 36 wells drilled in Franklin district, data for which by months were not obtainable.

The following table gives the number of drilling wells completed in each month from January, 1872, to the close of 1890.

Number of drilling wells completed in the Pennsylvania and New York oil fields each month for the years 1872-1890, by months and years.

Years.	Jan.	Feb.	Mar.	Apr.	May.	June.	July.	Aug.	Sept.	Oct.	Nov.	Dec.	Total.
1872	37	120	89	121	135	84	128	118	82	100	64	105	1,183
1873	93	94	100	105	102	130	114	120	106	101	100	98	1,263
1874	102	104	110	113	109	101	121	107	104	120	106	120	1,317
1875	190	187	195	186	172	190	200	210	201	220	217	230	2,398
1876	240	231	242	200	202	261	248	270	209	273	272	272	2,920
1877	281	241	291	269	320	403	317	255	322	467	391	382	3,939
1878	274	226	211	409	470	269	203	186	174	229	248	165	3,064
1879	136	132	238	270	402	330	327	283	210	232	227	261	3,048
1880	320	230	367	500	426	310	338	368	356	364	336	302	4,217
1881	222	220	271	316	406	374	336	332	312	322	363	406	3,880
1882	347	340	385	432	469	340	185	253	164	117	150	122	3,304
1883	125	126	142	209	231	228	261	309	321	321	302	272	2,847
1884	229	227	256	298	311	244	268	145	89	59	73	66	2,265
1885	64	62	82	116	213	242	217	283	356	397	384	345	2,761
1886	270	280	291	328	343	365	357	313	253	272	221	185	3,478
1887	158	162	138	160	148	162	159	142	134	100	101	96	1,660
1888	57	52	56	49	56	97	82	96	132	229	307	302	1,515
1889	284	288	353	401	431	537	549	508	478	559	540	471	(a)5,435
1890	553	482	522	556	534	571	555	579	571	567	520	348	6,358

a Including 36 wells drilled in Franklin district, data for which by months were not obtainable.

From this it will be seen that the total number of wells completed in 1890 was 6,358, as compared with 5,435 in 1889. This is the largest number of wells completed in these States in any one year.

In the following table is given the number of dry holes, that is, the number of wells drilled that produced no oil, in New York and Pennsylvania in 1889:

Number of dry holes drilled in the Pennsylvania and New York oil fields in 1889, by months and districts.

Months.	Bradford-Allegheny.	Forest.	Warren	Butler-Clarion-Venango.	Washington.	Allegheny.	Beaver.	Greene.	Total.
January	6	2	5	47	2	2	2	66
February	4	1	56	1	2	2	66
March	7	2	41	1	1	7	59
April	1	6	57	10	2	3	79
May	8	4	48	5	10	8	83
June	8	1	3	60	6	15	3	3	99
July	4	2	2	46	6	31	10	91
August	3	(b) 5	45	7	5	2	68
September	10	3	38	3	2	7	4	67
October	13	1	1	45	6	6	3	3	78
November	7	3	6	36	11	2	3	68
December	10	1	27	8	5	51
Total	(a) 81	9	40	546	66	73	13	47	875

a Nine gas wells.

b One gas well.

The total production of the new wells completed during 1889 is shown in the following table:

Initial daily production of new wells in the Pennsylvania and New York oil fields in 1889, by months and districts.

[Barrels.]

Months.	Bradford-Allegany.	Forest.	Warren.	Butler-Clarion-Venango.	Washington.	Allegheny.	Beaver.	Greene.	Total.
January.....	219	11	133	1,254	730	200	230	2,777
February.....	296	10	79	1,500	473	544	140	3,012
March.....	291	12	187	1,666	4,043	275	25	6,504
April.....	296	8	169	1,686	1,100	183	30	245	3,817
May.....	454	24	340	1,561	2,594	818	140	5,931
June.....	529	85	344	2,055	3,152	588	15	425	7,193
July.....	643	65	232	1,590	2,315	1,387	100	6,832
August.....	757	68	306	2,501	3,246	469	365	7,712
September.....	652	15	217	2,427	2,433	270	660	10	6,684
October.....	905	84	495	1,981	1,883	292	235	243	6,118
November.....	854	60	342	2,710	1,761	800	1,080	500	8,107
December.....	867	36	366	1,882	2,062	397	552	322	6,484
Total.....	6,863	478	3,210	22,813	26,297	6,223	2,572	2,745	a 71,323

a Including 122 barrels in Franklin district, data for which by months were not obtainable.

The average daily production of the new wells completed in the Pennsylvania and New York oil fields from 1882 to 1889 is as follows:

Average daily product of the new wells in the Pennsylvania and New York oil fields from 1882 to 1889, by months and years.

[Barrels.]

Months.	1882.	1883.	1884.	1885.	1886.	1887.	1888.	1889.
January.....	19.50	22.40	13.70	40.00	13.50	25.50	15.43	13.08
February.....	19.40	14.90	15.00	41.30	13.40	44.75	12.48	10.50
March.....	22.25	22.50	17.00	23.30	22.90	29.75	66.00	19.70
April.....	22.00	21.00	12.00	40.00	32.00	43.50	9.40	15.17
May.....	21.30	17.50	18.00	23.00	38.60	22.00	68.71	12.00
June.....	36.80	15.00	17.50	10.60	25.00	38.51	40.55	13.50
July.....	108.80	15.00	59.30	10.30	31.10	18.14	14.38	13.20
August.....	84.20	13.80	22.60	10.60	51.90	49.30	19.00	15.50
September.....	25.75	14.40	41.70	13.20	62.40	57.70	19.00	14.14
October.....	15.90	14.20	165.50	14.00	28.00	25.98	13.72	11.50
November.....	12.90	13.80	87.40	10.90	28.00	19.69	12.80	15.20
December.....	20.40	11.80	92.60	10.90	23.00	11.40	13.30	14.25

It will be seen from this table that the average production of each well for 1889 is less than for any year covered by the tables.

In the following table is given the number of producing, flowing, and pumping wells in each district of Pennsylvania and New York at the close of 1888 and 1889:

Total number of producing, flowing, and pumping wells in the Pennsylvania and New York oil fields at the close of 1888 and 1889.

Districts.	Producing wells.		Flowing wells.		Pumping wells.	
	Dec. 31, 1888.	Dec. 31, 1889.	Dec. 31, 1888.	Dec. 31, 1889.	Dec. 31, 1888.	Dec. 31, 1889.
Bradford-Allegany	14,371	16,293	179	182	14,192	16,111
Forest	240	299	84	67	156	232
Warren	2,880	4,178	790	1,586	2,090	2,592
Butler-Clarion-Venango- Armstrong, etc.	6,138	8,336	28	308	6,110	8,028
Allegheny	176	298	160	36	16	262
Beaver and Smith's Ferry	199	270	3	14	196	256
Washington	618	1,222	108	186	510	1,046
Greene	193	231	6	19	187	212
Franklin	605	631	605	631
Total	25,420	31,768	1,358	2,398	24,062	29,370

From the above table it appears that the number of producing wells in Pennsylvania increased from 25,420 at the close of 1888 to 31,768 at the close of 1889, a total increase of 6,348, though the number of producing wells completed in Pennsylvania and New York in 1889 was but 4,560, leaving an excess of 1,788 wells to be accounted for in addition to the wells that were abandoned in the State during the year. This difference is no doubt due to the fact that a large number of wells which were shut in at the close of 1888, owing to the restriction of production before referred to, were not counted as producing wells. So also a number of wells that were not producing and practically abandoned at the close of 1888 were drilled deeper or cleaned out and became producers in 1889.

As the production of Pennsylvania for the month of December, 1889, was 2,055,247 barrels, it appears that the average production per well for that month was 64.7 barrels, an average of a little over 2 barrels a day. The average for the different districts varies greatly, but can be readily ascertained by dividing the production by the number of wells given above.

The amount of money expended for materials used in pumping, operating, and caring for wells in 1889, including fuel, materials for repairs, replacing old machinery, and materials, was \$8,633,391. This is divided among the districts as shown in the following statement:

Value of materials used in pumping, caring for, and operating wells in the Pennsylvania and New York oil fields in 1889, by districts.

Districts.	Amounts.
Bradford-Allegany	\$2,603,248
Forest	29,900
Warren	1,022,966
Butler-Clarion-Venango-Armstrong, etc.	1,787,296
Allegheny	215,086
Beaver and Smith's Ferry	214,026
Washington	2,454,446
Greene	274,460
Franklin	31,953
Total	8,633,391

Well record.

	Number.
Total producing wells December 31, 1888	25,420
Total producing wells December 31, 1889	31,768
Total flowing wells December 31, 1888	1,358
Total flowing wells December 31, 1889	2,398
Total pumping wells December 31, 1888	24,062
Total pumping wells December 31, 1889	29,370
Wells completed in 1889	5,435
Dry holes in 1889	875
Producing wells completed in 1889	4,560
Initial daily production of new wells (barrels)	71,323
Rigs building December 31, 1888	179
Rigs building December 31, 1889	422
Wells drilling December 31, 1888	273
Wells drilling December 31, 1889	610

Capital employed in producing crude petroleum in Pennsylvania and New York oil fields in 1889.—The total capital employed in producing crude petroleum in Pennsylvania and New York districts at the close of 1889, according to the table given below, was \$89,562,008. Of this, \$27,184,857 represented the value of land and \$62,377,151 the value of all other property.

The total capital invested in Pennsylvania, the value of lands, and the total amount invested in all other property, by districts, are as follows:

Total capital invested in the production of crude petroleum in Pennsylvania in 1889, by districts.

Districts.	Total capital.	Total value of land.	Total value of all other property.
Bradford-Allegany	\$32,288,195	\$8,562,827	\$23,725,368
Forest	1,162,174	648,338	513,836
Warren	10,680,618	3,971,524	6,709,094
Butler-Clarion-Venango-Armstrong, etc.	26,020,574	8,322,204	17,698,370
Allegheny	2,070,926	739,876	1,331,050
Beaver and Smith's Ferry	2,203,219	998,055	1,205,164
Washington	12,238,107	2,703,816	9,534,291
Greene	2,171,763	978,427	1,193,336
Franklin	726,432	259,790	466,642
Total	89,562,008	27,184,857	62,377,151

The total amount of oil land owned and leased in the Pennsylvania and New York oil regions was 873,399 acres. Of this, 288,510 acres were owned and 584,889 leased. The value given to this land in the schedules was \$27,184,857, an average value, ignoring fractions, of \$31 an acre. The largest amount of land was held in the Butler-Clarion-Venango-Armstrong district, the smallest amount in the Franklin district. The highest average value per acre was in the Franklin district, being \$53 an acre. The lowest value was in the Forest district, the average being \$21 an acre. It is evident to any one at all acquainted with oil lands that these averages are very much below the actual value of this territory as oil land. This class of land is worth to-day all the

way from \$100 to \$400 an acre. Recent purchases in the Bradford district, one of the oldest, have been as high, where the fee has been bought, as \$150 to \$250 an acre, while it is almost impossible to place a value upon oil lands in the Washington district or in several of the newer ones of the southwestern fields. As is stated elsewhere, land was bought in 1889 at a valuation of \$1,500 for each barrel of daily production.

In leasing oil lands it is usual to pay a certain price for the lease, varying from \$1 to \$20 per acre, together with a certain proportion of the oil produced as royalty. This royalty varies from one-sixteenth to one-fourth of the oil produced, the almost universal custom being one-eighth. In estimating the worth of the oil land the value seems to have been put by the producer, so far as it relates to the leased land, at the amount paid per acre for the lease, while probably a fair price, though a low one, has been placed upon the land owned. It is evident, however, that this valuation is not a fair one, as certainly it should be estimated with some reference to the price paid for land when purchased in fee, having in consideration at the same time the amount of oil produced. Under these considerations it is believed that \$100 an acre would be a very conservative estimate as the average value per acre of the owned and leased oil lands in Pennsylvania. At this figure the value of these lands would be \$87,339,900, instead of \$27,184,857.

The number of acres of land held as oil territory in the Pennsylvania and New York oil districts, together with the total value of the same and the value per acre, are as follows:

Statistics of land held as oil territory in the Pennsylvania and New York oil districts in 1889.

Districts.	Total acreage.	Owued.	Leased.	Total value of land.	Value per acre.
		<i>Acres.</i>	<i>Acres.</i>		
Bradford-Alleghany	182,861	90,515	92,346	\$8,562,827	\$47
Forest	30,895	12,194	18,701	648,338	21
Warren	88,486	33,744	54,742	3,971,524	45
Butler-Clarion-Venango-Armstrong, etc	351,278	142,634	208,644	8,322,204	24
Allegheny	31,971	2,407	29,564	739,876	23
Beaver and Smith's Ferry	28,812	981	27,831	998,055	35
Washington	112,137	2,544	109,593	2,703,816	24
Greene	42,083	275	41,808	978,427	23
Franklin	4,876	3,216	1,660	259,790	53
Total	873,399	288,510	584,889	27,184,857	(a) 31

a. Average.

The total capital invested in the production of crude petroleum in Pennsylvania and New York, outside of that invested in lands, amounted in 1889 to \$62,377,151. Of this, \$55,936,194 was invested in wells, including rigs, wells proper, engines, boilers, casings, etc.; \$1,327,614 in tanks; \$7,255 in tank cars owned by the producers, but not including those owned by transportation companies; \$1,268,928 in pipe lines at

wells, but not including the lines owned by the pipe-line transportation companies; \$446,305 in oil in stock at wells, and \$3,390,855 in other property. One or two of these amounts demand some explanation. It should be distinctly noted that the value of tank cars and pipe lines given above does not include in any case the value of these properties owned by the various pipe-line and other transportation companies, but only the properties of the several kinds mentioned that were actually a part of the well outfit.

The total value of the wells, that is, rigs, wells proper, engines, boilers, and other apparatus, not including tanks, tank cars, or pipe lines, was \$55,936,194. On the basis of 31,768 producing wells, this would give an average value of \$1,761 per well. The average value of the wells in each district, as shown in the table of capital invested in them, is given below:

Average value per well in each of the districts in the Pennsylvania and New York oil fields in 1889.

Districts.	Amounts.	Districts.	Amounts.
Bradford-Allegany	\$1,237	Allegheny	\$4,297
Forest	1,360	Beaver and Smith's Ferry.....	4,202
Warren	1,335	Washington	7,428
Bulter-Clarion-Venango-Armstrong, etc	1,998	Greene	4,971
		Franklin	690

In the older districts it is customary to estimate the value of a well at the price at which the material at the well, including casings, rigs, engines, boilers, etc., could be sold. In the newer districts, especially in the southwestern country, a much higher estimate than this has been made, though even there it is believed that in arriving at the value sufficient account has not been taken of the income that the wells bring to their owners.

The number of producing wells at the beginning of 1889 was 25,420; at the close of 1889 it was 31,768. Assuming that the average number of producing wells throughout the year was in round numbers 28,000, they produced an average of 767 barrels, worth on the average in the neighborhood of \$1.10 a barrel, or \$844 per well. This number of wells (28,000), producing this value of oil in one year, should certainly be worth on an average more than \$1,761, when the old materials from these wells will be worth from \$1,250 to \$1,500 in the upper region, and in the lower fields from \$2,000 to \$3,000. Some of the wells in the Washington district will probably produce from 50,000 to 75,000 barrels of oil before they are abandoned.

The capital invested in the production of crude petroleum in Pennsylvania and New York, outside of that invested in land, was as follows in 1889, by districts:

Capital invested in the production of crude petroleum in Pennsylvania and New York in 1889.

Districts.	Rigs, wells, engines, etc.	Tanks.	Tank cars.	Pipe lines.	Oil in stock December 31, 1889.	Other property.	Total.
Bradford-Allegheny Forest.....	\$20, 149, 046	\$534, 594	\$510	\$681, 549	\$181, 376	\$2, 178, 293	\$23, 725, 368
Warren.....	406, 559	15, 911	495	42, 755	7, 668	40, 448	513, 836
Butler-Clarion-Venango-Armstrong, etc.....	5, 575, 578	160, 376	215, 212	60, 820	697, 108	6, 709, 094
Allegheny.....	16, 654, 912	421, 192	5, 250	233, 300	70, 676	313, 040	17, 698, 370
Beaver and Smith's Ferry.....	1, 280, 455	10, 900	4, 771	6, 857	28, 067	1, 331, 050
Washington.....	1, 134, 572	21, 046	2, 632	18, 904	28, 010	1, 205, 164
Greene.....	9, 151, 407	139, 590	81, 819	99, 054	62, 421	9, 534, 291
Franklin.....	1, 148, 224	13, 750	2, 762	950	27, 650	1, 193, 336
.....	435, 441	10, 255	1, 000	4, 128	15, 818	466, 642
Total.....	55, 936, 194	1, 327, 614	7, 255	1, 268, 928	446, 305	3, 390, 855	62, 377, 151

The totals of capital, acres of oil land held and its value, and the value of other property for the States of Pennsylvania and New York in 1889, were as follows:

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$89, 562, 008
Number of acres of oil land:	
Owned.....	288, 510
Leased.....	584, 889
Total acreage.....	873, 399
Present value of land, both owned and leased.....	27, 184, 857
Average value per acre, \$31.	
Value of rigs, wells, engines, boilers, etc.....	\$55, 936, 194
Value of tanks.....	1, 327, 614
Value of tank cars.....	7, 255
Value of pipe lines at wells owned by parties making report.....	1, 268, 928
Value of oil in stock at wells December 31, 1889.....	446, 305
Value of other property and improvements.....	3, 390, 855
Total.....	62, 377, 151

LABOR AND WAGES.

Census statistics of labor and wages.—The total number of persons reported as employed in the production of crude petroleum in Pennsylvania in 1889 was 19,832, to whom was paid \$7,423,781 in wages. The number reported as foremen or overseers was 1,230; as mechanics, 10,049; as laborers, 8,256; as boys under 16 years of age, 156; as employed in offices, males 134, females 7.

While these statistics may correctly represent what they claim to give, namely, the persons actually employed in producing crude petroleum whose wages were paid by the different individuals, firms, or companies producing petroleum, they are misleading, and do not by any

means represent the number of persons actually employed in building rigs, drilling wells, and building tankage and pipe lines in the oil regions. A great deal of this work is done by contract, building rigs at so much a rig or so much a foot, in drilling wells at so much a foot, or pumping wells at so much a day or so much a barrel. While the amounts so paid appear in a statement of payments for operating, pumping, and drilling wells, neither the number of men employed nor the amount so paid would appear under the head of wages paid for labor; nor is there any means of arriving at the total number of men so employed or their wages.

The classification of wages, though it is a general one in certain departments of the census, is unfortunate in the petroleum industry, as it is exceedingly difficult to classify the workmen engaged in drilling and operating wells under these classes. A pumper or engineer is neither a foreman, an overseer, a mechanic, nor a laborer, as the term "mechanic" is understood, meaning, as it does in the oil regions, usually a blacksmith, carpenter, or man engaged in a similar occupation. In some instances a pumper, who is the only workman at the well, has been classified as a foreman or overseer.

The division of employés in the table of classified wages given with each district is better than the list following, but as in many instances no return was made in the table of classified wages, the totals of the different employés given in these lists in no case equals the total number of employés given.

The total number of persons employed and the wages paid in the production of crude petroleum in Pennsylvania in 1889, so far as the same have been ascertained, are given in the following tables, by districts:

Classes of labor and wages paid in Pennsylvania and New York oil fields in 1889, by districts.

Districts.	Foremen or overseers.		Mechanics.		Laborers.	
	Num-ber.	Wages.	Num-ber.	Wages.	Num-ber.	Wages.
Bradford-Allegany.....	432	\$244,392	3,037	\$913,488	2,709	\$873,036
Forest.....	13	9,039	77	33,785	99	42,850
Warren.....	120	67,276	1,256	519,476	866	260,360
Butler-Clarion-Venango-Armstrong, etc.....	492	298,692	4,164	1,214,336	3,636	1,099,566
Allegheny.....	17	12,613	155	134,386	142	61,131
Beaver and Smith's Ferry.....	11	7,550	196	175,076	147	58,368
Washington.....	117	85,356	894	611,697	477	254,671
Greene.....	21	15,071	177	127,335	92	55,732
Franklin.....	7	4,685	93	12,837	88	42,739
Total.....	1,230	744,674	10,049	3,742,416	8,256	2,748,453

Classes of labor and wages paid in Pennsylvania and New York oil fields in 1889, by districts—Continued.

Districts.	Boys under 16 years.		Office.				Total number of employés.	Total wages paid.
			Males.		Females.			
	Number.	Wages.	Number.	Wages.	Number.	Wages.		
Bradford-Allegany.....	31	\$6,587	45	\$56,479	1	\$360	6,255	\$2,094,342
Forest.....			2	1,125			191	86,799
Warren.....	20	6,600	24	11,032			2,286	864,744
Butler-Clarion-Venango-Armstrong, etc.....	66	16,316	22	9,552	6	944	8,386	2,639,406
Allegheny.....			4	2,125			318	210,255
Beaver and Smith's Ferry.....							354	240,994
Washington.....	39	23,690	30	44,004			1,557	1,019,418
Greene.....			6	8,800			296	206,938
Franklin.....			1	624			189	60,885
Total.....	156	53,193	134	133,741	7	1,304	19,832	7,423,781

Employments of labor in Pennsylvania and New York oil fields in 1889, by districts.

Districts.	Building rigs.	Drilling wells.	Operating and caring for wells.	Torpedoing or cleaning wells.	Building or repairing tanks.	Building or repairing pipe lines.	Office.	Total wages paid.
Bradford-Allegany.....	\$120,868	\$548,558	\$1,296,607	\$44,153	\$9,286	\$18,031	\$56,839	\$2,094,342
Forest.....	5,015	31,849	45,547	110	1,562	1,591	1,125	86,799
Warren.....	81,048	393,668	333,848	23,248	11,830	10,070	11,032	864,744
Butler-Clarion-Venango-Armstrong, etc.....	161,908	1,097,416	1,326,976	21,230	18,406	2,974	10,496	2,639,406
Allegheny.....	8,919	117,977	79,565		1,669		2,125	210,255
Beaver and Smith's Ferry.....	27,696	126,409	82,989		3,900			240,994
Washington.....	66,780	373,689	464,846	12,882	52,950	4,267	44,004	1,019,418
Greene.....	3,277	75,747	101,191	3,572	10,590	3,761	8,800	206,938
Franklin.....	2,703	15,482	41,570	431	75		624	60,885
Total.....	478,214	2,780,795	3,773,139	105,626	110,268	40,694	135,045	7,423,781

The division of the \$7,423,781 into amounts paid for various purposes shows that \$478,214 was paid for labor engaged in building rigs, \$2,780,795 in drilling wells, \$3,773,139 in operating and caring for wells, \$105,626 in torpedoing and cleaning wells, \$110,268 in building and repairing tankage at wells, \$40,694 in building and repairing pipe lines at wells, and \$135,045 in the offices. The only figures that require much comment are those relating to the item of labor paid for drilling wells, which amounted to \$2,780,795. This includes not only the amount paid for drilling new wells, but in many instances the cost of drilling and cleaning out old wells. The number of new wells drilled and completed in Pennsylvania and New York in 1889 was 5,435. Where this was done by contract the price ran from 40 cents to \$1.50 per foot, the cost of drilling by contract including labor, fuel, wear and tear of tools, and use of machinery and appliances. Possibly 60 cents a foot would represent the cost of drilling a well, of which not much less than 40 cents would be the cost of labor. Assuming that the average depth of

wells drilled in Pennsylvania and New York in 1889 was 1,200 feet, this would make the cost of labor per well in round numbers \$500, making the total cost of labor in drilling the 5,435 wells drilled in 1889 \$2,717,500. A portion of this sum should be added to the \$2,780,795 given as the labor cost paid for drilling the same. Relative to drilling by contract, very full information on this subject has been received from Mr. J. L. Wilson, secretary of the Well Drillers' Association, of Titusville, Pennsylvania. Estimating the cost of wells in what is known as the Upper district, Mr. Wilson gives the following figures: Cost of rig, from \$275 to \$325; lumber in rig, from 8,000 to 10,000 feet, worth from \$8 to \$11 per thousand; iron, \$70 to \$80; timber, besides the lumber mentioned above, \$30 to \$50; carpenters' work and grading, \$75 to \$90; carpenters' wages, from \$2 to \$3.50 per day of 10 hours.

Relative to the cost of machinery, Mr. Wilson states that it is difficult to give exact information, as it is not known just how long machinery will last, its work being divided between drilling and pumping. Drilling machinery rents for drilling purposes, however, at from 10 to 15 cents per foot of drilling done, or from \$50 to \$75 for 30 days, the machinery including boiler, engine, pipes and fittings, belt, and bull rope. Boilers used in the oil region cost from \$275 to \$425, engines from \$150 to \$180, belts from \$30 to \$50, bull ropes from \$15 to \$20, and pipes and fittings from \$5 to \$10.

Drilling costs in the upper region from 40 to 50 cents per foot. This includes cost of labor, fuel, wear and tear of materials, and rent of tools, including ropes, the first cost of tools and rope being from \$800 to \$1,000. The depth of the new wells of the upper regions is from 600 to 1,000 feet, the time consumed in drilling being from 8 to 15 days of 24 hours each, drilling being continued night and day. The cost of labor is as follows: 2 drillers, at from \$3 to \$4.50 per day of 12 hours; 2 tool dressers, at from \$2.50 to \$3.50 per day; fuel, 4 to 5 cents per foot of well drilled, and casing from 30 to 45 cents per foot. The amount used is from 150 to 400 feet. Tubing used, according to depth of well, at from 13 to 17 cents per foot; fittings per well, \$12 to \$25; sucker rods, 5 to 7 cents per foot. The amount of sucker rods used is the same as tubing, varying with the depth of the well. The cost of drilling given above includes putting into the well the casing, tubing, and rods, but not the furnishing of them.

When the well is to be torpedoed, from 20 to 180 quarts of nitro-glycerin are used, worth from 90 cents to \$1 per quart.

The following is a condensed statement of the statistics of labor and wages for the entire States of Pennsylvania and New York in the production of crude petroleum in 1889:

Statistics of labor and wages in the Pennsylvania and New York oil regions in 1889.

All labor, not including office force:

Number of foremen or overseers.....	1,230
Total wages paid all workmen of this class in 1889.....	\$744,674

Statistics of labor and wages, etc.—Continued.

All labor, not including office force—Continued.

Number of mechanics.....	10,049	
Total wages paid all workmen of this class in 1889.....		\$3,742,416
Number of laborers.....	8,256	
Total wages paid all workmen of this class in 1889.....		2,748,453
Boys under 16 years.....	156	
Total wages paid all boys under 16 years.....		53,193

Office force:

Total number of males.....	131	
Total number of females.....	7	
Total wages paid males.....		133,741
Total wages paid females.....		1,304

Total number of persons employed and wages paid in 1889.....	19,832	7,423,781
--	--------	-----------

Wages paid for labor:

In building rigs.....	478,214
In drilling wells.....	2,780,795
In operating and caring for wells.....	3,773,139
In torpedoing wells.....	105,626
In building or repairing tankage.....	110,268
In building and repairing pipe lines.....	40,694
In office.....	135,045

Total.....	7,423,781
------------	-----------

OHIO.

In the three well-known districts, Lima, Macksburg, and Mecca, which make up the oil-producing territory of Ohio, the product in 1890 was 16,124,656 barrels, compared with 12,471,466 barrels in 1889. The statistics by districts and the value are shown in the following table:

Total production and value, and value per barrel, of petroleum produced in Ohio in 1889 and 1890.

Districts.	1889.			1890.		
	Total production.	Total value.	Value per barrel.	Total production.	Total value.	Value per barrel.
	<i>Barrels.</i>			<i>Barrels.</i>		
Lima.....	12,153,189	\$1,822,978	\$0.15	15,014,882	\$4,504,465	\$0.30
Macksburg.....	317,037	340,683	1.07½	1,108,334	1,127,730	1.01¼
Mecca-Belden.....	1,240	10,334	8.33½	1,440	12,000	8.33½
Total.....	12,471,466	2,173,995	0.17½	16,124,656	5,644,195	0.35

In the classification of this oil all of that produced in Lima was classed as fuel oil in 1889, that of the Macksburg district as illuminating, and all of that produced in the Mecca-Belden district as lubricating oil. This classification is correct with the exception of the Lima district. While it is true that most of the Lima oil that was consumed in 1889 was used

as fuel, strenuous efforts were being made to find a method for refining it, so that considerable of the oil that was produced in 1889 and went into pipe-line stocks has since been used for illuminating purposes, the oil producing some 22 per cent. of illuminants, the balance being sold for fuel purposes. All of the oil produced in the Mecca-Belden district was used for lubricating purposes, and all of that produced in the Macksburg district was what may be termed refinery oil, or for manufacture into illuminating oil.

In 1890 a large proportion of the Lima oil was refined and supplied domestic consumption, while the exports of refined oils were supplied by the Pennsylvania and New York fields.

Bringing the production in previous years to the end of 1890, it is seen that the total product for the State aggregates 46,637,198 barrels, allowing, as has already been done, 200,000 barrels as the aggregate product previous to 1876.

Production of petroleum in Ohio.

	Barrels.		Barrels.
Previous to 1876.....	200,000	1884.....	90,081
1876.....	31,763	1885.....	650,000
1877.....	29,888	1886.....	1,782,970
1878.....	38,179	1887.....	5,018,015
1879.....	29,112	1888.....	10,010,868
1880.....	38,940	1889.....	12,471,466
1881.....	33,867	1890.....	16,124,656
1882.....	39,761		
1883.....	47,632	Total.....	46,637,198

The enormous increase in production shown in the above table began in 1885, which marks the commencement of developments in the Lima field. In 1886 this district yielded 1,064,025 barrels; in 1887 it increased four fold to 4,650,375 barrels; in 1888, to 9,682,683; in 1889, to 12,153,189; and in 1890, to 16,124,656, an amount greater than Pennsylvania and New York together had produced in any year prior to 1878.

Stocks.—The total stocks of oil held in Ohio December 31, 1888, were 10,243,066 barrels, of which 10,161,842 barrels were held by the pipe lines and 81,224 were held in stock at the wells. At the close of 1889 these stocks had increased to 14,886,122 barrels, of which 14,415,997 barrels were held by the pipe lines and 470,125 at the wells. In 1890 these stocks decreased to 10,000,000 at the close of the year; due to the increased refining at the wells, there was a slight increase to 500,000 barrels. The distribution of these stocks by districts is shown in the following table:

Stocks of petroleum in Ohio December 31, 1888, 1889, and 1890.

[Barrels.]

Periods.	Lima.	Macksburg.	Mecca-Belden.	Total.
December 31, 1888:				
Pipe-line stocks	9,810,714	351,128	10,161,842
At wells.....	78,118	2,726	380	81,224
Total at close of 1888.....	9,888,832	353,854	380	10,243,066
December 31, 1889:				
Pipe-line stocks	14,105,149	310,848	14,415,997
At wells.....	466,308	3,337	480	470,125
Total at close of 1889.....	14,571,457	314,185	480	14,886,122
December 31, 1890:				
Pipe-line and refining stocks.....	9,400,000	100,000	9,500,000
At wells.....	500,000	500,000
Total at close of 1890.....	9,900,000	100,000	10,000,000

From the preceding table it will appear that not only was all the oil produced in the Macksburg district in 1889 disposed of, but stocks were drawn on to the extent of nearly 40,000 barrels. The stocks in this district at the close of 1889 were actually 39,669 barrels less than at the close of 1888. On the other hand, stocks in the Lima district had increased 4,682,625 barrels, which would indicate a consumption of 7,470,564 barrels of Lima oil in 1889. It should be remembered, however, that reductions in stocks in the pipe lines do not always indicate actual consumption, as oil may be carried in tanks outside of those owned by the pipe lines.

The following statistics in regard to the number of wells and the capital employed in the Ohio oil industry were collected with great care and detail for the Census Office and are taken from the final report:

Wells.—"The total number of wells in all districts in Ohio at the close of 1889 was 2,640, of which 2,242 were in the Lima district, 390 in the Macksburg district, and 8 in the Mecca-Belden district. At the close of 1888 there were 1,788 wells in the State the increase in 1889 being 852. Of this increase, 777 were in the Lima field, 73 in the Macksburg, and 2 in the Mecca-Belden.

"During the year 1889, 759 producing wells are reported as having been completed. Of these, 667 were completed in the Lima district, 86 in the Macksburg district, and 6 in the Mecca-Belden district. The initial daily production of all of these wells was 55,930 barrels, an average of $73\frac{7}{10}$ barrels. The average initial production per well in the Lima district was $82\frac{1}{2}$ barrels per day; the Macksburg district, $13\frac{1}{10}$; the Mecca-Belden, one half barrel.

“The well statistics for the whole State of Ohio for 1889 are as follows:

Well record.

	Number.		Number.
Total producing wells December 31, 1888	1,788	Producing wells completed in 1889	759
Total producing wells December 31, 1889	2,640	Initial daily production of new wells	
Total flowing wells December 31, 1888	255	(barrels)	55,930
Total flowing wells December 31, 1889	785	Rigs building December 31, 1888	26
Total pumping wells December 31, 1888	1,533	Rigs building December 31, 1889	59
Total pumping wells December 31, 1889	1,855	Wells drilling December 31, 1888	738
Wells completed in 1889	825	Wells drilling December 31, 1889	45
Dry holes in 1889	66		

Value of materials used in pumping, caring for, and operating wells in 1889, \$650,503.

Capital.—“The total capital invested in the oil business in Ohio in 1889, according to the reports received, was \$17,771,152. Of this, \$9,963,302 represents the value of land and \$7,807,850 the value of wells, tanks, pipe lines, oil in stock at wells, and other property and improvements.

“Of the total capital, as above stated, \$16,802,637 was invested in the Lima district, \$944,721 in the Macksburg district, and \$23,794 in the Mecca-Belden district.

“Of the \$7,807,850 invested in wells, etc., \$6,627,835 was invested in wells proper, including the rigs, engines, boilers, etc.; \$373,052 in tanks, and \$123,762 in pipe lines at wells, not including those belonging to pipe-line companies; \$76,063 represents the stock of oil at the wells on December 31, 1889, while \$607,138 represents the value of other property, including cash and improvements.

“The total acreage of oil lands, both owned and leased, is 440,401. Of this, 23,513 acres are reported as owned and 416,888 acres as leased. The total value of this land, both owned and leased, is given as \$9,963,302. This is but \$23 an acre, ignoring fractions, for all the oil lands throughout the State. The value of the 371,619 acres of oil lands in the Lima district is given as \$9,693,466, an average of \$26 an acre; that of the 68,171 acres of land in the Macksburg district is stated to be \$255,841, an average of only \$4 an acre; while the value of the 611 acres in the Mecca-Belden district is \$13,995, or an average of \$23 an acre. It is evident, as has already been stated in connection with the general discussion of the value of oil lands, that this is an underestimate, the probability being that to the actual value of the land owned is added the actual amount of money paid for the leased land, and these two sums are taken as the total value of all the land. Even with Lima oil at the prices ruling in 1889, \$100 an acre would be a very low estimate of the average value of the oil lands in the State of Ohio, and this amount would place these lands at \$44,040,100, instead of a little less than \$10,000,000.

“The total value of the wells, including rigs, engines, boilers, casings, etc., but excluding the tanks and pipe lines, as given below, is \$6,627,835. Of this amount, \$5,990,285 represent the value of the wells in the Lima district, \$630,950 the value of those in the Macksburg district, and \$6,600 the value of those in the Mecca-Belden district. This would make the value of each well in the Lima district \$2,672, in the Macks-

burg district \$1,618, and in the Mecca-Belden district \$825. As has already been stated, it is the usual custom in oil districts to estimate the value of a well at about what the casing, etc., would be worth to remove to another well, and not by its producing capacity.

The consolidated statistics of the capital in all of the districts of Ohio are as follows:

Statistics of the capital employed in the Ohio fields in 1889.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$17, 771, 152
Number of acres of oil land:	
Owned	23, 513
Leased	416, 888
Total acreage	440, 401
Present value of land both owned and leased.....	9, 963, 302
Average value per acre, \$23.	
Value of rigs, wells, engines, boilers, etc.....	6, 627, 835
Value of tanks	373, 052
Value of pipe lines at wells owned by parties making report	123, 762
Value of oil in stock at wells December 31, 1889	76, 063
Value of other property and improvements.....	607, 138
Total.....	7, 807, 850

Labor and wages.—In a general way it may be said that a large proportion of the work of building rigs, drilling and torpedoing wells, and erecting tankage is done by contract and the items for the labor in connection with these operations do not appear in this report; so also the general classification of foremen or overseers, mechanics, laborers, and boys is confusing and misleading, different proprietors classifying the same workmen under different heads, as, for instance, a pumper who has charge of the works at the well will be in some cases classed as a foreman, in others as a mechanic, and in others as a laborer.

The total number of employés at the oil wells in Ohio at the close of 1889 was 2,123. There was paid for labor by the proprietors of the wells, not including, as stated above, that paid drillers working by contract, \$836,377. Of the employés, 1,798 were in the Lima district, 318 in the Macksburg, and 7 in the Mecca-Belden district. The amount of wages paid in the Lima district was \$722,975, in the Macksburg \$111,402, and in the Mecca-Belden district \$2,000. There were 94 men classed as overseers, to whom \$71,613 was paid in wages; 724 classed as mechanics, to whom \$235,607 was paid, and 1,282 classed as laborers, to whom \$509,421 was paid. No boys under 16 years are reported as having been employed at wells, and the total office force reported was 23, to whom \$19,736 was paid in wages. This last item evidently includes only employés in offices, even if it includes all who are regarded as office force, and does not include owners, proprietors, or officers of companies.

The wages paid for labor in building rigs in Ohio, with the exceptions above noted, was \$30,254; for drilling wells, \$174,299; in operating and caring for wells, \$595,518; in torpedoing wells, \$3,728; in building or repairing tankage, \$9,440; in building and repairing pipe lines, \$3,402, and in the office, \$19,736.

The statistics of labor and wages in the Ohio oil fields in 1889 are as follows:

Labor and wages.

All labor, not including office force:

Number of foremen or overseers.....	94	
Total wages paid all workmen of this class in 1889.....		\$71,613
Number of mechanics.....	724	
Total wages paid all workmen of this class in 1889.....		235,607
Number of laborers.....	1,282	
Total wages paid all workmen of this class in 1889.....		509,421

Office force:

Total number (males).....	23	
Total wages paid (males).....		19,736

Total number of persons employed and wages paid in 1889..	2,123	836,377
---	-------	---------

Wages paid for labor:

In building rigs.....	30,254
In drilling wells.....	174,299
In operating and caring for wells.....	595,518
In torpedoing wells.....	3,728
In building or repairing tankage.....	9,440
In building and repairing pipe lines.....	3,402
In office.....	19,736
Total.....	836,377

Lima district.—Probably the most remarkable oil district ever developed in this country is that known as the Lima or Northwestern Ohio district. Its discovery opened up a new horizon (the Trenton limestone) as an oil-producer. Its development has been rapid since it first began to assume prominence in 1885, and its production has increased enormously. For a while it was believed that the character of the oil was such that no market could be found for it for illuminating purposes, but this theory has been exploded, and it is safe to predict that in the near future a large portion of the demand for illuminating oil, at least in the United States, will be supplied by the distillate from the limestone oil.

The Lima oil field, according to Professor Orton, who has written most fully upon it, constitutes a flat-lying tract of Trenton limestone. It is as near a level terrace as an area of this sort ever becomes. The very gentle slope that exists in it is mainly to the northward, not amounting to more than 4 feet to the mile, and at times reduced even to 1 or 2 feet. The rises in the floor, or, in other words, the knobs and bosses of this great limestone sheet, are always favorable to production, other things being equal. In this field are included all of the oil-producing districts in northwestern Ohio. They are generally divided into the Lima, Findlay, New Baltimore, Saint Mary's, Gibsonburg, Upper

Sandusky, and Spencerville fields. Oil was produced in this district in 1889 in Auglaize, Hancock, Mercer, Sandusky, and Wood counties.

The oil is found at Lima at a depth of 1,300 feet. It requires about sixty days to drill a well, the cost being some \$2,500. The first wells drilled in this territory were none of them very large producers. Early in 1886 no well exceeded, if, indeed, any reached, 150 barrels a day. Toward the close of 1886 and the first of 1887, however, some very large wells were brought in, one being reported at 1,500 barrels a day, another reaching the 1,000-barrel limit, and others maintaining a rate of several hundred barrels per day week after week. In 1889 the average production of the new wells in this district was 80½ barrels, some wells yielding as high as 1,500 barrels and others dropping as low as 30 barrels, from 50 to 75 barrels being the most common figures of production.

The Lima oil and, indeed, all limestone oils differ greatly in character from the oils of the sandstones. They are dark or black and rather heavy, and contain sulphur compounds. In these respects the oils of northwestern Ohio resemble those of Canada and Tennessee. These oils, though they would be classed as rather heavy, differ greatly in specific gravity. In the first wells struck the oil had a gravity of 36° B.; in the later wells it reaches 37° or 38° and in some even 41°.

There have been two great drawbacks to the use of Lima oil for illuminating purposes: first, the presence of sulphur compounds; and, secondly, the yield as compared with the Pennsylvania oils. It is claimed that a way has been found to deprive this oil of its sulphur, and the price and market that are being obtained for the residuum after distilling off the illuminating oil have largely done away with the second objection. As is stated elsewhere, this oil has largely entered into use as an illuminator.

The production of petroleum in the Lima, Ohio, oil fields from 1886 to 1890 is as follows:

Production of petroleum in the Lima, Ohio, district from 1886 to 1890.

	Barrels.
1886	1, 064, 025
1887	4, 650, 375
1888	9, 682, 683
1889	12, 153, 189
1890	15, 014, 882

The statistics of the production of petroleum in the Lima field in 1889 are as follows:

Total production and value.

Total production in 1889 (barrels of 42 gallons)	12, 153, 189
Total value at wells of all oil produced, excluding pipage	\$1, 822, 978
Value per barrel	\$0.15

Stocks of fuel oil on hand at wells.

	Barrels.
December 31, 1888	78, 118
December 31, 1889	466, 308

Well record.

Total number of producing wells December 31, 1888.....	1,465
Total number of producing wells December 31, 1889.....	2,242
Total number of flowing wells December 31, 1888.....	157
Total number of flowing wells December 31, 1889.....	682
Total number of pumping wells December 31, 1888.....	1,308
Total number of pumping wells, December 31, 1889.....	1,560
Number of wells completed in 1889.....	701
Number of dry holes in 1889.....	34
Number of producing wells completed in 1889.....	667
Initial daily production of new wells (barrels).....	54,800
Number of rigs building December 31, 1888.....	23
Number of rigs building December 31, 1889.....	57
Number of wells drilling December 31, 1888.....	33
Number of wells drilling December 31, 1889.....	38
Value of materials used in pumping, caring for, and operating wells in 1889.....	\$318,000

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$16,802,637
Number of acres of oil land:	
Owned.....	22,477
Leased.....	349,142
Total acreage.....	371,619
Present value of land, both owned and leased.....	9,693,466
Average value per acre, \$26.	
Value of rigs, wells, engines, boilers, etc.....	\$5,990,285
Value of tanks.....	355,157
Value of pipe lines at wells owned by parties making report.....	117,049
Value of oil in stock at wells December 31, 1889.....	69,946
Value of other property and improvements.....	576,734
Total.....	7,109,171

Labor and wages.

All labor, not including office force:	
Number of foremen or overseers.....	86
Total wages paid all workmen of this class in 1889.....	\$65,563
Number of mechanics.....	557
Total wages paid all workmen of this class in 1889.....	183,210
Number of laborers.....	1,134
Total wages paid all workmen of this class in 1889.....	454,826
Office force:	
Total number (males).....	21
Total wages paid (males).....	19,376
Total number of persons employed and wages paid in 1889.....	1,798
Total wages paid.....	722,975
Wages paid for labor:	
In building rigs.....	\$22,352
In drilling wells.....	129,638
In operating and caring for wells.....	537,201
In torpedoing wells.....	3,728

Wages paid for labor—Continued.

In building or repairing tankage	\$7, 640
In building and repairing pipe lines	3, 040
In office	19, 376
Total	722, 975

Classified wages.

Class of labor.	Number of each class.	Range of wages.
Foremen	81	\$15 to \$214 per month.
Pumpers or engineers	977	\$5 to \$75 per month.
Carpenters	48	\$2.50 per day.
Rig builders	151	\$60 to \$125 per rig.
Drillers	276	45 to 80 cents per foot.
Tool dressers	5	\$3 per day.
Laborers	186	\$1 to \$2 per day.
Teamsters	5	\$3 to \$5 per day.
Well cleaners	20	\$3.50 to \$5 per day.
Sundry mechanics	13	\$2.25 to \$2.50 per day.

Macksburg, Ohio, district—The second largest oil-producing district in Ohio, and the one producing oil that compares with the best product of Pennsylvania, is that known as the Macksburg district. The chief production of this district is in Washington county, but a large quantity is reported also from Noble county, and small amounts from Harrison and Belmont counties.

The development of the Macksburg district was almost coincident with that of the western Pennsylvania oil fields, the first well having been bored in 1860. This well was but 56 feet deep, and yielded many thousands of barrels of heavy lubricating oil. It is reported that at first the daily yield was from 100 to 200 barrels. A well a short distance west of this yielded at first 150 barrels a day. Notwithstanding the early exploitation of this district, it however assumed but little importance until the spring of 1884, when a number of successful wells were bored. During 1885 the production increased rapidly, the runs through the Macksburg pipe line being 661,586 barrels. In 1890 the production reached 1,108,334 barrels, and this was the year of its greatest output.

The production of the Macksburg district for the last 6 years has been as follows:

Production of petroleum in the Macksburg, Ohio, district from 1885 to 1890.

	Barrels.
1885	661, 580
1886	703, 945
1887	372, 257
1888	291, 585
1889	317, 037
1890	1, 108, 334

Though oil is produced from 4 sands in this field, the important one is the Berea grit. The first oil well in this formation was struck in 1878, and was a 10-barrel flowing well.

Search for oil in this horizon in 1889 was quite persistent. A dozen wells were drilled near Cadiz, several of which started with a production of from 5 to 10 barrels of oil per day, only a few maintaining a production of 4 or 5 barrels at the close of the year. In Belmont and Jefferson counties some work was done, but the result was, on the whole, somewhat unsatisfactory.

The statistics of the production of petroleum in the Macksburg district in 1889 are as follows:

Total production and value.

Total production in 1889 (barrels of 42 gallons).....	317, 037
Total value at wells of all oil produced, excluding pipage.....	\$340, 683
Value per barrel.....	\$1. 07½

Stocks of oil on hand at wells.

	Barrels.
December 31, 1888.....	2, 726
December 31, 1889.....	3, 337

Well record.

Total number of producing wells December 31, 1888.....	317
Total number of producing wells December 31, 1889.....	390
Total number of flowing wells December 31, 1888.....	98
Total number of flowing wells December 31, 1889.....	103
Total number of pumping wells December 31, 1888.....	219
Total number of pumping wells December 31, 1889.....	287
Number of wells completed in 1889.....	118
Number of dry holes in 1889.....	32
Number of producing wells completed in 1889.....	86
Initial daily production of new wells (barrels).....	1, 127
Number of rigs building December 31, 1888.....	3
Number of rigs building December 31, 1889.....	2
Number of wells drilling December 31, 1888.....	5
Number of wells drilling December 31, 1889.....	7
Value of materials used in caring for and operating wells in 1889.....	\$331, 255

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$944, 721
Number of acres of oil land:	
Owned	745
Leased	67, 426
	68, 171
Total acreage.....	68, 171
Present value of land, both owned and leased.....	255, 841

Average value per acre, \$4.	
Value of rigs, wells, engines, boilers, etc.....	\$630, 950
Value of tanks	17, 450
Value of pipe lines at wells owned by parties making report.....	6, 695
Value of oil in stock at wells December 31, 1889.....	3, 731
Value of other property and improvements.....	30, 054
Total	688, 880

Labor and wages.

All labor, not including office force:		
Number of foremen or overseers.....	8	
Total wages paid all workmen of this class in 1889.....		\$6, 050
Number of mechanics.....	167	
Total wages paid all workmen of this class in 1889.....		52, 397
Number of laborers.....	141	
Total wages paid all workmen of this class in 1889.....		52, 595
Office force:		
Total number (males).....	2	
Total wages paid (males)		360
Total number of persons employed and wages paid in 1889....	318	111, 402

Wages paid for labor:

In building rigs	\$7, 902
In drilling wells	44, 661
In operating and caring for wells.....	56, 317
In building or repairing tanks	1, 800
In building and repairing pipe lines.....	362
In office	260
Total	111, 402

Classified wages.

Class of labor.	Number of each class.	Range of wages.
Foremen.....	10	\$40 to \$75 per month.
Pumpers or engineers.....	111	\$10 to \$60 per month.
Carpenters.....	41	\$2.50 per day.
Rig-builders.....	75	\$50 to \$205 per rig.
Drillers.....	131	45 to 60 cents per foot.
Tool-dressers.....	13	\$2 to \$3.50 per day.
Laborers.....	24	\$1 to \$2 per day.
Teamsters.....	3	\$3 to \$5 per day.
Sundry mechanics.....	3	\$2.50 per day.

Mecca-Belden district.—The wells in this district are located in Lorain and Trumbull counties and include the Grafton and Mecca-Belden districts. All the oils in this district are from the Berea grit.

These districts produce a lubricating oil from a few shallow wells. The total production in 1889 was 1,240 barrels, worth at the railroad station, 3 miles distant, package included, from 30 to 35 cents, according to quality. There were eight producing wells in 1889, and all were pumped by heads. The oil is obtained mixed with water highly

charged with hydrogen sulphide, as many as 1,000 barrels of water being often pumped out for one barrel of oil. The wells are owned and operated by farmers, who engage in this work when circumstances permit. The wells range from 50 to 60 feet deep, at which depth a fissure or crevice is found containing inexhaustible quantities of water, carrying a greater or less amount of oil. This water is collected and the oil permitted to settle, when it is skimmed off and, after settling, is heated by steam to still further drive off the water, and it is then put up in barrels and sold. A well was drilled in 1889 to a depth of 2,375 feet with the hope of obtaining a larger amount of oil, but without success.

There are no productive wells now in Mecca proper, all being in East Mecca.

WEST VIRGINIA.

The descriptions given in Pennsylvania of the Lower oil field, the character of the strata and of the oil produced, will apply to the Mount Morris and the Turkey Foot districts. That given in Ohio concerning the Macksburg district will apply to the Eureka. Regarding the other districts, it is sufficient to say that in most of the producing wells of the Volcano and Burning Springs districts the oil is found near the top of the carboniferous rocks.

Production.—The total production of petroleum in West Virginia in 1889 was 544,113 barrels, valued at \$653,827, or \$1.20½ per barrel; in 1890, 492,578 barrels, valued at \$501,198, or \$1.01¾ per barrel. In 1889 the Turkey Foot district produced 199,460 barrels; the Mount Morris, 174,758 barrels; the Volcano and Eureka, 165,735 barrels, of which 23,602 barrels were lubricating, and the Burning Springs, 4,160 barrels; making a total of 520,511 barrels of illuminating oil, valued at \$595,730, or \$1.14½ per barrel, and 23,602 barrels of lubricating oil, valued at \$58,097, or \$2.46⅙ per barrel. Tabulating these figures, the result is as follows:

Total production and value of petroleum produced in West Virginia in 1889 and 1890.

Districts.	1889.			1890.		
	Total production.	Total value.	Price per barrel.	Total production.	Total value.	Price per barrel.
	<i>Barrels.</i>			<i>Barrels.</i>		
Turkey Foot.....	199,460	\$243,192	\$1.217½
Mount Morris.....	174,758	194,949	1.11½
Volcano and Eureka.....	165,735	211,526	1.27½
Burning Springs.....	4,160	4,160	1.00
Total.....	544,113	653,827	1.20½	492,578	\$501,198	\$1.01¾

Production and stocks.—There are no separate reports of stocks of West Virginia oil held by pipe lines. The stocks held in Turkey Foot and Mount Morris are probably reported with the stocks of the pipe line in southwestern Pennsylvania, while the stocks of Eureka oil held by pipe lines are in the Macksburg report. There were, however, 6,104

barrels of oil in stock at wells December 31, 1888, and 6,835 barrels December 31, 1889. As the production of December, 1888, was 19,060 barrels, this would make the stocks at wells at the close of December, 1888, 32.03 per cent. of the production of that month. The production of December, 1889, was 81,453 barrels, and 6,835 barrels were held in stock at wells at the close of the month, making stocks at wells but 8.39 per cent. of the production for that month.

The general statistics in the Census report, referring to the West Virginia field are as follows:

The number of producing wells in West Virginia at the close of December 1888, was 505, and 623 at the close of December, 1889. Of the wells producing in this field at the close of 1888, eight were flowing and 497 pumping. At the close of 1889 there were 23 wells flowing and 600 pumping. The well statistics for the entire region are as follows:

Well record.

Items.	Turkey Foot.	Mount Morris.	Volcano and Eureka.	Burning Springs.	Total.
Total number of producing wells December 31, 1888.....	5	493	7	505
Total number of producing wells December 31, 1889.....	103	23	490	7	623
Total number of flowing wells December 31, 1888.....	7	1	8
Total number of flowing wells December 31, 1889.....	11	3	8	1	23
Total number of pumping wells December 31, 1888.....	5	486	6	497
Total number of pumping wells December 31, 1889.....	92	20	482	6	600
Number of wells completed in 1889.....	153	24	29	206
Number of dry holes in 1889.....	40	1	41
Number of producing wells completed in 1889.....	113	23	29	165
Initial daily production of new wells (barrels).....	3,726	3,298	567	7,591
Number of rigs building December 31, 1888.....	2	1	2	5
Number of rigs building December 31, 1889.....	11	3	2	16
Number of wells drilling December 31, 1888.....	2	3	5
Number of wells drilling December 31, 1889.....	15	4	5	24
Value of materials used in caring for and operating wells in 1889.....	\$92,254	\$25,136	\$5,379	\$122,769

The total capital invested in oil production in West Virginia in 1889 was \$1,472,598. Of this amount \$411,663 represents the value of land and \$1,060,935 the value of other property.

The amount of land held as oil land in this State is 120,219 acres, of which 396 acres were owned and 119,823 acres leased. The value of this land was \$411,663, or, ignoring fractions, \$3 an acre. To this amount should be added 17,630 acres of land leased for oil purposes on which no developments have been made, representing an outlay for leases of \$10,243.

The total amount of capital invested in other property was \$1,060,935. Of this amount \$985,769 represents the value of rigs, wells, etc., \$35,904 the value of tanks, \$3,775 the value of pipe lines, \$17,713 the value of oil in stock at wells, and \$17,774 the value of other property.

As there were 623 producing wells in this State at the close of the year, and the value of these wells was \$985,769, the value of each well would be \$1,582.

The remarks made in Pennsylvania in discussing the question of land and value of wells will apply here also.

In the following table will be found a statement of the capital used in West Virginia, by districts, and its division into totals of land and other property:

Capital invested, by districts.

Districts.	Total capital.	Value of land.	Total value of other property.
Turkey Foot	\$489, 180	\$188, 173	\$301, 007
Mount Morris	501, 254	142, 111	359, 143
Volcano and Eureka	476, 028	80, 718	395, 310
Burning Springs	6, 136	661	5, 475
Total.....	1, 472, 598	411, 663	1, 060, 935

The following table shows the acreage of land in each district in West Virginia, together with the value of the same and the value per acre:

Acreage and value of land.

Districts.	Owued.	Leased.	Total.	Total value.	Value per acre.
	<i>Aces.</i>	<i>Aces.</i>	<i>Aces.</i>		
Turkey Foot	50	32, 295	32, 345	\$188, 173	\$5. 82
Mount Morris	244	49, 063	49, 307	142, 111	2. 88
Volcano and Eureka	100	36, 495	36, 595	80, 718	2. 21
Burning Springs	2	1, 970	1, 972	661	. 34
Total.....	396	119, 823	120, 219	411, 663	a 3. 42

a Average.

In the following table will be found the division of the capital invested in West Virginia other than land:

Division of capital other than land.

Districts.	Rigs, wells, etc.	Tanks.	Pipe line.	Oil in stock.	Other property.	Value per well.	Total.
Turkey Foot	\$291, 210	\$6, 413	\$620	\$850	\$1, 914	\$2, 827	\$301, 007
Mount Morris	337, 114	6, 056	110	863	15, 000	14, 657	359, 143
Volcano and Eureka.....	352, 795	22, 610	3, 045	16, 000	860	520	395, 310
Burning Springs.....	4, 650	825	664	5, 475
Total.....	985, 709	35, 904	3, 775	17, 713	17, 774	a 1, 582	1, 060, 935

a Average.

Labor and wages.—The total number of employés returned as engaged in the production of crude petroleum in West Virginia at the close of 1889 was 339, who were paid \$160,974. The division of these workmen into classes and wages paid is as follows:

All labor, not including office force:

Number of foremen or overseers.....	17
Total wages paid all workmen of this class in 1889.....	\$14, 520
Number of mechanics.....	213
Total wages paid all workmen of this class in 1889.....	108, 298
Number of laborers.....	107
Total wages paid all workmen of this class in 1889.....	36, 756

Office force:

Total number (males).....	2	
Total wages paid (males).....		\$1,400
Total number of persons employed and wages paid in 1889.....	339	160,974

The character of work for which this total amount of wages was paid is shown in the following table:

Wages paid for labor.

In building rigs	\$19,869
In drilling wells.....	82,312
In operating and caring for wells	55,903
In torpedoing wells.....	30
In building or repairing tankage.....	1,460
In office	1,400
Total.....	160,974

COLORADO.

Though indications of petroleum, such as oil springs, sandstones impregnated with petroleum, or with the residuum after evaporation, and "oozes," are reported from many parts of Colorado, the only locality from which oil has been produced in paying quantities is the field located in the valley of the Arkansas, near Florence, in Fremont county, known as the Florence field. This field extends from near Canyon, 8 miles above Florence, to an as yet undetermined distance southeast of Florence. The present productive field is confined to a small area, about 2 miles square, of the valley of the Arkansas river, and adjacent "mesa" or table land. It is reached by the Denver and Rio Grande and Atchison, Topeka, and Santa Fe railroads. The productive wells at present seem to be confined to a basin $1\frac{1}{2}$ to 2 miles wide. East and west of this basin the petroleum is displaced by water. A notable spring of soda water was recently struck about 2 miles east of Florence, at a depth of 2,200 feet, the water issuing from the ground at a temperature of 80° F. The length of this basin is northwest and southeast. What its extent is along its length is not as yet determined. The first wells, as will be seen below, were struck near Canyon, about 8 miles northwest of Florence. But these wells have been abandoned, and all the production is in the immediate vicinity of Florence. The drilling at the present time is chiefly toward the southeast from Florence, toward Pueblo, the larger bodies of land held by the different companies being in this direction. Wells have been bored near Pueblo, about 30 miles down the river, which have yielded water abundantly, but no oil. There is quite a stretch of country just below Florence which has the same geological structure as that in which the wells have been drilled. It is possible that the oil field may extend some distance down the river toward Pueblo.

As stated above, indications of oil have been found in many other

places in Colorado. Beneath the Laramie deposit the Colorado group of the cretaceous formation consists of bituminous shales 1,600 to 2,000 feet in thickness. These have been disturbed in the vicinity of the mountains, and gas and oil have been found issuing from them in many places, as on the north branches of the San Juan river, in the coal basin below Glenwood Springs, and in the White River country. These bituminous shales of the Laramie have yielded, and probably will still yield, large quantities of petroleum. At Morrison, 11 miles from Denver, on the Denver and South Park railroad, the Denver Natural Gas and Oil Company is drilling for oil, encouraged by the presence of a sand rock colored dark brown or black by the residual products of the liquid hydrocarbons, which exists five-eighths of a mile west of the drilling point. The rock outcrops at this point, dipping about 30° east. Drilling was begun five-eighths of a mile east of the outcrop under the supposition that oil would be found at greater quantities at this depth. The drilling is in a shale, and was, in May, 1891, down to a depth of 1,950 feet, no oil having been reached at that time. The drilling of this well, known as the Morrison well, has been discontinued.

The first indications of petroleum in Fremont county were found at Oil Springs, about 6 miles northeast from Canyon and half a mile above the mouth of Oil Creek cañon. Mr. Joseph Lamb and other pioneers claimed to have seen the springs in 1859, but Mr. Gabriel Bowen is generally credited with the discovery. In 1862 the late Mr. A. M. Cassady purchased the springs from Mr. Bowen, and in March of the same year began collecting the crude oil by sinking 6 wells, first digging and sinking shafts, following with spring-pole and drill to a depth of 60 to 100 feet. Two wells were sunk from 300 to 500 feet, but oil was only found near the surface.

Between the years 1862 and 1865 Mr. Cassady collected and refined oil, most of which was transported by team and sold in Pueblo, Denver, and Santa Fé. For some of the refined oil he realized as high as \$5 per gallon.

As Mr. Cassady's method of refining was crude and expensive, the advent of railroads across the plains from the Missouri river rendered his industry unremunerative and he abandoned it. Other parties at later dates attempted to sink wells in the same locality, but without success.

In 1881, while a well was being drilled near the coal mines at the town of Coal Creek for a water supply, oil was discovered at a depth of 1,260 feet. A company was organized, composed of citizens of Cañon City, called the Land Investment Coal and Oil Company, which commenced operations in November, 1882, and on April 7, 1883, after expending about \$20,000, struck oil on the farm of Mr. Edwin Lobach, near the town of Florence, the present center of the oil industry of Colorado. This company was not successful, and in a few years was merged into the Colorado Oil Company, which company, with the

Arkansas Valley Oil and Land Company and other interests, organized the United Oil Company in 1887.

Other operations since the organization of the United Oil Company have been undertaken at Florence. The only one, however, operating in the census year was the Florence Oil and Refining Company. These two companies produced all the oil from this district in 1889. Four other companies, however, have since begun operations in this field, namely, the Rocky Mountain Oil Company, Triumph Oil Company, Colorado Coal and Iron Company, and the Beaver Land Company.

The geology of the country near Florence is very simple. The Arkansas valley at Florence has cut through the Laramie group, the upper member of the Cretaceous, exposing the upper portion of the Colorado group, the middle member of the Cretaceous. East and west of Florence the rocks of the Laramie, sandstones and shales, with beds of coal lying nearly horizontal, are exposed on the mountain side. In the valley at Florence, where the wells have been put down, the formation consists almost entirely of blue or bluish-black shale, having a thickness of from 3,000 to 4,000 feet. The wells are all sunk in this shale, no well that has yet been put down having passed through it, though some wells have been drilled 3,500 feet or more. Farther up the valley of the Arkansas these sedimentary strata are uplifted and rest against a granite axis of the Greenhorn range. The slate or shale in which the oil is found dips southwest about 10°. As stated above, the wells drilled in this district have never gone through the shale, which lies just below the drift, but it is questionable if the origin of the oil is in the shale. The indications are that it drains into the shale probably from the direction of Cañon City. It is noted in drilling that when the shale seems to be solid and unbroken no oil is found, but when in drilling, crevices are struck and the strata appears broken, oil is almost sure to be discovered. A well at a given point, which, when drilled, shows crevices and broken strata, may produce 150 to 200 barrels a day, while another well 100 feet from it, drilled through solid shale, will not give the least indication of oil. About one well in three has proved a producer.

The depth at which oil is found varies greatly. There are producing wells as deep as 1,960 feet, and others not over 1,000 feet. In one case there are two wells within 300 feet of each other, in one of which oil was found at a depth of 1,630 feet, and in the other no oil was found until 1,960 feet had been reached. The earlier wells of the Florence field were drilled 1,000 to 1,200 feet. In many cases these wells, after producing for a while, ceased, but upon drilling deeper they began producing again. No water is found in the wells after leaving the surface.

It will thus be seen that the conditions under which oil is found in Colorado are very different from those of its occurrence in Pennsylvania and Ohio. There are no pools as the word is understood in the East, but the oil seems to flow through the crevices or shattered strata to the

drill hole. It is also a remarkable fact that the wells, instead of decreasing, actually increase in production. A certain well on the property of one of the companies, which began producing 90 barrels of oil, now produces 150, the maximum being reached within a short time after the well was struck, it gaining every day for about two weeks. Another well that began with a production of 100 barrels ran up in 5 days to 210, and has been producing at this rate for months. On the other hand, sometimes increase in production is very gradual, wells that are now several years old having recently increased their production. One well that started off producing 40 barrels in this way has recently run up to 150. The life of wells in the Florence district is also very long, and some wells have been remarkable producers, one having produced up to May 1, 1891, over 6,000,000 gallons. The large production and long life of the wells of this district may be due to the fact that it is a new field and comparatively few wells have as yet been put down.

It is also a fact that it does not hurt these wells to shut them down for a period. Often when the demand for oil has not been equal to the production the wells have been shut in, starting off again with full production when pumped. This will account for the variation in the number of producing wells shown in the table given elsewhere. This variation is not due to the drilling of new wells and the abandonment of old, but to stopping of production by shutting in the wells.

The Florence oil has a number of peculiarities as compared with Pennsylvania. It is a heavy oil, being about 31° B. It contains little or no lighter hydrocarbon, all the products that pass over in refining being sold as illuminating oil. Nor does the oil deposit any "B. S." It yields in refining about 35 to 44 per cent. water-white illuminating oils of about 125° fire test. There is little or no market for the residuum from refining other than fuel.

Product.—The following table gives the total product of all Colorado oil wells since 1887, when production first began, and includes all oil paid as royalty to owners of land upon which wells were drilled. There is no market in Colorado for crude oil, and none is bought and sold except a very small amount of royalty oil, which is pumped and bought by refineries, and is paid for at the rate of 2 cents per gallon or 84 cents per barrel.

Product of crude oil in Colorado from 1887 to 1890.

Years.	Barrels.
1887	76, 295
1888	297, 612
1889	316, 476
1890	368, 842

Stock of crude oil at wells.

1888.		Barrels.
December 31		13, 092
1889.		
January 31		10, 870
February 28		24, 496
March 31		34, 792
April 30		39, 593
May 31		41, 883
June 30		41, 953
July 31		38, 355
August 31		40, 516
September 30		35, 519
October 31		38, 418
November 30		40, 854
December 31		51, 034
Average		36, 524
Value of stock on hand at wells December 31, 1889		\$45, 267. 56

The value of these stocks is calculated on the same basis as that of production.

Distribution of product.—There are no pipe lines or distribution lines used in Colorado. All oil produced is consumed by refineries. The per cent. of oil evaporated is very small.

Distribution of the Colorado oil product.

	Barrels.
Stocks at wells December 31, 1888	13, 092
Produced in 1889	316, 476
Total	329, 568
Stock December 31, 1889	51, 034
Distribution in 1889:	
Dump oil	277, 211
Evaporated	1, 323
Remaining on hand December 31, 1889	51, 034
Total	329, 568

Total number of rigs building but not completed.

[No rigs building in months omitted in 1889.]

December 31, 1888	3	July 31, 1889	1
January 1, 1889	2	August 31, 1889	1
February 28, 1889	1	September 30, 1889	1

Total value of materials used in building rigs, \$3,600.

Total number of rigs completed.

[No rigs completed in months omitted in 1889.]

During— January, 1889 3 February, 1889 2 March, 1889 1 Total cost of rigs built in 1889, \$7,200.	During— July, 1889 1 August, 1889..... 1 September, 1889 1
---	---

Total number of wells drilling.

[No wells drilling in months omitted in 1889.]

December 31, 1888 4 January 31, 1889 3 February 28, 1889 1 Total value of materials used in drilling wells, \$27,500.	July 31, 1889 2 August 31, 1889 2 September 30, 1889 2
--	--

Where dry holes have been drilled it frequently occurs that the rig is removed and another well started, thus reducing the cost of the following well.

The value of materials used in drilling wells is that of the tools and fixtures necessary to drill wells, and is not the value of materials used within the wells, such as tubing, casing, rods, etc.

Oil wells completed in Colorado in 1889.

Months.	Total number of wells completed in each month.	Number of dry holes.	Number of wells producing.	Initial daily production of new wells.
				<i>Barrels.</i>
January.....	4	3	1	8
February.....	3	2	1	50
March.....	1		1	50
April.....				
May.....				
June.....				
July.....				
August.....	2	1	1	90
September.....	2	1	1	12
October.....	1		1	50
November.....	1	1		
December.....				
Total.....	14	8	6	260

Out of 14 wells completed it will be noticed that 8 were dry holes, 6 only being productive. The average initial production of wells was 43½ barrels for the first 24 hours.

Number of producing oil wells in Colorado.

Months.	Total number producing. (a)	Total number abandoned.	Months.	Total number producing. (a)	Total number abandoned.
1888.			1889.		
December 31.....	23		July 31.....	22	
1889.			August 31.....	23	
January 31.....	24		September 30.....	24	
February 28.....	25		October 31.....	24	1
March 31.....	25	1	November 30.....	23	
April 30.....	12	3	December 31.....	22	1
1889.			Total.....		6
May 31.....	16				
June 30.....	15				

a All pumping.

Some wells, although productive, were shut down during the year on account of lack of storage and limited demand for crude product at the refineries. Six wells that had ceased to produce were cleaned, but without results. Thirteen other wells were cleaned with good results, bringing the production back to almost the original amount. No wells were torpedoed in this State during 1889.

Tankage.—The tankage in this State consists chiefly of cement and brick cisterns, it having been demonstrated that evaporation is less than if wood or iron tankage were used.

Statistics of oil tanks in Colorado.

Material.	Number.	Size.		Capacity. (Barrels of 42 gallons.)
		Diameter.	Height.	
		<i>Ft. In.</i>	<i>Ft. In.</i>	
Cement and brick.....	1	20 2	13 0	672
Do.....	1	25 0	12 0	1,300
Do.....	1	25 0	13 9	1,086
Do.....	13	31 8	9 6½	1,258
Do.....	1	30 0	13 4	1,511
Do.....	1	28 7	15 5	1,581
Iron.....	1	30 0	22 0	2,770
Do.....	1	59 11	28 0	14,204
Do.....	1	86 0	17 6	18,105
Wood.....	7			37
Do.....	15	10 0	8 0	100

Tank record.

Total number of tanks.....	43
Total capacity of tanks (barrels).....	42,324
Total value of materials used in building or repairing tanks in 1889.....	\$9,039
Total value of all materials used in building or repairing tank cars in 1889.....	\$7,000
Total length of pipe lines at wells, not including that belonging to pipe-line companies (feet).....	39,228
Total value of pipe lines at well.....	\$7,904
Sizes of pipe used and length of each size:	
3-inch pipe (feet).....	8,781
2-inch pipe (feet).....	29,724
1-inch pipe (feet).....	723

The amount of money expended for tankage at wells is really an expense for storage, and includes a limited amount of expense incurred from pipe lines at wells to refineries and storage cisterns.

The condensed statistics of the production of petroleum in Colorado in 1889 are as follows:

Total production and value.

Total production in 1889 (barrels of 42 gallons).....	316,476
Total value at wells of all oils produced, excluding pipage.....	\$280,240
Value per barrel.....	\$0.88½

Stocks of illuminating oils on hand at wells.

	Barrels.
December 31, 1888.....	13,092
December 31, 1889.....	51,034

Well record.

Total number of producing wells December 31, 1888.....	23
Total number of producing wells December 31, 1889.....	22
Total number of pumping wells December 31, 1888.....	23
Total number of pumping wells December 31, 1889.....	22
Number of wells completed in 1889.....	14
Number of dry holes in 1889.....	8
Number of producing wells completed in 1889.....	6
Initial daily production of new wells (barrels).....	260
Number of rigs building December 31, 1888.....	3
Number of wells drilling December 31, 1888.....	4
Value of materials used in pumping, caring for, and operating wells in 1889.....	\$27,500

Capital invested in Colorado oil fields.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$3,000,000
Number of acres of oil land:	
Owned.....	33,015
Leased.....	6,100
Total acreage.....	39,115
Present value of land, both owned and leased.....	2,517,215
Average value per acre, \$64.....	
Value of rigs, wells, engines, boilers, etc.....	\$229,659
Value of tanks.....	63,581
Value of tank cars.....	8,333
Value of pipe lines at wells owned by parties making report.....	7,903
Value of oil in stock at wells December 31, 1889.....	45,268
Value of other property and improvements.....	128,041
Total.....	482,785

Labor employed in producing Colorado oil.

All labor, not including office force:	
Number of foremen or overseers.....	5
Total wages paid all workmen of this class in 1889.....	\$4,950
Number of mechanics.....	56
Total wages paid all workmen of this class in 1889.....	19,138
Number of laborers.....	28
Total wages paid all workmen of this class in 1889.....	8,744
Office force:	
Total number (males).....	1
Total wages paid (males).....	1,800
Total number of persons employed and wages paid in 1889.....	90 34,632

Wages paid in producing Colorado oil.

Wages paid for labor:	
In building rigs.....	\$2,703
In drilling wells.....	8,099
In operating and caring for wells.....	21,494
In building and repairing pipe lines.....	586
In office.....	1,800
Total.....	34,632

Classified wages.

Class of labor.	Number of each class.	Range of wages.	Average.	Days employed.
Foremen.....	4	\$4.17 to \$5 per day....	\$4.58	330
Pumpers or engineers..	20	\$2.50 per day.....	2.50	145
Carpenters.....	10	\$3 per day.....	3.00	86
Drillers.....	8	\$4 per day.....	4.00	127
Tool dressers.....	10	\$3 per day.....	3.00	112
Laborers.....	38	\$2 per day.....	2.00	115

CALIFORNIA.

The petroleum fields of California where oil is found in merchantable quantities are almost exclusively within the boundaries of the southern counties, though oil has been found in many other parts of the State.

The oil-producing territory in California in 1889 and 1890 may be divided into two general sections: (1) that included in the Santa Paula region, in which are found the Ojai, Sespe, Ex-Mission (which includes the Adams and other districts), the Torrey Cañon in the San Fernando mountain, 22 miles west of Newhall, the San Fernando district, including the Pico, Wiley, and Elsemere fields, and the Puente district, in which only one field, the Puente, is found; (2) the Santa Clara district, in Santa Clara county, which is known sometimes as Moody gulch.

The wells in the Santa Paula subdistrict of the southern fields are in Ventura county; the Pico and Puente subdistricts are in Los Angeles county.

Oil was at one time produced in San Mateo county, a short distance below San Francisco on the coast, and small amounts in other counties; but the only production in 1889 and 1890 was in Santa Clara, Ventura, and Los Angeles counties.

The oil belt commences near Santa Paula, in Ventura county, and extends thence in a southeasterly direction about 80 miles to Puente, in Los Angeles county, taking in the Sespe, Torrey cañon, and other wells in Ventura county, Pico, Newhall, Elsemere, Puente, and other districts in Los Angeles county. This belt has a variable width of from 2 to 3 miles, through oil is not found all through the entire length, it being apparently in pools.

Though petroleum has been known to exist in California from the time of its first settlement by the whites, no attempt was made to utilize the deposits until about the time of the discovery of the Pennsylvania oil fields, which led to the prospecting for petroleum at localities pointed out by petroleum and tar springs and by seepage from the asphaltum beds. During the years 1865 and 1866 upward of 70 companies were incorporated in California to search for petroleum and a large amount of money was spent, but no considerable amount of oil was found. The developments at this date were in Los Angeles and Ventura counties. Discouraged at the result of the first efforts, but little was done until 1875, when the business began to revive. In this year two wells were

put down in the Pico cañon, which have been producers ever since. These two wells produced in 1875 about 650 barrels of oil. In 1877, 6,332 barrels were produced from the Ex-Mission field, and in 1878, 300 barrels were produced from the Santa Clara district. The first wells put down in the Pico cañon were drilled with spring poles. At least three wells were drilled in this way, two of which are still producing.

The petroleum fields of California are the most interesting in the United States. In many respects they differ entirely from any other fields yet opened. The oil, with the exception of that from Santa Clara, has usually, as its "base", asphaltum instead of paraffin. The Pacific Coast Oil Company at one time pressed paraffin wax from the Santa Clara oil, but the low price of the wax and the reduction in the production of the crude compelled them to discontinue this production. The strata in which the oil is found are tilted at a high angle. Drilling is difficult and expensive, owing to the character of the rock and the angle at which the oil-bearing strata stand. The oil, while carrying but a small proportion of the illuminating hydrocarbons, finds a ready market as fuel, owing to the high price of coal in California, and it contains practically no "B. S."

While there is a certain general resemblance in all of the southern fields, there are certain important differences which make a description of each field of importance.

Describing the most northwesterly, the Santa Paula, first, it may be said that this field includes, as has been stated above, a number of small subdivisions, such as the Ex-Mission, Adams, Sespe, Ojai, Santa Paula, Torrey cañon, and others. These cañons are sharp ravines cut laterally in the sides of the mountains and usually at right angles with the course of the range. The strata in these various districts stand at an angle of about 75 degrees. In sinking wells the drills pass through shales until the oil sand is struck, which is from 2 to 40 feet in thickness. This sand is believed to be in the Tertiary strata, though of this there is some doubt. A red sand that used to be regarded as barren is now giving some very good wells.

The great angle at which the strata stand in this district makes drilling exceedingly difficult, resulting often in crooked holes, causing the drills to lodge in the wells and requiring torpedoing and reaming out and very expensive work in recovering them. This liability of the wells to become crooked suggested the employment of the diamond drill in boring. A well was bored in this way at Pico, but it was not a success, though a straight hole was secured. The fine mud that results from the use of the diamond drill seemed to fill up the interstices in the rock and prevented production. The reaming out of the well by a drill resulted in a very largely increased production. The same fact regarding the tilting strata also suggested the use of tunnels in producing petroleum. Some of the earliest work in mining for petroleum in California was by the use of tunnels. In fact, in the early history of this

field and of all southern California prospecting for petroleum was by these tunnels, which were driven into the sides of the mountains where the surface indications, such as tar springs or seepage from asphaltum deposits, gave any prospect of getting oil. Many of these tunnels are still in existence and some are producing. One of these tunnels was driven in 1864 by a company of which Senator Stanford was a member. This produced at first 25 barrels of oil a day. Twelve years later the production had fallen to 8 barrels a day, and when Messrs. Hardison & Stewart purchased the property, in 1885, it was producing 5 barrels a day, and at the present time 2 barrels a day. This method of producing oil has never been in great favor in California. It is somewhat dangerous, as is all tunneling. It is known locally as "coyoting." There are many things, however, to commend it for these fields. As suggested above, the difficulty and expense of drilling, and especially the caving in of the wells, owing to the peculiar structure of the shale through which the wells are drilled, makes it difficult and expensive, not only to put down wells, but to case off the water. In these tunnels there is no caving in of strata, no casing, no pumping, and in fact, no expense after the tunnel is once driven. The first or Stanford tunnel was driven 350 feet. One driven some four years ago was 625 feet long. The oil was found in different strata, and paid for it before it was finished. The yield of this tunnel was about 60 barrels a day when first finished; now it is 8 barrels a day. The cost of driving these tunnels is from \$5 to \$10 a running foot. The wells cost as much as this at times. The size of the tunnel is usually 4 by 6 feet. In 1889 there were 4 of these tunnels producing.

Another peculiarity of these wells, growing out of the tilting of the strata above referred to, is the great increase in the production of different wells put down to reach the strata at different depths. As has already been stated, these strata dip about 75 degrees. A series of five wells has been put down at one place in the Adams cañon, the wells being started on the surface at different heights up the mountain side above the stream at its base. The first well was put down a short distance above the point where the oil-bearing rock came to the surface, the presence of the oil showing itself by seepage from the outcropping rock. The sand rock was struck at a depth of 110 feet, and produced 20 barrels a day. The second well was started a little higher up the mountain side, the rock pitching toward the mountain, striking the oil-bearing rock at a depth of 130 feet, giving a production of 25 barrels a day, draining or perhaps better, stopping production entirely in No. 1. A third well was started still farther up the mountain side, which struck the rock at a depth of 330 feet, producing 75 barrels a day and stopping production in the second well. A fourth well, started still higher up the mountain side, struck the rock at a depth of 682 feet and started off producing 300 barrels a day, stopping production in No. 3. The fifth well is being put down very much higher up the mountain, but had not

struck the sand rock at the time this report closed, though it had been drilled to a depth of 2,450 feet. The fourth well described above produced up to a given period 123,000 barrels, the production of the four wells being for the same time 250,000 barrels. Another peculiarity is noticed in these wells. Sometimes the depth of shale is very slight, the well being drilled entirely through sand (not sand rock), a little oil being produced all the way down. It is customary to case the well and perforate the casing, the oil flowing in from the sand almost the entire depth of the well. In a short time, however, the sand packs around the casing, the oil begins to percolate through it, and, to use the expression of the region, the well "gets its pace and is a stayer."

The oil of the Santa Paula field produces about 15 per cent of distillate; 35 per cent can be secured, but the quality of the illuminant is not satisfactory. But little oil from this district is refined, most of it being sold for fuel purposes. The gravity is from 16° to 32° , the average being about 26° . The oil from the same region differs greatly in its character. In putting down wells up the sides of a hill, six or seven different grades of oil will be found in as many ledges. In one case six wells were put down, beginning at the bottom of the hill and going up the sides 400 feet. In the first well, going up the hill, a black oil of 26° gravity was found; in the second well the oil was black and of 28° gravity; in the third it was a heavy oil and brown; in the fourth well the oil was 18° gravity, tarry and black; in the fifth well the gravity was 18° , heavy and green, and in the sixth well the gravity was 30° and the oil was light green in color with some yellow.

The strata in the other districts are not pitched as in the Santa Paula, where they stand at an angle of some 75 degrees. In the Pico field they are 65 degrees, and in the Puente 30 degrees. This excessive tilting makes drilling difficult and expensive. Not only are the strata very much tilted, but they are so much so all through southern California that but little dependence can be placed in their continuity. This resulted in the early history of mining for oil in California in the spending of very large sums of money, but with very little result, but in later years it has led to very cautious explorations. It also has resulted in very small fields, with the exception of the Santa Paula. In this field there are practically continuous deposits for a distance of some 40 miles, though the deposits are in pools. The Pico producing field is but a few hundred feet, possibly a mile in length by 700 or 800 feet broad, though developments are being made for 8 miles, while the Puente, as developed, is but 3,500 feet long by 800 feet broad. This also is probably much larger.

Many of the conditions existing in the Pico cañon are similar to those in the Santa Paula district; but there are many conditions that are more manifest here than in Santa Paula. The San Fernando district, as stated above, comprises three subfields, the Pico, which is the most important, the Wiley, and the Elsemere, which are recent develop-

ments. The Pico field is some 7.5 miles west of Newhall, which is on the Southern Pacific railroad; the Wiley some 5.5 miles southwest, and the Elsemere 2.5 miles to the southeast. These are all connected with Newhall by pipe lines.

As has already been stated, drilling was begun in this field in 1875, August 22, being the date of the beginning of the first well, which was finished September 8. This well was drilled to a depth of 120 feet with a spring-pole. At the depth of 30 feet oil was struck in a shale, giving a production of 2 barrels a day. At the depth of 120 feet oil was found, also in shale, the production being 10 to 12 barrels a day. In 1887 this well was deepened with modern drilling tools to a depth of 600 feet. At a depth of 175 feet the well produced by pumping 30 barrels a day. In 1882 this well was still further deepened to 735 feet, but there was no increase in production. The best sand was found in this well at a depth of 170 feet. Well No. 2, very close to No. 1, was drilled in November, 1875, also with a spring-pole. The best sand was struck at a depth of 250 feet, the well flowing from 20 to 25 barrels a day. At 520 feet the production was 40 barrels, the well being pumped. In well No. 3, sand producing 4 barrels a day was struck at 90 feet, another at 145 feet producing 8 barrels a day, while at 170 feet one producing 11 barrels a day was struck. In well No. 5 the first oil-producing sand was struck at 900 feet, while in No. 7 sand was found at 850 feet, giving a flowing well. The deepest producing wells in this district are from 1,400 to 1,730 feet.

The same difficulty in drilling wells exists here as in the Santa Paula district. The wells are put down on the sides of very steep cañons, requiring very expensive work in securing a level place to begin drilling, oftentimes requiring blasting in the mountain sides. Crooked holes are not infrequent, and it is nothing uncommon for wells to cost from \$6,000 to \$20,000 apiece. Contracts have been taken in this district to put down wells at \$6 a foot, the company owning the land furnishing fuel, water, and casing. The wells in this district never suffer from drowning out by water. Though some of the wells produce both water and oil, the average proportion of water to oil is very small. In some wells the water contains material in solution that eats the casing, making it thin, like paper. In this district as in others, considerable gas is found in the wells, which is utilized for pumping and drilling, saving possibly in this district 20 tons of coal a day. Wells are never shot for production. Sometimes when a hole is crooked and tools are stuck in them they are shot to release the tools, but not to increase the yield of oil.

The oil of the Pico field is in some respects better than that of the other fields, some of it containing a little paraffin occasionally, and it yields a larger percentage of illuminants in refining than the Santa Paula oil, crude being about 40° gravity. In the Wiley subdivision of the Pico field two different oils are found, taken from the same well, a

green and a black. The production of these two oils is about $4\frac{1}{2}$ barrels a day, and was found at a depth of from 600 to 800 feet. In drilling this well sand, not sandstone, was struck at a depth of from 400 to 600 feet. This sand followed the drill up the well fully 50 feet. It is from this sand that the oil comes. It had to be shut off from the well by casing and the casing perforated. A similar phenomenon is noticed in the Santa Paula district.

The Elsemere field was not developed until after the close of 1889.

The Puente field is located in the Puente hills, 7 miles from Puente station, on the Southern Pacific railroad. Oil in some instances is found in a shale just above the sand, but mostly in the sand. It has asphaltum as its base, carrying about 15 per cent. Wells are struck at various depths, but the best producers begin at 500 feet. It is difficult to drill below 1,200 feet, owing to the caving in of the strata, noticed in connection with the remarks on other fields. One well has been drilled in this district to a depth of 1,200 feet, but the deepest producer is at 1,000 feet. The strata are very much pitched and broken, dipping about 30 degrees north, the strike being a little northwest of west. The field as at present developed is 3,500 feet long by 800 feet wide. The first well was drilled in this field in 1883. The occasion of drilling the well was the discovery of a large amount of seepage near where the well was first put down. No. 2 and No. 3 were drilled early in 1884, and no others were drilled until 1886. The earlier wells up to No. 3 were drilled to the depth of 200 feet, and produced a heavy oil to the amount of 3 or 4 barrels a day. These are still producing, but in smaller amounts, from 1 to 2 barrels daily. No. 4 well, which was drilled in 1886, was also a small producer, yielding 15 barrels a day. No. 5, drilled in 1886, began with a production of 75 barrels. Three wells were drilled in 1888 and three in 1889. The same difficulty in drilling noted in other districts in this State obtain here also, such as crooked holes, caving in of sides, losing of tools, etc. The cost of drilling is from \$3 to \$6 a foot or more. In this district what is known as stovepipe casing is used. This is a thin riveted casing, two joints being put together, one being smaller than the other. The inner casing on one end projects beyond the outer casing, while the outer casing projects at the other end beyond the inner, forming a socket at one end, into which the projection at the other fits. The casing is ticked together at the joints, requiring no nuts or screws or couplings. The casing is sometimes jacked down into place. All of the oil from this district is piped over the hills to near the Puente station, loaded in tank cars and sent to Los Angeles, and consumed for fuel. No dry holes have ever been found in this district. Every well that has ever been sunk was a producer and is still producing. The wells are all pumped by heads. Though one or two spouters have been struck, they soon dropped in production and are now pumping. The following is an analysis of various tests made of the oil from these wells, having a gravity of 32°:

Analysis of oil from the Puente field, California.

	Per cent.
Benzine, from 80° to 58°	15
Illuminating, 58° to 42°	26
Lubricating, 42° to 30°	14
Lubricating, 30° to 24°	27
Asphalt (maltha)	18
Total	100

Statistics of production of petroleum in California in 1889 and 1890.—In the table given below are the consolidated statistics of the production of petroleum in California in 1889. From this it appears that the total production was 303,220 barrels, of which 97,264 barrels were classed as illuminating and 205,956 barrels as fuel oil. The probability is that a small proportion of that oil classed as fuel oil was also sold to refineries, but the division named is the best that was possible under the circumstances. The illuminating oil was priced at \$1.25½ per barrel at the well, the fuel at \$1.13¾. Some of this oil classed as fuel oil was a very heavy oil carrying a large percentage of asphaltum, and was sold as a paint for painting iron pipes. A small portion of the oil classed as illuminating was sold for mixing with asphaltum for thinning or tempering it, as it is termed. This oil brought 20 cents a gallon. These amounts in each case, however, were so small that they may be ignored and the classification allowed to stand.

Production of oils in 1889 and 1890.

Kinds of oil.	1889.	1890.
	<i>Barrels.</i>	<i>Barrels.</i>
Illuminating	97,264	98,360
Fuel	205,956	209,000
Total	303,220	307,360

Value at wells of all oil produced, excluding pipage, in 1889 and 1890.

Kinds of oil.	1889.		1890.	
	Total value.	Value per barrel.	Total value.	Value per barrel.
Illuminating	\$121,684	\$1.25½	\$121,701	\$1.23
Fuel	234,364	1.13¾	262,499	1.25
Total	356,048	1.17¾	384,200	1.25

Concerning the other statistics but little need be said. It has been exceedingly difficult to collect these figures, and even now there is some doubt as to their accuracy. The business of producing crude petroleum in southern California is so complicated in certain fields as to lead to possible duplication of returns in some instances and to insufficient returns in others. It is believed, however, that the statements given

in this report are nearer correct than those usually published regarding the production of crude oil in California, being the result of a personal visit by the writer to the field.

Stocks of oil on hand at wells.

	Barrels.
December 31, 1888:	
Illuminating.....	1, 758
Fuel.....	5, 789
	<hr/>
Total.....	7, 547
December 31, 1889:	
Illuminating.....	1, 264
Fuel.....	2, 176
	<hr/>
Total.....	3, 440

Well record.

Total number of producing wells December 31, 1888.....	88
Total number of producing wells December 31, 1889.....	89
Total number of pumping wells December 31, 1888.....	88
Total number of pumping wells December 31, 1889.....	89
Number of wells completed in 1889.....	10
Number of dry holes in 1889.....	4
Number of producing wells completed in 1889.....	6
Initial daily production of new wells (barrels).....	76
Number of rigs building December 31, 1888.....	2
Number of rigs building December 31, 1889.....	1
Number of wells drilling December 31, 1888.....	3
Number of wells drilling December 31, 1889.....	2
Value of materials used in caring for and operating wells in 1889.....	\$51, 680

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$2, 186, 958
Number of acres of oil land owned.....	10, 607
Present value of land.....	1, 060, 000
Average value per acre, \$100.....	<hr/>
Value of rigs, wells, engines, boilers, etc.....	\$840, 164
Value of tanks.....	11, 250
Value of tank cars.....	40, 000
Value of pipe lines at wells owned by parties making report.....	61, 257
Value of oil in stock at wells December 31, 1889.....	4, 036
Value of other property and improvements.....	170, 251
	<hr/>
Total.....	1, 126, 958

Labor and Wages.

All labor, not including office force:	
Number of foremen or overseers.....	5
Total wages paid all workmen of this class in 1889.....	\$8, 000
Number of mechanics.....	25
Total wages paid all workmen of this class in 1889.....	18, 147
Number of laborers.....	62
Total wages paid all workmen of this class in 1889.....	46, 284

Office force:

Total number (males)	3	
Total wages paid (males)		\$2, 625
Total number of persons employed and wages paid in 1889	95	75, 056

Wages paid for labor:

In building rigs	3, 195
In drilling wells	20, 131
In operating and caring for wells	49, 055
In building or repairing tankage	50
In office	2, 625
Total	75, 056

Classified wages.

Class of labor.	Number of each class.	Range of wages.
Foremen	6	\$100 to \$200 per month.
Pumpers or engineers	9	\$65 to \$80 per month.
Carpenters	7	\$3 to \$4 per day.
Drillers	18	Do.
Laborers	58	\$1.50 to \$3 per day.
Sundry mechanics	2	\$2.50 to \$4 per day.

INDIANA.

Although reports of the discovery of oil in Indiana were rife in 1889, the only production in this State concerning which statistics have been secured was at Terre Haute, in Vigo county, and at Montpelier, Blackford county. The notable developments in Indiana have all been subsequent to that year.

On May 6, 1889, oil was struck in the Diall well at Terre Haute. The flow was estimated at 1,000 barrels per day, but its production rapidly declined, the total production for the eight months after the well was struck being but 30,000 barrels, an average for the entire time of 3,750 barrels a month, or about 125 a day. At the close of the year it was estimated that the production did not exceed 75 barrels a day. The excitement following this find, which was in some respects unlucky, was intense. Company after company was formed, and over \$60,000 was expended in exploiting for oil. Up to the close of the year only one producing well in addition to the Diall had been struck. This was a small producer, rated at first as a 50-barrel well, but averaging in December only 15 barrels a day. The oil in these wells is found in the upper part of the Hamilton limestone at a depth of 1,615 feet. The other locality in which oil was found in 1889 was in Montpelier, Blackford county. During that year two wells were drilled at this point. The well drilled by the citizens of the place as a company was intended to demonstrate the presence of oil or gas, and, finding oil, the well was plugged and as late as April, 1891, no use had been made of the product. A

well was also drilled at the same place by a firm composed of residents of Montpelier and some oil was secured. The production in 1889, however, was very small. This product is used on the spot for burning under a boiler at a stone quarry, and occasionally a tank car is sold to one of the fuel companies. In this case the price of Lima crude controls the market. The oil is of a dark color, is supposed to be a limestone oil, but has not the sulphurous odor peculiar to the limestone oil from Lima. At the close of the year developments were being pursued in this district with good prospects of securing a supply of oil. Some interest was also being taken in a territory at Keystone, Wells county, 3 miles north of Montpelier, in a section which it was assumed was a continuation of the Montpelier district, and in 1890 some wells were struck and the district gave great promise of becoming an important one in the future.

At Dundee, Madison county, about 6 miles west of Montpelier, and at Bryant, southeast of Montpelier, there are also indications of oil. This whole territory can be named the Montpelier district, from the point at which oil was first struck.

The statistics of the production of petroleum in Indiana in 1889 are given as follows:

Total production and value in 1889 and 1890.

	1889.	1890.
Total production (barrels of 42 gallons)	33,375	63,496
Total value at wells of all oil produced, excluding pipage.....	\$10,881	\$32,462
Value per barrel	\$0.32½	\$0.51½

The stock on hand at the wells December 31, 1889, was 12,250 barrels of fuel oil.

Well record.

Total number of producing wells December 31, 1889.....	3
Total number of flowing wells December 31, 1889	3
Number of wells completed in 1889	3
Number of producing wells completed in 1889.....	3
Initial daily production of new wells (barrels).....	1,135
Number of rigs building December 31, 1888	1
Value of materials used in pumping, caring for, and operating wells in 1889	\$15,777

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	(a)\$49,918
Number of acres of oil land leased	12,585
Present value of land.....	5,528
<hr/>	
Average value per acre, \$0.44.	

^a In addition to the above, information has been received of the expenditure of \$54,874 in the drilling of 17 wells in Vigo county, all of which were dry holes. Of this amount \$51,524 is reported as absolutely lost.

Value of rigs, wells, engines, boilers, etc	\$15, 650
Value of tanks	10, 335
Value of tank cars	5, 800
Value of pipe lines at wells owned by parties making report	2, 130
Value of oil in stock at wells December 31, 1889.....	4, 075
Value of other property and improvements	6, 400
Total	44, 390

Labor and wages.

All labor, not including office force:

Number of foremen or overseers	1	
Total wages paid all workmen of this class in 1889		\$1, 200
Number of mechanics	7	
Total wages paid all workmen of this class in 1889.....		725
Number of laborers	25	
Total wages paid all workmen of this class in 1889		4, 105

Office force:

Total number (males)	1	
Total wages paid (males).....		50

Total number of persons employed and wages paid in 1889.	34	6, 080
--	----	--------

Wages paid for labor:

In building rigs	\$125
In drilling wells	600
In operating and caring for wells.....	5, 305
In office	50

Total	6, 080
-------------	--------

Classified wages.

Class of labor.	Number of each class.	Range of wages.	Days employed.
Foremen	1	\$150 per month	240
Rig builders	3	\$125 per rig	
Drillers	4	60 cents per foot	
Laborers	1	\$25 per month	
Sundry mechanics	22	\$75 per month	

KENTUCKY.

The only petroleum produced in Kentucky in 1889 was from the Boyds Creek district, in Barren county, some 3.5 miles from Glasgow. From January to August five wells were operated in this district, and six from August to the close of the year. Some 5,400 barrels were produced, which were distilled (it could hardly be called refined) by the operator in a still near the wells, and the distillates sent to Louisville to be refined. The naphtha and residuum were also shipped to the Louisville refinery.

Near Somerset, Pulaski county, oil was struck about 85 feet below the surface. The oil sand was drilled into to a depth of 45 feet,

and it was in this rock that the oil was procured. Just before boring this well the same operators bored another at a point 4 or 5 miles north-east, in which the same oil-bearing rock was struck near the surface; there was, however, barely a showing of oil. The results obtained in drilling these wells convinced the operators that the dip of the oil-bearing sand rock was in a southwesterly direction, and their opinion is substantiated by the fact that many years ago some wells were developed at a point 40 miles southwest of the second well referred to. The well first referred to was plugged after some 3 or 4 barrels had been obtained, the operators concluding that to obtain oil in paying quantities they would have to go farther southwest.

This oil has been tested by Prof. W. Dicore, of Cincinnati, Ohio. It shows a specific gravity of 0.870 of 43½° B., and on distillation 5 per cent. of light oil boiling below 130° F., 18 per cent. of light oil boiling at from 130° to 300° F., and 34 per cent. of illuminant of 48° gravity B. After these are taken off a lubricating oil of 28° B. is obtained, which, on further heating, yields oil of 39° B., out of which 17 per cent. of heavy lamp oil of 43° can be produced, increasing the total of lamp oil to 51 per cent. The remainder is a lubricating oil (of a consistency like linseed oil) of 22° B., flashing at 330° F. The color of the crude oil is a greenish brown, and the odor not more offensive than that of well purified gasoline. There is no sediment or inorganic substance, nor a separation of the higher hydrocarbons after long standing.

In Russell county some 15 or 16 years ago (1874) a refinery was operated by some parties who also had a well at the same location, but during their operations there was a great depression in the price of oil, and, coupled with the burning of their tank and the fact that they had no means of transporting their product, except in wagons for a long distance in order to reach railway transportation, they could not make the continued operation of their well profitable. It was therefore abandoned and the well plugged. The oil is still there and can be seen seeping from the hole, and is of the same character as the oil found near Somerset. About the same time that this refinery and well were operated in Russell county there were some wells bored in Cumberland county, which adjoins Russell county, but they were also abandoned about the same time that the Russell county operators ceased, and for similar reasons, namely, lack of transportation facilities and depression in the price of oil. Early in 1890 there was one well being drilled in Cumberland county and three rigs in course of construction for the purpose of further development, and it was said that there would be ten or twelve rigs at work in this and Russell counties during the earlier months of that year. Natural gas in considerable volume was struck early in January, 1890, in Cumberland county, but was cased off, since the operators wished to continue drilling for the purpose of finding oil, for which there was every prospect of success.

Wayne county also had producing oil wells in former years, which

likewise were abandoned for the lack of transportation and the failure of the company prosecuting the development.

In all there are upward of 70,000 acres of land under lease for oil purposes in Pulaski, Wayne, Russell, Clinton, and Cumberland counties, to which that under lease in Barren county should be added. Operations are being energetically pushed in Barren county, which lies west of Russell and Cumberland counties, and a refinery was being erected near Glasgow late in 1889. Wells completed in this county, however, were not found to exceed 15 barrels daily production.

A little heavy, dark oil, with weak brine, has been found at a depth of 70 feet near Lexington, in the Trenton rock. Near North Middletown, Bourbon county, a well in the Lower Hudson 98 feet deep yielded in 1888, 100 gallons of good lubricating oil per week. The oil is black, and has a gravity of 23.5° B.

The statistics of the production of petroleum in Kentucky in 1889 and 1890 are as follows:

Total production and value.

	1889.	1890.
Total production (barrels of 42 gallons)	5,400	6,000
Total value at wells of all oil produced, excluding pipage.....	\$5,400	\$6,000
Value per barrel.....	\$1	\$1

No stock is reported on hand December 31, 1888 and 1889.

Well record.

Total number of producing wells December 31, 1888	5
Total number of producing wells December 31, 1889	6
Number of pumping wells December 31, 1888	5
Number of pumping wells December 31, 1889	6
Number of wells completed in 1889.....	3
Number of dry holes in 1889	1
Number of producing wells completed in 1889	2
Initial daily production of new wells (barrels)	7
Value of materials used in caring for and operating wells in 1889.....	\$3,050

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$25,000
Number of acres of oil land:	
Owned	100
Leased	51,500
Total acreage.....	51,600
Present value of land, both owned and leased (actual expenditures on same for oil purposes).....	10,150
Average value per acre, \$0.20.....	<u>2,000</u>
Value of rigs, wells, engines, boilers, etc.....	<u>9,000</u>

Value of tanks	\$750
Value of tank cars.....	1,800
Value of pipe lines at wells owned by parties making report	200
Value of other property and improvements.....	3,100
Total.....	14,850

Labor and wages.

All labor, not including office force:	
Number of foremen or overseers.....	2
Total wages paid all workmen of this class in 1889.....	\$1,248
Number of mechanics.....	8
Total wages paid all workmen of this class in 1889.....	660
Number of laborers.....	4
Total wages paid all workmen of this class in 1889.....	1,142
Total number of persons employed and wages paid in 1889....	14 3,050
Wages paid for labor:	
In building rigs.....	\$200
In drilling wells (part contract).....	1,650
In operating and caring for wells.....	1,200
Total.....	3,050

Classified wages.

Class of labor.	Number of each class.	Range of wages.	Days employed.
Foremen	2	\$52.50 to \$70 per month	50 to 313
Pumpers or engineers.....	4	\$24 to \$30 per month	50 to 313
Rig builders.....	2	\$1 per day	20
Drillers	4	60 cents per foot	40
Tool dressers.....	2	\$1.75 per day.....	40
Laborers	2	90 cents to \$1 per day	Various.

ILLINOIS.

The only oil produced in Illinois in 1889 was from some wells near Litchfield, in Montgomery county. The oil is a lubricating one, dark, almost black in color, and of 22° B. specific gravity. The cold test is remarkable, the oil remaining fluid at 20° below zero, Fahrenheit. It is largely used by the factories in the neighborhood of Litchfield, and is sold to consumers at near-by points for lubricating purposes, bringing from 8 to 10 cents per gallon in bulk, according to quantity. In all there have been thirty wells bored in the neighborhood of Litchfield, chiefly for gas. The depth of these wells ranges from 640 to 670 feet. All save five were abandoned years ago. These five wells continue to produce the character of petroleum mentioned above. The average production of these wells is about 4 barrels per day. They are pumped by heads, and one man attends to them all. Natural gas from wells near by is used to some extent in furnishing fuel for pumping the wells. The supply of gas is about equal to 12 tons of coal a year, and 12

tons additional are used in pumping. The supply of natural gas is gradually diminishing.

The statistics of the production of petroleum in Illinois in 1889 are as follows:

Total production and value.

Total production in 1889 (barrels of 42 gallons).....	1,460
Total value at wells of all oil produced, excluding pipage.....	\$4,996
Value per barrel.....	\$3.36

Stocks of oil on hand at wells.

	Barrels.
December 31, 1888.....	110
December 31, 1889.....	100

Well record.

Total number of producing wells December 31, 1888.....	5
Total number of producing wells December 31, 1889.....	5
Total number of pumping wells December 31, 1888.....	5
Total number of pumping wells December 31, 1889.....	5
Value of materials used in pumping, operating, and caring for wells in 1889.....	\$760

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business.....	\$12,336
Number of acres of oil land:	
Owned.....	20
Leased.....	5,000
Total acreage.....	5,020
Present value of land, both owned and leased.....	2,600
Average value per acre, \$0.52.	
Value of rigs, wells, engines, boilers, etc.....	9,000
Value of tanks.....	250
Value of pipe lines at wells owned by parties making report.....	150
Value of oil in stock at wells December 31, 1889.....	336
Total.....	9,736

Labor and wages.

Total number of persons employed in 1889.....	1
Total wages paid all workmen.....	a \$600

One engineer or pumper was employed 365 days, at \$50 per month.

a Paid for operating and caring for wells.

KANSAS.

The only section of Kansas in which oil has been found in what may be termed paying quantities, and even here the production is very small, is in Miami county, near Paola. In this county "tar" or oil springs have been known to exist from the earliest settlement of the State. One of these springs, some 8 miles east of the town of Paola, has led to the drilling of a number of wells in search of oil during the past thirty years. As early as 1858 leases were obtained and there was considerable talk of developing the oil field here. In 1861 a well was drilled 5 miles east of Paola, in which it is reported that oil was found, but the well filled with water, soon caved in, and no oil in commercial quantities was produced. Another well was started 2 miles east of Paola in the same year, but was abandoned before the oil rock was reached.

In a report made by Prof. Mudge, in 1864, he refers to the existence of oil and bitumen in the eastern tiers of counties of the State. In Prof. Swallow's report of 1865 he makes reference to 19 different tar springs within Miami county, and adds that "scarcely a well has been dug without finding petroleum in some of its forms." Prof. Swallow concludes that these facts are "very strong evidence of the existence of large reservoirs in these localities." Although large reservoirs of oil or gas may be found, as Prof. Swallow predicted, yet the facts which he presents in themselves are not necessarily sufficient to warrant such a conclusion. In 1865 a St. Louis company drilled 2 wells about 10 miles east of Paola. These wells were reported to have been drilled to a depth of 700 feet, when the tools were lost. In 1873 a company was organized, known as the Kansas Mining Company, and the same year drilled a well on the northeast quarter of section 16, township 19, range 24 (Westfall farm), near one of the largest of the "tar springs." At a depth of 320 feet a strong flow of gas was found and work stopped. Other gas wells were soon drilled on the same farm and gas was piped to Paola, a distance of 7 miles, by the Paola Gas Company. In 1888 one of the wells on the Westfall farm was drilled deeper, and it was found that under the gas rock there was an oil rock 12 to 16 feet thick, producing a very heavy black oil. This well bailed from 1 to 2 barrels per day. As the oil interfered with the gas, for which the well was drilled, it was plugged off at the bottom of the gas rock and the well turned again into the gas main. It was soon ascertained, however, that the oil was of such value as a lubricant that wells of 1 or 2 barrels per day could be worked at a profit, and the Paola Gas and Land Company purchased the property of the Paola Gas Company, and prospecting for oil began in the spring of 1889. The first well of recent years, drilled especially for oil, was put down in May, 1889, on the northwest quarter of section 16, township 17, range 24, and at a depth of 330 feet a good oil sand was struck, the gas sand lying at 316 and 328 feet and the oil sand at 330 to 341 feet. This well, known as No. 29, was shot with

10 quarts of nitroglycerin, and when cleaned out the gas shot a stream of oil to the top of the derrick. The well was tubed, the casing head packed, and the oil flowed by the gas. This well at first produced 15 barrels per day for 4 months.

In the fall of 1889 and spring of 1890, 4 wells were drilled by the same company 3 miles southwest of Paola, and the oil rock struck at about the same level as in the eastern field, but the rock was much harder and the oil much lighter. The west field has a much stronger head and promises a much larger yield than the east field.

There are at least three districts near Paola. The first is Russell tract, or Westfall farm, about 7 miles east of Paola and 2 miles from Somerset station, on the Missouri Pacific railroad; the others are nearer Paola, one being, as stated, 3 miles southwest, and the other just at the edge of the town. As above noted, gas was at first the object of the recent drilling near Paola. Well No. 1, in Russell tract, was bored for gas in 1882. Since that time 56 wells have been drilled by the Paola Oil, Gas and Mining Company and its predecessors. As stated above, it was not until 1888 that wells began to be drilled for oil. The Russell tract is now one of value as an oil producer, the pressure of the gas not being strong enough to force it through the 2½ inch pipe laid from Russell to Paola, a distance of 7 miles. Thirteen wells are now (1890) producing oil.

The structural geological conditions of Kansas when viewed by themselves are favorable to the existence of natural gas and oil. The rocks underlying Kansas are comparatively horizontal, the general dip being toward the west and northwest. The highest geological strata in eastern Kansas is the Carboniferous, while westwardly higher formations are found. Going from the northern toward the southern portion of the the State, within the Coal Measure area, the strata thicken, as the records of the oil and salt wells in Miami county seem to prove. The best oil well in this district, No. 39, drilled in May, 1889, has the following record:

Record of petroleum well in Miami county, Kansas.

	Feet.
Cased to.....	280
Soapstone.....	20
Sandy shale.....	11
White slate.....	3
Gas sand (very good).....	10
White slate.....	4
Oil sand.....	13
Total.....	341

The sand in which the oil is found is stated to be "identical with Bradford in appearance." It certainly has that look of light-colored coarse maple sugar that is seen in the Bradford sand when filled with oil. The oil itself is a heavy, black, fatty substance of remarkable lubricating

properties. A test taken by the writer on the afternoon of May 7, 1891, temperature 70° F., showed the gravity to be 23½° B., zero cold test, and 280° fire test. This refers to the oil in the Russell tract, or from the Westfall farm. That from the district 3 miles southwest of Paola is much lighter, having a gravity of 30°, zero cold test, 100° fire test, and not so densely black as the oil in the eastern field. The oil contains none of the lighter hydrocarbons; even at 300° F. nothing distilled over. A little water remains obstinately entangled in the oil, which at that temperature produces frothing to such a degree as to interrupt further distillation. Even in some cases the temperature of the retort has been carried to 400° F. without the production of a drop of distillate. As stated above, the quality of this oil as a lubricant is phenomenal. Without the least artificial preparation it has given some remarkable results as a lubricant under the most severe tests, especially on railroads running through the alkali country.

While the foregoing statements apply chiefly to the oil produced in Miami county, near Paola, oil has been found in other portions of the State apparently on the same general degree line as at Paola. These discoveries of oil have been made chiefly when boring for natural gas.

In Kansas City, Kansas, oil was struck when boring for natural gas, usually at a depth of from 300 to 400 feet. As natural gas was the product sought in drilling the wells, and as it was difficult to market the oil, which was produced in small quantities, at satisfactory prices, the wells were allowed to drown out in most cases when it was found that they did not produce sufficient natural gas to pay for operating them.

The record of a well bored in Kansas City is as follows:

Record of a well bored at Kansas City, Kansas, for natural gas in 1889.

[Feet.]

Strata.	Thickness of each stratum.	Total depth.	Strata.	Thickness of each stratum.	Total depth.
Loam and clay.....	14.0	14.0	Shale	25.0	180.0
Limestone	19.0	33.0	Limestone	15.0	195.0
Shale	30.0	63.0	Shale	18.0	213.0
Limestone	12.0	75.0	Limestone	10.0	223.0
Shale	5.0	80.0	Shale	170.0	393.0
Limestone	20.0	100.0	Limestone	5.0	398.0
Shale	5.0	105.0	Shale	38.0	436.0
Limestone	10.0	115.0	Limestone	4.0	440.0
Shale	30.0	145.0	Black shale	26.0	466.0
Flint	10.0	155.0	Sand rock	16.8	482.8

Oil was struck at a little over 400 feet; gas from 266 to 476 feet; hard, close sand from 476 to 480 feet; gas from 480 to 482.8 feet.

At Fort Scott, Kansas, oil was found in 2 or 3 wells when drilling for natural gas. Its character seemed to be the same as that of the Paola oil. As the quantity of gas was insufficient to pay for operating the wells they were abandoned. At Wyandotte and Coffeyville oil has

been found under similar conditions to those existing at Paola, but no attempt has been made to save the same.

It has been extremely difficult to secure statistics of the production of oil in Kansas for 1889, as no record was kept. The best information received indicates that there were three wells producing oil December 31, 1889, at Paola, the production for that year being about 300 barrels, valued at \$1,500. Nearly the entire amount of this oil remained on hand at the close of the year, little or no product having been sold. A small amount of oil, some 200 barrels, was also produced in Kansas City from wells drilled for gas. This was also lubricating oil of about the same quality as that produced in Paola. The statistics of the production of petroleum in Kansas in 1889 and 1890 are as follows:

Total production and value in 1889 and 1890.

	1889.	1890.
Total production (barrels of 42 gallons)	500	1,200
Total value at wells of all oil produced, excluding pipage.....	\$2,500	\$8,400
Value per barrel.....	\$5	\$7

Stocks of oil on hand at wells.

	Barrels.
December 31, 1888	100
December 31, 1889	100

Well record.

Total number of producing wells December 31, 1888.....	4
Total number of producing wells December 31, 1889.....	4
Total number of pumping wells December 31, 1888.....	4
Total number of pumping wells December 31, 1889.....	4
Number of rigs building December 31, 1889.....	2
Value of material used in pumping, caring for, and operating wells in 1889.....	\$500

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business	\$75,000
Number of acres of oil land leased	4,000
Present value of land	40,000
<hr/>	
Average value per acre, \$10.	
Value of rigs, wells, engines, boilers, etc.....	25,000
Value of tanks.....	2,500
Value of pipe lines at wells owned by parties making report	3,000
Value of oil in stock at wells December 31, 1889.....	500
Value of other property and improvements	4,000
<hr/>	
Total	35,000

Labor and wages.

All labor, not including office force:

Number of mechanics.....	2	
Total wages paid all workmen of this class in 1889.....		\$1,000
Number of laborers.....	6	
Total wages paid all workmen of this class in 1889.....		2,500

Office force:

Total number (males).....	2	
Total wages paid (males).....		2,500

Total number of persons employed and wages paid in 1889....	10	6,000
---	----	-------

Wages paid for labor:

In building rigs.....	\$300
In operating and caring for wells.....	3,000
In building or repairing tankage.....	100
In building and repairing pipe lines.....	100
In office.....	2,500
Total.....	6,000

Classified wages.

Class of labor.	Number of each class.	Range of wages (per day).	Days employed.
Pumpers or engineers.....	1	\$1.50	All.
Carpenters.....	1	2.50	200
Rig builders.....	1	2.50	100
Drillers.....	2	3.50	250
Tool dressers.....	2	2.00	250
Laborers.....	2	1.25	300

T E X A S .

Similar conditions to those found in Kansas, New Mexico, and the southern part of California exist in Texas. Springs, known locally as tar springs, are found scattered over various portions of the State, especially in the northeast, southeast, and central portions. The oil wells of Kansas and Missouri are found a little east of the ninety-fifth meridian of longitude west of Greenwich. The Texas springs are a little to the east of the ninety-fourth meridian, and some are also found on the ninety-third and east of it. The petroleum produced in Texas in 1889 was in Bexar county, near San Antonio, about midway between the ninety-eighth and ninety-ninth meridians. The product of these springs is known locally as petroleum, and is in this report so classified, though some geologists, especially those who have been connected with the geological survey of California, insist on calling it maltha. At present, however, they acknowledge that this so-called maltha and petroleum are similar substances. Chemically they may be; practically they are not.

The Texas oil is a natural lubricator of from 28° to 30° gravity, and is said to be found in a conglomerate. The wells are shallow, the oil being struck in various parts of the State at from 125 to 350 feet. The Bexar county wells, which produced the petroleum reported upon from this State in 1889, are about 300 feet deep. As there is but a limited demand for the oil, there is no effort to produce it in large quantities. The 2 wells producing in 1889, which were on the ranch of Mr. George Dulnig, were wells that had been drilled originally for procuring water. They were found to yield small quantities of oil and gas. The production of these 2 wells in 1889 was about 4 barrels a month.

Outside of the oil produced in Bexar county none seems to have been produced in the State on a commercial scale, though reports as to the discovery of oil at various points in Texas are frequent. At Sulphur Springs, in Hopkins county, there are certain so-called "sour wells," which produced a few gallons of oil. In 1887 and 1888 considerable excitement was occasioned by the reported striking of oil in Nacogdoches county. The locality was some 80 miles southwest of Shreveport. The wells were driven wells, and some oil was obtained at the depth of 85 feet; in other cases at a depth of 300 feet. Quite a number of wells were driven in 1887 and 1888, but no petroleum was produced in 1889. The oil produced in Bexar county was used for lubrication. It retailed in barrels at 20 cents a gallon, in tin cans of 5 gallons at 30 cents, and in smaller quantities than 5 gallons at 35 cents a gallon.

The statistics of the production of petroleum in Texas in 1889 and 1890 are as follows:

Total production and value in 1889 and 1890.

	1889.	1890.
Total production (barrels of 42 gallons).....	48	54
Total value at wells of all oil produced, excluding pipage.....	\$340.00	\$227.00
Value per barrel.....	7.08 $\frac{2}{3}$	4.20

Stocks of oil on hand at wells.

	Barrels.
December 31, 1888	6
December 31, 1889	48

Well record.

Total number of producing wells December 31, 1888	2
Total number of producing wells December 31, 1889	2
Total number of pumping wells December 31, 1888	2
Total number of pumping wells December 31, 1889	2

Capital.

Total capital invested in wells, (a) leases, etc., and employed in the business.	\$1,650
Value of rigs, wells, engines, boilers, etc.....	1,200
Value of tanks.....	100
Value of pipe lines at wells owned by party making report	10
Value of oil in stock at wells December 31, 1889.....	340
Total.....	1,650

The work is all done by ranch hands; no special men are employed, the production of the wells being but 4 barrels per month.

MISSOURI.

The only oil produced in Missouri in 1889 and 1890 concerning which it has been possible to secure any information was in West Boone township, Bates county, near the Kansas State line, southwest from Paola, where the oil produced in Kansas in 1889 was found. This oil was all produced from 1 well, drilled in 1886 for water. The oil comes from sand 220 feet in depth. It is similar in every respect to the Kansas oil. The well is pumped by a windmill and yields less than 1 barrel a day. The oil is sold to local trade for lubricating purposes. In 1889, 20 barrels of oil, valued at \$40, were produced. All oil is sold as soon as produced. The cost of operating the well in 1889 was \$350; the total capital, \$750. The territory consists of 600 acres of land, valued, as oil territory, at \$210, the rigs, wells, engines, etc., being valued at \$520 and tank at \$20. There was but 1 producing well and 1 tank. The cost of drilling the well was \$1.50 a foot.

There is an interesting history connected with the drilling of some wells at Adrian, Bates county, Missouri. Oil was discovered here in 1889 at a depth of 33 feet while prospecting for coal. The oil sand was some 25 feet thick, overlaid with soapstone shale to a thickness of 8 feet. The oil oozed from the rock into the shaft and was bailed out. The shaft was in the creek bottom, and being flooded by the first high water the well ceased to produce. A number of drill holes were then put down. Three of these produced about 6 gallons in ten hours, but the holes were not cased, and they were soon drained out by water. In 1883 a derrick was erected, proper oil tools procured, and a well sunk over 500 feet. All the oil secured in this well was found at from 33 to 90 feet in depth. The well was pumped but once, and then only for ten hours, the product being 20 gallons of oil, with a large quantity of water. The oil is similar in character to that found at Paola.

Mr. R. B. Marshall, of Adrian, states that he has done a great deal of prospecting for oil in that section of the country, and finds a strip

^a These wells are sunk on the ranch of the owner, and no value is placed on the land as oil territory.

of territory some 10 miles long and from 1 to 3 miles wide underlaid with gas and oil, but that the difficulty with the region as a producing territory is that the sand is too fine and the oil too thick to give any great production. There is a great deal of sand rock impregnated with oil which can be driven out by heat. The statistics of the production of petroleum in Missouri in 1889 and 1890 are as follows:

Total production and value in 1889 and 1890.

	1889.	1890.
Total production (barrels of 42 gallons)	20	278
Total value at wells of all oil produced, excluding pipage.....	\$40	\$556
Value per barrel.....	\$2	\$2

No stock was reported on hand at the wells December 31, 1888 and 1889.

Well record.

Total number of producing wells December 31, 1888	1
Total number of producing wells December 31, 1889	1
Total number of pumping wells December 31, 1888.....	1
Total number of pumping wells December 31, 1889.....	1
Value of materials used in pumping, operating, and caring for wells in 1889..	\$5

Capital.

Total capital (real and personal) invested in lands, wells, leases, etc., and employed in the business	\$750
Number of acres of oil land owned	600
Present value of land as oil territory	\$210
Average value per acre, \$0.35.	
Value of rigs, wells, engines, boilers, etc.....	\$520
Value of tanks.....	20
Total.....	540

Labor and wages.

Total number of persons employed in 1889.....	1
Total wages paid all workmen.....	(a) \$350

T E N N E S S E E .

At a point about 8 miles north of White Bluff, in Dickson county, Tennessee, on Jones creek, oil has been known to exist since 1865. It is said seven wells have been drilled at this place by different parties some of them being shallow and the deepest well being upwards of 2,000 feet deep. There was but one actually dry hole, and that was abandoned at 640 feet. The shallow wells produced oil in small quantities at a depth of 187 feet. Two wells have been cased and have

a Paid for operating and caring for wells.

small quantities of oil in them, but since there is no market for crude oil in this State or immediate vicinity, wells have been neglected and no attention paid to its development. The product is not utilized except to a small extent for lubricating purposes. It is firmly maintained by residents there that oil can be found in remunerative quantities.

Oil is generally found at an average depth of 150 feet, in a sandstone of 20 feet in thickness. Gas and salt water are also found.

A L A B A M A .

Though no oil was produced in Alabama during the census year, still, in view of the fact that drilling was recommenced in 1890, some account is given of the history of oil production in this State and the prospects of future production.

In various parts of northern Alabama there are found springs which yield natural gas and petroleum to a limited extent, though as yet these products have not been found in sufficient quantities to be of any commercial value. There are also found in the same section in the outcroppings of the Carboniferous formations "tar" springs somewhat similar to those of California, from which there exudes a thin bitumen, known as "maltha." Shortly after the beginning of the petroleum excitement in Pennsylvania in 1859 many wells were drilled at points indicated by these natural gas and petroleum and tar springs. Some oil was found, but not in sufficient quantities to justify the continuance of operations.

The best known of the Alabama tar springs are just outside of Moulton valley. These springs are in the outcroppings of a very highly fossiliferous, coarse-grained, siliceous limestone that has a cover of reddish and greenish argillaceous shales. Near the lower of the two springs is a well said to have been drilled for oil some years ago to a depth of 106 to 107 feet. The Goyer Oil Company, of Memphis, Tennessee, proposes to put down wells near these springs. At present (June, 1891), two wells have been completed, in one of which a dark-green oil was found at a depth of 1,509 feet. The first oil secured in small quantities was at the top of the Trenton limestone, at a depth of 1,355 feet. This well was computed by Dr. McRae to be a 25-barrel well. The second oil sand, from which most of the oil came, is believed by Mr. Henry McCalley to be some 300 feet down in the Trenton limestone, or some 200 feet lower geologically than any known productive oil sand in this country.

Oil wells are to be drilled in other parts of the State.

W Y O M I N G .

Though oil has been known to exist in Wyoming for more than thirty years and though developments made in 1885 and since point to the presence of valuable oil deposits in this region, the oil industry has

assumed, as yet, no importance, owing chiefly to the distance of the producing territory from any important market and the expense of transportation thereto. The developments of importance have been confined chiefly to two districts, one known as the "George B. Graff Oil-Mining district," in the county of Fremont, in the western part of the State, not far from Dallas, and at the base of the Wind River mountain, and the other known as the "Stockdale Oil-Mining district," in Weston county, in the extreme northeastern part of the State, near the Black Hills and New Castle. The first district, the "George B. Graff," is named for the late Dr. George B. Graff, of Omaha, who developed the property. The amount of oil in this district is indicated from the fact that there are about 50 open oil springs in Fremont county, 14 within a radius of 20 miles of Lander. In 1885 four wells were sunk to the upper oil-bearing sands. The depth of these wells and their product as given at that time are as follows:

Depth and flow of Wyoming oil wells.

Wells.	Depth.	Flow per day.
	<i>Feet.</i>	<i>Barrels.</i>
No. 1	85	85
No. 2	100	100
No. 3	350	325
No. 4	1,200	825
Total		1,335

It is probable the production of some of these wells as given is too great. Several statements received from this district are to the effect that three of the wells which were drilled about this time were shut in or "packed" with Hodley packers; that if they were allowed to flow, or (to use the local expression) "let loose," they would produce some 200 barrels per day per well; and that in the neighborhood of these wells a lake, 300 yards long by 30 yards wide, was made to receive their overflow, and it is estimated that in this lake there are now some 15,000 barrels that were produced as long ago as 1886. Nothing has been done in the way of development or production in this district since this date. Regarding this oil field, Mr. L. D. Ricketts, Territorial geologist, states: "These wells are cased and supplied with valves to prevent the oil from escaping, but, owing to the great gas pressure, a leakage can not be prevented. The pressure is so great that upon suddenly opening the valves the oil spurts up 75 feet into the air, like some black-watered geyser. After the pipe thus clears itself the steady flow of oil is resumed, which, as variously estimated, will aggregate from 600 to 1,000 barrels per 24 hours." The oil is found in two strata, the upper a "black sand," averaging about 70 feet in thickness, and the other is a "black pebble" or "dark conglomerate," varying in thickness, according to different authorities, from 400 to 800 feet. The oil in this district

is low in illuminants, averaging about 25 per cent. It is proposed, and a company has been organized for the purpose, to pipe the oil to Denver, 250 miles distant, and to sell it for fuel.

Regarding the second district, the "Stockade Oil-Mining district," which is located in the Black Hills, near New Castle, in Weston county, but little information has been obtained. A large quantity of Government land, supposed to contain oil, has been located in this district. A list of some 376 locations of 160 acres each, amounting to 60,160 acres, has been furnished the census special agent. This land, at the Government price of \$2.50 an acre, would be valued at \$150,400. In order to hold these leases \$200 worth of improvements must be put upon the land. If all of the claims were finally taken up this would add \$75,200 to the value of the land entered as oil land in this district. It is known, however, that in many cases the claims have been abandoned. So far as has been learned, no amount of oil has ever been produced in this district, though indications are very favorable to the securing of a large supply.

NEW MEXICO.

Information has been received of a very small production of a heavy lubricating oil in Bernalillo county, on section 11, township 16 north, range 16 west. This oil flows naturally from the rocks containing it. The product is stated to be a barrel a day, which is probably in excess of the actual production. It is sold in small quantities to consumers in the immediate vicinity at the rate of \$10 a barrel. The larger proportion of the production is wasted and lost. It is also reported that there are several places on the Navajo Indian reservation where petroleum exudes in a similar manner from the crevices in bituminous sandstone, and there is no doubt that at many places in New Mexico the same phenomena that are noticed in Colorado and Wyoming will be found to exist.

NATURAL GAS.

BY JOSEPH D. WEEKS.

Previous to the investigation into the production of natural gas by the Eleventh Census no attempt had been made to determine the volume of this fuel produced or consumed. The want of meters to measure the gas, the methods of use, and the profligate waste which characterized the early utilization of what is now known to be a valuable product, rendered even an approximate estimate of the amount utilized impossible. This waste has been checked, more economic methods have been adopted, and meters have been invented that give approximately correct measurements. That the supply of gas is limited and will ultimately be exhausted has never been questioned. There is no accurate method of estimating how great a store of this product we have to draw upon, and even when we are able approximately to determine how much is being consumed, it is impossible to say how long it will last at the same rate of consumption. During 1889, according to the census report, the total consumption of natural gas in the United States was 552,150,000,000 cubic feet. This figure is of course but an estimate, but must be taken as the best approximation possible. The distribution of this consumption by industries is ascertained to be about as follows:

Total consumption of natural gas in the United States in 1889.

	Cubic feet.
Iron and steel mills.....	171,500,000,000
Glass works.....	18,750,000,000
Other industrial establishments.....	236,900,000,000
Heating and cooking.....	62,500,000,000
Pumping oil.....	7,500,000,000
Drilling and operating oil and gas wells.....	30,000,000,000
Other uses.....	25,000,000,000
Total.....	552,150,000,000

Value.—It has been found, in the preparation of previous volumes of Mineral Resources, that the best mode of arriving at the value of natural gas consumed is by estimating the value of coal displaced by its use. In 1889 the value of the gas consumed as actually returned is given at \$11,044,858. The value of fuel displacement, which is regarded as the actual value, was \$21,097,099. This includes 69,018 cords of wood

displaced in Ohio and Indiana, valued at \$165,040. The amount of coal displaced in the United States is placed at 10,198,930 tons, with a value of \$20,732,059. In 1890 the value of the displacement is given as \$18,667,725.

The following table, from Mineral Resources of the United States, 1888, gives the amount and value of coal displaced by natural gas from 1885 to 1888, inclusive, by principal gas-producing districts:

Amount and value of coal displaced by natural gas from 1885 to 1888.

Localities.	1885.		1886.	
	Coal displaced.	Value.	Coal displaced.	Value.
Pennsylvania:	<i>Short tons.</i>		<i>Short tons.</i>	
Allegheny county.....	2,000,000	\$2,500,000	4,000,000	\$5,000,000
Remainder of Pittsburg district..	500,000	750,000	1,000,000	1,500,000
Western Pennsylvania, outside of Pittsburg district.....	500,000	1,250,000	1,000,000	2,500,000
New York.....	56,000	196,000	60,000	210,000
Ohio.....	50,000	100,000	200,000	400,000
West Virginia.....	20,000	40,000	30,000	60,000
Indiana.....			150,000	300,000
Illinois.....	600	1,200	2,000	4,000
Kansas.....			2,000	6,000
Michigan.....			4,000	12,000
Elsewhere.....	5,000	20,000	5,000	20,000
Total.....	3,131,600	4,857,200	6,453,000	10,012,000

Localities.	1887.		1888.	
	Coal displaced.	Value.	Coal displaced.	Value.
Pennsylvania:	<i>Short tons.</i>		<i>Short tons.</i>	
Allegheny county.....	5,477,000	\$6,846,250	7,302,700	\$10,223,780
Remainder of Pittsburg district..	1,610,500	2,415,750	2,447,330	3,670,995
Western Pennsylvania, outside of Pittsburg district.....	1,795,500	4,487,500	2,693,800	5,387,600
Total Pennsylvania.....	8,883,000	13,749,500	12,443,830	19,282,375
New York.....	111,000	333,000	125,000	332,500
Ohio.....	500,000	1,000,000	750,000	1,500,000
West Virginia.....	60,000	120,000	60,000	120,000
Indiana.....	300,000	600,000	660,000	1,320,000
Elsewhere.....	5,000	15,000	25,000	75,000
Total.....	9,859,000	15,817,500	14,063,830	22,629,875

In the following tables are shown the amount and value of fuel displacement in 1889 and 1890, by States. In the statement for the former year is also shown the actual amount received by the companies for the gas consumed. The amount and value of the coal displaced by gas in 1890 was less than in 1889, but owing to the higher prices the amount actually received was probably fully \$1,250,000 more than in 1889.

Value of natural gas consumed in the United States in 1889, by States, and the amount and value of coal and wood displaced by the same.

States and Territories.	Value of natural gas supplied and used.	Coal displaced.		Wood displaced.	
		Tons.	Value.	Cords.	Value.
Pennsylvania	\$8,287,383	6,863,062	\$11,593,939		
Indiana	1,362,472	716,461	2,002,762	44,888	\$72,940
Ohio	1,120,997	1,660,456	5,123,569	24,130	92,100
New York	204,325	130,159	530,026		
Missouri	27,825	11,859	35,687		
Kansas	13,660	4,538	15,873		
California	12,680	3,517	12,680		
Illinois	8,658	7,245	10,615		
Kentucky	2,580	615	2,580		
West Virginia	2,000	600	2,000		
Texas	1,728	288	1,728		
Arkansas	375	107	375		
Utah	150	18	150		
South Dakota	25	5	25		
Total	11,044,858	9,398,930	19,332,059	69,018	165,040
Used at pipe lines		100,000	200,000		
Used for drilling and pumping wells		400,000	800,000		
Other uses		300,000	600,000		
Grand total	11,044,858	10,198,930	\$20,932,059	69,018	165,040

Amount and value of coal and wood displaced by natural gas consumed in the United States in 1890, by States.

States and Territories.	Coal displaced.		Wood displaced.	
	Tons.	Value.	Cords.	Value.
Pennsylvania	6,334,017	\$9,551,025		
Indiana	897,000	2,242,500	30,000	\$60,000
Ohio	1,573,100	4,619,300	20,000	65,000
New York	138,000	552,000		
Missouri	3,000	10,500		
Kansas	6,000	12,000		
California	5,500	33,000		
Illinois	4,000	6,000		
Kentucky	10,000	30,000		
West Virginia	1,800	5,400		
Texas	2,000	6,000		
Arkansas				
Utah				
South Dakota				
Total	8,974,417	17,067,725	50,000	125,000
Used at pipe lines	100,000	200,000		
Used for drilling and pumping wells	400,000	800,000		
Other uses	300,000	600,000		
Grand total	9,774,417	18,667,725	50,000	125,000

Pipe lines.—The total number of feet of pipe line used in the distribution of natural gas in the United States at the close of 1888 was 25,564,594, and at the close of 1889 was 37,746,093, divided into sizes as follows:

Total number of feet of pipe line used in the distribution of natural gas in the United States at the close of 1888 and 1889.

Sizes (inches).	1888.	1889.	Sizes (inches).	1888.	1889.
2	2, 201	3, 341	6	3, 308, 077	3, 866, 192
2½	907	7, 135	8	5, 167, 462	6, 979, 459
3	423, 764	886, 925	9	1, 405, 120	2, 141, 368
1	1, 157, 774	3, 039, 912	10		
1½	324, 938	730, 454	12	642, 900	1, 369, 613
2	632, 774	840, 226	14	643	643
2½	4, 987, 328	7, 222, 308	16	369, 252	480, 693
3	52, 360	53, 780	20	193, 780	205, 942
3½	3, 052, 615	4, 213, 230	24	106, 669	148, 056
4	8, 422	8, 422	30		
4½			36	83, 091	92, 971
5	3, 165, 590	4, 013, 883			
5½	294, 127	308, 434	Total.....	25, 564, 594	37, 746, 093
6	184, 800	233, 106			

The tendency is toward the use of larger pipes, as these will transport more gas with less loss by friction than smaller pipes.

The following statements taken from the report of the Eleventh Census show very clearly the capital, wages, and other expenditures required for supplying the natural gas.

CAPITAL.

The total capital reported as invested in the production and transportation of natural gas in the United States at the close of 1889 was \$59, 682, 154. Of this amount \$12,795,715 is given as the value of lands and \$46,886,439 as the value of rigs, wells, pipe lines, and other property.

The total acreage of land, both owned and leased, held by natural gas producers, is reported at 564,700. Of this amount 46,802 acres are reported as owned and 517,898 acres leased. The average value per acre of this land is \$22.66. This is evidently too low a valuation, and probably comes from the fact that it is based on the amount paid for leases. This question has been so thoroughly discussed on the report on the production of petroleum that it need only be referred to here. It is customary in leasing oil or gas land to pay so much bonus down for the lease, the amount varying from \$5 to \$50 an acre, and a royalty of the gas produced. It is fair to assume (certainly it is fair in consideration of the fact that \$20,000,000 worth of gas was produced from these 564,700 acres of land) that the average value of this land is at least \$100 an acre.

Of the 564,700 acres of land held in the United States 467,175 acres were held in Pennsylvania, Indiana and Ohio. This amount is certainly worth an average of more than \$100 an acre, some of it considerably more. Assuming this price, \$100, for the average value of all land held, the value of land would be \$56,470,000, instead of \$12,795,715. It is but fair to say that some of this land reported as gas land is also oil land, certain wells on the same leases producing oil and others gas.

Of the \$46,886,439 reported as the value of property other than lands,

\$7,472,157 is given as the value of rigs, wells, etc., \$31,637,284 as the value of pipe lines used in transporting the gas from wells to consumers, and \$7,776,998 as the value of other property.

Capital invested in the natural gas industry in the United States in 1889.

States and Territories.	Number of acres of natural gas land.				Value of plant.			Total capital.
	Total acreage.	Owued.	Leased.	Value.	Rigs, wells, etc.	Pipelines.	Other property.	
Pennsylvania.....	277,430	25,411	252,019	\$7,589,968	\$3,757,961	\$18,955,018	\$4,095,885	\$34,398,832
Indiana.....	77,493	12,294	65,199	1,090,218	1,396,949	4,792,548	926,098	8,205,813
Ohio.....	112,252	3,712	108,540	3,241,679	1,702,051	6,418,342	1,591,678	12,953,750
New York.....	49,870	533	49,337	298,120	169,753	580,519	114,037	1,162,429
Missouri.....	15	5	10	176,800	90,800	44,200	1,500	313,300
Kansas.....	2,002	2	2,000	10,200	22,500	27,200	100,100	160,000
California.....	6	6	1,900	49,635	215	51,750
Illinois.....	19,044	44	19,000	3,200	23,620	18,400	45,220
Kentucky.....	23,215	3,800	19,415	275,550	128,950	800,700	941,200	2,146,400
West Virginia.....	218	218	11,280	103,395	25	114,700
Texas.....	725	725	72,500	1,500	6,000	80,000
Arkansas.....	2,000	2,000	20,000	3,500	500	24,000
Utah.....	2,970	30	3,000
South Dakota.....	1,273	87	1,360
New Mexico.....	3,000	3,000
Tennessee.....	270	270	2,700	11,800	14,500
Wisconsin.....	160	160	1,600	2,500	4,100
Total.....	564,700	46,802	517,898	12,795,715	7,472,157	31,637,284	7,776,998	59,682,154

Labor and wages in producing natural gas in 1889.—The total number of persons employed in the production of natural gas in the United States in 1889 is given as 6,684, to whom \$1,736,389 was paid in wages. Of the total number of employes, 374 were foremen or overseers, 889 mechanics, 5,004 laborers, 6 boys under 16 years, 395 males engaged in office work, and 16 females engaged in office work. It must be understood that these workmen were employed not only in the production of gas, but in its distribution. This report is by no means satisfactory and is to a large extent meaningless, or at least the terms used are such as to lead to confusion in the classification. A better classification is given in the second table below, which shows more in detail the number of persons employed and by more definite occupations.

Labor and wages in producing natural gas.

States and Territories.	Foremen or overseers.		Mechanics.		Laborers.	
	Number.	Wages.	Number.	Wages.	Number.	Wages.
Pennsylvania.....	145	\$126,424	399	\$207,210	2,529	\$571,445
Indiana.....	153	58,865	324	97,091	1,408	134,388
Ohio.....	59	40,702	97	32,997	757	125,938
New York.....	11	4,152	37	4,443	296	17,687
Missouri.....	1	50	1	35
Kansas.....	1	900	1	200
Illinois.....	1	750	3	172
Kentucky.....	3	3,360	14	8,056	3	520
West Virginia.....	6	1,800
Texas.....	1	900	1	720	1	360
Arkansas.....	4	2,500
South Dakota.....	1	73
New Mexico.....	4	2,000
Wisconsin.....	1	400	5	1,200
Total.....	374	235,553	889	357,840	5,004	851,945

Labor and wages in producing natural gas—Continued.

States and Territories.	Boys under 16 years.		Office.				Total.	
	Number.	Wages.	Males.		Females.		Number.	Wages.
			Number.	Wages.	Number.	Wages.		
Pennsylvania.....	1	\$50	202	\$185,567	6	\$2,013	3,282	\$1,092,709
Indiana.....	2	160	115	49,287	5	2,060	2,007	341,851
Ohio.....	3	438	63	40,337	4	806	983	241,218
New York.....			12	7,868	1	85	357	34,235
Missouri.....							2	85
Kansas.....			1	1,000			3	2,100
Illinois.....			1	300			5	1,222
Kentucky.....			1	1,080			21	13,016
West Virginia.....							6	1,800
Texas.....							3	1,980
Arkansas.....							4	2,500
South Dakota.....							1	73
New Mexico.....							4	2,000
Wisconsin.....							6	1,600
Total.....	6	648	395	285,439	16	4,964	6,684	1,736,389

Of the \$1,736,389 paid for wages in 1889, \$235,553 was paid to foremen or overseers, \$357,840 to mechanics, \$851,945 to laborers, \$648 to boys under 16 years, \$285,439 to office force, males, and \$4,964 to office force, females. In addition to these wages a large amount of money was paid to contractors for drilling wells, laying pipe lines, etc., into which labor entered largely. Of wages so paid no account is given.

In the following table will be found totals showing the occupation and number of employes of each kind in the United States:

Number and occupations of employes about gas wells in 1889.

Class of labor.	Pennsylvania.	Indiana.	Ohio.	New York.	Missouri.	Kansas.	Illinois.	Kentucky.	West Virginia.	Texas.	Arkansas.	South Dakota.	New Mexico.	Wisconsin.	Total.
Presidents.....	1														1
Treasurers.....	1	1													2
Bookkeepers.....	36	80	9	7											132
Clerks, males.....	160	41	40	4		1	1	1							248
Clerks, females.....	4		17	1											22
Telegraph operators.....	6		1	3											10
Superintendents.....	13	29	7	5											54
Foremen or overseers.....	130	121	44	10			1	3		1				1	311
Electricians.....	1		8												9
Inspectors.....	34	5													39
Station agents.....	25	10													35
Agents.....				1											1
Engineers.....	2	6		2											10
Fitters or plumbers.....	146	160	12												318
Drillers.....	61	38	32	10		1			4						146
Tool-dressers.....	22		12												34
Carpenters.....	21	5							2						28
Fieldmen or wellmen.....	52		6	3											61
Teamsters.....	19	10		13											42
Linemen.....	23	33		3											59
Warehousemen.....	2														2
Blacksmiths.....	3														2
Tongsmen.....	69														69
Watchmen.....	7			5											12
Mechanics.....	153	92	37	33	1			14		1	4	1	4		340
Laborers.....	2,291	1,374	755	257	1	1	3	3		1				5	4,691
Boys under 16 years.....		2	3												6
Total.....	3,282	2,007	983	357	2	3	5	21	6	3	4	1	4	6	6,684

Total expenditure for materials during 1889.—The total expenditure during 1889 for all materials used in drilling wells, operating and caring for the same, building pipe lines, and for all other materials, was \$13,184,497. Of this amount \$165,677 was paid for materials used in building rigs, \$467,540 for materials used in drilling wells, \$282,882 for materials used in operating, shutting in, and caring for wells, \$7,044,438 for pipe lines, \$285,180 for materials used in fitting, \$28,794 for torpedoes, and \$4,915,086 for all other materials. Considerable work was done by contract, including labor and materials. It was impossible to make a division of the amounts between labor, materials, etc.

Total expenditures for materials during 1889.

States.	Building rigs.	Drilling wells.	Operat- ing, shut- ting in, and car- ing for wells.	Pipe, coup- lings, etc., in build- ing and repairing pipelines.	Used in fitting.	Torpedoes.		All other materials.	Total.
						Num- ber.	Value.		
Pennsylvania	\$113,022	\$326,674	\$188,550	\$855,192	\$227,926	55	\$6,167	\$3,246,249	\$4,963,780
Indiana	3,800	42,710	38,712	1,761,203	40,190	82	10,275	24,182	1,921,072
Ohio	26,019	66,751	44,710	4,261,054	970	86	8,228	1,315,133	5,722,865
New York	17,336	22,405	5,810	131,144	16,094	41	2,330	316,022	511,141
Missouri	500			12,200				1,500	14,200
Kansas	4,500	6,500	1,800	1,555		2	350		14,705
California				90					90
Illinois			1,600	16,000					17,600
Kentucky	500		1,700	6,000		15	1,444	6,000	15,644
Wisconsin		(a) 2,500						900	3,400
Total ...	165,677	467,540	282,882	7,044,438	285,180	281	28,794	4,915,086	13,184,497

a Includes cost of rigs, drive pipes, casing, and tubing.

STONE.

BY WILLIAM C. DAY.

The present report on stone in the United States is intended particularly to show the distribution by counties of the different varieties in the various productive States and Territories. With this purpose in view, each productive State and Territory is treated of by itself. The statistical figures apply in the large majority of cases to the calendar year 1889, and they serve to show the relative magnitudes of the industries. In addition to the subject of distribution, other features of interest in regard to the properties, the chemical constitution and physical structure of the stone and the purposes to which it is applied are included in so far as the data at hand at this time will permit.

In 1889 there were produced in the United States limestone, granite, sandstone, marble, slate, and bluestone, named in the order of their commercial importance.

The total value of this stone product, according to the results of the Eleventh Census, was \$53,035,620, distributed as follows: Limestone, \$19,095,179; granite, \$14,464,095; sandstone, \$10,816,057; marble, \$3,488,170; slate, \$3,482,513; and bluestone, \$1,689,606. In 1890 no such detailed canvass of the United States was attempted as was executed in the previous year for the Eleventh Census. Building was more active in 1890 than in 1889, and the total shows fully the normal growth to a total value for stone of all kinds of \$54,000,000.

LIMESTONE.

Production.—The value of the limestone produced in the United States in 1889, as shown above, was \$19,095,179. It was produced in 40 States and Territories as follows:

Production of limestone in the United States in 1889, by States and Territories.

Rank.	States and Territories.	Value.	Rank.	States and Territories.	Value.
1	Pennsylvania	\$2,655,477	22	Connecticut	\$131,697
2	Illinois	2,190,607	23	New Jersey	129,662
3	Indiana	1,889,336	24	Massachusetts	119,978
4	Missouri	1,859,960	25	West Virginia	93,856
5	New York	1,708,830	26	Michigan	85,952
6	Maine	1,523,499	27	Tennessee	73,028
7	Ohio	1,514,934	28	Idaho	28,545
8	Wisconsin	813,963	29	Rhode Island	27,625
9	Minnesota	613,247	30	Utah	27,568
10	Iowa	530,863	31	Montana	24,964
11	California	516,780	32	Arkansas	18,360
12	Kansas	478,822	33	South Carolina	14,520
13	Alabama	324,814	34	New Mexico	3,862
14	Kentucky	303,314	35	Oregon	
15	Washington	231,287	36	Georgia	
16	Texas	217,835	37	Florida	
17	Nebraska	207,019	38	Arizona	77,935
18	Vermont	195,066	39	South Dakota	
19	Maryland	164,860	40	Wyoming	
20	Virginia	159,023			
21	Colorado	138,091			
				Total	19,095,179

Uses.—The principal purpose for which the limestone was used was for the production of lime, the value of the lime produced being \$8,217,015. For building purposes \$5,405,671 worth was used; for street work, \$2,333,456; for a flux in blast furnaces the limestone used was worth \$1,569,312; for bridge, dam, and railroad work, \$1,289,622, and for miscellaneous purposes \$230,103 worth was used.

GRANITE.

Production.—The value of the granite produced in the United States in 1889 was, as shown in the following statement, \$14,464,095. This product was distributed among twenty-eight States and Territories, as follows:

Production of granite in the United States in 1889, by States and Territories.

Rank.	States.	Value of output.	Rank.	States.	Value of output.
1	Massachusetts.....	\$2,503,503	16	South Dakota.....	\$304,673
2	Maine.....	2,225,839	17	Wisconsin.....	266,095
3	California.....	1,329,018	18	New York.....	222,773
4	Connecticut.....	1,061,202	19	Delaware.....	211,194
5	Rhode Island.....	931,216	20	North Carolina.....	146,627
6	Georgia.....	752,481	21	South Carolina.....	47,614
7	New Hampshire.....	727,531	22	Oregon.....	44,150
8	Pennsylvania.....	623,252	23	Texas.....	22,550
9	Vermont.....	531,870	24	Utah.....	8,700
10	Missouri.....	500,642	25	Montana.....	} 76,000
11	Maryland.....	447,489	26	Arkansas.....	
12	New Jersey.....	425,673	27	Washington.....	
13	Minnesota.....	356,782	28	Nevada.....	
14	Virginia.....	332,548		Total.....	14,464,095
15	Colorado.....	314,673			

Uses.—The purposes to which the granite product was put were as follows: Building, \$6,166,034; street work, \$4,456,891; cemetery, monumental, and decorative purposes, \$2,371,911; bridge, dam, and railroad work, \$1,238,401, and miscellaneous uses, including millstones, walls (fences) watering troughs, posts, engine and machine beds, yard stock, boundary stone, horse blocks, etc., \$230,858.

SANDSTONE.

Production.—The total value of the sandstone produced in the United States in 1889 was \$10,816,057. The States contributing to this total were, in the order of output, as follows:

Production of sandstone in the United States in 1889, by States and Territories.

Rank.	States and Territories.	Value of output.	Rank.	States and Territories.	Value of output.
1	Ohio.....	\$3,046,656	22	Alabama.....	\$43,965
2	Pennsylvania.....	1,609,159	23	Montana.....	31,648
3	Colorado.....	1,224,098	24	Arkansas.....	25,074
4	Connecticut.....	920,061	25	Illinois.....	17,896
5	New York.....	702,419	26	Wyoming.....	16,760
6	Massachusetts.....	649,097	27	Texas.....	14,651
7	New Jersey.....	597,309	28	North Carolina.....	12,000
8	Michigan.....	246,570	29	Virginia.....	11,500
9	New Mexico.....	186,804	30	Maryland.....	10,605
10	Wisconsin.....	183,958	31	Arizona.....	9,146
11	California.....	175,598	32	Oregon.....	8,424
12	Missouri.....	155,557	33	New Hampshire.....	3,750
13	Kansas.....	149,289	34	Tennessee.....	2,722
14	West Virginia.....	140,687	35	Idaho.....	2,490
15	Minnesota.....	131,979	36	Rhode Island.....	} 26,199
16	Kentucky.....	117,940	37	Nevada.....	
17	South Dakota.....	93,570	38	Vermont.....	
18	Iowa.....	80,251	39	Florida.....	
19	Washington.....	75,936	40	Georgia.....	
20	Utah.....	48,306		Total.....	10,816,057
21	Indiana.....	43,983			

Uses.—The principal use to which the sandstone product of 1889 was put was for building, \$7,121,942 worth, or over 65 per cent of the product being devoted to this purpose; for street work, a quantity valued at \$1,832,822 was used, while bridge, dam, and railroad work consumed \$1,021,920 worth of the product. For abrasive purposes \$580,229 worth was used, and for miscellaneous uses, \$259,144. The last classification includes the stone used for grout, hitching-posts, fence walls, sand for glass, sand for plaster and cement, furnace hearths, lining for blast furnaces, rolling-mill furnaces, adamantine plaster, millstones, cemetery work, watering troughs, fluxing, ganister, firebrick, silica brick, lining for steel converters, glass furnaces, core sand for foundries, and random stock.

MARBLE.

Production.—The value of the marble produced in the United States in 1889 was \$3,488,170. This was the product of ten States, as follows:

Production of marble in the United States in 1889, by States.

Rank.	States.	Value of output.	Rank.	States.	Value of output.
1	Vermont	\$2,169,560	7	Pennsylvania	} \$121,850
2	Tennessee	419,467	8	Massachusetts	
3	New York	354,197	9	Idaho	
4	Georgia	196,250	10	Virginia	
5	Maryland	139,816			
6	California	87,030		Total	3,488,170

Marble imported and entered for consumption in the United States, 1867 to 1883, inclusive.

Fiscal years ending June 30—	Sawed, dressed, etc., not over 2 inches in thickness.	Sawed, dressed, etc., over 2 and not over 3 inches in thickness.	Sawed, dressed, etc., over 3 and not over 4 inches in thickness.	Sawed, dressed, etc., over 4 and not over 5 inches in thickness.	Sawed, dressed, etc., over 5 and not over 6 inches in thickness.	Veined and all other, in blocks, etc.	White, statuary, Brocatella, etc.	Not otherwise specified.	Total.
1867						\$192,514	\$2,540	\$51,978	\$247,032
1868						309,750	4,403	85,783	399,936
1869						359,881	3,898	101,309	465,088
1870						332,839	3,713	142,785	479,337
1871	\$5,973	\$168	\$77	\$44	\$28	400,158	1,134	118,016	525,598
1872	3,499	1,081	452		318	475,718	4,017	54,539	539,924
1873	3,124	21				396,671	4,148	69,991	473,955
1874	1,837					474,680	2,863	51,699	531,079
1875	1,456	427	96			527,628	1,623	72,389	603,619
1876	595	126	203	87		529,126	1,151	60,596	591,884
1877	2,124					349,590	1,404	77,293	430,411
1878	198	11	8			376,936	592	43,915	421,660
1879	184					329,155	427	54,857	384,623
1880						531,908	7,239	62,715	601,862
1881	339					470,047	1,468	82,046	553,900
1882	655					486,331	3,582	84,577	575,145
1883	619					533,096	2,011	71,905	607,631

During the calendar years ending December 31, from 1886 to 1890, and fiscal years ending June 30, for 1884 and 1885, the classification has been as follows:

Marble imported and entered for consumption in the United States from 1884 to 1890.

Classification.	1884.	1885.	1886.	1887.	1888.	1889.	1890.
In block, rough or squared, of all kinds	\$511,287	\$429,186	\$408,895	\$355,648	\$357,220	\$498,275	\$510,354
Veined marble, sawed, dressed, or otherwise, including marble slabs and marble paving tiles ..	12,941	43,923	96,625	142,405	107,957	115,909	142,653
All manufactures of, not specially enumerated	67,829	54,772	44,053	31,880	69,086	61,231	132,376
Total	592,057	527,881	549,573	529,933	534,263	675,415	785,383

SLATE.

Production.—Slate valued at a total of \$3,482,513 was produced in the United States during 1889. Twelve States contributed to this product as follows:

Production of slate in the United States in 1889, by States.

Rank.	States.	Value of output.
1	Pennsylvania	\$2,011,726
2	Vermont	842,013
3	Maine	219,500
4	New York	126,603
5	Virginia	113,079
6	Maryland	110,008
7	California	18,089
8	Georgia	15,330
9	New Jersey	10,925
10	Michigan	} 15,240
11	Arkansas	
12	Utah	
	Total	3,482,513

Uses.—By far the greater portion of the slate produced in this country is used for roofing purposes, the value of the slate thus used in 1889 being \$2,797,904, while that devoted to other purposes was valued at \$684,609.

BLUESTONE.

Production.—This variety of sandstone was produced in only three States, the total value of the product being \$1,689,606, divided as follows:

Production of bluestone in the United States in 1889, by States.

Rank.	States.	Value of output.
1	New York	\$1,303,321
2	Pennsylvania	377,735
3	New Jersey	8,550
	Total	1,689,606

Uses.—Originally bluestone was used for flagging only, to which purpose the larger portion is still applied, but the use of it has extended to other purposes, such as rubble masonry, retaining walls and bridge stone, sidewalks, curbing, gutters, stepstones, flooring, vault covers, bases of tombstones, porch and hitching posts, and house trimmings.

ALABAMA.

The kinds of stone produced in this State are, in the order of their commercial importance, limestone and sandstone.

Limestone.—This comes from twenty-one quarries, distributed over the following counties: Shelby, \$87,540; Colbert, \$69,494; Lee, \$52,500; Blount, \$42,000; Franklin, \$28,586; De Kalb, \$16,333; Etowah, \$13,567; Jefferson, \$10,000, and smaller amounts in Jackson and Talladega counties. The value of the entire product as sold, including the value of the lime made from it, was \$324,814. Of this amount the value of lime produced was \$178,248. Other uses to which the stone is put are, in order of importance, blast-furnace flux, building, and street work.

Analysis of limestone from Chewacla, Lee county.

	Per cent.
Calcium carbonate	57.73
Magnesium carbonate	41.58
Ferric oxide and alumina12
Siliceous matter89
Total	100.32

Sandstone.—The amount produced in 1889 was valued at \$43,965. The stone comes mainly from Jefferson county, with a product of \$28,500, and small amounts from Colbert and St. Clair counties. It is used principally in the erection of buildings, a small quantity being devoted to bridge, dam, and railroad work.

New and prospective developments.—Marble has been found near Florence, Lauderdale county, 1 mile from the Louisville and Nashville railroad, and it is possible that developments may be made at this point. The Shelby Lime and Cement Company opened a new limestone quarry in February, 1890. The Cherokee Stone and Railroad Company opened a sandstone quarry in Colbert county in the fall of the same year.

ARIZONA.

Sandstone and limestone in small quantity are produced, the former in Maricopa and Yavapai counties and the latter in Gila county. The product is used locally.

New and prospective developments.—Messrs. Murphy and Austin, of Prescott, operated to a limited extent quarries of brown and lilac sandstone in 1890. The completion of prospective railroad facilities will increase their operations.

ARKANSAS.

The kinds of stone produced in this State are, sandstone, \$25,074; limestone, \$18,360; granite and slate in small amounts.

Sandstone.—The counties producing sandstone are, in the order of their importance, Johnson, Sebastian, Conway, and Miller. The product is used mainly for building purposes, although some is devoted to street and railroad work.

Limestone.—Limestone comes from Independence, Benton, Washington, and Carroll counties, and is used chiefly for burning into lime.

Granite.—The production of this stone is limited to Pulaski and Saline counties, and has extended over only a few years; but the outlook for larger operations in the future is good. The granites of Arkansas, which are, exactly speaking, syenites, are known as the Fourche Mountain or Little Rock, the Saline county and the Magnet Cove syenites. The first of these groups forms the Fourche mountain, a few miles south of Little Rock, and contains the so-called blue granite, which is an elæolitic augite hornblende syenite, and some gray granite, which is a light-gray cross-grained elæolite syenite. The blue granite has already become a very important building stone, and it is also used in the manufacture of paving blocks. The gray granite has been produced to a small extent. The Saline County region contains almost exclusively elæolite syenite of a reddish or grayish color, which has found little or no market on account of its distance from the railroad. The rock of the third region is worked to some small extent in building railroad culverts and foundations of houses. The following tests were made in the mechanical laboratory at the Rensselaer Polytechnic Institute at Troy, New York, on a 50,000-pound Tinois-Olsen testing machine. The specimens were cubical in form and were cushioned with pieces of bookbinders' board about three-sixteenths of an inch in thickness. They broke suddenly with an explosive force and in some cases the small fragments tore the heavy binders' board completely to pieces. In regard to the stone from Fourche mountain, it may be said that it is easily quarried, occurring in long ridges 200 to 300 feet in height, and by opening a quarry on the side of any one of these easy access to the stone is obtained, and perfect drainage and a convenient dump may be had at a minimum of cost.

Results of tests of Arkansas syenites.

Number.	Description of specimens.	County where found.	Area of surface.	Actual crushing load.	Pressure per square inch.	Reduced to correspond to pressure per square inch in two-inch cubes.	Ratio of absorption—1 to —	Specific gravity at 60° F.
			<i>Sq. in</i>	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>		
1	Light colored <i>elæolite</i> syenite, slightly decomposed	Saline ..	2.34	48,000	20,500	22,350	761	2.62
2	"Gray granite," a very light-colored <i>elæolite</i> syenite.....	Pulaski.	2.25	33,750	14,000	16,000	83	2.45
3	Brownish <i>elæolite</i> porphyry, occurs in narrow dikesdo ..	1.42	30,000	21,000	24,980	161	2.52
4	"Light-blue granite" (<i>syenite</i>).....do ..	1.64	47,000	28,700	33,280
5	"Light-blue granite" (<i>syenite</i>), somewhat darkerdo ..	1.07	22,800	21,500	26,820
6	"Light-blue granite" (<i>syenite</i>), still darkerdo ..	1.57	35,950	22,900	26,745	1,673	2.64
7	"Medium blue granite" (<i>syenite</i>).....do ..	1.50	43,500	29,000	34,150
8	"Dark blue granite" (<i>syenite</i> porphyry)do ..	1.57	43,800	27,900	32,630	4,530	2.69
	Mean of last five specimens.do
	Average for "blue granite".....do	26,000	30,740

Slata.—A small quantity was quarried in Pulaski county in 1889. There is good reason to anticipate an increased production in the future.

New and prospective developments.—Variegated marble is found in Marion county, and Mr. L. Matlock, of Yelville, opened a quarry of it in the summer of 1890. A large area of marble outcroppings has been traced out and mapped in the region north of the Boston mountains in this State. These marbles are susceptible of a high polish and are of several shades of red, pink, and variegated. They are said to compare favorably with the Tennessee marble, but investigations and developments have not yet proceeded to a point which justifies more definite statements as to the future. The American Onyx Company, of Kansas City, Missouri, opened a marble quarry in Benton county in the summer of 1890.

In northern Arkansas, according to the Geological Survey at present being conducted under the direction of Mr. John C. Branner, State geologist, there are six distinct beds of limestone. Each of these six beds will furnish good building material. The upper bed in places will furnish marble, although the greater part of it has little commercial value. The third bed in the series furnishes an excellent building stone at almost every outcrop, and it is found throughout nearly all the northern counties. It corresponds quite closely with the Indiana oölitic limestone, being in the same geological horizon and resembling it in structure, except that it is more crystalline and takes a finer polish than the Bedford, Indiana, stone. It is more crystalline, less oölitic, and more fossiliferous in the western than in the eastern part of the bed. It has been quarried at Batesville, Independence county, for building stone and burning into lime. The fourth bed in the series, belonging to the Trenton period, occupies the same geological position

as the Tennessee marble, which it resembles in structure and appearance. It has been traced and carefully mapped through Independence, Izard, Stone, Searcy, Marion, and parts of Newton and Boone counties. It is known to exist also in Madison and Carroll counties, and possibly extends as far west as the State line or beyond. Small quantities only have been quarried for local use in monuments and mantel. It varies in color through light gray, pink, red, variegated, and mottled. The fifth bed is found in great quantities in Independence, Izard, Stone, and Searcy counties. It is a fair building material and burns to produce good lime. Some lithographic stone has been obtained from it.

CALIFORNIA.

Until within a comparatively few years the demand for stone in this State has not been very great, and consequently the development and growth of the California industry is by no means in proportion to the resources in stone of all kinds which the State has revealed and which have been recognized and known for a long time. Most of the buildings of the State have been of pine or redwood, the abundance, accessibility and cheapness of which have caused their general adoption. The mild climate has also tended to retard the adoption of the more substantial stone in the erection of dwellings. Insufficient facilities for transportation have naturally also been an obstacle in the way of quarry development, and in some localities where fine stone is abundant and accessible this drawback will be felt for years to come.

Even where the demand for stone becomes as great in comparison with other building materials as could possibly be expected, the number of large cities in California and neighboring States is insufficient to offer inducements for the development of more than a small fraction of the valuable quarry property known to exist, and shipments to remote points will have to be made before production will be commensurate with the possibilities. Such shipments are, however, by no means out of the question in view of the fact that a larger amount of eastern stone is shipped to California than would ordinarily be suspected. This is notably the case with slate, and to some extent also with other kinds of stone produced at eastern quarrying centers. This State produces the following kinds of stone, named in the order of their commercial importance: Granite, limestone, marble, and slate.

Granite.—This comes from 76 quarries in the following counties, named according to the value of output: Placer, Sacramento, Sonoma, Alameda, Fresno, San Bernardino, Solano, Humboldt, San Diego, Tulare, Nevada, Los Angeles, Marin, and Calaveras. It is thus evident that granite is quarried at points scattered over an area extending from the extreme northern to the extreme southern part of the State. The great bulk of the product comes, however, from the first five counties, four of which are near Sacramento and San Francisco. The total output for the State in 1889 was valued at \$1,329,018. Of this

ount Placer county produced \$299,000 worth; Sacramento, \$289,000; Sonoma, \$215,000; Alameda, \$142,000, and Fresno, \$120,000. Somewhat less than half of the output is used for street paving and a slightly smaller quantity for ordinary building purposes. The granite quarries in the southern part of the State, while capable of producing large quantities of good stone, depend for their demand upon the southern portion of the State, and consequently the production will be necessarily limited until a wider territory of consumption is made available by a decided cheapening in transportation. In Fresno county are recently opened granite quarries 21 miles north of Berendo. Large developments are promised, the stone being so situated as to be accessible and easily handled. It is not regarded as a monumental stone, but it does not stain and answers very well for building. Large quantities of fine granite are to be found at Declezville, Victor and Riverside in San Bernardino county; and at Temecula in San Diego county. In Placer county, Rocklin and Lincoln are the most important producing centers. The stone from these quarries takes a brilliant and lasting polish and is quite popular with builders. Quarries have been operated for about twenty years at Rocklin, Lincoln, Loomis, and Penryn. The Central Pacific railroad takes about 90 per cent. of the product to San Francisco. At Penryn the latest improvements for finishing and polishing granite are to be found in more complete condition than at any other locality in the State.

The Folsom quarries of Sacramento county are at a point 1 mile above the town of Folsom City, which is 20 miles from Sacramento. Stone from these quarries has been used in the construction of the stone viaduct at Mare Island navy-yard, and also at the State capitol in Sacramento. It also enters largely into the stone buildings in San Francisco. These quarries lie for 2 miles on both sides of the American river. In its vicinity one of the prisons of the State is located. A large dam constructed of granite across the American river was completed in December, 1890. The labor was for the most part convict labor furnished by the State. This great work was commenced in 1866, but for a compilation of reasons was somewhat delayed until 1888, when it was reunder-taken and pushed with vigor. Most of the granite recently quarried has been used in the construction of this dam and also of the canal. The enormous water power which this dam will render available will be used in the prison and also in the city of Sacramento, where it is expected an important industrial era will be inaugurated by the utilization of power from this source. The dam and canal are the most substantial structures of the kind on the Pacific coast. It is the intention of the Granite Company operating at this point to put large quantities of stone upon the market as soon as the canal and dam operations are entirely completed.

The granite-quarrying operations of Sonoma county are practically limited to the production of basalt paving blocks, which has for years constituted an important industry in this county.

New and prospective developments.—During 1890 new granite quarries were opened by Mr. Matthew Lumber, of Rocklin. The Western Granite and Marble Company, of San José, the Carlow Brothers, of Sacramento, and the California Improvement Company, of Oakland, are all engaged in new developments of quarry property.

Sandstone.—In 1889 sandstone was produced to the value of \$175,598 from fifteen quarries scattered over the following counties, named in order of output: Santa Clara, Amador, Ventura, San Bernardino, Yolo, Solano, and Napa. Of the total output Santa Clara yielded \$100,000 worth; Amador county was second, with a product valued at \$35,000. At San José a sandstone of light color and good quality is quite extensively quarried. It has been adopted upon the basis of its merits and its accessibility for use in the construction of the Stanford University. The Sespe Mountain sandstone of Ventura county is claimed to be the finest sandstone in the State, particularly for ornamental building.

Marble.—Four quarries in San Bernardino, Amador, Inyo, and San Louis Obispo counties produced in 1889, \$87,030 worth of marble. Of the total output San Bernardino produced to the value of \$78,000, by far the most of the entire product. It is thus evident that Southern California yields the bulk of the marble output of the State. The marble industry of California is in its infancy. The most advanced development is found in the quarries at Colton, San Bernardino county. Equipment for sawing, dressing, and polishing has just been completed. The stone is not what could be called strictly first class, but occasionally fine blocks are quarried. The quarries are so situated as to render operations easy and inexpensive. The developments in Inyo county are watched with interest. Shipments are steadily being made, and it is expected that railroad communication with Mojave will be made before long. Considerable prejudice among California marble workers against the marble of the State has had to be overcome, but, in view of the fact that the best quality of stone is not usually obtained near the surface, such unfavorable impressions are natural, but not always fair. Time must elapse before the stone can be fairly judged.

New and prospective developments.—The stockholders of the Carrara Marble Company in Amador county have been prospecting for a new railroad to their quarry. The marble from this quarry is regarded by certain experts in the State as the best to be found on the Pacific coast.

Slate.—Eighteen thousand dollars' worth of slate was produced from three quarries in El Dorado county in 1889. The product was used for quite a variety of purposes and appears to give entire satisfaction to the consumers. The demand for slate has been such in the past as to cause its importation from the East; the industry which has been opened up in the State ought therefore to thrive, and from present appearances it will grow steadily. At the Chili Bar slate quarry abundant water power is available, and while at present a large amount of dead work in stripping, etc., is to be done, the outlook for liberal production in the course of a year is exceedingly good.

Limestone.—Twenty-two quarries, scattered over eight counties in the State, produced limestone valued at a total of \$516,780. Of this amount \$513,130 represents the value of lime manufactured, so that it appears that only a small quantity of the total limestone production of the State goes for anything else than lime. The productive counties, named in order of value of output, are as follows: Santa Cruz, \$266,650; San Bernardino, \$74,000; Kern, \$47,630; San Benito, \$37,500; and smaller amounts in El Dorado, Santa Clara, San Diego, and Placer. The first-named county has for years been the principal producer of lime. Wood is abundant, cheap, and to be had immediately at the quarries. Transportation to San Francisco is by water. These advantages will probably enable Santa Clara county to maintain the lead for years to come. The most improved appliances are in use, and the lime is undoubtedly the best in the State. In San Benito county active operations have been inaugurated and the stone is of good quality. The following analyses of the limestone in this county have been made:

Analyses of limestone from San Benito county, California.

	Per cent.	Per cent.	Per cent.
Carbonate of calcium	96.00	99.2	99.0
Silica	2.10	.7	.5
Gypsum	Trace.	Trace.	Trace.
Total.....	98.10	99.9	99.5

The lime produced has to be hauled by twelve-horse teams to the railroad, thus adding to the cost of the lime; but it is said that this increase to the cost is largely offset by the ease of quarrying.

COLORADO.

The stone interests of Colorado have within a comparatively few years increased to very surprising proportions. The kinds of stone now produced are granite, limestone, and sandstone. The value of the stone output of this State in 1880 was only \$50,400. The kinds of stone produced were sandstone and granite, the granite being valued at \$41,400, while the value of the sandstone was only \$9,000. The value of the stone output of Colorado in 1889 was \$1,676,862. The developments are mainly due to the very much improved transportation facilities. The resources of this State are still undeveloped, and in almost all the varieties of stone produced for commercial purposes are very great.

Granite.—Ten quarries produced in 1889 an output valued at \$314,673. This came from six counties of the State, named as follows, in order of value of output: Douglas, \$200,049; Clear Creek, \$75,000; Gunnison, \$25,000; and much smaller amounts from Chaffee, Larimer, and Boulder counties. The great bulk of the product was used for general building

purposes, a smaller amount being devoted to monumental and cemetery use, and a trifling quantity to street work. The counties producing granite are all in the central part of the State, running from the extreme northern limits to about half the distance to the southern boundary. The greater portion comes from counties in the neighborhood of Denver.

Sandstone.—In 1889 there were seventy-one quarries producing sandstone, the product of which was valued at a total of \$1,224,098. The product came from the following counties, named in the order of their outputs: Boulder, \$405,773; El Paso, \$377,800; Larimer, \$317,388; Eagle, \$60,000; Jefferson, \$41,496; and smaller quantities from Las Animas, Fremont, Park, Huerfano, and Montezuma. An amount valued at \$703,477 was devoted to general building purposes. For street work the product used was valued at \$509,955; the remainder was devoted to bridge, dam, and railroad work. The enormous strides made in the production of sandstone are largely due to the operations of the Union Pacific Railroad Company. This company not only quarried sandstone, but by the transportation facilities furnished to other quarries brought the industry to its present stage of advancement. Colorado sandstone is now being shipped to remote points and is becoming well known to the general trade.

The following is an analysis of sandstone from a quarry in Boulder county:

Analysis of Boulder county, Colorado, sandstone.

	Per cent.
Silica.....	95.37
Oxide of iron.....	2.40
Lime.....	.92
Magnesia.....	.50
Loss by ignition.....	.55
Total.....	99.74

Among the most important sandstones of the State may be especially mentioned that known as Peachblow. This stone has met with very favorable reception and appears to be of good quality and color. It has been well received in Chicago.

New and prospective developments.—The following firms opened new sandstone quarries in 1890: Messrs. Kirk, Cramer and Davis, of Breckenridge, Mr. William Coates, of Walsenburg, and Mr. C. S. Faurot, of Boulder.

Limestone.—The total value of the limestone output of 1889 was \$138,091. Fifteen quarries were productive. The product came from the following counties: Jefferson, \$54,950; Boulder, \$36,500; Pitkin, \$24,127, and smaller amounts from Fremont, Pueblo, La Plata, and Larimer counties. The value of the lime produced in this State is \$91,101. For flux the amount used was valued at \$35,940. The balance was used for building purposes mainly.

Marble.—Although marble has not actually been quarried for market, the prospect for the development of this industry in the near future seems to be very good. Large masses of pure white marble are to be found on Whitehouse mountain near Marble city. Preliminary steps toward development have been taken. Gunnison county also contains marble deposits varying in color from pure white to jet black. Efforts are being made to secure the investment of capital for development. The marble deposits in Pleasant valley, northwest of Fort Collins, are of great interest, and some slight work of development has been attempted. The colors found at this place are red and pearl. This marble property is about 4 miles from the railroad and is easily accessible by an extension of the road.

CONNECTICUT.

This State produced granite, sandstone, and limestone in 1889.

Granite.—The granite output of Connecticut was valued at \$1,061,202.

It came from the following counties: New Haven, \$421,246; New London, \$313,508; Fairfield, \$188,697; Litchfield, \$60,425; Middlesex, \$35,341; Windham, \$26,968, and smaller amounts from Hartford and Tolland counties. The product was used for the most part for building purposes. The amount devoted to this purpose was valued at \$758,915; for street work, including the value of all paving blocks, \$109,261; for cemetery and ornamental work an amount valued at \$111,155 was produced. For bridge purposes, \$65,659, and a much smaller amount for miscellaneous uses was produced. Granite is produced in every county in the State. The most important, however, are those along the Sound coast.

Sandstone.—The total value of the Connecticut sandstone produced in 1889 was \$920,061. By far the most of it came from the long known and celebrated brownstone quarries of Middlesex county. The counties in the order of the value of the product were: Middlesex, \$871,476; New Haven, \$40,495, and very much smaller amounts from New London and Hartford counties. The most important quarries are in the neighborhood of Cromwell and Middletown. The work is carried on on a large scale with the use of channeling machines. Some of the quarries have gone to a considerable depth. This stone has been extensively used in the largest cities of the East for many years, and it is so well known that it is unnecessary to touch upon the subject here at any great length. The principal quarries are at Portland and Middletown, on the east bank of the Connecticut river, in Middlesex county.

Limestone.—The value of the limestone output, including the value of lime made from it, produced in this State in 1889 is \$131,697. It came from Litchfield and Fairfield counties, the amounts from each being respectively \$87,342 and \$44,355. By far the most of the product was burned into lime, the value of the lime being \$129,663.

The following is an analysis of limestone from the Danbury Lime Company, whose quarry is in Fairfield county:

Analysis of limestone from Fairfield county, Connecticut.

	Per cent.
Lime.....	90.00
Silica.....	5.83
Alumina.....	3.90
Magnesia.....	.22
Total.....	99.95

New and prospective developments.—A new granite quarry was opened in 1890 by Mr. Patrick Garvey, of Bridgeport. The Totoket Granite Company, of New York City, began putting in a plant at the quarries at Stone creek in 1890. The quarries are not yet fairly in operation.

DELAWARE.

Granite to the value of \$211,194 was taken from five quarries in New Castle county in the northeastern part of the State. An amount valued at \$110,849 was devoted to bridge, dam, and railroad work, \$67,202 in street work, and \$32,443 for general building purposes.

FLORIDA.

Such a thing as the production of stone in this State has apparently been unheard of until careful investigation during the recent census developed the fact that Alachua county produced a small quantity of limestone for making jetties at the mouth of the St. Johns river. This stone is of course not the well-known coquina which has been used as a building material in this State in times long past.

Sandstone, flint, and limestone are reported as existing on the property of Mr. Louis Miller, of Sparr, Marion county. The sandstone has been quarried for local use.

GEORGIA.

Within the past few years the stone interests of this State have developed to a marked extent. The kinds of stone produced in 1889 were granite, sandstone, limestone, marble, and slate.

Granite.—Of these kinds, in point of value, granite was by far the most valuable, and it is interesting to know in this connection that while Georgia held twelfth place among the granite-producing States at the census of 1880 with a production of only \$64,480 worth of granite, at the Eleventh Census it takes sixth place with a production of more than ten times as much, namely, \$752,481 worth. This production in 1889 puts this State one place above New Hampshire, which has received the name of the "Granite State." The five States which produced more granite than Georgia in 1889 are: Massachusetts, Maine, California, Connecticut, and Rhode Island, in the order named. The granite-producing counties in the order of their importance are as fol-

lows: DeKalb, \$606,075; Hancock, \$68,083; Henry, \$57,950, and very much smaller amounts in Bibb, Elbert, Spalding, Rockdale, Jones, Oglethorpe, and Newton. Of the total product in 1889, \$347,100 worth went for building purposes and over \$250,000 worth for street work. Smaller amounts were used for cemetery and bridge and railroad purposes. Among the most important granite quarries in the State may be mentioned those conducting operations at Lithonia and Stone Mount. At these places the granite is quarried with great ease, Stone mountain being simply an uninterrupted and solid mass of granite almost entirely devoid of soil. The granite is loosened by blasting and then split by hand drills and wedges. The cheapness of unskilled labor, which is contributed entirely by negroes, together with the ease of quarrying, make it possible for operators to compete favorably with other granite-producing centers. The granite from Lithonia and Stone mountain has been quite thoroughly tested and examined by scientific authorities of high repute. The results of these examinations are very favorable to the stone.

Marble.—The value of the marble produced in Georgia in 1889 was \$196,250. Of this amount, \$10,000 worth came from Cherokee county, and of the remainder by far the most of the product came from Pickens county. The developments of Georgia marble have all been made within the past six years.

The following is an analysis of Pickens county marble made by Mr. John C. Jackson, of Chicago:

Analysis of Pickens county, Georgia, marble.

	Per cent.
Calcium carbonate	97.32
Magnesium carbonate.....	1.60
Silica.....	.62
Iron protoxide26
Alumina25
Total.....	100.05

It finds its chief application in wainscoting, mantels, table tops, counters, panels, etc.—in other words for purposes of interior decoration. The Georgia Marble Company has a very fine plant, and the shipping facilities are about all that could be wished. A very decided demand for this marble in most of the large cities of the Union has arisen, and seems likely to increase markedly from year to year.

New and prospective developments.—Deposits of marble have been known to exist in Whitfield county. Capt. Charles C. Davis, of Chattanooga, Tennessee, has recently purchased 160 acres of quarry land, and it is his intention to open quarries at once. The United States Marble Company has recently been incorporated to develop marble quarries in the State. The capital stock of this company is \$250,000.

Slate.—At the slate quarries at Rock Mart, Polk county, \$15,330 worth of stone was produced in 1889. These slate quarries have been operated for twenty-five years. Up to 1883, the slate was all hauled a distance of 23 miles by wagon, and yet was sold at a profit. In 1883 the East Tennessee, Virginia, and Georgia railroad was completed, and in 1885 the East and West Alabama railway, so that transportation facilities are now exceedingly good. The slate deposits are estimated to cover an area of about 360 acres and near the junction of the two railroads above mentioned. From all that can be learned of these quarries, the investment of a larger amount of capital could be made to pay well. In 1889, a determined effort was made to secure the investment of about a quarter of a million in the slate deposits as well as marble deposits which exist in the neighborhood of Rock Mart. The methods of quarrying and manufacturing have hitherto been of the very crudest nature, and the introduction of more improved methods would doubtless result in a very decided cheapening of the cost per square of roofing slate.

Limestone.—From Catoosa county was produced limestone to the value of \$24,656 in 1889; lime valued at \$20,000 was produced, and the remainder was used for furnace flux.

Sandstone.—A small amount of sandstone was produced in Randolph county, but the amount was almost insignificant.

IDAHO.

The stone industry in Idaho amounts to comparatively very little at present. The chief product is limestone, which in 1889 was valued at \$28,545, and came from three quarries in Kootenai, Bingham, and Alturas counties. Nearly the whole amount came from the first-named county and was entirely used for burning into lime. The lime is used entirely in neighboring towns.

Sandstone.—A small quantity of sandstone was produced in Ada county and was entirely used for building. The amount was insignificant.

Marble.—At Spring Basin, in Cassia county, marble was produced in sufficient quantities to supply local demands. The product is suitable for cemetery work, but it has never entered the market in competition with the well-known marbles of other regions.

ILLINOIS.

Limestone and sandstone have been produced in this State for some years. The latter, however, is of very small importance compared with the former.

Limestone.—The limestone produced in 1889 was valued at \$2,190,607. This product was obtained from 104 quarries, operated in the following counties, named in the order of the value of output: Cook, \$825,800; Will, \$742,177; Adams, \$91,000; Jersey, \$73,000; Madison, \$63,000;

Hardin, \$58,000; Kane, \$47,000; Pike, \$42,000; Kankakee, \$38,000; Hancock, \$35,000; Saint Clair, \$32,000; Winnebago, \$26,000; Rock Island, \$23,000; Henderson, \$22,000; Du Page, \$22,000; Randolph, \$16,000, and smaller amounts in Union, Whiteside, Monroe, Ogle, Stephenson, Kendall, Jo Daviess, McHenry, Greene, and La Salle. It is evident that the first two named counties produce the great volume of the limestone, the amount from Cook and Will counties together being \$1,567,977. Thus these two counties produce far more than the rest of the State put together. In the amount of limestone used for building purposes Illinois takes first place among the limestone-producing States. The amount devoted to building was valued at \$1,084,556. In the amount of limestone devoted to street work Illinois stands second among the limestone-producing States. The amount thus used was \$505,576. The value of the lime produced from limestone in this State, included in the total above given for the State, is \$366,245. As flux an amount valued at \$166,507 was used; for bridge work and miscellaneous purposes an amount valued at \$67,723. The operations in Cook and Will counties, on account of their magnitude, the general excellence of the stone produced, and the ease of quarrying and working out deserve special mention. The region embraced by these two counties is known generally as the Joliet region. It includes territory from about 5 miles south of the city of Joliet to about 10 to 12 miles north, taking in the towns of Lockport and Lemont and running along the valley of the Illinois river. Most of the quarries are situated on the banks of either the river or the canal. The stone exists in layers at the surface, varying from 1 inch to 3 inches in thickness, and growing in thickness with the increasing depth until at about 25 feet it is found of a thickness varying from 15 to 20 inches. It is, however, rarely quarried below the 25-foot level, owing to the expense of getting it out and dressing it, since at that depth it is much harder, although the quality of the stone is superior to that in the upper levels. At the depth of 25 feet the inflow of water materially adds to the expenses of quarrying. The stone found at or near the surface is almost valueless and is almost entirely thrown away in stripping the quarry. The next two-fifths furnish stone of sufficiently good quality to be used for riprap, rubble, sidewalks, and curbing. The last two-fifths contain the best stone, namely, that used for building. It is generally of a bluish-gray color. The exposed stone is of a yellowish color from the effects of exposure to the atmosphere. It is also true that most of the Joliet stone turns more or less yellow upon exposure. The beds are divided vertically by seams occurring at somewhat irregular intervals of from 12 to 50 feet, and continue with quite smooth faces for long distances, and also by a second set of seams running nearly at right angles with the first, but only continuous between main joints and occurring at very irregular intervals. This structure renders the rock very easily quarried and obtainable in blocks of almost any required lateral dimensions.

The stone is easily worked into required shapes and takes a fine, smooth finish, and is susceptible of being readily planed. This forms a very rapid and cheap method of finishing flagging stones and preparing such as are to receive a smooth finish on the polishing bed. Enormous quantities of flagging stone are taken out, most of which goes into Chicago; but business with other cities is decidedly on the increase. The finest varieties are readily produced in forms which are capable of being turned out by lathes.

The following is an analysis of Cook county limestone:

Analysis of Cook county, Illinois, limestone.

	Per cent.
Silica.....	26.08
Alumina and oxide of iron.....	6.57
Carbonate of lime.....	46.90
Carbonate of magnesia.....	14.19
Water.....	6.26
Total.....	100.00

The crushing strength of this stone is 16,017 pounds to the square inch; specific gravity, 2.512. The stone obtained in the vicinity of the towns of Sterling, Morrison, Fulton, Cordova, and Port Huron is largely burned into lime. This is true of much of the stone all along the Mississippi river. The best grades of Alton stone become whiter upon exposure to the air, and some of it that has stood in buildings for twenty to twenty-five years has become almost perfectly white. The quarry at the Chester, Illinois, State prison is an immense bluff about 200 feet in height. It has been worked for only the past two or three years and is now turning out fine stone. All work is done by the convicts.

Sandstone.—The sandstone of Illinois comes from counties in the north-western and western parts of the State. The total value of the product in 1889 was \$17,896. It came from the following counties, named in order of output: Henry, Fulton, Whiteside, Union, Knox, Lee, and Clay. By far the most, however, came from Henry county. It was nearly all used for building purposes.

INDIANA.

The kinds of stone produced in this State are limestone and sandstone. Much progress has been made in the stone industry in the last ten years.

Limestone.—The limestone produced in 1889, including the value of the lime made from it, was valued at \$1,889,336. The limestone industry is a very important one in this State. The productive counties are as follows, in the order of their relative magnitude: Lawrence, \$506,471; Huntington, \$228,679; Monroe, \$195,632; Decatur, \$169,195; Washington, \$137,200; Ripley, \$112,916; Owen, \$74,227; Clark, \$65,387; Franklin, \$51,558; Putnam, \$49,606; Wabash, \$38,640, and smaller amounts from Shelby, Grant, Carroll, Cass, Delaware, Howard, Black-

ford, Madison, Harrison, Jennings, Adams, Floyd, Wells, Crawford, Jackson, Jay, Fayette, Miami, Randolph, Vanderburg, Wayne and White. The most productive portions of the State are the southern and southeastern. The product of these portions amounts to \$1,312,586. The limestone of the State may for convenience be divided into three general classes: The oölitic limestone, otherwise known as cave limestone, from the numerous caverns which are to be found scattered through it; second, the harder and much more crystalline variety; and finally the rock which occurs in thin strata and which is well adapted for purposes of flagging, etc. The oölitic limestone extends in a southeastern direction from Greencastle in Putnam county. This stone is commonly known in trade as Indiana stone or Bedford stone and is well-known over a wide area in the United States and is an exceedingly popular building stone, not only in cities of the West, but in Eastern cities as well. It has been most extensively quarried at Stinesville, Ellettsville, and Bloomington, Monroe county, and at Bedford in Lawrence county; but owing to the increased demand for this stone, new quarries are being opened and extensively worked at frequent intervals along the line of the Louisville, New Albany, and Chicago railroad, from Gosport to Bedford, and these give promise of rich and practically inexhaustible supplies. This stone is almost exclusively used for building purposes, and it is the great production of this stone which enables Indiana to take second place among the States producing limestone for building purposes, Illinois standing in the first place. The stone is characterized by its oölitic character, is comparatively soft when first removed from the quarry, but hardens on exposure to air. The deposit varies from a few feet to a great many in thickness and it is practically free from fissures. Solid walls 40 to 50 feet in depth have already been revealed without a seam or fault of any kind from top to bottom. It is easily quarried in blocks of any size required, being cut from the solid mass by means of channelers. It is soft enough to be readily sawed, ordinary steel blades, with sand as the abrasive material, being used for sawing. Occasionally diamond saws are used with fine results. For most part the stone is fine grained, but contains also layers of coarser material in which shells are easily recognized with the unaided eye. Operations in all quarries producing this kind of stone are conducted on the largest scale and the machinery employed is usually of the very best.

The harder, more crystalline stone is found in the eastern and southeastern parts of the State, principally in Decatur county in the southeastern part. The quarries in general are rather small, there being twenty of them in Decatur county alone. Some of the quarries are operated on a large scale, as, for example, the Greensburg Limestone Company, the Big Four Company, and a number of others. On account of its hardness this stone can not be sawed. It is used quite largely for building purposes. In the northern and northeastern portions of

the State the stone is used somewhat for building and street purposes, and in Huntington county very largely for burning into lime. The great center of the lime industry is at Huntington, Huntington county. The most important concern producing lime at this point is the Western Lime Company. The product has a widespread reputation for use in building. On account of the flagging nature of the stone in the more northern portions of the State it is often quarried simply by aid of a pick and bar. This is more especially true in regard to the northeastern sections of the State. In the northern, northeastern, and eastern portions of Indiana are a great many small quarries. A number of them seem to be capable of more extended operations, but the lack of railroad facilities from the quarries to the main lines of travel exerts a retarding influence. The stone quarried at Greensburg, in Decatur county, is decidedly crystalline, and is susceptible of a high polish. The thin-bedded stone in the upper portions of these quarries is used to some extent for flagging. The development of the oölitic or Bedford stone is largely the result of operations conducted within a comparatively few years. In a small way it has been quarried and used for twenty-five years or more, but it is within the last twelve years that the stone has been recognized and appreciated by the larger cities of the East and West. It occupies at present a very prominent position among the best building stones of the country.

Considering the purposes to which the total limestone product of Indiana is devoted it appears that the value of the stone devoted to building purposes was \$994,313; the value of lime manufactured, coming chiefly from Huntington county, was \$340,315; to street and road work an amount valued at \$316,722 was devoted; to bridge work and light foundations \$233,710; and a small amount is used as flux. There are in all 172 limestone quarries in the State.

The following analyses may be found of interest:

Analysis of limestone from Adams county, Indiana.

	Per cent.
Carbonate of calcium.....	54.00
Carbonate of magnesium.....	45.00
Alumina.....	.46
Silica.....	.53
Iron.....	.01
Total.....	100.00

Analysis of limestone from Howard county, Indiana.

	Per cent.	Per cent.	Per cent.	Per cent.	Per cent.
Iron.....	.001	.001	.008	None.	None.
Carbonate of magnesium.....	Trace.	24.74	24.56	31.69	2.61
Carbonate of calcium.....	93.10	65.03	66.92	60.01	95.50
Insoluble matter incinerated.....	1.62	3.08	5.56	6.84	.90
Insoluble matter dried at 100°.....	1.74	8.73	7.63	7.03	1.82

Analysis of Lawrence county, Indiana, oölitic limestone.

	Per cent.
Lime	53.55
Carbonic acid	43.33
Water56
Magnesia	} 2.56
Iron	
Alumina	
Manganese	
Phosphoric acid	
Silica	
Total	100.00

Sandstone.—The sandstone produced in 1889 was valued at \$43,983. It was produced in the four counties following: Warren, \$19,163; Fountain, \$14,500, and smaller amounts in Orange and Putnam counties. There are in all eleven quarries. Of the total amount produced, \$16,033 worth was used for building purposes, whereas the entire product of Orange county was used for abrasive purposes. For bridge work, etc., an amount valued at \$18,080 was used. The sandstone of Orange county deserves especial mention on account of its value for abrasive purposes. This stone is said to need no oil to soften it, but is used with water alone, and it appears to be very popular for the purpose of sharpening tools. It has been very highly recommended for razor hones and sharpening axes and knives. It is found chiefly in the western part of Orange county, and appears to be produced in no other county of the State. Much of it is shipped in the rough to the various points in New York to be sawed. There are no works with good facilities for sawing the stone in the vicinity of the quarries. The presence of petrifications in these quarries occasions not a little trouble in working the stone.

IOWA.

Limestone and sandstone are produced in this State.

Limestone.—In 1889 the total value of the limestone product was \$530,863. It came mainly from counties in the eastern and south-eastern parts of the State. The limestone quarries are in a great many cases scarcely worthy of the name quarry, the operations being extremely limited and carried on frequently as work incidental to farming. There are comparatively few large operations in the State. It will, however, be noted that the value of the total output is considerable. The productive counties are as follows: Jackson, \$97,600; Dubuque, \$96,168; Cedar, \$67,941; Marshall, \$51,400; Jones, \$37,880; Scott, \$31,081; Lee, \$20,093; Clinton, \$14,631, and smaller amounts from Des Moines, Madison, Decatur, Cerro Gordo, Dallas, Wapello, Linn, Muscatine, Black Hawk, Mahaska, Washington, Benton, Clayton, Pocahontas, Montgomery, Tama, Floyd, Adams, Mitchell, Humboldt, Johnson, Jefferson, Clark, Van Buren, Howard, Taylor, Keokuk, Pottawattamie, Louisa, Webster, Allamakee, Story and Buchanan. The

number of quarries is 143. Of the total product an amount valued at \$236,792 was devoted to building purposes, while the value of the lime produced is \$170,043. The remainder was divided between street and road work and bridge piers and foundations.

Sandstone.—Eleven quarries in this State produced sandstone valued at a total of \$80,251. The productive counties are: Marion, \$61,451, and Hardin, \$10,197. The remainder producing small amounts are Cerro Gordo, Clayton, Lee, Jasper, Washington and Scott. The stone is almost entirely used for general building purposes.

New and prospective developments.—The following new limestone quarries were opened in 1890 by Mr. F. C. Chesterman, of Dubuque; Mr. Warren Bailey, of Cedar Falls, and Most & Stearns, of Humboldt.

KANSAS.

Limestone and sandstone were both produced in this State in 1889. The limestone was valued at \$478,822, the sandstone at \$149,289.

Limestone.—This comes from 115 quarries, many of them, however, very small, and contained in the following counties of the State: Cowley, \$95,000; Leavenworth, \$65,387; Marshall, \$57,700; Chase, \$53,000; Ripley, \$52,000; Butler, 47,000; Lyon, \$19,000; Wyandotte, \$19,000; and smaller amounts from Marion, Atchison, Wabaunsee, Shawnee, Washington, Johnson, Russell, Dickinson, Franklin, Morris, Elk, Brown, Douglas, Republic, Pottawatomie, Coffey, Anderson, Jefferson, Ness, Montgomery, Jackson, Harper, Sumner, Ellsworth and Osage. The stone is pretty well distributed over the eastern portion of the State. Most of it, however, comes from the vicinity of Atchison, Leavenworth, Topeka, and Fort Scott. Of the total production an amount valued at \$269,316 was used for building purposes. The value of the lime product is \$9,013. For street work \$97,502 worth was used; and for bridge, dam, and railroad work an amount valued at \$102,991.

The following is an analysis of Cowley county limestone made by Prof. F. W. Clarke, of the U. S. Geological Survey:

Analysis of limestone from Cowley county, Kansas.

	Per cent.
Silica.....	5.27
Water.....	.78
Ferric oxide.....	.71
Ferrous oxide.....	.32
Alumina.....	1.07
Carbonic acid.....	40.34
Lime.....	50.36
Magnesia.....	.56
Sulphuric acid.....	.07
Phosphoric acid.....	.06
Soda.....	.20
Potassa.....	.10
Total.....	99.84
Matter dried at 100°.	

According to the tests made in Washington a 2-inch cube crushed at 29,490 pounds.

Sandstone.—The sandstone product came from the following counties, named in order of value of output: Bourbon, \$90,000; Phillips, \$35,086; Rawlins, \$18,000, and smaller amounts from Crawford, Woodson, Clark, Wilson, Kingman, Harper and Comanche counties. The sandstone is found in all parts of the State, but the most productive portions are in the south and southeast. The product was used mainly for street work, a smaller quantity being devoted to building purposes.

KENTUCKY.

Sandstone and limestone were produced in this State in 1889. The value of the limestone produced was \$303,314, while that of the sandstone was \$117,940.

Limestone.—The limestone comes from fifty-four quarries scattered over the following counties, named in order of output: Warren, \$128,000; Jefferson, \$76,000; Kenton, \$36,000; Fayette, \$17,300; Pendleton, \$14,000; Lyon, \$7,000, and smaller amounts from Jessamine, Menifee, Logan, Montgomery, Caldwell, Crittenden, Boyd, Marion, Hardin, Washington, Carter and Trigg. The purposes for which the stone was used were mainly for building, to which was devoted the amount valued at \$187,570; \$24,414 is the value of lime produced. To street work an amount valued at \$86,054 was applied. Smaller amounts were used for flux and for bridge work. The product of Warren is deserving of special notice because of its peculiarities and its value as a building stone. This stone is known commercially as Bowling Green oölite. It is quite different from the oölitic stone of Indiana, inasmuch as it belongs to another limestone group, the constituent globules being large and distinct, whereas in most of the Indiana stone they are minute. It is quite similar to the Portland oölite of Ireland. The following analyses of Bowling Green and Portland oölite show the similarity between the two:

Composition of Bowling Green, Kentucky, limestone compared with Portland, Ireland, limestone.

	Bowling Green.	Portland.
	<i>Per cent.</i>	<i>Per cent.</i>
Carbonate of lime	95.31	95.16
Carbonate of magnesia.....	1.12	1.20
Silica.....	1.42	1.20
Water and loss.....	1.76	1.94
Iron and alumina.....	.39	.50
Total.....	100.00	100.00

The quarries are of large extent, well equipped with channeling machines, derricks, etc. A mill with twelve gangs of saws finishes the stone. Blocks of almost any size can be furnished. These quarries

were first opened in 1833, but until recently they were operated in the most primitive manner, and while the product has been used chiefly in the South, efforts are now being made to introduce the stone to the building trade of the northern States. Among the cities in which it has been most used are Louisville, Memphis, Nashville, and Bowling Green; to some extent also in Chicago. The stone is soft and easily worked, and like the Indiana stone hardens on exposure to the atmosphere. Carvings made upon the stone stand exposure to the air very well. Its color under the influence of sunlight tends to become continually lighter. Its crushing strength is such as to enable it to resist a pressure of 3,000 pounds to the square inch. When heated to redness on the surface and plunged into cold water it revealed no crack, even upon examination with a magnifying glass, and in some cases on being reheated for a second and third time and plunged into water still failed to present indications of cracking. According to present indications, the extended application of the stone in the northern and eastern portions of the country seems highly probable.

Sandstone.—The sandstone is produced from eleven quarries operated in seven counties of the State, namely: Rowan, \$52,400, Muhlenberg, \$25,000, Lewis, \$24,900, Bell, \$5,000, and smaller amounts from Crittenden, Rockcastle and Ohio. The greater portion of the stone, namely, \$77,877 worth, was used for building purposes, \$38,463 for bridge work, and a small quantity for street purposes.

MAINE.

The kinds of stone produced in this State, in order of commercial importance, are granite, limestone, and slate.

Granite.—In the value of granite produced in 1889 this State stood second in the list of all granite-producing States of the Union. The total value of the product was \$2,225,839. The counties producing this product are, in order of their importance: Knox, \$844,638, Hancock, \$685,720, Waldo, \$165,603, Kennebec, \$136,270, Washington, \$106,025, York, \$88,567, Franklin, \$72,033, and smaller amounts in Lincoln, Somerset, Penobscot, Cumberland, Androscoggin and Oxford. From the first seven counties above named comes the great bulk of the entire product. The most productive counties are those along the coast. The value of the granite devoted to building purposes is \$839,125. In the value of stone devoted to this purpose Maine is second only to Massachusetts, but in the value of stone devoted to street work, it stands first among all the granite-producing States, the total value of stone devoted to street work being \$927,949. Of this amount \$824,113 was the value of paving blocks, which were shipped to most of the large cities on the Atlantic coast, principally to New York. Considerable was devoted to cemetery and monumental work. Although Maine doubtless possesses much stone well adapted to these uses, it stands in fourth place among the granite-producing States in the value of output

for these purposes, being preceded by Rhode Island, Massachusetts, and Vermont, in the order named. The vast resources of this State in granite have been utilized to only a small fraction of the possibilities. The quarries situated along the coast have great advantages in the matter of transportation, inasmuch as this is largely by water and freight rates are naturally low. The granite quarries offer very excellent conditions for being worked. The stone opens easily, having peculiar co-hate joints that are such striking features of the syenite or granite of New England. Then there are generally at least two of these rift lines and there is a more or less complete division by what appear to be true beds as well as joints, so that the division of the rock is as complete as could be desired. At the same time the lines of weakness are not so numerous as to make the quarried masses in many cases too small for use, as is sometimes true of other regions. Many of the quarries on the coast are conducted on a very large scale with all the latest most improved facilities, not only for quarrying but for the subsequent handling and preparation of the stone for market. A shaft of granite 115 feet long and 10 feet square at the base and weighing 850 tons has recently been quarried. It is claimed to be the largest piece of stone ever quarried. It has not yet been utilized but is lying in the quarry yards at Vinal Haven. The color of the granite produced from quarries in Maine varies from light gray to black and red. From the commercial standpoint the most important are the lightest in color and the gray. The grain of the stone varies very much in size, that quarried at Augusta being quite fine, while the other extreme is seen in the product of the Biddeford quarries. The light-colored stone comes from Biddeford, Pownal, Norway, Lewiston, North Jay, and Augusta. In many cases the light-colored granite is interspersed with black spots of mica which render it unfit for fine work. Veins of quartz, and of quartz and feldspar are often quite troublesome. In many of the ledges, as for example those in Augusta, the stone lies in beds or sheets which are very easily loosened by a single blast. In many of the small quarries the method of quarrying and the tools employed are simple and have undergone little improvement. This, however, is not true of the largest plants for producing this stone. Stone from South Thomaston and St. George is very dark in color and in the latter town are quarries of black stone and the only ones worked to any extent in the western portion of the State. The black granite is largely worked into monuments and it presents very fine contrasts between the black, polished faces and the lighter-colored hammered parts. Quite a large number of small quarries are operated by men whose main occupation is farming, but who work quarries for a small part of the year and with few quarrymen. The usual method in such cases is to secure a few contracts after haying season and they are fulfilled before cold weather. Such firms as these rarely keep any books and it was extremely difficult to determine the exact amount of yearly business done by them.

Limestone.—The limestone of Maine, and which is converted entirely into lime, comes for the greater part from Knox county. Smaller quantities are also produced in Waldo and Penobscot counties. In this limestone region there are sixty quarries producing stone which is converted almost on the spot into lime. The total value of the lime produced in 1889 was \$1,523,499. The stone is almost inexhaustible in quantity and is admirably adapted to the purpose for which it is used. Operations of quarrying consist simply in blasting by means of dynamite, which breaks the stone up at once into sizes suitable for use in the kilns. It is then hoisted out by means of improved cables and machinery and sent directly to the limekiln, which are favorably situated for transportation by water. The stone is partially crystalline, but very coarse grained. Fine crystals of calcite are very numerous and gypsum also occurs. The operations at the quarries near Rockland are all below the surface of the ground. The fuel used in the kilns is entirely wood, which is imported from Canada. The stone produced for burning into lime is not measured as such, but is measured only by the quantity of lime produced from it, so that in speaking of the amount of stone quarried the producers name the amounts of lime obtained from it, and the unit of measurement is a bushel or barrel of lime. The lime produced at Rockland is of fine character and is the standard lime of New York City, to which it is shipped in enormous quantities. Boston also forms an important market for the product.

Slate.—The slate product of Maine comes entirely from quarries in Piscataquis county. The output in 1889 was valued at \$219,500 for roofing purposes. This slate is of very superior quality.

New and prospective developments.—New granite quarries were opened during 1890 by the following firms: Messrs. Graves Bros., Northeast Bar Harbor; Mr. J. P. Fogg, of Pownal, and the Norway Granite Company, of Norway.

MARYLAND.

Granite, limestone, marble, and slate are produced in this State.

Granite.—Twenty-two quarries in Baltimore, Cecil, and Howard counties were operated in 1889, producing an output valued at a total of \$447,489. Of this amount Baltimore County yielded stone valued at \$223,070; Cecil, \$219,863; and a smaller amount came from Howard County. The granite quarry at Port Deposit has won a wide reputation for the satisfactory stone produced. Throughout the mass of this granite, as it occurs in the quarry, seams occur at intervals from about one-half inch to a number of feet, and while they are discernible only by an experienced eye, they are very valuable in the operations of quarrying and can be opened readily by means of wedge and feather. They frequently reveal a perfectly level surface, ready at once for use in building without the intervention of the stonecutter. The expense of preparing the rock for use in the wall is accordingly reduced. The

stone is very hard, takes a beautiful polish, retains its color, and can be gotten out in enormous blocks, larger, indeed, than it is advisable under ordinary circumstances to handle. It was used in the construction of the piers of the Baltimore and Ohio railroad bridge across the Susquehanna river near Perryville, and has given entire satisfaction in this work.

New and prospective developments.—In the spring and summer of 1890 the following firms began the operation of granite quarries: E. S. Johnson, of Guilford; Benjamin Kepner, of Port Deposit; Oliver and Peach, Granite; and M. C. Pyle & Son, of Pylesville. The Maryland Granite Company was incorporated, with a capital stock of \$200,000, in December, 1890. Its object is to operate granite quarries and to do a general stone-contracting business. They are said to have purchased 184 acres of land at Deer Creek for the development of granite. The African Granite Company was incorporated at Baltimore during 1890, with a capital stock of \$30,000.

Sandstone.—Sandstone was produced in this State in 1889, in Allegany and Frederick counties, in small amounts, the total value of the product of the State being valued at only \$10,605. The Potomac Red Sandstone Company is operating sandstone quarries on the Potomac river, about 20 miles above Washington, in Montgomery county. This stone has been quarried since 1884, but for a period of nine years previous to that date there was no production. This production was originally known as Seneca red sandstone. It has been used in quite a large number of buildings in Washington City, notably the Smithsonian Institution. From all the evidence which has been submitted, it appears to be one of the best red sandstones in the country. Many of the strong and unqualified indorsements of this stone appear as the favorable result of an investigation of a committee of Congress appointed to investigate the use of this stone in the construction of the War, State, and Navy Department building in Washington.

Limestone.—Ordinary limestone from thirty quarries was produced in 1889 to an amount valued at \$164,860. The productive counties were the following: Baltimore, \$102,350; Frederick, \$38,296; Washington, \$15,184; and much smaller amounts from Carroll, Allegany, and Howard counties. The great bulk of the product was used in the production of lime, which was valued at \$148,432. The remainder was used for building and street work, and to some extent as a flux and in bridge and railroad work.

New and prospective developments.—The Frederick Lime Company, of Frederick county, has been incorporated with a capital stock of \$50,000 to develop limestone quarries for the manufacture of lime. Operations began in November, 1890.

Slate.—The slate product of Maryland comes from what is known as the Peach Bottom region, in the northern part of Harford county, where there were five quarries in operation in 1889. They produced an

output valued at \$110,008. For a more detailed description of what is known as the Peach Bottom region and of the slate produced from it, see the report on Pennsylvania in this volume.

Marble.—The production of marble proper is limited to Baltimore county, at a number of points in the vicinity of Baltimore, along the Northern Central railroad. The total value of the output in 1889 was \$119,675. In Harford county green serpentine was quarried from a single locality. While this is by no means marble in constitution, it is nevertheless used for purposes to which marble is continually applied, and it therefore enters into competition with marble in the market. This stone is an exceedingly valuable one for purposes of interior decoration and furniture tops. The quarry was opened in the year 1880, and has been in operation ever since that time.

The following is an analysis of Harford county serpentine made by Dr. F. A. Genth, of Philadelphia.

Analysis of serpentine from Harford county, Maryland.

	Per cent.
Silicic acid	40.06
Alumina	1.37
Chromic oxide20
Nickel oxide71
Ferrous oxide	3.43
Manganous oxide09
Magnesia	39.02
Water	12.10
Magnetic iron	3.02
Total	100.00

The specific gravity of the stone is 2.668; hardness, 4 on a scale of 10.

New and prospective developments.—The Texas Lime Company began operations in quarrying marble for the production of lime in February, 1890. The Lake Chrome and Mineral Company opened a serpentine quarry in Harford county early in 1890.

MASSACHUSETTS.

Granite, sandstone, limestone, and marble are produced in this State.

Granite.—In the granite industry Massachusetts stood in first place among the granite-producing States in 1880 as well as 1889. It will moreover probably continue to hold this position for some years to come. The value of the granite output, according to the Tenth Census, in 1880 was \$1,329,315. The corresponding figures for 1889 are \$2,503,503. There were in 1889, 151 quarries, distributed over the following counties, named in order of value of product: Essex, \$778,366; Worcester, \$751,413; Norfolk, \$485,353; Middlesex, \$172,161; Bristol, \$164,337; Hampden, \$112,849, and very small quantities also from Franklin and Hampshire counties. The product was most largely used for general building purposes, the value of the stone devoted to those purposes being \$1,362,451. The value of the product devoted to

cemetery uses was \$497,438; for street work, \$466,147. The remainder was devoted to bridge, dam, and railroad work, and to various miscellaneous uses. It is evident that the granite comes mainly from the counties along the eastern coast and principally from the northeastern part of the State.

Among the various granites of the State that quarried at Quincy, which is a bluish-gray syenite, is perhaps the most interesting. It was the first to acquire a reputation, and the success of the Quincy granite did much towards stimulating search for similar products in other parts of the State. The quarries on Cape Ann, in Essex county, are being very rapidly and successfully developed, the quality of the stone produced here leaving little to be desired. Transportation facilities at the Cape Ann quarries could hardly be better, in view of the fact that they are immediately on the coast and, furthermore, in immediate communication with the Old Colony railroad. There is still, however, considerable need of good harbors at this locality, and considerable money must yet be spent there before quarrying can increase as it should.

The products of Massachusetts granite are so well known all over the country that it is necessary to say but little here in regard to them. Stone for all purposes is shipped all over the United States. The methods of quarrying and of cutting and polishing the stone in vogue in this State are fully up to date.

The following is an analysis of Bradford red granite, made by L. P. Kinnicutt, Ph. D., of the Worcester Polytechnic Institute.

Analysis of Bradford, Massachusetts, red granite.

	Per cent.
Silica	72.73
Alumina and oxide of iron.....	16.95
Lime.....	1.05
Magnesia.....	trace.
Potassium oxide.....	8.15
Sodium oxide.....	.90
Loss and undetermined.....	.22
Total.....	100.00

The following is an analysis of Worcester granite. The analysis was made by Prof. C. F. Chandler, of New York.

Analysis of Worcester, Massachusetts, granite.

	Per cent.
Silica.....	76.07
Alumina.....	12.67
Iron peroxide.....	2.00
Manganese oxide.....	.63
Lime.....	.85
Magnesia.....	.10
Potash.....	4.71
Soda.....	3.37
Total.....	99.80

New and prospective developments.—New granite quarries were opened at various times in 1890 by the following firms: Messrs. Rowley & Hanscombe, of Lauesville; the Braintree Granite Company, of Boston; Messrs. Jones & Desmond, of West Quincy; Messrs. McDonald & Turner, of Quincy; the Old Colony Railroad Company, of Boston, and Messrs. Charles Johnson & Bros., of Quincy. Mr. J. T. Tank, of Providence, Rhode Island, opened a quarry in Worcester county.

Sandstone.—Sandstone was produced from 21 quarries, to an amount valued at \$649,097. The most important county is Hampden, in which the product was valued at \$563,179. Suffolk county produced an amount valued at \$82,018, while very small amounts came from Norfolk and Hampshire counties. The product is almost entirely used for general building purposes.

The following is an analysis of so-called Maynard sandstone, made by Dr. L. P. Kinnicutt.

Analysis of Maynard, Massachusetts, sandstone.

	Per cent.
Silica	79.38
Oxide of iron	2.43
Alumina	8.75
Lime	2.57
Soda and potassa	4.08
Carbonic acid, water, and loss	2.79
Total	100.00

The following is an analysis of Worcester sandstone, made by Dr. L. P. Kinnicutt.

Analysis of Worcester, Massachusetts, sandstone.

	Per cent.
Silica	88.89
Alumina	5.95
Iron oxide	1.79
Manganese dioxide41
Lime27
Potassa and soda86
Carbonic acid, water, and loss	1.83
Total	100.00

The following is an analysis of Kibbe quartz sandstone, made by Prof. C. F. Chandler, of New York.

Analysis of Kibbe, Massachusetts, quartz sandstone.

	Per cent.
Silica	81.38
Alumina	9.44
Oxide of iron	3.54
Lime76
Oxide of manganese11
Magnesia28
Carbonic acid, water, and loss	4.49
Total	100.00

Limestone.—The limestone of Massachusetts comes from twelve quarries in Berkshire county, in the western part of the State. The total product in 1889 was valued at \$119,978. Most of it was used for burning into lime. The remainder was devoted to building purposes and flux.

The following is an analysis of limestone from Berkshire county:

Analysis of Berkshire county, Massachusetts, limestone.

	Per cent.
Lime.....	95.66
Magnesia.....	.76
Oxide of iron and alumina.....	.17
Silica.....	1.14
Carbonic acid.....	None.
Loss at red heat (water).....	3.00
- Total.....	100.73

Marble.—Marble was produced in small amount at Lee, Berkshire county.

MICHIGAN.

In 1889 sandstone, limestone, and slate were produced in this State.

Sandstone.—This was valued at \$246,570. By far the most important producing county is Houghton, which yielded a product valued at \$165,000. Marquette county, with a product valued at \$35,970 stood second, while smaller amounts were produced in Huron, Ionia, Ottawa and Hillsdale counties. Most of the product was used for building purposes, although it is important to note that \$27,800 worth were used for abrasive purposes, Michigan being one of the three or four States producing good abrasive material.

Limestone.—Limestone valued at a total of \$85,952 was produced in the following counties, named in order of their importance: Huron, \$40,272; Wayne, \$16,715; Emmet, \$13,100; and smaller amounts from Monroe, Delta and Alpena counties. Most of the product was used for building purposes, although some was burned into lime, and a slightly larger quantity used for street work, the rest being devoted for fluxing uses.

Slate.—The value of the slate produced in Baraga county was \$15,000.

Marble.—Marble has been discovered at Ishpeming, Marquette county, and is said to be of very fine quality, even comparing favorably with the Mexican onyx. It must be said, however, that no full and definite information is yet at hand in regard to this discovery.

MINNESOTA.

The advances made by this State in the stone industry since 1880 are very remarkable. According to the census of 1880 the total number of quarries in Minnesota was 41 for all kinds of stone, and the total value of the product in that year was \$255,818. In 1889 there were 102 quar-

ries producing limestone, granite, and sandstone. The total value of the product of all kinds of stone in that year was \$1,102,008.

Granite.—The value of the granite produced in 1889 was \$356,782. The product came from 23 quarries scattered over the following counties: Stearns, \$139,265, Benton, \$110,650, Bigstone, \$95,000. Decidedly smaller quantities came from Sherburne, Morrison and Nicollet. The productive counties in 1880 were Benton, Sherburne and Chisago, and the product at that time was valued at \$28,815. The figures speak plainly for themselves as to the great strides which have been made in granite production. The product was devoted most largely to building, the value of the stone thus used being \$209,396; for street work an amount valued at \$141,554 was applied. Comparatively very small amounts were devoted to cemetery and bridge work.

Sandstone.—The value of the sandstone output in 1880 was \$41,150; in 1889 it was \$131,979. The product came from seven quarries operated in the following counties: Pine, \$89,750, Pipestone, \$20,279, St. Louis, \$13,950, and smaller amounts in Houston, Rock and Scott counties. Of the total value, \$82,000 worth was devoted to building purposes and the remainder between street and bridge work. The developments which have been made in Pipestone county in what is commercially known as "Pipestone red jasper" are of particular interest. This is a metamorphic quartzite rock of intense hardness, varying in color from cherry to lavender or violet. Its extreme hardness is another important characteristic. The following analysis was made by Dr. C. T. Jackson:

Analysis of red pipestone from Pipestone county, Minnesota.

	Per cent.
Water.....	8.4
Silica.....	48.2
Alumina.....	28.2
Magnesia.....	6.0
Peroxide of iron.....	5.0
Oxide of manganese.....	.6
Carbonate of lime.....	2.6
Loss.....	1.0
Total.....	100.0

The following tests of this stone have been made:

Tests of Minnesota red pipestone.

Crushing strength.....	pounds per square inch..	23,000
Specific gravity.....		2.8
Weight per cubic foot.....	pounds..	170.6

On account of its color and desirable properties which tend to make the stone durable, it is quite popular as a building material and has already been used in the construction of quite a large number of important buildings.

Limestone.—In 1880 limestone was produced from thirty-three quarries scattered over eleven counties of the State. In 1889 the limestone

came from seventy-two quarries contained in fifteen counties. Named in the order of the value of their output, these counties are as follows: Hennepin, \$137,728; Blue Earth, \$127,279; Ramsey, \$103,929; Goodhue, \$95,938; Le Sueur, \$41,553; Scott, \$34,030; Washington, \$16,387; Winona, \$13,695; Wabasha, \$12,050; Rice, \$9,700, and smaller amounts from Dodge, Houston, Brown, Fillmore and Olmsted. The total product was valued at \$613,247. Of this an amount valued at \$380,556 was used for building purposes, while \$124,266 was the value of the lime produced. Smaller amounts were devoted to street and bridge work. The great bulk of the limestone comes from counties situated in the southeastern part of the State, where the cities of Minneapolis and Saint Paul form important outlets.

MISSOURI.

The kinds of stone produced in this State are granite, sandstone and limestone.

Granite.—The total value of the granite produced in 1889 is \$500,642. The product came from four neighboring counties in the southeastern part of the State. They are as follows: Iron, \$373,558; Wayne, \$63,842; Saint Francois, \$60,842, and smaller amounts from Madison county. There are ten quarries contained in this area. The stone was about equally divided between general building purposes and paving blocks. The value of the stone devoted to building is \$219,518. The value of paving blocks produced is \$216,986. To bridge, dam and railroad work an amount valued at \$63,638 was applied. A very small quantity was devoted to cemetery uses. The granite-quarrying industry dates back to a short time previous to 1880, but it at present bids fair to develop into an industry of considerable importance to the State. The most extensive quarries are at Graniteville, Iron county. The various plants at this locality are well equipped and supplied with improved machinery. Many of the finest buildings in Saint Louis have been constructed of this stone. At Granite Bend, Wayne county, are extensive granite quarries well equipped. In 1887 a shaft 85 feet deep with drifts extending from the bottom of the shaft in various directions was sunk. It was then charged with 32,700 pounds of black powder. The result of the blast was such that they have stone enough broken up to supply the demands of the firm for fifty years. The cost of the blast was \$16,000. Unquestionably the granite industry in Missouri, although at present in its infancy, may easily assume vast proportions in the near future.

Sandstone.—Sandstone valued at a total of \$155,557 was quarried in the following counties of the State: Johnson, \$100,184; St. Clair, \$15,000; Cape Girardeau, \$12,734, and smaller amounts in Carroll, Barton, Saline, Franklin, Vernon, Holt, Lewis, Buchanan and Henry counties.

Limestone.—The limestone industry in Missouri is a very large and important one. A product valued at \$1,859,960 was produced in 1889. This includes the value of all lime produced, namely, to an amount valued at \$465,390. The productive counties are the following: Saint Louis, \$870,276; Jackson, \$211,743; Marion, \$151,908; Greene, \$103,324; Buchanan, \$82,301; Dade, \$72,327; Pike, \$68,127; Jasper, \$41,000; Perry, \$33,070; Clark, \$28,563; Mercer, \$26,287; Lawrence, \$26,060; Callaway, \$24,500; and smaller amounts in Jefferson, Lewis, Wright, Cape Girardeau, Livingston, Andrew, St. Charles, Macon, Clay, Pettis, Cole, Linn, Caldwell, Sullivan, Randolph, Ray, Harrison, Monroe, Saline, Boone, Henry, De Kalb, Webster and Nodaway. The purposes to which the product was devoted are as follows: For building purposes, \$542,871; the value of lime produced, \$465,390; for street work, \$670,351; for bridge, dam, and railroad work, \$169,720, and small amounts for flux and miscellaneous uses. It is evident that by far the most important county producing limestone is Saint Louis county. Many quarries in and around the city of Saint Louis are operated. The stone is used for purposes of heavy construction, such as bridge and railroad masonry, building, paving, macadam, riprap, and the manufacture of lime. It is of excellent quality and shows great strength. In some of the quarries steam drills are in use, but in most of them the old methods are adhered to. The manufacture of a superior quality of lime in Saint Louis has grown to be an immense industry. Most of the kilns are located just outside of the city limits; they are well equipped and numerous. The product is almost entirely used in Saint Louis.

The following are analyses of limestone from various localities:

Analysis of Marion county, Missouri, limestone.

[By Regis Chauvenet & Brother.]

	Per cent.
Silica.....	.08
Alumina and oxide of iron.....	.40
Magnesia.....	.02
Carbonate of lime.....	98.80
Total	99.30

These chemists state that this is the purest sample of limestone they have ever analyzed, leaving nothing to be desired for whiteness and purity.

Analysis of Ash Grove white lime.

[By Charles W. Eoff, chemist.]

	Per cent.
Carbonate of lime	99.815
Magnesia	Trace.
Alumina054
Oxide of manganese	Trace.
Oxide of iron011
Silicic acid12
Phosphoric acid	None.
Sulphuric acid	Trace.
Total	100.000

Analysis of Champion white limestone, Ash Grove, Missouri.

[By W. D. Church.]

	Per cent.
Carbonate of lime	92.750
Carbonate of magnesia	3.260
Silica and insoluble matter495
Alumina480
Oxide of iron400
Sulphate of calcium	Trace.
Water675
Alkalies and loss	1.940
Total	100.000

Analysis of limestone from Saint Louis county.

	Per cent.
Carbonate of lime	97.76
Carbonate of magnesia12
Insoluble matter26
Oxide of iron20
Total	98.34

Analysis of Lawrence county limestone.

[By J. F. Elson, of New Albany, Indiana.]

	Per cent.
Carbonate of lime	85.373
Carbonate of magnesia	12.112
Silica	1.289
Alumina	1.134
Iron001
Undetermined091
Total	100.000

In northern Missouri limestone is found in every county and is quarried to a greater or less extent over the entire region. With but a few exceptions the quarries are worked on a small scale. The product is used in the immediate vicinity for foundations, cellars, wells, etc. The quarries are generally owned and operated by farmers, who do no work beyond the immediate local demand. Lack of facilities for transportation makes quarrying too expensive to be entered into as a business. Quarries adjacent to Government works on the Missouri and Mississippi rivers have supplied quite an amount for riprap. At Ash Grove, Missouri, are very extensive limekilns. A large quantity of lime is manufactured of a superior quality. The demand for this lime is very great. It is largely shipped to Alabama, Tennessee, Texas, Arkansas and Kansas, besides being also very largely used in Missouri. Extensive plants for burning limestone into lime are operated at Springfield, the product being used in Springfield, Kansas City and Saint Louis. At Cape Girardeau a large quantity of lime of good quality is also produced. At this locality crude petroleum is used as fuel, and it is claimed that a whiter and stronger lime is obtained than can be produced by either wood or coal. The limestone quarries at Grafton produced stone which has been found most excellently adapted for foundation purposes. It is the stone chiefly used in the construction of the great Edes bridge across the Mississippi river.

Onyx.—Quite recently discoveries of onyx have been made in Crawford and Pulaski counties; also in Wright county a deposit has been discovered. A company has been formed to develop the industry and active work will soon be begun. This onyx is taken from what is known as the Ozark region, being found in caves in the Ozark mountains within 70 miles of Saint Louis.

MONTANA.

Granite.—Granite was produced from a single quarry in Lewis and Clarke county in comparatively small amount. It was entirely used for building purposes.

Limestone.—Limestone was produced to the value of \$24,964 from four quarries situated, in the order of their values, in Jefferson, Missoula, Park and Cascade counties. Sixteen thousand dollars worth of the product was used as flux and a small quantity for burning into lime, and about \$8,000 worth for building purposes.

Sandstone.—Six quarries at various localities in Deer Lodge, Cascade, Custer and Yellowstone counties produced sandstone valued at \$31,648. It was entirely used for building. About half the product came from Deer Lodge county.

NEBRASKA.

Limestone only was produced in this State. The value of the output was in 1889, \$207,019, including the value of lime produced from it.

The productive counties are as follows: Cass, \$148,567; Gage, \$24,552; Sarpy, \$13,339, and smaller amounts from Nemaha, Jefferson, Pawnee and Thayer. Ninety thousand five hundred and forty-two dollars worth were used for building; \$86,643 for street work, while for flux and bridge work smaller amounts were used. The product comes entirely from the southeastern part of the State.

NEVADA.

This State produced very small quantities of granite and sandstone. The granite came from Washoe county. A new granite quarry was opened in September, 1890, by Mr. J. M. McCormick, of Reno.

The sandstone came from Ormsby county.

The product of this State was sufficient in amount for nothing more than building and street work in Carson City, to which probably the most of it went.

NEW HAMPSHIRE.

Granite.—The granite produced in this State in 1889 was valued at \$727,531. The entire southern and middle parts of the State, with the exception of Belknap county, were productive of granite. There are seventy-eight quarries in the State, operating in the following counties: Carroll, \$197,284; Cheshire, \$189,590; Hillsboro, \$182,847; Merrimac, \$112,853; Strafford, \$22,535, and smaller amounts in Grafton, Sullivan and Rockingham counties. Of the total product an amount valued at \$324,567 was devoted to building purposes; to street work, \$252,256. Of this latter value \$87,569 was the value of the output of paving blocks. To cemetery and ornamental work an amount valued at \$135,029 was used. For bridge and miscellaneous purposes an amount valued at \$15,679 was used.

A resident of New Hampshire has developed a new use for granite, which consists in finely crushing the stone and afterwards molding it into the desired shape, and by the action of heat it is hardened and made to resemble closely the original granite, and it is said that to all appearances it is as strong and durable. Nothing can yet be said of the real value of this process, but experiments are yet being made.

New and prospective developments.—New granite quarries were opened in the spring, summer, and fall of 1890, by the following firms: Messrs. Bishop & Shalon, of Milford; Mr. William E. Elder, of Dover; Messrs. Lewis & Flanders, of Enfield; Mr. D. J. Winn, of Haverhill; the Troy Granite Company, of Worcester, Massachusetts (their quarry is located in Cheshire county, New Hampshire), and Mr. L. K. Hutchinson, of Milford.

Sandstone.—A trifling amount of sandstone, which, however, was entirely used for abrasive purposes, was produced in Grafton county in 1889.

NEW JERSEY.

Granite, sandstone, limestone, slate, and bluestone were produced in this State in 1889.

Granite.—The total value of the granite produced in New Jersey in 1889 was \$425,673. It came mainly from the northern and northeastern parts of the State, and the markets for it are largely New York City and Jersey City. The productive counties, in order of importance, are as follows: Somerset, \$86,250; Hudson, \$81,500; Essex, \$79,200; Sussex, \$52,000; Passaic, \$37,760; Mercer, \$27,513; Hunterdon, \$24,800, and smaller amounts in Union and Morris counties. There are in all twenty-three productive quarries. Of the total output an amount valued at \$236,310 was devoted to street work, including the value of all paving blocks produced, which amounted to \$168,555; to general building purposes an amount valued at \$42,175; for bridge, dam, and railroad work, \$147,063. A trifling amount was devoted to cemetery purposes.

New and prospective developments.—New quarries were opened in the spring and summer of 1890 by the following companies: The Waterloo Ice Company, of Newark; Thomas Nevins & Son, of Orange, and York & Bittenbender, of Belvidere.

Sandstone.—Sandstone was produced in 1889 to an amount valued at \$597,309. It came from twenty-six quarries, scattered over the following counties, named in order of importance: Essex, \$270,450; Hunterdon, \$173,007; Mercer, \$77,652; Passaic, \$63,200; and Somerset, \$13,000. The amount devoted to building purposes was valued at \$486,788; for bridge, dam, and railroad work the amount used was \$100,521.

Limestone.—The value of the limestone output of New Jersey in 1889 was \$129,662. It came from 33 quarries operated in the following counties: Sussex, \$72,529; Hunterdon, \$37,378, and smaller amounts in Warren, Somerset and Morris counties. The value of the lime produced was \$99,406; for flux an amount valued at \$29,620 was used, and a trifling amount for building. The following is an analysis of Hunterdon county limestone:

Analysis of Hunterdon county, New Jersey, limestone.

	Per cent.
Carbonate of lime	53.643
Silica	2.100
Carbonate of magnesia.....	40.750
Alumina252
Oxide of iron.....	.798
Total.....	97.543

This lime is especially valuable for fertilizing purposes.

Slate.—A small quantity of slate was produced in Sussex and Warren counties, New Jersey. Most of it was used for roofing purposes.

New and prospective developments.—A new slate quarry was opened by Messrs. Staton & Jones, at Lafayette, in the summer of 1890.

Bluestone.—Bluestone similar to that obtained in Pennsylvania and New York, and used mainly for flagging purposes, was produced in small quantities in Hunterdon and Sussex counties in 1889.

NEW MEXICO.

The kinds of stone produced in this Territory in 1889 were sandstone and limestone. The former was valued at \$186,804, the latter at only \$3,862.

Sandstone.—Sandstone was produced at eleven different quarries situated in the following counties, named in the order of their relative importance: San Miguel, \$139,124; Santa Fé, \$19,800; and Rio Arriba county, \$14,100. Small amounts also were produced in Valencia and Lincoln counties. Nearly the entire product was used for local building purposes, a very small quantity being devoted to street and bridge work.

Limestone.—The small limestone output was obtained from the following four counties: San Miguel, Lincoln, Sierra, and Santa Fé. The product was mostly burned into lime for local consumption.

Ricolite.—This name was given by Mrs. L. J. Cadwell, of Chicago, to a stone now quarried in the western part of Grant county. It resembles Mexican onyx, but is quite different in composition. It is susceptible of a very high polish, and is of a variety of colors. It can also be carved, and in this respect, as in others, differs from the Mexican onyx. Contracts to supply this stone for interior decoration in a number of buildings in Chicago have been signed.

NEW YORK.

The kinds of stone produced in this State include granite, sandstone, bluestone, limestone, marble, and slate. Among the stone-producing States New York stands third, being preceded by Pennsylvania and Ohio in the order named. In the number of kinds of stone produced, however, it is second to none.

Granite.—The value of the granite output in 1889 was \$222,773. The product comes from the following counties: Essex, \$85,200; Richmond, \$30,000; Orange, \$29,803; Westchester, \$16,000, and smaller amounts from Jefferson, Putnam and Rockland counties. The product was mainly used for building purposes, the amount devoted to these uses being valued at \$149,700. The remainder was divided between street, cemetery and ornamental work and bridge, dam and railroad uses.

Sandstone.—The sandstone of New York includes that which is recognized to the trade under the names of sandstone, brownstone, and bluestone, while the variety of sandstone known commercially as bluestone is hereinafter given by itself on account of its peculiar character and its almost exclusive application in street work for curbing and flagging. The value of the sandstone proper, exclusive of bluestone, produced in

1889 was \$702,419. The product came from sixty-three quarries scattered over the following counties: Orleans, \$573,773; Saint Lawrence, \$47,290, and smaller amounts from the following: Niagara, Oswego, Oneida, Jefferson, Chenango, Monroe, Allegany, Greene, Rockland, Washington, Tioga, Steuben, Schuyler, Franklin, Wyoming, Essex, Chautauqua, Otsego and Cattaraugus. Of the total amount produced, the value of that devoted to street work was \$459,158; to general building purposes an amount valued at \$241,216. A comparatively very small amount was devoted to bridge and miscellaneous work. As will be seen by an inspection of the productive counties, the greater part comes from the northwestern part of the State.

Among the sandstones deserving of special mention is what is known as the Potsdam red sandstone. This stone has been most thoroughly tested and has won a wide reputation for durability and its capacity to withstand the effects of strong heat and sudden cooling. It has been indorsed in a very unqualified manner by many of the leading authorities on structural material in the country.

New and prospective developments.—The following firms opened sandstone quarries in New York during 1890: Messrs. McVay, Tobin & Co., of Holley, Orleans county; Mr. Edward Jones, of Hulberton, New York, opened a sandstone quarry at Murray, Orleans county; Baldwin & Hinds, of Hindsburg, opened a sandstone quarry in Orleans county.

Bluestone.—This is the name given to the variety of sandstone which consists almost entirely of granules of silica cemented together by silica. The identity of this stone with sandstone is not generally recognized among the bluestone producers, and, in fact, many of them seem almost hurt if it is called sandstone. The bluestone industry is entirely distinct from what is herein given as the sandstone industry. Owing to the hardness and durability of bluestone, as well as the manner in which it occurs in the earth, it is well adapted to purposes of street paving, such as flagging and curbing, and most of it is devoted to these uses. A certain amount of the stone is quarried from regular organized quarries, with a definitely invested capital and plant, or facilities for quarrying, but in addition to stone taken from these regularly operated quarries a large amount is produced irregularly and spasmodically by men who invest no capital and have no definite organization as producers of stone. Their operations are conducted as follows: Provided with a very simple equipment of the most ordinary quarry tools they dislodge the stone found on land belonging to other persons and transport it to a number of shipping points, selling it there to dealers who make it a business to collect the stone in this manner and then ship it to the places where it is used. The dealers pay the individuals who quarry the stone an amount which simply compensates them for their time and labor, while the owner of the property receives a certain definite percentage from the dealer for the amount of stone thus taken from his land. During the year 1889, and a number of years previous,

some of the dealers at various points in New York State constituted the members of the Union Bluestone Company, with headquarters in New York city. Each member of this company was entitled to furnish a certain percentage of the total amount sold by this company in a given year. The dealers may, therefore, be regarded in a certain sense as producers. The land on which this stone is quarried is, generally speaking, of little value for anything but the bluestone contained in it. Originally, the stone was quarried for flagging only, but more recently it has been applied to quite a long list of purposes, such as rubble masonry, retaining walls and bridge stone, curbing, gutters, stepstones, flooring, vault covers, bases of tombstones, porch and hitching posts, house trimmings, such as platforms, steps, door and window sills, lintels and caps.

The stone is known commercially by quite a number of names which designate approximately the region from which it is taken. Among the names in common use may be mentioned the following: Hudson River bluestone, Hudson River flagging, North River bluestone, North River flagging, Pennsylvania bluestone, Wyoming Valley bluestone, Delaware River bluestone, Delaware flags, bluestone flagging and bluestone.

The value of the bluestone produced in New York in 1889 was \$1,303,321. This product came from 142 quarries in addition to numerous minor quarries or holes from which the product was taken by laborers, as has already been described. The productive counties are seen in the following list: Ulster, \$662,324; Delaware, \$150,866; Chenango, \$93,100; Sullivan, \$87,930; Wyoming, \$50,260; Schenectady, \$47,906; Orange, \$33,405; Albany, \$23,285, and smaller amounts from Otsego, Jefferson, Tompkins, Schoharie, Steuben, Seneca, Greene, Chemung, Broome, Saratoga, Oneida, Rockland, Franklin, Washington and Yates. The Union Bluestone Company, as organized in 1889, has dissolved.

New and prospective developments.—Messrs. Swartwout & Terry, of Read's Creek, Delaware county, and Mr. John McQuirk, of Hartwood, Sullivan county, New York, opened bluestone quarries during 1890.

Limestone.—Limestone, including the value of the lime made from it, was produced in 1889 to the value of \$1,708,830. The product came from 157 quarries distributed as shown in the following list of counties: Erie, \$331,011; Onondaga, \$180,849; Washington, \$172,987; Ulster, \$107,683; Rockland, \$104,000; Warren, \$103,600; Montgomery, \$95,319; Monroe, \$94,891; Westchester, \$83,313, and smaller amounts from Jefferson, Schoharie, Clinton, Niagara, Genesee, Cayuga, Albany, Oneida, Greene, Saint Lawrence, Orange, Saratoga, Lewis, Herkimer, Wayne, Seneca, Orleans, Essex, Fulton, Rensselaer, Madison, Otsego, Yates and Wyoming. The value of the lime produced is \$837,613. The stone used for building was valued at \$444,291. For street and road work an amount valued at \$197,091 was used, and for bridge, dam and railroad work \$175,736 worth.

New and prospective developments.—The following firms opened limestone quarries in 1890: Messrs. Schunacher & Edwards, of Buffalo, at Eggertsville, Erie county; Mr. J. H. Gould, Smiths Landing, Greene county; and Messrs. Andrews, Warner & Co., of Le Roy, Genesee county.

Marble.—The value of the marble output of this State in 1889 was \$354,197. The product came from thirteen quarries, operated in four counties of the State. They are as follows: St. Lawrence, \$138,200; Westchester, \$135,104; Columbia, \$54,717; and Warren, \$26,176. The St. Lawrence county marble varies from white to dark blue and green in color, and mixtures of these shades produce in some cases a mottled appearance. The stone is adapted to monumental work, but is mainly used for building purposes. In general it is too coarsely crystalline for fine carving, scroll work, or tracing. In Westchester county the most important localities producing marble are Tuckahoe and Pleasantville. This product is especially well adapted for use in the preparation of carbonic acid.

New and prospective developments.—The following persons opened marble quarries during 1890: Mr. Mark W. Spaulding, Rensselaer Falls, Saint Lawrence county; Mr. Thomas S. Clarkson, Potsdam, Saint Lawrence county; and Mr. John Webb, jr., Gouverneur, Saint Lawrence county. Mr. M. W. Spaulding, of Rensselaer Falls, also opened a serpentine marble quarry in July, 1890.

Slate.—The slate output of New York State in 1889 was valued at \$126,603. The product came from sixteen quarries in Washington county. This is the only locality in the world at which red slate is produced. The prices received for this variety of slate are much better than those which hold for the product from the neighboring slate regions of Vermont.

New and prospective developments.—Messrs. R. R. Jones & Co., of Middle Granville, Washington county, N. Y., opened a slate quarry during 1890.

NORTH CAROLINA.

Granite and a very small quantity of sandstone were produced in 1889. The granite was valued at \$146,627, and was obtained from twenty-two quarries scattered over the following counties, named in the order of their outputs: Vance, \$88,737; Iredell, \$22,860; Anson, \$10,000, and smaller amounts from McDowell, Rowan, Guilford, Gaston, Burke, and Wake counties. Of the total output \$44,000 worth was used for bridge work, \$42,000 for street work, and the rest was distributed between building and cemetery purposes.

New and prospective developments.—Three quarries of granite in the vicinity of Salisbury have recently been opened. The Stone Mountain Granite Company recently commenced operations in Rowan county. It is expected that quarries will be developed according to the most

improved methods, with a view of supplying local demands and also of putting the stone upon the market in competition with granite from Northern centers. Near Mount Ayre the Mount Ayre Granite Company has commenced quarrying operations on quite a large scale for the purpose of supplying paving blocks for a number of cities, among which may be specially mentioned Cincinnati, Ohio. The recently organized Dunn Mountain Granite Company, of Salisbury, is about to commence the development of granite quarries in that locality.

Sandstone.—A recent scientific examination of Moore county brown stone, contained in property in the vicinity of Carthage, has been made by Mr. Henry E. Colton, of Chattanooga, Tennessee. The results of this examination are decidedly favorable to the quality of the stone. It is probable that quarrying operations will be undertaken in the near future. The stone is so situated as to be quarried with a minimum of expense.

Marble.—A large deposit of white marble in McDowell county has been examined by experts and is reported both as being of fine quality and of large extent. A plant valued at \$50,000 has recently been established for the purpose of quarrying marble in Cherokee county.

Slate.—Deposits of slate in Montgomery county have recently been discovered, and steps toward their development have been taken by Mr. C. C. Wade. The North Carolina Slate Company has recently applied to the legislature of the State for an act of incorporation.

OHIO.

The kinds of stone produced in this State are exclusively sandstone and limestone. The total output of sandstone in 1889 was valued at \$3,046,656. In the production of sandstone Ohio stands in first place among the sandstone-producing States of the Union and second in the value of its total stone output. The next State in order in 1889 was Pennsylvania, with an output valued at \$1,609,159. It is thus evident that Ohio not only occupied first place, but was largely in advance of the State standing second.

Sandstone.—One hundred and ninety-two quarries were operated in 1889. The product came from the following counties, named in the order of the value of their output: Cuyahoga, \$1,118,409; Lorain, \$1,067,240; Stark, \$140,426; Scioto, \$71,700; Washington, \$59,736; Huron, \$59,118; Fairfield, \$57,162; Summit, \$50,310; Trumbull, \$41,440; Morrow, \$41,037; Wayne, \$29,250; Muskingum, \$25,095, and smaller amounts from Crawford, Richland, Holmes, Harrison, Tuscarawas, Belmont, Jefferson, Mahoning, Erie, Delaware, Franklin, Lucas, Meigs, Montgomery, Ross, Licking, Guernsey, Columbiana, Perry, Portage, Wood, Ashland, Pike and Lawrence. It is evident that by far the most of the stone comes from Cuyahoga and Lorain counties, in the northern part of the State. The stone was used for the following purposes: Building, \$1,846,918; abrasive purposes, \$525,548; street work, \$430,552, and the remainder

was used for bridge, dam, and railroad work and for miscellaneous purposes. In the production of stone for abrasive purposes Ohio stands first. The total value of the stone produced in 1889 for these purposes was \$580,000, so that it is evident that Ohio produces nearly the entire amount. Some of the sandstone quarries of Cuyahoga and Lorain counties are operated in a most thorough, complete, and economical manner; the latest appliances are in use, and for smoothness of working very few quarries in the country can compare with them. The operations of the Cleveland Stone Company are the most important. The use of the Knox system of blasting in the quarries of this company is attended with great success. The stone is of such a thoroughly homogenous character that the result of a blast by the Knox system is simply to move, slightly, large masses of stone without sprawling or weakening them in any manner. It might almost be said that one could stand upon the mass of rock while being blasted out without danger of personal injury.

The following are a number of analyses of sandstone taken from various quarries in the State:

Analyses of Ohio sandstone.

	No. 1. Buff.	No. 2. Berea.	No. 3. Euclid bluestone.	No. 4. Columbia.	No. 5. Elyria.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Silica.....	97.00	96.90	95.00	96.50	87.66
Alumina.....	2.50	1.72
Iron oxides.....	1.00	1.68	1.00	3.52
Lime.....	1.15	.55	1.00	.17
Magnesia.....20
Potash and soda.....	.64	.5550
Carbonic acid, water, and loss.....	.21	.32	1.50	2.00	2.03
Total.....	100.00	100.00	100.00	100.00	100.00

No. 1 came from Amherst, Ohio; No. 2, from Berea; No. 3, from Euclid county; No. 4, from Columbia county, and No. 5, from Grafton, Ohio.

The analyses of Nos. 1 and 2 were made by Messrs. J. H. Salesbury and John Eisenmann, respectively, and No. 5 by Mr. F. F. Jewett.

The sandstone of Ohio is so well known all over the country as a building and grindstone material that it is necessary to say very little here in regard to its desirable qualities. It is shipped practically over the entire United States.

New and prospective developments.—Developments of new quarries are rapidly being made both by companies long established as well as by new ones which are forming from year to year. The following firms opened new sandstone quarries during 1890: Mr. T. S. Gerhard, of Independence Township, Cuyahoga county; Mr. J. M. Crouch, of Gann, Knox county; Mr. J. N. Kisner, of Warsaw, Coshocton county; Mr. R. G. Garver, of Wilmot, Stark county; the Youngstown Stone Company, of Youngstown, Mahoning county; Messrs. Richard & Dicky, of Mill Rock, Columbiana county, and Mr. H. M. Friend, of Summit Hill, Ross county. The Uniontown Firestone Company, of Uniontown,

Pennsylvania, began to operate a sandstone quarry at New Lisbon, Columbiana county, in August of 1890.

Limestone.—The Ohio limestone, including the value of lime produced from it, amounted to a value of \$1,514,934 in 1889. It came from the following counties, named in the order of their importance: Ottawa, \$230,485; Stark, \$132,821; Erie, \$128,169; Clark, \$101,707; Miami, \$91,810; Montgomery, \$87,650; Wood, \$79,799; Franklin, \$76,778; Seneca, \$68,772; Lucas, \$53,568; Preble, \$52,700; Sandusky, \$52,122; Hamilton, \$49,683; Allen, \$42,515; Hancock, \$37,253; Highland, \$35,557; and smaller amounts from Greene, Hardin, Lawrence, Wyandotte, Butler, Delaware, Muskingum, Scioto, Shelby, Van Wert, Logan, Guernsey, Jackson, Putnam, Clermont, Crawford and Clinton. The value of the lime produced from the limestone of the State in 1889 was \$581,325. For building purposes an amount valued at \$407,388 was used; for street and road work the amount used was \$183,235. An amount valued at \$105,963 was used for flux. The remainder was devoted to bridge, dam and railroad work mainly. It is evident from the consideration of the productive counties that most of the limestone comes from the western part of the State, particularly the northwestern part.

The following analyses of limestone in Ohio are presented:

Analyses of Ohio limestone.

No.	Locality.	Carbonate of lime.	Carbonate of magnesia.	Alumina and oxide of iron.	Silica.	Organic matter.	Moisture.
		<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
1	Sandusky county.....	54.06	45.20	0.27	0.74
2	Wood county.....	53.98	43.25	.43	1.53
3	Seneca county.....	54.30	45.14	.16	.23
4	Marble Head, Ottawa county.....	83.20	15.8315	0.02	0.80
5	Marble Cliff, Franklin county ..	81.14	16.00	1.08	1.94
6	do.....	93.28	2.69	2.18	1.41
7	Kellys Island, Erie county	97.28	2.00	.27	.85
8	do.....	89.16	9.49	.25	1.05
9	do.....	87.35	10.68	.20	1.49
10	Athens county.....	86.58	11.00	.32	2.10
11	Fremont, Sandusky county.....	40.01	58.91	.50	.41
12	Portage, Wood county.....	55.92	38.21	1.92	3.92
13	Genoa.....	54.20	44.60	.79	.15
14	Fostoria.....	55.41	42.99	.65	.21
15	Put-in Bay, Ottawa county.....	59.28	38.52	.49	1.60
16	Springfield, Clarke county.....	50.91	41.09	1.39	5.50

The analyses of Nos. 1, 2, 3, 4, and 10 were made by Prof. Edward Orton, State geologist, Columbus, Ohio.

Analyses of limestone from Findlay, Hancock county, Ohio.

	<i>Per cent.</i>	<i>Per cent.</i>
Carbonate of lime.....	50.298	49.221
Carbonate of magnesia.....	42.000	37.837
Oxide of iron.....	2.021	4.101
Alumina.....	3.100	5.002
Silica.....	2.291	2.341
Sulphuric acid.....	Undetermined	1.285
Total.....	99.710	99.787

OREGON.

In 1889 Oregon produced granite, limestone, and sandstone.

Granite.—The counties producing granite are as follows: Columbia, Multnomah, Clackamas and Jackson. By far the most important is the first-named county, the product of which went entirely into paving blocks. Small quantities were used for building, cemetery purposes, and bridge work.

Limestone.—Forty-one thousand dollars is the value of both limestone and lime produced in Baker county, in the northwestern part of the State. It was used entirely for burning into lime and for flux.

Sandstone.—Sandstone was produced in Linn and Jackson counties in small amount. According to the tests which have been made, the sandstone appears to do very well as a cupola lining.

New and prospective developments.—Mr. L. M. Perkins, of Hudson, opened a new sandstone quarry in the summer of 1890.

Marble.—Extensive deposits of marble near Roseburg, Douglas county, have been opened by Messrs. Woodard & Willis, of that city. The product is said to resemble the famous Tennessee marble, and includes all colors. Future developments will have to determine the value of this discovery. The Variety Marble Company, of Roseburg, has put in machinery for the purpose of developing marble quarries in Douglas county.

PENNSYLVANIA.

Among all the States producing stone, Pennsylvania takes first place when all of the kinds of stone are considered, yielding a product valued at \$7,319,199. The total value of the entire stone product of the United States in 1889 was \$53,035,620. By comparing these figures, it will be noted that of the entire product Pennsylvania yielded 13.8 per cent. Its preëminence as a stone-producing State is due to the large amount of limestone and slate produced. In both of these kinds of stone Pennsylvania holds first place, and second place in the production of sandstone and bluestone. All of the various kinds of stone which are commercially distinguished from each other are produced in Pennsylvania. These kinds are, in the order of their relative importance for the State: Limestone, \$2,655,477; slate, \$2,011,726; sandstone, \$1,609,159; granite, \$623,252; bluestone, \$377,735, and marble, \$41,850.

Granite.—The total value of the granite output in 1889 was \$623,252. This product came from sixty-four quarries contained in the following counties: Delaware, \$122,279; Philadelphia, \$108,736; Montgomery, \$91,214; Bucks, \$90,884; Chester, \$66,398, and smaller amounts from Lancaster, Luzerne, Adams, Berks, Dauphin, Lehigh and York. Of the total output that devoted to street work is the most important, the value for this purpose being \$292,114. For general building purposes an amount valued at \$143,231 was used, and smaller amounts for bridge purposes. A little was used for cemetery work.

New and prospective developments.—Messrs. W. G. Cunningham & Co., of Philadelphia, opened a new granite quarry in Adams county in September, 1890.

Sandstone.—The total value of the sandstone produced in 1889 was \$1,609,159. The product came from the following-named counties, the most productive of which are in the northwestern, western, and southwestern parts of the States. The productive counties, in the order of their importance, are as follows: Beaver, \$344,038; Dauphin, \$243,219; Lawrence, \$130,973; Allegheny, \$120,315; Westmoreland, \$108,518; Montgomery, \$87,994; Lackawanna, \$72,260; Fayette, \$68,602; Luzerne, \$54,054; Somerset, \$51,717; and smaller amounts from Huntingdon, Bucks, Chester, Tioga, Philadelphia, Lancaster, Indiana, Berks, Blair, Lehigh, Erie, Lebanon, Clearfield, Lycoming, Venango, Jefferson, Cambria, Warren, Elk, Crawford, Armstrong, Clarion, McKean, Delaware, Greene and Susquehanna. Scattered over these are 159 quarries. Most of the product was used for building purposes, the amount devoted to this use being valued at \$777,123; for bridge work an amount valued at \$496,902 was used; for street work, \$175,062; to miscellaneous uses a smaller amount was devoted.

The following is an analysis made by Prof. Breneman, of Ithaca, New York, of a sandstone from Luzerne county:

Analysis of sandstone from Luzerne county, Pennsylvania.

	Per cent.
Silica and insoluble matter.....	94.00
Ferric oxide.....	1.98
Lime.....	1.10
Magnesia.....	1.00
Volatile matter at red heat (water and carbonic acid).....	1.92
Alumina.....	Trace.
Total.....	100.00

The specific gravity of this stone is 2.656.

Further tests made of this stone show it to be of fine quality, eminently fitted for street work.

Analysis of sandstone from McKee's Gap, Blair county, Pennsylvania.

	Per cent.
Silica.....	99.10
Iron and alumina.....	.60
Magnesia.....	Trace.
Loss on ignition.....	.25
Total.....	99.95

Below are given two analyses of sandstone from Fayette county. The quarry from which this stone was taken is operated by Messrs. W. C. & H. S. Drumm, of Layton's Station.

Analyses of sandstone from Fayette county, Pennsylvania.

	No. 1.	No. 2.
	<i>Per cent.</i>	<i>Per cent.</i>
Silica	96.54	99.46
Alumina	3.39	.45
Iron01	Trace.
Water06	.09
Total	100.00	100.00

No. 1 from Layton quarry.
No. 2 from Oakdale quarry.

New and prospective developments.—Sandstone quarries were opened in 1890 by the following firms: Messrs. Jute, Stratton & Foley, of Pittsburg, opened a sandstone quarry at Layton's Station. The Bellevue Land Company, of Washington, commenced operations upon a sandstone quarry; Mr. William E. Cunningham, of Pennsylvania, opened a brownstone quarry in Bucks county in December of 1890; Messrs. Robinson Brothers, of Homewood, Beaver county, began quarrying sandstone in August, 1890. The Middletown and Hummelstown Stone and Lime Company, of Middletown, began quarrying brownstone in the summer of 1890; Messrs. F. T. Scott's Sons, of York, opened a brownstone quarry in July, 1890; Messrs. Foster Brothers, of Allegheny, began quarrying brownstone at Homewood, Beaver county, in April, 1890.

Bluestone.—Bluestone is the name given to a variety of sandstone, which consists of grains or granules of silica cemented together by silica. This stone is used almost entirely for street work in the form of curbstones and flagging. It is quarried chiefly in New York State, although the product from Pennsylvania is scarcely to be distinguished from the New York stone, and enters into competition with it in the market. The total value of bluestone produced in Pennsylvania in 1889 was \$377,735. It came from seventy-two quarries reported in the following counties: Susquehanna, \$144,619; Pike, \$126,250; Wyoming, \$74,004; Bradford, \$16,476; and much smaller amounts in Monroe, Wayne, Lackawanna, Schuylkill and Lycoming counties.

Limestone.—The total value of the limestone produced in Pennsylvania in 1889 was \$2,655,477. Of the product, however, comparatively little was used as limestone itself, most of it being used for burning into lime and as blast-furnace flux. The productive counties, in order of their importance, are as follows: Montgomery, \$475,572; Lawrence, \$434,935; Chester, \$321,680; Lebanon, \$203,986; Lancaster, \$184,962; Northampton, \$171,674; York, \$135,575; Berks, \$129,651; Blair, \$122,665; Lehigh, \$85,559; Columbia, \$66,738; and smaller amounts in Huntingdon, Adams, Dauphin, Mifflin, Cumberland, Bedford, Lycoming, Franklin, Montour, Allegheny, Union, Bucks, Armstrong,

Northumberland, Somerset, Butler, Bradford, Beaver, Erie, Monroe, Crawford and Washington. For building purposes an amount valued at \$238,431 was used. The value of the lime produced, a large portion of which went for agricultural purposes, was \$1,195,955. For blast-furnace flux the value of the product consumed was \$949,083. The remainder was used for street and bridge work chiefly. It is probable that the amount named above as consumed for flux is smaller than the true amount. This is due to the fact that considerable quantities of limestone are quarried by blast-furnace establishments for fluxing purposes, of which, apparently, a careful account is not in all cases kept.

The following are analyses of the so-called Acme Avondale limestone of Chester county. The analyses were made by Messrs. Booth, Garrett and Blair, of Philadelphia:

Analyses of Acme limestone from Chester county, Pennsylvania.

	Dark colored stone.	Light colored stone.
	<i>Per cent.</i>	<i>Per cent.</i>
Carbonate of lime.....	73.07	94.82
Carbonate of magnesia.....	5.58	1.10
Oxide of iron and alumina.....	1.27	.13
Insoluble matter.....	20.87	4.34
Total.....	100.79	100.39

This stone shows a tendency to become popular as building stone, and its qualities generally render it desirable.

The following are analyses of stone from Hyndman, Bedford county, Pennsylvania, made by Mr. Otto Wirth, of Pittsburg:

Analyses of limestone from Hyndman, Bedford county, Pennsylvania.

	Blue stone.	Fossil stone.
	<i>Per cent.</i>	<i>Per cent.</i>
Insoluble matter.....	4.14	2.70
Carbonate of lime.....	95.76	97.30
Total.....	99.90	100.00

The following is an analysis of a limestone from a quarry in Armstrong county:

Analysis of Armstrong county, Pennsylvania, limestone.

	<i>Per cent.</i>
Carbonate of lime.....	96.007
Carbonate of magnesia.....	1.498
Oxide of iron and alumina.....	1.462
Phosphorus.....	.034
Silica.....	.790
Total.....	99.791

The following is an analysis of limestone from Midvale, Franklin county, by Prof. William P. Tourey, of Baltimore, Maryland:

Analysis of limestone from Midvale, Pennsylvania.

	Per cent.
Carbonate of lime	94.427
Carbonate of magnesia	3.880
Silica	1.700
Total.....	100.007

The following is an analysis of Franklin county limestone:

Analysis of limestone from Franklin county, Pennsylvania.

	Per cent.
Calcium carbonate	92.079
Magnesium carbonate.....	4.420
Iron.....	1.420
Silica	2.130
Total.....	100.049

The following are analyses of limestone from Fayette county:

Analyses of Fayette county, Pennsylvania, limestone.

	Per cent.	Per cent.	Per cent.
Calcium carbonate	95.210	95.180	94.460
Magnesium carbonate.....	3.400	1.840	3.520
Phosphorus005	.004	.005
Insoluble matter	1.385	2.976	1.980
Total.....	100.000	100.000	99.965

The following is an analysis of limestone from Columbia county:

Analysis of Columbia county, Pennsylvania, limestone.

	Per cent.
Carbonate of lime	90.47
Silica	6.08
Oxide of iron and alumina.....	1.36
Carbonaceous matter and water.....	1.50
Carbonate of magnesia.....	.59
Total.....	100.00

The following are analyses of limestone from Lime Ridge, Columbia county, Pennsylvania, by Messrs. Booth, Garrett, and Blair, of Philadelphia:

Analyses of limestone from Lime Ridge, Columbia county, Pennsylvania.

No.	Carbonate of lime.	Carbonate of magnesia.	Oxide of iron and alumina.	Phosphorus.	Siliceous matter.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
1.....	88.450	4.782	.660	.020	6.26
2.....	82.371	7.791	1.190	.023	8.83
3.....	70.981	5.630	3.444	.032	19.51
4.....	92.314	3.901	.530	.006	3.34
5.....	96.125	1.767	.500	.006	1.86
6.....	94.267	1.934	.550	.020	3.48
7.....	93.378	2.004	.630	.014	4.17

The following is an analysis of gray limestone from a quarry in Lawrence county, made by Mr. Otto Wirth, of Pittsburg:

Analysis of gray limestone from Lawrence county, Pennsylvania.

	Per cent.
Carbonate of lime.....	95.25
Carbonate of magnesia.....	1.03
Oxide of iron.....	.91
Alumina.....	.74
Silica.....	2.03
Phosphoric acid.....	.04
Sulphuric acid.....	Trace.
Total.....	100.00

The following is an analysis of East Conshohocken stone, Conshohocken, Montgomery county:

Analysis of East Conshohocken limestone, Montgomery county, Pennsylvania.

	Per cent.
Lime.....	51.600
Magnesia.....	8.300
Alumina.....	10.000
Oxide of iron.....	3.600
Silica.....	26.200
Phosphorus.....	.040
Sulphuric acid.....	.400
Total.....	100.140

The following is an analysis of limestone from Lawrence county:

Analysis of Lawrence county, Pennsylvania, limestone.

	Per cent.
Carbonate of lime.....	95.070
Carbonate of magnesia.....	.750
Silica.....	2.240
Phosphoric acid.....	.052
Oxide of iron and alumina.....	1.620
Organic matter.....	.150
Manganese.....	.100
Total.....	99.982
Phosphorus.....	.023

The following is an analysis of limestone from Hellertown, Northampton county:

Analysis of limestone from Hellertown, Northampton county, Pennsylvania.

	Per cent.
Carbonate of lime	53.875
Carbonate of magnesia	25.494
Sesquioxide of iron	4.060
Alumina	6.090
Silica	5.470
Phosphoric acid089
Sulphuric acid174
Manganese	1.016
Water and organic matter	3.640
Total	99.908

New and prospective developments.—Mr. Joseph Gassert, of Lebanon, began quarrying limestone for burning into lime in February, 1890. Limestone quarries were also opened during 1890 by Mr. J. B. K. Richenbach, of Leesport, Berks county, and William E. Laut, of Lancaster, Lancaster county.

Slate.—The slate industry of this State, everything considered, is perhaps the most interesting subdivision of its stone industry. The slate industry is in by far the greater part limited to Pennsylvania and Vermont. The total value of all slate produced in the United States in 1889 was \$3,482,513. The value of all slate produced in Pennsylvania in the same year was \$2,011,726. The total value of all slate produced in the State of Vermont was \$842,013. The importance of Pennsylvania as a slate-producing State is evident from these comparisons. While there is a great variety in the colors of the slate produced in Vermont, a similar statement does not apply to Pennsylvania, the product of which is entirely black, although a very fine distinction is locally made between black and a sort of bluish-black.

The actively quarried slate belt of Pennsylvania really begins in Sussex county, in the northeastern part of New Jersey, where, at La Fayette and Newton, there are slate quarries in operation, and also in Warren county, at Polkville. The Pennsylvania portion of this slate belt begins at the Delaware Water Gap, in the northeastern part of Northampton county, and extends through Northampton, Lehigh and Berks counties in a southwesterly direction. There is then a break filled up by Lebanon and Lancaster counties to the southwest, but in the southern part of York county operations in what is known as the Peach Bottom region reappear. Passing from the Delaware Water Gap in a southwesterly direction, the most important producing localities are as follows: Slateford, Mount Bethel, East Bangor, Pen Argyl, Wind Gap, Belfast, Edelman, Chapman Quarries, Treichlers, Danielsville, Walnutport, Slatington, Tripoli, Lynnport, Steinsville, and finally, in York county, a portion of what is known as the Peach Bottom region, which is for the most part in the northern part of

Harford county, Maryland. The most important localities in York county are West Bangor and Delta, which may be regarded as the principal points for the entire Peach Bottom region. The slate of Pennsylvania is frequently divided, more for commercial reasons than anything else, into the following regions: The Bangor region, the Lehigh, the Northampton Hard Vein, the Pen Argyl, and the Peach Bottom regions. The Bangor region is entirely within Northampton county, and is the most important. It includes quarries at Bangor, East Bangor, Mount Bethel, and Slateford; the Lehigh region includes Lehigh county entire, also a few quarries in Berks and Carbon counties, and also a small number of quarries in Northampton county on the side of the Lehigh river opposite Slatington; the Pen Argyl region embraces quarries at Pen Argyl and Wind Gap, in Northampton county. The Northampton Hard Vein region is especially distinguished on account of the extreme hardness of the slate as compared with that produced in other regions of the State. It includes the following localities: Chapman Quarries, Belfast, Edelman, Seemsville, and Treichlers, all in Northampton county. The Peach Bottom region includes four quarries in York county, Pennsylvania, and five in Harford county, Maryland.

One of the chief difficulties met with in quarrying the so-called "soft" slate of Pennsylvania is the occurrence of what are known as "ribbons." These ribbons are composed of foreign material and are exceedingly hard and interfere not a little with the smooth and economical quarrying of the slate. These ribbons are entirely wanting in the Peach Bottom slate, and this makes a great difference in the ease of quarrying in favor of the product of the Peach Bottom region. The slate produced at Chapman quarries and other localities quarrying the same kind of slate that is produced at this locality is so extremely hard that although it can be split with about the same readiness as the soft slate, it has to be sawed with diamond saws. This hardness is naturally an advantage to the slate, rendering it durable and nonabsorptive. For flagging purposes it is extremely adapted, chiefly on account of its hardness. The most important product into which this hard vein slate is made is roofing slate, although it finds considerable application for billiard tables, imposing stones, blackboards, cisterns, lintels, window sills, copings, ridgepoles, stairsteps, and floor tiles. For paving purposes it has given great satisfaction. For use in blackboards and school slates it does not appear to compare favorably with the output of Bangor and Lehigh.

Considering the slate product according to the counties, the following statement will suffice: Northampton, \$1,467,653; Lehigh, \$487,133; York, \$36,558, and very much smaller amounts from Berks and Carbon counties. There are in all 104 quarries. The value of all the slate produced for roofing purposes in 1889 was \$1,636,945; for other purposes the value amounted to \$374,831. It appears to be generally acknowledged that for the sum total of desirable qualities for roofing, the Peach

Bottom slate is far ahead of that from any other locality in Pennsylvania. The advantages are its unchangeable color, and the smooth and glassy appearance which it presents upon the roof, together with great durability.

The production of slate according to the various regions which have been enumerated for Pennsylvania is as follows: The Bangor region, \$707,162; Lehigh, \$690,382; Northampton Hard Vein region, \$184,595; Pen Argyl, \$393,030; Peach Bottom, including, however, that produced in Maryland, \$146,565.

The largest quarry in the State, and probably in the country, is the old Bangor quarry at Bangor. The dimensions of this quarry are 1,100 feet long, 350 feet wide, with an average depth of 175 feet. Operations are conducted on a very large scale here in every respect, two locomotive engines and a large number of cars being kept during a part of the year almost constantly employed in stripping and transporting the surface material to the dump.

Slate quarrying, not only in Pennsylvania but in all other States producing slate, is carried on almost entirely by the Welsh, in so far as skilled labor is concerned. This is of course due to the fact that operations of quarrying slate have been better studied in the enormous slate quarries of Wales than in any other part of the world, and naturally labor skilled in slate-quarrying comes from that country. For ordinary labor, such as stripping, Italians supply most of the demand. A large school-slate factory is in active operation at Bangor. In this factory the operations are carried on almost entirely by machinery, which is so perfect in its working that the manual labor required in attending to it is largely monopolized by children of both sexes. Similar statements may be made of large and prosperous school-slate factories in operation in Slatington and Walnutport. In the manufacture of roofing slate, boys are quite freely employed in the work of trimming the slates after they have been split to the proper thickness and approximate size. This practice enables the Welsh to keep the skilled work largely in their own hands, as they bring up their sons to learn the business after them, beginning with the light work of trimming, and as they grow older and stronger extending their work to the heavier operations.

Slate is well adapted for ornamental purposes after it has gone through the process of marbleizing. Quite a variety of stones and wood are thus imitated in a very successful manner. The following is a list of different kinds of stone which are thus imitated: Gray granite, Mexican onyx, fossil limestone, Devonshire marble, Tennessee marble, Circassian, Egyptian, and Pyrenees marble, and in fact all the better known varieties of variegated marble; also blue agate, red granite, red serpentine, the various kinds of woods, and petrified wood of California. As the industry progresses the number of different kinds of imitations increases. The slab to be marbleized is first rubbed by hand with fine sand, using a wooden block covered with cloth. The marbleizing proc-

ess is done in two ways. For the marble having fine veins and lines running through it, like Spanish marbles, it is colored on a float, as it is called; that is to say, a large vat of water is sprinkled with the different oil paints required. The effect desired on the stone is thus produced on the surface of the water and is then transferred to the slab by simply immersing the slab and leaving the representation on it. According to the other method the coloring is done by hand, using brushes, sponges, and feathers to smear on the paint. In this process water colors are used. At this stage the slab is baked over night, the temperature of the oven or kiln varying from 175° F. to 225° F. After this first baking it is varnished, and the baking repeated. Next, it is scoured with ground pumice dust, varnished, and baked again. If any gilding is to be done, this is effected after coming out of the kiln for the third time. The next stage consists in rubbing with very fine pumice stone and a felt block, after which it is baked for the last time. Rubbing with rotten stone follows, and the final polish is put on by rubbing with the palm of the hand.

The purposes to which slate are applied are increasing quite rapidly from year to year. For quite a complete list of the uses to which slate is at present put, see the report on Vermont.

New and prospective developments.—Mr. George W. Geiser, of Easton, expected to develop slate property during 1890. Messrs. Jackson Brothers, of Pen Argyl, began operations upon a new slate quarry in the spring of 1890. The Doster Slate Company, of Bethlehem, organized late in 1889, began operations as slate producers in 1890.

Marble.—Marble was quarried in Montgomery county, at quarries near Conshohocken and King of Prussia. The total amount produced was valued at \$41,850. It was used largely for building purposes, chiefly for steps, window sills, exterior trimmings of houses, etc. The waste is used as flux in iron furnaces and also in the manufacture of glass. The quarries have been operated for a number of years.

RHODE ISLAND.

Granite, sandstone, and limestone were produced in Rhode Island in 1889.

Granite.—The value of the granite output was \$931,216. Rhode Island stands first among the granite-producing States in the value of granite devoted to monuments and general cemetery and decorative work. The productive counties are as follows: Washington, \$737,456; Providence, \$184,655, and smaller amounts from Newport and Kent counties. The value of the granite sold as cemetery and monumental stock was \$588,199; for general building purposes \$266,400 worth was used; for street work, including \$45,817 as the value of paving blocks, an amount valued at \$65,817 was used. The remainder was devoted to bridge, dam, and railroad work. The granite quarries and works located at Westerly, Washington county, have long been celebrated for the very fine orna-

mental stock produced. Most elaborately ornamented monuments and statues are turned out in great number. The plants for finishing and polishing are exceedingly well equipped, all the latest improvements in quarry tools being freely used. The stone is particularly well adapted for successful ornamentation and fine finish, and this accounts largely for the prominence of this branch of the granite industry in the State. In fine carving a pneumatic tool, striking exceedingly rapid blows and operated by heavy air pressure is becoming popular among granite-cutters. The rapidity with which fine work can be executed is very much increased by the use of this tool. Its value in connection with granite as well as with ornamental marble has already been satisfactorily demonstrated.

Sandstone.—Sandstone valued at \$21,170 was produced in Providence county. The product was used entirely for building.

Limestone.—Providence county also yielded limestone and lime together valued at \$27,625. Practically the whole amount was used for burning into lime, a very small quantity being used for flux.

SOUTH CAROLINA.

Granite and limestone were produced in this State in 1889.

Granite.—Nine quarries contained in Fairfield and Richland counties produced granite valued at \$47,614. Nearly the entire product came from the first-named county. It was used mainly for street work, the remainder being divided up between building, cemetery, and bridge work.

New and prospective developments.—New granite quarries were opened during 1890 by the following: Mr. A. J. Gilbert, in the neighborhood of Bordeaux, Abbeville county; the Columbia Granite Construction and Manufacturing Company, of Columbia; and Mr. F. Hopperfield, of Yorkville, York county.

Limestone.—Limestone valued at \$14,520 was produced in Abbeville and Spartanburg counties. It was used for bridge work and burning into lime.

Marble.—In 1889 Mr. C. E. Mayhew, of Columbia, discovered a bed of blue marble near Walhalla, Oconee county, and was taking steps to organize a stock company with a capital of \$25,000 with the purpose of developing it.

SOUTH DAKOTA.

The kinds of stone produced in this State are granite, sandstone, and limestone.

Granite.—The granite product in 1889 was valued at \$304,673. The entire amount came from Minnehaha county, in the southeastern part of the State. The product was divided in its application between paving blocks, valued at \$170,695, and building, which consumed the re-

mainder. Much of the stone classified here, for commercial reasons, as granite is really quartzite, a variety of sandstone.

Sandstone.—The production of sandstone in 1889 amounted to \$93,570. It was produced at twelve quarries located in the following counties, the most important of which is the first-named: Fall River, Lawrence, Pennington and Custer. Of the total value, \$81,941 worth was devoted to building purposes and the remainder to abrasive purposes. The above-mentioned counties are all in the southwestern part of the State. The following data were secured by Maj. John R. McGinnis, of the Ordnance Department, Rock Island Arsenal, Illinois. The stone was from Fall River county:

Tests of South Dakota sandstone.

Percentage of water absorbed	8.08
Specific gravity	2.47
Crushing strength, pounds per square inch	3,850

Another specimen gave:

Percentage of water absorbed	7.45
Crushing strength, pounds per square inch	5,200

New and prospective developments.—New sandstone quarries were opened in 1890 by the following companies: The Fall River Stone Company and the Norfolk Stone Company, at Hot Springs; Mr. Henry C. Ashe, of Sturgis county; and Messrs. Scott & Holmes, of Fairburn, in the southern Black Hills region of Custer county.

Limestone.—A very small quantity of limestone was produced in Custer county in the southwestern part of the State in 1889.

T E N N E S S E E .

The stone interests of this State center chiefly in the marble production of Knox, Loudon, and Hawkins counties. In addition to the production of marble, however, comparatively small quantities of limestone and sandstone were also produced during the year 1889.

Sandstone.—A small quantity of sandstone, valued at \$2,722, was produced at four localities, situated in Giles, Marion, Campbell and Maury counties. It was almost entirely used for ordinary building purposes.

Limestone.—Limestone, valued at \$73,028, was produced in 1889 from the following counties: Houston, \$47,950; Davidson, \$9,120, and smaller amounts from Maury, Montgomery, Hickman, Franklin and Marshall counties. Most of the product was used for conversion into lime, the lime produced being valued at \$60,625. The remainder was divided up between the ordinary building, flux, and street work.

Marble.—The total value of the marble output of Tennessee in 1889 was \$419,467. This product came from twenty-two quarries in Knox, Hawkins and Loudon counties. Of the total value, a product valued at \$283,154 was produced in Knox county. The value of that from

Hawkins county was \$103,813. The remainder, \$32,500, came from Loudon county.

The marble-producing region of Tennessee is in the extreme eastern and northeastern parts of the State. Tennessee marble first came into notice about 1863, following immediately upon the close of the war. The first notable use to be made of it was in the United States Capitol building at Washington. Ever since the discovery of the product it has been valued chiefly for purposes of interior decoration and for use in furniture. The product from Hawkins county is the handsomest and brings a much higher price than the product from either Knox or Loudon county. The principal shipping point for the Hawkins county product is Whitesburg. The most important cities in the country for the manufacture of marble into furniture tops are Cincinnati, Ohio, and Baltimore, Maryland. The marble product of Tennessee is so generally well known for its attractive qualities that it is scarcely necessary to enter upon the subject further here. Judging from efforts which were being made to secure further investment of capital and to improve transportation facilities, greater strides will be made in the next few years in the marble regions of Tennessee than have been known heretofore. The consolidation of some six or seven previously independent firms into what is known as the Tennessee Producers' Marble Company will doubtless have the effect of stimulating the industry and preserving a definite grade of prices. The demand for the stone, particularly for interior decoration in dwellings as well as in public buildings, seems to be all that could be desired, and probably the condition of trade would stand a much more active development of the quarries than has heretofore been effected. Improvements in transportation facilities are sadly needed.

New and prospective developments.—The Awalt Marble Company, of Tullahoma, has been organized as a branch of the Tennessee Land and Improvement Company. It expects to commence the development of marble deposits in the vicinity of Tullahoma, Coffee county. Marble similar to Hawkins county marble has been discovered at Fountain City, a suburb of Knoxville, Knox county. It is expected that the Fountain City Land Company, which owns the property, will organize a company to develop the stone. The Athenian Marble Company has been incorporated for the purpose of developing marble quarries near Athens, McMinn county. Marble has been discovered recently in Marion county, a few miles from South Pittsburg. The product has been analyzed, and is pronounced of good quality, susceptible of high finish and of beautiful color.

Slate.—Although as yet no slate has been quarried in Tennessee, it is probable that this State will shortly become productive of this stone. The Tennessee Slate Company has been organized to quarry slate at a point between Chilhowee mountain and McGregor's Knob. The slate is regarded as of fine quality and suitable for roofing, as well as most of the other purposes to which slate is applied.

TEXAS.

Granite, sandstone, and limestone were produced in Texas in 1889. The stone industry of this State dates back for only a few years, no mention whatever being made of the production of stone in Texas in the Tenth Census report.

Granite.—Eight quarries in Burnet, Gillespie and Llano counties, all in the central part of the State, produced granite valued at \$22,550. Almost the entire output was used for ordinary building, a very small quantity being devoted to cemetery purposes. The locality in Burnet county at which the granite for the new capitol was quarried is Marble Falls. The quarrying operations involved in obtaining stone for the capitol were largely conducted with convict labor. The amount of granite at this point is inexhaustible and appears to be of good quality. The presence of an enormous water power is an inducement for more extended quarrying operations than have yet been attempted. The adoption of this stone for the new capitol is the best guaranty of its merit. It shows considerable variety in color, ranging from red or rose color—the stone of which the capitol was constructed—to a light gray, with various intermediate shades. It has shown a resistance to a pressure of 11,891 pounds to the square inch before crushing. At or near Marble Falls marble said to be of fine quality is found in large quantities. It has shown a crushing strength of 14,782 pounds to the square inch, the tests having been made by Col. D. W. Flagler at Rock Island, Illinois. It is said that quarrying operations could be conducted at small cost, as there is but little stripping to be done. One of the largest dams in the world is now in course of construction across the Colorado river just above the city of Austin. The principal stone used in the work is granite from the quarry near Marble Falls. The Houston and Texas railroad has secured control of the Austin and Northwestern railroad, running from Austin to Burnet and Marble Falls, has changed the gauge from narrow to standard, and gives a direct outlet from the quarry to the seaboard and to other railway transportation. This granite is also used to considerable extent for the jetty work at Galveston. Sandstone is also found at the same locality.

Sandstone.—The value of the sandstone produced in 1889 in Texas was \$14,651. It was taken from seven quarries contained in the following counties named in order of relative outputs: Washington, Parker, Grimes, Llano, Brown, Collin and Wise. It was entirely used for building.

Limestone.—Limestone, valued at \$217,835, including the value of lime made from a portion of it, was obtained from eighteen quarries contained in the following counties, named in order of their importance: Travis, \$62,686; Hood, \$50,000; Bell, \$35,698; Grayson, \$23,040; El Paso, \$19,138, and smaller amounts from Washington, Lamar, Fannin, Lampasas, Coryell and Dallas. The product to the value of \$135,901 was used for building. The value of the lime produced was \$6,700. The remainder was used for flux, street, and bridge work.

The following is an analysis of limestone from El Paso county.

Analysis of limestone from El Paso county, Texas.

	Per cent.
Carbonate of calcium.....	97.50
Silica and trace of iron.....	2.50
Total.....	100.00

UTAH.

Sandstone valued at \$48,306, limestone at \$27,568, and granite at \$8,700 were quarried in 1889.

Sandstone.—The sandstone output came from Utah, Summit, Emery, and Box Elder counties, nearly the entire amount coming from the first two named. The entire product was used for building in Salt Lake City, Provo City, and Ogden.

New and prospective developments.—Mr. H. W. Lawrence, of Salt Lake City, opened a sandstone quarry in February, 1891.

Limestone.—Limestone came from Salt Lake and San Pete counties, by far the greater part, however, from Salt Lake county. It was used mainly for burning into lime and for fluxing.

Granite.—A very small quantity of granite was produced in Salt Lake and Weber counties. The amount was small and was used mainly for building, although a little was devoted to cemetery work.

Marble.—The marble interests would apparently well repay more extended investigation than has been thus far devoted to them. There are marble beds south of Nephi which are said to be of good quality, although it has not yet been proved that they are capable of yielding large blocks free from flaws. Another deposit is the property of the Wasatch Marble Company on the divide between the heads of the Big Cottonwood and Snake creeks. The marble here covers many acres and is said to be hundreds of feet in thickness. It is white in color and free from cracks or stains. It is said that blocks could be taken out as large as it would be possible for the heaviest machinery to handle. Efforts are now being made to develop this property.

Slate.—Mr. F. W. C. Hathenbruck, of Provo City, commenced quarrying slate and serpentine during the summer of 1890.

VERMONT.

This State occupies a unique position in the United States in regard to the stone industry. This is due to the fact that it is the great marble-producing State of the Union, producing vastly more than all the rest of the country put together, and, secondly, to the fact that it is only second to Pennsylvania in the production of slate. The kinds of stone produced are granite, sandstone, limestone, marble, and slate.

Granite.—The total value of the granite produced in 1889 in this State was \$581,870. The product came from 53 quarries in the following counties: By far the most important granite-producing county is Washington, the output of which was valued at \$474,341; second is Windham county, with a product valued at \$52,460. The remaining are: Orange, \$24,100; Caledonia, \$18,027; and smaller amounts from Chittenden, Orleans and Windsor counties. The most important developments of the last decade in this State are those which have been made at Barre. At this point there is an enormous supply of granite of the finest quality, such that the product is well adapted, not only to all the ordinary uses to which granite is put, but also for the finest kinds of monumental and decorative work, to which it is quite largely applied. The methods of quarrying are modern. In one of the quarries in this locality the Knox system of blasting is in very successful use. The application of this recent method of blasting granite is quite limited, and is not received with favor by a great many of the large producers of granite in this and other States. The objections to the system as applied to granite are probably, however, due more to the results of single, and in some cases, unsuccessful experiments than to long continued and fair trials of it. The amounts devoted to the various purposes to which granite is applied are: Cemetery and ornamental work, \$412,287; ordinary building, \$45,198; street work, \$48,323; bridge work and miscellaneous uses, \$76,062.

New and prospective developments.—The following firms have opened granite quarries during the year 1890: The Green Mountain Granite Company, at Barre; the Excelsior Granite Company, at Montpelier; Mr. Jacob B. Taylor, at Barre; and the Berlin Granite Company, at West Berlin.

Sandstone.—A very small quantity of sandstone for abrasive purposes was produced in Orleans county.

Limestone.—The total value of limestone and lime produced in 1889 was \$195,066. Of this amount \$168,808 was the value of the lime produced. For building purposes an amount valued at \$5,010 was produced. The remainder was divided up between street and bridge work.

Marble.—As already stated, the marble output of Vermont amounts to more than is produced in all other localities in the United States. The total value of the marble product in 1889 was \$2,169,560. This came from but three counties in the State: Rutland, \$1,844,301; Bennington, \$229,059; Franklin, \$96,200. From this it is evident that the Rutland quarries produce nearly the entire output. The productive counties are all in the western part of the State, and, interrupted only by Chittenden county, extend from the Dorset quarry in the southwestern corner to the Champlain marbles at Swanton in the extreme northern part. The quarries now operated are in or near the towns of Manchester, Dorset, East Dorset, Wallingford, Rutland, West Rutland, Proctor, Pittsford, Brandon, Fair Haven, Middlebury, North

Ferrisburg and Swanton. Abandoned quarries are found all along the railroad from Dorset to Middlebury. The largest operators in the State are to be found at West Rutland and Proctor. At these places quarrying operations are carried on on an enormous scale with the very latest and most improved machinery, and taken all together they are the finest examples of economically quarried property to be found in the world. The abundant water power at Proctor is fully utilized in the operations of the large mills owned by the Vermont Marble Company. Power is transmitted largely through the medium of compressed air.

New and prospective developments.—The Taconic Marble Company was formed for the purpose of developing marble property in Bennington in the summer of 1890. Two quarries are now in working order and a considerable output may be looked for in 1891.

Slate.—The total value of the slate output in 1889 was \$842,013. This product comes entirely from Rutland county. The area in which slate is actually produced at present is confined to a narrow strip in Washington county, New York, and a somewhat wider one lying next to it in Rutland county, Vermont. It extends from Castleton, Vermont, on the north, to Salem, New York, on the south, a distance of 35 or 40 miles, and has a maximum width of 6 miles, but the average is not more than a mile and a half. Scattered over this territory there are about forty-nine quarries in Vermont, and abandoned quarries or those which for one cause or another are at present idle number many more. The first commercial use to be made of the slate of this region was between thirty and forty years ago, when Messrs. Alanson and Ira Allen began on a small scale the manufacture of school slates from the stone obtained at Scotch Hills, 2 miles north of the village of Fair Haven. This quarry is still in operation. The industry has now reached large proportions, the number of quarries keeping pace with the demand for the stone, and this is steadily increasing as new purposes are found for its application. Besides its well-known adaptability for roofing, slate is used locally in a comparatively rough state for sidewalks, curbstones, hitching posts, underpinning, cellar walls, and door steps. As a manufactured article, after going through the mill, it is offered for the following purposes: Billiard-table beds, mantels, fireboards, register frames, radiator tops, steps and risers, platforms, tiles, wainscoting, moldings, thresholds, window sills, lintels, brackets, laundry tubs, washbowl tops, cisterns, sinks, urinals, refrigerators, blackboards, mangers, carriers' slabs, imposing stones, grave boxes, grave covers, headstones, grave markers, vault doors, water tables, belting courses, counter tops, brewers' vats, greenhouse shelves, chimney tops, switch boards, and panels for electric work. In the marbleizing process it is susceptible of considerable ornamentation, which makes it more desirable still for many of the above uses and also extends the list of its uses as follows: Table tops, stand tops, card-receivers, soda-water fountains, checker boards, doorplates, signs, and paper weights.

The slate differs somewhat in its physical properties, such as hardness, homogeneity, and cleavage, but the greatest variation is to be found in its color, no other place in the world showing as many colors in an area of equal size. Most of the commercial names under which the slate is sold are descriptive of the color of each kind and are as follows: Sea green, unfading green, uniform green, bright green, red, bright red, cherry red, purple, purple variegated, variegated and mottled.

The line dividing Vermont and New York also marks the division of two important varieties of slate. The true sea green is found only in the former State, while the red is entirely confined to the latter, some of the quarries producing the respective kinds being, however, but a few hundred yards apart. The sea-green slate is manufactured almost entirely into roofing slates, more than three times as many squares being made from it as from all other varieties combined. It is quarried very extensively in the villages of Pawlet and Poultney. The selling price per square is lower than for any other prominent kind quarried in the region, and the greater output results both from its predominance in the localities mentioned and from the ease with which it is worked, the split being remarkably pronounced. When first quarried its color is a pleasant grayish-green, but after being exposed to the weather it gradually fades and changes in a very unequal manner, certain sheets turning brown, others light gray, while some remain practically unchanged. A roof covered with it presents, after a year or two, a peculiar spotted appearance. It is, however, a good wearing slate and the objection to its color is the principal one against it.

As already stated, no red slate is produced in Vermont, while the red-slate quarries of New York, just across the dividing line, are the only ones in the world producing red slate.

New and prospective developments.—A movement was on foot in the latter part of 1890 to purchase all the sea-green slate quarries in Vermont. The syndicate is said to be backed by English capital and its ultimate object is to obtain control of the entire sea-green slate product of the world.

VIRGINIA.

The stone resources of this State are as yet comparatively undeveloped. The great drawbacks to progress in the stone industry have been lack of capital and facilities for transportation. Production at a not distant day in the future will probably far exceed anything that has yet been accomplished in any one year. The kinds of stone at present actually produced are granite, sandstone, limestone, slate, and marble.

Granite.—In 1889 thirteen quarries, scattered over six different counties, produced granite valued at \$332,548. These counties and the value of stone produced in 1889 are as follows: Chesterfield, \$135,916; Amherst, \$59,125; Henrico, \$55,507; Alexandria, \$40,000;

Campbell, \$27,000, and Dinwiddie, \$15,000. The product was more largely used for building purposes than any other, the amount devoted to this purpose being valued at \$120,467; \$79,925 worth went for street work and the remainder was used chiefly for bridge and railroad work. A number of the quarries in the vicinity of Richmond have been operated successfully for quite a number of years. The plants are comparatively well equipped, and, while operations might be conducted upon a considerably larger scale, they may be said to be prosperous. The stone from most of these quarries is of good quality and is generally well received.

New and prospective developments.—The Rocky Mount Granite Company has recently purchased quarries near Rocky Mount, Franklin county, and apparently their intention is to materially increase operations at these quarries, which have previously been carried on by other parties. The Roanoke Granite Company, of not less than \$35,000 capital, has recently been incorporated for the purpose of developing granite quarries in the State.

Sandstone.—The sandstone output of 1889 came from Campbell and Prince William counties and was valued at \$11,500. It was entirely used for building purposes.

New and prospective developments.—A new sandstone quarry in the vicinity of Manassas, Prince William county, was commenced in 1890.

Limestone.—Eleven quarries in nine counties of the State produced limestone and lime together valued at \$159,023. The productive counties are, in order of importance, Botetourt, \$46,000; Alleghany, \$45,646; Shenandoah, \$27,295, and smaller amounts in Roanoke, Montgomery, Warren, Pulaski, Loudoun and Washington. The larger part of this product comes from quarries in the southwestern part of the State. The value of lime produced was \$83,667. For fluxing, principally in blast furnaces, \$48,146 worth was used. A small quantity was used for street and road purposes.

Slate.—The Virginia slate product comes entirely from Bingham county. The product in 1889 was valued at \$113,079. The product enters the market in competition with that from the important regions of Pennsylvania and Vermont, and is well adapted for roofing and many of the other purposes to which slate is applied. Amherst county will doubtless produce slate before long. The Mount Ayre Slate Company is at present engaged in the development of a slate quarry near Scottsville, Albemarle county.

Marble.—The only marble produced in Virginia in 1889 was taken from a quarry in Mountsville, Loudoun county, by the Virginia Marble Company. Although considerable merchantable stone has been quarried, practically none has been sold, as it has been found impracticable to transport the product by wagons over the roads which connect the quarries with Leesburg, the nearest point on the railroad. There are prospects that a branch road connecting with the Chesapeake and

Ohio railroad may be built to the quarries, but until this is done the product can not be considered as on the market. For the purpose of interior decoration and furniture tops, the stone is undoubtedly very fine.

New and prospective developments.—Experts have examined the marble property in the neighborhood of Staunton. According to indications thus far, it is likely that quarrying operations, will be undertaken. Mr. J. S. Smith has just organized a stock company, with a capital of \$100,000, to develop marble property near Fincastle, Botetourt County, and the preliminary operations of stripping have already begun.

WASHINGTON.

Limestone, sandstone and granite were produced in this State in 1889. The value of the limestone was \$231,287. The bulk of the entire product comes from San Juan county, in the northwestern part of the State. Very small quantities were produced in Kitsap and Douglas counties. Practically nearly the whole product is used for burning into lime, small quantities being devoted to building and blast-furnace flux.

Sandstone.—The sandstone output was valued at \$75,936. It is used entirely for building and comes from the following counties, named in order of their importance: Whatcom, \$42,000; Thurston, \$18,000; and Pierce, \$15,936. According to investigations made by experts sent out by the Cleveland Stone Company, of Cleveland, Ohio, very fine sandstone in inexhaustible quantities has been revealed on the shores of Lake Whatcom.

Granite.—A small quantity of granite—\$10,000 worth—was produced in Stevens county, in the northeastern part of the State. It was entirely used for building purposes. Mr. O. D. Guilfoil has recently opened a quarry of black granite in King county. Small shipments have been made.

WEST VIRGINIA.

Sandstone, valued at \$140,687, and limestone, at \$93,856, were produced in this State in 1889.

Sandstone.—The sandstone comes from the following counties, named in the order of their outputs: Kanawha \$66,000; Wood, \$18,839; Summers, \$18,800; Ohio, \$15,150; and smaller amounts from Marion, Lewis, Preston, Ritchie, Harrison, McDowell and Taylor. Most of the product was used for bridge, dam, and railroad work; \$40,000 worth was used for building, and a smaller amount for street work. A large proportion of it was used in the city of Charleston, situated in Kanawha county.

Limestone.—The limestone comes mainly from Berkeley county, with a production of \$61,000; \$21,411 from Jefferson, and the remainder from Greenbrier. The total value of the product was \$93,856. These counties are in the northeastern and southeastern parts of the State. The great bulk of the stone was used for burning into lime. Smaller amounts

were used for flux, building, and railroad work. There are but eight operative quarries in the State. The value of the lime produced was \$82,471.

There are large quantities of sandstone and limestone in West Virginia which have not yet been at all developed. There seems to be a decided need of increased capital and better railroad facilities. Near Martinsburg, in the northeastern part of the State, are the most important limestone quarries. At this place patent kilns are in use and a good quality of lime is produced. The Alderson brown stone quarries in Summers county yield a valuable stone, which is easily quarried and well adapted to building purposes and also for street work.

WISCONSIN.

Sixty quarries producing limestone and sandstone were operated in 1880. A total output valued at \$227,065 was produced. In 1889, a total of 119 quarries produced granite, sandstone, and limestone, the entire output of stone being valued at \$1,264,016. These comparisons speak for themselves in showing the great strides in the stone industry which have been made in the last decade in this State.

Granite.—The granite production of the State has been entirely confined to the past decade, no mention of granite in this State having been made in the Tenth Census report. The value of the granite in 1889 was \$266,095 and represented the output from eight quarries scattered over Green Lake, Marinette, and Marquette counties. The product was distributed as follows: Green Lake, \$154,645; Marinette, \$79,950, and Marquette, \$31,500. The great bulk of the product was used for street work in the manufacture of paving blocks. The total value of granite devoted to street work is \$223,825. Of this amount \$179,075 was the value of the paving blocks produced; \$40,640 worth was used for building purposes and a comparatively very small amount for cemetery work. The marked advances made in the production of granite are emphatically shown by the statement that this State stands in sixth place among the granite-producing States of the Union in the value of paving blocks produced. Most of the paving blocks came from Green Lake and Marquette counties, for which Milwaukee forms an important place of consumption.

Sandstone.—Thirty-two quarries, scattered over fourteen counties in the State, produced sandstone in 1889. The productive counties, in the order of importance, are as follows: Bayfield, \$69,995; Pierce, \$28,980; Douglas, \$28,096; Ashland, \$28,000; Dunn, \$15,261, and smaller amounts from Sauk, Lafayette, Monroe, Portage, Jackson, Lacro, Trempealeau, Dane and Grant. Bayfield, Douglas and Ashland counties, in the northwestern extremity of the State, produced together \$126,091 worth of stone. The remainder comes from the central, western, and southwestern parts of the State. Nearly the

entire product was used for building purposes, a small amount being devoted to bridge and railroad work.

Limestone.—Seventy-nine quarries produced \$813,963 worth of limestone and lime. The productive counties are as follows: Fond du Lac, \$160,800; Calumet, \$133,842; Milwaukee, \$99,550; Waukesha, \$98,020; Racine, \$57,017; Ozaukee, \$53,640; Dodge, \$35,844; Manitowoc, \$31,370; Winnebago, \$27,120; Brown, \$25,669; Washington, \$25,358; Door, \$20,254, and smaller amounts from Saint Croix, Lacrosse, Sheboygan, Rock, Walworth, Buffalo, Trempealeau, Outagamie, Jefferson, Portage, Dane, Grant, Iowa, Columbia, and Green. The first twelve counties produced \$768,484 worth of the entire output. They are all in the southeastern part of the State, and Milwaukee is the most important outlet. Of the total value of limestone and lime \$514,947 is the value of the lime produced. For building purposes an amount valued at \$232,780 was used. Smaller amounts were devoted to street, bridge, and railroad work; and also for blast-furnace flux. The following analyses have been made:

Analysis of limestone from Calumet county, Wisconsin.

	Per cent.
Calcium carbonate	55.50
Magnesium carbonate.....	38.20
Alumina	2.27
Oxide of iron.....	.67
Silica.....	3.14
Total.....	99.78

Analysis of limestone from Winnebago county, Wisconsin.

[By Dr. John C. Jack.]

	Per cent.
Calcium carbonate	51.97
Magnesium carbonate.....	42.91
Iron.....	.18
Alumina	1.82
Silica.....	3.01
Total.....	99.89

Analysis of limestone from Brillion, Calumet county, Wisconsin.

	Per cent.
Carbonate of calcium.....	55.09
Carbonate of magnesium.....	43.96
Alumina36
Silica.....	.59
Total.....	100.00

This stone is used almost entirely for burning into lime, which appears to be very popular throughout the territory in which it is used.

WYOMING.

Sandstone.—Sandstone to the value of \$16,760 was produced in the following counties, in the order of value: Laramie, Albany, Converse, Carbon and Sweetwater. The product was entirely used for building, and chiefly in Cheyenne.

Limestone.—In Laramie county a trifling amount of limestone was produced.

Marble.—A marble quarry has been discovered in Converse county. No output has yet been secured, but, according to the evidence so far, the stone is of a fair quality and efforts have been made to secure the investment of capital in the deposit, but as yet without success. The locality is seven miles from the nearest railroad.

POTTERY.

Owing to the large number of small potteries where the clay used is found on the spot and not purchased, it has been impracticable to determine the entire amount of clay used in pottery in the United States, except for the larger concerns. For these the statement given below for the years 1887 and 1888 are fairly accurate. But in the census investigation for the calendar year 1889 the scope was extended to all the clay for white ware burned in pottery kilns. The large result is not surprising, especially in view of the relatively low value assigned to the clay from the small potteries where rough stoneware and even unglazed pottery are the chief products. The results for 1890 are not obtained from a census, but from an inquiry as to the general condition of the industry among the large potteries. They are only offered to show this condition.

Amount and value of potters' materials from 1887 to 1890.

	1887.		1888.		1889. ^a		1890. ^a	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
Kaolin or china clay.....	<i>Tons.</i> 22,000	\$231,000	<i>Tons.</i> 18,000	\$189,000	<i>Tons.</i> 294,344	\$635,578	<i>Tons.</i> 350,000	\$756,000
Ball clay.....	6,000	36,000	5,250	31,500				
Fire clay.....	15,000	45,000	13,500	40,500				
Ground flint.....	19,800	168,000	16,250	138,125	11,113	49,137	13,000	57,400
Ground feldspar.....	10,200	112,200	8,700	95,700	6,970	39,370	8,000	45,200

^a In 1889 and 1890 all clays burned in kilns are considered.

The pottery trade in 1888 was depressed compared with 1887, but nevertheless several new enterprises were started. In 1889 and 1890 fully the normal growth was obtained and the improvement in the grade of the product was especially pronounced. Nearly all the large potteries have extended their facilities for products of better designs and decorated in far better manner.

Among the new developments which add to the known stores of good potters' clay which have been mentioned in earlier reports, is the discovery of kaolin in Florida, near Lake Eustis. Dr. Francis Wyatt, of New York, has examined this clay for a company, and already tableware made from it is exhibited at nearby hotels. This is a different deposit from the clay found in the Florida phosphate region, which is more or less mixed with aluminum phosphate, and found as the matrix with boulders of phosphate rock.

There are many new establishments begun in the last two years for working clays or marketing them for sale, especially in the Southern States. Near Chattanooga, Tennessee, five new and rather pretentious potteries have been established. Good white kaolin has also been found near Tullahoma. Other deposits have been found at Piney Flats, near London, near Smithville, and at Cookville, in Tennessee. In Georgia kaolin has lately been found at Atlanta, Buena Vista, Taylor, Augusta, and Milledgeville. Clays are being developed at Blacksburg, Florence, and Graniteville, South Carolina. In Virginia there are new potteries at Strasburg and Broadway, and clay deposits are being developed at Newport News, Murray, Harrisonburg, Staunton, and Williamsburg. In Kentucky pottery clay has been found at Rice's Station, near Red House, and the needed capital for its development has been supplied. In North Carolina two new companies are now established at Sylva. An unusually large bed of kaolin is reported at Kings mountain, and the works at Columbia, Dillsboro, and at Greensboro are to be enlarged. In Texas kaolin has been worked near Austin, and sedimentary clays are common in eastern Texas, particularly near Athens, in Henderson county; near Jefferson, Marion county, and Rusk, Cherokee county. The Geological Survey of Arkansas has called attention to large deposits of kaolin in Pulaski, Saline, Pike and Ouachita counties. One important bed examined in Ouachita county has a thickness of more than 12 feet. This bed outcrops in but few places, but it is probably several miles in length. Prof. Branner, the State geologist, says that the true nature of this material would hardly be suspected from its general appearance or analysis. As it comes from the ground it resembles a sandy clay. With the sand washed out it is found to have about the same composition as the kaolin from Brandywine Summit, Pennsylvania. The *Mining Industry*, of Denver, has called attention to some deposits of fine kaolin near Golden, Colorado. In California a large deposit of kaolin has been found near Grass Valley, and developments have begun on a large deposit near Oro Grande.

Imports and exports.—The following tables show the imports of various clay products and the extent to which this country supplies foreign demands.

Earthenware and china imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Years ending—	Brown earthen and common stone ware.	China and porcelain not decorated.	China and decorated porcelain.	Other earthen, stone, or crockery, glazed, etc.	Total.
June 30, 1867	\$48,618	\$418,493	\$439,824	\$4,280,924	\$5,187,859
1868	47,208	309,960	403,555	3,244,958	4,005,712
1869	34,260	400,894	555,425	3,468,970	4,459,549
1870	47,457	420,442	530,805	3,461,524	4,460,228
1871	96,695	391,374	571,032	3,573,254	4,632,355
1872	127,346	470,749	814,134	3,896,664	5,308,893
1873	115,253	479,617	867,206	4,289,868	5,751,944
1874	70,544	397,730	676,656	3,686,794	4,831,724
1875	68,501	436,883	654,965	3,280,867	4,441,216
1876	36,744	409,539	718,156	2,948,517	4,112,956
1877	30,403	326,956	668,514	2,746,186	3,772,059
1878	18,714	289,133	657,485	3,051,393	3,996,725
1879	19,868	296,591	813,850	2,914,567	4,044,876
1880	31,504	334,371	1,188,847	3,945,666	5,500,388
881	27,586	321,259	1,621,112	4,413,369	6,383,326
1882	36,023	316,811	2,075,708	4,438,237	6,866,779
1883	43,864	368,943	2,587,545	5,685,709	8,686,061
1884	50,172	982,499	2,664,231	666,595	4,363,497
1885	44,701	823,334	2,834,718	963,422	4,666,175
Dec. 31, 1886	37,820	865,446	3,350,145	951,293	5,204,704
1887	43,079	967,694	3,888,509	1,008,369	5,907,642
1888	55,558	1,054,854	4,207,598	886,314	6,204,324
1889	48,824	1,148,026	4,580,321	788,391	6,565,562
1890	56,730	974,627	3,562,851	563,568	5,187,776

Clay imported and entered for consumption in the United States, 1867 to 1883, inclusive.

Fiscal years ending June 30—	Fuller's earth.		Kaolin.		Unwrought pipeclay and fireclay.		Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
1867	<i>Long tons.</i> 280.25	\$3,113	<i>Long tons.</i>	<i>Long tons.</i> 6,383.75	\$72,204	\$75,317
1868	211.00	2,522	8,383.75	66,958	69,480
1869	324.10	3,587	12,963.75	84,645	88,232
1870	239.40	2,619	8,014.15	76,057	78,676
1871	290.20	3,383	10,900.48	103,144	106,527
1872	274.00	3,358	13,081.20	128,130	131,488
1873	251.18	2,978	1,378.30	\$13,091	12,883.82	141,927	157,996
1874	277.20	3,440	89.21	1,378	12,909.14	147,782	152,600
1875	300.06	3,694	130.47	1,977	10,374.65	116,307	121,978
1876	246.73	3,097	142.00	2,152	11,799.12	126,738	131,987
1877	400.00	4,460	204.26	3,009	11,680.14	129,016	136,485
1878	335.07	4,095	3,490.30	38,899	9,406.74	95,877	138,871
1879	361.21	4,269	4,774.60	45,272	8,477.80	87,948	137,489
1880	578.00	6,925	7,823.66	67,740	11,899.80	117,350	192,015
1881	267.55	3,207	6,887.37	66,654	12,444.28	123,545	193,406
1882	908.27	11,444	13,954.85	135,448	12,181.39	119,620	266,512
1883	1,241.27	14,309	12,870.60	115,492	7,841.32	74,673	204,474

Classified imports of clay during the calendar years ending December 31 from 1885 to 1890.

Kinds.	1885.		1886.		1887.	
	Long tons.	Value.	Long tons.	Value.	Long tons.	Value.
China clay or kaolin	10,626	\$83,722	16,590	\$123,093	23,486	\$141,360
All others:						
Unwrought	9,736	76,899	13,740	113,875	17,645	139,405
Wrought	3,554	29,839	1,654	20,730	2,187	22,287
Total	23,916	190,460	31,984	257,698	43,318	303,052

Classified imports of clay during the calendar years, etc.—Continued.

Kinds.	1888.		1889.		1890.	
	Long tons.	Value.	Long tons.	Value.	Long tons.	Value.
China clay or kaolin	18, 150	\$102, 050	19, 843	\$113, 538	29, 923	\$270, 141
All others:						
Unwrought.....	20, 604	152, 694	19, 227	145, 983	21, 049	155, 486
Wrought.....	6, 832	53, 245	8, 142	64, 971	2, 978	29, 143
Total	45, 586	307, 989	47, 222	324, 492	53, 950	454, 770

Value of earthenware and stoneware of domestic manufacture exported from the United States from 1790 to 1890, inclusive.

Years ending—	Value.	Years ending—	Value.	Years ending—	Value.
Sept. 30, 1790.....	\$1, 990	June 30, 1847.....	\$4, 758	June 30, 1870.....	\$42, 120
1791.....	1, 984	1848.....	8, 512	1871.....	37, 383
1826.....	1, 958	1849.....	10, 632	1872.....	48, 941
1827.....	6, 492	1850.....	15, 644	1873.....	53, 909
1828.....	5, 595	1851.....	23, 096	1874.....	59, 494
1829.....	5, 592	1852.....	18, 310	1875.....	92, 253
1830.....	2, 773	1853.....	53, 685	1876.....	73, 846
1831.....	7, 378	1854.....	33, 867	1877.....	87, 355
1832.....	6, 333	1855.....	32, 119	1878.....	98, 035
1833.....	12, 159	1856.....	66, 696	1879.....	80, 898
1834.....	12, 745	1857.....	34, 256	1880.....	106, 724
1835.....	16, 427	1858.....	36, 783	1881.....	123, 177
1836.....	13, 391	1859.....	47, 201	1882.....	180, 773
1837.....	14, 249	1860.....	65, 086	1883.....	227, 547
1838.....	12, 019	1861.....	40, 524	1884.....	236, 247
1839.....	11, 645	1862.....	32, 108	1885.....	135, 385
1840.....	10, 959	1863.....	88, 244	Dec. 31, 1886.....	203, 699
1841.....	6, 737	1864.....	67, 591	1887.....	221, 282
1842.....	7, 618	1865.....	99, 258	1888.....	138, 502
June 30, 1843 (9 mos)	2, 907	1866.....	31, 616	1889.....	189, 133
1844.....	4, 884	1867.....	29, 308	1890.....	157, 321
1845.....	7, 393	1868.....	29, 528		
1846.....	6, 521	1869.....	19, 213		

Fire brick imported for consumption in the United States, 1884 to 1890, inclusive.

Calendar years ending December 31 from 1885 to 1890; previous years end June 30.	Number.
1884.....	1, 524, 000
1885.....	3, 401, 449
1886.....	4, 904, 075
1887.....	5, 836, 300
1888.....	6, 093, 491
1889.....	8, 098, 618
1890.....	6, 206, 856

PRECIOUS STONES.

BY GEORGE F. KUNZ.

During 1890 work was carried on at the tourmaline locality at Mount Mica, Paris, Maine. The work was more or less successful and over \$2,000 worth of fine gems were obtained. For the first time in the history of America, turquoise of fine color, in many respects equal to the Persian, was mined at the Castilian mine between Los Cerrillos and Santa Fé, New Mexico, of which over \$10,000 worth was sold in 1890. These stones are well received by the gem trade, as the Persian mines have proved less and less prolific for many years past. Turquoise has also been discovered in the Burro mountains, Grant county, New Mexico, and Saguache county, Colorado. Of especial interest among newer discoveries was the finding of a few crystals of diamond on Plum Creek, Pierce county, Wisconsin, where they were found in searching for gold under conditions almost identical with the finding of diamonds in North Carolina. The option was obtained on a tract of 4,000 acres on the Missouri River near Helena, Montana, for the purpose of mining sapphires. A preliminary examination made at the sapphire locality in Montana reveals the fact that sapphires exist in large quantities in the gold glacial gravels that lie immediately on the bed rock, a green slate. From present appearances extensive workings will be carried on for these fancy-colored stones, which are not true ruby red nor true sapphire blue. The success of the enterprise depends very much upon how many of these peculiar-colored gems the markets of the world will absorb.

As in former years, large quantities of garnets have been found in the vicinity of Gallup and Fort Wingate, New Mexico, and Fort Defiance, Arizona, whereas the search that is still being carried on at Ison's Mills, Elliott county, Kentucky, with the hope of finding diamonds there, has brought to light the fact that immense quantities of ruby red garnets—pyrope—exist in that vicinity.

With the exception of a single pebble of fire opal described in a former report, no true gem opal had been found in the United States. During 1890, however, near Whelan, southwest of Colfax, Washington, almost on the Idaho and Washington line, a brilliant fire and noble opal has been found filling the cavities of amygdaloidal basaltic rock, the cavities of which vary in size from that of a pea to a large walnut. Some of these opals have sold for almost the price of fine noble opals from Hungary.

Estimated production of precious stones

Species.	1884.			1885.		
	Value of stones found and sold as specimens and curiosities, occasionally polished to beautify or show structure.	Value of stones found and sold to be cut into gems.	Total.	Value of stones found and sold as specimens and curiosities, occasionally polished to beautify or show structure.	Value of stones found and sold to be cut into gems.	Total.
Diamond		\$800	\$800			
Sapphire gems.....	\$250	1,500	1,750		\$500	\$500
Chrysoberyl.....	25		25			
Topaz.....	200	300	500	\$1,000	250	1,250
Beryl.....	300	400	700	250	500	750
Phenacite.....						
Emerald.....				3,000	200	3,200
Hiddenite.....				500	2,000	2,500
Tourmaline.....	1,500	500	2,000	500	100	600
Smoky quartz.....	2,000	10,000	12,000	2,000	5,000	7,000
Quartz.....	10,000	1,500	11,500	10,000	1,500	11,500
Silicified wood.....	10,000	500	10,500	5,000	1,500	6,500
Garnet.....	1,000	3,000	4,000	200	2,500	2,700
Anthracite.....		2,500	2,500		2,500	2,500
Pyrite.....	2,000	1,000	3,000	1,500	500	2,000
Amazonstone.....	2,500	250	2,750	2,500	250	2,750
Catlinite (pipestone).....	10,000		10,000	10,000		10,000
Arrow points.....	1,000		1,000		2,500	2,500
Trilobites.....	500		500		1,000	1,000
Sagenitic rutile.....	500	500	1,000		250	250
Hornblende in quartz.....	500	100	600		300	300
Thomsonite.....	250	500	750	250	500	750
Diopside.....				100		100
Agate.....	4,000	500	4,500	1,000	1,000	2,000
Chlorastrolite.....	500	1,000	1,500			
Turquoise.....	1,500	500	2,000	1,500	2,000	3,500
Moss agate.....	1,000	2,000	3,000	500	2,000	2,500
Amethyst.....	2,000	250	2,250	2,000	100	2,100
Jasper.....	2,000	500	2,500			
Sunstone.....	250	200	450	250	100	350
Fossil coral.....	500	250	750			
Rutile.....				750		750
Total.....	54,275	28,550	82,825	39,300	30,550	69,850
Gold quartz.....	40,000	100,000	140,000	40,000	100,000	140,000

in the United States from 1884 to 1888.

1886.			1887.			1888.		
Value of stones found and sold as specimens and curiosities, occasionally polished to beautify or show structure.	Value of stones found and sold to be cut into gems.	Total.	Value of stones found and sold as specimens and curiosities, occasionally polished to beautify or show structure.	Value of stones found and sold to be cut into gems.	Total.	Value of stones found and sold as specimens and curiosities, occasionally polished to beautify or show structure.	Value of stones found and sold to be cut into gems.	Total.
	\$60	\$60						
\$250	500	750		\$500	\$500		\$500	\$500
1,000		1,000	\$1,500	500	2,000	\$500	100	600
	5,500	5,500	500	3,000	3,500	300	500	800
						650		650
3,000	200	3,200				100		100
3,500	1,000	4,500						
3,500	2,000	5,500	300	200	500			
2,000	5,000	7,000	1,500	3,000	4,500	1,000	3,000	4,000
10,000	1,500	11,500	10,000	1,500	11,500	10,000	1,150	11,150
500	1,000	1,500	35,000	1,000	36,000	1,000	15,000	16,000
1,250	2,000	3,250	2,500	1,000	3,500	2,000	1,500	3,500
	2,500	2,500	2,000		2,000	1,500		1,500
1,500	500	2,000	2,000	500	2,500	2,000	500	2,500
2,000	250	2,250	1,500	200	1,700	1,500	200	1,700
10,000		10,000	5,000		5,000	5,000		5,000
	2,500	2,500		1,500	1,500	1,500		1,500
1,000		1,000	500		500	500		500
1,750		1,750						
200		200		100	100			
100	300	400	250	500	750	300	200	500
			50		50			
1,000	1,000	2,000	3,000	1,000	4,000	3,000	1,000	4,000
500	500	1,000	300	500	800	300	500	800
1,000	2,000	3,000	1,000	1,500	2,500	1,500	1,500	3,000
1,000	1,000	2,000	200	750	950	200	750	950
2,000	100	2,100	2,000	100	2,100	2,200	300	2,500
						100		100
200	100	300	50	100	150			
1,000		1,000	1,500	500	2,000	2,500	500	3,000
750		750						
49,000	29,510	78,510	70,650	17,950	88,600	37,650	27,200	64,850
		40,000			75,000			75,000

Production of precious stones, ornamental minerals, etc., in 1889 and 1890.

Names of gems or precious stones.	1889.			Total value.	Names of gems or precious stones.	1890.			Total value.
	Value of stones before cutting.	Value of stones after cutting into gems for ornamental purposes.	Value of stones sold as specimens and curiosities, occasionally polished to beautify or show the structure.			Value of stones before cutting.	Value of stones after cutting into gems for ornamental purposes.	Value of stones sold as specimens and curiosities, occasionally polished to beautify or show the structure.	
Sapphire.....	\$2,600	\$6,725		\$6,725	Sapphire.....	\$2,600	\$6,725		\$6,725
Emerald.....		300	\$150	450	Emerald.....				
Aquamarine.....	225	597	150	747	Aquamarine.....				
Phenacite.....			200	200	Phenacite.....				
Topaz.....	100	200	200	400	Topaz.....				
Turquoise.....	10,000	23,175	500	23,675	Turquoise.....	10,000	28,175	\$500	28,675
Tourmaline.....	1,030	2,250		2,250	Tourmaline.....	1,030	2,250		2,250
Garnet.....	510	1,633	675	2,308	Garnet.....	510	1,633	675	2,308
Quartz.....	510	2,750	11,250	14,000	Quartz.....	510	2,750	11,250	14,000
Amethyst.....	15	98		98	Amethyst.....				
Rose quartz.....	200	400	200	600	Rose quartz.....			200	200
Smoky quartz.....	700	4,007	225	4,232	Smoky quartz.....	700	2,000	225	2,225
Gold quartz.....	6,000	9,000		9,000	Gold quartz.....	6,000	9,000		9,000
Rutilated quartz.....	2	30		30	Rutilated quartz.....				
Dumortierite in quartz.....			250	250	Dumortierite in quartz.....			250	250
Quartz coated with chalcidony.....	1,000	2,000	2,000	4,000	Quartz coated with chalcidony.....			2,000	2,000
Chrysoprase.....	50	200		200	Chrysoprase.....			200	200
Agatized and jasperized wood.....	42,725	53,000	175	53,175	Agatized and jasperized wood.....	1,000	5,000	1,000	6,000
Banded and moss jasper.....		80	550	630	Banded and moss jasper.....				
Amazon stone.....			500	500	Amazon stone.....			500	500
Pyrite.....	100	500	1,500	2,000	Pyrite.....	100	500	1,500	2,000
Chlorastrolite.....	200	300	200	500	Chlorastrolite.....	100	200	200	400
Thomsonite.....	100	200	200	400	Thomsonite.....	100	200	200	400
Fluorite.....			500	500	Fluorite.....			500	500
Fossil coral.....	100	200	500	700	Fossil coral.....	100	200	500	700
Azurite and malachite.....	1,000		2,037	2,037	Azurite and malachite.....				
Catlinite (pipe-stone).....			5,000	5,000	Catlinite (pipe-stone).....			5,000	5,000
Zircon (a).....			16,000	16,000	Zircon (a).....				
Gadolinite, ferugonite, etc. (a).....			1,500	1,500	Gadolinite, ferugonite, etc. (a).....			15,500	15,500
Monazite (a).....			1,000	1,000	Monazite (a).....				
Spodumene (a).....			200	200	Spodumene (a).....			20,000	20,000
Wooden ornaments decorated with minerals (b).....			15,500	15,500	Wooden ornaments decorated with minerals (b).....				
Miscellaneous minerals (c).....			20,000	20,000	Miscellaneous minerals (c).....				
Total.....		107,645	81,162	188,807	Total.....		58,633	60,200	118,833

a Used to extract the rarer elements for chemical purposes.

b Such as clocks, horseshoes, boxes, etc.

c For cabinets, museums, etc.

FERTILIZERS.

PHOSPHATE ROCK.

In 1889 more phosphate rock was produced in the United States than in any previous year—541,645 long tons in South Carolina, 4,100 long tons in Florida, and 500 tons in North Carolina. It was absorbed by the consumptive demand with no great accumulation of stocks by the producers. A larger amount than usual was exported, owing to low freights and good demand in England. In that country it probably displaced a corresponding amount of Belgian phosphates and reacted also on the lower grades of phosphate rock produced in England. Higher ocean freights and the hope that Florida phosphates would be mined in large quantities and at lower prices depressed the foreign demand for South Carolina river rock in 1890, and the total sales of South Carolina rock were reduced to 463,998 long tons, worth \$2,875,605 in first hands at the place of shipment. In Florida the product in 1890 was 46,501 long tons, worth \$338,190.

The phosphates of North Carolina have received little attention during the last two years, and one of the two establishments was burned out early in 1891. In Alabama the phosphate rock has only been used locally, and this is true also in Virginia, although an effort has been made to separate apatite from a phosphatic iron ore. Attention in the development of new deposits has been limited to Florida.

SOUTH CAROLINA.

As indicated above, the great product of 541,645 long tons, worth \$2,892,276 in 1889 was followed by a decreased product of 463,998 long tons, worth \$2,875,605 in 1890. This was due principally to failure to arrange European contracts. Further, important interests in river mining were concerned in a controversy with the State government in regard to the actual rights of phosphate miners, and this did not aid in keeping up the yield, which, however, was considerably greater than the product of 1888.

The following statement shows the annual product of phosphate rock in South Carolina since it became an industry. The figures for 1886, 1887, 1888, 1889 and 1890 are for calendar years; the previous years are trade years, ending May 31:

Phosphate rock (washed product) mined by the land and river mining companies of South Carolina.

Years ending May 31—	Land companies.	River companies.	Total.
	<i>Long tons.</i>	<i>Long tons.</i>	<i>Long tons.</i>
1867.....	6		6
1868.....	12,262		12,262
1869.....	31,958		31,958
1870.....	63,252	1,989	65,241
1871.....	56,533	17,655	74,188
1872.....	36,258	22,502	58,760
1873.....	33,426	45,777	79,203
1874.....	51,624	57,716	109,340
1875.....	54,821	67,969	122,790
1876.....	50,566	81,912	132,478
1877.....	36,431	126,569	163,000
1878.....	112,622	97,700	210,322
1879.....	100,779	98,586	199,365
1880.....	125,601	65,162	190,763
1881.....	142,193	124,541	266,734
1882.....	191,305	140,772	332,077
1883.....	219,202	159,178	378,380
1884.....	250,297	181,482	431,779
1885.....	225,913	169,490	395,403
1885 (June 1 to December 31).....	149,400	128,389	277,789
1886 (calendar year).....	253,484	177,065	430,549
1887.....	261,658	218,900	480,558
1888.....	290,689	157,878	448,567
1889.....	329,543	212,102	541,645
1890.....	353,757	110,241	463,998

A good demand, particularly from the domestic trade, has kept the price good and the business in a remunerative condition, so that it can not be questioned that if attention had not been diverted to Florida most astonishing products must have come from South Carolina to supply the increased consumption.

A further item influencing the smaller product in 1890 was the increase in imported fertilizers in the previous year. In 1890, however, the imports declined again to the lowest amount and value in many years.

Phosphates imported and entered for consumption in the United States, 1868 to 1890, inclusive.

Calendar years ending December 31 from 1886 to 1890; previous years end June 30.	Guano.		Crude phosphates and other substances used for fertilizing purposes.		Total value.
	Quantity.	Value.	Quantity.	Value.	
	<i>Long tons.</i>		<i>Long tons.</i>		
1868.....	99,668	\$1,336,701		\$88,864	\$1,425,625
1869.....	13,480	217,004		61,529	278,533
1870.....	47,747	1,414,872		90,817	1,505,689
1871.....	94,344	3,313,914		165,703	3,479,617
1872.....	15,279	423,322		83,342	506,664
1873.....	6,755	167,711		218,110	385,821
1874.....	10,767	261,085		243,467	504,552
1875.....	23,925	539,808		242,118	781,926
1876.....	19,384	710,135		164,849	874,984
1877.....	25,580	873,459		195,875	1,069,334
1878.....	23,122	849,607		285,089	1,134,696
1879.....	17,704	634,546		223,283	857,829
1880.....	8,619	168,733		317,068	485,801
1881.....	23,452	390,552		918,835	1,318,387
1882.....	46,699	851,463	133,956	1,437,442	2,291,905
1883.....	25,187	537,080	96,586	798,116	1,335,196
1884.....	28,090	588,033	35,119	406,233	994,266
1885.....	20,934	393,039	40,068	611,284	1,004,323
1886.....	13,520	306,584	82,608	1,179,724	1,486,308
1887.....	10,195	252,265	53,100	644,301	896,566
1888.....	7,381	125,112	36,405	329,013	454,125
1889.....	15,991	313,956	35,661	403,205	717,161
1890.....	4,642	59,580	31,191	252,787	312,367

Guano brought from islands, rocks, and keys, appertaining to the United States, 1869 to 1890, inclusive.

Fiscal years ending June 30—	Quantity.	Value.	Fiscal years ending June 30—	Quantity.	Value.
	<i>Long tons.</i>			<i>Long tons.</i>	
1869.....	15,622	\$253,545	1880.....	12,795	\$147,051
1870.....	14,318	356,830	1881.....	16,883	179,882
1871.....	14,154	340,235	1882.....	15,249	160,016
1872.....	4,209	60,865	1883.....	7,873	92,130
1873.....	11,014	161,690	1884.....	9,333	106,431
1874.....	6,877	100,345	1885.....	12,100	86,166
1875.....	7,269	122,012	1886.....	5,770	38,839
1876.....	14,785	192,972	1887.....	8,226	55,671
1877.....	6,060	79,822	1888.....	5,765	41,226
1878.....	17,930	211,239	1889.....	8,295	64,777
1879.....	8,733	95,137	1890.....	6,853	44,752

FLORIDA.

The report for 1888 announced the discovery of phosphate rock in Florida in large quantity, covering a great area, and rich in phosphoric acid. This rock is markedly different in character, and particularly in amount, from the small deposits which had been known for several years in this State. The discovery is of much more importance than all the other mineral resources of the State, and, indeed, this is certainly regarded as of more importance in the world's supply of fertilizing material than any other known deposit. Since the report in 1888 the deposits have been examined by representatives of practically all the phosphate mining regions of the world with a view to determining the influence of the new discovery upon phosphate mining elsewhere. So much had been written on the subject as to lead to great expectations of a large product immediately, especially as the mining problems are unusually simple. But the railroad facilities require great development in this rather new country, and numberless items necessary in preparing for a large and continuous product are seldom considered, especially by those at a distance. In England the consumers delayed their purchases in 1890 until the last moment in hopes of large Florida shipments and resultant low prices. The shipments which were made did affect the prices, although the quantity was not great. The material was in a condition new to the consumers and offering some new problems in its conversion to superphosphate. This gave the material a lower price than it deserved, and soon called a halt in reckless mining and shipping without profit. The cheap offset to bad mining afforded by a combination is under trial now, but the more intelligent development of the mines and lower costs everywhere is the ultimate solution.

In the report for 1888 a product of 3,000 long tons was noted. In 1889, 8,100 long tons were mined, and of this quantity 4,100 long tons went into use in that year. In 1890 the product developed satisfactorily and was fully in pace with the facilities afforded for getting the rock to the consumers. The sales amounted to 46,501 long tons worth, as shipped, \$338,190—more than the total mineral product of the State in previous years.

The area in which phosphate rock has been found in the State has been increased each time it has been described, and at present it is very uncertain, and this particularly because of variations in quality, as the material shades out into limestone. Thus far the developments have been west of the longitudinal ridge of the State, although some beds of washed pebble rock have been found on the lower St. Johns river.

At the close of 1888 Mr. Albertus Voght, living near Dunnellon, a village on the Withlacoochee river, in Marion county, found fossil teeth in a white subsoil. Some of this white soil was submitted to a chemist for analysis and found to contain a large proportion of calcium phosphate—ordinary phosphate of lime. Active exploration began at once and extended rapidly with the speculative excitement usual to such discoveries. The fact is well established that much of the material is of unusually high grade—the highest in the United States. This developmental or rather speculative work was the main feature of the years 1889 and 1890, with more real development work in the latter.

Florida phosphates may be divided into four classes: (1) hard rock; (2) soft rock; (3) land pebble; and (4) river pebble. Of the hard-rock phosphate there are the following local variations: The massive rock itself; the laminated rock, in which there are narrow layers of phosphate separated by equally narrow interspaces, and the plate phosphate, which is probably derived from the laminated variety and is thus far found in only one or two localities in Florida in the more recent deposits. The hard-rock phosphate is white, creamy, and varies in texture and structure from one of homogeneous appearance to a brecciated variety, and to still others carrying considerable sand and clay. It is sometimes stained in a slight degree with iron, and always contains more or less alumina. The percentage of phosphate of lime contained in this class of phosphate rock is from 80 to 86. The hard-rock phosphate as thus far developed is from a point about south of Tallahassee, following the line of the Gulf at a distance of 20 to 30 miles around to below Dade City in peninsular Florida. Its length is a little less than 200 miles. This deposit is not continuous, but may occur at any point within this length. It also extends into the north of Florida quite to the Georgia line in the vicinity of the Suwannee river. The width of the belt is between 6 and 10 miles. Mining is by open pits, and will be conducted in the future with the most improved plants. The hard-rock phosphate consists of masses of bowlders piled together over large areas; the actual depth of any of these piles has not been determined, the greatest yet reached being about 60 feet from the surface. Hard-rock phosphate bowlders have been derived from rocks of two geological ages—the Eocene, which has the widest areal distribution, and the Miocene, which is found within the comparatively limited area southeast of Tallahassee. Phosphate has also been mined near Boston, Georgia, a station on the line of the Savannah, Florida and Western Railroad. In the vicinity of Dunnellon, where the hard-rock region is

crossed by the Withlacoochee river, the phosphate has been broken down and is now dredged from the bottom of the stream in a form somewhat altered from its original condition, or as pebbles. Vertebrate remains occur in abundance.

The soft-rock phosphate occurs both as a deposit by itself and in the deposits of hard rock, filling the spaces between the bowlders. It may be either clayey or sandy in its nature. It falls considerably below the hard rock in the percentage of phosphate of lime, and naturally shows a higher percentage of alumina and iron.

The land-pebble phosphate is found in a number of localities in peninsular Florida, the center of production at present being in Polk county, within a radius of 18 miles of Bartow. Thus far it has been worked only to the west of the Peace river, within 12 or 15 miles of it, but prospectors have reported its occurrence beneath a large part of the surface between Peace river and the Gulf. It is essentially a mass of white phosphatic pebbles lying in a matrix of phosphatic clay or sand, usually a combination of the two. The matrix is easily disintegrated by water and the pebbles are washed out by appropriate machinery. The pebbles vary in size from grains to one inch in diameter, the average being between one-quarter and one-half an inch. They are hard, and usually pure white or cream colored on fresh fracture. The percentage of phosphate which they contain is about 75 to 80, but the yield of the rock as mined would not reach this standard. The land pebble is found in several parts of Florida, in the vicinity of Bartow, in connection with the plate rock at Anthony and Sparr, 10 miles north of Ocala, and again northeast of Gainesville, occupying an extensive area here. The age of the land-pebble deposits is probably older Pliocene. Land-pebble mining is developing rapidly; the most complete plant is that of the English company, seven miles south of Bartow, where, under favorable conditions existing, enormous basins have been dug, in which dredges of great capacity are floated. The pebble is dredged, washed by machinery adapted to this purpose, dried, and then shipped.

The river pebble is found in bars in the rivers of southern Florida the greatest production at present being from the Peace river, which furnishes nearly the entire product. The other rivers in southern Florida that are known to carry river pebble in quantity are the Alafia, the two Manatees, the Caloosahatchee; in northeast Florida, Black creek, a tributary to the Saint Johns, which enters the latter stream about 20 miles south of Jacksonville, also furnishes a small amount. Pebble phosphates are also found in many other streams entering the Gulf, but thus far not in workable quantities. With the pebbles the remains of vertebrate animals are often found. The river pebble is blue or black, from one inch down in size, usually finer as distance down the stream is gained. It occurs as pebbles, or more rarely as the hardened casts of small mollusks, which show some attrition by water. In the Caloosahatchee river the pebble is mixed with ordinary

shells of carbonate of lime washed out from the Pliocene and Post-Pliocene beds bordering the river above. The derivation of the river pebble is probably very largely from the land pebble deposits, the streams in which they occur draining the country occupied by these deposits. Some of them may also have been derived from the hard rock phosphate. The percentage of phosphate of lime in the river pebbles is between 58 and 68, the average of the cargoes running between 60 and 65 per cent. The river pebble is dredged, washed, and floated on the river to the works, where it is dried, cleaned, and made ready for shipment. The phosphate drying works are very extensive.

The distribution of the phosphate deposits in Florida as they were known in 1889 and 1890 is well given in the volume, *Mineral Industries in the United States*, of the final reports of the Eleventh Census, which also shows quantitatively the number of enterprises engaged in developing the rock and their importance. In 1891, 215 companies had been formed for work in this field, and the number is constantly increasing.

Marl.—The production of marl in the United States during 1889, as determined by the Eleventh Census, was 139,522 tons, valued at \$63,956. In 1890 there was a slight increase in the production, which is estimated at 153,620 tons, valued at \$69,880. As heretofore, New Jersey produced nearly the entire amount, North Carolina and Arkansas contributing only about 1,500 tons. The producers of this substance in New Jersey are so numerous that exact statistics of production and value are almost impossible to obtain—certainly impossible with the means at command—as a large percentage of the farms in the marl belt, which extends from Raritan bay to near the mouth of the Delaware river, with an average width of about 15 miles, is underlaid with workable deposits of marl. The open winters of the past few years have tended to materially decrease the production of marl, owing to the difficulty of hauling during such seasons. By far the larger portion of marl is produced by farmers and sold to their neighbors or used on their own farms, which accounts for the difficulty of obtaining exact statistics on this subject, the producers very rarely keeping accurate accounts of the amount of marl used or sold.

Canadian apatite.—The product of apatite in Quebec and Ontario in the last few years has been determined by Mr. E. D. Ingall, of the Canadian Geological Survey, and is given below, together with the product since 1878. The greater part of the product came from Ottawa county, Quebec; here the producing mines are the North Star, of the Dominion Phosphate Company; the High Rock, owned by the Phosphate of Lime Company; the Star Hill and Crown Hill, of the Canadian Phosphate Company; the Emerald mine, of the Ottawa Company, and the Blackburn mine, in Templeton Township. In Ontario the output is largely the intermittent work of farmers, but there are regular plants at the Toxton, Ottly Lake, and Bob's Lake mines, and at those in North Burgess.

Although the higher grades of Canadian rock finds a very ready market in England, and receive 1 to 3 cents more per unit of phosphate than most other sorts, the trade was considerably disturbed by the Florida developments. This affected the price rather than the shipments.

Product of Canadian apatite from 1878 to 1890.

Years.	Quantity.	Years.	Quantity.
	<i>Long tons.</i>		<i>Long tons.</i>
1878	3,701	1885	24,290
1879	11,927	1886	20,495
1880	7,974	1887	23,690
1881	15,601	1888	22,485
1882	17,181	1889	30,988
1883	17,840	1890	31,753
1884	22,143		

BUHRSTONES.

Value of buhrstones produced in 1889, \$35,155; value of buhrstones produced in 1890, \$23,720. The domestic production of flint and quartz grit for the manufacture of buhrstones and millstones has shown a steady decrease since 1886. Grinders of paint, gypsum, and cement rock continue to use the domestic millstone to some extent, but its use in grinding cereals has been almost entirely abandoned for the more modern roller process. French buhr is still used in some flouring mills which have not adopted the roller process. The decreasing tendency of the industry may be seen from the following table, showing the annual production since 1883. The producing States in 1889 and 1890 were New York, Pennsylvania, and Virginia:

Value of buhrstones produced in the United States since 1883.

Years.	Value.	Years.	Value.
1883	\$150,000	1887	\$100,000
1884	150,000	1888	81,000
1885	100,000	1889	35,155
1886	140,000	1890	23,720

Value of buhrstones and millstones imported into the United States from 1868 to 1890.

Years ended—	Rough.	Made into millstones.	Total.	Years ended—	Rough.	Made into millstones.	Total.
June 30, 1868..	\$74,224	\$74,224	June 30, 1880..	\$120,441	\$4,631	\$125,072
1869..	57,942	\$2,419	60,361	1881..	100,417	3,495	103,912
1870..	58,601	2,297	60,898	1882..	103,287	747	104,034
1871..	35,406	3,698	39,104	1883..	73,413	272	73,685
1872..	69,062	5,967	75,029	1884..	45,837	263	46,100
1873..	60,463	8,115	68,578	1885..	35,022	455	35,477
1874..	36,540	43,170	79,710	Dec. 31, 1886..	29,273	662	29,935
1875..	48,068	66,991	115,059	1887..	23,816	191	24,007
1876..	37,759	46,328	84,087	1888..	36,523	705	37,228
1877..	60,857	23,068	83,925	1889..	40,432	452	40,884
1878..	87,679	1,928	89,607	1890..	32,892	1,103	33,995
1879..	101,484	5,088	106,572				

CORUNDUM AND EMERY.

The total product of corundum and emery in 1889 was 2,245 short tons, valued at \$105,565. In 1890 the product decreased somewhat, being 1,970 tons, worth at the mines \$89,395. The States of Massachusetts, New York, North Carolina, and Georgia furnish the supply. A small quantity, about 5 tons, came from South Carolina. The value of corundum at the mines varies from \$20 to \$100 per ton, the best coming from the Georgia and North Carolina mines.

Production of corundum and emery for the years 1881 to 1890.

Years.	Quantity.	Value.	Years.	Quantity.	Value.
	<i>Short tons.</i>			<i>Short tons.</i>	
1881.....	500	\$80,000	1886.....	645	116,190
1882.....	500	80,000	1887.....	600	108,000
1883.....	550	100,000	1888.....	589	91,020
1884.....	600	108,000	1889.....	2,245	105,567
1885.....	600	108,000	1890.....	1,970	89,395

Emery imported into the United States from 1867 to 1890, inclusive.

Years ended—	Grains.		Ore or rock.		Pulverized or ground.		Other manufac- tures.	Total.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.		
	<i>Pounds.</i>		<i>Tons.</i>		<i>Pounds.</i>			
June 30, 1867.....			428	\$14,373	924,431	\$38,131		\$52,504
1868.....			85	4,531	834,286	33,549		38,080
1869.....			964	35,205	924,161	42,711		77,916
1870.....			742	25,335	644,080	29,531		54,866
1871.....			615	15,870	613,624	28,941		44,811
1872.....			1,641	41,321	804,977	36,103		77,424
1873.....	610,117	\$29,706	755	26,065	343,828	15,041	\$107	70,919
1874.....	331,580	16,216	1,281	43,886	69,890	2,167		62,366
1875.....	487,725	23,345	961	31,972	85,853	2,990		20
1876.....	385,246	18,999	1,395	40,027	77,382	2,533		94
1877.....	343,697	16,615	852	21,964	96,351	3,603		42,182
1878.....	334,291	16,359	1,475	38,454	65,068	1,754	34	56,601
1879.....	496,633	24,456	2,478	58,065	133,556	4,985		87,506
1880.....	411,340	20,066	3,400	76,481	223,855	9,202	145	105,894
1881.....	454,790	22,101	2,884	67,781	177,174	7,497	53	97,432
1882.....	520,214	25,314	2,765	69,432	117,008	3,708	241	98,695
1883.....	474,105	22,767	2,447	59,282	93,010	3,172	269	85,490
1884.....	143,267	5,802	4,145	121,719	513,161	21,181	188	148,890
1885.....	228,329	9,886	2,445	55,368	194,314	8,789	757	74,800
Dec. 31, 1886.....	161,297	6,910	3,782	88,925	365,947	24,952	851	121,638
1887.....	367,239	14,290	2,078	45,033	a144,380	6,796	2,090	68,209
1888.....	430,397	16,216	5,175	93,287			8,743	118,246
1889.....	503,347	18,937	5,234	88,727			111,302	218,966
1890.....	534,968	20,382	3,867	97,939			5,046	123,267

a To June 30 only ; since classed with grains.

GRINDSTONES.

The value of grindstones produced in the United States in 1889 was \$439,587. In 1890 the value of the product increased to \$450,000. To this production four States contributed, Ohio, Michigan, South Dakota and California, named in the order of importance. It is difficult, if not practically impossible, to separate the product of Ohio and Michigan, as many producers operate in both States and the manufacture of the finished stones is carried on principally at Cleveland, Ohio. These two States contribute about 98 per cent. of the entire product.

The following tables show the value of the grindstones produced in the United States since 1880 and the imports from 1868 to 1890.

Value of grindstones produced in the United States, 1880 to 1890, inclusive.

Years.	Value.	Years.	Value.
1880	\$500,000	1886	\$250,000
1881	500,000	1887	224,400
1882	700,000	1888	281,800
1883	600,000	1889	439,587
1884	570,000	1890	450,000
1885	500,000		

Grindstones imported and entered for consumption in the United States, 1868 to 1890, inclusive.

Years ended—	Finished.		Unfinished or rough.		Total value.
	Quantity.	Value.	Quantity.	Value.	
	<i>Long tons.</i>		<i>Long tons.</i>		
June 30, 1868		\$25,640		\$35,215	\$60,855
1869		15,878		99,715	115,593
1870		29,161		96,444	125,605
1871	385	43,781	3,957.15	60,935	104,716
1872	1,202	13,453	10,774.80	100,494	113,947
1873	1,437	17,033	8,376.84	94,900	111,933
1874	1,443	18,485	7,721.44	87,525	106,010
1875	1,373	17,642	7,656.17	90,172	107,814
1876	1,681	20,262	6,079.34	69,927	90,189
1877	1,245	18,546	4,979.75	58,575	77,121
1878	1,463	21,688	3,669.41	46,441	68,129
1879	1,603	24,904	4,584.16	52,343	77,247
1880	1,573	24,375	4,578.59	51,899	76,274
1881	2,064	30,288	5,044.71	56,840	87,128
1882	1,705	30,286	5,945.61	66,939	97,225
1883	1,755	28,055	6,945.63	77,797	105,852
1884					86,286
1885					50,579
Dec. 31, 1886					(a)39,149
1887					(a)50,312
1888					(a)51,755
1889					(a)57,720
1890					(a)45,115

a Classed as finished or unfinished.

INFUSORIAL EARTH.

The product in 1889 amounted to 3,466 short tons, valued at \$23,372. In 1890 the product was 2,537 tons. Of this amount 2,532 tons were marketed, realizing \$50,240. The difference in value as appearing between the products of 1889 and 1890 is not due to any notable rise in the price, but simply to the value being estimated at different stages of preparation. In California, for instance, the amount of crude earth produced was 39 tons, but this was sold only in the form of "Callustro" preparations, valued at \$10,335. The mines at Dunkirk, Maryland, produced 1,500 tons and those of Pope's Creek 560 tons, with an aggregate value of \$29,000. The remainder of the product was from Connecticut, Nevada, and New Hampshire. Thirty-five tons of earth carried over from production in previous years were marketed from New Jersey, but none was mined in that State during the year.

The production of infusorial earth in 1880, according to the Tenth Census, was 1,833 short tons, valued at \$45,660, or about \$25 per ton. The product for the subsequent years is shown in the following table. The figures for 1889 are from the Eleventh Census.

Production of infusorial earth from 1880 to 1890.

Years.	Short tons.	Value.	Years.	Short tons.	Value.
1880.....	1,833	\$45,660	1886.....	1,200	\$6,000
1881.....	1,000	10,000	1887.....	3,000	15,000
1882.....	1,000	8,000	1888.....	1,500	7,500
1883.....	1,000	5,000	1889.....	3,466	23,372
1884.....	1,000	5,000	1890.....	2,532	50,240
1885.....	1,000	5,000			

OILSTONES, WHETSTONES, ETC.

Total product in 1889, 2,991 short tons, valued at the quarries at \$32,980.

The product in 1890 consisted of 761,348 pounds of Washita and Arkansas oilstone, valued at the quarries at \$12,384; 15,000 gross of scythestones, valued at \$46,000; 500,000 pounds of Hindostan and Orange stone, valued at \$10,275; 2,000 pounds of Labrador oilstone, valued at \$250, and 8,000 pounds of chocolate whetstones, valued at \$1,000. The total value of the 1890 product, as above, was \$69,909. In this the value is taken for the manufactured product, with the exception of the Arkansas and Washita oilstone. This is quarried in Arkansas, shipped in its rough state to New Hampshire, and there made into the oilstones of commerce. The difference in the value of the product in 1889 and 1890 is due to the fact that the value of the entire product of the former year was taken in the rough state. The producing States remain as heretofore noted, Arkansas, Indiana, New Hampshire, and Vermont.

Imports of whetstones and razor hones for the years 1880 to 1890.

Years ended—	Value.	Years ended—	Value.
June 30, 1880	\$14, 185	Dec. 31, 1886	\$21, 141
1881	16, 631	1887	24, 093
1882	27, 882	1888	30, 676
1883	30, 178	1889	27, 400
1884	26, 513	1890	37, 454
1885	21, 434		

CEMENT.

Production.—The following table shows the product of the natural rock cements in the leading districts during the years named:

Product of natural cement in 1889, 1890, and 1891.

Localities.	1889.	1890.	1891.
	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>
Rosendale, New York	2,547,225	2,683,579	2,815,010
Louisville, Kentucky	1,338,464	1,533,579	1,501,200
Buffalo and Akron, New York	682,275	698,396	745,450
Lehigh Valley, Pennsylvania	350,000	450,000	520,000
Milwaukee, Wisconsin	350,000	400,000	425,000
Utica and La Salle, Illinois	350,000	400,000	450,000
Potomac River	200,000	200,000	250,000
Fort Scott, Kansas	150,000	150,000	140,000
Mankato, Minnesota	78,912	87,650	101,875
Onondaga and Schoharie counties, New York	225,000	202,000	215,000
Virginia, Georgia, Texas, Ohio, Missouri, and New Mexico	270,000	277,000	288,000
Totals	6,531,876	7,082,204	7,451,535

The above statement was compiled at the close of the year 1891 by Mr. U. Cummings, who has collected statistics of this character for many years. In preparing a statement of the technical features involved in cement manufacture for the report to follow the present volume, Prof. Spencer B. Newbury has made an independent canvass of the entire country and the following table shows the results of this work. The wonderfully close agreement of the two statements is especially gratifying from the difficulty of securing returns with such remarkable promptness from scattered producers who are also engaged in very active competition. The agreement would be even more striking if the grouping of districts had been identical.

Product of hydraulic cement in the United States.

BY SPENCER B. NEWBURY.

	Works.	1890.		1891.	
		Barrels.	Value.	Barrels.	Value.
Georgia	1	40,000	\$40,000	40,000	\$40,000
Illinois, Utica and La Salle	2	363,117	292,784	409,877	276,931
Indiana and Kentucky (Louisville region)	11	1,533,579	1,150,184	1,513,009	983,456
Kansas and Missouri (Kansas City and Fort Scott)	2	175,000	122,500	135,000	94,000
Maryland, Hagerstown, Cumberland, and Hancock	3	223,209	203,785	204,900	187,855
Minnesota, Mankato	1	87,650	65,737	101,875	76,406
New York, Onondaga county	8	281,086	183,268	288,941	188,944
New York, Ulster county	17	2,683,579	2,213,982	2,815,010	2,252,008
New York, Schoharie county	1	25,357	20,286	27,055	21,644
New York, Buffalo and Akron	4	765,734	560,277	788,300	575,283
Ohio, Bellaire and New Lisbon	2	57,000	56,000	70,000	68,000
Pennsylvania (Lehigh Valley)	6	555,000	434,900	695,000	536,600
Tennessee, Chattanooga	1	48,423	43,540	33,100	36,026
Utah, Salt Lake City	1	—	—	5,000	10,000
Virginia and West Virginia	2	20,000	15,000	20,000	15,000
Wisconsin, Milwaukee	1	450,000	180,000	460,000	150,000
Total	63	7,308,734	5,582,243	7,607,067	5,512,153

Product of Portland cement in the United States in 1890 and 1891.

BY SPENCER B. NEWBURY.

	Works.	1890.		1891.	
		Barrels.	Value.	Barrels.	Value.
California, San Diego.....	1			5,000	\$15,000
Colorado, Denver.....	1	12,500	\$40,000	12,500	40,000
Dakota, Yankton.....	1			31,813	71,579
Indiana, South Bend.....	1	15,000	36,000	15,000	36,000
New York, Onondaga county, Buffalo, etc.....	5	65,000	140,000	87,000	290,000
Ohio, Bellefontaine and Columbus.....	2	22,000	49,000	35,000	82,000
Pennsylvania, Lehigh and Lawrence counties	7	221,000	439,050	268,500	532,850
Total.....	18	335,500	704,050	454,813	1,067,429

Price.—The average price, considering all grades of natural rock cement, was 72 cents per barrel in 1889, 70 cents per barrel in 1890, and 68 cents per barrel in 1891. This is for cement in wood. The lower prices are due, to a considerable extent, to fierce competition in the West. Fully one-half of the cement sold at Buffalo, New York, and all points west of that, is in sacks. All cement sold in Buffalo and west of it is rated at 265 pounds to the barrel, all sold east of Buffalo contains 300 pounds to the barrel, and Portland cement is 380, so that there are three different weights for a barrel of cement in this country. The fact that Portland cement is frequently said to do better than the natural cement may be in many cases due to the fact that one-third more cement is given to the barrel.

Cement imported and entered for consumption in the United States, 1868 to 1890.

Years. (a)	Quantity.	Value.	Years. (a)	Quantity.	Value.
	<i>Barrels.</i>			<i>Barrels.</i>	
1868.....		\$10,168	1880.....		\$373,264
1869.....		9,855	1881.....		441,512
1870.....		18,057	1882.....	370,408	683,684
1871.....		52,103	1883.....	456,418	802,294
1872.....		172,839	1884.....	(b) 585,768	825,095
1873.....		209,097	1885.....	534,396	874,070
1874.....		286,420	1886.....	915,255	962,689
1875.....		261,741	1887.....	1,514,095	1,470,846
1876.....		247,200	1888.....	1,835,504	1,731,456
1877.....		201,074	1889.....	1,740,356	1,704,253
1878.....		184,086	1890.....	1,940,186	2,249,741
1879.....		212,719			

a Calendar years ending December 31 from 1886; previous years end June 30.

b Classed simply as cement; kind not specified since 1883. It is probable, however, that about 95 per cent of the total imports is Portland cement.

Lime and cement of domestic production exported from the United States, 1864 to 1890.

Years. (a)	Quantity.	Value.	Years. (a)	Quantity.	Value.
	<i>Barrels.</i>			<i>Barrels.</i>	
1864.....		\$86,386	1879.....	60,657	\$74,097
1865.....		94,606	1880.....	41,989	52,584
1870.....	31,175	61,490	1881.....	57,555	83,598
1871.....	27,575	51,585	1882.....	67,030	100,169
1872.....	39,686	69,218	1883.....	74,687	120,156
1873.....	27,873	52,848	1884.....	65,768	108,437
1874.....	41,349	69,080	1885.....	79,627	127,523
1875.....	64,087	98,630	1886.....	83,247	123,687
1876.....	53,827	77,568	1887.....	63,520	97,771
1877.....	78,341	97,923	1888.....	100,070	147,309
1878.....	82,507	98,334	1889.....	89,995	142,298
			1890.....	86,963	152,295

a Calendar years ending December 31 from 1886 to 1890; previous years end June 30.

New developments.—A new and important discovery of cement rock was made during 1890 in the coast range of mountains near Sierra Peak, about $3\frac{1}{2}$ miles southwest of South Riverside, in southern California. It is owned and controlled by Messrs. Fraser Brothers of South Riverside, California.

It comprises about 330 acres in extent, and is fully 90 feet in thickness.

It lies in horizontal strata, the edges being exposed in a cañon passing through it. It is capped in most places by 3 to 5 feet of limestone. The deposit lies partly in Orange and partly in San Bernardino counties, the county line running north and south through its eastern portion.

A thorough examination of this deposit was made during the spring and summer of 1891 by a competent authority on cements, and it developed qualities as good as any known cement deposit; only trifling variation exists in the proportion of ingredients between the upper and lower layers, and a thorough admixture of the different layers, calcined and ground together, resulted in a cement showing the following analysis :

Composition of cement from South Riverside, California.

	Per cent.
Silica.....	24.34
Alumina.....	8.56
Lime.....	63.62
Magnesia.....	0.40
Oxide of iron.....	2.08
Alkalies.....	1.00
Total.....	100.00

The rock is blue-black in color, and is extremely fine grained, hard and compact, the fracture conchoidal.

A series of tests of the cement extending over a period of eight months exhibit no signs of shrinking, swelling, checking, or disintegration. It bears submersion immediately after being made up into balls, patties, or briquettes, and it neither heats nor falls down, and its induration is in perfect keeping with the laws governing the action of first quality hydraulic cements. Several experiments were made as to its Portland-making qualities, and it was found that a first quality of Portland cement can be produced without the admixture of any extraneous material whatever, as shown by the analysis.

The Portland experiments were made by grinding the various layers together in the raw state, then moistening sufficiently to press into balls or cakes, and exposing to a white heat until the point of incipient vitrification was reached, the clinker, after a gradual cooling, was reduced to powder and spread out in a thin layer for a week, and then made into briquettes and tested in the usual way—by tensile strain per square inch.

The following table is the average result of many tests:

Tests of South Riverside Portland cement.

Hours in air.	Days in water.	Breaking strength per square inch.
		<i>Pounds.</i>
1	1	135
1	7	280
1	30	475

The table following is the result of several hundred tests of the cement made after the manner of natural cements, by first calcining the rock, then reducing it to powder. All stages of calcination was resorted to from an under-burn up to the melting point, with a view to the development of imperfections, if any existed:

Tests of natural cement from South Riverside, California.

Hours in air.	Days in water.	Average breaking strength per square inch.	Hours in air.	Days in water.	Average breaking strength per square inch.
		<i>Pounds.</i>			<i>Pounds.</i>
1	1	115	1	28	291
1	7	178	1	90	354
1	14	223	1	210	485
1	21	256			

A bed of good bituminous coal about 7 feet thick probably underlies the entire cement rock deposits, as it is mined on both sides of the mountain range adjacent to the cement deposits, and it is probable that the coal can be reached at a reasonable depth by sinking a shaft in the cañon mentioned, and the shaft would undoubtedly pass through a bed of snowy gypsum of at least 40 feet in thickness, judging from the exposures on both sides of the narrow mountain.

No cement is produced in California, the entire supply coming from Europe, amounting in the aggregate to upwards of a million barrels during the year 1891.

Two or three attempts have been made to produce artificial Portland cement in that State, but the excessive cost has tended to a discontinuance of that industry. Therefore the discovery of this vast body of cement rock, containing upwards of 300,000,000 barrels of the raw material, from which a cement of most excellent quality can be produced at a very low cost, must prove of incalculable value to the people of that State, as it is located in the very heart of the famous orange belt, where the demand for cement for the construction of irrigation dams, canals, and pipe lines is already immense, yet increasing, and must continue to increase for many years to come.

A first-class cement plant capable of producing 1,200 barrels per day is projected and will probably be put in operation during the season of 1892 on the line of the Sante Fé railroad system at South Riverside, California, the rock to be brought down to the plant by a narrow-gauge system.

G Y P S U M .

Total product in 1889, 267,769 short tons; value as first sold, \$764,118. Total product in 1890, 182,995 short tons; value as first sold, \$574,523.

The total amount of gypsum produced in the United States in 1890 was 84,774 short tons less than during 1889. The decrease in value was \$189,595. Ninety per cent. of this loss will be covered by the decrease in Michigan and New York, the aggregate output in these two States alone being 76,595 tons less in 1890 than in 1889, and showing a total decrease in value of \$188,024. The falling off in New York was due to the exceptionally wet weather which prevailed during the year. The entire product of the State is used as land plaster, which is most useful during a dry season. This assistance not being needed when plenty of rain has fallen, the production of gypsum decreases accordingly. The production in Michigan in 1889 was unusually large. One concern reporting a large output in that year produced no gypsum in 1890. The mill of Mr. Lorin Day, at Grandville, was burned May 19, 1890. The mill was rebuilt, but produced nothing more during the year (a).

An interesting feature of the gypsum-producing industry is the observation of the conditions in which it is marketed in the different producing localities. A limited amount is sold in the condition as mined. The sales in this particular in 1890 were limited to New York, Ohio, and Virginia. This portion of the product, though originally sold crude, is used as a fertilizer.

The distribution of the total product may be seen from a study of the following tables, showing the production in 1889 and 1890, by States:

Production of gypsum in 1889, by States.

States.	Amount produced.	Amount sold crude.	Value.	Amount sold as land plaster.	Value.	Amount of gypsum calcined into plaster of Paris or stucco.	Amount of plaster of Paris or stucco after calcining.	Value.	Total value.
	<i>Short tons.</i>	<i>Short tons.</i>		<i>Short tons.</i>		<i>Short tons.</i>	<i>Short tons.</i>		
California	3,000					3,000	2,250	\$30,000	\$30,000
Colorado	7,700			100	\$140	7,600	4,325	28,800	28,940
Iowa	21,784			14,434	23,000	7,350	5,507	32,250	55,250
Kansas	17,332					17,332	613,896	94,235	94,235
Michigan	131,767	35,100	\$35,100	54,084	123,143	42,583	32,434	215,497	373,740
New York	52,608	21,537	21,537	31,071	57,834				79,476
Ohio	9,920	106	212	2,744	9,604	7,070	5,656	41,675	51,491
South Dakota	320					320	253	2,650	2,650
Utah	16,000	16,000	25,000						25,000
Virginia	6,838	500	750	6,338	19,586				20,336
Wyoming	4500					500	390	3,000	3,000
Total	267,769	73,243	82,704	108,771	233,307	85,755	64,711	448,107	764,118

a Mr. Lorin Day's new mill was burned May 13, 1891.

b Of the Kansas product 600 tons were made into fireproof cement, producing 400 tons of cement, valued at \$6,000.

c Estimated, and value given for crude material.

d Began operations November 1, 1889.

Production of gypsum in 1890, by States.

States.	Total amount produced.	Amount sold, crude.	Value.	Amount ground into land plaster.	Value.	Amount calcined (weight before calcining).	Value (after calcining).	Stocks Jan. 1, 1891.	Total value.
	<i>Short tons.</i>	<i>Short tons.</i>		<i>Short tons.</i>		<i>Short tons.</i>		<i>Short tons.</i>	
Colorado	4,580			50	\$125	4,530	\$21,925		\$22,050
Iowa	20,900			2,900	2,350	18,000	45,000		47,350
Kansas	20,250			80	215	19,420	72,242	750	72,457
Michigan	74,877	15,000	\$15,000	12,714	28,980	47,163	148,119		192,099
New York	32,903	3,072	2,858	29,831	70,235				73,093
South Dakota	2,900			2,900	7,750				7,750
Virginia	6,350	100	150	4,948	29,632			1,302	20,782
Other States <i>a</i>	20,235	570	1,140	3,102	12,727	16,563	125,075		138,942
Total	182,995	18,742	19,148	56,525	143,014	105,676	412,361	2,052	574,523

a Ohio, California, and Wyoming.

In addition to the two States named, in which the product for 1890 was much less than in 1889, there was a decreased output in Colorado, Iowa, Utah and Virginia (*a*). The States showing increased production were California, Kansas (*a*), South Dakota and Wyoming. The following table is arranged to show the total amount and value of gypsum produced in each State for both years, with increases and decreases in 1890:

Comparative statistics of gypsum production for two years.

States.	Total product.		Increase.	Decrease.	Total value.		Increase.	Decrease.
	1889.	1890.			1889.	1890.		
	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>	<i>Short tons.</i>				
Colorado	7,700	4,580		3,120	\$28,940	\$22,050		\$6,890
Iowa	21,789	20,900		884	55,250	47,350		7,900
Kansas	17,332	20,250	2,918		94,235	72,457		21,778
Michigan	131,767	74,877		56,890	373,740	192,099		181,641
New York	52,608	32,903		19,705	79,476	73,093		6,383
South Dakota	320	2,900	2,580		2,650	7,750	\$5,100	
Virginia	6,838	6,350		488	20,336	20,782	446	
Other States (<i>b</i>)	29,420	20,235		9,185	109,491	138,942	29,451	
Total	267,769	182,995		c84,774	764,118	574,523		c189,595

a Kansas has an increased product and decreased value. Virginia decreased product and increased value.

b Includes California, Ohio, Utah, and Wyoming.

c Net decreases.

The following table, showing the annual product of land plaster and stucco in Michigan, is taken from the annual report of Mr. Charles D. Lawton, commissioner of mineral statistics:

Amount of land plaster and stucco produced in Michigan.

Years.	Land plaster. (Short tons.)	Stucco. ^a (Barrels of 300 pounds.)	Years.	Land plaster. (Short tons.)	Stucco. (Barrels of 300 pounds.)
Previous to 1866	100,000	-----	1878.	40,000	48,346
1866.	14,604	-----	1879.	43,658	50,800
1867.	17,439	-----	1880.	49,570	106,004
Previous to 1868	-----	a80,000	1881.	33,178	112,813
1868.	28,837	-----	1882.	37,821	135,165
1869.	29,996	-----	1883.	33,227	201,133
1870.	31,437	-----	1884.	27,888	156,677
1871.	41,126	-----	1885.	28,184	141,575
1872.	43,536	-----	1886.	29,378	153,274
1873.	44,972	-----	1887.	28,704	170,107
1874.	39,126	-----	1888.	22,177	196,698
1875.	27,019	-----	1889.	19,823	206,080
1876.	a39,131	-----	1890.	29,500	238,700
1877.	a40,000	a55,000			

a Partly estimated.

Gypsum imported into the United States from 1867 to 1890.

Years ended—	Total.	Ground or calcined.		Unground.		Value of manufac- tured plas- ter of Paris.
		Quantity.	Value.	Quantity.	Value.	
		<i>Long tons.</i>		<i>Long tons.</i>		
June 30, 1867.	\$125,281	-----	\$29,895	97,951	\$95,386	-----
1868.	114,350	-----	33,988	87,694	80,362	-----
1869.	186,512	-----	52,238	137,039	133,430	\$844
1870.	148,720	-----	46,872	107,237	100,416	1,432
1871.	154,013	-----	64,465	100,400	88,256	1,292
1872.	168,873	-----	66,418	95,339	99,902	2,553
1873.	165,459	-----	35,628	118,926	122,495	7,336
1874.	170,901	-----	36,410	123,717	130,172	4,319
1875.	171,096	-----	52,155	98,772	115,664	3,277
1876.	179,070	-----	47,588	139,713	127,084	4,398
1877.	162,917	-----	49,445	97,656	105,629	7,843
1878.	140,587	-----	33,496	89,239	100,102	6,989
1879.	125,542	-----	18,339	96,963	99,027	8,176
1880.	150,409	-----	17,074	120,327	120,642	12,693
1881.	171,724	-----	24,915	128,607	128,107	18,702
1882.	200,922	5,737	53,478	128,382	127,067	20,377
1883.	218,969	4,291	44,118	157,851	152,982	(a) 21,869
1884.	210,904	4,996	42,904	166,310	168,000	-----
1885.	173,752	6,418	54,208	117,161	119,544	-----
1886.	153,338	5,911	37,642	122,270	115,696	-----
1887.	195,890	4,814	33,736	146,708	162,154	-----
Dec. 31, 1888.	190,787	3,340	20,764	156,697	170,023	-----
1889.	220,140	5,466	40,291	170,965	179,849	-----
1890.	229,859	7,568	55,250	171,289	174,609	-----

a Not specified since 1883.

FLUORSPAR.

The only locality producing fluorspar continues to be at Rosiclair, Illinois. The product in 1889 was 9,500 short tons, valued at \$45,835. In 1890 there was a decrease in production, the product being 8,250 short tons, but an advance in the price increased the value to \$55,328. The following table exhibits the annual production of this mineral since 1882:

Production of fluorspar in the United States from 1882 to 1890.


Years.	Quantity.	Value.	Years.	Quantity.	Value.
	<i>Short tons.</i>			<i>Short tons.</i>	
1882.....	4,000	\$20,000	1887.....	5,000	\$20,000
1883.....	4,000	20,000	1888.....	6,000	30,000
1884.....	4,000	20,000	1889.....	9,500	45,835
1885.....	5,000	22,500	1890.....	8,250	55,328
1886.....	5,000	22,000			

Regarding the reintroduction of fluorspar for metallurgical uses, Dr. Foehr, of Germany, has contributed the following to the *Chemiker Zeitung*:

“Fluorspar was considered an indispensable flux until the commencement of this century; it diminishes the loss of metal and was then the only energetic means of reducing the melting point of slag from ores carrying a high percentage of clay and zinc. Without fluorspar very refractory ores could not be smelted at all.

“Gradually, however, as the blast furnaces and smelting apparatus were improved, fluorspar was superseded by lime and other cheap fluxes, but of late its use has been reintroduced into nearly all branches of metallurgy.

“While fluorspar is regarded merely as a material to unite with excessive silicic acid, the possibility of its adoption is surprising in view of the fact that the cost of fluorspar is six to seven times greater than that of limestone while the reactions of fluorspar and limestone, respectively,



show that the quantitative economy in fluxing with fluorspar compared with limestone is as 156 to 300. The fact is, however, that one part of fluorspar goes further than ten parts of limestone. The former is specially effective in reducing the quantity of fuel; it forms two parts of

slag where limestone forms three, and it forms possibly also fluorsilicate, whereby heat is likely to be liberated.

“While the rather high price of fluorspar prevents its use in the production of ordinary white and gray pig iron, it has proved a rapid and energetic solvent in blast-furnace work, where it is blown in as powder through the nozzles.

“In making silicon iron, fluorspar plays a more important part. A ferro-silicon iron, with 10 per cent. silicon, made specially in Upper Silesia, is almost indispensable for works that make very tough, deep gray castings. This ferro-silicon can be obtained in any ordinary blast furnace from any siliceous iron ore if it is only fluxed with fluorspar and the slag is strongly basic. The fluorspar reduces the silicon energetically; at all events, fluorsilicon is formed which is reduced to silicon by the hydrogen contained in the furnace gases, and possibly also directly by the coke. It does not seem impossible that the greatly increased price for coke will result in a reintroduction of fluorspar as a fuel-saving flux in the manufacture of foundry pig, particularly as even a very small quantity of fluorspar added to the charge at once raises the product to No. 1 deep gray pig, rich in graphite.

“The remarkable property of fluorspar, that it facilitates the reduction of the most different bodies—a property common to almost all the fluorides—makes it a valuable flux in the production of spiegeleisen. It has long been known that fluoride of manganese, as well as a mixture of a manganese combination with fluorspar, can comparatively easily be reduced to metallic manganese by means of sodium. This reaction served Brunner in his successful attempts, the first ever made, to produce metallic manganese in large quantities. The modern application of this method to the blast furnace substitutes carbon for sodium. A highly basic slag, rich in fluorides, seems nearly indispensable for the production of a rich ferro-manganese in the blast furnace.

“The property of fluorspar of carrying phosphorus into the basic slag has never been of special importance as far as pig iron is concerned, but it is utilized by the Krupp & Rollet methods of dephosphorizing pig in the basic-lined cupola furnace. While, at all events in the blast furnace process, the property of calcium fluoride of forming an easily melting slag with phosphates is of some importance, fluorspar in the process of purifying the pig iron serves probably only as a flux for the highly basic lime slag saturated with phosphorus.

“In the Thomas process too, and even in the Bessemer converter, fluorspar is in recent practice being added in small quantities for the purpose of concentrating the slag and reducing the loss of metal; very great care, however, is needed to prevent such a slag from attacking the acid lining. It is also said that in puddling in the various steel-making methods and in the Siemens-Martin process fluorspar is added partly as a slag-forming flux. The details are, however, not known.

“In foundry work, it is an astonishing fact that limestone, which, be-

cause of its cheapness, superseded fluorspar, of late is losing ground to the latter. The limestone flux in cupola-furnace work serves only to slag the ashes of the fuel, the sand adhering to the pig, etc., no chemical effect on the iron being intended. But fluorspar affects the iron noticeably, keeps it gray and soft by keeping the silicon as an alloy, while a limestone flux favors the tendency of the silicon to slag. Besides, fluorspar carries some phosphorus and sulphur into the slag. Fluorspar makes it possible to melt inferior pig iron and a higher percentage of scrap. But, strange enough, practice has shown that too much fluorspar is rather injurious than advantageous; one reason for this being that the manganese contained in the iron is thereby prevented from slagging.

“The quantity of fluorspar which is added to 100 kilograms of pig iron to be remelted is one-third or at the most one-half, kilogram. The improvement of the product caused by this flux is specially manifest in the improved cupola furnaces, particularly the Herbert furnace, which has much facilitated the utilization of inferior iron for soft castings. The property of fluorspar to protect manganese does not seem favorable enough to offset the injury due to its silicon-reducing power. Its use would, at least, require melting in a basic furnace or as cold as possible.

“As the small quantity of the phosphorus and sulphur which is contained in Swedish charcoal iron is almost entirely carried off in the comparatively acid slag by fluorspar, this is of prominent importance for the treatment of very pure qualities of iron.

“Fluorspar was formerly the most important flux for smelting copper ores in the German stack, as well as in the English reverberatory furnace. The Mansfeld copper slate, for instance, was fluxed with up to 10 per cent. of fluorspar, the cost of this being about 8 per cent. of the total smelting cost. The effect of this flux depended essentially on the volatilization of fluorsilicon, whereby the strongly acid slag was reduced in silica. The introduction of improved and heated blasts in the Mansfeld works has almost confined the use of fluorspar to the blowing in of furnaces. Five per cent. of fluorspar is commonly added at the start, but the quantity decreases gradually until after from two to five weeks no fluorspar at all is used. The English reverberatory furnace process fluxed formerly with as much as 10 per cent. of fluorspar, but nowadays this takes place only with ores rather rich in arsenic. Fluoride of calcium with arsenides of metals gives very volatile fluoride of arsenic, which, with a reducing flame, easily escapes. The risk of loss involved in the volatile fluoride of copper necessitates the presence of excessive carbon whenever fluorspar is employed in the metallurgy of copper.

“While fluorspar is at present of small value in the treatment of copper ores containing sulphur, its property of giving very fluid combinations with gypsum and barytes may prove an important means for

working poor oxides and siliceous ores as well as charges containing azurite, malachite, red oxide of copper, atacamite and earthy red oxide of copper, by reducing the smaller part of the sulphate and forming a matte very rich in copper, and by forcing its larger part together with the fluoride of calcium into the slag which thereby becomes thin and very fluid. Equal quantities of fluorspar with gypsum or barytes produce the most fluid slag. A significant point particularly with poor ores high in silica is that this slag is poor in copper—a fact on which was based the former Freiberg practice of resmelting the copper slag, together with pyrites and fluorspar, thus obtaining copper matte and poor slag, the intention probably being to enrich the matte in copper and impoverish it in iron.

“Fluxing copper ores containing nickel with fluorspar is very favorable for the collection of the nickel in the matte, and has been in use in the Riechelsdorf, Grünthal and Mansfeld works. The chemical process is still entirely obscure and worthy of study in the laboratory. Possibly nickel arsenide is decomposed into volatile fluoride of arsenic and nickel, which latter goes into the matte. Fluorspar is an almost indispensable flux for making tough copper and, generally, whenever silicon, which makes copper highly brittle, has to be removed. As a means of producing a matte poor in iron in the reverberatory furnace, a mixture of fluorspar, barytes, and quartz is more energetic and rapid than an addition of only the two last named, the proportion of the fluorspar and the barytes being for this purpose as between 1 and 3, whilst the quantity of quartz depends upon how much iron the roasted matte contains. Too much fluorspar gives a matte rich in iron. For refining and resmelting copper, fluorspar finds a constantly increasing use. Mixed with some soda it is most excellent in resmelting copper ingots and for removing from the metal bath small quantities of arsenic and silicon. The process is kept a secret; the refining slag is, however, reported to be resmelted with gypsum or glauber salts and fluorspar.

“The introduction of the Pils and Raschette furnace has made lead and silver smelting without fluorspar a possibility. It is too expensive for this purpose, except for particularly refractory ores; but it has proved most excellent for fluxing ores containing barytes and zinc. Possibly the temperature of the slag formation is reduced, thus diminishing the quantity of metal that is lost through volatilization. This is of greater importance in the reverberatory than in the stack furnace, so that the use of fluorspar might occasion a special modification of the English reverberatory furnace process, a Derby process, with a flux of about 7 per cent. fluorspar. For resmelting lead slags also, a small fluorspar flux is serviceable. It is used, too, for smelting on the Spanish slag hearth.

“As in improved lead works the ores to be smelted are almost invariably first roasted; the fluorspar is added at the roasting. The quan-

tity varies from 1 to 5 per cent. according to the percentage of the quartz in the ores. One per cent. of fluorspar, if ground as finely as possible, causes a noticeable economy in fuel. As this flux lowers the temperature in a roasting furnace and shortens the roasting process, the yield of metal must also be favorably affected.

“In refining, also, fluorspar is very advantageous, especially when sprinkled on the bath in a fine powder. The litharge is thereby made thinner and retains fewer metallic grains mechanically. The same effect is reached by adding a small quantity of soda, or mixture of soda and fluorspar.

“The slags from tin ores are generally very acid in the stack as well as in the reverberatory furnace. As it is particularly desirable here to reduce the quantity of slag as much as possible, fluorspar, which has this property and in addition makes the slag fluid, has long ago found use, especially in English tin works, where it sometimes forms 5 per cent. of the charge. Commonly, burnt limestone and fluorspar are mixed, although it seems far preferable to employ soda than lime. The fluorspar fluxing must not be too liberal, as otherwise the furnace walls are attacked and tin seems then to go into the slag.

“Fluorspar with zinc ores is very undesirable, as it attacks the distilling vessels. On the other hand, in order to overcome this obstacle, a material composed of pure quartz sand with about 3 per cent. fluorspar and some soda, has tentatively been used for tubes and muffles, which though apt to frit on the surface in annealing, become, on the escape of fluorspar, far more dense and fireproof than otherwise can be obtained. In fact a small quantity of fluorspar is regularly used in any considerable factory making fireproof ware. The ordinary zinc-distilling vessels are said to be extraordinarily improved by a glaze baking consisting of sulphate of zinc and fluorspar in equal quantities, in regard to product as well as the durability of the muffles. In refining pig zinc the remelting is sometimes facilitated by adding a mixture of glauber salt, rock salt, and fluorspar.

“When the price is not too high, fluorspar is an advantageous means of fluxing garnierite, but still more important in the concentration of speiss.

“Fluorspar has been recommended for regenerating brittle silicon platinum, by keeping the platinum in powdered fluorspar incandescent and cemented long enough to enable the total amount of silicon to escape as a fluoride. It appears, however, more rational to substitute ammonium fluoride for fluorspar, the price being immaterial because of the small quantity used.

“It would be a worthy object for scientific ambition to study the physical properties of fluorspar experimentally smelted together with oxides of metals, ores, and metal salts, with or without fluxes of silicates and sulphates, and in different proportions, specially if the range of the investigation were extended to the conduct of metal fluorides and silicon by incandescence in oxidizing and reducing atmosphere.”

Cryolite.—The only source of supply remains at Ivigtok, Greenland. The importations since 1871 have been as follows:

Imports of cryolite for the years 1871 to 1890, inclusive.

Years ended—	Amount.	Value.	Years ended—	Amount.	Value.
	<i>Long tons.</i>			<i>Long tons.</i>	
June 30, 1871.....		\$71,058	June 30, 1881.....		\$103,529
1872.....		75,195	1882.....	3,758	51,589
1873.....		84,226	1883.....	6,508	97,400
1874.....		28,118	1884.....	7,390	106,029
1875.....		70,472	Dec. 31, 1885.....	8,275	110,750
1876.....		103,530	1886.....	8,230	110,152
1877.....		126,692	1887.....	10,328	138,068
1878.....		105,884	1888.....	7,388	98,830
1879.....		66,042	1889.....	8,603	115,158
1880.....		91,366	1890.....	7,129	95,405

M I C A .

The product of mica in 1889 was 49,500 pounds, valued at \$50,000 at the mines in the condition in which it was first sold. In addition to this, 196 short tons of scrap or waste mica were sold for grinding purposes, with a value of \$2,450. The industry, as it plainly shows, has declined rapidly. In 1890 there were signs of improvement. The product aggregated 60,000 pounds, worth \$75,000 at the mines. The scrap mica sold for grinding increased also to 300 tons.

Increased interest in mica properties was evident during 1890. There were some sales of mines in North Carolina, and a company of greater capacity than usual was organized as the Western Carolina Mica Company. The modern apparatus which they have introduced bids well for a much greater yield in the future.

Cut mica produced in the United States from 1880 to 1890.

Years.	Amount.	Value.	Years.	Amount.	Value.
	<i>Pounds.</i>			<i>Pounds.</i>	
1880.....	81,669	\$127,825	1886.....	40,000	\$70,000
1881.....	100,000	250,000	1887.....	70,000	142,250
1882.....	100,000	250,000	1888.....	48,000	70,000
1883.....	114,000	285,000	1889.....	49,500	50,000
1884.....	147,410	368,525	1890.....	60,000	75,000
1885.....	92,000	161,000			

The States producing mica in 1889 were New Hampshire, North Carolina, Virginia, and South Dakota. Only one mine in Virginia, at Amelia Court House, was productive, and that was discontinued early in 1889. The mines in the West, where labor is higher, naturally felt the decline in prices most severely, and hence the New Mexican development at Cerrillos was discontinued in 1888, and in the Black Hills only one mine remained in 1889 out of eleven in 1884. The occurrence of good mica has been determined in Wyoming and Washington, but the owners have not yet developed the mines. This is not surprising when the valuation for the mines determined by the Eleventh Census aggregates \$691,550 and the returns for the year 1889 show a net loss for the entire industry.

The most encouraging outlook for the industry is in connection with the increasing use for the scrap mica, which accumulates in about the proportion of 10 pounds of waste to 1 of cut sheets, even when the cut sheets take in the smaller sizes now used for stoves. By mills located in Denver, Richmond, New York, and Boston a large propor-

tion of this is now ground and used for making lubricants, for insulators, and in wall paper.

Imports.—In October, 1890, mica was placed on the dutiable list by the new tariff, with a duty of 35 per cent. ad valorem. It had previously been imported free. The imports for the year, especially before the law went into effect, were exceptionally heavy—more than double the value of the imports in any previous year. This undoubtedly provides for an accumulation of stock beyond immediate needs.

Unmanufactured mica imported and entered for consumption in the United States, 1869 to 1890, inclusive.

Years ending—	Value.	Years ending—	Value.
June 30, 1869	\$1,165	June 30, 1880	\$12,562
1870	226	1881	5,839
1871	1,460	1882	5,175
1872	1,002	1883	9,884
1873	498	1884	28,284
1874	1,204	1885	28,685
1875	Dec. 31, 1886	<i>a</i> 56,354
1876	569	1887	<i>a</i> 49,085
1877	13,085	1888	<i>a</i> 57,541
1878	7,930	1889	<i>a</i> 97,351
1879	9,274	1890	<i>a</i> 207,375

a Including mica waste.

SOAPSTONE.

Total product in 1889, 12,715 short tons; value, \$231,708. Total product in 1890, 13,670 short tons; value, \$252,309.

The amount of soapstone produced in the United States in 1889 (exclusive of the output of fibrous tale at Gouverneur, New York), was 12,715 short tons, valued at \$231,708. The value here quoted represents the aggregate amount received by operators for their product in the condition in which first marketed, whether rough, manufactured, or pulverized. In some cases the mineral is sold without further preparation than being sawed into slabs convenient for shipping. In other cases, it is manufactured at the quarries into various useful articles for mercantile, domestic, or scientific purposes, or pulverized for use in the manufacture of soap, paint, paper, and rubber, and in such instances the only value obtainable is for the manufactured product. Following the same line of computation in the investigation for 1890, the product was 13,670 short tons, valued in its first selling condition at \$252,309.

Fibrous tale.—The fibrous variety of soapstone obtained at Gouverneur, New York, is especially valuable as a filler in the manufacture of medium grades of paper. The product in 1889 was 23,746 short tons, valued at \$244,170. In 1890 the product increased to 41,354 tons, valued at \$389,196. Of the product in 1890, 10,350 tons were sold in the crude state as mined, and the remainder, 24,459 tons, sold ground ready for use. Mr. Frank C. Goodall, in a paper read before the Institute of Naval Architects records his experience that a paint with soapstone as the mineral ingredient serves unusually well for protecting metallic ship bottoms, and that similar paint has been used for many years in China and Japan.

Talc imported into the United States from 1880 to 1890, inclusive.

Years.	Quantity (pounds).	Value.	Years.	Quantity (pounds).	Value.
1880.....		\$22,807	1886.....		\$24,514
1881.....		7,331	1887.....	(a)	49,250
1882.....		25,641	1888.....	24,165	22,446
1883.....		14,607	1889.....	19,229	30,993
1884.....		41,165	1890.....	1,044	1,560
1885.....		24,356			

a Quantity not reported previous to 1888.

ASPHALTUM.

BY E. W. PARKER.

The production of asphaltum and its allied mineral, bituminous rock, in 1889 was limited to California, Kentucky, and Utah. The commercial product in 1890 was also confined to these localities. Ohio produced 600 tons, but the product was not marketed during the year and is not considered in the total. The varieties, qualities, and values of the several bitumens are so widely different that they might readily be classed as separate minerals. In fact, a new name is usually given to each new discovery. In this manner the names of gilsonite, elaterite, uintite, wurtzilite, albertite, grahamite, and a number of others have been bestowed. The latest discovery has been honored with the name of "litho-carbon." It is found a few hundred miles west of San Antonio, Texas, near the line of the Southern Pacific Railroad. This has been thought by some to be an entirely new mineral, and great claims have been made regarding its possibilities. What is most strenuously claimed for it, and seemingly with some reason, is that it serves unusually well as the foundation for a paint or varnish for covering metallic surfaces. Thin metal covered with a coating of this varnish may be bent and twisted repeatedly without perceptible crack to the covering and without appearance of peeling off. A company has been organized in New York which claims to have obtained possession of several thousand acres of land on which the new mineral occurs, but with the exception of capitalizing the company no steps have been taken toward developing the property. Nor has it been possible to ascertain the extent of the deposit, and the probable effect its development will have industrially. There can be little doubt, however, that it is like the others, a species of asphaltum. It is found as a fossil limestone impregnated with bitumen, yielding upon refining a good quality of asphaltum which dissolves in turpentine to form varnish. This when dry does not crystallize, but remaining soft and pliable, and possessing strong adhesive qualities will doubtless serve the principal purpose claimed for it. Two unknown quantities must, however, be determined—the amount of available mineral and the cost of production and transportation.

The bituminous rock of California occurs in four different counties—Ventura, Santa Cruz, Santa Barbara, and San Luis Obispo. The product of Ventura county is of higher grade than any of the others; that is, it carries a larger percentage of bitumen. The product of the other three counties is used almost exclusively for street paving, it being necessary only to heat the mineral and thoroughly mix the ingredients

before spreading. The average price of the product of Santa Cruz and San Luis Obispo counties is from \$2 to \$2.50 per ton. The Santa Barbara product is a grade between this and the Ventura county mineral, and is worth about \$4 per ton. The Ventura rock is valued at from \$10.50 to \$12 per ton. Some of this is used for street paving, in the preparation of which it is necessary to mix the natural product, while heated with the sand of the locality where used. A considerable saving in transportation expenses is effected by this means. A considerable part of the Ventura product is refined, and used for a covering for piling, wharf timbers, wood conduits, etc., which it renders practically indestructible by protecting them from the action of air, water, insects, and other destructive agents.

The bituminous rock of Kentucky is not essentially different from the product of Santa Cruz and San Luis Obispo counties in California. It is worth about \$2.50 per ton at the mines, which are in Grayson and Hardin counties, and is used for street paving, cellar, warehouse, and brewery flooring, and similar purposes.

The product of Utah consists of bituminous rock worth about \$7.50 at the mines and of "gilsonite," an exceptionally pure form of asphaltum. Gilsonite contains about 90 per cent. pure bitumen. It is used for making street paving by mixing when heated with petroleum, sand, and limestone; for paint and varnish by dissolving in turpentine, and as an insulator for electrical wires. Gilsonite is valued at from \$50 to \$60 per ton at St. Louis, its point of distribution.

The following table shows the annual production of asphaltum and bituminous rock since 1882. Previous to 1888 the output was entirely from California and was consumed in street paving in the large cities. The industry can hardly be considered as having assumed commercial importance until 1888, and in the same year began the production of gilsonite in Utah.

Production of asphaltum and bituminous rock since 1882.

Years.	Short tons.	Value.	Years.	Short tons.	Value.
1882.....	3, 000	\$10, 500	1887.....	4, 000	\$16, 000
1883.....	3, 000	10, 500	1888.....	50, 450	187, 500
1884.....	3, 000	10, 500	1889.....	51, 735	171, 537
1885.....	3, 000	10, 500	1890.....	40, 841	190, 416
1886.....	3, 500	14, 000			

The increased value of the product of 1890 as compared with that of 1889 is due to a decreased production of bituminous rock in California and a largely increased output of gilsonite in Utah.

Trinidad asphaltum.—Notwithstanding the large proportions which the asphaltum and bituminous rock industry has attained in the West, the bulk of the supply for the United States, in fact nearly all that is consumed in the Eastern cities, continues to be procured from the island of Trinidad. This is due to the excessive cost of transportation

from our Western localities. The European demand is supplied from the bituminous limestone deposits of Neufchatel, Switzerland, and Seyssel, France. A limited amount of Neufchatel asphaltum is imported into the United States. The following table shows the imports of asphaltum from 1867 to 1890, inclusive:

Asphaltum imported into the United States from 1867 to 1890.

Years ended—	Quantity.	Value.	Years ended—	Quantity.	Value.
	<i>Short tons.</i>			<i>Short tons.</i>	
June 30, 1867.....		\$6,268	June 30, 1879.....	8,084	\$39,635
1868.....	185	5,632	1880.....	11,830	87,889
1869.....	203	10,559	1881.....	12,883	95,410
1870.....	488	13,072	1882.....	15,015	102,698
1871.....	1,301	14,760	1883.....	33,116	149,999
1872.....	1,474	35,533	1884.....	36,078	145,571
1873.....	2,314	38,298	Dec. 31, 1885.....	18,407	88,087
1874.....	1,183	17,710	1886.....	32,565	108,523
1875.....	1,171	26,006	1887.....	30,808	95,735
1876.....	807	23,818	1888.....	36,494	84,045
1877.....	4,532	36,550	1889.....	61,952	138,163
1878.....	5,476	35,932	1890.....	73,861	223,368

Capt. F. V. Greene, of New York City, vice-president of the Barber Asphalt Company, contributed some very interesting information to the census report on asphaltum from Trinidad and other foreign sources. As the figures and statements given by Captain Greene cover also the calendar year 1890, the following is abstracted from his contribution. Some of the information is obtained from the books of his company. Other portions are estimates which, while not derived from positive records, may be considered substantially correct:

Imports of Trinidad asphaltum by all companies from 1880 to 1890, inclusive.

Years.	Long tons.	Years.	Long tons.
1880.....	3,913	1887.....	26,593
1881.....	6,707	1888.....	35,137
1882.....	14,263	1889.....	52,881
1883.....	23,309	1890.....	54,692
1884.....	19,650		
1885.....	15,289	Total.....	280,171
1886.....	27,757		

Pavements of Trinidad asphaltum.—The number of square yards of Trinidad asphaltum laid in the United States in the past decade is as follows:

Number of square yards of Trinidad asphalt paving laid in the United States from 1880 to 1890, inclusive.

Years.	Sq. yards.	Years.	Sq. yards.
1880.....	106,838	1887.....	799,335
1881.....	116,629	1888.....	757,101
1882.....	196,184	1889.....	1,130,863
1883.....	387,510	1890.....	1,857,000
1884.....	424,524		
1885.....	403,882	Total.....	a6,803,054
1886.....	623,188		

a Equivalent to 446 miles of roadway 26 feet wide.

Trinidad asphaltum is being used for street paving in the forty-nine cities in the United States and Canada named in the following list:

Cities where Trinidad asphalt pavements are used.

Washington and Georgetown, D. C.	Omaha, Nebraska.
Savannah, Georgia.	Newark, New Jersey.
Chicago, Illinois.	Albany, Binghampton, Brooklyn, Buffalo,
Fort Wayne and Indianapolis, Indiana.	Lockport, Long Island City, New York,
Topeka, Wichita, and Wyandotte, Kansas.	Rochester, Schenectady, Syracuse,
Louisville, Kentucky.	Troy, and Utica, New York.
New Orleans, Louisiana.	Cincinnati, Cleveland, Columbus, Toledo,
Baltimore, Maryland.	and Youngstown, Ohio.
Boston, Massachusetts.	Allegheny, Altoona, Erie, Harrisburg,
Detroit, Michigan.	Philadelphia, Pittsburg, Scranton, and
Saint Paul, Minnesota.	Wilkesbarre, Pennsylvania.
Kansas City, Saint Joseph, and Saint	Chattanooga, Tennessee.
Louis, Missouri.	Montreal, Quebec, and Toronto, Canada.

Percentage of uses for Trinidad asphaltum.—From the best information obtainable the proportions of Trinidad asphaltum used for different purposes are about as follows:

Proportions of uses of Trinidad asphaltum.

	Per cent.
For laying sheet asphalt pavements.....	72
For manufacturing asphalt blocks and tiles for pavements.....	24
Total for paving	96
For roofing.....	3
For all other purposes	1
Total.....	100

The amount of asphalt blocks manufactured and laid as pavements has varied from 5,000 to 100,000 square yards per annum, and the total from 1880 to 1890, inclusive, is estimated at 500,000 square yards.

Pavements from bituminous limestone.—About 55,000 square yards of bituminous limestone pavements were laid in Washington, D. C., during 1876 and 1877, and about 3,000 square yards in New York in 1883 or 1884. Nearly all of this was subsequently taken up and replaced by Trinidad asphaltum. In 1887 about 10,000 square yards were laid in Rochester, New York; in 1888 about 20,000 square yards in Saint Augustine, Florida, and in 1890, 40,000 square yards in New York City. Captain Greene estimates that the total amount of bituminous limestone pavement now in use in the United States does not exceed 75,000 square yards.

Asphalt pavements in European cities.—The asphalt pavements in Europe are all made from the bituminous limestones obtained from the localities mentioned previously in this report. The pavements are found in Berlin, London, Paris, and a few other cities, probably not exceeding ten in all. The total area covered is, approximately, as fol-

lows, according to the authorities cited, and it is about one-fourth of that covered by Trinidad asphalt pavements in the United States.

Areas of bituminous limestone pavements in use in European cities.

	Square yards.	Authorities.
Berlin	681,486	United States Consular Reports, No. 120. Reports of paving companies. Annuaire Statistique de la Ville de Paris, 1888, page 26. Estimated.
London	360,000	
Paris	357,360	
Other cities	300,000	
Total	1,698,846	

Ozocerite.—The amount of refined ozocerite or mineral wax produced in the United States in 1889 was 50,000 pounds, valued at \$2,500 at the mines. In 1890 the product increased to 350,000 pounds. The value at the mines was about the same per pound as in 1889. The price quoted during the year was 7½ cents per pound at New York. The locality from which this product is obtained is near Thistle, Utah. It was discovered in 1885, but no work of any importance was done upon the property until 1888, when 65,000 pounds of crude mineral were mined. The principal supply of mineral wax is from Galicia, in Austria. This property was discovered in 1859. It was not until 1865, however, that sufficient capital could be obtained to push the enterprise. Now about thirty-five companies are in the field.

Imports of mineral wax. (a)

Years ended—	Quantity.	Value.	Years ended—	Quantity.	Value.
	<i>Pounds.</i>			<i>Pounds.</i>	
June 30, 1873.....	25,135	\$4,244	June 30, 1882.....	272,509	29,322
1874.....	380	40	1883.....	565,658	52,774
1875.....	7,430	1,026	1884.....	617,992	69,026
1876.....	16,525	2,229	1885.....	1,056,438	123,976
1877.....	101,604	11,720	Dec. 31, 1886.....	800,496	71,220
1878.....	69,884	7,870	1887.....	718,769	59,084
1879.....	44,963	6,016	1888.....	1,164,940	89,131
1880.....	103,973	14,057	1889.....	1,078,725	86,682
1881.....	98,911	12,792	1890.....	1,669,241	142,333

a Up to and including 1883 imported under "Wax and manufactures of," and classed as "bay or myrtle, Brazilian and Chinese," since as "Mineral wax."

SALT.

BY WILLIAM A. RABORG.

The production of salt in the United States during the years 1889 and 1890 was as follows: In 1889, 8,005,565 barrels, valued at \$4,195,412, and in 1890, 8,776,991 barrels, valued at \$4,752,286. The amount and value of the salt produced in the various States and Territories in the latter year, 1890, is given in the following table:

Quantity and value of salt produced in the United States during the year 1890.

States and Territories.	Production.	Value.
	<i>Barrels.</i>	
Michigan	3,837,632	\$2,302,579
New York	2,532,036	1,266,018
Ohio	231,303	136,617
West Virginia	229,938	134,688
Louisiana	273,553	132,000
California	62,363	57,085
Utah	427,500	126,100
Kansas	882,666	397,199
Nevada, Illinois, Indiana, Virginia, Tennessee, Kentucky, and other States and Territories, estimated	300,000	200,000
Total	8,776,991	4,752,286

Comparative table of production of salt in States and Territories during years 1883 to 1890.

States and Territories.	1883.		1884.		1885.		1886.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
	<i>Barrels.</i>		<i>Barrels.</i>		<i>Barrels.</i>		<i>Barrels.</i>	
Michigan	2,894,672	\$2,344,684	3,161,806	\$2,392,530	3,297,403	\$2,967,663	3,677,257	\$2,426,989
New York	1,619,486	680,638	1,788,454	705,978	2,304,787	874,258	2,431,563	1,243,721
Ohio	350,000	231,000	320,000	201,600	306,847	199,450	400,000	260,000
West Virginia	320,000	211,000	310,000	195,000	223,184	145,070	250,000	162,500
Louisiana	265,215	141,125	223,964	125,677	299,271	139,911	299,691	108,372
California	214,286	150,000	178,571	120,000	221,428	160,000	214,285	150,000
Utah	107,143	100,000	114,285	80,000	107,140	75,000	164,285	100,000
Nevada	21,429	15,000	17,857	12,500	28,593	20,000	30,000	21,000
Kansas								
Illinois, Indiana, Virginia, Tennessee, Kentucky, and other States and Territories (a)	400,000	377,595	400,000	364,443	250,000	243,993	240,000	352,763
Total	6,192,231	4,251,042	6,514,937	4,197,734	7,038,653	4,825,345	7,707,081	4,825,345

a Estimated.

Comparative table of production of salt in States and Territories during years 1883 to 1890—Continued.

States and Territories.	1887.		1888.		1889.		1890.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
	<i>Barrels.</i>		<i>Barrels.</i>		<i>Barrels.</i>		<i>Barrels.</i>	
Michigan....	3,944,309	\$2,291,842	3,866,228	\$2,261,743	3,856,929	\$2,088,909	3,837,632	\$2,302,579
New York....	2,353,560	936,894	2,318,483	1,130,409	2,273,007	1,136,503	2,532,036	1,266,018
Ohio.....	365,000	219,000	380,000	247,000	250,000	162,500	231,303	136,617
West Vir- ginia....	225,000	135,000	220,000	143,000	200,000	130,000	229,938	134,688
Louisiana...	341,093	118,735	394,385	134,652	325,629	152,000	273,553	132,000
California...	200,000	140,000	220,000	92,400	150,000	63,000	62,363	57,085
Utah.....	325,000	102,375	151,785	32,000	200,000	60,000	427,500	126,100
Nevada.....								
Kansas.....			155,000	189,000	450,000	202,500	882,666	397,199
Illinois, In- diana, Vir- ginia, Ten- nessee, Kentucky, and other States and Territo- ries (a)....	250,000	150,000	350,000	143,999	300,000	200,000	300,000	200,000
Total....	8,003,962	4,093,846	8,055,881	4,374,203	8,005,565	4,195,412	8,776,901	4,752,286

a Estimated.

MICHIGAN

With a production of 3,837,632 barrels of salt, valued at \$2,302,579, Michigan headed the list of salt-producing States and Territories in 1890. In 1889 the production was 3,856,929 barrels, valued at \$2,088,909. Since 1887 there has been a yearly decrease in the production, although the amount of salt made continued to represent over one-half the product of the United States.

The average depths of the wells in the different counties were as follows: Mason, 2,200 feet; Manistee, 2,000 feet; Saint Clair, 1,700 feet; Huron, 1,200 feet; Midland, 1,200 feet; Bay, Saginaw, and Iosco, 850 feet.

During 1890 there were 122 salt-producing companies in the State, 97 of which were in operation, having a capacity of production of 5,950,000 barrels.

Product of Michigan salt in 1890, by districts.

Counties.	Fine.	Bulk.	Fine packers'.	Packers'.	Solar.	Second quality.	Total.
	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>
Saginaw.....	655,293	305,127	308	1,659	18,896	25,571	1,006,854
Bay.....	581,072	214,787	462	3,138	20,644	820,103
Manistee.....	826,293	84,527	3,716	12,691	79,298	1,006,525
Mason.....	333,871	16,013	2,270	15,463	367,617
Huron.....	32,676	22,968	37	55,681
St. Clair.....	155,754	81,123	1,619	2,812	703	242,011
Iosco.....	289,232	289,232
Midland.....	46,812	1,353	55	1,389	49,609
Total.....	2,921,003	725,898	8,430	20,337	18,896	143,068	3,837,632

Grades of salt produced in Michigan as reported by the inspectors from 1869 to 1890, inclusive.

Years.	Fine.	Packers'.	Solar.	Second quality.	Common coarse.	Total for each year.
	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>	<i>Barrels.</i>
1869.....	513,989	12,918	15,264	19,117	561,288
1870.....	568,326	17,869	15,507	19,650	621,352
1871.....	655,923	14,677	37,645	19,930	728,175
1872.....	672,034	11,110	21,461	19,876	724,481
1873.....	746,702	23,671	32,267	20,706	823,346
1874.....	960,757	20,090	29,391	16,741	1,026,979
1875.....	1,027,886	10,233	24,336	19,410	1,081,865
1876.....	1,402,410	14,233	24,418	21,668	1,462,729
1877.....	1,590,841	20,389	22,949	26,818	1,660,997
1878.....	1,770,361	19,367	33,541	32,615	1,855,884
1879.....	1,997,350	15,641	18,020	27,029	2,058,040
1880.....	2,598,037	16,691	22,237	48,623	2,685,588
1881.....	2,673,910	13,885	9,683	52,821	2,750,299
1882.....	2,928,542	17,208	31,235	60,222	3,037,307
1883.....	2,828,087	15,424	16,735	33,526	2,894,672
1884.....	3,087,033	19,308	16,957	38,508	3,161,806
1885.....	3,230,646	15,480	19,849	31,428	3,297,403
1886.....	3,548,731	22,221	31,177	71,235	3,893	3,677,257
1887.....	3,819,738	19,385	13,903	73,905	17,378	3,944,309
1888.....	3,720,319	18,126	26,174	87,694	13,915	3,866,228
1889.....	3,721,099	19,780	17,617	93,455	4,978	3,856,929
1890.....	3,655,331	20,337	18,896	143,068	3,837,632

NEW YORK.

Of the 2,532,036 barrels of salt, valued at \$1,266,018, which is given as the production of the State of New York during 1890, 1,546,412 barrels were made in the Onondaga reservation and 985,624 barrels in the Warsaw district. An annual decrease in the production of the Onondaga district has occurred each year since 1882, when the amount of salt made was nearly double that of 1890, while the product of the Warsaw district in 1890 was very nearly 13 times as great as that of 1883.

Product of salt in New York for the years 1883 to 1890.

	1883.	1884.	1885.	1886.
	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>
Onondaga reservation.....	7,497,431	6,942,270	6,934,299	6,101,757
Warsaw district.....	600,000	2,000,000	4,589,635	6,056,060
Total.....	8,097,431	8,942,270	11,523,934	12,157,817
	1887.	1888.	1889.	1890.
	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>
Onondaga reservation.....	5,695,797	5,657,367	5,365,039	4,923,122
Warsaw district.....	6,072,000	5,935,000	6,000,000	7,732,060
Total.....	11,767,797	11,592,367	11,365,039	12,660,182

Salt inspected at the Onondaga wells in 1839 and 1890.

Districts.	Solar.		Fine ground.		Ground solar.		Ground dairy.	
	1839.	1890.	1839.	1890.	1839.	1890.	1839.	1890.
Syracuse	<i>Bushels.</i> 841,042	<i>Bushels.</i> 837,807	<i>Bushels.</i> 647,693	<i>Bushels.</i> 637,539	<i>Bushels.</i> 146,933	<i>Bushels.</i> 142,734	<i>Bushels.</i> 77,773	<i>Bushels.</i> 44,495
Salina	163,200	138,803	629,035	537,783
Liverpool	756,760	688,133	142,947	142,965
Geddes	1,008,987	918,994	832,046	714,458	118,618	124,411
Total	2,769,989	2,583,737	2,251,726	2,032,745	146,933	142,734	196,391	168,906

Production of the Onondaga district, 1797 to 1890, inclusive.

[Bushels of 56 pounds.]

Years.	Solar.	Fine.	Total.	Years.	Solar.	Fine.	Total.
	<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>		<i>Bushels.</i>	<i>Bushels.</i>	<i>Bushels.</i>
1797	25,474	25,474	25,474	1844	332,418	3,671,134	4,003,552
1798	59,928	59,928	59,928	1845	353,455	3,408,903	3,762,358
1799	42,704	42,704	42,704	1846	331,705	3,507,146	3,838,851
1800	50,000	50,000	50,000	1847	262,879	3,088,476	3,351,355
1801	62,000	62,000	62,000	1848	342,497	4,394,629	4,737,126
1802	75,000	75,000	75,000	1849	377,735	4,705,834	5,083,569
1803	90,000	90,000	90,000	1850	374,732	3,894,187	4,268,919
1804	100,000	100,000	100,000	1851	378,967	4,235,150	4,614,117
1805	154,071	154,071	154,071	1852	633,595	4,288,938	4,922,533
1806	122,577	122,577	122,577	1853	577,947	4,826,577	5,404,524
1807	175,448	175,448	175,448	1854	734,474	5,068,873	5,803,347
1808	319,618	319,618	319,618	1855	498,124	5,584,761	6,082,885
1809	128,282	128,282	128,282	1856	709,391	5,257,419	5,966,810
1810	450,000	450,000	450,000	1857	481,280	3,830,846	4,312,126
1811	200,000	200,000	200,000	1858	1,514,554	5,518,665	7,033,219
1812	221,011	221,011	221,011	1859	1,345,022	5,540,250	6,884,272
1813	226,000	226,000	226,000	1860	1,462,565	4,130,682	5,593,247
1814	295,000	295,000	295,000	1861	1,884,697	5,315,694	7,200,391
1815	322,058	322,058	322,058	1862	1,983,022	7,070,852	9,053,874
1816	348,665	348,665	348,665	1863	1,437,656	6,504,727	7,942,383
1817	408,665	408,665	408,665	1864	1,971,122	5,407,712	7,378,834
1818	406,540	406,540	406,540	1865	1,886,760	4,499,170	6,385,930
1819	548,374	548,374	548,374	1866	1,978,183	5,180,320	7,158,503
1820	458,329	458,329	458,329	1867	2,271,892	5,323,673	7,595,565
1821	526,049	526,049	526,049	1868	2,027,490	6,039,126	8,066,616
1822	481,562	481,562	481,562	1869	1,857,942	6,804,295	8,662,237
1823	726,988	726,988	726,988	1870	2,487,601	6,260,422	8,748,113
1824	816,634	816,634	816,634	1871	2,464,404	5,910,492	8,374,896
1825	757,203	757,203	757,203	1872	1,882,604	6,048,321	7,930,925
1826	811,023	811,023	811,023	1873	1,691,359	5,768,998	7,460,357
1827	983,410	983,410	983,410	1874	1,667,368	4,361,932	6,029,300
1828	1,160,888	1,160,888	1,160,888	1875	2,655,955	4,523,491	7,179,446
1829	1,129,280	1,129,280	1,129,280	1876	2,308,679	3,083,998	5,392,677
1830	1,435,446	1,435,446	1,435,446	1877	2,525,335	3,902,648	6,427,983
1831	1,514,037	1,514,037	1,514,037	1878	2,788,754	4,387,443	7,176,197
1832	1,652,985	1,652,985	1,652,985	1879	2,957,744	5,364,418	8,322,162
1833	1,838,646	1,838,646	1,838,646	1880	2,516,485	5,482,265	7,998,750
1834	1,943,252	1,943,252	1,943,252	1881	3,011,461	4,905,775	7,917,236
1835	1,209,867	1,209,867	1,209,867	1882	3,032,447	5,307,733	8,340,180
1836	1,912,858	1,912,858	1,912,858	1883	2,444,374	5,053,057	7,497,431
1837	2,167,287	2,167,287	2,167,287	1884	2,353,860	4,588,410	6,942,270
1838	2,575,033	2,575,033	2,575,033	1885	2,439,332	4,494,967	6,934,299
1839	2,864,718	2,864,718	2,864,718	1886	2,772,348	3,329,409	6,101,757
1840	2,622,305	2,622,305	2,622,305	1887	3,118,974	2,576,823	5,695,797
1841	220,247	3,120,520	3,340,767	1888	3,115,314	2,542,053	5,657,367
1842	163,021	2,128,882	2,291,903	1889	2,916,922	2,448,117	5,365,039
1843	318,105	2,809,395	3,127,500	1890	2,726,471	2,201,651	4,928,122

Average strength of Onondaga brines.

Years.	Syracuse.	Salina.	Liverpool.	Geddes.	Average.
1865	66.17	66.47	60.65	66.17	64.86
1866	65.90	65.81	58.34	65.90	63.98
1867	64.44	64.35	64.35	63.95	64.27
1869	60.98	60.36	60.36	59.02	60.18
1870	59.49	58.94	58.94	59.34	59.17
1871	63.00	62.35	62.35	63.82	62.88
1872	65.10	66.00	67.00	66.20	66.07
1873	63.43	65.33	65.43	67.52	65.43
1874	63.80	66.15	66.15	67.15	65.81
1875	63.88	66.38	66.38	69.50	66.54
1876	66.75	67.70	67.70	69.33	67.87
1877	68.94	69.19	69.19	69.59	69.23
1878	69.93	70.58	70.58	70.02	70.27
1879	66.61	67.47	67.47	67.16	67.17
1880	66.13	67.10	67.10	67.55	66.97
1881	67.02	66.68	66.68	68.21	67.14
1882	67.75	67.24	67.24	68.63	67.71
1883	66.67	68.30	68.30	69.34	68.15
1884	67.88	71.58	71.58	70.10	70.28
1885	67.63	70.99	70.99	69.25	69.72
1886	68.27	73.84	73.84	72.46	72.10
1887	67.30	70.77	70.77	72.20	70.26
1888	67.91	69.95	69.95	72.41	70.05
1889	67.02	69.28	69.28	71.93	69.38
1890	67.43	71.05	71.05	72.42	70.49

Production of salt in the Warsaw district, New York, in 1890.

Subdistricts.	Bushels.
Warsaw	5,000,000
Mount Morris	700,000
Silver Springs	586,040
Le Roy	500,000
Piffard	700,000
Castile	246,020
Total	7,732,060

The Tully Rock Salt and Brine Supply.—The town of Tully, in which is situated the rock salt deposit which furnishes the Solvay Process Company with its brine, is situated in the southern portion of Onondaga county. It is bounded on the south by Cortland county, on the east by the town of Fabius, on the north by the town of Lafayette, and on the west by the towns of Otisco and Spafford. Its southern portion, with the village of the same name and three lakes (though a fourth lake is on the same plateau, but in Cortland county), is surrounded by hills of considerable size and extent. The artificial outlet of Crooked lake formed the beginning of Onondaga creek and is at present used by the Solvay Process Company to furnish the fresh water for dissolving the rock salt in their wells. The Tully lakes are some 800 feet above Syracuse, while the twenty-one wells are about 300 feet below these lakes, so that the water from the lakes not only furnish the solvent of the rock salt but also the power by which the saturated brine is forced to the surface and into a reservoir from whence it runs by gravity to Syracuse. This advantage can not be overestimated, since it does away with the daily expense of pumping the brine and all that pertains to the latter operation.

The first well which was sunk in this locality is situated at a point near the center of the valley, when descending from the Tully Hills, near the cross road between the western and eastern portion of the valley. This well had to be abandoned at about 400 feet depth, since the tube collapsed after passing into quicksand. The next well was sunk 1,400 feet east of the former. It was started in the shales of the Hamilton group, through which it passed for 713 feet, then entering the limestones of the Helderberg group and continuing in the same for about 498 feet, when a bed of rock salt was penetrated for about 45 feet, making the total depth of the well 1,261 feet. The dip of the rock, as ascertained in these borings is 40.7 feet per mile from north to south, while the ground rises from the north to the south about 120 feet for 7,000 feet, the distance between the most northern and the most southern wells. This first successful well is called the Tully well or well "A 1" of group A (not used at present). Later a well was sunk about 4 miles farther north or about 1 mile south of Cardiff village. The drill hole penetrated through 244 feet of the Hamilton shales, 500 feet of the limestones belonging to the Helderberg group, and finally 100 feet in red shales of the salt group, when it was abandoned.

The twenty wells now in use by the company are in groups, four wells in each group. The distance between the groups is 1,000 feet from north to south and 400 feet between the wells of the same group in the same direction, while the distance from the east to the west between the wells of the group is but 150 feet. Thus each group of wells forms a rectangle of 400 feet by 150 feet with a well at each corner, and all the groups together occupy a rectangle 6,000 feet by 150 feet. The greater number of these wells were only sunk through the first rock-salt bed, though a second bed of 54 feet thickness was found in some of them. The results obtained in these borings are given in the following table:

Depth of salt wells at Tully, New York.

Well.	Depth to salt.	Thick-ness of salt-bed.	Well.	Depth to salt.	Thick-ness of salt-bed.	Well.	Depth to salt.	Thick-ness of salt-bed.
	<i>Feet.</i>	<i>Feet.</i>		<i>Feet.</i>	<i>Feet.</i>		<i>Feet.</i>	<i>Feet.</i>
A 1.....	1,218	43	C 3.....	1,070	45	E 2.....	1,040	44
B 1.....	1,175	318	C 4.....	1,057	44	E 3.....	1,011	61
B 2.....	1,435	50	D 1.....	1,072	43	E 4.....	1,023	39
B 3.....	1,170	228	D 2.....	1,075	43	F 1.....	1,014	35
B 4.....	1,456	25	D 3.....	1,053	48	F 2.....	992	47
C 1.....	1,085	47	D 4.....	1,053	52	F 3.....	1,012	40
C 2.....	1,069	45	E 1.....	1,030	53	F 4.....	974	41

From this table it may be concluded that the first layer of the rock-salt deposit underlying the southern part of Onondaga county is at least 43 feet thick and separated from a second layer of salt of 54 feet thickness by 25 feet of shales except in those parts where the wells of group B are situated.

KANSAS.

In 1890, the salt production of Kansas was 882,666 barrels, valued at \$397,199. The rapid growth of the industry in this State has placed Kansas prominently on the list of salt-producing States, and accounts for the decrease in production at other localities which formerly supplied the sections of country which now depend upon the Kansas product.

OHIO.

In 1890, 231,303 barrels of salt, valued at \$136,617, was made in the State of Ohio, being about 20,000 barrels less than the production for 1889.

Estimated production of salt in Ohio from 1882 to 1890.

Years.	Barrels.	Value.	Years.	Barrels.	Value.
1882.....	400,000	\$300,000	1887.....	365,000	\$219,000
1883.....	350,000	231,000	1888.....	380,000	247,000
1884.....	320,000	201,600	1889.....	250,000	162,500
1885.....	306,847	199,450	1890.....	231,303	136,617
1886.....	400,000	260,000			

WEST VIRGINIA.

The production of salt in West Virginia during the year 1890 is estimated at 229,938 barrels, valued at \$134,688.

Estimated production of salt in West Virginia from 1882 to 1890.

Years.	Barrels.	Value.	Years.	Barrels.	Value.
1882.....	400,000	\$300,000	1887.....	225,000	\$135,000
1883.....	320,000	211,200	1888.....	220,000	143,000
1884.....	310,000	195,300	1889.....	200,000	130,000
1885.....	223,184	145,070	1890.....	229,938	134,688
1886.....	250,000	162,500			

LOUISIANA.

The production of salt at the Petite Anse mine in 1890 was 273,553 barrels (39,079 tons), valued at \$132,000, being 46,493 barrels less than the product for 1889.

Production of the Petite Anse salt mine from 1882 to 1890.

Years.	Short tons.	Years.	Short tons.
1882.....	25,550	1887.....	47,750
1883.....	37,130	1888.....	55,214
1884.....	81,355	1889.....	45,588
1885.....	41,898	1890.....	39,079
1886.....	41,957		

UTAH.

In 1890, 427,500 barrels of salt, valued at \$126,100, were produced in Utah. The following table gives the production and value of salt made in the Territory during the years 1883 to 1890, inclusive:

Production of salt in Utah, 1883 to 1890.

Years.	Quantity.	Value.	Years.	Quantity.	Value.
	<i>Barrels.</i>			<i>Barrels.</i>	
1883.....	107, 143	\$100, 000	1887.....	325, 000	\$102, 375
1884.....	114, 285	80, 000	1888.....	151, 785	32, 000
1885.....	107, 140	75, 000	1889.....	200, 000	60, 000
1886.....	104, 285	100, 000	1890.....	427, 500	126, 100

CALIFORNIA.

The salt made in Alameda, San Bernardino, and San Diego counties in 1890 amounted to 62,363 barrels, valued at \$57,085.

In San Bernardino county the Cook-Perkins mine produced 150 tons of salt, valued at \$1,275. The whole product was shipped to the stock ranges of Arizona and New Mexico for supplying cattle. The area of the deposit includes 160 acres, there being about 90 acres exposed to the surface. The quarrying is done with giant powder for 30 cents per ton; the transportation charge from the mine or quarry to the railroad, 17 miles, is \$4.50 per ton.

Five years ago about 200 tons were shipped to New Mexico for the stock ranges, in blocks weighing from 200 to 1,400 pounds. It was put out on the ranges at convenient places for the cattle to use, and there are a number of the blocks still on the range, shipped that year, with no material loss. It has saved the stock ranchers the employment of herders to a considerable extent, as the cattle will invariably come back from once to twice a month to the place where the salt is deposited for their use.

IMPORTS AND EXPORTS.

Salt imported and entered for consumption in the United States, 1867 to 1890, inclusive.

[Calendar years ending December 31 from 1886 to 1890; previous years end June 30.]

Years.	In bags, barrels, and other packages.		In bulk.		For the purpose of curing fish.		Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>		
1867.....	254, 470, 862	\$696, 570	229, 304, 323	\$336, 302	\$1, 032, 872
1868.....	308, 446, 080	915, 546	219, 975, 096	365, 458	1, 281, 004
1869.....	297, 382, 750	895, 272	256, 765, 240	351, 168	1, 246, 440
1870.....	288, 470, 287	797, 194	349, 776, 433	507, 874	68, 597, 023	\$87, 048	1, 392, 116
1871.....	283, 993, 799	800, 454	274, 730, 373	355, 318	64, 671, 139	66, 008	1, 221, 780
1872.....	258, 232, 807	788, 893	257, 637, 230	312, 569	57, 830, 029	80, 155	1, 161, 617
1873.....	239, 494, 117	1, 254, 818	388, 012, 132	525, 585	86, 756, 628	86, 193	1, 866, 596
1874.....	358, 375, 496	1, 452, 161	427, 294, 209	649, 838	105, 613, 913	126, 896	2, 228, 895
1875.....	318, 673, 091	1, 200, 541	401, 270, 315	549, 111	110, 249, 440	119, 607	1, 869, 259
1876.....	331, 266, 140	1, 153, 480	379, 478, 218	462, 106	118, 760, 638	126, 276	1, 741, 862
1877.....	359, 005, 742	1, 059, 941	444, 044, 370	532, 831	132, 433, 972	140, 787	1, 733, 559

Salt imported and entered for consumption in the United States, etc.—Continued.

Years.	In bags, barrels, and other packages.		In bulk.		For the purpose of curing fish.		Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>		
1878	352, 109, 963	\$1, 062, 995	414, 813, 516	\$483, 909.	100, 794, 611	\$96, 898	\$1, 643, 802
1879	375, 286, 472	1, 150, 018	434, 760, 132	532, 706	94, 060, 114	95, 841	1, 778, 565
1880	400, 970, 551	1, 180, 082	449, 743, 872	548, 425	109, 024, 446	119, 667	1, 848, 174
1881	412, 442, 291	1, 242, 543	529, 361, 042	658, 068	133, 395, 065	144, 347	2, 044, 958
1882	329, 969, 300	1, 036, 932	399, 100, 238	474, 200	134, 777, 569	147, 058	1, 708, 190
1883	312, 911, 360	1, 035, 946	412, 938, 686	451, 001	142, 065, 557	154, 671	1, 641, 618
1884	340, 759, 010	1, 093, 628	441, 613, 517	433, 827	126, 605, 276	122, 463	1, 649, 918
1885	351, 276, 969	1, 030, 029	412, 322, 341	386, 858	140, 067, 018	121, 429	1, 538, 316
1886	319, 232, 750	966, 993	366, 621, 223	371, 000	103, 360, 362	94, 721	1, 432, 714
1887	275, 774, 571	850, 069	343, 216, 331	328, 201	105, 577, 947	107, 089	1, 285, 359
1888	238, 921, 421	629, 435	272, 650, 231	246, 022	113, 459, 083	111, 120	977, 577
1889	180, 906, 293	627, 134	234, 499, 635	249, 232	97, 960, 624	100, 123	976, 489
1890	172, 611, 041	575, 260	243, 756, 044	252, 848	98, 279, 719	96, 648	924, 756

Salt of domestic production exported from the United States from 1790 to 1890, inclusive.

Fiscal years ending September 30 until 1842, and June 30 since.	Quantity.	Value.	Calendar years ending December 31 from 1886 to 1890; previous years end June 30.	Quantity.	Value.
	<i>Bushels.</i>			<i>Bushels.</i>	
1790	31, 935	\$8, 236	1860	475, 445	\$129, 717
1791	4, 208	1, 052	1861	537, 401	144, 046
1830	47, 488	22, 978	1862	397, 506	228, 109
1831	45, 847	26, 848	1863	584, 901	277, 838
1832	45, 072	27, 014	1864	635, 519	296, 088
1833	25, 069	18, 211	1865	589, 537	358, 109
1834	89, 664	54, 007	1866	670, 644	300, 980
1835	126, 230	46, 483	1867	605, 825	304, 030
1836	49, 917	31, 943	1868	624, 970	289, 936
1837	99, 133	58, 472	1869	442, 947	190, 076
1838	114, 155	67, 707	1870	298, 142	119, 582
1839	264, 337	64, 272	1871	120, 156	47, 115
1840	92, 145	42, 246	1872	42, 603	19, 978
1841	215, 084	62, 765	1873	73, 323	43, 777
1842	110, 400	39, 064	1874	31, 657	14, 701
1843 (nine months)	40, 678	10, 262	1875	47, 094	16, 273
1844	157, 529	47, 755	1876	51, 014	18, 378
1845	131, 500	45, 151	1877	65, 771	20, 133
1846	117, 627	30, 520	1878	72, 427	24, 968
1847	202, 244	42, 333	1879	43, 710	13, 612
1848	219, 145	73, 274	1880	22, 179	6, 613
1849	312, 063	82, 972	1881	45, 455	14, 752
1850	319, 175	75, 103	1882	42, 085	18, 265
1851	344, 061	61, 424	1883	54, 147	17, 321
1852	1, 467, 676	89, 316	1884	70, 014	26, 007
1853	515, 857	119, 729	1885	41, 101, 587	26, 488
1854	548, 185	159, 026	1886	4, 828, 863	29, 580
1855	536, 073	156, 879	1887	4, 685, 080	27, 177
1856	698, 458	311, 495	1888	5, 359, 237	32, 986
1857	576, 151	190, 099	1889	5, 378, 450	31, 405
1858	533, 100	162, 650	1890	4, 927, 022	30, 079
1859	717, 257	212, 710			

a Pounds from 1885.

Customs districts and ports into which salt was imported during the fiscal years ending June 30, 1889 and 1890.

Districts.	1889.		1890.	
	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>	
Aroostook, Me.	551,700	\$1,716	599,800	\$1,796
Baltimore, Md.	45,895,135	70,467	33,254,515	63,371
Bangor, Me.	3,923,232	4,148	3,073,575	2,631
Bath, Me.			4,112,148	4,289
Boston and Charlestown, Mass.	97,562,445	144,220	78,003,812	120,468
Brazos de Santiago, Tex.	2,667	20	6,750	37
Buffalo Creek, N. Y.	300	2		
Cape Vincent, N. Y.	190	1		
Champlain, N. Y.	81,936	598	26,070	94
Charleston, S. C.	4,446,104	4,479	1,620,453	2,178
Chicago, Ill.	18,291,313	61,884	22,080,301	84,361
Cincinnati, Ohio.	223,776	608	336,000	1,168
Cuyahoga, Ohio.	1,248,800	2,007	875,640	4,725
Detroit, Mich.	389,200	2,642	358,800	2,578
Duluth, Minn.	145,600	949		
Fairfield, Conn.	979,840	1,107	672,707	734
Galveston, Tex.	16,932,789	22,714	4,970,007	8,812
Gloucester, Mass.	41,419,640	39,552	61,517,700	55,196
Huron, Mich.	649,600	3,871	308,000	1,818
Indianapolis, Ind.	2,688,000	7,297	1,680,000	5,426
Kansas City, Mo.	3,438,016	11,521	4,590,014	12,690
Key West, Fla.	89,043	106	107,410	150
Miami, Ohio.			56,000	633
Milwaukee, Wis.	884,800	5,037	1,012,617	6,365
Mobile, Ala.	4,959,360	8,093		
New Haven, Conn.	2,757,701	2,701	2,065,507	1,892
New Orleans, La.	35,878,849	36,091	37,006,746	69,295
Newport News, Va.	5,145,490	10,197	2,278,270	7,081
New York, N. Y.	140,710,084	265,287	109,844,216	219,608
Norfolk and Portsmouth, Va.	28,711,512	43,037	15,308,354	31,126
Omaha, Nebr.	691,332	1,824		
Oregon.	230,400	588	402,040	1,578
Oswegatchie, N. Y.	33,600	300		
Paso del Norte, Tex. and N. Mex.	358,796	2,032	469,365	3,399
Passamaquoddy, Me.	4,837,767	11,838	4,293,705	8,469
Pensacola, Fla.	896,000	681	5,600,000	7,938
Philadelphia, Pa.	45,987,154	63,881	36,748,437	48,788
Portland and Falmouth, Me.	18,160,494	19,793	11,736,366	17,188
Providence, R. I.	9,257,260	8,071	7,448,762	6,915
Puget Sound, Wash.	453,827	1,330	3,354,550	11,287
Richmond, Va.	3,128,389	5,264	3,438,954	9,223
St. Johns, Fla.	348,000	335	471,400	647
St. Louis, Mo.	1,702,610	7,640	650,530	3,325
San Diego, Cal.	5,760	39	1,440	28
San Francisco, Cal.	7,729,004	26,138	17,272,427	65,067
Savannah, Ga.	11,258,273	9,550	9,982,813	12,169
Superior, Mich.	39,200	420		
Tampa, Fla.			27,000	70
Vermont.	24,827	244	7,200	10
Waldoboro, Me.			549,690	568
Willamette, Oregon.	4,699,950	14,741	8,966,959	33,059
Wilmington, N. C.	10,933,943	13,679	6,603,007	10,697
All other customs districts, etc.	3,593,439	4,331	1,649,807	2,078
Total.	582,377,147	943,071	506,039,864	950,925

Exports of salt, by countries, during the fiscal years 1889 and 1890.

Countries to which exported.	1889.		1890.	
	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>	
Argentine Republic.....			24,400	\$190
Brazil.....	6,200	\$39		
Central American States:				
Costa Rica.....	238,412	1,687	188,115	1,433
Guatemala.....	5,960	64	3,500	47
Honduras.....	20,879	263	25,568	318
Nicaragua.....	159,750	1,726	175,019	1,812
Chile.....	1,600	16	4,000	55
China.....	3,000	15	3,000	18
Colombia.....			411,880	4,392
Danish West Indies.....			1,540	16
France.....	4,000	40		
French Guiana.....			4,200	32
Miquelon Langley, and St. Pierre Islands.....	500	5	2,480	38
French Possessions.....	89,280	506	107,800	575
Nova Scotia, New Brunswick, and Prince Edward Island.....	12,193	161	3,150	35
Quebec, Ontario, Manitoba, and the Northwest Territory.....	909,990	4,835	65,290	348
British Columbia.....	434,400	2,774	561,275	3,149
Newfoundland and Labrador.....	291,825	634	14,740	131
British West Indies.....	72,224	797	161,737	1,735
British Honduras.....	3,515	37	8,890	80
British possessions in Australasia.....	116,000	580	25,000	150
Hawaiian Islands.....	837,740	3,963	839,500	4,317
Haiti.....	11,400	158	8,113	109
Japan.....	19,800	123	29,500	152
Mexico.....	136,540	1,637	201,325	2,527
Netherlands.....			10,000	125
Dutch West Indies.....			300	3
Azore, Madeira, and Cape Verde Islands.....	3,777	43	2,000	18
Russia, Asiatic.....	1,794,800	7,212	1,314,000	6,539
San Domingo.....	54,730	607	44,450	385
Cuba.....	34,025	209	37,600	273
United States of Colombia.....	530,060	6,055		
Uruguay.....	1,540	20		
All other islands and ports.....	9,700	60	3,200	20
Total.....	5,803,900	34,266	4,281,692	29,073

BROMINE.

Bromine is produced as a by-product of the salt industry. The mother liquor from the salt works in West Virginia, Ohio, and Michigan are treated for this purpose and the bromine saved. The bromides contained in the mother liquor are oxidized by manganese dioxide in West Virginia and Ohio; potassium chlorate is the favorite oxidizing agent in Michigan, because of the large proportion of chloride of calcium in the liquor.

The product of this substance in the last three years is given below.

Product of bromine in the United States from 1888 to 1890.

States.	1888.	1889.	1890.
	<i>Pounds.</i>	<i>Pounds.</i>	<i>Pounds.</i>
Ohio	61,540	165,973	101,813
West Virginia	81,124	90,028	118,184
Michigan	61,609	45,968	59,696
Pennsylvania	100,113	116,922	108,154
Total.....	307,386	418,891	387,847

The total value of the product in 1890 was \$96,962, the price being about 27 cents per pound on the average for that year. In the preceding years a syndicate of producers has kept the price comparatively free from competition at 31 cents per pound.

The use of bromine as a disinfectant is increasing slowly. Of course the bulk of the product goes into the manufacture of potassium and sodium bromides.

BORAX.

BY CHARLES G. YALE.

STABLE CONDITION OF THE INDUSTRY.

The manufacture of borax in this country has for the past three years undergone little variation as regards either production made or net profits realized, the product during this period having amounted to nearly 9,000,000 pounds per annum. California and Nevada continue to be the only sections of the United States in which this salt is manufactured in commercial quantities; nor is it made, except in a small way, anywhere else on the Western continent, though a good deal of the crude material is exported from the west coast of South America, mostly from Chile and Peru. Some small shipments of the borate of lime have also been made from a deposit of that mineral found east of the Andes, in the States of La Plata.

Production.—The annual and the total production of manufactured borax made to date in the States of California and Nevada is exhibited in the following table:

Borax produced in the United States.

Years.	Pounds.	Years.	Pounds.	Years.	Pounds.
Prior to 1873 . . .	1, 750, 000	1879	1, 584, 966	1885	8, 000, 000
1873	2, 000, 000	1880	3, 860, 748	1886	9, 778, 290
1874	4, 000, 000	1881	4, 045, 405	1887	11, 000, 066
1875	5, 433, 658	1882	4, 236, 291	1888	7, 830, 000
1876	5, 180, 810	1883	6, 500, 000	1889	8, 800, 000
1877	3, 727, 280	1884	7, 000, 000	1890	9, 500, 000
1878	2, 802, 800				

Of the quantity of this salt manufactured prior to 1873 nearly the whole was the product of the California and the American borax companies, operating in the localities hereinafter mentioned, three-fourths of this quantity having been made by the California company.

The considerable falling off noted since 1887 is explained by the following statement of facts: During the six months that elapsed between the date of the enactment of the present tariff law, in January, 1883, and the first day of July, when it went into effect, the English dealers in borax, in anticipation of higher prices ruling here, and with a view to discouraging our home producers, sent to this country, while imports were so free from duty, 5,000,000 pounds of boracic acid, the equivalent

of 7,000,000 pounds of the salt. As our own manufacturers kept on making meantime a large product, the price of borax, instead of advancing, as was expected, declined, by reason of large accumulations on the American market, to $4\frac{1}{2}$ cents per pound, being less than cost of production. In this strait our home manufacturers entered into an arrangement whereby this output has, for the past three years, been curtailed to the extent denoted by the figures given for these years respectively. They could easily turn out here a great deal more of this salt, but self-preservation requires that production should be restricted to something like present figures.

DISCOVERY AND FIRST WORKINGS.

Although a brief account of the discovery and earlier workings of the borate fields of California and Nevada has been given in previous reports of this series, it may be in order to recapitulate the history of this industry in these States and bring it to the present time.

The credit of having first discovered a workable deposit of borax on the Pacific coast belongs to the late Dr. John A. Veatch, a skilled mineralogist and indefatigable explorer, who in his day made many other important mineral discoveries, he having also contributed much valuable matter to the mining literature of California. Having detected the presence of boracic acid in certain springs located in the northern part of the State, Dr. Veatch spent much time exploring the adjacent country in the hope of finding a deposit of borax that would prove of commercial value. Proceeding from one spring to another a little boracic acid was found in nearly all, in the most of them hardly more than a trace, but generally enough to keep alive the hope that inspired this tireless devotee of science. After traveling hundreds of miles, much of the distance being made on foot and under circumstances of great discomfort, Dr. Veatch came upon an extensive deposit of the baborate of soda, the material occurring in the form of crystals imbedded in the mud at the bottom of a lagoon situated on the margin of Clear lake, Lake county, California. To this lagoon was afterwards given the name Borax lake. Although this find occurred in 1856, not until 1864 was any attempt made at working this deposit, the California Borax Company having during the latter year commenced the business of recovering these crystals and converting them into a marketable commodity, which process was conducted after the following manner:

Coffer dams, made of boiler iron, each 4 feet square by 6 feet deep, and open at both ends, having been prepared, were suspended over the water from pontoons and suddenly dropped, their weight carrying them down through the softer mud to the more compact clay below. This done, the contents of these coffer dams were raised and thrown into troughs, through which a stream of water being passed, the mud and smaller crystals were washed out and returned to the lake, only the larger crystals being retained. These latter were then dissolved in

hot water and recrystallized in tanks lined with lead, under which treatment they yielded their full weight of first-class borax, less the weight of the small percentage of mud they contained.

The above was, of course, a very wasteful process, as the company at the end of four years came to realize. Their stock of available material, confined to the upper 5 feet of mud, had by this time become depleted to an extent that considerably curtailed production, and even threatened it with entire cessation at no distant day, a dénouement that was finally precipitated by the occurrence of an excessive rainfall, which so filled up the lake that further operations at that point became impracticable.

In this emergency the company transferred their labors to a small pond near by, the water of which holds in solution the salts of soda in the following proportions: Sodium carbonate, 75.4; sodium chloride, 8.3; sodium biborate, 16.3 per cent.

Neither the water here nor the mud beneath contains any crystals. Under these changed conditions a different method of treatment had to be adopted from that before employed; nor did the company succeed in finding a method entirely adapted to these changed conditions, even after much experimentation had been made. What worked right in laboratory practice failed to give satisfaction when tried on a large scale. The plan of concentrating the water by boiling and evaporating the solution in small pans was finally adopted. The borax and the carbonate were then crystallized together, after which the latter was washed away, its greater solubility making this an easy matter. Some 4,000 of these evaporating pans, holding from 2 to 3 gallons each, constituted a part of the plant here in use.

The California Borax Company continued work at this place until 1874, when they were obliged to suspend operations owing to the low price of this salt consequent on the large production made at the newly discovered salines in Nevada. During the period they were at work this company turned out a total of about one and a quarter million pounds of refined borax, for which they received an average of 25 cents per pound. Notwithstanding the high price obtained for their product the investment proved an unfortunate one for the company.

While the manufacture of borax was so struggling to obtain a foothold in California, a company of San Francisco capitalists undertook the manufacture of this salt in Nevada, the site of their operations being a small circular lake situated near Ragtown, Churchill county. This lake, about 2 miles in circumference and very deep, is walled in on every side but the southwest by steep banks, which spring up from the narrow beach to a height of 200 feet or more. The slope of these banks is as smooth and regular as the face of an artificial mound, the upper edge being on a level with the surface of the surrounding country. But for the absence of other confirmatory evidence this lake, so deep and nearly circular, might be supposed to occupy the crater of an

extinct volcano. The water of this lake carries in solution a small percentage of boracic acid and chloride of sodium or common salt. The region about abounds in "alkali flats," shallow depressions, in which the water during the wet season collects to a depth of a few inches, and, evaporating, leaves a slight deposition of the above salts behind. Much of the soil here appears, in fact, to be impregnated with these and other saline substances. In the vicinity of this lake occurs a remarkable deposit of carbonate of soda, fully described in the Fourth Annual Report of the California State Mineralogist. In utilizing the water of this lake the plan was adopted of pumping it up into troughs, through which it was carried out and discharged on an alkali flat near by and there evaporated, the crystallized borax being left behind. After a short trial this enterprise was abandoned, the borax produced being limited in quantity and of low grade, owing to the presence of the baser salts and other impurities, there being in the neighborhood neither fuel nor other facilities for refining the crude material on the spot. In addition to these natural disadvantages there was manifested here, as there had been at Borax lake, a surprising ignorance of the conditions as well as of the methods of procedure requisite to success.

Proceeding to notice in the order of their occurrence these abortive efforts at manufacturing borax on the Pacific Coast, the enterprise inaugurated at Sand Springs, in Nevada, next claims attention. At this locality, situated on an extensive alkali flat, in Churchill county, there was put up by the American Borax Company, in the year 1870, reduction works having a capacity of one ton of the refined salt per day. After operating these works for a period of about three years this company relinquished the business, mainly for the same causes that had militated against their predecessors in the field. About the same time, or a little later, a small plant was put up on a deposit of the borates similar to that at Sand Springs and situated 50 miles to the northwest of that locality. Although near the line of the Central Pacific railroad, insuring the operators at that point cheap transportation, results here did not differ from those previously reached in both California and Nevada.

Before the last-mentioned company had closed its works the discovery of much richer as well as more extensive deposits of borax in both of these States had served so to reduce the price of this commodity that it could no longer be profitably produced by any of the parties previously engaged in its manufacture on the coast.

Concerning the salines so discovered, their subsequent outfit, and active workings, enough has been said in previous volumes of this series to make unnecessary any detailed account of the same here. Every year has seen some improvements made in the industry in the way of more perfect appliances and processes, and through the introduction of which, production has been so cheapened that the manufacturer has,

without any material advance in the price of the salt, been able to realize a living profit where before he had failed to do so.

As the improvements above alluded to are well represented by what has, during the year under review, been accomplished by the San Bernardino Borax Company, an article bearing on the subject is reproduced, with slight omissions, from the last Annual Report of the California State Mineralogist. As this article, prepared by Dr. Henry De Groot, describes also the general features of the saline belonging to that company, the character of the crude material there obtained, and the manner of its occurrence, together with the mechanisms and methods employed in its reduction, it may, in so far as the above particulars are concerned, be accepted as describing with much accuracy this entire class of properties.

THE SEARLES BORAX MARSH.

This marsh is situated in the northwestern corner of San Bernardino county, California, occupying a portion of township 25 south, range 43 east, Mount Diablo meridian.

The site is distant from San Francisco southeast 500 miles; from San Bernardino, the shire town of the county, due north 175 miles; and from Mojave, nearest station on the Southern Pacific railroad, northeast 72 miles; these distances being measured by the usually traveled routes.

Physical peculiarities and probable origin.—Locally considered, Searles' marsh lies near the center of an extensive mountain-girdled plain, to which the phrases "alkali flat," "dry lake," "salt bed," and "borax marsh" have variously been applied. The contents and physical features of this basin-shaped depression well justify the several names that have been so applied to it. It is, in fact, a dry lake, the bed of which has been filled up in part with the several substances named. Its contents do, in reality, consist of mud, alkali, salt, and borax, largely supplemented with volcanic sand. This depression, which has an elevation of 1,700 feet above sea level, and an irregular oval shape, is about 10 miles long and 5 miles wide, its longitudinal axis striking due north and south. It is surrounded on every side but the south by high mountains, the Slate range bounding it on the east and north, and the Argus range on the west, the view to the south being shut out by low mountains, conical peaks, and broken hills which break away to the southeast. Conspicuous in that direction stands a series of splintered buttes, so slender and pointed that the name "Needles" has been applied to them.

No doubt but this basin was once the bed of a deep and wide-extended lake, the remains of a former inland sea. The shore line of this lake is distinctly visible along the lower slopes of the surrounding mountains at an elevation of 600 feet above the surface of the marsh. Farther up, one above the other, faint marks of former water lines can be seen showing the different levels at which the surface of the ancient

lake has stood. In the course of time this lake was extinguished, having been filled up with the wash from the adjacent mountains, originally much taller than they are to-day.

What may have originally been the depth of this lake has not yet been ascertained, borings put down 300 feet having failed to reach bed rock.

Borings commenced in 1887 disclosed the following underlying formations, the successive strata passed through having been observed and noted by Superintendent Searles, who had the work in charge

1. Two feet of salt and thenardite.
2. Four feet of clay and volcanic sand, containing a few crystals and bunches of hanksite.
3. Eight feet of volcanic sand and black, tenacious clay, with bunches of trona of black, shining luster, from inclosed mud.
4. Eight-foot stratum, consisting of volcanic sand containing glauberite, thenardite, and a few flat hexagonal crystals of hanksite.
5. Twenty-eight feet of solid trona of uniform thickness—other borings showing that this valuable mineral extends over a large area.
6. Twenty-foot stratum of black, slushy, soft mud, smelling strongly of hydrosulphuric acid, in which there are layers of glauberite, soda, and hanksite. The water has a density of 30 degrees Baumé.
7. Two hundred and thirty feet (as far as explored) of brown clay, mixed with volcanic sand and permeated with hydrosulphuric acid.

Overlying No. 5 a thin stratum of a very hard material was encountered. Being difficult to penetrate and its character not recognized, this was simply called "hard stuff," its more exact nature being left for future determination.

Whatever the agencies that in the first place scooped out the bed of this lake, or however it came afterwards to be drained of its water, the process by which it has since been filled up, as well as the sources of its wonderful enrichment, is well understood. The rocks of the surrounding region being mainly of volcanic origin, abound with the various salts found in this marsh. As these rocks have undergone decomposition these salts, set free, have mingled with and become constituent parts of the soil. The rains falling on this soil have carried it, together with the salts it contained, down and deposited it in this central basin, filling it up to the extent now seen. That this filling-up process must have been slow in a climate marked by such extreme aridity, admits of no question. The wash from the watershed of this basin is not large, and would have been extremely limited but for the cloud-bursts that occasionally occur on the surrounding mountains, and which in former times were probably heavier and of more frequent occurrence than at present. Only in excessive wet winters do more than a few small streams flow down the ravines eroded in the rim of this basin, and these dry up almost as soon as the rain ceases to fall. But the filling up of this ancient lake has not been due solely to the soil washed in by the surface

water. It has been greatly hastened by the large quantities of dust and sand swept in by the strong winds that blow here periodically from the west. While the solfataric action may have had something to do with the production of these salts, it seems probable that their presence here is mainly, if not wholly, due to the source above indicated.

As is the case with all salines of like character, this has no outlet. The water that comes into it can escape only by evaporation, which process goes on here very rapidly for two-thirds of the year. While most of the water contained in this basin is subterranean, a little during very wet winters accumulates and stands for a short time on portions of the surface. In no place, however, does it reach a depth of more than a foot or two, hardly anywhere more than 3 or 4 inches. Within the limits of the actively-producing portion of the marsh, which covers an oblong area of about 1,700 acres, the water stands on a tract of some 300 acres for a longer period than it does elsewhere, but even here it nowhere reaches a depth of more than a foot. Between this 300-acre tract and the main flat lying a little lower, there interposes a slight ridge which prevents the surface water from escaping to the lower ground. This entire productive section is, in fact, slightly depressed below the general level of the flat, to which circumstance, no doubt, its greater fertility is due. As certain degrees of moisture are necessary to maintain the process of capillary attraction, this goes on at this lower point, to which the water gravitates, with greater steadiness and activity than elsewhere.

After a slight winter rainfall, causing the water to subside to an unusually low level, the restoration of these surface deposits goes on slowly and may even be wholly arrested.

Mineral substances found.—This water, which is of a dark brown color, and strongly impregnated with alkali, has a density of 28° Baumé. The salts obtained from it by crystallization contain carbonate and chloride and baborate of sodium, with a large percentage of organic matter. Summarized, the following minerals have been found associated with the borax occurring in the Searles marsh: Anhydrite, calcite, celestite, cerargyrite, colemanite, dolomite, embolite, gay-lussite, glauberite, gold, gypsum, halite, hanksite, natrone, soda, niter, sulphur, thenardite, tincal, and trona, the most of these occurring, of course, in only minute quantities. There is, however, reason to believe that hanksite will yet be found abundantly, both here and in the other salines of this region.

The submerged tract above described is called the "crystal bed," the mud below the water being full of large crystals, which occur in nests at irregular intervals to a depth of 3 or 4 feet; many of these crystals, which consist of carbonate of soda and common salt, with a considerable percentage of borate, are of large size, some of them measuring 7 inches in length. The water 15 feet below this stratum of mud contains, according to Mr. C. N. Hake, who made, not long since, a careful examination of these deposits, carbonate of soda, borax, and salts of ammo-

nia. The ground in the immediate vicinity, a dry hard crust about one foot thick, contains, on the same authority:

Composition of ground near Searles' marsh, California.

	Per cent.
Sand	50
Sulphate of soda	16
Common salt	12
Carbonate of soda	10
Borax	12

The borax here occurs in the form of the borate of soda only, no ulexite (borate of lime) having yet been found.

Gathering.—It is the overlying crust mentioned that constitutes the raw material from which the refined borax is made. The method of collecting it is as follows: When this crust, through the process of efflorescence, ever active here, has gained a thickness of about 1 inch, it is broken loose and scraped into windrows far enough apart to admit the passage of carts between them, and into which it is shoveled and carried to the factory located on the northwest margin of the flat 1 to 2 miles away. As soon as removed, this incrustation begins again to form, the water charged with the saline particles brought to the surface by capillary attraction evaporating and leaving these particles behind. This process having been suffered to go on for three or four years, a crust thick enough for removal is again formed; the supposition being that this incrustation, if removed, will, in like manner, go on reproducing itself indefinitely. In order to determine the proportionate growths of the various salts contained in this crust while undergoing this recuperative process, Mr. Hake took samples representing, respectively, six months, two, three, and four years' growth. From the ground from which these samples were taken, the crust has been removed several times during the preceding twelve years.

The analyses of these samples gave the following results:

Composition of old and new crusts at Searles' borax marsh, California.

	Six months' growth.	Two years' growth.	Three years' growth.	Four years' growth.
	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>	<i>Per cent.</i>
Sand	58.0	55.4	52.4	53.3
Carbonate of soda	5.2	5.0	8.1	8.0
Sulphate of soda	11.7	6.7	16.6	16.0
Chloride of soda	10.9	20.0	11.1	11.8
Borax	14.2	12.9	11.8	10.9
Totals	100.0	100.0	100.0	100.0

The above determination shows that the first six months' growth is richest in borax, and that the proportion of carbonate of soda to borax increases regularly. The presence of so much sand as is here indicated

is caused by the high winds that blow at intervals, bringing in great quantities of that material from the mountains to the west. This sand, it is supposed, facilitates the formation of the surface crust by keeping the ground in a porous condition.

Process of manufacture.—The crude stuff having been collected on the marsh and hauled to the factory in the manner stated, is thrown on the dumping ground close by, a stock of several thousand tons being kept constantly on hand. As required, this material is carted into the works and thrown into dissolving tanks filled with a boiling saline solution, and there kept until it is completely dissolved, free ammonia being meantime copiously given off. The heat supplied to the tanks consists of steam passed through a coil placed near their bottoms, this coil being pierced with many minute holes for the escape of the steam. The various salts being dissolved, there is left at the bottom of the tank an insoluble residue, chiefly mud and sand. The hot solution having been left about eight hours to settle and clarify, is run off into long wooden crystallizing tanks and allowed to cool, which requires from five to nine days, according to the temperature of the weather. The product of the first crystallization is a somewhat impure article of borax, slightly discolored by organic matter, and which is either sold as “concentrates” or redissolved in boiling mother liquid, and the resultant solution allowed to cool to 120° F. From the solution thus obtained borax of a superior quality is made. By a system of careful experimentation kept up for a year Superintendent Searles has succeeded in extracting the borax from the crude material treated up to a high percentage, very little of the salt being lost.

Reduction works.—While these are as complete perhaps as any extant, additional improvements are contemplated here, not, however, with a view to increasing the output so much as effecting further economy in the manufacture of the salt. Although the present works are capable of turning out over one hundred tons refined borax per month, they are not run to their full capacity, a slightly restricted production having been found expedient. The buildings occupied by the plant consist of a dissolving, a concentrating, a refining, and a boiler and engine house, and all those numerous other buildings required about an establishment of this kind.

Fuel and water supply.—The fuel formerly used in these works consisted of greasewood and sagebrush, the only kinds found in the country. No trees grow here. For about three years an acceptable substitute for these shrubs has been found in crude petroleum, which, besides proving far more economical and less troublesome, affords a steadier heat.

The water used here for drinking and for feeding the boilers is obtained from a group of springs $7\frac{1}{2}$ miles distant in the Argus Mountains, whence it is brought in through iron pipes, being delivered at the works under a 1,000-foot head. It is abundant and of excellent quality, being soft and pure. The water required for other purposes is

derived from artesian wells, of which 14, sunk on the border of the marsh to a uniform depth of 55 feet, afford an ample supply. This water, which flows steadily, rising from 5 to 10 feet above the surface, contains about 1 per cent of carbonate of soda, strong traces of borax, and salts of ammonia equal to about 18 grains per gallon. It answers well for dissolving the crude material and for most other uses about the works, in which the consumption is large.

Labor, wages, transportation, etc.—This company employs about 60 men in the several departments of the business, subdivided and paid as follows: One foreman, \$8 per day; 4 mechanics, each \$4 per day; 50 laborers, each \$2 per day; 2 teamsters, \$100 per month; 3 persons in the clerical force \$150 per month, the company boarding all but the latter. The sum paid out on labor account amounts to \$50,000 annually. Owing to favorable climatic conditions operations can be continued here nearly the whole year round. On an average not more than one month in twelve is lost, the cause of stoppage being rains, sandstorms, and repairs. It may here be observed that the wages paid by the other borax companies operating on the Pacific coast do not vary much from the above, except that they are as a general thing somewhat less.

For their transportation service this company requires about 50 animals, most of them being heavy draft mules. For hauling the raw material from the marsh to the factory horses are used. For transporting the manufactured article to Mojave, the shipping and receiving station on the Southern Pacific railroad, and bringing back supplies mules are employed. Twenty of these animals constitute a team, which, being attached to two large wagons coupled together and capable of carrying a total of 15 tons, make the trip to Mojave, 72 miles distant, in eight days. As the country to be traversed is an arid and sandy desert, water having to be carried part of the way, freighting over it is attended with heavy expense, it costing the company more than twice as much to get their products from their plant to Mojave as from that place to Eastern markets.

The Pacific Coast Borax Company.—This company consists of a consolidation, recently effected, of the Pacific Borax, Salt, and Soda Company, the new organization taking in also the several properties known as the Chetco borax mine of Oregon, the Death Valley and the Amargosa borax deposits, the Calico borate mine, and the Alameda refinery. The amount of marketable borax turned out by this company from their four salines now actively worked aggregated in the present year (1890) about 6,000 tons, the most of it being the Calico, the Teel's marsh, and the Columbus marsh deposits, with a small contribution from the Chetco mine. Owing to change of ownership and the many natural disadvantages under which they require to be worked, nothing has for the past three years been done with either the Death Valley or the Amargosa deposit.

The Calico mine.—This deposit, situated in the Calico district, San Bernardino county, California, is remarkable in that it occurs in the form of a vein or ledge, being exploited in the same manner as that class of deposits. Though discovered in 1883, only for the past few years has this mine been actively worked, the plan of operating here being as follows: The crude material, which occurs intermixed with shale, jasper, and carbonate of lime, is broken out, hoisted to the surface, and dumped into cars which carry it to the ore bins near by. Taken from these it is loaded on wagons and hauled to the town of Daggett and there shipped by rail to the company's Alameda refinery, located on the bay of San Francisco, where it undergoes final treatment, about 700 tons of the raw material being handled per month. This material is priccite and carries about 34 per cent. boracic acid. In stoping it out much blasting is required. After being brought to the surface it has to be carefully assorted, being intermixed with so much foreign matter. The deposit is now believed to be extensive, as it measures fully 4 feet between the walls and can be traced by the croppings for a distance of nearly 2 miles. This company employs at the Calico mine 45 men and 45 animals, two 20-mule teams doing the hauling to Daggett. The entire labor force employed by them, the Alameda works included, amounts to about 150 men.

Rhodes marsh.—There were turned out here in the year 1890 about 700 tons of concentrated borax, the product being sacked and sold in that shape or sent elsewhere for refining. This company employs about 15 or 20 men, the most of them Indians, these latter being found very serviceable hands. The company manufactures a considerable quantity of common salt, which is used in the reduction of silver ores at the several mills in the neighborhood.

The Preservaline Company, an eastern incorporation, which has been in existence about four years, has built a refinery on the Columbus marsh at a point 12 miles east from the town of Columbus. The output, amounting to some 250 tons per year, is handled by the New York Chemical Importing Company, which converts the most of it into a "preservaline" for keeping meats and other food products, the efficacy of this article being enhanced by the addition of certain other antiseptics. This company, which employs about 20 men, undertook the manufacture of boracic acid, but finding the business unprofitable abandoned it after having expended a considerable sum in the experiment. This acid could be made on the Pacific coast were the present tariff on the imported article slightly increased.

The Chetco deposit.—This is located in Curry county, Oregon, the crude material, priccite, occurring in the shape of bowlders weighing from a few ounces up to several hundred pounds. These being buried irregularly in the earth, with little or no surface indications, the exploitation of the deposit becomes troublesome and costly, disadvan-

tages that are measurably offset by the great richness of the material and the facilities that exist at the spot for shipping it by sea. Professor Silliman, who carefully examined this mineral, obtained the following mean of three analyses:

Analysis of priceite from Cheteo, Oregon.

	Per cent.
Boracic acid.....	49.00
Lime.....	31.83
Water.....	18.29
Alumina, salt, and oxide of iron.....	.96
Total.....	100.08

The absence of soda distinguishes this mineral from ulexite and cryptomorphite, making it a new species, named after Prof. Thomas Price, of San Francisco. Several hundred tons of this material have lately been gathered and sent to the Alameda refinery, where it was treated with excellent results. A hundred tons of it has also been reduced elsewhere to pure boracic acid. Notwithstanding the difficulty of working it, this deposit is likely to prove valuable. Eight men are kept steadily employed in the work of hunting after and getting it out. When extracted it is shipped by sea to the Alameda works and there reduced.

The Saline Valley deposit.—A discovery of comparatively recent date is located to the east of the White mountains, Inyo county, California, being distant easterly 60 miles from Alvord, a shipping station on the Carson and Colorado railroad. The marsh in which the crude material, the borate of soda, occurs covers some 20,000 acres, though the more fertile portion, so far as known, is confined to less than one-tenth that area. Over much of this the borate of soda incrustation varies from 3 to 6 inches in thickness. The owners of this more fertile section, Messrs. Conn & Trudo, have erected here a plant after the usual style, having a capacity of 40 tons concentrated per month. A working force of thirty men is employed here. Water for these works is brought through iron pipes from the mountains to the west, a distance of 1½ miles. Mesquite trees, which make an excellent fuel, are abundant in the neighborhood. An average of eight assays of this crude material, made by Mr. John Fleming, gave 66.83 per cent. boracic acid. During 1890 Messrs. Conn & Trudo turned out 400 tons of concentrated borax, with nearly as much the preceding year.

While the borax industry on the Pacific coast is in a fairly prosperous condition, this would be changed should there occur any largely increased production, as lower prices would inevitably follow, thereby extinguishing the narrow profit margin that at present exists.

In this country the "spot" price of borax is understood to mean price delivered on cars at shipment points on either of the transconti-

mental railroads. During the past year this price has been $6\frac{1}{2}$ cents per pound for the concentrated and 7 cents for the refined article, this being for not less than car load lots. Eastern prices exceed the above by 1 to $1\frac{1}{2}$ cents per pound. Latterly the most of the salt has been shipped by rail directly east from points of production, only such amount going to San Francisco as is intended for shipment by sea, plus consumption on the Pacific coast, which latter is less than 100 tons.

GRAPHITE.

The production of graphite in 1889 amounted to 7,003 short tons of crude mineral. The value of the product in its first selling condition was \$72,662. In 1890 the product consisted of 1,000 tons from Michigan worth at the mines, \$12,000; 500 tons from Pennsylvania and New Jersey, marketed in pulverized form for \$20,500, and 600,000 pounds (estimated) of refined from the Ticonderoga, New York, mines worth \$45,000. The qualities of graphite differ widely. The uses and prices depend upon the quality. The inferior qualities are used in the manufacture of paints, foundry facings, crucibles, and lubricants. There is no uniformity in the value per ton. The production of the finer grade used for lead pencils is limited to the Ticonderoga mines.

Graphite imported into the United States from 1867 to 1890.

Years ended—	Unmanufactured.		Manufactured.	Total.
	Quantity.	Value.		
	<i>Cwt.</i>			
June 30, 1867.....	27, 113	\$54, 131	\$54, 131
1868.....	68, 620	149, 083	149, 083
1869.....	74, 846	351, 004	351, 004
1870.....	80, 795	269, 291	\$833	270, 124
1871.....	51, 628	136, 200	3, 754	139, 954
1872.....	96, 381	329, 030	329, 030
1873.....	157, 539	548, 613	548, 613
1874.....	111, 992	382, 591	382, 591
1875.....	46, 492	122, 050	122, 050
1876.....	50, 589	150, 709	17, 605	168, 314
1877.....	75, 361	204, 630	18, 091	222, 721
1878.....	60, 244	154, 757	16, 909	171, 666
1879.....	65, 662	164, 013	24, 637	188, 650
1880.....	109, 908	278, 022	22, 941	300, 963
1881.....	150, 927	381, 966	31, 674	413, 640
1882.....	150, 421	363, 835	25, 536	389, 371
1883.....	154, 893	361, 949	21, 721	383, 670
1884.....	144, 086	286, 393	1, 863	288, 256
1885.....	110, 462	207, 228	207, 228
1886.....	83, 308	164, 111	164, 111
1887.....	168, 841	331, 621	331, 621
Dec. 31, 1888.....	184, 013	353, 990	353, 990
1889.....	177, 381	378, 057	378, 057
1890.....	255, 955	594, 746	594, 746

MINERAL PAINTS.

Ocher.—The total amount of ocher produced in 1889 was 15,158 short tons, valued at \$177,472. In 1890 the product was 17,555 short tons, valued at \$237,523. The domestic production of ochers, umbers, siennas, and metallic paints has shown a decided increase in the past few years. In "Mineral Resources of the United States, 1883-'84," the annual production of ocher was given at 7,000 tons, valued at \$84,000. No reliable information regarding umber, sienna, and iron ore ground for paint was obtainable at that time. During the last two or three years operators have shown a greater amount of interest in the effort to publish statistics, and in most instances give valuable assistance in the prosecution of the work. The statistics for 1890 are made up from direct returns from all known producers. The values are not obtained from current market reports, but represent the total amount received by producers for their output. The results of the present investigation show that the annual production of American ocher has increased 10,555 short tons, or 150.8 per cent., since 1884. The value of the product in the same time has increased from \$84,000 to \$237,523, or 182.8 per cent. From the following table the annual increase of this now important industry since 1884 can be noted:

Annual production of ocher since 1884.

Years.	Short tons.	Value.	Years.	Short tons.	Value.
1884.....	7,000	\$84,000	1888.....	10,000	\$120,000
1885.....	8,950	43,575	1889.....	15,158	177,472
1886.....	6,300	91,830	1890.....	17,555	237,523
1887.....	8,000	75,000			

Ocher is produced in a number of localities in the United States. Previous to 1889 no statistics of the production by States have been published. In the following table the figures for that year are obtained from the report of the Eleventh Census. Those for 1890 are compiled from individual returns made to the Survey.

Production of ocher in 1889 and 1890, by States.

States.	1889.		1890.	
	Short tons.	Value.	Short tons.	Value.
Alabama.....	336	\$3,500	350	\$4,100
Colorado.....	50	150	1,000	15,000
Georgia.....	2,612	29,720	800	12,800
Maryland.....	616	12,000	7,000	84,000
Massachusetts.....	80	750	300	2,700
Missouri.....			2,200	30,000
New York.....			365	4,493
Pennsylvania.....	7,922	103,797	4,173	61,458
Vermont.....	1,884	7,800		
Virginia.....	1,658	18,755	1,307	22,972
Wisconsin.....	100	1,000		
Total.....	15,158	177,472	17,555	237,523

Exports and imports.—The first shipment of American ocher to Europe is reported to have been made in December, 1890, from the mines of the Cartersville Ocher Company, at Cartersville, Georgia, a consignment of 50 tons to England. The imports since 1867 are shown in the following tables:

Ocher imported from 1867 to 1883.

Fiscal years ending June 30—	All ground in oil.		Indian red and Spanish brown.		Mineral, French and Paris green.		Other, dry, not otherwise specified.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>	
1867.....	11, 373	\$385		\$35, 374		\$2, 083	1, 430, 118	\$9, 923
1868.....	6, 949	333		11, 165		500	3, 670, 093	32, 102
1869.....	65, 344	2, 496	2, 582, 335	31, 624	8, 369	2, 495	5, 379, 478	39, 546
1870.....	149, 240	6, 042	3, 377, 944	41, 607	9, 618	3, 444	3, 935, 978	32, 593
1871.....	121, 080	4, 465	2, 286, 930	40, 663	33, 488	11, 038	2, 800, 148	24, 767
1872.....	277, 617	9, 225	2, 810, 282	38, 763	41, 422	10, 341	5, 645, 343	56, 680
1873.....	94, 245	3, 850	135, 360	2, 506	34, 382	8, 078	3, 940, 765	51, 318
1874.....	98, 176	4, 623	203, 389	3, 772	102, 876	18, 153	3, 212, 988	35, 365
1875.....	280, 517	12, 352	646, 009	9, 714	64, 910	13, 506	3, 282, 415	37, 929
1876.....	63, 916	3, 365	1, 524, 989	19, 555	21, 222	5, 385	3, 962, 646	47, 405
1877.....	41, 718	2, 269	2, 179, 631	24, 218	27, 687	6, 724	3, 427, 208	32, 924
1878.....	25, 674	1, 591	2, 314, 028	23, 677	67, 655	14, 376	3, 910, 947	33, 260
1879.....	17, 649	1, 141	2, 873, 550	26, 929	17, 598	3, 114	3, 792, 850	42, 563
1880.....	91, 293	4, 233	3, 655, 920	32, 726	16, 154	3, 269	4, 602, 546	52, 120
1881.....	90, 431	4, 676	3, 201, 880	30, 195	75, 465	14, 648	3, 414, 704	46, 069
1882.....	159, 281	7, 915	3, 789, 586	34, 136	18, 293	2, 821	5, 530, 204	68, 106
1883 (a).....	137, 978	6, 143	1, 549, 968	13, 788	6, 972	885	7, 022, 615	90, 593

a Since 1883 classified as "dry" and "ground in oil."

Imports of ocher of all kinds from 1884 to 1890.

Years ended—	Dry.		Ground in oil.		Total.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>	
June 30, 1884.....	6, 164, 359	\$63, 973	108, 966	\$4, 717	6, 273, 325	\$68, 690
1885.....	4, 983, 701	51, 499	79, 666	3, 616	5, 063, 363	55, 115
Dec. 31, 1886.....	4, 939, 183	53, 598	112, 784	6, 574	5, 051, 967	60, 167
1887.....	5, 957, 200	58, 162	54, 104	7, 337	6, 011, 304	65, 499
1888.....	6, 574, 608	64, 123	43, 142	9, 690	6, 617, 750	73, 813
1889.....	5, 540, 267	52, 502	51, 063	9, 072	5, 591, 330	61, 574
1890.....					6, 471, 863	71, 953

Imports of umber from 1867 to 1890.

Years ended—	Quantity.	Value.	Years ended—	Quantity.	Value.
	<i>Pounds.</i>			<i>Pounds.</i>	
June 30, 1867.....	2, 147, 342	\$15, 946	June 30, 1879.....	986, 105	\$6, 959
1868.....	845, 173	2, 750	1880.....	1, 877, 645	17, 271
1869.....	570, 771	6, 159	1881.....	1, 475, 835	11, 126
1870.....	708, 825	6, 313	1882.....	1, 923, 648	20, 494
1871.....	470, 392	7, 064	1883.....	785, 794	8, 419
1872.....	1, 409, 822	18, 203	1884.....	2, 946, 675	20, 654
1873.....	845, 601	8, 414	1885.....	1, 198, 060	8, 504
1874.....	729, 864	6, 200	Dec. 31, 1886.....	1, 262, 930	9, 187
1875.....	513, 811	5, 596	1887.....	2, 385, 281	16, 538
1876.....	681, 199	7, 527	1888.....	1, 423, 806	14, 684
1877.....	1, 101, 422	10, 213	1889.....	1, 555, 070	20, 887
1878.....	1, 038, 880	8, 302	1890.....	1, 556, 823	19, 329

Metallic paint.—The use of metallic paint continues to increase. The total product in 1889 was 21,026 short tons, valued at \$286,294. In 1890 the product was 24,177 tons, valued at \$340,369. The returns for

1887 showed a product of 12,000 tons worth \$235,000, and those for 1888 a product of 14,000 valued at \$280,000. From the above it will be seen that while the product has increased over 100 per cent. since 1887 the value has increased only 45 per cent. Part of this comparative decrease in value arises from the estimates for previous years, being based upon the average market prices as quoted through technical periodicals, while the values for 1889 and 1890 represent the total amount actually received by the operators for their product. The following table shows the production for 1889 and 1890 by States:

Production of metallic paint in 1889 and 1890, by States.

States.	1889.		1890.	
	Product.	Value.	Product.	Value.
Alabama.....	<i>Short tons.</i> 3,000	\$30,000	<i>Short tons.</i>	
California.....			40	\$480
Colorado.....	90	2,500	1,300	22,100
New Jersey.....			10	130
New York.....	3,658	63,698	5,224	72,952
Ohio.....	540	11,123	637	16,341
Pennsylvania.....	8,849	128,036	8,955	145,243
Tennessee.....	3,057	24,237	5,386	46,088
Vermont.....			500	6,000
Wisconsin.....	1,832	26,700	2,125	31,035
Total.....	21,026	286,294	24,177	340,369

Venetian and Indian reds.—In addition to what are known as “metallic” red and brown paints, there were produced in the United States in 1890, 4,000 short tons of Venetian and Indian “reds,” valued at \$84,100. Mr. S. P. Wetherill, president of the S. P. Wetherill Company of Philadelphia, one of the two concerns engaged in the manufacture of these paints, states that the manufacture of Venetian red in this country began about 1878 (*a*), and from its beginning the growth of the demand has been gradual, as each barrel had to displace one of English manufacture, and the prejudice in favor of the latter was very strong.

The English reds with which the American product competes are made from the same material (sulphate of iron), but by a different process of manufacture. The American market was formerly entirely dependent upon English manufactures for their supply of what is known in the trade as “English Venetian red;” that is, red of high color which can only be made practically from sulphate of iron. Mr. Wetherill adds that the cost of importing English red before the American works started was 3 cents per pound. About one-third of the Venetian red now used in this country is of domestic make and the price has been reduced about 50 per cent. in the contest for trade. The cost of the crude material is quite as cheap in this country as abroad, and the domestic production is increasing every year, with the prospect of eventually excluding the foreign article.

a No statistics of previous production have been published.

White lead.—The product of white lead in 1890 was 155,272,115 pounds (or 77,636 short tons), valued at \$9,332,967, against 84,000 tons in 1888. The product for 1889 has not been determined in this investigation, though it is probable that the Census Office (division of manufactures) will publish the figures for that year. This subject was not considered as coming within the scope of the mining investigation of the Census Office, the limit in that division being reached with the production of pig lead. It is tolerably certain that the product of white lead in 1889 was somewhat less than that of 1888, and more than that of 1890. In 1889 the Corroders' Association or "Trust" was succeeded by an incorporated company organized by the stockholders of the companies and members of the firms formerly in the trust. All but eight of the former independent operators are now incorporated in the National Lead Company, the various plants being operated as branches of one corporation, with one central office and board of directors.

Red lead, litharge, and orange mineral.—The total product of red lead in 1889 was 11,821,084 pounds, or 5,911 tons, valued at \$726,844. Of litharge there were 10,230,090 pounds, or 5,115 tons, worth \$665,631. The amount of orange mineral produced was 730,000 pounds, or 365 tons, worth \$48,000. No statistics of these three subjects have been published since 1887, when the combined product was estimated at 7,000 tons, though the amounts actually reported by producers for that year were: red lead, 2,634 short tons; litharge, 1,492 short tons, and orange mineral, 245. The returns, however, were incomplete.

Red lead, white lead, and litharge imported from 1867 to 1890.

Year ended—	Red lead.		White lead.		Litharge.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>		<i>Pounds.</i>	
June 30, 1867.....	926, 843	\$53, 087	6, 636, 508	\$430, 805	230, 382	\$8, 941
1868.....	1, 291, 144	76, 773	7, 533, 225	455, 698	250, 615	12, 225
1869.....	898, 686	46, 481	8, 948, 642	515, 733	187, 333	7, 767
1870.....	1, 042, 813	54, 626	6, 228, 285	365, 706	97, 398	4, 442
1871.....	1, 295, 616	78, 410	8, 337, 842	483, 392	70, 889	3, 870
1872.....	1, 513, 794	85, 644	7, 153, 978	431, 477	66, 544	3, 396
1873.....	1, 583, 089	99, 891	6, 331, 373	408, 986	40, 799	2, 379
1874.....	756, 644	56, 305	4, 771, 509	323, 926	25, 687	1, 440
1875.....	1, 048, 713	73, 131	4, 354, 131	295, 642	15, 767	950
1876.....	749, 918	54, 884	2, 546, 766	175, 776	47, 054	2, 562
1877.....	387, 260	28, 747	2, 644, 184	174, 844	40, 331	2, 347
1878.....	170, 608	9, 364	1, 759, 608	113, 638	28, 190	1, 490
1879.....	143, 237	7, 237	1, 274, 196	76, 061	38, 495	1, 667
1880.....	217, 033	10, 397	1, 906, 931	107, 104	27, 389	1, 222
1881.....	212, 423	10, 009	1, 068, 030	60, 132	63, 058	2, 568
1882.....	288, 946	12, 207	1, 161, 889	64, 493	54, 592	2, 191
1883.....	249, 145	10, 503	1, 044, 478	58, 588	34, 850	1, 312
1884.....	265, 693	10, 589	902, 281	67, 918	54, 183	1, 797
1885.....	216, 449	7, 641	705, 535	40, 437	35, 283	1, 091
Dec. 31, 1886.....	597, 247	23, 038	785, 554	57, 340	51, 409	1, 831
1887.....	371, 299	16, 056	804, 320	58, 602	35, 908	1, 302
1888.....	529, 665	23, 684	627, 900	49, 903	62, 211	2, 248
1889.....	522, 026	24, 400	661, 694	56, 875	41, 230	1, 412
1890.....	450, 402	20, 718	742, 196	57, 659	48, 283	2, 146

Whiting and Paris white.—These substances and terra alba are still only articles of import, as per the following tables:

Imports of whiting and Paris white from 1867 to 1890.

Years ended—	Whiting and Paris white, dry.		Years ended—	Whiting and Paris white, dry.	
	Quantity.	Value.		Quantity.	Value.
	<i>Pounds.</i>			<i>Pounds.</i>	
June 30, 1867.....	8, 168, 123	\$40, 879	June 30, 1879.....	1, 365, 867	\$5, 976
1868.....	5, 530, 042	19, 390	1880.....	1, 803, 577	7, 503
1869.....	3, 438, 396	17, 289	1881.....	1, 974, 913	7, 806
1870.....	5, 650, 728	27, 293	1882.....	1, 722, 711	6, 675
1871.....	5, 219, 396	24, 710	1883.....	2, 216, 018	8, 396
1872.....	6, 392, 717	31, 464	1884.....	3, 910, 829	15, 189
1873.....	6, 197, 017	32, 622	1885.....	1, 401, 783	6, 157
1874.....	3, 749, 122	24, 734	Dec. 31, 1886.....	770, 248	3, 547
1875.....	4, 170, 569	22, 491	1887.....	907, 281	2, 999
1876.....	2, 605, 332	13, 270	1888.....	407, 065	1, 679
1877.....	2, 390, 333	11, 269	1889.....	1, 142, 198	3, 768
1878.....	1, 871, 374	7, 903	1890.....	1, 636, 490	6, 387

Imports of terra alba from 1869 to 1890.

Years ended—	Not aluminous.		Aluminous.	
	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>	
June 30, 1869.....		\$7, 002. 00		
1870.....		7, 911. 00		
1871.....		133, 028. 00		
1872.....		6, 444. 00		
1873.....		2, 235. 00		\$44, 994. 00
1874.....		1, 029. 00		56, 821. 00
1875.....				45, 726. 00
1876.....		27, 897. 00		20, 376. 00
1877.....		45, 171. 00		344. 75
1878.....		33, 509. 00		683. 46
1879.....		33, 250. 00		7, 081. 30
1880.....		34, 718. 00		14, 737. 08
1881.....		30, 186. 00		9, 796. 56
1882.....	283, 946	1, 572. 00	12, 008, 101	30, 522. 37
1883.....	149, 782	800. 00	10, 592, 552	19, 533. 00
1884.....			10, 066, 496	25, 187. 89
1885.....			20, 510, 540	41, 378. 21
Dec. 31, 1886.....			15, 988, 807	33, 223. 00
1887.....			10, 824, 749	29, 809. 00
1888.....			20, 899, 516	40, 761. 00
1889.....			23, 945, 674	00, 292. 00
1890.....			27, 503, 730	46, 137. 00

BARYTES.

The amount of barytes produced in 1889 was 21,460 short tons, valued at \$106,313. The producing States were: Illinois, 200 tons; Missouri, 7,558 tons; North Carolina, 3,000 tons; and Virginia, 10,702 tons.

The product in 1890 was 21,911 tons. Of this amount Missouri produced 9,883 tons; North Carolina, 700 tons (*a*), and Virginia, 11,528 tons. There was no product from Illinois in 1890. The total value of the product in 1890 was \$86,505. In computing this the value of the Missouri barytes is taken at the price paid at the mines by the St. Louis manufacturers.

Product of crude barytes from 1882 to 1890.

Years.	Quantity.	Value.
	<i>Short tons.</i>	
1882.....	22,400	\$80,000
1883.....	30,240	108,000
1884.....	28,000	100,000
1885.....	16,800	75,000
1886.....	11,200	50,000
1887.....	16,800	75,000
1888.....	22,400	110,000
1889.....	21,460	106,313
1890.....	21,911	86,505

Imports of barium sulphate from 1867 to 1889.

Years ended—	Manufactured.		Unmanufactured.	
	Quantity.	Value.	Quantity.	Value.
	<i>Pounds.</i>		<i>Pounds.</i>	
June 30, 1867.....	14,968,181	\$141,273		
1868.....	2,755,547	26,739		
1869.....	1,117,335	8,565		
1870.....	1,684,916	12,917		
1871.....	1,385,004	9,769		
1872.....	5,804,098	43,521		
1873.....	6,939,425	53,759		
1874.....	4,788,966	42,235		
1875.....	2,117,854	17,995		
1876.....	2,655,349	25,325		
1877.....	2,368,373	19,273		
1878.....	1,366,857	10,340		
1879.....	453,333	3,496		
1880.....	4,924,423	37,374		
1881.....	1,518,322	11,471		
1882.....	562,300	3,856		
1883.....	411,666	2,489		
Dec. 31, 1884.....	3,884,516	24,671	5,800,816	\$8,044
1885.....	4,095,287	20,606	7,841,715	13,567
1886.....	3,476,691	18,338	6,588,872	8,862
1887.....	4,057,831	19,769	10,190,848	13,205
1888.....	3,821,842	17,135	6,504,975	9,037
1889.....	3,601,506	22,458	13,571,206	7,660

^a The total amount mined in North Carolina was 1,300 tons, but only 700 tons were marketed.

ASBESTOS.

The total amount of asbestos mined in the United States in 1889 and marketed was 30 tons, valued at \$1,800. In 1890 the product increased to 71 tons, valued at \$4,260. The production in each year was limited to California. Asbestos mines are being developed in Wyoming, but so far only a few tons have been mined and none of it has been marketed. A small amount obtained as a by-product in the quarrying of soapstone at Easton, Pennsylvania, is not considered in the product. The California product is manufactured into fire-proof paints and coatings, boiler and steam-pipe coverings, lubricants, and cement. The form of asbestos best adapted for the manufacture of fire-proof textile materials is more properly chrysotile, a variety of serpentine, and which may be distinguished from asbestos by yielding water when heated in a glass tube. The fibers of asbestos are short and brittle, while those of chrysotile are flexible, slightly elastic, and of great tensile strength. The most of the chrysotile used in the United States is produced in Canada, and the rapid progress made in the utilization of the mineral may be seen from the amount imported, as shown in the following table:

Asbestos imported from 1869 to 1890.

Years ended—	Unmanufactured.	Manufactured.	Total.
June 30, 1869		\$310	\$310
1870		7	7
1871		12	12
1872			
1873	\$18		18
1874	152		152
1875	4,706	1,077	5,783
1876	5,485	396	5,881
1877	1,671	1,550	3,221
1878	3,536	372	3,908
1879	3,204	4,624	7,828
1880	9,736		9,736
1881	27,717	69	27,786
1882	15,235	504	15,739
1883	24,369	243	24,612
1884	48,755	1,185	49,940
Dec. 31, 1885	73,026	617	73,643
1886	134,193	932	135,125
1887	140,264	581	140,845
1888	168,584	8,126	176,710
1889	254,239	9,154	263,393
1890	252,557	5,342	257,899

S U L P H U R .

The total product of crude sulphur in the United States in 1889 was 1,150 short tons, worth \$7,850. The producing localities were Nevada and Utah. In 1890, Utah produced 500 tons which was not placed on the market. Nevada produced 260 tons of refined sulphur, worth \$30 per ton, at Winnemucca. This value is much higher than the prices at either the Atlantic or Pacific seaboard, owing to the fact that high freight rates put it out of the way of competition. It supplies a local demand and is principally consumed in the manufacture of sheep dip.

Work on the Louisiana properties is being prosecuted, but the operators do not expect to have any product before 1893.

Sicily continues to furnish the bulk of the world's supply, lack of facilities for mining and shipping Japanese sulphur keeping that source of supply in the background. Practically all the sulphur exported from Japan is shipped to San Francisco, and so does not compete with Sicilian sulphur. During 1890 facilities for reclaiming sulphur from alkali waste by the Chance process were introduced at a number of works in England, Austria, and France. Some of this regained sulphur is said to have been exported to the United States. In order to prevent the cutting of prices among the alkali-makers using this process and consequent unremunerative prices, a combination was formed in the shape of a limited company which shall control the entire sale of the sulphur.

The following table shows the imports of sulphur for the years 1867 to 1890, inclusive:

Sulphur imported and entered for consumption in the United States, 1867 to 1890, inclusive.

Years ended—	Crude.		Flowers of sulphur.		Refined.		Oro. (a)	Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.		
June 30, 1867....	<i>Long tons.</i> 24, 544. 10	\$620, 373	<i>Long tons.</i> 110. 05	\$5, 509	<i>Long tons.</i> 250. 55	\$10, 915	\$636, 797
1868....	18, 150. 55	446, 547	16. 48	948	64. 75	2, 721	450, 216
1869....	23, 589. 69	673, 642	96. 59	4, 576	645. 04	27, 149	710, 367
1870....	27, 379. 60	819, 408	76. 34	3, 927	157. 24	6, 528	\$1, 269	831, 132
1871....	36, 131. 46	1, 212, 448	65. 54	3, 514	92. 26	4, 328	754	1, 221, 044
1872....	25, 379. 55	764, 798	35. 97	1, 822	56. 94	2, 492	769, 112
1873....	45, 533. 27	1, 301, 000	55. 29	2, 924	35. 97	1, 497	1, 305, 421
1874....	40, 989. 55	1, 260, 491	51. 08	2, 694	56. 68	2, 403	1, 265, 588
1875....	39, 683. 10	1, 259, 472	17. 83	891	1, 260, 363
1876....	46, 434. 72	1, 475, 250	41. 07	2, 114	43. 87	1, 927	1, 479, 291
1877....	42, 962. 69	1, 242, 888	116. 34	5, 873	1, 170. 80	36, 962	1, 285, 723
1878....	48, 102. 46	1, 179, 769	158. 71	7, 628	149. 51	5, 995	1, 193, 332
1879....	70, 370. 28	1, 575, 533	137. 60	6, 509	68. 94	2, 392	1, 584, 434
1880....	87, 837. 25	2, 024, 121	123. 70	5, 516	158. 36	5, 292	2, 034, 899
1881....	105, 096. 54	2, 713, 485	97. 66	4, 226	70. 96	2, 555	2, 720, 266
1882....	97, 504. 15	2, 627, 402	158. 91	6, 926	58. 58	2, 196	2, 636, 524
1883....	94, 539. 75	2, 288, 946	79. 13	3, 262	115. 33	4, 487	2, 296, 695
1884....	105, 112. 19	2, 242, 697	178. 00	7, 869	126. 00	4, 765	2, 255, 331
1885....	96, 839. 44	1, 941, 943	120. 56	5, 351	114. 08	4, 060	1, 951, 354
1886....	117, 538. 35	2, 237, 989	212. 61	8, 739	116. 05	3, 877	2, 250, 605
1887....	96, 881. 55	1, 688, 360	278. 56	9, 980	83. 54	2, 383	1, 700, 723
Dec. 31, 1888....	98, 252. 15	1, 581, 583	127. 67	4, 202	27. 02	734	1, 586, 519
1889....	135, 933. 00	2, 068, 208	15. 34	1, 954	10. 00	299	2, 070, 461
1890....	162, 674. 00	2, 762, 953	12. 06	1, 718	103. 00	3, 060	2, 767, 731

^a Latterly classed under head of pyrites.

Statement by countries and by customs districts, showing the imports into the United States of crude sulphur or brimstone each fiscal year from 1876 to 1890.

Countries whence exported and customs districts through which imported.	1876.		1877.		1878.		1879.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
COUNTRIES.								
Dutch West Indies and Guiana	Short tons. 1,515	\$15,427	Short tons. 425	\$14,631	(?)	\$16	Short tons. 2	\$335
England	30	1,211	472	13,231	160	3,961	806	19,287
Scotland	24	910	290	7,789				
Gibraltar								
Quebec, Ontario, Manitoba, etc.					12	264		
Italy	46,941	1,439,839	41,819	1,194,000	47,494	1,161,367	64,420	1,453,138
Japan	456	16,291	437	13,137	256	7,548	224	4,528
Portugal							467	10,410
Total	48,966	1,473,678	43,443	1,242,788	47,922	1,173,156	65,919	1,487,698
DISTRICTS.								
Baltimore, Md.	5,157	\$157,828	3,882	\$105,175	5,455	\$138,202	6,969	\$157,243
Barnstable, Mass.							600	13,780
Boston and Charlestown, Mass.	5,031	154,883	3,931	101,215	5,795	131,945	7,841	173,506
Charleston, S. C.					526	12,267	605	13,812
Delaware, Del.	450	13,500					890	21,907
Huron, Mich.					12	264		
Newark, N. J.			1,071	31,802	462	13,240	443	10,175
New Orleans, La.	172	5,705	150	4,750			100	2,087
New York, N. Y.	24,524	721,092	21,867	654,997	28,240	690,989	36,543	827,193
Philadelphia, Pa.	12,549	385,071	9,216	256,224	6,657	167,222	11,704	263,467
Providence, R. I.	600	18,232	1,739	45,487	519	11,479		
San Francisco, Cal.	483	17,367	862	27,768	256	7,548	224	4,528
Savannah, Ga.			725	15,370				
Total	48,966	1,473,678	43,443	1,242,788	47,922	1,173,156	65,919	1,487,698
COUNTRIES.								
England	Short tons. 1	\$22	Short tons. 1,668	\$43,311	755	\$20,294	Short tons. 13	\$379
Scotland	1,664	36,444	1,668	\$43,311	755	\$20,294	3	88
France	988	23,580			526	13,770	34	858
French West Indies					2	8		
Greece					500	13,927		
Italy	80,301	1,862,712	102,771	2,645,293	92,944	2,504,862	92,861	2,248,870
Japan	282	4,744	691	16,253	2,980	66,356	1,038	23,714
San Domingo					240	7,875		
Spain			308	8,637			500	12,850
Spanish Possessions in Africa and adjacent islands					9	310	87	2,030
Total	83,236	1,927,502	105,438	2,713,494	97,956	2,627,402	94,536	2,288,795
DISTRICTS.								
Baltimore, Md.	13,827	\$313,342	16,477	\$430,917	13,781	\$364,384	11,977	\$286,438
Beaufort, S. C.					540	13,889		
Boston and Charlestown, Mass.	8,207	183,486	8,860	226,801	7,467	194,317	7,756	173,569
Charleston, S. C.	1,061	25,398	3,065	78,741	6,025	161,281	4,051	106,235
Middletown, Conn.					9	310		
New Orleans, La.	280	7,121	100	2,646	220	6,516	428	10,378
New York, N. Y.	46,657	1,063,784	57,608	1,463,082	46,531	1,260,222	45,385	1,110,313
Philadelphia, Pa.	10,679	254,892	17,987	477,547	14,839	408,611	22,772	549,095
Providence, R. I.	1,255	31,155	650	17,507	1,244	33,036	535	13,830
Richmond, Va.					660	17,760		
San Francisco, Cal.	1,270	28,324	691	16,253	6,054	151,234	1,072	24,572
Savannah, Ga.					586	15,842	560	14,365
Total	83,236	1,927,502	105,438	2,713,494	97,956	2,627,402	94,536	2,288,795

Statement by countries and by customs districts, showing the imports into the United States of crude sulphur or brimstone each fiscal year from 1876 to 1890—Continued.

Countries whence exported and customs districts through which imported.	1884(a).		1885.		1886.		1887.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
COUNTRIES.	<i>Short tons.</i>		<i>Short tons.</i>		<i>Short tons.</i>		<i>Short tons.</i>	
Belgium			190	\$4,766	60	\$1,718		
Danish West Indies							861	\$5,250
England			606	15,084	81	2,535	162	4,437
France							290	6,951
Quebec, Ontario, Manitoba, and the Northwest Territory								
Italy			94,370	1,894,858	112,283	2,166,565	89,924	1,588,146
Japan			1,541	25,683	4,972	66,505	6,146	83,576
Spain			134	1,552				
Total	105,143	\$2,242,678	96,841	1,941,943	117,396	2,237,332	97,383	1,688,360
DISTRICTS.								
Baltimore, Md.	15,037	\$303,226	14,505	\$285,006	19,307	\$364,958	12,547	\$225,669
Barnstable, Mass.	650	16,163	480	11,040	1,617	35,385	1,152	22,816
Beaufort, S. C.	600	13,259	610	12,847				
Boston and Charlestown, Mass.	5,294	112,152	5,125	99,712	3,681	69,898	4,850	85,575
Champlain, N. Y.							9	
Charleston, S. C.	6,125	132,570	8,525	169,564	13,350	265,265	12,420	220,598
New Orleans, La.			102	2,282	250	5,102		
New York, N. Y.	52,478	1,135,725	45,537	909,123	58,758	1,115,519	46,711	792,114
Philadelphia, Pa.	18,786	401,568	18,696	381,010	15,568	300,749	15,267	269,216
Providence, R. I.	651	15,517	1,840	37,422	1,265	25,930	600	11,291
San Francisco, Cal.	5,522	112,598	1,421	33,937	3,600	54,517	3,176	50,521
All other customs districts.							660	10,560
Total	105,143	2,242,678	96,841	1,941,943	117,396	2,237,332	97,383	1,688,360

Countries whence exported and customs districts through which imported.	1888.		1889.		1890.	
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.
COUNTRIES.	<i>Short tons.</i>		<i>Short tons.</i>		<i>Short tons.</i>	
Belgium	83	\$1,993	180	\$4,086	182	\$3,995
Danish West Indies					550	9,076
England	310	7,200	305	8,337	4,898	101,100
Scotland					20	487
France						
Quebec, Ontario, etc.						
Italy	92,528	1,499,720	123,260	1,935,368	115,240	1,800,585
Japan	6,332	72,729	6,446	77,853	21,031	221,316
Spain						
Total	99,253	1,581,582	130,191	2,025,644	141,921	2,136,559
DISTRICTS.						
Baltimore, Md.	11,989	\$182,769	15,791	\$234,693	21,198	\$322,018
Barnstable, Mass.						
Beaufort, S. C.	500	9,000	600	9,213		
Boston and Charlestown, Mass.	3,760	62,298	6,446	104,257	7,410	135,044
Champlain, N. Y.						
Charleston, S. C.	12,005	199,048	23,377	364,859	15,752	255,106
New Orleans, La.	200	3,845			200	3,397
New York, N. Y.	50,486	816,286	60,922	959,872	66,359	983,754
Philadelphia, Pa.	10,519	173,699	13,288	202,357	13,919	210,576
Providence, R. I.	1,310	21,012	570	8,581	1,240	19,160
San Francisco, Cal.	6,352	78,732	4,539	57,925	8,223	87,391
Savannah, Ga.			2,345	44,244	5,560	86,826
Wilmington, N. C.	1,532	25,893	1,753	28,443	2,040	32,800
All other customs districts.	600	9,000	560	11,200	20	487
Total	99,253	1,581,582	130,191	2,025,644	141,921	2,136,559

a Sources not reported.

PYRITES.

Total product in 1889, 104,950 short tons; spot value, \$202,119. Total product in 1890, 111,836 short tons; spot value, \$273,745.

In the foregoing statements the pyrites included is only that which is consumed in the production of sulphuric acid. The increasing use of pyrites in the manufacture of acid is attested by the steady increase in the production of the mineral in the past few years. With properly constructed furnaces there can be little doubt that acid sufficiently pure for commercial purposes may be economically prepared from pyrites and compete successfully with that made from sulphur. For medicinal or other purposes when chemically pure acid is essential pyrites will not answer, owing to arsenic or other injurious impurities which are apt to be contained in the ore and which are not eliminated in the process of manufacture. The Chicora Fertilizer Company, of Charleston, South Carolina, is reported as having constructed its new and extensive fertilizer works so as to use pyrites entirely in the manufacture of acid. Other large producers have gone so extensively into the use of pyrites that the importations have increased and will probably increase still more rapidly. In Mineral Resources for 1886 were published comparative statements of the cost of acid produced respectively from sulphur and pyrites.

Production of pyrites in the United States from 1882 to 1890.

Years.	Quantity.	Value.
	<i>Short tons.</i>	
1882.....	13,440	\$72,000
1883.....	28,000	137,500
1884.....	39,200	175,000
1885.....	54,880	220,500
1886.....	61,600	220,000
1887.....	58,240	210,000
1888.....	60,851	167,658
1889.....	104,950	202,119
1890.....	111,836	273,745

Imports of pyrites containing not more than 3½ per cent copper. (a)

Years.	Quantity.	Value.
	<i>Long tons.</i>	
1884.....	16,710	\$50,632
1885.....	6,078	18,577
1886.....	1,605	9,771
1887.....	16,578	49,661

^a Previous to 1884 classed among sulphur ores; subsequent to 1887 classed among other iron ores.

LITHOGRAPHIC STONE.

Up to the close of 1890 no lithographic stone had been produced in the United States except for testing purposes. Active preparations for the development of properties said to contain lithographic stone of good quality were being made during the year in Blanco county, Texas, at Fincastle, Virginia, and near Little Rock, Arkansas. The property in Blanco county, Texas, is controlled by the Texas Lithographic Stone Company, composed of New York men engaged in the lithographing art. The resident superintendent is Mr. John A. Ropes, of Marble Falls, Burnet county, Texas, who reports that the company has placed on the grounds machinery for quarrying the stone, sawing it into slabs, and dressing for immediate use.

No work has been done on the Arkansas deposit except to get out samples for testing. The property is not favorably situated for shipping at present, being 80 miles from the railway, but on the line of two projected roads. Mr. Eben W. Kimball, vice-president of the Bank of Commerce of Little Rock, and who is interested in the property, states that the stone has been subjected to tests by lithographing firms in Philadelphia, St. Louis, and Nashville, and pronounced of excellent quality, comparing very favorably with Bavarian stone. Large quantities are reported available, and work will begin as soon as transportation facilities are obtained.

The deposit near Fincastle, Virginia, was discovered in April, 1890, by Mr. Alfred Beckley, of Fincastle. Mr. Beckley reports that the stone is confined to a ridge about 10 miles long. The stone has been tested by the Bell Lithographing Company, of Washington, District of Columbia, the Maryland Lithographing Company, of Baltimore, Maryland, and Johns & Co., of Cincinnati, Ohio, with evidently satisfactory results. Machinery suitable for quarrying is being placed upon the grounds, and the projectors express themselves as confident of producing a domestic stone which will fill all the requirements made upon it by the lithographic art.

Imports.—The imports of unengraved lithographic stone during late years have been as follows:

Lithographic stone imported into the United States from 1868 to 1890.

Years ended—	Value.	Years ended—	Value.
June 30, 1868.....	\$13, 258	June 30, 1880.....	\$56, 310
1869.....	17, 044	1881.....	77, 894
1870.....	14, 225	1882.....	111, 925
1871.....	21, 311	1883.....	104, 313
1872.....	36, 146	1884.....	128, 035
1873.....	44, 937	1885.....	54, 022
1874.....	36, 902	1886.....	71, 009
1875.....	41, 963	Dec. 31, 1887.....	83, 182
1876.....	47, 101	1888.....	113, 365
1877.....	44, 503	1889.....	78, 077
1878.....	42, 709	1890.....	105, 288
1879.....	37, 746		

MINERAL WATERS.

BY A. C. PEALE.

The production of mineral waters for 1889 from 258 springs was 12,780,471 gallons, valued at \$1,748,458. This was an increase of 3,201,823 gallons, and the increase in the value of the product was \$69,156.

For 1890 the total number of springs was increased to 273, and of this number 220 springs have reported their sales, which amounted to 12,215,187 gallons, valued at \$2,493,948. If for the 53 springs delinquent at the time of making up this report we estimate the product and value at the same as given for 1889, we would have a total production of 15,691,650 gallons, with a valuation of \$2,839,223.

In the tables, however, the delinquent springs have been estimated at a little less than one-half the figures of 1889, giving for the totals the following figures: 13,907,418 gallons, with a value of \$2,600,750. This is an increase from 1889 of 1,126,677 gallons and an increase in value of \$852,292.

The total number of springs in the North Atlantic States reporting sales in 1889 was 60, which was 18 more than reported the previous year, and was only 4 less than the total on the list for that year. In 1890 the number reporting is 43 out of a total of 66. The 60 springs reporting in 1889 reported an increase of 1,249,665 gallons, with an increase in value of \$224,467 over the total for 1888.

In 1890 there is an increase of 936,610 in the number of gallons reported, and if the sales of the 14 nonreporting springs were included it would doubtless be greater. There is, also, an increase of \$703,937 in the total value of the water sold.

In the South Atlantic division the total number of springs increased from 41 in 1888 to 47 for 1889, and for 1890 has increased to 51, six new springs having been added and two taken from the list of 1889. There are 12 springs from which no reports have been received, but the 39 reporting give an increase in value over the sales of the 47 reporting in 1889.

The Northern Central States, from a total of 45 in 1888, increased to 86 in 1889, with an increase in production of over 4,000,000 gallons. In 1890 the list contains a total of 84, of which only 71 report, and the total production reported is slightly less than for the previous year. However, there is a considerable increase in the value of the pro-

duction of the springs reporting as compared with the previous year. Seven springs were added to the list of 1889 and nine taken from it.

In the Southern Central States one more spring for 1889 is added to the number on the list as published in 1888, making the total 33. There is also a slight increase in production, but a falling off in its value. For 1890 three springs were added, bringing the total up to 36. Of these, however, only 30 have reported, and of course the figures are not as much greater than those of the previous year, as would have been the case had all reported.

The Western States and Territories in 1889 show a large increase in the number of spring waters used commercially, as compared with 1888, the number being 32 instead of 16. Notwithstanding this there was a decrease of over 400,000 gallons in the production as reported. One new spring is added to and one taken from the list for 1890, leaving the total 32. Of these 25 have reported, and they report an increase over the figures for 1889.

Production of mineral waters by States and Territories.

States and Territories.	1889.			1890.		
	Number of springs reporting.	Product.	Value of product.	Number of springs reporting.	Product.	Value of product.
		<i>Gallons.</i>			<i>Gallons.</i>	
Alabama.....	5	24,380	\$2,430	3	12,500	\$11,130
Arkansas.....	3	110,200	10,020	5	97,609	22,211
California.....	14	808,625	252,241	12	258,722	89,786
Colorado.....	8	304,600	87,400	7	445,435	92,125
Connecticut.....	3	4,410	2,630	2	4,700	1,950
Georgia.....	3	31,120	9,412	4	66,000	18,450
Illinois.....	10	2,207,216	38,697	7	61,900	12,470
Indiana.....	8	125,162	9,525	8	67,823	7,487
Iowa.....	5	12,780	2,490	5	55,440	8,330
Kansas.....	9	245,633	15,394	7	251,792	15,114
Kentucky.....	5	121,350	14,378	5	86,500	10,025
Maine.....	8	888,600	79,060	7	406,367	67,990
Maryland.....	4	74,160	12,057	2	1,550	162
Massachusetts.....	8	1,011,173	63,622	8	967,465	60,992
Michigan.....	7	333,345	67,987	6	453,000	98,700
Mississippi.....	2	8,870	1,174	2	24,762	5,020
Missouri.....	} 14	289,720	23,270	} 7	45,100	5,260
Nebraska.....						
New Hampshire.....	2	60,000	4,500	3	930,000	340,500
New Mexico.....	4	32,700	10,225	3	17,365	5,357
New York.....	21	1,795,543	239,875	19	2,315,472	631,254
North Carolina.....	11	70,644	19,431	6	86,009	47,457
Ohio.....	11	251,610	26,696	8	82,290	13,246
Oregon.....	2	4,800	1,680	0		
Pennsylvania.....	12	275,700	65,163	10	309,420	64,676
Rhode Island.....	2	47,000	2,975	2	77,000	2,975
South Carolina.....	2	50,520	10,046	0		
Tennessee.....	4	21,500	5,000	2	85,000	17,000
Texas.....	14	213,700	10,354	13	298,200	16,040
Vermont.....	3	16,150	11,975	4	32,650	5,575
Virginia.....	22	397,395	141,476	20	421,466	158,016
Washington.....	3	113,748	14,943	2	23,248	3,943
West Virginia.....	4	21,900	5,360	6	28,000	6,850
Wisconsin.....	20	2,292,910	409,179	20	2,623,068	489,399
Other States (a).....	5	513,907	77,793	5	1,569,734	162,283
Total.....	258	12,780,471	1,748,458	220	12,215,187	2,493,948

a For 1889 the States of Florida, Idaho, Minnesota, New Jersey, and South Dakota are included; for 1890 the States of Florida, Idaho, Minnesota, Nebraska, and South Dakota are included, only one spring reporting in each of these States.

Imports.—Prior to 1884 the Treasury Department did not distinguish natural mineral waters from those that were artificial; since 1883 the

distinction has been made, but the artificial waters have not been classified according to the receptacles in which they have been imported. The importation is shown in the two tables following, with a table of exports appended.

In 1889 there was an increase in the imports of artificial waters, but a decrease in the amount of natural mineral waters brought into the country, although the value was slightly above that of 1888.

In 1890 the importation of natural mineral waters was very greatly increased over that of 1889, while the importation of the artificial waters decreased.

The amount of natural and artificial mineral waters exported is trifling.

Mineral waters imported and entered for consumption in the United States, 1867 to 1883, inclusive.

Fiscal years ending June 30—	In bottles of 1 quart or less.		In bottles in excess of 1 quart.		Not in bottles.		All, not artificial.		Total value.
	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	Quantity.	Value.	
	<i>Bottles.</i>		<i>Quarts.</i>		<i>Gallons.</i>		<i>Gallons.</i>		
1867	370,610	\$24,913	3,792	\$360	\$137	\$25,410
1868	241,702	18,458	22,819	2,052	554	104	20,594
1869	344,691	25,635	9,739	802	1,042	245	26,682
1870	433,212	30,680	18,025	1,743	2,063	508	32,931
1871	470,947	34,604	2,320	174	1,336	141	34,919
1872	892,913	67,951	639	116	68,967
1873	35,508	2,326	355	75	394,423	\$98,151	100,552
1874	7,238	691	95	16	199,035	79,789	80,496
1875	4,174	471	5	2	395,956	101,640	102,113
1876	25,758	1,899	447,646	134,889	136,788
1877	12,965	1,328	22	520,751	167,458	168,808
1878	8,229	815	883,674	350,912	351,727
1879	28,440	2,352	3	4	798,107	282,153	284,509
1880	207,554	19,731	927,759	285,798	305,529
1881	150,326	11,850	55	26	1,225,462	383,616	395,492
1882	152,277	17,010	1,542,905	410,105	427,115
1883	88,497	7,054	1,714,085	441,439	448,493

Imports for years 1884 to 1890.

Years ended—	Artificial mineral waters.		Natural mineral waters.	
	Gallons.	Value.	Gallons.	Value.
June 30, 1884	29,366	\$4,591	1,505,298	\$362,651
1885	7,972	2,157	1,660,072	397,875
Dec. 31, 1886	62,464	16,815	1,618,960	354,242
1887	13,885	4,851	1,915,511	385,906
1888	12,752	4,411	1,716,461	341,695
1889	36,494	8,771	1,558,968	368,661
1890	22,328	7,133	2,322,008	433,281

Exports of natural mineral waters, of domestic production, from the United States.

Fiscal years ending June 30—	Value.	Fiscal years ending June 30—	Value.
1875	\$162	1881	\$1,029
1876	80	1882	421
1879	1,529	1883	(a) 459
1880	1,486		

a None reported since 1883.

Production of natural mineral waters sold from 1883 to 1890.

Geographical division.	Springs reporting.	Gallons sold.	Value.	Geographical division.	Springs reporting.	Gallons sold.	Value.
1883.				1887.			
North Atlantic....	38	2,470,670	\$282,270	North Atlantic....	40	2,571,004	\$213,210
South Atlantic....	27	312,090	64,973	South Atlantic....	34	614,041	147,149
North Central....	37	1,435,809	323,600	North Central....	38	1,480,820	208,217
South Central....	21	1,441,042	139,973	South Central....	29	741,080	87,946
Western.....	6	169,812	52,787	Western.....	12	1,236,324	288,737
	129	5,829,423	863,603		153	6,643,269	945,259
Estimated.....	60	1,700,000	256,000	Estimated.....	62	1,616,340	316,204
Total.....	189	7,529,423	1,119,603	Total.....	215	8,259,609	1,261,463
1884.				1888.			
North Atlantic....	38	3,345,760	328,125	North Atlantic....	42	2,856,799	247,108
South Atlantic....	27	464,718	103,191	South Atlantic....	32	1,689,387	493,489
North Central....	37	2,070,533	420,515	North Central....	38	2,002,373	325,839
South Central....	21	1,526,817	147,112	South Central....	19	426,410	71,215
Western.....	6	307,500	85,200	Western.....	15	1,853,679	421,651
	129	7,715,328	1,084,143		146	8,828,648	1,559,302
Estimated.....	60	2,500,000	375,000	Estimated.....	52	750,000	120,000
Total.....	189	10,215,328	1,459,143	Total.....	198	9,578,648	1,679,302
1885.				1889.			
North Atlantic....	51	2,527,310	192,605	North Atlantic....	60	4,106,464	471,575
South Atlantic....	32	908,692	237,153	South Atlantic....	47	646,239	198,032
North Central....	45	2,925,288	446,211	North Central....	86	6,137,776	604,238
South Central....	31	540,436	74,100	South Central....	33	500,000	43,356
Western.....	10	509,675	86,776	Western.....	32	1,389,992	431,257
	169	7,411,401	1,036,845		258	12,780,471	1,748,458
Estimated.....	55	1,737,000	276,000	Total.....			
Total.....	224	9,148,401	1,312,845	1890.			
1886.				North Atlantic....	55	5,043,074	1,175,512
North Atlantic....	49	2,715,050	177,969	South Atlantic....	39	647,625	245,760
South Atlantic....	38	720,397	123,517	North Central....	71	5,050,413	737,672
North Central....	40	2,048,914	401,861	South Central....	30	604,571	81,426
South Central....	31	822,016	58,222	Western.....	25	869,504	253,578
Western.....	14	781,540	137,796		220	12,215,187	2,493,948
	172	7,087,917	899,365	Estimated.....	53	1,692,231	106,802
Estimated.....	53	1,862,400	384,705	Total.....	273	13,907,418	2,600,750
Total.....	225	8,950,317	1,284,070				

Alabama.—1889.—The number of springs on the list is not changed from that of 1888. The springs reporting are: Bailey Springs, Bailey Springs, Lauderdale county; Bladen Springs, Bladen Springs, Choctaw county; Healing Springs, Healing Springs, Washington county; Jackson White Sulphur Springs, Jackson, Clarke county; Matchless Mineral Water, Greenville, Butler county.

1890.—Only three springs have reported for 1890. They are: Bailey Springs, Bailey Springs, Lauderdale county; Healing Springs, Healing Springs, Washington county; Matchless Mineral Spring, Greenville, Butler county.

Arkansas.—1889.—Only three springs report for 1889, although the list for 1888 contained the names of five. The three reporting are: Arkansas Lithia Springs, Hope, Hempstead county; Fairchild's Pot-

ash Sulphur Springs, Potash Sulphur, Garland county; Mountain Valley Springs, Mountain Valley Springs, Garland county.

1890.—Two more springs are added for 1890, bringing the list up to five, as in 1888. All of these five report. They are: Arkansas Lithia Springs, Hope, Hempstead county; Fairchild's Potash Sulphur Springs, Potash Sulphur, Garland county; Dovepark Spring, Dovepark, Hot Spring county; Eureka Springs, Eureka Springs, Carroll county; Mountain Valley Springs, Mountain Valley, Garland county.

California.—1889.—Instead of nine springs, as in 1888, California has fourteen on the list for 1889. They are the following: Azule Seltzer Springs, San José, Santa Clara county; Bartlett Springs, Bartlett Springs, Lake county; Byron Hot Springs, Byron Hot Springs, Contra Costa county; Castalian Mineral Water, Inyo county; Coronado Natural Mineral Water, Coronado, San Diego county; El Toro Spring, Marin county; Geyser Soda and Litton Seltzer Springs, Sonoma county; Hot Springs of Elsinore, City of Elsinore, San Diego county; Napa Soda Springs, Napa Soda Springs, Napa county; Ojai Hot Springs, Ventura county; Pacific Congress Springs, San José, Santa Clara county; Pacific Congress Springs, Saratoga, Santa Clara county; Paraiso Springs, Paraiso Springs, Monterey county; Tolenas Springs, Fairfield, Solano county; Witter Springs, Lake county.

1890.—One new spring is added to and one taken from the list, making a total of fourteen; of these the following twelve report for 1890: Azule Seltzer Spring, San José, Santa Clara county; Bartlett Springs, Bartlett Springs, Lake county; Castalian Mineral Water, Inyo county; Coronado Natural Mineral Water, Coronado, San Diego county; El Toro Spring, Marin county; Geyser Soda and Litton Seltzer Springs, Sonoma county; Napa Soda Springs, Napa Soda Springs, Napa county; Ojai Hot Springs, Ventura county; Paraiso Springs, Fairfield, Solano county; Tuscan Spring, Red Bluff, Tehama county; Witter Springs, Upper Lake, Lake county.

Colorado.—1889.—Colorado's two springs of 1888 increased to eight in 1889; they are the following: Boulder Springs; Clark Magnetic Spring, Pueblo, Pueblo county; Fariss Magnetic Well, Pueblo, Pueblo county; Idaho Mineral Spring, Idaho Springs, Clear Creek county; Little Ute and Iron Duke Springs, Cañon City, Fremont county; Manitou, Navajo, and Shoshone Springs, Manitou Springs, El Paso county; Seltzer Springs, Springdale, Boulder county; Ute and Little Chief Iron Springs, Manitou, El Paso county.

1890.—The number of springs on the list remains the same, and all of the eight report their sales. They are: Boulder Springs, Boulder Springs, Boulder county; Clark Magnetic Mineral Spring, Pueblo, Pueblo county; Fariss Magnetic Well, Pueblo, Pueblo county; Idaho Mineral Spring, Central City, Gilpin county; Little Ute and Iron Duke Springs, Cañon City, Fremont county; Manitou, Navajo, and Shoshone Springs, Manitou, El Paso county; Seltzer Springs, Springdale, Boul-

der county; Ute and Little Chief Iron Springs, Manitou, El Paso county.

Connecticut.—1889.—Three springs make up the list for Connecticut, as follows: Aspinock Springs, Putnam Heights, Windham county; Oxford Chalybeate Spring, Oxford, New Haven county; Stafford Mineral Spring, Stafford Springs, Tolland county.

1890.—Only two springs, viz, Aspinock Spring and Stafford Mineral Spring, report sales.

Florida.—1889.—For the first time Florida is represented on the list with one spring, viz: Cantoment Spring, near Pensacola, Escambia county, which reports also for 1890.

Georgia.—1889.—Three springs report. They are the following: Bowden Lithia and Georgia Bromine-Lithia Springs, Lithia Springs, Douglas county; Daniels' Springs, Greene county; Hughes' Springs, Floyd county.

1890.—One spring not on the list for 1889 is added, and all four report. They are: Bowden Lithia and Georgia Bromine-Lithia Springs, Lithia Springs, Douglas county; Daniels' Springs, Greene county; Hughes' Springs, Floyd county; Ponce de Leon Mineral Spring, Atlanta, Fulton county.

Idaho.—1889 and 1890.—As in the preceding years, Idaho is represented by the Idanha Springs of Soda Springs, Bingham county.

Illinois.—1889.—Ten springs report for this year, whereas only four reported in 1888. The following are the ten springs: Black Hawk Springs, Rock Island, Rock Island county; Diamond Mineral Spring, Grantfork, Madison county; Glen Flora Mineral Spring, Waukegan, Lake county; Hillsboro Mineral Spring, Hillsboro, Montgomery county; Kirkwood Mineral Spring, Kirkwood, Warren county; Peoria Magnetic Artesian Spring, Peoria, Peoria county; Perry Springs, Perry Springs, Pike county; Red Avon Mineral Spring, Fulton county; Sanicula Springs, Ottawa, La Salle county; Silver Springs, Greenup, Cumberland county.

1890.—One spring is taken from the list, and reports have been received from the following: Black Hawk Springs, Rock Island, Rock Island county; Diamond Mineral Spring, Grantfork, Madison county; Kirkwood Mineral Spring, Kirkwood, Warren county; Peoria Magnetic Artesian Spring, Peoria, Peoria county; Perry Springs, Perry Springs, Pike county; Red Avon Mineral Spring, Fulton county; Sanicula Springs, Ottawa, La Salle county.

Indiana.—1889.—Indiana's list increased from six in 1888 to eight in 1889. These are: Ash Iron Springs, De Gonia, Warwick county; Buffalo Saline Well, Millport, Washington county; Elliot's Mineral Spring, Shoals, Martin county; Kickapoo Magnetic Springs, Kickapoo, Warren county; King Mineral Springs, Muddy Fork, Clark county; Lodi Artesian Well, Lodi, Fountain county; Magnetic Mineral Spring, Terre Haute, Vigo county; West Baden Springs, West Baden, Orange county.

1890.—The number of springs on the list remains the same as for 1889, two springs being added and two taken from it. The springs reporting are: Elliot's Mineral Spring, Martin county; Kickapoo Magnetic Springs, Kickapoo, Warren county; King's Mineral Springs, Muddy Fork, Clark county; Lodi Artesian Well, Silverwood, Fountain county; Magnetic Mineral Spring, Terre Haute, Vigo county; West Baden Springs, West Baden, Orange county; French Lick Springs, French Lick, Orange county; Indiana Mineral Springs, Indiana Mineral Springs, Warren county.

Iowa.—1889.—In 1888 the list included three springs from this State; two were added for 1889, making the total number for which reports were received as follows: Black Hawk Springs, Salt Creek township, Davis county; Cherokee Magnetic Mineral Spring, Cherokee, Cherokee county; Lake View Medical Spring, Lake View, Sac county; Ottumwa Mineral Springs, Ottumwa, Wapello county; White Sulphur Springs, White Sulphur, Scott county.

1890.—One new spring is added to the list and reports were received from the following: Black Hawk Springs, Salt Creek township, Davis county; Cherokee Magnetic Mineral Spring, Cherokee, Cherokee county; Ottumwa Mineral Springs, Ottumwa, Wapello county; White Sulphur Springs, Scott county; Colfax Mineral Water, Colfax, Jasper county.

Kansas.—1889.—In 1888 Kansas had five springs reporting sales. They had increased in 1889 to nine, as follows: Blazing's Artesian Mineral Wells, Manhattan, Riley county; Boiling Springs, Mound Valley, Labette county; Geuda Mineral Springs, Geuda Springs, Cowley county; Great Spirit Springs, Cawker City, Mitchell county; Jewell county Lithium Springs, Montrose, Jewell county; Osage Mission Mineral Well, Osage Mission, Neosho county; Providence Mineral Wells, Providence, Butler county; Topeka Mineral Wells, Topeka, Shawnee county; Wichita Mineral Spring, Wichita, Sedgwick County.

1890.—One new spring is added to the list and two are taken from it, leaving the total eight. Seven report as follows: Blazing's Artesian Mineral Wells, Manhattan, Riley county; Geuda Mineral Springs, Geuda Springs, Cowley county; Great Spirit Springs, Cawker City, Mitchell county; Providence Mineral Wells, Providence, Butler county; Topeka Mineral Wells, Topeka, Shawnee county; Wichita Mineral Spring, Wichita, Sedgwick county; Iola Mineral Well, Iola, Allen county.

Kentucky.—1889.—No change so far as number of springs reporting is concerned is noted for 1888 to 1889. The following springs reported: Anita Springs, La Grange, Oldham county; Bedford Springs, Bedford, Trimble county; Blue Lick Springs, Blue Lick Springs, Nicholas county; Crab Orchard Springs, Crab Orchard, Lincoln county; St. Patrick's Well, Louisville, Jefferson county.

1890.—Kentucky's list remains the same for the previous year. The following five springs report sales: Anita Springs, La Grange, Old-

ham county; Bedford Springs, Bedford, Trimble county; Blue Lick Springs, Blue Lick Springs, Nicholas county; Crab Orchard Springs, Crab Orchard, Lincoln county; St. Patrick's Well, Louisville, Jefferson county.

Maine.—1889.—The list for this year showed an increase of one spring over those reporting for 1888. The following springs, eight in number, reported: Hartford Cold Spring, Oxford county; Cold Bowling Spring, York county; Keystone Spring, East Poland, Androscoggin county; Old Point Indian Spring, Somerset county; Poland Spring, Poland, Androscoggin county; Seal Rock Spring, Saco, York county; Underwood Springs, Falmouth Foreside, Cumberland county; Windsor Mineral Spring, Androscoggin county.

1890.—One spring on the list of 1889 reports no sales for 1890 and three springs new to the list are added, which makes the total number ten. The springs reporting are seven in number, as follows: Barker Mill Spring, Auburn, Androscoggin county; Crystal Springs, Auburn, Androscoggin county; Keystone Spring, East Poland, Androscoggin county; Poland Spring, South Poland, Androscoggin county; Underwood Springs, Falmouth Foreside, Cumberland county; Wilson Spring, North Raymond, Cumberland county; Windsor Mineral Spring, Lewiston, Androscoggin county.

Maryland.—1889.—Four springs reported, as against none for the preceding year. They are the following: Cecil Spring, Cowentown, Cecil county; Chattolane Mineral Spring, Chattolane, Baltimore county; Flintstone Mineral Springs, Flintstone, Allegany county; Strontia Mineral Spring, Brooklandville, Baltimore county.

1890.—Only two springs report. They are: Chattolane Mineral Spring, Chattolane, Baltimore county; Flintstone Mineral Springs, Flintstone, Allegany county.

Massachusetts.—1889.—Eight springs, an increase of two over 1888, reported sales for this year. The following are the ones reporting: Allendale Springs, West Roxbury, Suffolk county; Belmont Hill Spring, Everett, Middlesex county; Belmont Natural Spring, Everett, Middlesex county; Echo Grove Springs, West Lynn, Essex county; Everett Crystal Spring, Everett, Middlesex county; Sheep Rock Spring, Towell, Middlesex county; Simpson Spring, South Easton, Bristol county; Undine Spring, Brighton, Suffolk county.

1890.—One spring is added to the list, and eight springs in all report sales, as follows: Allendale Spring, West Roxbury, Suffolk county; Belmont Hill Spring, Everett, Middlesex county; Belmont Natural Spring, Belmont, Middlesex county; Everett Crystal Spring, Everett, Middlesex county; Sheep Rock Spring, Towell, Middlesex county; Simpson Spring, South Easton, Bristol county; Undine Spring, Brighton, Suffolk county; Commonwealth Mineral Spring, Waltham, Middlesex county.

Michigan.—1889.—Although but one spring reported sales in 1888

there were seven reporting in 1889. They are the following: Americanus Well, Lansing, Ingham county; Eastman Springs, Benton Harbor, Berrien county; Magnetic Mineral Springs, Spring Lake, Ottawa county; Mount Clemens Original Mineral Springs, Mount Clemens, Macomb county; Salutaris Mineral Spring, Saint Clair Springs, Saint Clair county; Ypsilanti Mineral Spring, Ypsilanti, Washtenaw county; Zauber Wasser Spring, Hudson, Lenawee county.

1890.—There is no change in the list for 1890, but one of the springs has sent no report. Those reporting are: Americanus Well, Lansing, Ingham county; Eastman Springs, Benton Harbor, Berrien county; Magnetic Mineral Springs, Spring Lake, Ottawa county; Mount Clemens Original Mineral Springs, Mount Clemens, Macomb county; Salutaris Mineral Spring, Saint Clair, St. Clair county; Zauber Wasser Spring, Hudson, Lenawee county.

Minnesota.—1889.—The only spring reporting for this State in 1889 and 1890 is Inglewood Springs, Hennepin county.

Mississippi.—1889.—Instead of three springs, as in 1888, only the following two report for 1889: Brown's Wells, Copiah county, S. J. Morehead, Brown's Wells post-office; Castilian Springs, near Durant, Holmes county. The same two wells report for 1890.

Missouri.—The six springs of 1888 have more than doubled in 1889, thirteen springs reporting, as follows: Artesian White Sulphur Well, Clinton, Henry county; B. B. Spring, Bowling Green, Pike county; Blue Lick Springs, Saline county; Eldorado Springs, Eldorado Springs, Cedar county; Electric Springs, Johnson county; Haupt's Mineral Spring, Milan, Sullivan county; Lebanon Magnetic Spring, Laclede county; Paris Springs, Paris Springs, Lawrence county; Randolph Springs, Randolph Springs, Randolph county; Reed Springs, Clay county; Reiger Mineral Springs, Mercer county; Sweet Springs, Sweet Springs, Saline county; Young's Medical Well, corner Twenty-fifth and Vine streets, Kansas City, Jackson county.

1890.—Three springs are taken from the list and seven springs have sent returns, viz, B. B. Spring, Bowling Green, Pike county; Blue Lick Spring, Saline county; Eldorado Springs, Eldorado Springs, Cedar county; Paris Springs, Paris Springs, Lawrence county; Randolph Springs, Randolph Springs, Randolph county; Reiger Springs, Mercer county; Young's Medical Well, Warrensburg, Jackson county.

Nebraska.—1889.—The Victoria Mineral Spring, Custer county, represents Nebraska for the first time on the list.

1890.—Nebraska is still represented on the list by the Victoria Mineral Spring, Custer county.

New Hampshire.—1889.—Two springs report, viz: Londonderry Lithia Spring, Nashua, Rockingham county, and Milford Springs, Amherst Station, Hillsboro county.

1890.—Three springs report sales, namely, Londonderry Lithia Springs, Londonderry, Rockingham county; Milford Springs, Amherst

Station, Hillsboro county; White Mountain Springs, Conway, Carroll county.

New Jersey.—1889.—New Jersey for the first time is put upon the list with one commercial water, viz: that from Kalium Springs, Collingswood, Camden county.

1890.—No reports have been received from New Jersey.

New Mexico.—1889.—Four springs make up New Mexico's list for 1889 instead of one, as in the previous year. The springs reporting are: Aztec Springs, Santa Fé, Santa Fé county; Baca Springs, Coyote district, Bernalillo county; Ojo Caliente Springs, Ojo Caliente, Taos county; Soda Springs, near Albuquerque, Bernalillo county.

1890.—The list remains the same as for 1889, and the following three are the only springs reporting: Aztec Springs, Santa Fé, Santa Fé county; Ojo Caliente Springs, Ojo Caliente, Taos county; Soda Springs, Coyote Cañon, Bernalillo county.

New York.—1889.—Twenty-one springs made reports as compared with seventeen in 1888. The springs reporting are: Crystal Springs, Barrington, Yates county; Deep Rock Springs, Oswego City, Oswego county; Empire Seneca Springs, Dunkirk, Chautauqua county; Geneva Magnetic Mineral Springs, Geneva, Ontario county; Massena Springs, Massena, St. Lawrence county; Oneita Springs, Utica, Oneida County; White Sulphur Springs, Sharon Springs, Schoharie county.

Saratoga Springs, Saratoga county: Champion Springs, Columbia Springs, Congress Springs, Empire Springs, Excelsior and Union Springs, Hathorn Springs, High Rock Springs, Imperial Spring, New Putnam Spring, Royal or New Putnam Spring, Patterson Spring, Saratoga Carlsbad Spring, Saratoga Magnetic and Peerless Springs, Saratoga Vichy Springs.

1890.—Nineteen of the twenty-six springs on the list for New York send returns; five of these are new to the list for 1890, and one of the springs of 1889 is taken from the list. The list reporting for 1890 is: Cayuga Springs, Cayuga, Cayuga county; Deep Rock Springs, Oswego, Oswego county; Miller's Geneva Mineral Spring, Geneva, Ontario county; Massena Springs, Massena, St. Lawrence county; White Sulphur Springs, Sharon Springs, Schoharie county; Artesian Lithia Springs, Ballston Spa, Saratoga county; White Sulphur Spring, Richfield Springs, Otsego county; Avon Spring, Avon, Livingston county; Oak Orchard Acid Springs, Alabama, Genesee county.

Saratoga Springs, Saratoga county: Empire Springs, Excelsior and Union Spring, Hathorn Springs, High Rock Spring, Imperial Spring, Royal or New Putnam Spring, Saratoga Carlsbad Spring, Saratoga Vichy Springs, Saratoga Kissingen Spring.

North Carolina.—1889.—The six springs on the list for 1888 have increased to the following eleven: All-Healing Spring, Alexander county; Ashley's Bromine and Arsenic Springs, Ashe county; Barium Springs, Barium Springs, Iredell county; Black Mountain Iron and Alum

Springs, Black Mountain, Buncombe county; Lemon Springs, Lemon Springs, Moore county; Lincoln Lithia Springs, Lincolnton, Lincoln county; Minnekalta Springs, Gaston county; Panacea Springs, near Littleton, Halifax county; Park's Alkaline Springs (near Danville, Va.), Caswell county; Seven Springs, Seven Springs, Wayne county; Shaw's Healing Springs, Littleton, Halifax county.

1890.—One new spring is added to the list and one is taken from it. Only the following six report, viz: Ashley's Bromine and Arsenic Springs, Bristol, Ashe county; Barium Springs, Barium, Iredell county; Lemon Springs, Lemon Springs, Moore county; Lincoln Lithia Springs, Lincolnton, Lincoln county; Park's Alkaline Springs, Caswell county (post-office Danville, Virginia); Thomson's Bromine Arsenic Spring, Crumpler, Ashe county.

Ohio.—1889.—The seven springs of 1888 have increased to eleven, from all of which reports have been received. They are: Adams County Mineral Spring, Mineral Springs, Adams county; Belbrook Magnetic Springs, Belbrook, Greene county; Crystal Mineral Spring, Urbana, Champaign county; Devonian Mineral Spring, Lorain, Lorain county; Electro-Magnetic Springs, Fountain Park, Champaign county; Lenape Spring, Delaware, Delaware county; Magnetic and Saline Spring, Marysville, Union county; Ohio Magnetic Springs, Magnetic Springs, Union county; Rex Mineral Water, New Richmond, Clermont county; Ripley Bromo-Lithia Spring, Ripley, Brown county; Sulphur Lick Spring, Frankford, Ross county.

1890.—One spring is taken from the list and one added, which leaves the total the same as for 1889. Only eight springs have reported, viz: Adams County Mineral Spring, Mineral Springs, Adams county; Crystal Mineral Spring, Urbana, Champaign county; Devonian Mineral Spring, Lorain, Lorain county; Electro-Magnetic Springs, Fountain Park, Champaign county; Rex Mineral Spring, New Richmond, Clermont county; Ripley Bromo-Lithia Spring, Ripley, Brown county; Sulphur Lick Spring, Anderson, Ross county; Magnetic and Saline Spring, Marysville, Union county.

Oregon.—1889.—The following report: Wagner Soda Spring, Ashland, Jackson county; Wilhoit Spring, Clackamas county.

1890.—No reports have been received from Oregon.

Pennsylvania.—1889.—The three springs of the list for 1888 have increased to twelve. They are: Allegheny Spring, Warren county; Bedford Springs, Bedford, Bedford county; Black Barren Mineral Spring, Pleasant Grove, Lancaster county; Corry Artesian Fountain, Corry, Erie county; Cresson Springs, Cresson, Cambria county; Enreka Mineral Springs, Saegerstown, Crawford county; Parker Magnetic Mineral Springs, Gardeau, McKean county; Pavilion Springs, Wernersville, Berks county; Pulaski Mineral Spring, Pulaski, Lawrence county; Roscommon Springs, Wind Gap, Monroe county; Sizerville Magnetic Mineral Spring, Sizerville, Cameron county; Susquehanna Spring and Kingsland Spring, Rush, Susquehanna county.

1890.—One spring is taken from the list and ten springs report sales. These springs are: Black Barren Mineral Spring, Pleasant Grove. Lancaster county; Corry Artesian Fountain, Corry, Erie county; Cresson Springs, Cresson, Cambria county; Eureka Mineral Springs, Saegerstown, Crawford county; Parker Magnetic Mineral Spring, Gardau, McKean county; Pavilion Springs, Reading, Berks county; Pulaski Mineral Springs, Pulaski, Lawrence county; Roscommon Springs, Wind Gap, Monroe county; Sizerville Magnetic Mineral Spring, Sizerville, Cameron county; Susquehanna Spring and Kingsland Spring, Rush, Susquehanna county.

Rhode Island.—1889.—Both springs on Rhode Island's list report sales. They are: Ochee Mineral and Medical Springs, Johnson, Providence county; Holly Springs, Woonsocket, Providence county.

1890.—Both localities report for this year, viz: Ochee Mineral and Medical Springs, Johnson, Providence county; Holly Springs, Woonsocket, Providence county.

South Carolina.—1889.—Two springs report sales, viz: Chick's Springs, Chicks Springs, Greenville county; Glen Springs, Glen Springs, Spartanburg county.

1890.—No reports have been received for 1890.

South Dakota.—1889.—South Dakota is represented for the first time on the list by Dakota Hot Springs, Fall River county, which reports also for 1890.

Tennessee.—1889.—Four springs, a decrease of two from 1888, report. They are: Estill Springs, Estill Springs, Franklin county; Idaho Springs, near Clarksville, Montgomery county; Red Boiling Springs, Red Boiling Springs, Macon county; Rhea Springs, Rhea Springs, Rhea county.

1890.—Only one of the springs on the list of 1889 has reported: Idaho Springs, Clarksville, Montgomery county; and one, new to the list, reports sales, viz: Tate Spring, Tate Spring, Grainger county.

Texas.—1889.—The number of springs reporting in 1889 is fourteen, just double the number for 1888. They are: Capp's Well, Longview, Gregg county; Dalby Springs, Texarkana, Bowie county; Elkhart Mineral Well, near Elkhart, Anderson county; Hynson's Iron Mountain Springs, Marshall, Harrison county; Mineral Wells Springs, Mineral Wells, Palo Pinto county; Montvale Springs, Marshall, Harrison county; Overall Mineral Well, Franklin, Robertson county; Page's Well, Georgetown, Williamson county; Richards's Wells, Rockdale, Milam county; Rosborough Springs, Marshall, Harrison county; Slack's Well, Fayette county; Texas Sour Springs, Luling, Caldwell county; Tioga Mineral Well, Tioga, Grayson county; Wooten Wells, Robertson county.

1890.—Thirteen springs report sales. They are: Capp's Well, Longview, Gregg county; Dalby Springs, Dalby Springs, Bowie county; Elkhart Mineral Well, Elkhart, Anderson county; Hynson's Iron Mountain Spring, Marshall, Harrison county; Mineral Well Springs,

Mineral Wells, Palo Pinto county; Montvale Springs, Marshall, Harrison county; Overall Mineral Well, Franklin, Robertson county; Richards' Wells, Rockdale, Milam county; Rosborough Springs, Marshall, Harrison county; Slack's Well, Fayette county (post-office, Walder Depot, Gonzales county); Texas Sour Springs, Luling, Caldwell county; Tioga Mineral Well, Tioga, Grayson county; Wooten Wells, Robertson county.

Vermont.—1889.—The list of springs decreased from six in 1888 to three, as follows: Alburg Sulphur and Lithia Springs, Alburg Springs, Grand Isle county; Brunswick White Sulphur Springs, Brunswick, Essex county; Clarendon Springs, Clarendon Springs, Rutland county.

1890.—One new spring is added to the list, making the total four for the State, all reporting, as follows: Alburg Sulphur and Lithia Springs, Alburg Springs, Grande Isle county; Brunswick White Sulphur Spring, Brunswick, Essex county; Clarendon Springs, Clarendon, Rutland county; Missisquoi Springs, Sheldon, Franklin county.

Virginia.—1889.—Twenty-one springs reported sales. The following is the list: Bear Lithia Springs, Elkton, Rockingham county; Blue Ridge Springs, Blue Ride Springs, Botetourt county; Buffalo Lithia Springs, Buffalo Lithia Springs, Mecklenburg county; Cove Lithia Water, Wytheville, Wythe county; Farmville Lithia Springs, Farmville, Prince Edward county; Hot Springs, Hot Springs, Bath county; Hunter's Pulaski Alum Springs, Walker's Creek, Pulaski county; Jordan White Sulphur Springs, Jordan Springs, Frederick county; Massanetta Springs, Massanetta Springs, Rockingham county; Osceola Springs, near Pleasant Valley, Rockingham county; Otterburn Lithia and Magnesia Springs, Amelia C. H., Amelia county; Pæonian Spring, Loudoun county; Powhatan Lithia and Alum Spring, Powhatan, Powhatan county; Rawley Springs, Rawley Springs, Rockingham county; Roanoke Red Sulphur Springs, Roanoke county; Rockbridge Alum Springs, Alum Springs, Rockbridge county; Rockingham Springs, McGaheysville, Rockingham county; Seven Springs, 2 miles northwest of Glade Springs, Washington county; Stribling Springs, Stribling Springs, Augusta county; Virginia Arsenic Bromine and Lithia Springs, near Allegheny Springs, Montgomery county; Wallawhatoola Alum Springs, Millboro Springs, Bath county; Wolf Trap Lithia Springs, Wolf Trap Station, Halifax county.

1890.—By the addition of two new springs the list is increased to twenty-three, and the following twenty report: Blue Ridge Springs, Blue Ridge Springs, Botetourt county; Buffalo Lithia Springs, Buffalo Lithia Springs, Mecklenburg county; Cove Lithia Springs, Wytheville, Wythe county; Elk Lithia Spring, Elkton, Rockingham county; Farmville Lithia Springs, Farmville, Cumberland county; Hunter's Pulaski Alum Springs, Walkers Creek, Pulaski county; Jordon White Sulphur Springs, Stephenson, Frederick county; Massanetta Springs, near Harrisonburg, Rockingham county; Osceola Springs, Harrisonburg, Rockingham county; Otterburn Lithia and Magnesia Spring, Amelia C. H.,

Amelia county; Pæonian Spring, Clarks Cap, Loudoun county; Roanoke Red Sulphur Springs, Catawba, Roanoke county; Rockbridge Alum Springs, Goshen, Rockbridge county; Rockingham Springs, McGaheysville, Rockingham county; Seven Springs, Abingdon, Washington county; Stribling Springs, Stribling Springs, Augusta county; Virginia Arsenic, Bromine, and Lithia Springs, Christiansburg, Montgomery county; Wallawhatoola Alum Springs, Richmond, Bath county; Wolf Trap Lithia Springs, Wolf Trap Station, Halifax county; Shenandoah Alum Springs, Mount Jackson, Shenandoah county.

Washington.—1889.—The State of Washington presents a list of three instead of one as in 1888. The springs reporting are: Cascade Springs, Skamania county; Medical Lake, Medical Lake, Spokane county; Yakima Soda Springs, North Yakima, Yakima county.

1890.—Two springs report as follows: Medical Lake, Medical Lake, Spokane county; Yakima Soda Springs, North Yakima, Yakima county.

West Virginia.—1889.—Four springs report for 1889, as follows: Capon Springs, Capon Springs, Hampshire county; Salt Sulphur Springs, Salt Sulphur Springs, Monroe county; Triplett Springs, Willow Island, Pleasant county; White Sulphur Springs, White Sulphur Springs, Greenbrier county.

1890.—Two springs are added to the list and the total number report. They are Red Sulphur Springs, Monroe county; Irondale Springs, Independence, Preston county; Triplett Springs, Willow Island, Pleasant county; White Sulphur Springs, White Sulphur Springs, Greenbrier county; Capon Springs, Capon Springs, Hampshire county; Salt Sulphur Springs, Salt Sulphur Springs, Monroe county.

Wisconsin.—1889.—Twenty springs report in this year as compared with the twelve in the list of 1888. The springs reported are: Allouez Magnesia Mineral Spring, Green Bay, Brown county; Ashland Mineral Spring, Ashland, Ashland county; Darlington Mineral Spring, Darlington, Lafayette county; Fort Crawford Spring, Prairie du Chien, Crawford county; Lebens Wasser Spring, Brown county; Salvator Mineral Spring, Brown county; Shealtiel Springs, Waupaca, Waupaca county; Sheboygan Springs, Sheboygan, Sheboygan county; Silver Sand Spring, Milwaukee county; Vita Mineral Spring, Beaver Dam, Dodge county; Nee-Ska-Ra Spring, Milwaukee, Milwaukee county.

Waukesha Springs, Waukesha county: The Alma Spring, Arcadian Mineral Spring, Bethesda Mineral Springs, Clysmic Springs, Henk Mineral Springs, Horeb Mineral Spring, Mineral Rock Spring, Waukesha Hygeia Mineral Spring, White Rock Mineral Spring.


1890.—Two springs are added to the list, and the name of the Alma Springs at Waukesha is changed to Almanaris. The following twelve springs report sales: Allouez Magnesia Mineral Spring, Green Bay, Brown county; Darlington Mineral Spring, Darlington, Lafayette county; Fort Crawford Spring, Prairie du Chien, Crawford county;

Lebens Wasser Spring, Green Bay, Brown county; Salvator Mineral Spring, Green Bay, Brown county; Shealtiel Mineral Spring, Farmington, Waupaca county; Sheboygan Springs, Sheboygan, Sheboygan county; Silver Sand Spring, Milwaukee, Milwaukee county; Nee-Ska-Ra Spring, Wauwatosa, Milwaukee county; Palmyra Springs, Palmyra, Jefferson county; Rainbow Mineral Spring, Wautoma, Waushara county; Vita Mineral Spring, Beaver Dam, Dodge county; Bethania Mineral Springs, Osceola Mills, Polk county.

Waukesha Springs, Waukesha county.—Almanaris Spring, Arcadian Spring, Bethesda Mineral Spring, Henk Mineral Spring; Hygeia Mineral Spring; Mineral Rock Spring, White Rock Mineral Spring.

Summary of reports of mineral springs for 1890.

	Springs re- porting.	Springs not reporting.	Total used commercially.		Springs re- porting.	Springs not reporting.	Total used commercially.
North Atlantic States:				North Central States:			
Maine	7	3	10	Ohio	8	3	11
New Hampshire	3	0	3	Indiana	8	0	8
Vermont	4	0	4	Illinois	7	2	9
Massachusetts	8	1	9	Michigan	6	1	7
Rhode Island	2	0	2	Wisconsin	20	3	23
Connecticut	2	1	3	Minnesota	1	0	1
New York	19	7	26	Iowa	5	1	6
New Jersey	0	1	1	Missouri	7	3	10
Pennsylvania	10	1	11	North Dakota	0	0	0
South Atlantic States:				South Dakota	1	0	1
Delaware	0	0	0	Nebraska	1	0	1
Maryland	2	2	4	Kansas	7	1	8
District of Columbia	0	0	0	Western States and Terri- tories:			
Virginia	20	3	23	Alaska	0	0	0
West Virginia	6	0	6	Wyoming	0	0	0
North Carolina	6	5	11	Montana	0	0	0
South Carolina	0	2	2	Colorado	7	1	8
Georgia	4	0	4	New Mexico	3	1	4
Florida	1	0	1	Arizona	0	0	0
South Central States:				Utah	0	0	0
Kentucky	5	0	5	Nevada	0	0	0
Tennessee	2	3	5	Idaho	1	0	1
Alabama	3	2	5	Washington	2	1	3
Mississippi	2	0	2	Oregon	0	2	2
Louisiana	0	0	0	California	12	2	14
Texas	13	1	14	Total			
Indian Territory	0	0	0		220	53	273
Oklahoma	0	0	0				
Arkansas	5	0	5				

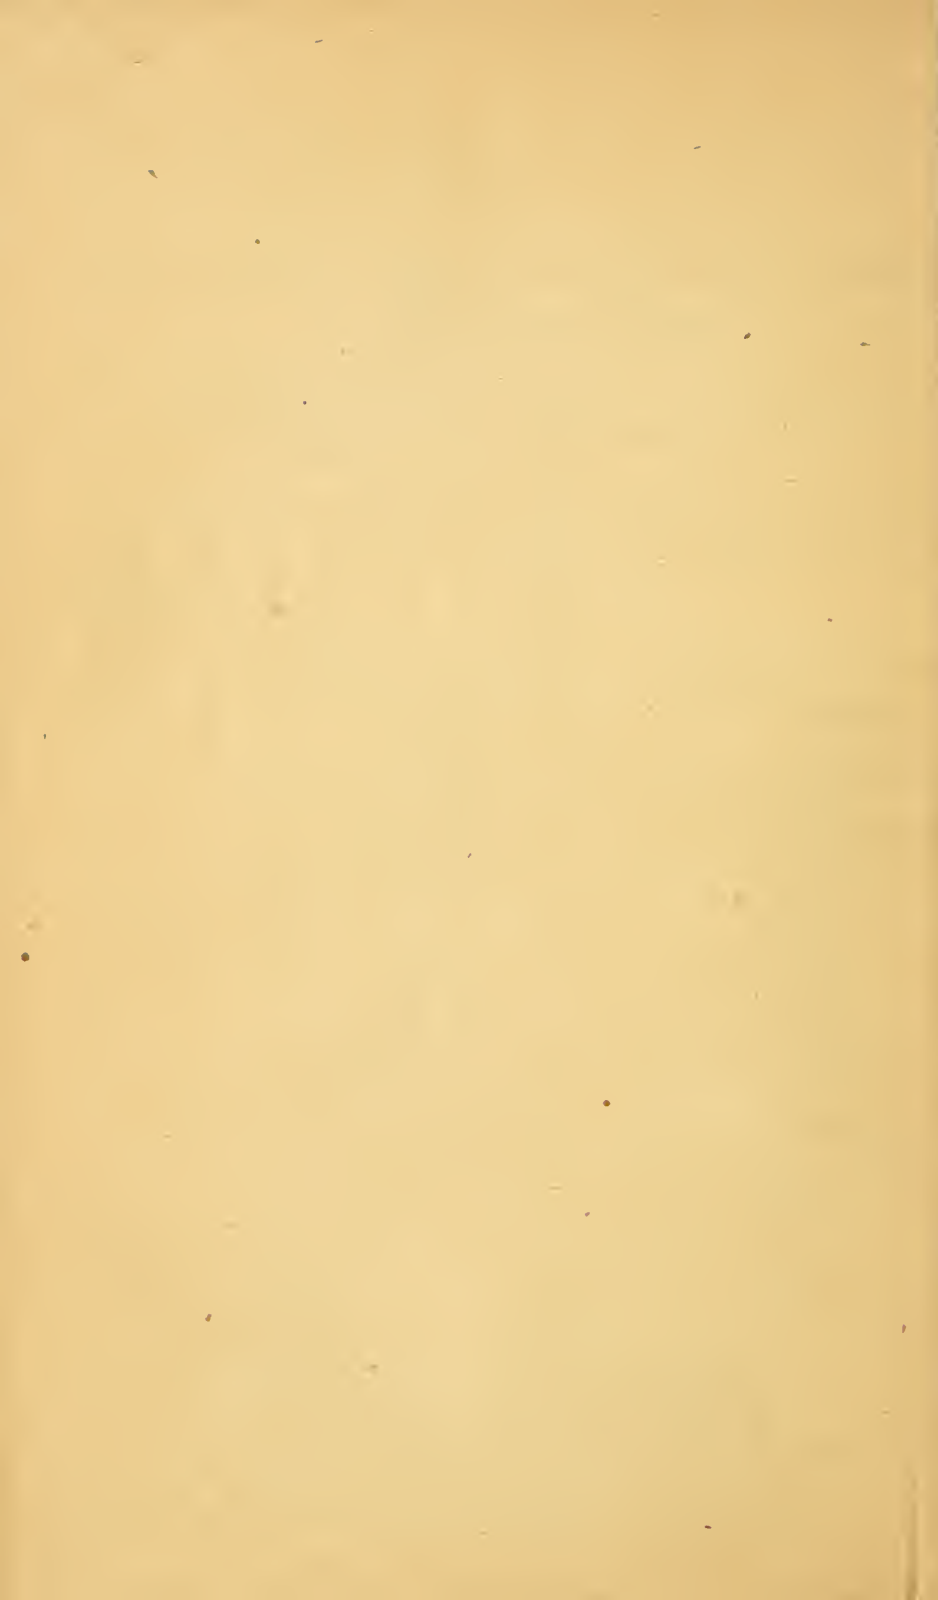

GENERAL INDEX TO MINERAL RESOURCES OF THE UNITED STATES FROM 1882 TO 1890.

	1882.	1883-'84.	1885.	1886.	1887.	1888.	1889-'90.
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Abbott quicksilver mine, California.....	389	494	236	161	119	98	95
Abrasive materials.....	476	712	428	581	552	576	456
buhrstone.....	477	712	428	581	552	576	456
corundum.....	476	714, 733	429	585	553	577	457
emery.....	476	714	431	586	554	577	457
grindstones.....	479	713	428	582	552	545, 576	458
imports.....	476	713, 719	428, 432	582, 586	552	576	456
infusorial earth.....	479	720	433	587	554	578	459
novaculite.....	492		433	589	4, 7	5	460
pumice stone.....	480	721	433				
rotten stone.....		722					
summary.....				4	4	5	3
Accidents in coal mining.....	107	126	27	254	225	255, 299, 387, 389	205
Actinolite.....		382, 765			785		
Afghanistan, petroleum.....		232					
Africa, copper.....		355	229, 242	129, 139	88	73	73
gold.....		319					
iron ore.....				98, 102			
Agalmatolite, North Carolina.....	713				769		
Agate.....	491	756, 781	441, 443	597, 604	556, 561	584	446
in Arizona.....		757			561		
Arkansas.....		757			700		
California.....		757		597	704		
Colorado.....	491	757					
Connecticut.....	672	756			714		
Illinois.....		757					
Lake Superior region.....	491	757					
Massachusetts.....	694	756			743		
Minnesota.....		757					
New York.....		756	442				
North Carolina.....	713	757			769		
Oregon.....		757					
Rhode Island.....	727				785		
Texas.....	734	757			793		
Washington.....			441				
Wisconsin.....		757					
Yellowstone National Park.....		757					
Agatized wood.....	492	759		596	561	581	446
Alabama, alum.....		949		681			
asbestos.....	669		521		693		
asphaltum.....						513	
barytes.....	669				693		
blast furnaces.....	121				20		
brick production.....					535, 537	557, 565	
buhrstones.....		712					
cassiterite.....	667, 669	767			693		
chalcopryrite.....	669				693		
clay.....	667	678			690		
coal.....	6, 34, 36	12, 14, 156	11, 13, 83	230, 235	171, 189, 205, 690	171, 206, 208	146, 172
fields.....	667	156			189	208, 211	
miners' wages.....	103	14	85	235	187, 192, 203	206	
operatives.....						210, 213	173
prices and receipts at Mobile.....						201	167
value.....			11	235	171	208	148, 172
coke.....	98	145, 149	75, 85	378, 389	22, 383, 394	4, 395, 406	
copper.....	231, 669				693		
corundum.....	669				553, 693		
covellite.....	669				693		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Alabama, fire brick and clay	466	678			541, 690	564, 570	
flagging stone	667				690		
galena	669				694		
gold	176, 179.				691, 694	37	49
granite	667				515, 691	521	
graphite	590, 667			686	691		
grindstone					693, 694		
gypsum	526	809			694		
halloysite	667				691		
hematite	149, 667,	278		85	691, 692,		40
	668				694		
iron	119, 133,	252	182	18, 33,	11	14, 23	10, 17
	149, 160			85			
ores	149, 156	278		86, 88,	49, 694	17	24, 40
				91			
kaolin	668			573	691	572	
lead ore					694		
lignite	669				694		
lime					532		
limestone						521	373, 377
limonite	149, 668			85	691		
lithographic stone	595	935					
magnetite	149, 669	278		85	694		
manganese	669	552	345		694		
marble	668			543	692	542	
marls	523, 668	808	454, 464	619	592	595	
melanconite	670				694		
menaccanite	149						
metallic paint				711			510
mica	670	908			671, 693,		
					694		
millstones and grindstones	669						
mineral waters		979	536	715	683	626, 630	522
mining law				731			
nails	125		186				
natural gas		236, 243	161		494		
ocher		926			693		508
petroleum production							363
phosphate rock		783, 794	164	618	584, 694		
		803					
phosphatic greensand		798, 801					
pottery						572	
pyrites	150, 670		506		695		
pyrolusite	669, 670				695		
pyrrhotite					695		
quartz	670				695		
sandstone	669				693, 695	521	374, 377
siderite	670				695		
silver	176			105	59	37	49
slate					695		
sphalerite	670				695		
steel	137			18		14	
structural materials					507	521	
talc	669	601			693		
tin ore	669				693		
zinc blende	670				695		
Alabandite, Colorado		814			712		
Alabaster and spar ornaments	762		464		602		
Arizona	762				698		
California	768				704		
Utah	775	780			796		
Alaska, amber							
antimony ores					695		
argentite					695		
asbestos					696		
berthierite		655			695		
bismuth							
calcite	760				696		
chalcopyrite	760	17			696		
coal	760		14		695	214	
copper	760				695		
galena		747			695		
garnet		312			695		
gold and silver	172, 176		200	104	58, 60,	36	49
					695		
graphite	760				696		
jadeite	498						
lead					695		
lignite	760				695	214	
limestone	760	665			696		
marble		911					
mica	584	979			696		
mineral waters						630	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Alaska, pyrites	760	750			695		
quartz							
Ru slan-American Coal Co						215	
silver	172, 176, 179		200	105	59, 695	36	49
sphalerite					695		
sulphur		867					
tetrahedrite					695		
Alaskaite, Colorado	748				707		
Albany, N. Y., structural materials				523		529	
Albite					562		
Connecticut					714		
Pennsylvania	725				783		
Algeria, antimony		645					
cop per			229	128	88	73	73
iron ores				16			
manganese			307				
Alipite, Maryland					741		
Alkalies in Great Britain					655		
Allanite		773			668, 769, 802		
Allegheny county, N. Y., petroleum fields	190		131			445	295
Allegheny county, Pa., coal	33	82	57	322	322	332, 338	296
natural gas			162			482	367
Mountain, Pa., coke district			83, 102	412	414	419, 425	
Valley, Pa., coke district		191	107	416	418	422, 425	
Allouez copper mine, Lake Superior	215, 219			113		53, 57, 68	59
Almaden, Spain, quicksilver mine		496				105	101
Altaite, Colorado	748				707		
Altoona, Cal., quicksilver mine	389				119	98	94
Alum	606	949		681	646		
in Alabama		949		681			
Arizona	762			681			
California	606	949			698	705	
Colorado	606	949					
Georgia		949					
Indiana		949					
Nevada				681			
New Jersey	606	949		681			
New York	606						
Ohio	720	949			777		
Pennsylvania	606			681			
South Carolina				681			
Tennessee	732	949			791		
Texas		949					
Utah	775					796	
Wyoming						809	
prices				681	646		
process of preparation				682			
production	xv, 606	5		5, 681	646		
shales, Texas	734				793		
Utah	775				796		
Virginia					802		
uses				682	647		
Aluminum	445	658	390	220	138	160	110
alloys		659			139	162	115
brass			391		139	162	
bronze		658	390	221	139	162	115
cap Washington Monument		659					
imports		658, 660	390, 392	221	138	162	118
in cast iron						162	
iron alloys			391			163	112
manufacture of		658			653	160	
prices	445	658	390	220	138	160	100
production		3, 6, 8, 658	3, 5, 7, 392	2, 7, 9, 221	2, 6, 8, 139	3, 160	6, 111
steel							117
sulphate	762				698		
uses		658	390	220		160	116
Alunogen, Arizona	762				698		
Amargosa (California) Borax Co	571						
Amazon stone	495	770	443	604	550, 562	584	446
in Colorado	495	724					
Maine		770					
Massachusetts		770					
North Carolina	495						
production	495	781	443	604	556	584	
Amber	498	779	444	598, 605	573	583	
in Alaska		780					
Delaware	675	780			719		
Maryland		780					
Massachusetts	498, 694	779			743		
Mexico		583					
New Jersey	498, 708	779		598	762		
Amethyst	491	750, 781	443	604	556	584	446
in Arizona		751					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Amethyst in Colorado.....	491	751					
Connecticut.....		750					
Georgia.....	676	750			721		
Lake Superior region.....		751					
Maine.....	491	750		596			
Massachusetts.....					743		
Michigan.....	696	751			747		
Nevada.....		751					
New Hampshire.....	705	750			759		
New Jersey.....		751					
North Carolina.....		725, 752					
Pennsylvania.....	491, 725	750			783		
Rhode Island.....		750		596			
Texas.....	734	751			793		
Virginia.....	491						
Wisconsin.....		751					
Yellowstone National Park.....		751					
Amphibolite, Wyoming.....	759						
Anaconda, Montana, copper mines.....			216, 233	117	74	57	
Analyses, anthracite coal, Colorado.....	43		19	245			
Pennsylvania.....		69					141
antimony ore, Nevada.....	438						
apatite.....		806					
brines, Stassfurt, Germany, salt wells.....					630, 636, 639		
calcined plaster.....					600		
cannel coal, Tennessee.....					357		
cement.....	460	676			531		
chromite.....		571					
clays, California.....		678					
coal, Alabama.....			13	239	194, 199, 202		
Alaska.....			14			215	
Arkansas.....	38		15			222	176
California.....					210		
Colorado.....	39	24, 31	21	245			181, 186
Dakota.....				251	222		
Georgia.....						241	
Illinois.....	51	162					
Indiana.....	53	45		396	238, 241		
Indian Territory.....	51			266	244	261	210
Kansas.....		165				275	
Kentucky.....	57			399	257, 262		
Maryland.....			34				
Missouri.....		52			274	287	
Montana.....	62	53	37	285		291	229
Nebraska.....					277		
New Mexico.....	62	56					232
Ohio.....		60, 172					
Oregon.....	95	66		295	289		
Pennsylvania.....		177, 181, 183, 190, 193	99, 104	307, 327, 330, 334	245		
Tennessee.....		197		344	354, 357	366	
Utah.....	78, 81	203	117	351	359	375	
Virginia.....	82	205		355	365	380	
Washington.....	96	99, 206		359	373		
West Virginia.....	84	208		374, 428	379	389, 432	282, 284
Wyoming.....	85, 87	101		375		391	
cobalt ore, Nevada.....		545	361				
coke, Colorado.....	41	158		393			
Illinois.....		162					
Indiana.....				396	399		
Indian Territory.....		164	90		400	261	
Kentucky.....		166		398, 401	402	411	
Montana.....		169					
Ohio.....		172					
Pennsylvania.....		178, 182, 185, 187, 189, 195	103, 106, 109		413	419	
Tennessee.....		197	114	421			
Utah.....		203	117				
Virginia.....			118	423			
Washington.....						426	
West Virginia.....		208, 210, 212	121	428	424, 426, 428	439	282, 284
Wyoming.....				619			282
coprolitic marl, North Carolina.....		791					
fertilizers, South Carolina.....				626	593		
fire-clay.....	468, 473	678				569	
granite, Arkansas.....						537	
green sands, Alabama.....		798					
gypsum.....					600		
infusorial earth.....		721		587	554		
iridosmine.....		581					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Analyses, iron ore, Alabama	150, 154, 157, 159	278		86, 91	50		26
Colorado	146	282			53		
Connecticut		271					
Kentucky		279		97			
Michigan		264, 268		71	38		
Minnesota		267		77	41		
Missouri		269			47		
Montana						34	
New Jersey		275		51			
New York		272		45	43		
North Carolina		277		83			
Pennsylvania		270		53	44		
Utah		288					
land plaster					600		
lead slags		449, 454					
limestone					588, 598		421
manganese ore		550	311, 323, 330, 334	185	148, 156	129, 132, 138	133, 171
silver ore		379					
meteoric iron		290					
natural gas		235				510	
phosphatic rock, Alabama		798, 802					
North Carolina		790	449	616			
platinum ore		577					
salt			482	636	614, 619		
smaltite		544					
spiegel iron		561, 564					
tin ore	454	614	370, 375			146, 153	
tourmaline					500		
tungsten ore		575					
Andalusite	497	382, 741					
André, M., experiments with copper mat- tes.	649						
Anglesite		382				707	
in Arizona	760, 762					698	
Colorado	748					706	
Idaho	770					722	
Iowa	682					731	
Massachusetts	694					743	
Nevada	772					756	
Utah	773					794	
Wyoming						809	
Anhydrite, Arizona	762					698	
Anthracite coal	7	778, 781	443	604	556	3, 226, 302, 584	242
fields	7, 8, 9	105	49	297, 300	291, 296	168, 306	243
in Colorado	32, 749		18	243	708	238	146
Massachusetts		87			744		
New Mexico	32	56	41	288	763	293	146
Pennsylvania	7	70	45	295	290, 779	168, 302	146, 242
Rhode Island	32	87		2	785		146
Virginia	32	93, 98	69				
West Virginia		93, 98			804		
industry, chronology	11						
inspection districts, Pennsylvania	25		49	298	293	303	
mining, Pennsylvania		104				302, 328	
prices	28	75	55	308	176, 180, 317	180	242
receipts at Chicago					236	192	161
shipments, Chicago					236	191	160
Pennsylvania	13, 24	70	47, 52	299	294	304, 323, 328	244
shipping routes, Penn- sylvania		73			312	323	246
tonnage of transportation companies	14	71	49	303	313	327	
trade report	30	74		232	317	185	150
Antimonial lead ores	760	650			696		
sulphide of lead, Colorado					712		
silver, Arizona	761				697		
Antimony	xiii	641	7, 387	2, 7, 9	2, 6	7, 10	141
alloys		650					
and iron sulphide					695		
exports		648					
extraction processes		647, 649					
gold associated with	439	642, 646					
imports		651	387				142
in Algeria		645					
Arizona	764				700		
Arkansas	672				703		141
Austria		646					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Antimony in Bohemia		646					
Borneo		649					
California	438, 769	641	387		704, 706		
France		645					
Hungary		646					
Idaho	439				723		
Italy		645					
Japan		649					
Maine	690						
Montana							141
Nevada	438, 772	642			757		141
New Brunswick		644					
New South Wales		648					
North Carolina	716						
Nova Scotia		645					
Portugal		645					
Prussia		645					
Spain		645					
Utah	774	643			796		
Victoria, Australia		646					
Other, Arizona	763				698, 700		
Idaho					722		
Utah	774				796		
ore analysis	438						
grey	672				701, 717		
imports			387				
in Rocky Mountains	439						
shipments.	438		387				
prices.	439	651	388				142
production	xiii, xvi			2, 7	2, 6, 9	7, 10	6, 141
sources	438	641, 644	387		2		141
Apatite	521	775, 803, 805	455		594	596	454
analysis		806					
exports, Canada	521	807					
in Arkansas					701		
Canada	521	803, 805			594	596	454
Connecticut	672				714		
Kentucky	686				735		
Massachusetts	521, 694				743		
New Jersey	521, 707				761		
New York	521, 711				768		
North Carolina mica veins					668		
Pennsylvania	725				783		
production		807	457		594	596	455
Apophyllite		775					
Aquamarine	487		439	596	770		
Aragonite		728					
in California	767				703		
Dakota		777					
Iowa		777					
Wyoming					808		
Arethumite					668		
Argasoid		632		128			
Argentine Republic copper						73	73
gold		319					
silver		319					
Argentite		382					
in Alaska					695		
Arizona	760				696		
Colorado	748				707		
Idaho	770				722		
Maine	687				736, 738		
Montana	754				753		
New Mexico	756				762		
North Carolina	713						
Wyoming					809		
Arizona agate		757					
agate wood		759		596			581
alabaster	762				698		
alum	762			681	698		
alunogen	762				698		
amethyst		751					
anglesite	760, 762				696, 698		
anhydrite	762				698		
antimonial lead ores	760				696		
silver ores	761				697		
antimony and iron sulphide					696		
other	763				698, 700		
sulphide	439				700		
argentite	760				696		
arsenical lead ore					697		
arsenopyrite	760				696		
asbestos	762				698		
asphaltum	762				698		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Arizona atacamite	760				696		
aurichalcite	762				698		
azurite	760				696		
barnhardite	760				696		
barytes	762				698		
berthierite	760				698		
biotite	762						
bismuth	440	654			696, 700		
bitumen	762				698		
bluestone	760				696		
bornite	760				696		
breunerite	762				698		
brognardite	760				696		
building stone	762				698		373, 378
calamine	763				698		
calcite	763				698		
caledonite	763				698		
cerargyrite	760				696		
cerussite	760				696		
cervantite	763				698		
chalcanthite	760, 763				696, 698		
chalcocite	760				696		
chalcopyrite	760				696		
chromate of lead	763						
chrysocolla	760	778			697		
cinnabar	763				698		
coal	37, 763	18	14		699		
coke		157					
copper	216, 221, 761	329, 334, 397	210, 215, 221	112, 116	74, 697	54, 58	60
copperas	763				698		
crednerite	763				699		
crocoite	763				699		
cupola copper smelting		397					
cuprite	761				697		
dechenite	763				699		
desclouzite	763				699		
diamond		733					
diopside		769					
diopase	761				697		
dolomite	761, 763				697, 699		
dufrenoyite					697		
dumortierite						582	
dyscrasite	761				697		
embolite	761				697		
Epsom salt	763				699		
fahlerz	762				698		
feldspar	761						
fire clay	763				699		
fluorspar	761, 763				697, 699		
freieslebenite	761				697		
galena	761				697		
garnet	488, 761, 763	747			697, 699	581	
glauberite	763				699		
gold	172, 182, 763	312	200	104	58, 697, 699	36	49
granite	761				697		
graphite	761				697		
grossularite	488						
gypsum	529, 763	813		623	698		
hausmannite	763				699		
hematite	761, 763				697, 699		
hyalite	761						
iron ore	761, 763	289			697, 699		
itabirite	763				699		
jasper			440				
kaolin	763						
lead		416, 425	258	140	1, 10, 698		80
ores	760, 763				696, 698		
leadhillite	763				699		
leucopyrite	761						
lignite	761, 763				697, 699		
lime					698		
limestone	761, 763				697, 699		373, 378
limonite	761, 763				697, 699		
magnesite	763				699		
magnetic iron ore	761, 763				699		
malachite		777					
manganese ores	762				697, 699		
melaconite	761				697		
miargyrite	761				697		
mica	764	911			699		
mineral waters		979				630	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Arizona							
mirabilite	763						
mispickel	760				696		
molybdenite	762, 764				698, 700		
ocher					697		
opal	764				699		
peridot	492						
phoenicochroite	764				699		
platinum	764	576			699		
polybasite	761				697		
proustite	761				697		
psilomelane	764				699		
pyrargyrite	761				697		
pyrite	761				696		
pyrolusite	762, 764				697, 699		
pyromorphite	764				699		
pyrrhotite	762				697		
quartz	762				697		
salt	550, 763	848	483		699		
sandstone	764				700		374, 378
sapphire	486						
siderite	762				697		
silver	172, 176 760, 762	312	200	104	58, 698 700	36	49
smithsonite	764				700		
sodium sulphate	763				699		
sphalerite	762				698		
stephanite	762				698		
sternbergite	762				698		
stibnite	764				700		
stromeyerite	762				698		
talc	762, 764				698, 700		
tellurium	762			648	698		
tetradymite	440				700		
tetrahedrite	762				698		
thenardite	764				700		
topaz	486						
turquois	493	767			698		
vanadate of copper	764				700		
lead	763				699		
vauquelinite	764				700		
volborthite	764				700		
volgerite	764				700		
wad	762						
willemite	764				700		
wulfenite	762, 764				698, 700		
zinc carbonate					700		
silicate					698		
sulphide	762				698		
Arkansas, agate		757			700		
antimony	672				703		141
apatite					701		
arkansite	671	772					
azurite	671				701		
barite					701		
brick clay					700	558, 565	
brookite	671						
buhrstone		712			701		
cairn gorm	490						
calamine	671				700		
celestite					701		
cerargyrite	670						
chalcedony		757					
chalcopyrite	671				701		
clay	671				700, 702	558, 505	
coal	7, 34, 37	18	11, 15	230, 241	171, 207, 216		147, 174
copper	221, 671				701		
elæolite	496						
fahlerz					701		
fire clay	671				702		
flagging stone					703		
galena	670				700, 702		
gold	670				702		
granite	671				701	537	374, 378
graphite					686		
gypsum	526, 671	809			702		
halite	671				702		
hematite	671				702		
hydrozincite	671				701		
iron ores	671	280	188	39	49, 702		
jamesonite	671				701		
kaolin	671				702		
lead sulphide	670				700		
lignite	670						

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Arkansas, limestone	670				701		373, 378
limonite	671				702		
lithographic stone					701		519
magnetite					702		
malachite	671				702		
manganese ores	671	553	305, 332	181, 184	145, 147,	124, 126	127, 130
					701		
marble	670				701	542	
marcasite					702		
marl	524			619	701		
melaconite					702		
mica					702		
millierite					701		
mineral waters		980	536	715	683	626, 630	522
natural gas					498		
nickel					128, 701	109	
niter	671				702		
novaculite	492, 671		433	589	553, 701	5	460
ocher	671				702		
oilstone (see novaculite)	671						
perovskite					702		
petroleum					702		
phosphate rock			454		701		
pottery's clay	470				701		
pyrites	671				702		
quartz	490, 671				701		
rutile	671				702		
salt	671	843			702		
salt-peter	671				702		
sandstone	672				701		374, 378
schorlomite		742					
serpentine	672				703		
siderite	672				703		
silica					703		
silver					701		
slate	672				525, 703		376, 379
smithsonite	672				703		
sphalerite	672				701, 703		
stibnite	672				703		
strontium sulphate					701		
structural materials				530		522	373, 378
syenite					701		379
talc.					703		
tetrahedrite	671				701		
titanic acid	671				701		
topaz	490						
zinc	672	476			700		88
zincite	672				703		
Arkansite	671	772					
Armstrong county, Pa., coal	72	85	57	323	323	340	257
Arrow points		727, 750,	443	604	556	584	446
		781					
Arsenic	441, 768	656, 959	386		704, 795		
Arsenical ores	689, 760				696, 707,		
					803		
Arsenopyrite		382					
in Arizona	760				696		
Colorado	748				707		
Connecticut	672				714		
Dakota					716		
Georgia	676				721		
Idaho	771				722		
Maine	689				738		
Massachusetts	694				743		
Montana	754				753		
New Hampshire	705				759		
New Jersey	707				761		
New York	711				768		
North Carolina	716				773		
Rhode Island	727						
Utah	773				794		
Vermont	737				798		
Virginia	742				803		
Asbestos	588	913	521	5, 8, 9	5, 7	8, 10	514
in Alabama	669				693		
Alaska					696		
Arizona	762				698		
California	588	1 3	521		703		514
Canada	589	1 3	521				
Colorado		913					
Dakota		913			716		
Delaware	675				719		
Georgia	588, 676	913	521		721		
Idaho					723		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Asbestos in Maryland	588, 692	913			741		
Massachusetts		913			743		
Nevada	588	913					
New Jersey	588, 707	913			761		
New York	588, 708	913			765		
North Carolina	588, 659, 713	913			769, 773		
Pennsylvania	588, 721	913			779		514
Rhode Island					785		
South Carolina	728	913			786		
Texas	734				793		
Utah		913					
Vermont	737				798		
Virginia	588, 738	913			799		
Wyoming	759	913			809		514
production	xv, 588	5, 7, 9	4, 6, 8	5, 8	5, 7, 8	8	6, 514
Asbolite, Missouri	701				752		
Pennsylvania	725				783		
Ashburner, Dr. Charles A., on coal	7		10	234	168	168	
natural gas					474, 476		
Asia, copper production				128		74	74
manganese						142	130
Minor, chrome iron ore		571		177		120	
Asphaltum	605	937		5, 8, 10		513	477
imports						8, 10	479
in Alabama						513	
Arizona	762				698		
California	605, 767	937		5	703	513	477
Colorado		937					477
Illinois	678				726		
Missouri	701				752		
Tennessee	732				791	513	
Texas	734				793	513	477
Trinidad	605						478
Utah					794	513	477
West Virginia	605, 745	937			806		
Wisconsin	747						
Wyoming					809	513	
preparation of	605						477
summary	xv	5, 7, 9	4, 6, 8	5, 8, 10	7, 8	6	4, 6
Assaying, electrolytic	658						
Atacamite, Arizona	760				696		
Atlanta, Ga., structural materials				529		523	
Aurichalcite, Arizona					698		
Aurora, Ill., structural materials						524	
Austin, Tex., structural materials				530		533	
Australia, antimony		646					
bismuth		655					
coal	5		11, 16	235	189		
copper	254	356, 360, 370		128, 131	88, 96	73	74
diamond					569		
gold		319					
iridium		581					
lead		434					
manganese				207			130
platinum		576					
quicksilver	390						
silver		319					
Austria, coal	5, 109	13	11	235	189	208	20
copper		356, 372	242	128	87	73	73
gold		319					
iron ore	109			21	18	28	
lead	323	434, 439	271				
manganese		555				142	130
mining law		1001					
nickel	410						
pig iron	109					29	21
quicksilver	292	496				105	
salt		849					
silver		319					
steel	109			21		29	21
tin ore		618					
zinc		480, 490		159		95	92
Autunite					668		
Aventurine		752					
Axinite	498	765					
Azurite		282		597			
in Arizona	760				696		
Arkansas	671				701		
California	768				704		
Idaho	770				722, 724		
Missouri	701				752		
Nevada	772				756		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Azurite in New Hampshire	705				759		
New Jersey	707				761		
New Mexico	756				762		
North Carolina	716				773		
Pennsylvania	721				779		
Tennessee	730				788		
Utah	773				794		
Wisconsin	745				807		
Wyoming					809		
Baku, petroleum shipments				470	463	479	
Baltimore, Md., bluestone manufacture	297						
coal market					178	181	155
brick		697		567		560	
structural materials				528		526	
terra cotta		700					
Banca tin		594, 622		217			
Bancroft, Thos. B., coal in Ohio				290		294	236
limestone in Ohio				540			
Bangor, Me., structural materials				519			
tin ore	434						
Barite. (<i>See</i> Barytes.)							
Barium carbonate	686				735		
Barnhardt, Arizona	760				696		
North Carolina	716			773			
Barytes	XIV, 580	922	4, 524	5, 7, 705	676, 704	6, 8, 10, 618	4, 513
imports		923		706	676	618	513
in Alabama	669				693		
Arizona	762				698		
Arkansas					701		
California	768				704		
Canada						618	
Connecticut	580, 672	922	524		714		
Dakota					716		
Georgia	676				720		
Illinois	580						513
Iowa	682				731		
Kentucky	580, 686				735		
Maine	580, 689				738		
Massachusetts	694				744		
Michigan	696				747		
Minnesota	697				748		
Missouri	580, 699	922	525	706	676, 750	6, 618	513
Nevada					756		
New Jersey	707				761		
New York	580, 711		525	705	768	6	
North Carolina	580, 660, 713	922	525	705	770		513
Oregon					778		
Pennsylvania	580, 725				783		
Tennessee	580, 730	922			788		
Utah	773				794		
Virginia	580, 738	922	525	705	676, 799	6	513
West Virginia	745				805		
Wisconsin	747				807		
Wyoming					809		
preparation of	580						
prices				706		618	
production	XVI, 580	5, 9, 923	4, 6, 8	5, 7, 9	5, 676	618	4, 6, 513
tariff	581						
uses	581	923					
Basanite		763					
Basic slag as a fertilizer		805	468	627			
Batoum, petroleum shipments				475	462		
Battle Mountain, Nev., antimony	438						
Bauman, D., lead in Colorado			244, 253, 257				
Beaver, Pa., coke district			107	415	417	422	
Beaver county, Pa., bituminous coal			57	324	324	341	358
Beaver Meadow, Pa., coal basin	20	68					
Becker, Geo. F., quicksilver deposits					125		
Bedford county, Pa., bituminous coal			57	324	324	341	258
Belgium coal	5, 109		11	235	189	208	20
coke				435			
copper	251, 256		240				
iron ore	109			21, 100	18	28	22
lead		434, 438					
manganese					154	143	
mining law		998					
pig iron	109		193	21		29	21
steel	109			21	18	29	21
zinc	357	480, 488	280	159		95	
Bell, I. Lowthian, on American iron			192	37		21	

	1882.	1883-'84.	1885.	1890.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Bell, Robert, on Canadian apatite			455				
Bellingham Bay, Wash., coal	96		70	366	368		276
Benjamin, Marcus, on mineral paints uses of quicksilver			524 295	702			
Bernouille, F. A., iron and tungsten al- loys.	432						
Berthierite in Alaska					695		
Arizona					696		
Berthoud, E. L., on Colorado quarries	554						
Beryl	487	617, 738	439, 443	595, 604	556, 559, 576	580, 581	446
in Colorado			439			580	
Connecticut	672	740	439	595	714		
Dakota					717		
Maine	739	723, 739		595			
Massachusetts	694	739		595	744		
New Hampshire	705		439		759		
North Carolina		725, 728, 739		596	668, 770	580	
Pennsylvania		740					
production	487	781	413	604		584	
Bessemer pig iron	109		182	36	13	20	
steel	125	254, 558	180, 187	11, 19	13, 21, 27	12, 21	14, 16
steel rails		255	187	11	10, 14, 27	13	14
steel works	126	255		19			
Bichromate of potassium		572	359	177	133	121	140
Bilboa, Spain, iron ore exports				101			
Billiton tin		594, 622	384	217			122
Birkinbine, John, on blast-furnace prog- ress.		290					
iron ores				39	30		
Birmingham, Ala., structural materials					507	521	
Bischoff, H. A., coal market reports					224	177, 193	
Bismuth	440	654	389		712		
imports		655	389				
in Alaska		655					
Arizona	410	654			696		
Australia		655					
Bolivia		655					
California	768	655			704		
Chile		655					
Colorado	410	654	389		707, 712		
Connecticut	672	654			714		
Cornwall		655					
Germany			389				
Hungary		655					
Idaho			387				
Montana			389				
New Hampshire	705				759		
New York		654					
North Carolina		654					
South Carolina		654					
Texas	434				793		
Utah	440, 773	654			796		
Virginia		654					
ocher					707, 786		
prices		655					
sources		654					
sulphate	771				724		
telluride					700		
uses		655					
Bismuthinite	728, 771				707, 724, 786, 809		
Bitumen in Arizona	762				698, 809		
California	768			5	704	513	477
Illinois	678				726		
Missouri	701				752		
North Carolina	716				773		
Tennessee	732				791		
Texas	734				793		477
Wisconsin	747						
Bituminous coal	33, 130	11	5, 8, 57	224, 227, 314, 317	168	169	145
areas					169	168	146
displacement by natural gas.			85		26	482	367
rock						513	477
Black band ore in Alabama					695		
Kentucky	685				735		
Maryland					742		
North Carolina					772		
Ohio				56	777		
Pennsylvania					783		
West Virginia					805		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Black Hills, Dakota, coal.....			26				
mica.....						614	
tin ore.....		602, 635	370	214	134	144	120
lead (see Graphite).....							
Blair county, Pa., bituminous coal.....		80, 85	57	324	325	342	259
Blake, W. P., on antimony.....		641					
arsenate of cobalt.....			363				
gold production.....	181						
green turquoise.....	493						
nickel.....	399	537					
tin.....		592					
turquoise localities.....	493						
Blanc fixe, manufacture and uses.....		923					
Blast-furnaces.....	120	290		28			
capacity.....		306					
fuels used in.....		292, 304			22		
out-put averages.....		307					
utilization of slag.....	161						
Bloodstone.....		763					
Blossburg, Pa., coal and coke district.....		194	61, 111		419	424	
Blue Hill Bay, Maine, molybdenite.....	446						
wolfram.....	431						
Bluestone (copper sulphate).....	297	951	397	683	520		
(sandstone).....	711				767		370, 376
West Virginia, coke district.....			75, 123			430	
Bog iron ore (see limonite).....							
Bog manganese in Arizona.....	762	550					
Arkansas.....	672				703		
Maine.....		551			738		
New Hampshire.....		551			760		
New York.....	713	551			769		
North Carolina.....		551			774		
Pennsylvania.....	726	551			784		
Rhode Island.....	727				786		
Bohemia antimony.....		646					
Boise City, Idaho, lignite.....	49						
structural materials.....						524	
Bolivia bismuth.....		655					
copper ores, exports.....	250			128	88	73	73
production.....							
gold.....		319					
silver.....		319					
Borate of calcium, California.....	767, 769				706		
Nevada.....	772				756		
Oregon.....	773						
Borax.....	566	859	491	678	4, 6, 8	5	494
analyses.....	573						501, 505
deposits, history.....	566, 571,						495
574.....							
domestic receipts, San Francisco.....	573			679			
eastern markets.....	576						
exports.....	572			679			
imports.....		861		680			
in California.....	566, 767	859	491	678	704		494
Nevada.....	566, 576	859, 861	491	678			494
prices.....	577	859	491	678			494
production.....	XIV,	5, 7, 10,	4, 8, 492	4, 7, 9,	4, 6, 8	5	6, 494
571.....		860		679			
refineries in California.....	570						502
tariff.....	577						494
uses.....	576						
Borneo antimony.....		649					
coal.....			11	235	189		
diamond mines.....					569		
iridium.....		581					
platinum.....		576					
Bornite, Arizona.....	760				696		
Colorado.....	749				707		
Connecticut.....	673				714		
Maine.....	687				736		
Maryland.....	690				739, 741		
Massachusetts.....	694						
Montana.....	754				753		
New Hampshire.....	703				757		
New Mexico.....	756				762, 764		
North Carolina.....	713				770, 773		
Pennsylvania.....	725				783		
Virginia.....	742				803		
Bosnia manganese.....						142	130
Boston, Mass., blue stone manufacture.....	297						
coal market.....	102				176	178	153
structural materials.....				521	509	525	
terra cotta.....		700					
Boulder county, Colo., bismuth ore.....	440						
tellurium.....	447						

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Bowenite	497						
Bower, A. S., on the Bower-Barff process	164						
Bowling Green, Ohio, natural gas			166	489		493	
Bradford county, Pa., coal			57	318	326	342	259
petroleum district.			132	443	440	445	291
Brass consumption					80	64	
exports	346	220	121	79	63	69	
imports	345	219	120	76	60	66	
ore, Arizona	702				698		
Brattleboro, Vt., structural materials						534	
Braunite	737, 762	382	303		696, 798		
Brazil diamond mines					568		
gold		319					
iridium	444						
platinum		576					
Brazilian pebbles				605			
Breunerite, Arizona	762				698		
Brick and tile	xiii,	3, 679	3, 415	3, 566,	3, 534	4, 557	
	457			579			
buildings, value				518	504, 507	516	
burned with oil as fuel		681			540		
clay	458				765	572	
exports		708	426	579	550	571	
imports		704		576	548	571	
industry	xiii	6, 7, 9, 704		566	535, 540	557, 564	
prices		703, 710					
production		695	416	566	535	557	
in Alabama				568	535, 537	557	
Arkansas					535	558	
Baltimore, Md.						560	
California						558	
Colorado					535, 537	558	
Connecticut					535, 537	558	
Dakota						558	
Delaware					535, 537		
District of Columbia	696				535, 537	558	
Florida						558	
Georgia				568	535, 537	558	
Idaho						558	
Illinois	695			568	535, 537	558	
Indiana			416		535, 537	559	
Iowa					535, 538	559	
Kentucky					535, 538	560	
Louisiana				568	536, 538	560	
Maine					536	560	
Maryland				567	536, 538	560	
Massachusetts					536, 538	560	
Michigan					536, 538	560	
Minnesota					536, 538	561	
Mississippi					536	561	
Missouri					536, 538	561	
Nebraska				568	536, 538	561	
New Hampshire					536, 538	561	
New Jersey		696		567	536, 538	561	
New York	458	695, 710		568	536, 539	562	
North Carolina						562	
Ohio	458	696	416	567	536, 539	562	
Pennsylvania	458	696		567	536, 539	563	
Rhode Island					536, 539		
South Carolina						563	
Tennessee					536, 539	563	
Texas				568	536, 537	563	
Vermont						563	
Virginia					536, 539	563	
Washington						564	
West Virginia					536	564	
Wisconsin				568	536, 539	564	
Bridgeport, Conn., structural materials				522		523	
Brimstone (see sulphur)	579		510				
Brine springs, New York	532, 537	830, 831	170, 474	634	765	601	184
Brines in Illinois		842			725		482
Indiana		842			728		482
Kansas	532				732	607	482, 488
Kentucky	532				734		482
Louisiana	532, 687			636	736		482, 488
Michigan	535	828		628	746		482, 483
Missouri		843			752		
New York		939	170, 474	654	765	601	484
North Carolina					773		
Ohio					776	604	482, 488
Pennsylvania					780		
Tennessee					791		482
Texas					792		
West Virginia					804		482, 488

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
British Columbia coal.....			11, 16	235, 367, 369	171	385	
gold and silver.....		314					
India, copper imports.....	251						
North America exports copper.....	250						
Britannia metal.....		632					
Broad Arrow tin mines, Alabama.....	434			214			
Broad Top, Pennsylvania, coke district.....			105		415	420	
Brochantite, Colorado.....					707		
Brogniardite, Arizona.....	760				696		
Broken Arrow coal and coke district, Ala.....			87			212	
Bromine.....		851	486	642	626	613	493
imports.....					627		
in Michigan.....			486	642	626	613	493
Ohio.....		852	487	642	626	613	493
Pennsylvania.....			487	642	626	613	493
West Virginia.....		852	487		626, 804	613	493
manufacture.....		558, 852			648		493
prices.....		852	487	642		613	493
production.....		851	487	642	626	613	6, 493
summary.....		5, 7, 9	4, 6, 9	4, 7, 10	4, 8	5	4
uses.....		852		643	627	613	
Bronze, aluminum.....			390	221		162	115
Bronzite.....		728, 773					
Brookite.....	671	772					
Brooklyn, N. Y., coal trade.....	102						
structural materials.....				523		530	
Brucite.....	707				761		
Buck, Stuart M., on coal in Kanawha Valley, W. Va.....		131					
Burchard, H. C., mint statistics.....		312				38	
Buffalo, N. Y., cement.....							461
coal market.....	102				181	185	155, 157
structural materials.....						530	
Buhrstones.....	477	712	428	581	552	576	456
foreign.....			428	581			
imports.....		713	428	582	552	576	456
in Alabama.....		712					
Arkansas.....		712			701		
California.....	768	712	428		704		
France.....		713	428	532	552		
Georgia.....	675	712			720		
Germany.....				581			
Missouri.....		712					
New York.....	477	712	428	581			456
North Carolina.....		712					
Ohio.....	477, 719	712			776		
Oregon.....	773						
Pennsylvania.....		712	428	581			456
Virginia.....		712					456
sources of supply.....		712	428	581			456
production.....				581	552		456
summary.....		4		4	4	5	3
uses.....	477		428				
Building sand.....		677	404				
stone.....	450	662	396	536	526	516	6, 374
exports.....	452	666	402	555	526	548, 551	
imports.....	452	666	402	555	525		
production.....	xii, xvi,	3, 7, 10,	3, 5, 8	3, 7, 9,	3, 6, 8,	4	3, 6, 373
uses.....	450	662		536	511		
Buildings, value.....				518	504	516	
Burlington, Vt., structural materials.....				520			
Burmah, petroleum.....		232		480		474	
ruby mines.....					572	583	
tin ore.....		623					
Burra Burra copper mines, South Australia.....	254						
Butler co., Pa., bituminous coal.....		85	57		327	343	259
Butte, Mont., mines and reduction works.....	224	374	217	117			
Byssolite.....			428				
Cadmium.....	726				752, 784		
Cahaba, Ala., coal fields.....	36	15	85	236	204	212	173
Cairngorm.....	490						
Calamine in Arizona.....	763				698		
Arkansas.....	671				700		
Connecticut.....	673				714		
Kansas.....	682				732		
Maryland.....	692				741		
Missouri.....	699				750, 753		
New Jersey.....	706				760		
Pennsylvania.....	721				783		
Tennessee.....	730				788		
Virginia.....	738				799		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Calcareous marl, New Jersey	522			619		595	
North Carolina	715			619	772		
Virginia					801		
West Virginia					805		
tufa	711				722, 768, 805		
Calcined plaster		810	461	620	595		465
Calcite		382					
in Alaska	760				696		
Arizona	763				698		
California	767			597	703		
Colorado					707		
Connecticut					714		
Idaho	770				722, 724		
Kentucky					733		
Louisiana					736		
New York	711				768		
Oregon					778		
Utah	773				794, 796		
Washington					803		
Wyoming					808		
Caledonite in Arizona	763				698		
California agate		757			704		
alabaster	768				704		
alum	606	949			705		
andalusite		742					
antimony	438	641	387		2, 701, 706		
aragonite	767				703		
arsenic ores	768				704		
asbestos	588, 768	913	521		703		514
asphaltum	605, 767	938		5	703	513	477
azurite	768				704		
barytes	768				704		
bismuth	768	655					
bitumen	768			5	704	513	477
borate of lime	767, 769				706		
borax	566	859	491	678	704		494
brick clay	767	678, 703			705	558	
buhrstones	768	712	428		704		
calcite	767				703		
carnelian					704		
cassiterite. (<i>See also Tin</i>)	768	767			705		
cement	767	675	409	564	703, 705		463
chalcedony		757					
chalk	768				705		
chiastolite	497						
chrome iron ore	767	569, 572	357	2, 176	2, 132, 703	119	137
chrysocolla	768				705		
cinabar. (<i>See Quicksilver.</i>)							
coal	6, 767	12, 19	11, 15	230, 242	171, 209, 704	171, 202, 225	147, 178
fields	91	21	15				147
imports		20	15	231, 242		202, 225	168
market				242		203	168
cobalt ore	768				705		
copper	216, 226, 769	329, 340	210	112, 118	69, 76, 704	59	60
copperas		952					
corundum	768				705		
diamond	484, 768	730			705		
erubescite	768				705, 738		
erythrite	768		361		705		
feldspar	768		523		705		
fire-brick		704				566, 570	
fluorspar	768				705		
galena	767				703, 705		
garnet	768	747			705		
gaylussite	766, 769						
gold	172, 182	312	200	104	58	36	49
quartz	184 490	763					
granite	453, 767	663		537	514, 703, 705	536, 538	374, 380
graphite	768	915		686	672, 705		
gypsum	529, 769	812		623	602, 704, 706		465
hematite	705, 767						
infusorial earth	480	720		588	554, 705		459
iridium	444	581					
iridosmine	768		222		705		
iron ores	133, 148 767, 769	286	198, 367		705	15	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
California jasper		762					
kaolin		732		573	705		
lead	767	416		140	104, 703		80
lignite	767			704			
limestone and lime	767		412	565	532, 703, 705	555	373, 383
limonite	769				705		
litharge	769				705		
lithographic stone	769	935			705		
magnesite				696	704		
magnetite	767, 769				706		
malachite	769				705		
manganese ores	424, 769	554	305, 349		706	124, 128	127, 131
marble	456, 767		412	545	518, 520, 703, 706	541	375, 382
marl	769						
mercury. (See Quicksilver).							
metallic paint							510
mica	584, 769	911	519		706		
mineral waters		980	537	715	683	626, 630	522
nails			186				
natural gas		236, 243	161		499, 706	509	
nickel	403, 769	539			706		
obsidian	496, 769				706		
ocher	769				706		
onyx	768	757			703		
opal		760					
ozocerite	609						
petroleum	767, 769	218	130, 148	461	438, 452, 704, 706	442, 446	292, 340, 346
production	189	219	150	462	438	4, 442, 444, 446	292, 346
refineries			150				
wells		219	149, 152			464	340, 347
pig iron	129	252	182	18		15	
platinum	442, 769	576			706		
pottery industry		702					
priceite					706		504
pumice-stone	767, 769	721			706		
pyrites	769				706		
pyrolusite	769				706		131
quartz		749, 752, 755.					
quicksilver	387, 391, 393, 767	492, 494, 496	284	160	118	97	95
native	767				704		
prices	393	498	289	162, 164	121		98, 104
production	389, 390	493, 496, 501	285, 288	2, 7, 9, 165	6, 8, 9, 120, 123	98, 100, 103	6, 94
reduction at New Almaden. shipments	396	503, 513					
shipments		500				103	100
rock soap	767, 769				704, 706		
rolled iron	125, 133, 135		185			15	
salt	532, 547, 570, 767	845	480	628	611, 622, 704	597, 605	482, 489
sandstone	767, 769	664			704, 706	545	374, 382
saponite	475, 767, 769				704, 706, 810		
sewer pipe, manufacture						570	
silver	172, 176, 182	312	200	104	59	36	49
slate	457, 769				524, 704, 706		376, 382
sodium carbonate					704, 706		
nitrate	599				706		
sulphate					706		
sphalerite	769				706		
spinel	486						
steel	130, 137		186	18	11	15	12
stibnite	769				704, 706		
strontianite	769				706		
structural materials				535	508	522	
sulphur	578, 769	864		644	706		
syenite	769				706		
talc	767, 769				704, 706		
tellurium	447			648			
terra cotta manufacture						565, 570	
thenardite	769				706		
thinolite	767, 769				704, 706		
tin ore	434, 768	614			136, 785		120
tincal					704		
trona	769				706		
tufa	767, 769				704, 707		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
California tungstate of iron	769				707		
niexite	767, 769				707		
umber	769				707		
wolfram	769				707		
zincblende	769				706		
Calumet and Hecla mine, copper	215, 219	327, 329	210, 213	111	70, 71	52	59
Cambria county, Pa., bituminous coal production.					327	344	260
Camden, N. J., nickel works		537					
Cameron county, Pa., bituminous coal production.		85	57	327	327	345	260
Canada, apatite	521	807	455		594	596	454
arsenic, Del Oro mine		656	386				
asbestos		913	521				514
barytes						618	
chrome iron ore						121	
copper	257	356, 361		128	87, 97	73	
gold		373					
graphite	590	319, 320					
gypsum exports		810	459		603		
iridium		581					
iron ore imports	172	257, 260	189	16, 98	15	88	92
manganese			350	198			130
metallic paint production						619	
mining law		103					
nickel	402					110	125
ocher						618	
petroleum	206	232			456	43, 467	
platinum		577					
pyrites	217	881	506	656			
silver		319					
zircon	487, 657	661, 741		598	559, 576, 772, 810		
Cancrinite		773					
Cannel coal	57				357	215	
Cape May, N. J., smoky quartz		752					
Cape of Good Hope, copper	250	256, 360, 370	228, 232, 242	604	96	73	73
Carbon imports, for fertilizing				607			
used in glass making		970					
Carboniferous ores Alabama	158						
Carbonite, Virginia	742				803		
Carbons	480						
Carll, John F., on natural gas			163		467		
Carnallite					633, 635		
Carnegie Brothers & Co., coke works		181					
iron ore analyses.		267					
Carnelian			444	605	704		
Carondelet, Mo., zinc works	347, 381						
Carrollite, Md.	692				741		
Cassiterite	498	592, 602, 607, 623, 767				153	
analyses						153	
in Alabama	667, 669	767		214	693		
California	768	767			705		
Colorado				214	712		
Connecticut	673				714		
Dakota		767		214	716	153	
Maine	687	767			738		
Massachusetts	694				744		
New Hampshire	705				759		
North Carolina		767			773		
Virginia	738				799, 803		
Wyoming					808		
Castner process for aluminum and sodium manufacture.					651, 653	162	
Casualties in coal mines						255, 299	205
Caswell, Edward A., on lead			246			389	
Catlinite	498	724, 778	443	604	556	83	83
		781				584	446
		728					
Catseye minerals							
Cedar Rapids, Iowa, structural materials						524	
Celestite, Arkansas					701		
Ohio	720				777		
Pennsylvania	725				783		
Cement	459	671	405	556	527	551	461
imports	461, 464	672, 675	407	558	528	552	462
in California	767			564	703, 705		462
magnesia						554	
manufacture	460, 463	672, 674		563	529		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Cement, new developments				564	529	553	
Portland, American, production		671		557	528	552	462
prices		676		559, 564	529	553	
production from natural rock	460	671	405	506	527, 735	551	461
Roseendale, analysis	460						
summary	XII, XVI	4, 7, 10	3, 5, 8	4, 7, 9	4, 6, 8	4, 10	6
tests			408			553	
uses		672					
Central America quicksilver	390					107	
zinc	378						
Center County, Pa., bituminous coal mining statistics.		85	57	321	328	345	260
Cerargyrite		382					
in Arizona	760				696		
Arkansas	760						
Colorado	749				707		
Dakota					716		
Idaho	770				722, 724		
Maine	687				738		
Montana	754	382			753		
New Mexico	756				762		
Utah	773				794		
Wyoming					808		
Cerussite		382					
in Arizona	760				696		
Colorado	749				707		
Dakota					716		
Idaho	770				722, 724		
Illinois	678				726		
Iowa	682				732		
Kansas	682				732		
Massachusetts	694				744		
Missouri	699				750		
Montana		382			754		
Nevada	772				756		
New Mexico	756				762		
New York	711				768		
North Carolina	716				773		
Pennsylvania	721				779		
Tennessee	732				791		
Utah	773				795		
Virginia	738				799		
Washington					804		
Wisconsin	747						
Wyoming					808		
Cervantite in Arizona	763				698		
Idaho	770				722		
Utah	774				796		
Ceylon graphite	592			688	672		
Chalcanthite, Arizona	760, 763				696, 698		
Colorado	753				712		
Chalcedony	491	756		597			
in Arkansas		757					
California		757					
Colorado		757					
Dakota					717		
Illinois		757					
Nevada		757					
New York		756					
North Carolina		757					
Pennsylvania		756					
Rhode Island	727				785		
Texas	734	757			793		
Utah				597			
Wisconsin		757					
Chalcocite		382					
in Arizona	760				696		
Colorado	749				708		
Connecticut	673				715		
Georgia	675				721		
Maine	687				736		
Maryland	690				739		
Minnesota	697				748		
Missouri	701				752		
Montana	754	382			754		
New Mexico	756, 758				763		
North Carolina	713				770		
Pennsylvania	725				783		
Tennessee	730				788		
Texas	735				793		
Virginia	738				799		
Wisconsin	747				807		
Wyoming	758				808		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Chalcopyrite							
in Alabama	669				693	111	
Alaska	760				696		
Arizona	760				696		
Arkansas	671				701		
Canada						111	
Colorado	749				708		
Connecticut	673				715		
Dakota					716		
Georgia	675				720		
Idaho	770				723		
Illinois	678				726		
Maine	687				736		
Massachusetts	694				742, 744		
Maryland	690				739, 741		
Michigan	696				747		
Minnesota	697						
Missouri	699				750		
Montana	754	382			754		
New Hampshire	703				757		
New Jersey	707				761		
New Mexico	756				763		
New York	711				768		
North Carolina	713				770		
Oregon					778		
Pennsylvania	721				779		
Rhode Island	727				785		
South Carolina	728				787		
Tennessee	730				788		
Utah	773				795		
Vermont	736				796, 798		
Virginia	739				799		
Wisconsin	745				807		
Wyoming					808, 810		
Chalk	693, 768	930			705		
Champlain, N. Y., iron mines development				16			
Chance, H. M., on anthracite coal mining		104					
bituminous coal statistics.		78, 82		316			
Chandler, C. F., analysis of Alaska coal			14				
Charcoal pig iron production by States	131	256, 296					
Charleston, S. C., manufactured fertilizers' shipments.		787			591	594	
structural materials						533	
Chart, showing production of copper		328					
gold and silver		317					
pig iron		253					
quicksilver			287	165	123	101	
Chatard, T. M., on corundum and emery		714					
Chateaugay mines, Lake Champlain iron ore production.		272	188	14			35
Chlastolite	497						
Chicago, Ill., anthracite coal				260	236	191	
bessemer steel production					27		
coal market					182	191	160
prices	103				182, 237	192	162
receipts				260	235	191	160
trade	103			260	182, 235	191	160
structural materials				519, 532	508	524	
terra cotta		700					
Chihuahua, Mexico, tin ore deposits	436						
Chile, bismuth		655					
coal	5						
copper	249	356, 360	229, 232	109, 132	87, 92	73	73
gold		363					
manganese		319		206		139	130
silver		319					
China clay (kaolin)	469		424	572	545	572	441
China, coal	5						
iron-ore industry	111						
natural gas		243					
petroleum		232					
quicksilver imports	391					107	
steel	111						
tin ore		623					
Chinaware, imports				571, 577	545	573	413
Chisolm, F. F., on coal mining in Montana				286		168	
production statistics.			10	224		168	
iron in Rocky Mountain division.		281	196		28	33	
lead statistics, Colorado	310						

	1882.	1883-'81	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Chisolm, F. F., New Mexican turquoise	494						
in mineral paints			531				
structural materials			396				
Chlorastrolite	496	774, 781	443	604	556	584	446
Chlorine, manufacture, manganese used in.		556					
Chondrodite		767					
Christy, S. B., on quicksilver reduction		503					
Choctaw coal fields, geology of							208
Chromate of potash imports			359	177	133	121	139
Chrome iron ore	428	3, 572		2, 8	112	119	137
imports			359	177	133	121	139
in Asia Minor		571					120
California	428, 767	3, 5, 72, 569	358	176	132, 703, 705	119	137
Canada						121	
Georgia					721		
Maryland	428, 690	567, 569	358		739, 741		
Massachusetts	694	569			744		
New South Wales						121	
New York	429, 712	569			768		
North Carolina	716	569			773		
Pennsylvania	721	567			779		
Russia	428	571	358				120
Turkey	429	571	358	177			121
Vermont	737				798		
Victoria, Australia						121	
Virginia	742	569			803		
principal supply		572					130
production	XIII, XVI, 429	3, 572	3, 358	2, 8, 177	2, 6, 8, 132	120, 121	2, 6
utilization	429	572	359	178			122
Chromic acid, imports		572	359		133	121	139
Chromium (see Chrome iron ore)							
steel, peculiar properties			359	178			122
Chrysoberyl			443	505, 508, 604	556, 574	584	446
Chrysocolla		728, 736, 781					
Arizona	760	382, 778					
California	768	778			697		
Colorado	753				705		
Lake Superior region		778			712		
Maryland	692				741		
New Jersey	707				761		
New Mexico	756, 758				763		
North Carolina	716				773		
Pennsylvania	725	778			783		
Utah	773				795		
Wyoming	788				808, 810		
Chrysolite	492						
Chrysoprase		760			561		
Cincinnati, Ohio, coal trade	103, 105				376	197, 301	165
ornamental pottery		700					
structural materials				531			
Cinnabar in Arizona	763				698		
California. (See Quicksilver.)							
Colorado	753				713		
Idaho					724		
Nevada	387, 772				756		
Oregon. (See Quicksilver.)							
Utah	774				796		
Cinnamon stone, New Hampshire	705				759		
Citrine		751					
Clarion County, Pa., bituminous coal statistics.	67, 768	85	57		330	346	261
Clarke, F. W., on iridium	444						
mica		906					
Clays	464, 474	678	414	576	547	573	441
Clay, deposits, where found	465	677					
exports		707	426	578	549	573	
for glass potmaking		973, 975					
imports		705	424	576	547	574	443
in Alabama	465	678			690	570	
Arkansas	470, 671				700, 702		
California	767	678			703, 705	570	
Colorado	751				709	572	
Connecticut	469, 673				715		
Delaware	465, 469				718		
District of Columbia	674						
Florida					719		
Georgia	470				722		
Idaho	770				723		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Clay in Illinois	471, 677				725		
Indiana	471, 679				728		
Iowa	467				732		
Kansas	467, 682				732		
Kentucky					734	568	
Louisiana	686				736		
Maine		677					
Maryland	470, 690				739, 740,		
					742		
Massachusetts	465				742, 744		
Michigan					746		
Minnesota					747		
Mississippi	466, 470,				749		
	698						
Missouri	470				750, 753		
Nebraska	467, 471,				755		
	702						
New Jersey	469				760		
New York	469				765		
North Carolina	470, 717			545	773	572	
Ohio	470				775		
Pennsylvania	469				780	572	
Rhode Island	727				785		
South Carolina	470, 728			515	786		
Tennessee	470, 730				788, 791	570	
Texas	733				792		
Utah	773				795		
Vermont	465, 469,				797		
	736						
Virginia	465, 470,	678			803		
	743						
Washington					804		
West Virginia	466				804, 806	569	
Wisconsin	471, 746				806		
Wyoming					810		
manufacture, statistics	471	695, 704					
summary	XIII						
uses	467						
Clearfield, Center district, Pennsylvania, coal and coke, statistics.		85	57	413	332, 415	346	261
Clerc, F. L., on zinc mining	358						
Cleveland, Ohio, bluestone manufacture	297						
coal trade	103					188	159
natural gas						498	
structural materials				531		532	
Stone Company						545	
Clipper Gap, Cal., iron furnace			197				
Coal	1	11	10	224	168	168	145
amount displaced by natural gas			156	490	3, 465	482, 484	368
amount used for coke		151	83	387	391	404	148
analyses, Alabama	37	17, 156	13	239	194, 199,	202	
Alaska			14				
Arkansas	38		15		208	222	176
British Columbia				369			
California					210		
Colorado	39, 44	24, 31, 34	19	245			181, 186
Dakota				251	252		
Georgia						241	
Illinois	51	42, 162					
Indiana	53			396	238		
Indian Territory	51	45		266	244	261	210
Kansas						375	
Kentucky	57				257, 262		
Michigan				280			
Missouri		52			274	287	
Montana	62	53	37	285		291	
Nebraska					277		
Ohio		62, 174					
Oregon	95	66		295	289		
Pennsylvania		177, 180,	99, 104		317		
		183, 190,					
		193					
Tennessee		197, 200		344	354, 357	366	
Texas				348, 350			
Utah	76	203	117	351	359	375	
Virginia	82	205		355	365, 367	380	
Washington	96	206		359	373		
West Virginia	84	208		429		389, 432	
Wyoming	85, 87	101		375		391	
anthracite	7	66, 104	45	295	290	302	242
boring, Virginia	32				236	192	161
consumption, Chicago, Ill.							

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Coal, anthracite, distribution	26	73	52	303	314	322, 331	246
exports		14	13	230	171	172	150
fields, Pennsylvania	4	105	45, 47	297	291	302	243
freight rates, Baltimore, Md.					179	181	155
imports		13	12	230	171	171	150
in Alaska		17					
Colorado	32	32	19	242	708	226, 238	146
Massachusetts					744		
New Mexico	63	31, 57			763	293	146
North Carolina					773		
Pennsylvania	7	66	52	295	779	302	242
Queen Charlotte's Island.	90						
Rhode Island					785		
Virginia		98					
West Virginia					804		
market, Philadelphia, Pa.						174, 180	
mines, Colorado		35		214		238	
mining accidents		127					
Brown's panel system.		130					
cage rests and keeps.		122					
costs						320	
drainage		107					
economy		126					
explosions		126					
fans		125					
fires		127					
hoisting machinery.		121					
methods of opening.		106					
mine railroads.		117					
safety clutches.		122					
lamps.		125					
speed of hoisting.		123					
surveys		126					
Veith's boundary plan.		130					
ventilation		124					
wages	27, 103					330	
waste in mining and preparing.		129					
Pennsylvania, heat producing value.	31						
prices	105	75	16, 55	308	175, 317	180, 328	242
production control				309		175, 185	
Colorado					215	238	
Pennsylvania.	6	12	11	230, 295	290, 294	302, 322	242
Pa., by counties.	24		51	304	292	302	245
Pa., by fields	16		49	300	292	302	244
Pa., by inspectors' districts.	24		49	298		303	
receipts, Chicago, Ill.					236	192	161
St. Louis, Mo.						199	166
shipments	6, 13	70	47	299	291	304	244
Buffalo, N.Y.						187	157
Chicago, Ill.					236	192	161
Pennsylvania	13				294	304, 323, 326, 328	244, 245
Pa., by inspectors' districts.	24		49	298	293	303	
Pa., by railroads.	14	71	85	300	312	304	
trade	102		55	234	172	173, 185	
transportation companies, Pennsylvania.				303		327	
value at mine	1	11	11	295	290	173	245
for consumption.				227	169	174	
bituminous, area	3					169	
exports		14	13	231	172	172	150
imports		14	12	231	172	172	150
mining, Pennsylvania	71	85				337	
labor.							

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Coal, bituminous, prices	105	87	16, 33, 59	232, 321	177, 181, 321	175, 181, 185, 335	
production	34	12	10	229	170	332	148
control						175	
Pennsylvania	6, 67, 72	12, 83	11, 57	321, 340	346, 349	332	252
shipments			58			355	156, 158, 160, 163
trade	105	85	63	232	172	173, 199, 333	151
value	1,	1, 11	10	230	170	332	148
brown. (<i>See</i> Lignite.)							
calorific value	76				237	256	
classification			52	224	315		197
composition	37, 49, 104	17, 39, 89	14	252, 347	351	214, 222, 241, 361	
Cumberland shipments	59, 70	50	33	276	264, 337	282	225
exports	101	13	13	230, 367	171	171	149
fields of the United States	4	14	13	224	169	168	145
freight rates					179	181	
graphitic, Rhode Island					785	361	
imports	98, 101	13	12	230	171	171, 202	149
in Alabama	6, 35, 667	12, 14	11, 13, 85	230, 235	171, 189, 690	171, 208, 213	146, 172
Alaska	760	17	14		696	214	
Arizona	37, 763	18	14		699	216	
Arkansas	5, 34, 670	12, 18	11, 15	230, 241	171, 207, 700	171, 206, 216	147, 174
California	6, 90, 767	12, 19	11, 15	230, 242	171, 209, 704	171, 201, 225	147, 178
Colorado	6, 38, 749	12, 24, 34	11, 18, 22	230, 243	171, 212, 708, 712	206, 226, 235	147, 179
Dakota	49, 754	12, 38, 338	11, 26	230, 250	171, 222, 716	171, 206, 240	147, 234
Florida	675				720		
Georgia	6, 675	12, 39	11, 26	230, 252	171, 223, 720	171, 240	146, 194
Idaho	49, 771	12, 39	11, 26	230, 252	171, 223, 724	171, 206, 241	147
Illinois	6, 34, 49, 678	12, 39	11, 27	230, 253	223, 725	171, 242	146, 195
Indiana	6, 42, 54, 679	12, 43	11, 29	230, 261	171, 237, 727	171, 206, 256	146, 205, 348
Indian Territory	51, 681	12, 45	11, 29	230, 265	171, 244, 730	171, 206, 260	147, 207
Iowa	4, 34, 55, 681	12, 45	11, 30	230, 261, 266	171, 245, 731	171, 262	147, 215
Kansas	5, 683	12, 46	11, 30	230, 268	171, 253, 732	171, 206, 269	147, 217
Kentucky	6, 56, 684	12, 47	11, 32	230, 270	171, 256, 734	171, 206, 276	146, 219
Louisiana	678				739		
Maryland	6, 58, 690	12, 49	11, 33	230, 272	171, 263, 744	206, 280	146, 221
Massachusetts	694				744		
Michigan	4, 17, 695	12, 50	11, 34	230, 279	171, 270, 745	171, 206, 284	146, 220
Minnesota	698						
Mississippi	698						
Missouri	6, 60, 699	12, 51	11, 35	230, 280	171, 272, 750	171, 285	147, 226
Montana	7, 61, 756	12, 52, 55	11, 36, 39	230, 282, 286	171, 275, 754	171, 289	147, 228
Nebraska	4, 702	55		225	171, 276, 755	171, 282, 292	147, 231
Nevada			40				
New Jersey	707				761		
New Mexico	6, 62, 757	12, 56	11, 40	230, 288	171, 278, 764	171, 282, 292	147, 231
New York	712				768		
North Carolina	7, 713	59	41		279, 773		146, 234
North Dakota	754			250	716		147, 234
Ohio	6, 65, 718	12, 59	11, 43	230, 289	171, 281, 775	171, 294, 297	146, 235
Oregon	6, 94, 773	12, 66	11, 45	230, 294	171, 288, 778	171, 206, 301	146, 240
Pennsylvania	4, 7, 12, 67, 722	66, 76, 82	11, 45, 57	226, 295, 300, 314	168, 290, 318, 780	108, 170, 206, 301, 332	146, 241, 252
Rhode Island	6, 727	12, 87	11	225	171, 351, 785	171, 206, 361	
South Carolina	729				787		
Tennessee	6, 34, 72, 730	12, 88	11, 64	230, 341	171, 192, 352, 788	171, 206, 362	146

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Coal, in Texas.....	74, 733	12, 89	11, 67	230, 347	171, 357, 792	171, 208, 367	147, 271
Utah.....	6, 74, 773, 775	12, 89	11, 68	230, 350	171, 359, 795	208, 374	147, 272
Vancouver Island.....	90					385	
Vermont.....	738				798		
Virginia.....	6, 82, 739	12, 90	11, 69	230, 352	171, 360, 799	171, 206, 377	146, 272
Washington.....	6, 95, 775	12, 99	11, 70	230, 357	171, 367, 804	171, 381, 384	147, 275
West Virginia.....	6, 83, 743	12, 90	11, 71	230, 369	171, 373, 804	171, 385	146, 277
Wyoming.....	6, 85, 758	12, 101	11, 71	230, 374	171, 380, 808	171, 390	147, 280
miners' wages, Alabama.....					203		
Indian Territory.....						260	
Michigan.....						285	
Pennsylvania, bitu- minous regions.....						337	
Washington Terri- tory.....	100			363			
Wyoming.....	104			377	382		
mining accidents.....	107	126	27	254	225	255, 299, 387, 389	205
machines, advantages.....		136				253	
methods.....		134				250	
wages.....	43, 95	85		363	186, 232	184, 204, 250, 300	169
oil. (<i>See Petroleum.</i>)							
prices.....	105	87		232, 243	177	184	242
production, foreign, Australia.....	5		11	235	189		
Austria.....	5	13	11	235		28, 208	22
Belgium.....	5, 109		11	235		28, 208	22
Borneo.....			11	235			
British Colum- bia.....			11	235, 367	189	385	
France.....	5, 109	13	11	235	189	28, 206, 208	22
Germany.....	5, 109	13	11	235	189	28, 208	21, 22
Great Britain.....	5	13	11	11, 235	189	32	20, 22
Hungary.....		13	11	235	189	28, 208	22
India.....	5		11	235			
Italy.....	109	13	11	235		28, 208	22
Japan.....	5		11				
Luxembourg.....		13	11		208	28, 208	22
New Zealand.....			11	235	189		
Nova Scotia.....			11	235	189		
Russia.....	5, 109	13	11	235	189	28, 208	22
Spain.....	5, 109	13	11	235	189	28, 208	22
Sweden.....	5, 109	13	11	225	189	28, 208	22
Vancouver Is- land.....	5					385	
of United States com- pared with other countries.....	5			235	17	28, 208	22
semi-bituminous, Pennsylvania.....					780		
sieve meshes, sizes.....					318		248
statistics, methods of collecting.....						168	
strikes.....	102	85			186	205	
summary.....	xr	1	1	2	2	3	3, 6
tariff.....	783	13	12	230	171	171	149
trade in Alabama.....				237	203		
Baltimore, Md.....	103				178	181	155
Boston, Mass.....	102				176	178	153
Buffalo, N. Y.....	102, 106			260	181	185	157
Burlington, Iowa.....						200	
Chicago, Ill.....	103, 106				182, 237	192	162
Cincinnati, Ohio.....	103, 106				180, 376	182, 197	165
Cleveland, Ohio.....	103					188	159
Cumberland, Md.....			33		268		
Davenport, Iowa.....					184	200	
Detroit, Mich.....					181	190	
Dubuque, Iowa.....					184	200	
Duluth, Minn.....	103					176, 195	164
Erie, Pa.....	103					188	158
Fargo, N. Dak.....					184		
Indian Territory.....						260	
Indianapolis, Ind.....					184		
Iowa.....						262	
Joliet, Ill.....					184		
Kansas City, Mo.....	103				185	200	166
Kentucky.....						279	
Louisville, Ky.....	103, 106				180	182, 197	165
Michigan.....						284	

	1882.	1883-'81	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Coal trade in Milwaukee, Wis.	103					193	162
Minneapolis, Minn.						196	164
Missouri						199, 207	
Mobile, Ala.	103					201	167
New Mexico						293	
New Orleans, La.	103, 106				179	182, 201	168
New York City	102	75		308	176	179	151
Ohio				290	285	297, 300	
Pacific coast						177	
Philadelphia					177	180	153
Pittsburg, Pa.	106	87			179	182	156
St. Louis, Mo.	103, 106				185	198	166
St. Paul, Minn.					183	196	164
San Francisco, Cal.	94, 106		15	242		204	169
Tennessee					357	177	
Texas					358		
Toledo, Ohio.	103, 106					189	169
Utah						376	
Washington						384	
value at mine	2, 89		28		232	4, 170	148
washing		186		438			
world's product	108	257	11	235	18, 189	28, 208	22
Cobalt.	421	544	361	174	130	108, 620	121
domestic manufactures	421						
earthy			362			752, 783	
extraction from ores		547					
in California					705		
Colorado	421, 753	544			713		
Connecticut	674	544			716		
Germany			364				
Great Britain		539	364				
Hungary			365				
Maryland	692	544			741		
Missouri	421, 701	545	362		753		124
Nevada		545	361	171	756	108	124
New Mexico		545					
Pennsylvania		546					124
Sweden	405						
ore analyses		545	362				
imports		547					
oxide			364	174		2, 108,	124
exports					131	620	125
imports	422	547	364	175	131	620	124
Nevada						621	
prices				174			
production	423	546	363	174	7, 130	2, 620	6, 124
value	423	549	364	175		2, 620	7, 124
prices	422	549	364	174	131	621	
pyrites, Maryland					741		
sources	421	544		174			
summary	XIII	3, 7, 9	3, 6, 8	2, 7, 10	2, 8	2	2
uses	423	549	365, 545				
Cobaltite	701	773	361		752		
Cocalco stone			428	581		576	
Coke	98	144	74	378	383	395	
analyses, Alabama.		156		391			
Colorado		158					
Illinois		162					
Indiana			396	396	399		
Indian Territory		164			400	261	
Kentucky		166		398	402	411	
Ohio		172					
Pennsylvania		178, 185,	103, 106,		413	419	
187, 189		109					
Tennessee		197, 200		344, 421			
Utah		203	117	423			
Virginia							
Washington						426	
West Virginia	208		121	428	424, 426,	429, 432,	
428					428	439	
chemical and physical qualities					396		
consumption in France					435		
districts, Ohio			94	406	407	413	
Pennsylvania		175	96	408	409	414	
Tennessee		197	112	418, 420		427	
West Virginia		207	120	424, 428	422	427	
establishments by States	98	149	77	381	386	397	
exports			85	389	434	405	
from natural gas				501			
imports			84	388	393, 435	204, 405	
in Alabama		145, 154	75, 77	378, 389	394	395, 406	
Arizona		157					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Coke in Belgium				135			
Colorado	98	160	87	378, 392	395	395, 407	
France				435			
Georgia	98	160	75, 77	378, 393	397	395, 408	
Great Britain				430			
Illinois	98	163	77, 84	378, 394	398	395, 408	
Indiana	98		77, 84, 90	378, 395	398	395, 409	
Iowa		164		398			
Indian Territory		164	74, 90	378, 397		395, 409	
Kansas		165	77, 84, 91	378, 398	401	395, 410	
Kentucky		166	77, 84, 91	378, 398	401	395, 410	
Missouri				401	405	395, 411	
Montana		168	77, 92	378, 402	405	395, 412	
New Mexico		170	77, 93	378, 402	406	395, 412	
Nova Scotia				436	435		
Ohio	98	171	75, 77, 93	378, 403	407	395, 413	
Pennsylvania	72, 98	175, 196	77, 96	378, 421	383, 409	375, 414	
Tennessee	98	196	77, 111	342, 378,	352, 383,	395, 425	
				417	420		
Texas	98			378, 421	421	425	
Utah		202	77, 116	378, 422		441	
Virginia	98, 742	204	77, 84,	355, 378,	383, 421	395, 425	
			117	422			
Washington		206	77, 120	378, 423	383, 422	395, 426	
West Virginia	98	207	77, 120	374, 378,	383, 422	395, 427	
				424			
Wisconsin						395, 411	
manufacture, amount of coal used,	98	151	83	387	391	404	
cost, Flat Top region,						438	
West Virginia,							
percentage yield of	100	154	84	387	392	405	
coal.							
market	99					198, 403	
ovens building		150	79	383	388	400	
Flat Top region, West Vir-						435	
ginia.							
number		150	78	382	387	398	
prices		152	81	385	390	402	
Chicago, Ill.						192	
Connellsville, Pa.	99				412	416	
Pittsburg, Pa.						182	
production	98	147, 152		378, 384	385, 388	395	
by States and Territories	98	152, 157,	80, 97,	384	383	396, 406,	
		196	101, 105,			415, 421,	
			111			428	
in Aix la Chapelle					434		
of the world					434		
receipts, Pittsburg, Pa.						183	
St. Louis, Mo.						199	166
Soldenhof ovens, West Virginia		143					
southern, analyses,					403	411	
resources				37			
summary		1	1	3	3	4	
value	98	153	81	385	390	402	
Coking coals, where found		144					
in Belgium				435			
Europe				430			
Germany					432		
the United States	98					396	
processes						436	
Colombia, gold		319					
petroleum						474	
platinum		567				165	
silver		319					
Colophonite		747					
Colorado, agate	491	757					
alabandite					712		
alaskaite	748				707		
altaite	748				707		
alum	606	949					
amazon stone	495	724					
amethyst	491						
anglesite	748				707		
anthracite	749			245	708	238	146
antimonial sulphide of lead					712		
argentite	748				707		
arsenical fahlerz					712		
arsenopyrite	748				707		
asbestos		913					
asphaltum	605	937					
aventurine quartz		752					
beryl			439			580	
bismite					707		
bismuth	440	654	689		707, 712		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Colorado, bismuthinite	121				707		
blast furnaces	753				712		
bluestone	749				707		
bornite					535, 537	558	
brick production					707		
brochantite							
cairngorm	490						
calcite					707		
casalite					708		
cassiterite				214	712		
cement		674		564	601		462
cerargyrite	749				707		
cerussite	749				707		
chalcantite	753				712		
chalcedony		757					
chalcocite	749				708		
chalcopyrite	749				708		
chrysocolla	753				712		
chrysoprase		760					
cinnabar	753				713		
clay	751	701			709		
coal	6, 38, 749	12, 24, 158	11, 18, 75, 83	230, 243	11, 171, 212	226	147, 179
Coal and Iron Company:							
coal production	144			247	214	234	
coke ovens		158					
iron and steel production	147	284					
iron-ore mines		281					
coal fields, area	38				219		
mines	39	26, 30, 34	22		221		
miners' wages	103			250	217	237	
production	44, 48	37	24	2, 230, 243	215, 219	171, 235	179
value at mines	48	38	11, 26	226, 236	171, 212	236	179
cobalt	753	544			713		
coke	48, 98	152, 157	77	378, 399	383, 395	395, 407	
establishments		149	77	381	386	397	
manufacture, coal used		151	83	387	391	404	
ovens		150	79	382	387	400	
production		152, 160	80	393	389	400, 407	
value		153	81	385	390	402	
copper	216, 227, 749, 752	329, 341	210	112	69, 708, 712	54	60
corundum					713		
cryolite	608	954					
dechenite	449						
desclouizite	449						
embolite	750				709		
emery					713		
enargite	750				709		
fahlerz, arsenical					712		
fire brick	472, 750	701		570	541, 709	565	
fluorite	587, 753				713		
gahnite		737					
galena	750				709		
garnet	188			596			
gold	172, 176, 750	312	200	105	59, 709	36	49
granite	454			538	515		374, 383
graphite	590, 753			686	713		
gypsum	528, 753	812		622	601, 710, 713		465, 466
hematite	751				710, 713		39
hessite	751				710		
idocrase		767					
infusorial earth					713		
iron	129, 144, 751	252, 281	182	18	52, 710	15, 33	10, 17
ores	751	279, 283			52, 710	33	24, 35
pyrites	751				711		
jasper	492	760					
jet	497	780					
kaolin						572	
lead	310, 748, 751	412, 416, 419	250	140, 144	105, 712	87	80
smelting works, list						87	
lignite	43, 749				708		
limestone					710		373, 384
magnetite	751, 753				710, 713		
manganese ores					144, 712		127, 131
marble	753			544	518, 707, 713		385
massicot	751				710		
metallic paint							510

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Colorado, mica	583, 753	911	518		713		
mineral waters		980		715	683	626, 630	522
mispickel	748				707		
molybdenite	753				713		
moss agate	491				711		
natural gas			161		498, 713		
niccolite	752				713		
nickel ore	404	539					
obsidian		772					
ocher							508
oil shales					713		
onyx		757					
opal		760					
peacock ore	749				707		
peridot	492						
petroleum	211	216			438, 455, 710, 713	442, 464	292, 332, 339
petzite				648			
phenacite	487	724, 740			710	580	
pitchblende	752				712		
plaster of Paris	529						465
polybasite	751				710		
potteries		702					
precious stones		724				580	
proustite	751				710		
pyrargyrite	751				710		
pyrites	498, 751				707, 711		
pyromorphite	752				711		
pyrrhotite	454, 490, 752	752			711		
quartz	752	755		596	711		
quicksilver	387						
rose quartz		753					
ruby silver	751						
salt	541	843					
sandstone	451, 752			535	521, 711	544	374, 383
sapphire	485						
sardonyx		757					
schirmerite	752				711		
serpentine	753				713		
silicified wood	492	758	443		556, 711		
silver ores	172, 182, 748	312, 315	200	165	56, 707 711 524		49
slate					713		
smaltite	753	544			714		
sphaeroiderite	753				711, 714		
sphalerite	752						
spiegeleisen, production		263					
steel	120, 137		184, 186	18, 32	11	15	
stephanite	752				712		
stromeyerite					712		
structural materials				585			373, 383
sylvanite	752				712		
tellurium	447, 748			648	707, 712		
tennantite	752				712		
tetrahedrite	752				712		
tin ore	434				712		
topaz	486, 490	724, 737		696	712	580	
turquoise						582	
uraninite	448, 752						
vanadium	449						
zirconite		741			712		
Columbite in Dakota		618			717	151	
North Carolina					668		
Connecticut					714		
agate	672	756			714		
albite							
amethyst		750					
apatite	672				714		
arsenopyrite	672				714		
barytes	580, 672	922	524	705	714		
beryl	672	740		595	714		
bismuth	672	654			714		
bornite	673				714		
brick					535, 537	558	
building stone	672		397	522, 537	513, 714	536	374, 385
calamine	673				714		
calcite					714		
cassiterite	673				714		
cement works		672					
chalcocite	673				715		
chalcopyrite					715		
chrysoberyl		736					
clay	673				715		
cobalt ore	674	544			716		

	1882.	1883-'81	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Connecticut copper, native	673				715		
ores					714		
refineries	218						
copperas	607						
corundum, emery	673				715		
dolomite					714		
emerald		739					
epidote		766					
feldspar	672	933			714		
fire brick						566	
flagging stone	672				714		
galena	673				715		
garnet	673		439		715		
granite	672			537	513, 714	536	374, 385
graphite	673				715		
hematite					714		40
iolite		743					
iron	125, 133, 673	252	182	23, 42	715	14	10, 17
ores	120, 672	263, 271, 728		14	42, 716		24, 35
kaolinite	469						
kyanite		748					
lime			410		532	555	
limestone	673		411		715		373, 385
malachite	673				715		
marble	672				714		
manganese			342				
mica		908			714		
mineral waters		980	537	716	683	626, 630	522
mispickel					714		
molybdenite	673				715		
nickel ores	402, 673	539					
pitchblende	674				716		
phosphate of lime					714		
precious stones				595			
pyrites	673				715		
quartz	490, 674				714		
rhodonite		766					
rutile	674	765			716		
sandstone	457, 672			522	521, 714		374, 385
smaltite	674				716		
sphalerite					716		
spodumene	488						
steel			186	17	11	14	
structural materials			397	522		523	374, 385
staurolite		743					
talc	674				716		
tin ore	673				714		
topaz	674				716		
trap rock	672				714		
uraninite	674				716		
wolfram	431	574			716		
zinc	673						
ores	674				716		
zircon		661					
Connellsville, Pa., coke	99	167	74, 97	379	410	415	
Cook, George H., New Jersey iron ore statistics	117						
Cookite				595			
Coos bay, Oregon, coal field	94		45				
Coosa, Alabama, coal fields			87	236		212	173
Copper	213	322, 629	208	109	66	43	56
alloys							
carbonate, Arizona	761	777			696		
Arkansas					701		
California	769				704		
Connecticut					715		
Dakota					717		
Idaho	770, 772				772		
Maryland	264				740, 742		
Missouri					752		
Montana					754		
Nevada	772				756		
New Hampshire					758		
New Jersey					761		
New Mexico					762, 764		
North Carolina					773		
Pennsylvania					779, 782		
South Carolina					787		
Tennessee					788, 791		
Utah	773				794		
Vermont	736				797		
Virginia					801		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Copper, carbonate, Wisconsin	746				807		
Wyoming					809		
consumption			323, 324	123	80	64	
exports	242, 767	346	219	121	78, 92, 738, 801	63	67
imports							
Australia	255	371					
Canada		373					
Chile			234	132	92		
Germany		369	240				
Great Britain		358, 362	234	132	89, 92	74, 77	74
Austria	244	344	217	118, 131	76	60	60
France		373					
Germany		372		139		50, 76	77
Great Britain		370	240				
in Africa		357, 361		130	89	50, 74	76
Alabama	231	355	229, 242	129, 139	88	74	73
Alaska					696		
Argentine Republic				128		73	73
Arizona	221, 761	334	215, 221	110	74, 697	58	60
Arkansas	671				702		
Asia				128		73	74
Australia	254	256, 360, 370		139		73	74
Austria			242	128		73	73
Belgium	256						
Bolivia					88	73	73
California	226, 767	340	210	111, 118	76, 703	59	60
Canada	257					73	73
Chile	252			128, 132		73	73
Colorado	227, 749	329, 341	210	112	69, 708	54	60
Connecticut	752				712		
Dakota	673				715		
France		343			716		
Georgia	256	371	241	138		77	77
Germany	231, 675				721		
Great Britain	255	368	238	128, 135	87	48, 73	73
Idaho	245	356	230	128	87	74	73
Illinois	229	342	210	112	69	54	60
Indiana	678				726		
Indian Territory	680				729		
Italy	681				730		
Japan		356	228	128	87	73	73
Maine		356	229	128	88	73	74
Maryland	230, 687		210	112	69, 736		60
Massachusetts	231, 690, 692				741		
Michigan	231, 694				744		
Minnesota	695	325, 331	210	113	745, 747	52	
Missouri	697		214		748		
Montana	230, 699	342	210	112	69	54	60
Nevada	224, 754, 756	336	215	111, 117	74, 754	2, 57	60
New Hampshire	230	342	210	112	69	54	60
New Jersey	230, 703		210	112	69, 759	54	60
Newfoundland	231, 707				761		
New Mexico	257	356, 361, 373		128	87	73	73
New York	225, 756	340	210	111	76, 763	54, 59	60
North Carolina	711						
Norway and Sweden	231, 713, 716				76, 773		
Pennsylvania	721, 724, 726				783		
Peru			233	128	88	73	73
Portugal	254	367	237	128	93	73	73
Russia	257		241	128	87	73	73
South America			233	128	88	73	73
South Carolina	729						
Spain	253	356, 364	234	128, 133	93	73	73
Tennessee	231, 730, 732				788		
Texas	735	342					
Utah		342	210	112	795	59	60
Vermont	231, 736	343	210	112	68, 796, 803		60
Virginia				653	803		
Wisconsin	231, 738, 741						
Wyoming	745				807		
manufacture, cost of	229, 758	342	710	112	76, 810	59	60
market	219	331	212	114	71	56	56, 62
list of works						64	
	232	348	225	125, 127	84	70	69

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Copper metallurgy of.....	257, 270, 627	374, 397, 401	211				
nickel.....	673				715, 753		
prices.....	232, 241	348, 354	225	126	84	43, 48, 67	70
principal foreign producers.....	245	355	227	128	87	73	73
production.....	xii, 215 217, 649	2, 327, 423	2, 210, 228, 235	1, 111, 113, 128	68, 71, 88	1, 47, 52, 73	6, 74
pyrites.....	669, 760, 770				693, 720, 754	52	60
smeltingfurnaces, Arizona.....	225, 257, 262	374, 391, 401	211			58	
refineries.....	217, 649	330		118			60
Société des Métaux.....						45	
stocks.....	232	348	225	127	84	50	
sulphate.....	763	951		683	698, 793		
trade.....	213	372	208	109	66	71	
value.....		351		1	85	1, 73	
Copperas.....	xv, 607, 720	5, 952		5, 684	777		
imports.....		953		685			
in Arizona.....	763				698		
California.....		952					
uses.....	607	952		684			
Coquina stone, Florida.....	675				719		
Coral imports.....			444	605	573		
Cornwall, England, bismuth tin mines.....		655 594, 615 593, 615					154
ore.....	436						17
Pennsylvania, iron ore mines.....			188	15			28
Corundum.....	476	714, 733	429	585	553	577	457
in Alabama.....	669				693		
California.....	768				705		
Colorado.....					713		
Connecticut.....	673				715		
Dakota.....					716		
Delaware.....	477						
Georgia.....	477, 676	715, 735		585	721	577	457
Maryland.....					741		
Massachusetts.....	476, 694			585	742		457
Nevada.....		735					
New York.....	476				705		457
North Carolina.....	477, 660, 714	715, 717 733		585	770, 773	577	457
Pennsylvania.....	477, 722				780		
Wyoming.....					810		
production.....	xiv, 477		8	4, 585	6, 553	5, 577	6, 457
Covellite.....	669, 676				693, 721		
Cranberry iron ore mine.....		277	188	14, 16		17	
Crednerite.....	763				699		
Crested Butte, Colorado, coal.....	42		88	392		234	
Crimora, Virginia, manganese mine.....		551	304, 313, 315	181, 195	151	132	136
Cripple Creek iron ore.....				78			
Crocidolite.....		775			563, 575		
Crocoite.....	763				699		
Cross, C. Whitman, on phenacite.....			440				
Cryolite.....	608	954		682, 692	650		473
Cuba, iron ore.....		260		16, 98	56	18	
manganese.....					154	137	130
Cubanite, Utah.....	773						
Cumberland coal.....		49		274	337	280	225
Cummings, U., on natural cement.....						516	461
Cyanite.....		382			563, 785		
Dactolite.....		774					
Dakotas the, antimony ore.....					717		
aragonite.....		777					
arsenical pyrites.....					716		
asbestos.....		913			716		
barite.....					716		
beryl.....					717		
brick production.....						558	
cassiterite.....		767		214	716	153	
catlinite.....		779					
cement.....							462
cerargyrite.....					716		
cerussite.....					716		
chalcodony.....					717		
chalcopyrite.....					717		
coal.....	49, 754	12, 38	11, 26	230, 250	171, 223, 716	171, 209, 240	147, 234
columbite.....					717	151	
copper.....		343			716		
pyrites.....					716		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Dakotas the, corundum					716		
emery					716		
feldspar					717		
galena	754				716		
garnet					717		
gold	172, 179, 754	312	200	104	716	36	49
granite							374, 428
graphite					718		
gypsum	538, 754	812		622	717		465
hematite					717		
iron ores	147, 754	285			717	35	
jamesonite					717		
jasper					717		
lead				140	110, 716		80
limestone					717		
lithographic stone					718		
malachite					717		
manganese					718		
marble					519, 717		
mica					717		
mineral waters	533, 754	604, 909				614	
natural gas		980				630	
nickel ore		236, 243	161, 168		718	510	
petrified wood					718	109	
pyrites	754				717		
quartz			440		718		
ruby					718		
salt	541						
sandstone	451				717		374, 429
silver	172, 176, 178	312	200	104	58, 717	36	49
slate		603			718		
sphalerite					717		
stibnite					717		
structural materials	451				508		374, 428
talc					718		
tantalite, analysis						151	
tin ore	434	602, 612, 635	370	214	134, 716	145	120
tourmaline					718		
uranium					718		
whetstone					718		
wolfram					718		
zincblende					717		
Dallas, Tex., structural materials						534	
Danburite	489	748					
Davis, Herbert J., on pyrites			501				
Day, David T., on bromine		851	486				
chromium	423	567	357	176			
cobalt		544	361				
feldspar		933					
fertilizers		783, 787, 815	445				
lodine		854	488				
manganese	424	550					
sulphur		864					
tungsten	431	574	366				
zirconium		661	393				
Day, William C., on feldspar			523	701			
potassium salts					628		
sodium salts					651		
structural materials				517	503	516	373
sulphur			494	644	604		
Dechenite	449, 763				699		
Delaware, amber	675	780			719		
asbestos	675				719		
blue rock	674				718		
bog-iron ore	674				719		
brick production					535		
clay	469, 674				718		
corundum	477						
feldspar	674	933			718		
fluorspar	587						
granite							384, 386
greensand marl	674				718		
hematite					719		40
iron	111, 120, 133	276	184	18, 23	11	14	
kaolinite	469, 674				718		
kyanite		748					
limestone	674				718		
limonite	674				719		
marls	522, 674				719		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Delaware, mineral waters		981				630	
porcelain clay					718		
quartzite					719		
serpentine	675				719		
steel						14	12
structural materials				526			381, 386
succinite	675				719		
Delawarite		760					
Del Oro, Canada, arsenic mine		656	386				
Denver, Colo., cement	462	674		561			462
structural materials				535			
Desclozite	449, 763				699		
Des Moines, Iowa, structural materials				534		525	
Detroit, Ariz., copper furnaces		405, 407					
Mich., coal market					181	190	
structural materials				531		527	
Diamond	484	728	438, 443	598	556, 563	580	446
carat, South African					565		
uniform value					571		
weight			443				
cutting				599	570		
exports South African					567		
imports			444	605	558, 569		
in Arizona		733					
California	481, 768	730, 732			705		
Georgia	484, 676				721	580	
Idaho	484	732					
Indiana					729		
Kentucky				599	558	580	
Maine		730					
Montana		733					
North Carolina	484, 716	729		598	773		
Oregon	484						
Virginia	484	728					
Wisconsin		732					
minerals associated with		732		600			
mines, Australia					569		
Borneo					569		
Brazil					568		
India					569		
South Africa					563		
production		781		604	565	584	
Diaspore		738					
Diatomaceous earth	479	720	433	4, 587	705, 738	6, 578	5, 6, 459
Diopside	496	769, 781	443	604	556	584	446
Diopside, Arizona	761				697		
District of Columbia, brick clay		696			585, 537,	558	
fertilizers			469		719		
gneiss					719		
gold					719		
iron and steel	120, 125,			18	11		
135							
lime production						555	
mica schists					719		
mineral waters		981				630	
quartz					719		
structural materi- als				528			
terra-cotta clay					719		
Divining rod	525, 610						
Dolomite	761, 763				697, 699,		
Dolomitic marble, Wyoming					724, 734		
Domeykite, Michigan	696				808		
Douglas, James, jr., metallurgy of copper	257				747		
Drain pipe		397					
Drain tile		694					
production in Illinois		694	421	575	545		
Indiana		700		575	546		
New Jersey		700		575	547		
Ohio		700		575			
Pennsylvania		700					
Drums, coal-mining, Pennsylvania		122					
Dudley, Wm. L., on iridium		581					
Dufrenite, Virginia					803		
West Virginia					806		
Dufrenoy'site, Arizona	745				697		
Idaho	770				722		
Duluth, Minn., coal trade	103					176, 195	164
Dumortierite						582	
Dyserasite, Arizona	1				697		
Eames' graphic process for iron				686			

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Earthenware and china		686, 698, 704	425, 427	571, 577, 580	545, 551	572	443
Egleston, Thomas, on tellurium in copper				648			
Egyptian petroleum				478			
Elaolite	496	770, 773					
Elba iron ore				101			
Eldridge, Geo. H., on coal in Dakota				250			
Electrolysis in metallurgy of copper	627						
Electroplating with iridium	444						
Elizabeth, N. J., structural materials				525			
Embolite	750, 761				679, 709		
Emerald	487	738, 781	437, 443	565, 604	556	580, 584	446
Connecticut		739					
Maine		739					
North Carolina	487, 500	725, 734, 739			770	580	
Emery	476	714, 719	429	586			457
exports		719	432	586	554	578	
imports	476	719	432	586	554	577	457
in Alabama	669				693		
Colorado					713		
Connecticut	673				715		
Dakota					716		
Georgia	676				721		
Maryland	692				741		
Massachusetts	694				742		
New York					765		
North Carolina	714				586	770, 773	
Pennsylvania					780		
Wyoming					810		
mines, Naxos			431				
Employés in mines						254, 257, 279	
Enargite	750	382			709		
Encaustic tile		692, 699					
Englehardt, Dr., tables in regard to salt brines.						602	
Enstatite		728, 773					
Epidote	492	382, 766				581	
Epsom salt	686, 732, 763	766			735, 810		158
Erie, Pa., coal trade	103					188	158
Erubescite,		382					
in California	786				705		
Idaho	771				724		
New Jersey	708				761		
Utah	773				795		
Erythrite	768		361		705		
Esmeralda, Nev., copper company salt deposits	230 545						
Esopus stone			428	581			
Essonite	488	746					
Etowah region, Georgia manganese ores.		552					
Euclase		740					
Eureka, Nev., lead district	309						
Europe, copper production			228	128	87	74	78
Euxenite, in North Carolina					668		
Exports, antimony		649					
apatite, Canada		807					
asbestos, manufactured		913	522				
borax	572			679			
brass	251	347	220	121	79	63	69
brick		708	426	579	550	571, 575	
building stone	452	666	402	555	527	551	
calced plaster			461				
cement				579	534	557	
chalk		932					
chrome iron ore		572	360				
clay		707	426	578	549		
coal	101	14	13	230	171	172	149
cobalt oxide					131		
coke			85	389	393	405	
copper	242	346	219	122	79, 92	62	67
Australia		371					
Canada		373					
Chile	252	363	234	132			
Germany	256	369					
Great Britain	246, 251	357, 362	234	129		74, 77	74, 77
Mexico		373					
New Foundland		373					
earthenware			427	580	551	572	443
emery		720	432	586	554	578	
fertilizers		825	473				
fire brick		709	427	579		571	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Exports, glass			556				
gold	181	321	207	108	62, 64		
graphite		916					
grindstones		713					
gypsum		810			603		
iron	140						
lead	323	433	260, 265	150	111	90	86
lime		669	411	566	534	557	462*
manganese		557					
marble		666	404	505	526	551	
mica		912					
mineral waters		987	543	721	682	624	523
nickel		543	298	171	127	109	126
petroleum		328				452	301
Canadian						472	
Russian				474		479	
phosphates			473	608			
platinum		578	369	223	142	167	144
pyrites	254	358, 364					
quicksilver	391	500	294		124	104	108
salt		50	484	641	625	610	490
silver		321		108	62	40	
slate		667	400	551	523	549	
steel	140						
stoneware				580	551	572	444
tin	436	618, 640	384	216	136	157	122
zinc	350	477	274	157	115	94	90
whetstone				593			
Fahlerz	762				712		
in Arizona					698		
Arkansas					701		
Idaho	770				723		
Montana					755		
Mexico	757				764		
Utah	774				796		
Fall River, Mass., structural materials				521			
Fargo, Dak., structural materials					508		
Feldspar		933	523	595, 701	5, 8	6	6
imports		934					
in Arizona	761						
California	768		523		705		
Connecticut	672	933			714		
Dakota					717		
Delaware	674	933			718		
Maine	689	933			737		
Massachusetts	694	933			744		
Missouri			523				
New Hampshire	705				759		
New York	708	933			765		
North Carolina	717			701	773		
Pennsylvania	722, 724		523	701	780, 782		
South Carolina	728				787		
Texas	735				793		
Vermont	737				798		
Virginia	742				803		
Wyoming					810		
production		5, 933	4, 523	5, 701	5, 8	6	
Ferro-aluminum			391	221	140	161	
Ferro-manganese	424	559, 563	306	17	146	125	11
Fertilizers	504	4, 783	445	606	580	586	449
analyses	510	821	471		593		
apatite	521	805			594	596	
basic slag		805	468	627			
bone				607			
commercial	531			611	592	593	
exports		826	473				
foreign production		803					
guano				607	583	591	451
gypsum		809		607			465
imports		804		650			450
manufactured	520, 531	787, 815	465	623	590	593	
marls	522	808	464	607	592	595	454
phosphate rock	504	783	445	607	580	586	449
phosphates, imports		804	455	607	583	591	450
phosphoric acid from iron slag		805		627			
prices			447	611	580, 592	586	
raw materials for				607			
Fibrous talc							6, 476
Findlay, Ohio, natural gas				507	482	484, 491	
Finland tin ore		593					
Fire brick		683, 697,	418	568	540	565	
		705					
exports		709		579	550	571	444
imports		704, 706		569, 577	542, 548	570	444

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Fire brick, machinery						568	
prices		711	419	569	541		
production in					541	564, 570	
Alabama						566, 570	
California		703					
Colorado		701		570	541	566	
Connecticut						566	
Georgia					541	570	
Illinois						566	
Indiana						566	
Maine						566	
Maryland						566	
Massachusetts						566	
Michigan						566	
Missouri					541		
Montana		702			542		
New Jersey		697		569	540	566	
New York						566	
North Carolina						566	
Ohio		697		569	540	566	
Pennsylvania		697		569	540	566	
Tennessee						570	
Texas					541	566	
West Virginia						566, 569	
Fire clay	465, 467	676	414	569	540	567	441
analyses	468, 473	678				569	
exports			424		549	571	
imports			424	576	542		443
in Alabama	466, 667				690	570	
Arizona	763				699		
Arkansas	671				702		
Colorado	474, 750	701		570	542, 709		
Georgia						570	
Idaho					723		
Illinois	467, 677				725		
Indiana	467				728		
Iowa	681				731		
Kentucky	466, 684				734	568	
Maryland	691						
Michigan	696				746		
Minnesota	697						
Missouri	466, 699				750		
Montana	472						
Nebraska	703				756		
New Jersey	706						
New Mexico	472			570		570	
New York	708				765		
North Carolina	466, 717						
Nova Scotia			414				
Ohio	466, 718		414	569	540, 775		
Pennsylvania	465, 722				540, 780		
South Carolina	466, 728				786		
Tennessee	466, 732				791	570	
Texas	466, 735						
Virginia	742				803		
West Virginia	744				804, 806	568	
Wisconsin	467				806		
Wyoming	472						
production				569	540		581
opal		760					
Fischer, Moritz, on natural gas					489		
Fisk, J. H., on platinum in Oregon			367				
Flagging stone, Alabama	667				690		
Arkansas					703		
Connecticut	672				714		
Illinois	677				725		
Indiana					728		
Iowa					731		
Maine	687				737		
Maryland					740		
Massachusetts					742, 744		
Michigan	696				746		
Minnesota	697				748		
Missouri	699				750		
New Hampshire	704, 706				757		
New Jersey					760		
New York	708				765		
Ohio	718				775		
Pennsylvania	722				780		
Rhode Island	727				785		
Tennessee	730				788		
Vermont	737				798		
Virginia	739				799		
Wyoming					808		
Flat Top, W. Va., coal and coke			71, 127	424	425	436, 441	277

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Fleming, H. S., report on Tennessee coal						366	
Flint				5, 7, 10	5, 8	6, 8, 10	6, 386
Florida bog iron ore					720		
brick			415			558, 565	441
clay					719		
coal	675				720		
coquina	675				719		
limonite					720		
limestone	675				719		373, 386
marl	523, 675		452	619	592, 719	595	
mineral waters		981				630	
mining law				729			
phosphate deposits		783, 793	450	617	584, 720	592	451
sandstone							374, 386
slate					718		
structural materials					508		373, 386
sulphur		864					
Fluorspar	497, 587	776	518	692	659	583	468
in Arizona	761, 763				697, 609		
California	768				705		
Colorado	587, 753	777			713		
Delaware	587						
Illinois	497, 678	776		692	726		468
Indiana	587						
Kentucky	587, 686			692	735		
Missouri		777					
Montana	587						
New Hampshire	587, 705			692	759		
New Mexico	587, 757				763		
New York	587, 712	776			798	583	
North Carolina					668		
Ohio	587						
Pennsylvania	726			692	784		
Tennessee		776					
Virginia		777					
West Virginia	745			692	806		
production	587	776	518	5, 8, 692	5, 7, 659	6	4, 6, 468
Fontaine, Wm. M., on maganese in Virginia.			313				
Fossil, coral	497	777	443	604	556	584	464
iron ore, Alabama	667			89, 91	691		
Georgia	675			84	720		
Kentucky	684				734		
New York	709			49	766		
Ohio	720				778		
Pennsylvania	723			55	781		
Virginia	740			80	800		
West Virginia	744				805		
Fostoria, Ohio, natural gas						493	
France, antimony		645					
burstones		713	428	582	552		
coal	5, 109	13	11	235	189	208	22
coke					435		
copper	256	371	240	139		77	77
exports, iron ore		258					
lead		439					
tin		617					
zinc		488					
imports, coke					435		
copper	251	372		139	92	76	
lead		439					
zinc		488					
iridium		581					
iron	109	257	193	21	18	29	21
ore	109	258		98	18	28	22
lead	323	434, 439	271				
manganese				200		141	130
mining law		998					
nickel		540		173			
pyrites		885	510	657			
salt		849			624		
silver		320					
steel	109	257		21	18	29	21
tin		617					
zinc		480, 488	282			95	92
Franklin, copper mine	215, 219	329	209, 213	111, 115	70	53	59
Franklinite	360, 706	773			760		
Froehville, R. J., on dressing tin ores			377				
Freibergite	718, 770				723, 774		
Freieslebenite	761				697		
French chalk					742		
Frisbuth, William, aluminium process		658					
Friswell, R. J., on cement manufacture.				560			
Fuel, natural gas for		239, 241	158	3	24, 464	482	367

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Fuels, summary.....				2, 7	2	3	3
Fuller's earth.....		705	424		547, 744	574	
Furnace, linings.....	121	805, 685		17		122	
Gadolinite.....						582	
Gahnite.....		737					
Galena.....		617, 382	252				
in Alabama.....	669				694		
Alaska.....					695		
Arizona.....	761				697		
Arkansas.....	670				700, 702		
California.....	767				705		
Colorado.....	750				709		
Connecticut.....	673				715		
Dakota.....	754				716		
Georgia.....	676				721		
Idaho.....	770				723		
Illinois.....	677				725		
Iowa.....	682				731		
Kansas.....	683				732		
Kentucky.....	686				735		
Maine.....	687				738		
Maryland.....	692				741		
Massachusetts.....	694				741		
Minnesota.....	698						
Missouri.....	700				750		
Montana.....	755				754		
Nebraska.....	703						
Nevada.....	772				756		
New Hampshire.....	704				757, 759		
New Jersey.....	708				761		
New Mexico.....	757				763		
New York.....	712				768		
North Carolina.....	714				770		
Ohio.....	720				777		
Pennsylvania.....	723				780		
Rhode Island.....	727				785		
South Carolina.....	729				787		
Tennessee.....	730				789		
Texas.....	735				793		
Utah.....	773				795		
Vermont.....	737				796, 798		
Virginia.....	739				800		
Washington.....					804		
Wisconsin.....	745				806		
Wyoming.....					808		
Galveston, Texas, structural materials.....	476			530		584	
Gannett, Henry, on abrasive materials.....							124
Gap mine, Pennsylvania, cobalt and nickel.....	421					110	
Garnet.....	487, 660	382, 618,	439, 443	596, 604	556, 559,	581, 584	446
in Alaska.....		745			576		
Arizona.....	488, 763	747		601	695	581	
California.....	768	747			705		
Colorado.....	487			596			
Connecticut.....	673				715		
Dakota.....					717		
Georgia.....	676				721		
Maine.....		745					
Massachusetts.....	694	746			744		
Nevada.....		745					
New Hampshire.....	705	746			759		
New Jersey.....	708				762		
New Mexico.....	487					581	
New York.....					765		
North Carolina.....	488, 660	746			668, 770		
Pennsylvania.....	488, 726	746			784		
Rhode Island.....					785		
Texas.....	735				793		
Virginia.....		747				581	
Wisconsin.....	747						
production.....		781				584	448
Garnierite.....				170	778		
Gaylussite, California.....	767, 769						
Gems and precious stones, American.....	483, 498, 661	4, 723, 781	3, 437	595	555, 577	580	445
Genthite.....					721, 795		
Georgia, alum.....		949					
amethyst.....	676	750			721		
arsenopyrite.....	676				721		
asbestos.....	588, 676	913	521	721			
barytes.....	676				720		
bloodstone.....		763					
brick.....			415	568	535, 537	558	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Georgia, buhrstone	675	712			720		
cement					527	551	461
chalcocite	675				721		
chalcopyrite	675				720		
chrome iron ore					721		
clay, porcelain					722		
coal	6, 7, 34, 675	12, 39, 154	11, 26, 83	230, 252	171, 233, 720	171, 206, 240	146, 194
coke	98	149, 152, 160	75, 82	378, 387, 393	383, 397	395, 406, 408	
copper	231, 675				720		
corundum	477, 676	715	429	585	553, 721		457
covellite	676				721		
diamond	484, 676				558, 721	580	
emery	676				721		457
epidote						581	
fertilizers			469				
fire brick					541	570	
gahnite		737					
galena	676				721		
garnet	676				721		
genthite					721		
gold	172, 176, 179	312	200	104	58, 720	36	49
granite	676			538	514, 721	536, 538	374, 386
graphite	676			686	672, 720		
halloysite					720		
hematite	493, 675			84	720		39
infusorial earth					722		
iron	129, 133	252	182, 185	32, 84	11	14, 23	10, 17
ore	676	278		84	722		24, 32, 35
itacolumite	676				722		
kaolin (kaolinite)	676				722		
limestone					517		373, 388
limonite	676			84	721		
manganese ores	424	551	305	181	144, 150, 721	127	127, 133
marble	676			542	518, 721	541, 543	375, 387
marl	523, 676				721		
mica	676	908			671, 721		
mineral waters		981	537	716	683	626, 630	522
mispickel	676				721		
molybdenite	676				722		
nickel silicate					721		
novaculite	677				722		
ocher			528	709	722		503
oilstone	677				722		
opal	677	700			722		
phosphates			454				
platinum	442						
pottery	470						
pyrites	677	880	506		722		
pyrolusite. (See Manganese ores.)							
roofing slate					721		
ruby					722		
sandstone	676						374, 388
flexible. (See Itacolu- mite.)							
sapphire	677				722		
serpentine	677				722		
silver	172, 176, 677	312, 318	200	104	58, 722	36	49
slate	452				524, 721	550	376, 388
staurolite		742					
steel	137			18		14	
structural materials				529		523	373, 386
talc	585, 677				722		
tellur-bismuth	677				722		
tetradymite	677				722		
tin ore		601					
tripolite					722		
German silver	411					161	
Germany, antimony		645					
bismuth			389				
buhrstone				581			
coal	5, 109	13	11	235	189	208	21
cobalt			364				
coke					432		
copper	251, 255	356, 368	238	135		73	73
gold	319						
graphite				688			
iridium		581					
iron	109		193	21		29	20, 21

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Germany, iron ore	109					28	22
kainite			465				
lead	322	434, 436	267				
manganese ore		555			161		
mining law		1001					
petroleum		232					
potassium-chloride industry				624	635, 644		
pyrites		885					
salt		849					
silver	322	319					
steel	109			21		29	21
tin ore		618					
whetstones				594			
zinc	356	481, 483, 385	277	159	117	95	
761							
Heysenite							
Hilsonite, Utah					795	513	478
Hignoux, J. E., on the manufacture of bluestone.	297						
Glass, coloring materials			544				
constituents		958					
exports			556				
imports			556				
manganese as a decolorizer		554					
materials		958	544, 556				
pots, manufacturing processes		684, 697					
sand, Connecticut	674				715		
Indiana					728		
Maine	690				737, 739		
Mississippi					750		
Missouri					752		
South Carolina					787		
Tennessee					892		
Wyoming					600		
Hauber's salt, Arizona	763				799		
Porphyritic mines, Michigan, iron ore			188	67	56, 35		35
Gold	172	312, 642, 648	200	104	8	36	48
coinage of the mints					63	39	
consumption in the arts		319	206		63		
exports	181	321	207	108	62, 64	40, 42	
extraction	646	358					
imports		321	206	108	62, 64	40	
in Alabama	176, 667				690, 694	37	49
Alaska	172, 176	312	200	104	38, 60, 695	36	49
Arkansas	670				702		
Arizona	172, 182, 761	312, 318	200	104	58, 60, 697, 699	37	49
California	172, 182	312, 318	200	104	58	36	49
Colorado	172, 182, 750	312, 318	200	104	58, 709	36	49
Dakota	172, 754	312, 318	200	104	58, 716	36	49
District of Columbia					719		
Georgia	172, 176, 675	312, 318	200	104	58, 720	36	49
Idaho	172, 182, 770	312, 318	200	104	58, 723	36	49
Illinois	678				726		
Indiana	680				730		
Indian Territory	681						
Maine	172, 176, 688				58, 737		
Maryland	692				740		49
Massachusetts	694				744		
Michigan	696				746	37	49
Minnesota	698				748		
Missouri	701				752		
Montana	172, 182, 755	312, 318	200	104	58, 754	36	49
Nebraska	703						
Nevada	172, 182	312, 318	200	104	58, 756	36	49
New Hampshire	176, 704				758		
New Mexico	172, 182, 757	312, 318	200	104	58, 763	36	49
North Carolina	172, 176, 714	312	200	104	58, 770	36	49
Ohio	720				777		
Oregon	172, 182	312, 315	200	104	58, 778	36	49
Pennsylvania	726				784		
South Carolina	172, 176, 728	312	200	104	58, 786	36	49
South Dakota							49

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'9
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Gold in Tennessee.....	172, 176, 730	312	200	104	58, 789	37	
Texas.....	174, 735				793	37	49
Utah.....	172, 182, 774	312, 318	200	104	58, 795	36	49
Vermont.....	737	318			798	37	
Virginia.....	172, 176, 739	312	200	104	58, 800	36	49
Washington.....	172, 182	312	200	104	58, 804	36	49
Wisconsin.....	747						
Wyoming.....	172, 182, 758	312	200	104	58, 808	36	49
mining profits.....		318					
production.....	172, 180	312, 317, 320	200			37	6, 49
of the world.....		319			62	40	52
quartz.....	490	7, 763, 781	5, 8	7, 604	6, 556	584	6
summary.....	XII, XVI	2, 6, 9		1, 7, 9	1, 8	1	1
uses.....			544		63		
Gould, E. R. L., on mining law.....				722			
Grahamite.....	745				806		
Grand Rapids, Mich., structural materials.....						527	
Granite.....	455	662	396	537	512	536	374
in Alabama.....	667				691		
Arizona.....	761				697		
Arkansas.....	671			530	701	537	374, 378
California.....	455, 767		663	537	514, 703	536, 538	374, 380
Colorado.....				538	705		374, 383
Connecticut.....	672			537	513, 714	536	374, 385
Delaware.....							374, 386
Georgia.....	676			538	514, 721	536, 538	374, 386
Idaho.....	771				724		
Indian Territory.....	681				730		
Maine.....	688			520, 537	513, 737	536, 538	374, 396
Maryland.....	691				515, 740	536, 538	374, 398
Massachusetts.....	693			537	513, 743	536, 538	374, 400
Michigan.....	696				746		
Minnesota.....	697			538	747		374, 404
Missouri.....	700				751		374, 405
Montana.....							374, 408
Nevada.....							374, 409
New Hampshire.....	704			520, 537	514, 758	536, 539	374, 409
New Jersey.....	706				760	536	374, 410
New York.....	709				765	536	374, 410
North Carolina.....	714			538	771	539	374, 410
Oregon.....							374, 410
Pennsylvania.....	723			537	514, 780	536	374, 410
Rhode Island.....	727			537	513, 785	536	374, 410
South Carolina.....	728				515, 786	539	374, 428
South Dakota.....							374, 428
Tennessee.....	732				791		
Texas.....	735			530	793		374, 431
Utah.....	774				795		374, 432
Vermont.....	736				513, 797	536, 539	374, 433
Virginia.....	740			537	514, 800	536, 539	374, 435
Washington.....							374, 437
West Virginia.....							
Wisconsin.....	746				514, 806	536	374, 438
Wyoming.....					808		
production.....						536	374
quarries.....					515	538	
tests.....				538			
Graphite.....	590	382, 915	533	225, 686, 713	672, 679	6, 152, 361	6, 507
analyses.....	592						
exports.....		916					
imports.....		916		687	672		507
in Alabama.....	590, 667			686	691		
Alaska.....	760				696		
Arizona.....	761				697		
Arkansas.....				686			
Austria.....				688			
California.....	768	915		686	672, 705		
Canada.....	590						
Ceylon.....				688			
Colorado.....	753			686	713		
Connecticut.....	673				715		
Dakota.....					718	152	
England.....				688			
Georgia.....	676				672, 720		
Germany.....				688			

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Graphite, in Italy				688			
Maine	689				737, 738		
Maryland	692				741		
Massachusetts	694			225	744		
Mexico				688			
Michigan	696				747		507
Nevada	772				757		
New Hampshire	704			686	672, 758		
New Jersey	590, 706				762		507
New Mexico	590						507
New York	590, 709	915	533	713	672, 679	6	
North Carolina	590, 714			686	765 672, 679	6	
Nova Scotia				688	771		
Ohio				686			
Pennsylvania	726			686	784		507
Rhode Island	727			225, 686	672, 785	6, 361	
South Carolina	729			686	787		
Vermont	737				798		
Virginia	590, 743			686	803		
West Virginia				686			
Wyoming	759				810		
ore dressing methods	591						
prices	592		533				
production	xv, 592	5, 9, 916	8, 533	5, 7, 10, 687	5, 7	6	5, 507
sources	591				672		507
uses	593	917	533	687	672, 679		507
varieties	592						
Great Britain alkalies					655		
alum clay		950					
coal	5, 109	13	11	235		208	20
cobalt		539, 547					
coke				430			
copper	245	356	230, 240	128	87	74	73
gold extraction from pyrites.		358					
iron	109		193	21		29	11, 18, 22 35
lead	321	434	268				
manganese		555		199	154	440	130
mining law		1002					
nickel		539					
pyrites, imports		358	230	130	90		
salt		848					
silver extraction from pyrites.		358					
steel	109	257	192	21	18	29	16, 21
sulphuric acid production		359					
tin		616, 625					
zinc	358	480, 486	281	159	117	95	92
Great Salt Lake, Utah, salt industry	549	844	483	628, 639	622	606	
Great Salt Valley, Nevada, salt deposits	545	847	483	638			
Greece, lead		434, 440	270				
manganese				200		143	130
mining law		999					
zinc exports			283				
Greenland, cryolite		954					473
Greenockite	701				752, 784		
Grindstones	xiv, 479	4, 713	3, 428	1, 582	4, 552	5, 545, 576	458
analyses				583			
exports	479	713					
foreign sources of supply				584			
imports	479	713	428	585	552	577	458
in Alabama					693		
Indiana					728		
Massachusetts	694				744		
Michigan		713		582	552	576	458
New Hampshire					553		
Ohio	479, 718	713		582	552, 775	576	458
summary						5	3, 6
Grossularite	488	747					
Guano. (<i>See</i> Fertilizers.)					608		
Gummite, North Carolina					796		
Gunnison paint, Utah	775				595		
Gypsum	526, 763	809	458	620	598, 600	6	465
analyses							
chief sources of supply				620			465
exports		810	459		595		
imports	530	810, 813	460, 464	622	602		467
in Alabama	523	809			694		
Arizona	529, 763	813		623	699		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Gypsum in Arkansas	526, 671	809			762		
California	529, 769	812		623	602, 704, 706	6	465
Colorado	528, 753	812		622	601, 710, 713	6	465
Dakota	528, 754	812		622	717	6	465
Illinois					727		
Iowa	526, 682	809			731		465
Kansas	527, 683	809		623	595, 732	6	465
Louisiana	526, 686	809			736		
Maryland	692				741		
Michigan	527, 696	809	459	620	595, 601, 746	6	465
Minnesota	698				748		
Mississippi	698				749		
Missouri	701				752		
Montana	528	812					
Nebraska	703			623	756		
New Mexico	528, 758	812			763		
New York	526, 709	809	459		765	6	465
Nova Scotia			460			6	
Ohio	527, 719	809	459	620	593, 775	6	465
South Dakota							465
Tennessee	733				791		
Texas	526, 735	809	793				
Utah	774	812			795		465
Virginia	526, 740	809	459		800	6	465
Wyoming	759				810		465
prices	528	809, 813	461				
production	XIV	4	4, 461	621	6, 595	6	4, 6, 465
uses	531	814					465
Hadfield's manganese steel		565		211			
Hale, J. P., on salt	539						
Halite. (<i>See</i> Salt.)							
Halloysite, Alabama	667				691		
Georgia					720		
Hamilton, Patrick, on Arizona coal		18					
Hamson, J. W., iron statistics in California			197				
Harney Peak, Dakota, tin		605, 611		214	135	144	120
Harrisburg, Pa., structural materials						532	
Harrison, J. W., California coal trade						203	
Hartford, Conn., structural materials				522			
Hatchetolite, North Carolina					668		
Hausmannite, Arizona	763				699		
Hay, Robert, on Kansas salt						607	
Hayti, platinum		576					
Hazleton, Pa., coal district	19, 107	68				312	
Heavyspar. (<i>See</i> Barytes.)							
Hedstrom, E. L., on coal receipts at Buffalo						187	
Hematite in Alabama	667	278		87	691, 694		40
Arizona	761, 763	289			697, 699		
Arkansas	671				702		
California	767				705		
Colorado	751	282			710, 713		39
Connecticut		271			714		40
Dakota					717		
Delaware					719		40
Georgia	493, 675			84	720		40
Idaho	770				723		40
Illinois	678				727		
Indiana	680				730		
Iowa	682				732		
Kentucky	684				734		40
Louisiana					736		
Maine	689				737		40
Maryland	691			77	740		40
Massachusetts	693				743		40
Michigan	696	265			746		40
Minnesota	697	266			747		39
Mississippi	699				749		
Missouri	700				751		40
Montana							40
Nebraska	703						
Nevada	772				757		
New Hampshire	705				759		
New Jersey	706				760		39
New Mexico	147, 758	285			764		40
New York	709				766		40
North Carolina	714, 717	278			771, 774		
Ohio	719				776, 778		
Oregon							40
Pennsylvania	723			53	780		40
Rhode Island	727			13	785		
South Carolina	729				787		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Hematite in Tennessee	731			92			
Texas					789		40
Utah	773	288			794		40
Vermont	736				795		40
Virginia	740			78, 80	797		
Washington					800		40
West Virginia	744				804		40
Wisconsin	746				805		40
Wyoming	758	285			806		40
production by States					809		
specular analysis						35	
Henderson, J., on marl in Georgia	523						
hessite, Colorado	751						
heterosite		618			710		
Hewitt, Abram S. on the iron industry			195				
Hidden, W. E., on emeralds in North Carolina.	500						
hiddenite	502						
Hiddenite	488, 502	748, 781	438, 442	604	556, 560, 772	584	446
Hildreth, S. P., on the Ohio petroleum	186						
Hilgard, E. W., on asphaltum in California		938					
the salines of Louisiana	554						
Hills, R. C., on Colorado coals			19				
Hoboken, N. J., structural materials				525			
Hocking Valley, Ohio, coke district			94	407			
Hoffman, H. O., on desilverizing lead		462					
Holland, manganese						143	130
Holmes, Prof. J. A., phosphatic nodules	507				509	526	
Holyoke, Mass., structural materials					556	584	446
Hornblende	491	382, 728, 781	443	604	556	584	446
Hot Springs, Ark., novaculite				589	553		
Hotchkiss, Jed., on manganese in Virginia.			307, 324				
Virginia anthracite coal.		98					
Houston, Va., manganese mine				196		133	136
Howard, C. C., on Ohio natural gas						490	
Hungary, antimony		646					
coal	109	13	11	235		208	21
cobalt			365				
copper		356, 373		128	87	73	73
gold		319					
iron ore	109					28	
lead		434, 439					
pig iron	109		193			29	21
quicksilver			293				
salt		849					
silver		319					
steel	109					29	21
zinc ore		491					
Hutchinson, Kans., structural materials						525	
Hyalite		761					
Hydraulic cement			405	556	747		461
limestone, in					702		
Arkansas							463
California				564			
Colorado				564			
Connecticut	673				715		
Dakota					718		
Illinois	678				726, 728		
Iowa	682				731		
Kansas					733		
Kentucky	685				734		
Maryland					740		
Massachusetts	694				744		
Minnesota					748		
Mississippi	698				749		
Missouri	702				752		
New York	709				766		
Ohio	719				776		
Pennsylvania	723				781		
Tennessee	733			564	791		
Virginia	740				801		
West Virginia					805		
Wisconsin	746				806		
Wyoming					810		
Hydrophane				597			
Hydrozincite	671, 702,				701, 753		
	726						
Idaho, anglesite	770				722		
antimony	439						
ocher	770				722		
sulphide	439		387		723		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Idaho, argentine	770				722		
arsenopyrite	770				722		
asbestos					723		
azurite	770				722, 724		
bismuthinite	771				724		
bog-iron ore					723		
brick production						558	
calcite	770				722, 724		
cerargyrite	770				722, 724		
cerussite	770				722, 724		
cervantite	770				722		
chalcopyrite	770				723		
cinnabar					724		
clay	770				723		
coal	49	12, 39	11, 26	230, 252	171, 223, 241	171, 206, 241	147
copper	229, 770	329, 342	210	112	722, 724	54	60
cuprite	771				724		
diamond	484	732					
dolomite	771				724		
dufrenoy'site	770				723		
erubescite	771						
fahlerz	770				723		
fire clay					723		
freibergite	770				723		
galena	770				723		
gold	172, 770	312, 315, 318	200	104	58, 723	36	49
quartz	490						
granite	771				724		
hematite	770				723		40
infusorial earth				558			
iron ores	770	289			723	35	40
lead	311	416	253	140, 146	107, 722	88	80
ore shipments	770	425				88	
lignite	49, 771			230, 252	724		
limestone	770				722		
limonite	770				723		373, 388
magnetic iron ore					724		
malachite	770				723		
manganese ore	771				724		
marble	771			540	724		375, 388
marcasite	770				723		
mica	583, 771				723		
mineral waters		981, 986			682	626, 630	526, 535
mispickel	770				722		
molybdenum sulphide	771				724		
platinum		567					
proustite	770				723		
pyrargyrite	770				723		
pyrites	770				723		
pyrolusite	771				724		
salt	550, 771	848	484		724		
sandstone	770				723	544	374, 388
silver	172, 176, 182, 770	312	200	104	58, 60, 723	36	49
sphalerite	770				723		
stephanite	770				723		
stibnite	770				723		
structural materials						524	
sulphur		864					
tetrahedrite	770				723		
tin	434	613					
trachyte					724		
tufa					722		
Idocrase	492	767					
Idria, Austria, quicksilver mine		496				105	
Iles, Malvern W., on lead slags		440					
Illinois, agate		757					
asphaltum	678				726		
barytes	580						513
brick	457			568	535, 537	558, 565	
brines	678				725		482
cement		672	406	556	527, 529	551	461
cerussite	678				726		
chalcopyrite	678				726		
clay	677	695			725		
coal	6, 34, 678	39, 43	11, 27	230, 253	171, 227, 725	206, 242	146, 195
analyses	51	42, 162					
area	49			225		242	
boiler tests						256	
mining methods						250	204

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Illinois coal, prices at Chicago.....	50	43		255	228	192	161
production.....						171, 242,	149
receipts at Chicago.....				230		249	
shipments from Chicago.....						191	160
value.....				256	232	191	160
coke.....	98	144, 157, 162	77, 82	378, 394	383, 398	242, 249	149
copper.....	678				726		
drain tile.....		695, 700		575	546		
fire clay.....	467, 677				725	566	
flagging stone.....	677				725		
fluorspar.....	497, 678	776		692	726		468
galena.....	677				725		
gold.....	678				726		
gypsum.....					727		
hematite.....	678				727		
iron.....	49, 120, 133	252, 416	182, 184	18	11	14, 23	10, 17
lead.....	312, 678	414, 425			726		
lignite.....	678				727		
lime.....						555	
limestone.....	451, 678			540	515, 726, 728	540	373, 388, 390
lithographic stone.....		935					
marble.....	451				727		
marl.....	679						
metallic paint.....				711			
mineral waters.....		981	537	716	683	626	522
natural gas.....		236, 243	156, 158, 167	511	466, 497, 726	511	367
niter.....	679				727		
peat.....	679				727		
petroleum.....	679				727		292, 353
pottery clay.....	471				727		
pyrites.....	679				726		
quartz.....	678				727		
salt.....	678	842		628	611, 725	597	482
saltpeter.....					727		
sand.....	678				726		
sandstone.....	451, 678				726		374, 390
selenite.....					727		
sewer pipe.....		701					
siderite.....	679				727		
silver.....	679				727		
smithsonite.....	679				727		
sphalerite.....	679				727		
steel.....	108, 119, 137	254	186			14, 20, 23	12
structural materials.....	450			532	508	524	373, 388
terra cotta.....			422				
zinc.....	347, 365, 679	475	273	154	727	92	89
Ilmenite.....		772			793		
Ilvaite.....	498	768					
Imports, agate.....			444, 605	605			
agricultural salt.....		817		624			
alabaster.....		814	464		602		467
alum.....	606	950		682	647		
aluminum.....		600	390, 392	221	138	162	118
amber.....				605	658		
antimony.....		651	387				141
arsenic.....		657	386				
asbestos.....		914	522				514
asphaltum.....	605	938					479
barytes.....		923		706	676	618	513
bismuth.....		655	389				
bluestone.....		951		683			
bones for fertilizing.....				607			
boracic acid.....		861					
borate of lime.....		861					
borax.....		861					
brass.....		345	219	120	78	61	66
Brazilian pebbles.....				605			
brick.....		704, 706	424	576	548		
brimstone.....	579	871					515
bromine.....					627		
buhrstones.....		713	428		552	576	456
building sand.....		668					
stone.....		666	402	555	526		
carbon for fertilizing.....				607			
carnelian.....			444				
caustic potash.....					649		
cement.....		672, 675	407	558	528	552	462

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
Imports, chalk	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
chrome ore		931					
chromic acid		572	359	177	133	130	139
clay		705	359		133	121	139
coal	101	14	424	576	547	574	443
cobalt	422	547	12, 17	230	171	172	149
coke			364	175	131	620	125
copper			35	388	393	406	
Austria			217, 219	118, 120	76, 78	60	60
France							
Germany	256	370		139		77	76, 77
Great Britain	246, 249	360		130	91	75	74, 75, 76
copperas		953		685			
coral			444		573		
cryolite		954		693	659		473
diamond			444	605	558		
earthenware and china		707	425	571, 577	545, 549	573	444
emery	476	719	432	586	554	577	457
feldspar		934					
fertilizers		804	455	607	583	591	450
fire brick and clay		704, 706	424	569, 576	542, 548	570	444
fuller's earth		705	424		547	574	
glass			556				
gold		321	206	108	62, 64		
graphite		916		687	672		507
grindstones		713	428	585	552	577	458
guano		804	455	607			450
gypsum		810, 813	460, 464	622	602		467
iodine		858	488				
iridium		583	369	223	143		
iron	139	257, 261	190	12	12	13	
ores	117	257, 261	189	16, 101	15, 17		44
kainite		817	467	607	650		
kaolin		705	424	576	547	574	443
kieserite				607	650		
kyanite				607			
lead	307	432	259	149	110	90	86
Austria		439					
Belgium		439					
France		439					
Germany	323	436					
lead, Great Britain		435					
Hungary		439					
lime	458	669	411	566	534		
litharge		925			675	617	511
lithographic stone	596	936		691			520
magnesia				698			
manganese ores	426	556		698	155		129
marble		665	404	554	525, 527	550	375
meerschaum			444				
mercurial preparations		499	293	166	125	104	101
mica		912	520		660, 664	614	475
millstones		713	428		552	576	456
mineral paint					675	618	509, 511
waters		987	543	721	681	624	522
wax						515	481
nickel	410	543	298	171	126	108	126
novaculite					553		
ocher		927	529	710	678	619	509
Paris white		932		707	677	621	512
petroleum, Canada						472	
phosphates		804	454, 458	607	583	591	450
phosphorus				677			
plaster		813	463	622	*		467
platinum	443	578	368	223	143	167	144
potash		967					
potassium bicarbonate		572		177	132, 650		139
bicarbonate and pearlash					649		
carbonate					649		
chlorate					650		
chloride				624	649		
chromate					650		139
ferricyanide					649		
ferrocyanide					649		
iodide					650		
nitrate					650		
sulphate			167	625	646, 650		
pottery products					545, 549	572	443
precious stones	482	782	444	605	558		
pumice stone		721	433				
pyrites	247	358, 886	509	130	610		518
quicksilver		499, 502	293	166	124, 679	622	101
red lead					675	617	511

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
ports, rotten stone		722					
salt	550	850	481, 484	640	623	610	489
sienna		928	532	712			
silver		321	206	108	62	40	
soda ash			550				
sodium bichromate		572					
steel	139		191	12	12	13	
strontium				700			
sulphur		868	497, 500	645	605		515
talc							476
terra alba		924		706	676	621	512
tiles		707		575, 578	549	573	
tin	436	639	384	215	137	157	122
from Great Britain		618, 625					
Japan		623					
South America		625					
Sweden		619					
ore, Great Britain		618, 625					
plates			191	14		13	
ultramarine		929		708	677	622	
umber		928	444	713	678	620	509
whetstone				593			400
white lead		921		703	675	617	511
whiting		932			677	621	512
zinc	349	477	274	157	115	93	90
Great Britain	358	487					
Austria		491					
Belgium		489					
France		488					
white					675	617	89
dia, coal	5			235			
diamond mines					569		
iridium		583					
iron ore	111			480			
petroleum		932					
platinum		576					
tin ore		623					
Indiana, alum		919		681			
bog iron ore					730		
brick	458	696	416		535, 537	559, 565	
brines					728		
cement		673			529		461
clay	679				728		
coal	6, 34, 52,	12, 43	11, 29, 83	228, 230,	137, 237,	171, 256	146, 205
analyses	679			261	727		
area	53	45		396	238, 241		
miners' wages	52			225		256	
production	103	45	29	265	243	171, 256,	146, 205
	55					258	
coke		149, 152	77, 81, 90	378, 387,	383, 392,	395, 404,	
				395	398	409	
copper	680				729		
drain tile		700	421	575	547		
diamond					729		
encaustic tile		699					
fire brick and clay	458, 467		414		728	566	
flagging stone					728		
fluorspar	587						
glass sand					728		
gold	680				730		
grindstone	679				728		
hematite	680				730		
indianite	680						
infusorial earth	681				730		
iron	131, 133,		185	18	11	14	10, 17
ores	137						35
kaolin	680				728		
lime					533	555	392
limestone	451, 680			541	515, 729	540	373, 390
analysis							392
limonite	680				730		
lithographic stone					729		
marble	451						
marls	681				730		
mineral waters		981	537	716	683	626, 620	522
natural gas		243	161	508	26, 464,	485, 499	367
					466, 485,		
					729		
					730		
					729		
					553, 729		460
					729		
niter	681						
ocher							
oilstone			435	592			
peat					729		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Indiana, petroleum	681				729	464	292, 349
pig iron	129	252	182	18	11	23	
porcelain clay	471						
potash and pearlash					643		
pyrites	680				730		
quartz	680				729		
salt	679	842	474	628	611, 728	597	482
saltpeter	681				730		
sandstone	451, 680				729		874, 393
sewer-pipe production		701					
siderite	681				730		
sphalerite	681				730		
steel	120, 137		184	18	11	14	12
stone	679					524	373, 390
structural materials	451				509	524	373, 390
tripolite	681				730		
whetstone			435		729		460
Indianaite	471						
Indian reds							510
Indian Territory, coal	51, 681	12, 45	11, 29	230, 265	171, 244, 730	260	147, 207
analyses						261	210
coke		140, 152, 164	77, 90	378, 397	383, 400	261, 395, 409	
copper ore	681				730		
gold	681						
granite	681				730		
mineral waters		981	537			630	
salt					730		
Iridosmine	768		367				
Infusorial earth	479	720	433	4, 587	4, 554	6, 578	5, 6, 459
analyses	479	721	587				
in California	480	720		588	554		459
Colorado					713		
Georgia	677				722		
Indiana	681				730		
Maryland	693	720	433	587	551, 742	578	459
Massachusetts					743		
Nevada	479	720					459
New Hampshire	704				758		459
New Jersey	708			587	762		459
New Mexico				587			
Oregon					778		
Vermont	737				798		
Virginia	743				803		
Wyoming					809		
uses	480					578	479
Iodine		854	488				
imports		858	488				
West Virginia		854					
industry, Scotland			489				
manufacturing processes			490				
prices		855	490				
production in South America			489				
receipts at New York			488				
sources		855					
Iolite	488	743					
Iowa, anglesite	682				731		
aragonite		777					
barytes	682				731		
brick					535, 538	559	
cement		672					
cerussite	682				732		
clay	167						
coal	6, 34, 55,	12, 45	11, 30	230, 266	171, 215, 731	206, 262, 267	147, 215
68							
area	55			225			
miners' wages	103						
production	56	46		266		171, 262	147
trade						200, 262	
coke		164		398			
fire clay	681				731		
flagging stone	682				731		
fossil coral	497						
galena	682				731		
gypsum	527, 682	809			731		465
henrinite	682				732		
hydraulic limestone	682				731		
iron			185	18	11	14	
lead ores	682				731		
lime					533	555	
limestone	451, 682			534	516, 731	540	373, 390
limonite	682				732		
lithographic stone	595	935					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
iron, marble	451, 682				731		
mineral waters		982	537	716	684	627, 630	522
natural gas				513			
sandstone	451					544	374, 394
smithsonite	682				732		
sphalerite	682				731		
steel				18	11	14	
structural materials	451			534		524	373, 393
zinc	682				732		58
iodosmine	444, 768		367	2	705		
iridium	444	581	367	2, 222	143		
bibliography		588					
exports and imports		583					
in Australia		581	369	223	143	167	
Borneo		581					
Brazil	444						
California	444	581					
Canada		581					
France		581					
Germany		581					
India		581					
Oregon	444	581					
Russia		581					
South America		581					
Spain		581					
methods of working		584					
ores, analyses		581					
prices	444	588					
properties		583					
uses		584					
iron and steel	108	246	180	11	10	12	10
consumption	110				10	14	14
imports	139		190	13	12	13, 18, 19	
industries	108	257	181	12	10	12	10
manufacture		246	189	35	24	29	
natural gas for					24		
prices	141	255			14	16	15
production	xi, 108 114, 120	250, 257	181	1, 17, 20	10, 13, 18	12, 23	1, 10
buildings, value						516	
exports	140						
first exports to Great Britain		247					
imports	139	287	191	12	12	13	
in Alabama	119, 133 149	278	182	18, 33, 85	11, 49	14	10, 17
Arizona		259					
California	148	252, 286		18	11	15	12
Colorado	144, 147 751	281	182	18	11, 28, 52	15, 33	10, 17
Connecticut			182	42	11	14	10, 17
Dakota	147, 754	285				35	
Delaware				18	11	14	12
Georgia		278	182	33, 84	11	14	10, 17
Great Britain	109		193	21		29	16
Illinois			182	18	11	14	10, 17
Indiana			182	18	11	14	10, 17
Iowa			199	39	11, 47	14	12
Kentucky		278	182	96	11	14	10, 17
Louisiana					50		
Maine	689		182	41	11, 42	14	10, 17
Maryland	691		182	77	11	14	10, 17
Massachusetts	695		182	42	11	14	10, 17
Michigan	696	264, 267	182	62	11, 34	14, 17, 23	10, 17
Minnesota	698	266	182	73	11, 39		10, 17
Mississippi					48		
Missouri	700	285	182	97	11, 46	14	10, 12, 17
Montana	147, 755	285	196			34	
New Hampshire	705				11	14	12
New Jersey	706	274		30, 50	11, 44	14	10, 17
New Mexico	147	285	196				
New York	709, 711	270, 273		30, 43	11, 43	14	10, 17
North Carolina	714	246		82	11		10, 17
Ohio	721	275		56	11, 46	14	10, 17
Oregon		287	199			15	10, 17
Pennsylvania	119, 723	270, 275		52	11, 42	14	19, 17
Rhode Island	727			42	11	14	12
Russia	109		193	21		29	21
South Carolina	729			83			
Spain				21		29	21
Sweden				21		29	21
Tennessee	119, 731	278	65, 67	92	11	14	10, 17
Texas	735			18	11, 51	14	10, 17
Utah	755	288	199				
Virginia	119, 740	274		77	11, 16	14	10, 17

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Iron in Vermont.....	737				42		
Washington.....	148	268	199		11	15	10, 17
West Virginia.....	745	277		81	11	14	10, 17
Wisconsin.....	746	268		18	11	14	10, 17
Wyoming.....	147	285	196		11	15, 35	12
meteoric.....		289					
on Pacific coast.....	148	286	196				
ores, analyses, Africa.....				102			
Alabama.....	150, 157,	278		86, 91	50		
	159						
Colorado.....	146	282			50, 52		
Connecticut.....		271					
Elba.....				101			
Great Britain.....				103			
Greece.....				103			
Iowa.....					48		
Kentucky.....		279		97			
Louisiana.....					50		
Michigan.....		264		65, 71	38		
Minnesota.....		267		75	41		
Missouri.....		269		98	47		47
Montana.....						34	
New Jersey.....		275		51			
New York.....		272		46	43, 54		
North Carolina.....		277		82			
Pennsylvania.....		270		53	44		
Rhode Island.....					56		
Spain.....				102			
Tennessee.....				93			
Texas.....					51		
Utah.....		288					
Virginia.....				77, 81			
Wisconsin.....				71	37		
Wyoming.....	147						
by John Birkinbine.....				39	30		23
concentration.....					54		
consumption.....	112			40	15, 30	18	
exports.....	140				33		
foreign.....				98			19, 43
imports.....	117	257, 260	189	16, 99	15	17	43, 45
in Alabama.....	149	278		85	49, 694	17	24, 27
Arizona.....	761, 763	289			697, 699		
Arkansas.....	671	280			702		
Austria-Hungary.....	109				21	28	21, 22
Belgium.....	109				21, 100	28	22
California.....	767	286		100	705		10
Canada.....							22
Colorado.....	751	279, 284	196		52, 710,	33	24, 35, 39
					713		
Connecticut.....	120, 674		188	14	16, 42,	17	24, 35, 40
					716		
Cuba.....	118	260		98	56	18	
Dakota.....		285			717	35	
Delaware.....							40
France.....	109			98		28	22
Georgia.....	676	278		84	720, 722		24, 32, 35
Germany.....	109			100		28	22
Great Britain.....				100		28	22
Idaho.....	770	289			723	35	40
Illinois.....	678				727		
Indiana.....					430		35
Iowa.....	682				7, 732		
Italy.....	109			98		28	22
Kansas.....	684				733		
Kentucky.....	684	263, 278		96	734		24, 34, 40
Louisiana.....					50, 736		
Maine.....	120, 689			41	42, 737,		24, 40
					739		
Maryland.....	691			77	740		24, 34, 40
Massachusetts.....	120, 693,	267		42	744		24, 40
	695						
Michigan.....	111, 116,	262, 267,	188	62, 69	34, 746	17	24, 35, 40
	695	276					
Minnesota.....	697	262, 266		73, 75	16, 39,	17	24, 39
					747		
Mississippi.....	699				47, 749		
Missouri.....	700	263, 268		96	46, 751	17	24, 35, 40
Montana.....		285	196			34	24, 40
Nevada.....	772				757		
New Hampshire.....	705				759		
New Jersey.....	117, 706	262, 274		50	16, 44,	17	24, 35, 39
					760		
New Mexico.....	757	285	196		764		24, 40

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Iron ores in New York	117, 120, 709	262, 271	188	43	43, 766	17	24, 30, 35, 40
North Carolina	714	263, 278	188	82	16, 771, 774	17	24, 34
Ohio	719	263, 275		56, 61	16, 46, 776, 778	17	24, 33
Oregon			199		778		24, 40
Pennsylvania	721, 725	262, 275	188	15, 52	16, 44, 781	17	24, 28
Rhode Island	727			42	785		
Russia	109					28	22
South Carolina				83	787		
Spain	109			101		28	22
Sweden	109					28	22
Tennessee	731	278		92	790	17	24, 40
Texas	735				51, 794		24, 40
Utah	773, 775	288	199		795		24, 40
Vermont	120, 736				42, 798		
Virginia	738	276		77	801	17	24, 40
Washington	775	288	199		804		40
West Virginia	744	277		81	805		24, 34, 40
Wisconsin	120, 746	268		71	806	17	24, 31, 40
Wyoming	147, 759	285	196		810	35	35
production	109, 112	261	187	14	15	17, 28	22, 24, 26, 35
shipments				14	16, 33	17	27
oxides for coloring glass			545				
prices	109, 141	257		21, 99	18	16	13
pyrites, arsenical, in					716		
Dakota					729		
Maine	689				768		
New York	711				803		
Virginia					697		
in Arizona	761				702		
Arkansas	671				711		
Colorado	751				717		
Dakota	754				722		
Georgia	677			652	727		
Illinois	679				733		
Kansas	684				739		
Maine	689				743		
Massachusetts	693, 695			654	749		
Minnesota	698				753		
Missouri	702				754		
Montana	755				760		
New Hampshire	706			652	762		
New Jersey	708				764		
New Mexico	757				769		
New York	712				772, 774		
North Carolina	717				784		
Pennsylvania	726				787		
South Carolina	729				792		
Tennessee	733			652	794		
Texas	735				795		
Utah	774				797		
Vermont	736			652	802		
Virginia	741			653	808		518
Wisconsin	747				809		
Wyoming	758				11, 17, 21	12	14
ralls, production	120			11, 17, 21	10, 12	12	13
rolled, production	114	250	184	12, 18	10	12	13
slag as fertilizer, Thomas-Gilchrist process.		805	468	627			
spiegel		263, 561	187, 306			12	11
sulphate	607, 763	953		684	698		
summary	XLXVI, 114	2	2, 5, 68	1	1	1	1
titanic, New York					769		
tungstate, California	739				707		
Connecticut	431				716		
Dakota					718		
Isopyre, New Jersey	493						
Itabiryte	729, 763				787		
Itacolumite	676, 715				722, 786		
	728						
Italy, antimony		646					
coal	5, 109	13	11	235	18	28, 208	22
copper production		356	228	128	87	73	73
gold		319					
graphite				688			
iron	109					29	21
ore	109				18	28	22
lead	323	434, 440	269				
mangauese				202		143	130
mining law		999					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1888-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Italy, nickel speiss	110						
silver		319					
steel	109				18	29	21
sulphur		868	500	646			515
tin ore		618					
Ithaca, N. Y., structural materials						530	
Jade	498	766			576, 743		
Jamesonite, Arkansas	671				701		
Japan, antimony		649					
coal	5		11	235	189		
copper production		356	229	128	88	73	74
gold		319					
imports, quicksilver	390		295				
tin		623					
natural gas						511	
petroleum		232				474	
silver		319					
tin ore		623					
Jasper	492	761, 781	440, 443	506, 604	556	584	446
in California	492	762					
Colorado	492	762					
Dakota					717		
Kansas	492	762					
Maine		762					
Massachusetts		762			743		
New Mexico		763					
New York	192	762					
North Carolina		762					
Oregon		758, 763					
Pennsylvania		762					
Rhode Island		762			785		
Texas	735	762			793		
Jencks, C. W., on rubies in place			439				
Jennings, J. R., on manganese, Nevada			349				
Jet	497, 773	780					
Johnson, L. C., on phosphate in Florida			452				
Jones, John H., on Pennsylvania anthracite coal	12	70	47	298	293	303	242
Kainite		816	465	697	633		
Kanawha, W. Va., coal and coke	63	131, 207	71, 121	373, 424	374, 423	358	279
Kansas, bog iron ore	684				733		
brines					732	607	
calamine	682				732		
cement					527	551	461
cerussite	682				732		
clay	682				732		
coal	6, 34, 683	12, 46	11, 30	230, 268	171, 253, 732	269	147, 217
analyses		165				275	
fields		46				269	
miners' wages			31			274	
mines				269		274	
production		47	30	269	254	269, 273	147, 217
coke		119, 153, 165	77, 91	378, 398	383, 401	395, 410	
galena	683				732		
gypsum	527, 683	809		623	595, 732	6	465
iron and steel ore	120, 133		184				
pyrites	684				733		
jasper	492	762			733		
lead	312, 682	414, 416, 425		147	110, 732	89	
lignite	683	47			733		
limestone	451, 683				516, 733	540	373, 394
analysis							394
limonite	684				733		
marble	451				733		
mineral waters		982	537	716	684	627, 630	522
natural gas		236, 243	161, 168	514	466, 496, 483	483	367
petroleum	684				733		292, 355
plaster	527	809		623	733		465
pyrites	684				733		
salt	532, 683	843			622, 732	597, 607	482, 488
sandstone	451, 684				733	544	371, 395
siderite	684				733		
smithsonite	683				733		
sphalerite	683				733		
steel rails	137						
structural materials	451			534		525	373, 394
sulphur		861			733		394
zinc	347, 682	475	273	156		92	88
coal trade	103					200	166

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Kansas City, Mo., structural materials	464, 469	676	424	573	509	528	441
Kaolin	464, 469	676	424	573	547	572	441
imports	688	678	424	576	547	574	443
in Alabama	688	678		573	691	572	
Arizona	763						
Arkansas	671				702		442
California		678		573	705		442
Colorado						572	442
Connecticut	469						
Delaware	469, 674				718		
Florida							441
Georgia	676				722		442
Indiana	680		414		728		
Maryland	470, 691				740		
Massachusetts	695				744		
Minnesota	471, 698				748		
Missouri	702				753		
New Jersey	707	678			760		
New York	469, 709				766	572	
North Carolina	659, 717				773		442
Pennsylvania	723		414	573	781	572	442
South Carolina	728				786		442
Texas	734			573	793		442
Utah	775				796		
Vermont	469, 736				797		
Virginia	743	678			803		
Wisconsin	471, 746				806		
Wyoming					810		
manufacture	471	679	415				
new discoveries		678	414	573	545	571	441
Kelp imports		855	490				
Kent, William, on gold and silver							48
Kentucky apatite	686				735		
barium carbonate	686				735		
barytes	580, 686				735		
bituminous rock							478
brick production				568	535, 538	560	
brines	684				734		
calcite					733		
cannel coal	57						
carbonate iron ore	685				735		
cement		672		556	527, 735	551	461
charcoal pig iron	131						
coal	6, 34, 130, 684	12, 47	11, 32	230, 270	171, 256, 734	276	146, 219
analyses	57	167		309, 401	257, 262		
consumption, Louisville						198	
miners' wages	103					206	
mining				271	260	206	
percentage used for coke		154	83				
prices						197, 279	
production	58	49	32	272	258, 263	171, 276, 278	146, 219
shipments				271		290	146, 219
coke	130	149, 152, 166	77, 91	378, 398	261, 383, 401	395, 410	
diamond discovery				600		580	
dolomite					734		
epsom salt	686				735		
fire clay	466, 684				734	568	
fluorspar	587, 686			692	735		
freestone	685						
galena	686				735		
hematite	684				734		
iron	58, 125, 129	252	182	33, 96		14, 23	10, 17
ore	57, 684	263, 278		96			24, 34
lignite	686				735		
lime	686				533		394
limestone	451, 685			531	516, 733, 734	540	373, 395
limonite	685			96	734		
lithographic stone	595, 685	935			734		
marble	451, 685		398		734		
marl	685			620	734		
mineral waters		982	538	716	734		
mining law				729, 731	733	627, 630	522
natural gas		236, 242	161				
niter	686				489, 492	481, 506	
peridotite			438	599	735		
petroleum	189, 685	216	147	461	735		
salt	532, 684, 686	842		628	452, 735	442, 463	292, 350
saltpeter	686				611, 734	597	482
	686				735		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Kentucky sandstone	685				735		374, 396
siderite	685				735		
sphalerite	686				735, 11	14	
steel	120, 137		184, 186	18		525	12
structural materials	451		398	531	735		373, 395
witherite	686						
Kerr, W. C., on North Carolina minerals.	659						
Kieserite				607, 697	637		
Wyoming					810		
Kimberly diamond mines, South Africa					563, 568		
Kirchhoff, Charles, on copper	213	322	208	109	66	43	56
lead	306	411	244	140	98	78	70
zinc	346	474	272	154	113	92	88
Kunz, George F., on precious stones	483	723	437	595	555	580	445
Kupfernickel	753, 758				765		
Kyanite		748		607			
Labradorite	495	728, 769			563		
Lake Champlain, New York, iron	117			43	43	17	30, 35
Lake George diamonds	489						
Lake Superior, agate		757					
amethyst		751					
apophyllite		775					
chrysocolla		778					
copper	215, 218, 220	325, 327, 329, 331	210	109	84	54	59, 60, 71
datolite		774					
iron ore	116	262, 264		14, 62, 71	34	17	35
Langson, W. J., coal receipts at Milwaukee.						194	
Lapis lazuli	498	773					
Lead	306	411	244	140	98	78	78
alloyed with tin		632					
and copper chromate					700		
desilverizing	650	462					60
chromate in Arizona					699		
electro-metallurgy	627						
exports		433	260	150	111	90	86
Austria-Hungary		439					
Belgium		439					
France		439					
Germany	323	436, 438					
Great Britain	321	435					
Spain	322	436					
imports		432	259	149	110	79, 90	86
Austria		439					
Belgium		439					
France		439					
Germany	323	436					
Great Britain		435					
foreign industry	321						
in Alabama					694		
in Alaska					695		
in Arizona		416	258	140	110		80
in Arkansas					700		
in Austria	323		271				
in California	767	416		140	104, 703, 710		80
in Colorado	310, 748, 751	412, 416, 419	250, 257	144	105, 712	87	80
in Dakota				140	110, 716		
in France	322	439	271				
in Georgia					721		
in Germany	322	436	267				
in Great Britain	321	435	268				
in Greece	323	440	270				
in Hanover	322						
in Idaho	311	416, 424	258	146	107	88	80
in Illinois	312, 678	414, 416, 425					
in Iowa	682				731		
in Italy	323		269				
in Kansas	312, 682	414, 416, 425		147	110, 732	89	
in Massachusetts	694						
in Mexico	323			141	99	79	
in Missouri	312, 699, 702	414, 416, 425	259	147	110	89	
in Montana	311	416, 422	257		109	89	80
in Nevada	309	412, 416, 418	250	143	104	86	80
in New Jersey	706, 708					761	
in New Mexico	757	416, 425	258	146	110, 764	89	80
in New York	711						
in North Carolina	716						

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Lead in Pennsylvania	721, 726						
Prussia	322						
Russia	323						
Saxony	322						
South Carolina	729						
Spain	322		264				
Tennessee	732						
Texas	735						
Utah	308	412, 416	248	142	103	86	80
Virginia	738	414, 416					
Wisconsin	312, 747	414, 416, 425		148			
market	313			151	101	82	82
molybdate, Arizona					698, 700		
Colorado	446						
Massachusetts					745		
Pennsylvania					785		
Utah					796		
ocher, Virginia	743				803		
ore antimonial, Arizona					696		
prices	315	415, 428	261	151	101	82	83
producing regions	308	416			103	85	
production	XII, XVI, 306	2, 6, 9, 413, 434	2, 5, 7, 245	1, 7, 9, 141	1, 6, 8, 99	2, 7, 10, 79	1, 6, 78
in Australia		434					
Austria-Hungary		434, 439					
Belgium		434, 438					
France		434, 439					
Germany		434, 436					
Great Britain		434					
Greece		434, 440					
Italy		434, 440					
Mexico		434, 440					
Russia		434					
South America		434					
Spain		434					
Sweden		434					
Turkey		434					
world's		434					
refining and desilverizing works		427					
slags		440, 449, 454					
smelting	313, 324, 335					81, 87	
vanadate, Arizona					699		
uses in glass-making		971					
leadhillite	763, 774				699		
Lebanon County, Pa., coal			47				
leblanc, soda process				655			
Ledoux, Albert R., on Florida phosphates						592	
Lennig, Charles, on pyrites			505				
leucoprite		769					
leopardite		770					
lepidolite		777					
Lesley, J. P., on natural gas			179				
leucopyrite	761						
Lewis, H. Carvil, on diamond sources			438				
Lewis, James, & Son's estimate on copper imports into Great Britain.						75	75
lgulite, Alabama	669				694		
Alaska	760				695		
Arizona	761, 763				697, 699	214	
Arkansas	670				702		
California	767				704		
Colorado	43, 749				708	226, 228, 237, 239	
Dakota					716		
Florida	675				720		
Idaho	49, 771	39		252	724		
Illinois	678				727		
Indian Territory	681				730		
Kansas	683	47			733	274	
Kentucky	686				735		
Louisiana	687				736		
Maryland	692				741		
Massachusetts	695				744		
Minnesota	698				743		
Mississippi	698				749		
Montana	756	53	56	282	755		
Nebraska	703						
Nevada			40		757		
New Jersey	708				761		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Lignite, New Mexico	757	56			763		
New York	712				769		
North Carolina	717				773		
Oregon	773		45		778		
Pennsylvania					783		
South Carolina	729				787		
Tennessee	733				791		
Texas	734	89	68	347	792	369, 372	
Utah	774			350	795	376	
Vermont	738				798		
Washington	96, 775	99		358	804		
Wyoming	758	100		374	808		
Lima, Ohio, petroleum			146	458	451	460	318
Lime	458	668, 968	410	565	532	554	
analyses			411				
borate imports		861	493				
in California	767	859			706		
Nevada	772	859			756		
exports	458	669	411	566, 579	534	557	462
imports	458	669	411	566	534		
prices		668		565	534	557	
production	458	668	410	565	6, 532	4, 554	6
in Alabama					532		
California			413	565	532	555	
Connecticut			410		532	555	
District of Columbia						555	
Illinois						555	
Indiana					533	555	
Iowa					533	555	
Kentucky					533		
Maine					533	555	
Maryland					533	555	
Massachusetts					533	555	
Michigan					533	555	
Minnesota					533	555	
Missouri						555	
Montana						555	
New Jersey						556	
New York	458	45		565	533	556	
Ohio			412		533	556	
Pennsylvania					533	556	
Tennessee					533	556	
Texas					533	556	
Vermont					533	556	
Virginia			410			556	
West Virginia			410			556	
Wisconsin					533	556	
summary	13, 16	3, 7, 10	3, 5, 8	3, 7, 9	4, 8	4	6
use in glass-making		670, 968	555				
Limestone			412	539	515	539	373
analyses				542	598		421
for iron flux		7, 669	5, 8, 412	7, 9	13	8, 10	6
hydraulic, Arkansas					702		
California	463						
Connecticut	673				715		
Dakota					718		
Illinois	678					726, 728	
Iowa	682				731		
Kansas	683				733		
Kentucky	685				734		
Maryland	691				740		
Massachusetts	694				744		
Minnesota					748		
Mississippi	698				749		
Missouri	702				752		
New York					766		
Ohio	719				777		
Oregon	463						
Pennsylvania					781		
Tennessee	733				791		
Virginia					801		
West Virginia					805		
Washington	463						
Wisconsin	746				806		
Wyoming					810		
in Alabama				529			373, 377
Alaska	760				606		
Arizona							373, 378
Arkansas	670				701		373, 378
California	767		412	565	703, 705		373, 383
Colorado	462				710		373, 384
Connecticut	673						373, 385
Dakota					717		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Limestone in Delaware	674				718		
Florida	675				719		373, 386
Georgia					517		373, 388
Idaho	770				722		373
Illinois	451, 678			540	515, 726	540	373, 388
Indiana	451			541	515, 729	540	373, 390
Iowa	451, 682				516, 731	540	373, 393
Kansas	451, 683				516, 733	540	373, 394
Kentucky	451, 685			531	516, 733	540	373, 395
Maine	688				737		373, 398
Maryland	451, 691				740		373, 399
Massachusetts	451, 694				744		373, 403
Michigan	451, 696				746	540	373, 403
Minnesota	451, 697				516, 747	540	373, 406
Mississippi	698				749		
Missouri	451, 700, 702			541	516, 751	540	373, 406
analysis							406
Montana							373, 408
Nebraska	451, 703				755	540	373, 408
New Jersey	706				760		373, 410
analysis							410
New Mexico					764		373, 411
New York	451, 709				766	540	373, 413
North Carolina	715				771		
Ohio	451, 719		412	540	516, 776	540	373, 417
analysis							417
Oregon			412		778		373, 418
Pennsylvania	451, 723			527	516, 781	541	373, 420
Rhode Island							373, 428
South Carolina	728				786		373, 428
South Dakota							373, 429
Tennessee	451, 731, 733				789		373, 429
Texas	734				793		373, 431
analysis							432
Utah	773				794		373, 432
Vermont	451						373, 433
Virginia	451, 740				801		373, 436
Washington			412		803		373
West Virginia	744				806		373, 437
Wisconsin	451, 746				516, 807	541	373, 439
analysis							439
Wyoming					808		373, 440
magnesia in Arizona					697, 699		
Rhode Island					785		
Utah					795		
new developments			412	542	517	541	
oolitic, rendering impervious							
production						539	373
quarries and capital invested	450		5, 412	539	6, 8, 515	517	
Limonite		382, 728					
in Alabama	449, 668			85	691		
Arizona	761, 763				697, 699		
Arkansas	671				702		
California	769				705		
Colorado	751				710		
Connecticut	672	728			714		
Dakota					718		
Delaware	674				719		
Florida					720		
Georgia	676			84	721		
Idaho	770				723		
Illinois	679				727		
Indiana	680				730		
Iowa	682				732		
Kansas	684				733		
Kentucky	685			97	734		
Maine	689			41	737, 739		
Maryland	691				740		
Massachusetts	693, 695	728			743		
Michigan	696				747		
Minnesota	698				748		
Mississippi	699				749		
Missouri	700			97	751, 753		
Nebraska	703						
New Hampshire	705				759		
New Jersey	707			52	760		
New Mexico	757				763		
New York	709				766		
North Carolina	715			83	668, 771		
Ohio	719, 721			56	776, 778		
Oregon					778		
Pennsylvania	723				781		
Rhode Island	727				785		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Limonite in South Carolina	729				787		
Tennessee	731				789		
Texas					794		
Utah	774				795		
Vermont	736				797		
Virginia	740			80	801		
Washington	775				804		
West Virginia	744				805		
Wisconsin	746				807		
Wyoming					810		
Lincoln, Nebr., structural materials						529	
Linnæite, Maryland	692				741		
Litharge and red lead	769	925, 971	524		705	616	511
imports		925			675	617	511
prices		925	524			616	
Lithia emerald or hiddenite	501	748	437			584	
Lithographic stone	595	935		690			6, 519
foreign	596	935		691			
imports	596	936		691			520
in Alabama	595	935					
Arkansas					701		519
California	769	935			705		
Dakota					718		
Illinois		935					
Indiana					729		
Iowa	595	935					
Kentucky	595	935			734		
Missouri	595	935			735		
Nebraska	703				756		
Tennessee	595, 731	935		690	790		
Texas		935		691			519
Virginia							519
Wyoming					810		
production				5, 690			6, 519
Little Rock, Ark., structural materials				530		522	
Löllingite, Maine	689				739		
Longfellow (Ariz.), smelting works	261					320	
Lorberry, Pennsylvania, coal district	23		53				
Los Angeles, Cal., structural materials				530	508	528	
Louisiana, brick production				568	536, 538	560, 565	
brines	687				736		
calcite					736		
clay	686				737		
coal	687				736		
gypsum	526	809			736		
hematite					736		
iron ore					50, 736		
lignite	687				736		
marble					736		
marl	524, 686				736		
mineral waters		982	538		630	630	
natural gas			161				
petroleum	687				736		
pottery clay	470		414				
rock salt					736	604	
salines	554						
salt	532, 686	841	480	623, 636	611, 620,	597, 604	482, 488
sandstone	687				736		
structural materials					736		
sulphur	687	864	496		509	525	
Louisville, Ky., coal trade	103				736		
structural materials				531		197	165
Lower California, nickel		539				525	
Lower Kittanning, Pennsylvania coal bed,		80				342, 345	
Loyalsock, Pennsylvania coal basin	15, 25		46	297	290	302, 320	
Luxemburg, coal production						208	
pig-iron production						29	21
Luzerne county, Pa., coal			46	304	292	302	245
Lycoming county, Pa., bituminous coal		76					
Lykens Valley, Pennsylvania, coal	23		53		310	320	
Lynchburg, Va., structural materials						535	
McKean county, Pa., bituminous coal		85	57		340	355	266
Macksburg, Ohio, petroleum			130, 146	460	451	462	318
Madison, Wis., structural materials					511		
Magnesia				696			
cement						554	
imports				698			
Magnesite	708			6, 695	699		
Arizona	763				699		
California				696	704		
New Jersey	708				762		
New York	712				769		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Magnesite, North Carolina	717				774		
Pennsylvania	726				784		
Magnesium				694			
chloride					639, 810		
hydrate	707				761		
sulphate	732				791, 810		
Magnetic iron ores in							
Alabama	149, 669			85	694		
Arizona	761, 763				699		
Arkansas	671				702		
California	767, 769				706		
Colorado	651, 753				710, 713		
Connecticut	673				715		
Georgia	76, 722				722		
Idaho					724		
Maine	689			41	739		
Maryland	692				742		
Massachusetts	695				745		
Michigan	696			63	746		
Minnesota	697			73	748		
Missouri	701				751		
Nevada					757		
New Hampshire	705			42	759		
New Jersey	707	274		50	761		
New Mexico	758				764		
New York	710			46	766		
North Carolina	715	277		82	668, 771		
Oregon	723				778		
Pennsylvania	724			52	781		
Rhode Island	727			42	785		
South Carolina	729			34	787		
Tennessee	732			92	790		
Texas	735				794		
Utah	775				796		
Vermont	738				798		
Virginia	741, 743			78, 80	801		
Wisconsin	746			71	807		
Wyoming					810		
iron pyrites in							
Arizona	762				697		
Colorado	752				711		
Connecticut	673				715		
New Hampshire	706				760		
New Jersey	708				762		
Oregon					779		
Pennsylvania	726				784		
Virginia	743				803		
Magnetite. (<i>See</i> Magnetic iron ore.)							
Mailloux, C. O., on electro-metallurgy	627						
Maine, amazon stone		770					
amethyst	491	750		596			
andalusite	497	742					
antimony	690						
apatite		775					
aquamarine	487						
argenteite	687				736		
arsenopyrite	689				738		
axinite		765					
barytes	580, 689				738		
beryl	739	723, 739		595	744		
bog iron ore	689				737, 739		
manganese	689				738		
bornite	687				736		
brick					536	560, 565	
cancrinite		773					
cassiterite	687	767			738		
cement	461	672					
cerargyrite	687				738		
chalcocite	687				736		
chalcopyrite	687						
chrysoberyl		736					
clay		677					
copper	216, 360	329	210	112	736	54	60
diamonds	687	730					
elæolite		770, 773					
emerald		759					
essonite	488	746					
feldspar	689	933	523	701	737		
fire-brick production						566	
flagging stone	687				737		
galena	687				738		
garnet		745					
gems and precious stones	483	723		595	555		
glass sand	690				737, 739		
gneiss	688				737		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Maine, gold	172, 176,		200	104	737	36	
granite	688			520, 537	513, 737	536, 538	374, 396
graphite	688					737	
grossularite	689	747					
hematite	689				737		40
idocrase	492	767					
infusorial earth					738		
iron	129, 689	252	182	17, 41	11, 739	14	10, 17
ores	120, 689		182	41	42, 737	14	24
jasper		672					
kyanite		748					
lepidolite		777					
lime	458				533	555	
limestone	688				737		373, 398
limonite	689			41	737		
löllingite	689				739		
magnetic iron ore	689, 690			41	739		
malachite	688						
manganese ore	689	551			145, 738		
marble	688				737		
marl	524, 689				739		
mica	583, 688	907	437		737		
mineral waters		982	538	630, 716	684	627, 630	522
mispickel	689				738		
molybdenum sulphide	689				739		
ocher	689				737, 739		
potash and pearlsh					643		
precious stones				505	555		
pyrargyrite	688				737		
pyrites	689				739		
pyrolusite	690	551			739		
pyrrhotite	690						
quartz	490, 690	749, 751		505	737, 739		
rhodonite		766					
sandstone	688			520	737, 739		
serpentine	690	776					
sienna			532				
silver	172, 176,	312	200	104	736	36	
	687						
slate	452, 688		308	519	522, 737	547, 549	376, 398
sodalite		773					
sphalerite	688				737, 739		
spodumene					758		
staurolite		743					
steel	137		184	17	11	14	
stephanite	689				738		
stibnite	690						
structural materials				519			
syenite					737		
talc	689				738		
tetrahedrite	689				738		
tin ore	687	598			738		
topaz	486	738		506			
tourmaline	488	743		505			
tripolite	689				738		
wad					738		
zircon		661, 741					
Malachite.	497	382, 777	441	597			
Arizona	761	777	441		697		
Arkansas	671				702		
California	769				705		
Connecticut	673				715		
Dakota					717		
Idaho	770				723		
Maine	683						
Maryland	691				740, 742		
Missouri	702				753		
Montana	755				754		
Nevada	772	777			756		
New Hampshire	704				758		
New Jersey	708				762		
New Mexico	757				764		
New York	712						
North Carolina	715	778			774		
Pennsylvania	724	778			782		
South Carolina	729				787		
Tennessee	732	778			790		
Utah	774				795		
Vermont	736				797		
Virginia	741	777			801		
Wisconsin	746				807		
Wyoming					809		
Manchester, N. H., structural materials				520			

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Manganese, by Joseph D. Weeks		550	303	180	144	123	127
alloy	424	566					
as glass decolorizer		554, 959					
carbonate, Wales						140	
exports and imports		556				136	129
in Alabama	669	552	345	183	694		
Algeria			307				
Arizona	762				696, 699		
Arkansas	671	553	305, 332	181, 184	144, 147, 701	126	127, 130
Asia							130
Australia				207		143	130
Belgium					154	143	
Bosnia						142	130
California	424, 769	554	305, 349	197	706	124, 128	127
Canada			350	198		136	130
Chile				206			130
Colorado			348		144		127, 131
Connecticut			342				
Cuba					154	137	130
Dakota					718		
France				200		141	130
Georgia	424, 676	551	305, 328	181, 185	144, 150, 722	124, 127	127, 133
Germany		555		201	161		
Great Britain		555		199	154	140	130
Greece				203		143	130
Holland						143	130
Idaho	771				724		
Italy				202		143	130
Magdalen Islands			355				
Maine	689	551	342		145		
Maryland	692	551	344		742		
Massachusetts	695	551	342				
Michigan			346	188		124, 128	
Missouri			346				
Montana	755		349		144, 754		
Nevada	425	554	305, 349	197		124, 128	127, 134
New Brunswick			350			135	130
New Hampshire	706	551	342				
New Jersey			336				
New South Wales				207			
New York		551					
New Zealand				207		142	130
North Carolina	424, 717	551	344	190	144, 151	124, 129	127, 134
Nova Scotia		554	351, 356	198	153	133	130
Oregon				197			
Pennsylvania	726	551	342		784	124	
Portugal		555		201		143	130
Quebec							130
Rhode Island	727	551	342				
Russia		555		204	161	141	
South Australia				207		142	
South Carolina	424, 552			193	787	124, 130	127, 134
Spain		555		201	155, 159	143	130
Sweden		555				142	130
Tennessee	424, 733		344	193	791	124, 131	127, 135
Texas	736						
Turkey				205		142	130
Utah	774				795		
Vermont	737		551	342	145, 798	124, 131	127, 135
Virginia	424, 741	551, 555	305, 307, 309 312, 314, 323	181, 195	144, 151, 802	123, 132	127, 135
West Virginia	424, 745				806		
Wisconsin				188		128	
Wyoming					810		
ore analyses	425	551, 553	302, 311	180, 185, 200	144, 148, 156	129, 132, 138	
argentiferous production			305	181	147	126	128, 129, 133
exports		556				139	
imports		556			155	141, 143	
prices		556					
production	XII XV	3, 7, 555	3, 5, 304, 315	2, 7, 181, 183	2, 6, 145, 151	2, 123, 134, 143	2, 6, 127, 129
value		556	304	182	145	125	
steel, electrical properties		562, 565			161		
uses	426	550, 555, 560	545, 555				
Manganiferous iron ore	427		304	181	146, 151	125	128, 129, 133
zinc ore			336				129

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Manganite.....	763	382			699		
Marble.....	450, 456, 464	666	398	543	517, 527, 808	541	375
analyses.....				543			
exports.....	452	606	404	555	526	551	
imports.....	452	605	404	554	525, 527	550	375
in Alabama.....	608			543	692	542	
Alaska.....		605					
Arkansas.....	670				701	542	127, 130
California.....	450, 767		412	545	518, 703	541	375, 382
Colorado.....	454, 753		544	544	518, 707, 713		385
Connecticut.....	672				714		
Dakota.....					717		
Georgia.....	676			542	518, 721	541, 543	375, 387
Idaho.....	771			546	724		375, 388
Illinois.....	451						
Indiana.....	451						
Iowa.....	451, 682				731		
Kansas.....	451				733		
Kentucky.....	451, 685				734		
Louisiana.....					736		
Maine.....	688						
Maryland.....	451, 691			541	518, 740, 742	541	375, 400
Massachusetts.....	451, 693			541	743, 745		375, 403
Michigan.....	451						375, 403
Minnesota.....	451						
Missouri.....	451, 701				520, 751		
Montana.....	454						
Nebraska.....	451						
Nevada.....	457				519		
New Jersey.....	707				761		
New Mexico.....					764		
New York.....	451, 710			541	518, 767	541	375, 414
North Carolina.....	717				774	543	415
Ohio.....	451						
Oregon.....							418
Pennsylvania.....	451, 724				782		375, 427
South Carolina.....	728						375, 428
Tennessee.....	451, 732			541, 543	518, 790	541, 543	375, 429
Texas.....	735				794		
Utah.....	774			546	519, 796	543	432
Vermont.....	451, 736			541	518, 797	541	375, 433
Virginia.....	741			544	520, 801	544	375, 436
Washington.....							
Wisconsin.....	451					544	
Wyoming.....					809		375, 440
onyx.....					703		408
production.....			398	541	517	541	
quarries.....	450				519	542	
Marcasite.....	770		516		702, 722		
Marl.....	XIV, 512	4, 7, 10	464	4, 619	4, 595, 824	5, 595	451
composition.....	525			620			
green sand.....				619	718		
Delaware.....					740		
Maryland.....						5, 595	
New Jersey.....	525			619	772		
North Carolina.....					790		
Tennessee.....					801		
Virginia.....					592, 692	5, 595	
in Alabama.....	668	868	464	619	701		
Arkansas.....	524			619	706		
California.....	769				719		
Delaware.....	522, 674				721		
Florida.....	523, 675			619	592, 719	5, 595	
Georgia.....	523, 676		454		727		
Illinois.....	679				730		
Indiana.....	681				734		
Kentucky.....	685			620	735		
Louisiana.....	524, 686				739		
Maine.....	524, 689				740		
Maryland.....	522, 691				749		
Minnesota.....					756		
Mississippi.....	524, 698		464		759	5, 595	
Nebraska.....	703				756		
New Hampshire.....	524, 705				759		
New Jersey.....	522, 707	808	464	619	592, 761	5, 595	
New York.....	524, 710				767		
North Carolina.....	523, 715			619	772	5, 595	
Ohio.....	524, 721				778		
Pennsylvania.....	724				782		
South Carolina.....	505, 513, 523, 728				786		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Marl in Tennessee	524, 732				790		
Vermont	738				798		
Virginia	523, 741				592, 801	5	
West Virginia					805		
Wyoming					810		
summary				4		5, 8, 10	4, 6
uses	527					596	
Martite, Michigan		877			746		
Martyn, William, on pyrites					741		
Maryland, alipite							
amber		780					
asbestos	588, 692	913			741		
bornite	690				739, 741		
brick				567	536, 538	560	
bronzite		773					
calamine	692				741		
carrollite	692				741		
cement		672					461
chalcocite	690				739		
chalcopyrite	690				739, 741		
chalk	693						
chrome iron ore	428, 690	507	358		739, 741		
chrysocolla	692				741		
clay	690				739		
coal	6, 33, 58, 690, 692	12, 49	11, 33	230, 272	171, 263, 270	280	146, 221
miners' wages	103		34	279			
production			33	278	268	171, 280	
receipts, Baltimore						182	
shipments	59	50	59	271	264	182, 282	
value				272	263	280	
cobalt	692	544			741		
coke	130				22		
copper	231, 690, 692				741		
ores	690				739		
works	217						
corundum					741		
emerald nickel	693				742		
emery	692				741		
enstatite		773					
fire brick and clay	691				740	566	
freestone	691				740		
galena	692				741		
gneiss	691				740		
gold	692				740		49
granite	691				515, 740	536, 538	374, 398
graphite	692				741		
gypsum	692				741		
hematite	691			77	740		40
hydraulic limestone	691				740		
infusorial earth	693	720	433	587	554	578	
iron	125, 133, 691	252	182, 184	18, 23, 32, 77	11	14, 23	10, 17
ores	692			77	740		24, 34
kaolin	470, 691				740		
lignite	692				741		
lime	691				533	555	
limestone	451, 691				740		373, 399
limonite	691			77	740		
magnetic iron ore	692			77	742		
malachite	691				740, 742		
manganese ore	692	551	344				
marble	451, 691			541	578, 740, 742	541	375, 400
marl	522, 691				740		
melacomite	691						
mica		908					
mineral waters		982	538	716	684	627, 630	522
molybdenite	692				742		
nickel silicate					741		
ocher	692		527		742		508
potters' clay	470						
pyrites	692				742		
pyrolusite	692						
quartz					740		
sandstone	691			528	740		374, 399
serpentine	691				740		400
siderite	693	776			741		
silver					742		49
slate	452, 692			550	741		376, 399
smithsonite	692				741		

	1882.	1883-'84	1885	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Maryland, sphalerite	692				741		
steel			186			14	
structural materials				528		526	
sulphuric acid	578						
talc	693				742		
terra cotta		700	422				
tripolite	693				742		
zaratite	693				742		
zinc ores	365, 692				741		
Massachusetts, agate	694	756			743		
amazonstone		770					
amber	498, 694	779			743		
amethyst					743		
anglesite	694				743		
apatite	521, 694				743		
aquamarine	487						
arsenopyrite	694				743		
asbestos		913			743		
barytes	694				744		
beryl	694	739			744		
brick	458				536, 538	500, 566	
cassiterite	694				744		
cerussite	694				744		
chalcopyrite	694				742, 744		
chiastolite	497						
chrome iron ore	694	569			744		
clay	465				742, 744		
coal, anthracite	694	87			744		
receipts at Boston					178	178	
copper ores	231, 694				742, 745		
copperas	607						
corundum	476				742		
diaspore		738					
elæolite		770					
emery	694				742		
feldspar	694	933		701	744		
flagging stone	693				743		
fuller's earth					744		
galena	694				744		
garnet	694	746			744		
gmelss	693				743		
gold	694				744		
granite	693			537	513, 743	536	374, 400
graphite	694			225	744		
grindstone	694				744		
hematite	693			42	743		40
hornblende		728					
ilvaite		768					
infusorial earth					743		
lolite		743					
iron	133, 695	252	182	17	11	14	10, 17
ore	120, 693			42	743		24
pyrites		878	503	651	743		
jade					743		
jasper		762			743		
kaolin	695				744		
kyanite		748					
lead	694				743		
lignite	695				744		
lime	694				533	555	
limestone	451, 694				744		373, 403
limonite	693, 695	728			743		
manganese	695	551	342		745		
marble	451, 693			541	743, 745		373, 403
meerschaum		781					
mica	695	908			745		
mineral waters		982	538	717	684	627, 630	522
mispickel	694				743		
molybdate of lead	695				745		
ocher	695				745	618	508
peat	693				743		
pyrites	693, 695	878	503	654	743, 745		
pyrolusite	695				745		
pyroxene		728					
quartz		751			743		
rhodonite	496	766				582	
sand	693				743		
sandstone	451, 693				743		374, 402
scapolite		773					
serpentine	695	776			745		
siderite	695				745		
slate	452, 693				743		
sodalite		773					
sphalerite	695				745		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Massachusetts, staurolite		743					
steel	120, 137		184, 186	17	11	14	
structural materials	450			521	500	526	
syenite					743		
talc	695				745		
terra cotta		700					
tetrahedrite	695				745		
tin ore	694	597			744		
topaz					743		
tripolite					743		
wulfenite	695				745		
zincblende	695				745		
zircon		661					
Massicot, Colorado	751				710		
New Mexico	757				764		
Virginia	743				803		
Meerschaum		780		605			
imports			444				
in Massachusetts		781					
New York		781					
Pennsylvania		780					
Melaconite, Alabama	670				694		
Arizona	761						
Maryland	691						
North Carolina	715				774		
Pennsylvania	726				784		
Tennessee	732				790		
Virginia	741				801		
Wyoming					810		
Memphis, Tenn., structural materials				529		533	
Menaccanite	149, 712		441		688, 769		
Menominee range, Lake Superior, iron ore			188	65	16, 39		35
Mercer County, Pa., bituminous coal		85	57	335	341	355	
Mercurial preparations, imports		499	293	166	125	104	101
Mercury, native, California	767				704		
selenide, Utah					796		
(See also quicksilver.)							
Merton, Henry R., & Co., on spelter in Europe.						95	92
Metallic paint							
Metals, summary	XI	2	2	1	1	1	1
Meteoric, iron		289					
Mexican onyx					563		
Mexico, amber						583	
copper		356, 361, 373	233	123	87	73	
gold		314, 319					
graphite				688			
lead ores	323	434, 440		145	99	79	
mining law		999					
opal mines					575		
petroleum		233					
silver-lead ores		314, 319		106, 141	62	79	
tin ore		623					
Miargyrite, Arizona	761				697		
Mica	583	906	518	5, 7, 9	660	614	474
exports		912			661		
imports		912	520		660, 664	614	475
in Alabama		908			671, 693		
Alaska		584			696		
Arizona	762, 764	911			697		
Arkansas		911			702		
California	587, 769	911	519		706		
Colorado	583, 753	911	518		713		
Connecticut		908			714		
Dakota	583, 754	604, 909			660, 717	614	
Georgia	672	908			671, 721		
Idaho	583, 771				723		
Maine	583, 688	907			737		
Maryland		908					
Massachusetts	695	908			745		
Nevada	583		519				
New Hampshire	583, 704	907	518		660, 671, 757	614	
New Jersey	708				762		
New Mexico	583, 758	911			660, 764	614	
New York	712				769		
North Carolina	583, 661, 715	908	518		660, 665, 671	614	474
Oregon		911					
Pennsylvania	583, 726	908	518		784		
South Carolina		908			671		
Utah	774				796		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Mica in Virginia	743	908			660, 671, 803 671	614	
West Virginia							
Wisconsin	747						
Wyoming	583, 759	911	518		809		
prices			520		664	614	
production	14, 584	5, 7, 912	4, 519	5, 7, 9	6, 660, 671	6, 614	4, 6, 474
uses						615	
veins, North Carolina					666		
waste					661, 669		
Michigan, amethyst	696	751			747		
arsenical copper					747		
barytes	696				747		
brick					536, 538	560	
brines				628	746		482, 484
bromine			486	642	626	613	493
chalcopyrite	696				747		
coal	6, 34, 695	12, 50	11	230, 279	171, 270, 745	171, 284	146, 226
prices			34			190, 284	
production				230, 279	271	171, 206, 284	146, 226
receipts at Detroit						191	
copper	215, 695	329, 331	210	111, 113, 126	745, 747	52	
domeykite	696				747		
fire brick and clay	467, 696				746	566	
flagging stone	696				746		
gold	696			105	59, 746	37	49
granite	696				746		
graphite	696				747		
grindstones		713		582	552	576	
gypsum	527, 696	809	459	620	595, 601, 746	6	465
iron	125, 696	135, 252, 264	182	14, 18	11	14, 17, 23	10, 17
ores	696	264, 268, 276	182	14, 62	746	17	24, 40
lime					533	555	
limestone	451, 696				746	540	373, 403
limonite	696				747		
magnetic iron ore	696			63	746		
manganese ores				71, 188		123, 128	
manganiferous iron ore				189	151	125	
marble	451						403
martite					746		
mineral waters		982, 986	538, 542	717, 720	684, 687	627, 630	522
natural gas				513		483	367
plaster	527	810	462	621	746		465
potash and pearlash					643		
salt	532, 536, 696	828	474	629	611, 746	597, 600, 613	482, 484
sandstone	451, 696			582	746	544	374, 403
siderite	697				747		
silver	176, 697			105	59, 746	37	49
slate	696		398		522, 746	547	376, 403
specular ore				63	746		
steel	120, 137		186		11	14	
structural materials						527	
tile					575		
Microlite		772					
Millerite	724				701, 769	113	
Millstones	477	713	3	581	552	576	3, 6, 456
in Alabama	669				693		
Georgia	675				720		
Missouri	701				752		
New York				581	552	576	456
North Carolina	715			581	772	576	
Ohio	719				552, 776		
Pennsylvania				581	552	576	456
Tennessee	732				790		
Virginia	741				801		456
Wyoming					810		
Milwaukee, Wis., coal market	103				182	193	162
structural materials				535		535	461
Mine La Motte, Mo., cobalt	421					110	
nickel	403					110	
wolfram	431						
Mineral paints		920	524	702	674	616	508
barytes	580	922	524	705	676	618	513
cobalt oxide	421	547	364	174	131	620	124
graphite	590	915	533	713	679	361	507

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Mineral paints, imports				703	675	617	
litharge	925	524	703	675	616	511	
ocher	926	526, 529	708, 710	677	618	508	
orange mineral		524	703	675		511	
Paris white	920, 930	526	707	677	621	512	
production	xiv	5	4	5	6, 8	6	4, 6, 508
quicksilver vermilion	501		713	679	622		
red lead	920, 924		703	675	616	511	
971							
sienna	928	532	712				
slate	929	532	713				
terra alba	924	526	706	676	621		
ultramarine	928	526	707	677	622		
umber	927	532	713	678	619		
white lead	920	524	702	674	616	512	
whiting	920, 931	526	707	677	621		
zinc white	921	524	704	675	617		
pitch, Missouri				752			
soap	772				756, 810		
waters, by A. C. Peale	772	5, 7, 978	4, 536	5, 7, 10, 715	5, 680	2, 623	4, 522
wax	774				795, 809		481
wool	161						
Minerals found in Butte City, Mont., mines		382					
Stassfurt salt beds					631		
Mining law				722			
historical sketch		988					
of Alabama				731			
Georgia				731			
Illinois				750			
Indiana				746			
Kentucky				731			
Maryland				730			
Massachusetts				730			
Michigan				731			
New York				732			
North Carolina				731			
Ohio				734			
Pennsylvania				759			
Tennessee				731			
Virginia				730			
Wisconsin				731			
rights of aliens				729			
Minneapolis, Minn., coal trade						196	164
structural materials			398	532		527	
Minnesota agate		757					
barytes	697				748		
brick					536, 538	561	
catlinite	498	778			747		
cement		672		556	527, 747	551	461
chalcocite	697				748		
clay					747		
coal	698				748	196	
receipts, Duluth						195	164
Minneapolis						196	
St. Paul						196	
shipments at Minneapolis						196	
copper	697				748		
fire clay	697						
flagging stone	697				748		
galena	698						
gold	698						
granite				538	747		374, 404
gypsum	698				748		
hematite	697			73	747		39
iron	120, 698	952	182	18, 73	11		10, 17
ore	697	267		14, 73	39, 748	17	24, 35, 39
kaolin	471, 698				748		
lignite	698				748		
lime					533	555	
limestone	451, 697				516, 747	540	373, 404
limonite	698				748		
magnetic iron ore	697			73	748		
marble	451						
mineral waters		982	538	717	684	627, 630	529
natural gas					749		
peat	698				749		
pipestone	498				747		404
potash and pearlash					643		
pyrites	698				749		
quartzite	697				748		
salt brines					748		
sandstone	451, 697			532	748	544	374, 404

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Minnesota, shell marls					749		
silver	698				749		
slate	697				749		
sphalerite	698				749		
structural materials	451			532		527	
Mints, coinage of gold and silver					83		39
Mirabilite	763				778, 809		
Mispickel		617	516				
in Arizona	760				696		
Colorado	748				707		
Connecticut	672				714		
Georgia	676				731		
Idaho	770				722		
Maine	689				738		
Massachusetts	694				743		
Montana	754				753		
New Hampshire	705				759		
New Jersey	707				761		
New York	711				768		
North Carolina	716				773		
Rhode Island	727						
Utah	773				794		
Vermont	737				798		
Virginia	742				803		
Mississippi brick and clay	466, 698				536, 749	561, 565	
coal	698				749		
glass sand					750		
gypsum	698				749		
hematite	699				749		
iron ore					48		
lignite	698				749		
limestone	698				749		
limonite	699				749		
marl	521, 698		453, 464		592, 749	595	
mineral waters		982	538	717	684	627, 630	522
ocher	699				750		
phosphate			453	618			
pottery clay	470						
quartz					750		
sand	699						
sandstone					750		
structural materials						528	
umber				713			
Missouri antimonial lead production		650					
arsenical nickel					753		
asbolite	701				752		
asphaltum	701				752		
azurite	701				752		
barytes	580, 699			706	750, 676	618	513
bitumen	701				752		
bog ore	700				751		
brick					531, 538	561, 565	
brines					752		
buhrstones		712					
cadmium sulphide					752		
calamine	699				750, 753		
cement					527, 529	551	461
cerussite	699				750		
chalcocite	701				752		
chalcopyrite	699				750		
clay					750, 753		
coal	6, 34, 61, 699	12, 51	11, 35	230, 380	171, 372, 750	199, 285	147, 226
analyses		52			274	287	
prices						198	
production		52		281	273	171, 285	147, 226
receipts St. Louis						199	166
shipments				282		200	147, 226
value				280		285	147, 226
cobalt and nickel	701	545	362		753	110	124
cobaltite	701				752		
coke	130			401	383, 405	199, 395, 410	
copper	216, 230, 701	329, 342	210	112	69, 750, 752	54	60
copperas	607						
feldspar			523				
fire brick and clay	466, 699				511		
flagging stone	699				750		
fluorspar		777					
galena	700				750		
glass sand					752		
gold	701				752		
granite	700			533	751		374, 405

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Missouri greenockite	701				752		
gypsum	701				752		
hematite	700				751		40
hydrozincite	702				753		
iron	125, 700	252, 268	182	18	11, 46	14, 23	10, 12, 17
ores	702			14, 97	751		24, 35, 40
kaolin	702				753		
lead	312, 609,	414, 416,	259	147	110, 750	89	80
	702	425					
lime						555	
limestone	451, 700,			541	516, 751	540	373, 406
	702						
limonite	700			97	751		
lithographic stone	595	935			753		
magnetic iron ore	701				751		
malachite	702				753		
manganese			346				
marble	451, 701				520, 751		
millstone	701				752		
mineral pitch					752		
waters		982	538	717	684	627, 630	522
natural gas			161		495		
nickel	702	539			753	110	124
niter	702				753		
ocher	702			709	750, 753		508
onyx							408
petroleum		220					292, 361,
							368
potter's clay	470						
pyrite	702				753		
pyritous copper					750		
pyromorphite	702				753		
quartz	701				752		
salt	702	843			752		
salt peter	702				753		
sand	701				752		
sandstone	451, 701			533			374, 405
sewer pipe production		701					
siderite	702				753		
silver	702				753		
smallite	702				753		
smithsonite	701	752			752		
sphalerite	701				752		
steel	120		184, 186	18	11	14	12
rails	136, 702		184	18	11	14	12
structural materials				583	509	523	
tin ore		602					
zinc	347, 368,	476	114	155	750, 753	92	88
	699, 701						
Mobile, Ala., coal trade	103					201	167
structural materials					567	523	
Molybdate of lead, Arizona	762, 764				698, 700		
Massachusetts	695				745		
Pennsylvania					785		
Utah	774				796		
Molybdenite		382, 617					
in Arizona	764				699		
Colorado	753				713		
Connecticut	673				715		
Georgia	676				722		
Idaho	771				724		
Maine	446, 689				739		
Maryland	692				742		
New Hampshire	446, 705				759		
New Jersey	708				762		
New York	712				769		
North Carolina	717				774		
Pennsylvania	726				784		
Rhode Island	727				786		
Texas	735						
Utah	444, 774				795		
Monazite, North Carolina					772		
Montana antimony							141
argentite	754				753		
arsenopyrite	754				753		
bismuth			389				
bornite	754				753		
Butte City mines	224	374					
cerargyrite	754				753		
cerussite					754		
chalcocite	754				754		
chalcopyrite	754				754		
coal	7, 61, 756	12, 52	11, 36, 83	230, 282,	171, 275,	289	147, 228
				754			

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Montana coal analyses	53			285		291	
fields	52			283		289	
mines and localities				282		292	
production	53			230, 282,	275	171, 206,	147, 228
value				288		289, 291	
value				282, 288		289	147, 228
coke		149, 152,	77, 82, 92	378, 402	383, 405	395, 400,	
		168				412	
copper ores	216, 224,	329, 336	210, 215	112, 117	74, 753	2, 57	60
	754						
corundum crystals		736					
crucible manufacture		702					
diamond		733					
fahlerz					755		
fire brick and clay	472	702			542		
fluorspar	587						
galena	755				754		
gold	172, 176,	312	200	105	59, 754	36	49
	182, 755						
quartz	490						
granite							374, 408
gypsum	528	812					
iron	147, 755	285	196		754	34	
ore						1	24, 40
lead	311	416, 422	257		109, 754	89	80
carbonate					754		
production		422	257		109	89	
telluride					754		
lignite	756				755		
lime						555	373, 408
limestone							373, 408
malachite	755				754		
manganese ores	755		349	180	144, 754		
mineral waters		983	538	720	687	630	
mispickel	754				753		
moss agate	491						
nagyagite	755				754		
peridot	492						
pyrargyrite	755				754		
pyrites	755				754		
rhodonite		766			755		
salt	541						
sandstone							373, 408
sapphire	485	736					
silver	172, 176,	312	200	105	59, 753	36	49
	182, 754						
sphalerite	755				755		
telluride of lead					754		
tellurium	447						
tetrahedrite	756				755		
tin ore		613					
Montgomery, Ala., structural materials					507	522	
Moonstone	495	770			574		
Moonita copper mine, South Australia	254						
Moreman, Ky., natural gas well						506	
Morrisey diamond		729					
Morrison, Colo., fire clay from	473						
Moses, Otto A., on South Carolina phosphates	504						
Moss agate	491	759, 781		604	556, 711,	584	446
					810		
Muriate of potash					641		
Nagyagite, Montana	755				754		
Nails	134	250	185, 187	11, 19	10	12	13
Napa, Cal., chromium	428						
consolidated quicksilver mine	389, 396			161	119	99	95
Natrolite	497	774					
Natural coke, Virginia					803		
gas		233, 235	155	488	464	481, 510	366
capital invested in				493	466		369
chief sources of supply		236	162	488	464	490, 499	
coal displaced by		233	156	490	26, 465	482, 484	367
coke				501			
consumption		233	156	489	24, 27,	481, 483,	366
					465, 543	504	
economies in the use of				497			
geological distribution		236		489	464, 475	481, 500	
history		238	169		25	486, 498	
in Alabama		236, 243	161		494		
Arkansas			161		498		
California		236	161		499, 706	509	
China		243					
Colorado			161				
Dakota		236, 243	161, 168		498, 713	510	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Natural gas in Illinois	236, 243	156, 168	511	466, 726	483	367	
Indiana	243	161	508	26, 464, 485, 729	499	367	
Iowa		161	513				
Japan					511		
Kansas	236, 243	161, 168	514	466, 496, 733	483	367	
Kentucky	236, 242	161		489, 735	481, 497, 506		
Louisiana		161					
Michigan			513		483	367	
Minnesota				749			
Missouri		161		495			
New York	233, 243	156, 166, 170		464, 769	489	367	
Ohio	233, 242	156, 161, 166, 172	504	26, 464, 482, 776	484, 489, 496	367	
Pennsylvania	233, 243	156, 167, 171	491, 502	24, 464, 474, 782	334, 481, 489	367	
Quebec				501			
Russia, Baku district	243						
Tennessee		161		492	510		
Utah		161	515				
West Virginia	233, 242	156, 173	504	26, 466, 484	483	367	
Wisconsin		161					
Wyoming		161					
Industry, Bowling Green, Ohio.					493		
Findlay, Ohio					491		
Fostoria, Ohio					493		
North Baltimore, Ohio.					494		
Tiffin, Ohio.					494		
pipe lines							368
prices		159	496	478			366
production	2, 7, 10	2, 5, 9, 157	3, 7, 10	6, 8, 465, 481	486, 504	366	
storage		176					
transportation			493				
uses	242	169, 172, 174	497	24, 27	334, 485		
waste		176	498			487	
Nebraska, brick					536, 538	561	
clay	467, 703				756		
coal	34, 702	55			171, 276, 755	171, 206, 292	147, 231
galena	703						
gold	703						
gypsum	703		623	756			
hematite	703						
iron and steel	120, 125, 133		185	18	11		
limestone	451, 703				755	540	373, 408
limonite	703						
lithographic stone					756		
marble	451						
marl	703				756		
mineral waters		983				630	522
ocher	703				756		
peat	703				756		
salt	703	843			756		
sandstone					755		
structural materials				534	510	529	
zincblende	703						
Nevada, alum				681			
amethyst		751					
anglesite	772				756		
antimony	438, 772	642			757		141
bestos	588	913					
azurite	772				756		
barytes					756		
borate of lime	772				756		
borax	566, 568, 570, 573, 576	859	491	678	4		494
carbonate of soda	601, 772						
cerusite	772				756		
chalcedony		757					
cinnabar	772				756		
citrine		751					
clay	702				755		
coal			40		757		
cobalt ores		515	361			620	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Nevada copper	216, 290, 772	329, 342	210	112	69, 757	69	60
corundum		735					
galena	772				756		
garnet		745					
gold	72, 176, 182	312	200	104	59, 756	36	49
granite							374, 409
graphite	772	916			757		
gypsum	529, 772	813					
hematite	772				757		
infusorial earth	479	720		588	554		
iron ores	772				757		
lead	309	250, 412, 425	250	140, 143	104, 756	86	80
lime borate					756		
malachite	772	777			756		
manganese ores	425	554	305, 349		757	124, 128	127, 134
marble	457				519		
mica	583	911	519				
mineral soap	772				756		
waters		983	539	715	680	630	522
nickel	404, 772	539		171	757	109	124
nitrate of soda	599						
opal		760					
prase		753					
pyrites	772				757		
quartz		753					
salt	532, 543, 772	847	483	628, 638	611, 756	597	482
saltpeter					645		
sandstone					521		374, 409
silver	172, 182	312	200	105	59, 756	36	49
slate					757		
soda carbonate					756		
sulphate					757		
stibnite	772				757		
sulphur	578, 772	865	496	644 646	757		
tellurium							
thenardite	772				757		
thiinite	772				757		
trachyte	772				756		
trona	772				756		
turquois	493	768			757		
ulxite	772				756		
New Almaden, Cal., quicksilver mines	396	503, 535		167			95
Newark, N. J., bluestone manufacture	297						
structural material				526			
New Bedford, Mass., structural materials						526	
Newberry, J. S., on the origin of salt beds		834					
Newbury, Spencer B., hydraulic cement							461
New Brunswick, antimony		645				135	130
manganese						361	146
New Caledonia, nickel	406		299		76		
New England, coal basin	4				11	23	12
copper							
iron and steel	127			17			
Newfoundland copper	257	356, 373	506	128	759	73	
New Hampshire, amethyst	705	750					
aquamarine	487						
arsenopyrite	705				759		
azurite	705				759		
beryl	705				759		
bismuth	705				759		
bornite	703				757		
brick					536	561, 565	
cassiterite	705				759		
cinnamon stone	705				759		
chalcopyrite	703				757		
copper	230, 703	329	210	112	757	54	60
epidote		766					
essonite	488				759		
feldspar	705				759		
flagging stone	701				759		
fluorspar	587, 705			692	759		
galena	704				757		
garnet	488, 705	746			759		
gold	176, 704				758		
granite	704			520, 537	514, 758	536, 539	374, 409
graphite	704			086	672, 758		
grindstones					552		
hematite	705				759		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
New Hampshire, idocrase	492						
infusorial earth	704				758		
iolite		743					
iron	705			17		14	
ores	120, 705			42	759		
pyrites	706			652	760		
malachite	704				758		
manganese	706	551	342		760		
marl	524, 705				759		
mica	583, 704	907	518		660, 671,	614	
mineral waters		983	539	717	757		
mispickel	705				759	627, 630	522
molybdenite	446, 705				759		
novaculite			433	590	553		
ocher	704				758		
peat	705				759		
phenacite						581	
pyrites	706	877	501	652	760		
pyrolusite	706				760		
quartz	704				758		
rhodonite		766					
sandstone							374, 400
silver	176						
slate	706				760		
sphalerite	706				760		
staurolite		743	186				
steel				17	11	14	
structural materials				520			
talc	704				758		
tin ore	705	597			759		
topaz						581	
tripolite	704				758		
wad					760		
zincblende	706				760		
New Haven, Conn., structural materials				522			
New Idria, California, quicksilver	390, 394,			161		98	95
	396						
New Jersey alum	606	949		681			
amber	498, 708	779			762		
amethyst		751					
apatite	521, 707	775			761		
apophyllite		775					
arsenopyrite	707				761		
asbestos	588, 707	913			761		
azurite	707				761		
barytes	707				761		
bluestone							370, 411
brick		696	415		536, 538	561	
brucite	707				761		
calamine	705				760		
chalcopyrite	707				761		
chrysocolia	707				761		
clay		677, 695			760		
coal	707				761		
colophonite		747					
copper	217, 261,				761		
	707						
crocidolite		775					
earthenware		698					
encaustic tile		699					
epidote		766					
erubescite	708				761		
fire brick and fire clay	706	697	418		540	566	
flagging stone	706				760		
franklinite	706	773			760		
galena	708				761		
garnet	708				762		
gneiss	706				760		
granite	706				760	536	374, 410
graphite	590, 706				762		
hematite	706				760		39
infusorial earth	708				762	14, 23	
iron	125, 706	252	182	587	11	17	10, 17
ore	117, 130,	263, 274	188	18, 50	16, 44,		24, 35
	708				760		
isopyre	493						
kaolin	707	677			760		
lead	706, 708				761		
lignite	708						
lime	707					556	
phosphate					761		
limestone	706				760		373, 410
analysis							410

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
New Jersey							
limonite	707			52	760		
magnesite	708				762		
magnesium salts	707				762		
magnetic iron ore	707				761		
malachite	708				762		
manganese			336				
marble	707				761		
marl	522, 707	808	5, 8, 464	7, 619	6, 8, 592,	595	451
					761		
metallic paint				711			510
mica	708				762		
mineral waters		983		720		630	530
mispickle	707				761		
molybdenite	708				762		
natrolite		774					
ornamental pottery		699					
ozocerite		957					
pottery clay	469		420				
prehnite	493						
pyrites	708				762		
quartz	490	752					
rhodonite		766					
rubies	485						
sandstone	451, 706				761		374, 410
sapphire	485, 708				762		
serpentine	708	776			762		
sewer pipe production		701	423	576			
sienna			532	712			
silver	708				762		
slate	452, 707				761	547	376, 410
smithsonite	707				761		
sphalerite	708				762		
spinel	485	737					
steel	137		184	18	11	14	12
stoneware production		698					
structural materials				535		529	
succinite	703				762		
talc	708			762	762		
terra-cotta lumber		697	422				
tile		699	698				
tin ore		599					
tripolite	708				762		
willemite	496, 707	773			761		
zinc	360, 706,	476, 564,			44, 761		
	707	773					
		661, 741					
zircon							461
New Lisbon hydraulic cement							
New Mexico							
anthracite coal	32, 63	57	40	288	763	293	
argentite	756				762		
azurite	756				762		
bornite	756				762		
cement					527	551	461
cerargyrite	756				762		
cerussite	756				762		
chalcocite	756				763		
chalcopyrite	756				763		
chrysocolla	756, 758				763		
coal	662, 757	56, 170	40	230, 288	171, 278,	171, 206,	147, 231
					764	292	
cobalt		545					
coke		149, 170	93	378, 402	383, 406	395, 412	
copper	216, 756	329, 340	210	112	76, 762	59	60
fahlerz	757				764		
fire clay	472			570		570	
fluorspar	575, 587		518		763		
gahnite		737			763		
galena	757				763		
garnet	487					581	
gold	172, 182,	312	200	105	59, 763	36	49
	757						
graphite	590						
gypsum	528, 758	812			763		
hematite	147, 758				761		40
infusorial earth				587			
iron	147	285			764		
ores	147, 757	285	196		763		24, 40
		763					
jasper					765		
kupfernickel	758				110	89	80
lead	313	416, 425	258	146	763		
lignite	757				764		373, 411
limestone					764		
limonite	757				763		
magnetic iron ore	758				764		
malachite	757				764		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
New Mexico marble	454				764		
massicot	757				764		
mica	583, 758	911	518		660, 765	615	
mineral waters		983	539	717	685	627, 630	522
nickel ores	758	539			765		
obsidian		772					
peridot	492						
petroleum	211						365
pyrargyrite	757				764		
pyrites	757				764		
quicksilver	387						
ricolite							411
salt	542, 757	843			763		
sandstone							374, 411
sapphire	485						
siderite	758				765		
silver	172, 182, 756	312	200	105	59, 762	36	49
sulphur			496				
tetrahedrite	757				764		
tin ore	756				763		
topaz	486						
turquois	484, 493, 757	768			764	582	
zincblende	757				764		88
New Orleans, La., coal trade	103					201	167
structural materials					509	525	
Newport, R. I., structural materials						533	
New Quebrada copper				128			73
New South Wales antimony		648					
chrome iron ore						121	
iron ore industry	111						
nickel	407	539					
tin exports		620					
ore		593, 619					
New York agate		756					
alum	606						
anthracite coal trade						185	151
apatite	521, 711				768		
arsenopyrite	711				768		
asbestos	588, 708	913			765		
axinite		765					
barytes	580, 711		525	705	768		
basanite		763					
beryl		740					
bismuth		654					
bluestone	711				767		376, 412
bog iron ore	710				766		
manganese					769		
brick		695, 710	415		536, 539	562	
brine springs					765		
brookite		772					
buhrstones	477	712	428	581	552	576	456
building stone			397	523		529	373, 411
calcareous tufa	711				768		
calcite	711				768		
cement		671		556	527, 529	551	461
cerussite	711				768		
chalcedony		756					
chalcopryite	711				768		
chondrodite		767					
chrome iron ore	712				768		
chromium		569					
chrysoberyl		736					
coal	189, 712				768	178, 185	151
colophonite		747					
copper	711				768		
copperas	607						
corundum	476				765		457
danburite	489	748					
dioptside	496	769					
dumortierite						582	
emery					765		
feldspar	708	933		701	765		
fire brick and clay	708				765	566	
flagging stone	708				765		
fluorspar	587, 712	776			768	583	
galena	712				768		
garnet					765		
granite	709				765	336	374, 411
graphite	590, 709	915	533	713	672, 679,		507
					765		
gypsum	526, 709	809	459		765		465
hematite	709			48	766		40

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
New York							
hyalite	761						
iodine	854						
iron	25, 709	252	182	18, 43	11, 767	14, 23	10, 17
ores	117, 120, 137	203, 271		43	43, 766	769	24, 40
jasper	492	762					
kaolin	469, 709				766	572	
labradorite	495	728, 769					
lead	711				2, 768		
white					768		
lignite	712				769		
lime	711			565	533	556	
limestone	451, 709				766	540	373, 413
limonite	709				766		
magnesite	712				769		
manganese	713	551			769		
marble	451, 710			541	518, 767	541	375, 414
marl	524, 710				767		
meerschäum		781					
menaccanite	712				769		
metallic paint				711			510
mica	712				769		
millerite	712				769		
millstones	477	712	428	581	552	576	456
mineral waters		983	539	717	685	627, 630	522
mispickel	711				768		
molybdenite	712				769		
natural gas		233	156, 174		464, 767	489	367
nickel	712				769	108	
novaculite				591			
ocher				709			508
peat	710				767		
peristerite		771					
petroleum	189, 221, 710, 712	214		442	438, 767	442	292, 312
plaster					765		
portland cement				556			462
potash					643		
potteries						572	
prase		753					
pyrites	712	879	504		769		
quartz	710	749, 755			489, 767		
salt	532, 709	830	476	628, 632	611, 765	597	482, 484
prices	538						
production	537			628, 632	614	600	482
wells				632	616	600	
sandstone	710			546	520, 767	544	374, 411
serpentine	712	776			769		
sewer pipe		701		576			
siderite	711				767		
silicified coral		758					
slate	452, 711		398	713	522, 768		376, 414
sphalerite	713				769		
spinel		737					
steel	119		184, 186	18	11	14	12
stontianite	582			699			
structural materials				523	510	529	
sulphur	578	864					
sunstone		771					
talc	711		534		768		476
tin ore		599					
tourmaline	488	745			769	582	
trap rock	711				768		
travertine					768		
tufa, calcareous					768		
wad	713				769		
zincblende	713				769		
zircon	487	661					
New York City							
biuestone manufacture	297						
coal trade	102	75			176	178	151
structural materials				524		530	
New Zealand			11	235			
coal				207		142	130
manganese						473	
petroleum		232					
platinum		577					
quicksilver exports	390						
Niagara Falls, N. Y.					510		
structural materials					713		
Niccolite in Colorado	753				715		
Connecticut	673				753		
Missouri	702				765		
New Mexico	758						
Nickel	399	537	297	169	126	108	124
alloys	411		365, 391			116	
ammonium sulphate				2, 169	2		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Nickel, census statistics							125
coinage	412	538	602	173			
in Belgium	413						
England				173			
German Empire	413			173			
consumption		537					
crucibles		541					
exports		543	298	171	127	109	126
extraction		537, 542				113	
foreign sources	405	539	299				
imports	410	543	298	171	126	108	126
in Arkansas					128		
Austria-Hungary	410		365				
British Columbia	404						
California	403, 759	539			706		
Canada	502					110	125
Colorado	404	539					125
Connecticut	401	539					
Dakota					718		
England	404, 772	539			757	109	
Europe	410						
France		540					
Germany		540					
Idaho							125
Italy	410						
Michigan	403						
Missouri	403, 702	539			753		124
Nassau	410						
Nevada	404	539	297	171		109	124
New Caledonia	406		299				
New Mexico		539					
New South Wales	407	539					
New York	712					109	
North Carolina				170	127	109	125
Norway	410						
Oregon	403, 773	539		171	127, 778	109	
Pennsylvania	404, 726	537			784		124
Russia	410						
Saxony	406						
South Dakota							125
Spain	407						
Sweden	405						
Vermont	738						
industry						110	
metallurgy	415	540					
new discoveries		539	297	171	127		125
ores	399, 403, 773			170	721	109	
plate	411	541		173			
prices	407		297	172	127		
production	XII, 406	3, 6, 537	2, 5, 297	2, 7, 9, 169	2, 6, 8	2, 108	2, 6, 124
sulphide	409				701, 769, 782		
uses	411	541	301			116	
values	407			170	127		
Nickeliferous pyrites	405			712			
Nigger Hill, Wyoming, tin		613				148	
Niter	597						
in Arkansas	671				702		
Illinois	679				727		
Indiana	681				730		
Kentucky	686				735		
Missouri	702				753		
Tennessee	733				791		
Texas	735				794		
Utah	775				796		
West Virginia	744				805		
Nitrate of soda	599	966	465				
Nitrogen in fertilizers		816	465				
North Baltimore, Ohio, natural gas						494	
North Carolina agalmatolite	713				769		
agate	713	757			769		
allanite					769		
amazon stone	495						
amethyst		725					
anthracite coal					773		
antimony	716						
aquamarine	487				770		
argentite	713						
arsenopyrite	716				773		
asbestos	588, 659, 713	913			769, 773		
azurite	716				773		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
North Carolina							
barhardite	716				773		
barytes	580, 660, 713	922	525	705	770		513
beryl	715	725, 739			770	580	
bismuth		654					
bitumen	716				773		
bornite	713				770, 773		
brick						562	
brines					773		
buhrstones	525, 715	712		581		576	
calcareous marls	525, 715				772		
cassiterite		767			773		
cerussite	716				773		
chalcedony		757					
chalcocite	713				770		
chalcopyrite	713				770		
chrome iron ore	428, 716	569			773		
chrysocolla	716				773		
chrysoprase		760					
citrine		751					
clay	717				773		
coal	7, 34, 713	59	41	328	279, 773.		146, 234
copper	231, 713				76, 770 770		
ore							
coprolitic marl		791					
corundum	477, 660, 714	715, 733	429	585	553, 770	577	457
crocidolite		775					
cuprite	714				773		
diamond	716, 484	729			773		
diaspore		738					
emerald	487, 500	725, 734			770	580	
emery	714				770, 773		
epidote		766					
euclase		741					
feldspar	717			701	773		
fertilizers			449, 469	613	592	595	
fire brick and clay	466, 717				773	566	
freibergite	718				774		
gahnite		737					
galena	714				770		
garnet	488, 660	746			770		
gems	488, 661						
gold	173, 176, 714	312	200	104	58, 770	36	49
granite	714			538	771	539	374, 414
graphite	590, 714				672, 771		
hematite	714				771, 774		
hiddenite	501	748			772		
hyalite		761					
iron	131, 716	246, 263	182	33, 82	11, 771	14, 23	10, 17
carbonate					774		
ore		263, 278		82	49	17	24, 34, 36
pyrites					772, 774		
itacolumite	715						
jasper		762					
kaolin	659				659, 773		
kyanite		748					
lead	716						
leopardite		770					
lignite	717				773		
limestone	715				771		
limonite	715			83	771		
magnesite	717				774		
magnetic iron ore	715			82	771		
malachite	715	778			774		
manganese	424, 717	551	344	190	151	129	127, 134
marble	717				774	543	415
marls	523, 715			619	772	595	
melaconite	715				774		
mica	583, 661, 715	908	518	5, 7, 9	5, 660, 671	614	474
millstone	525, 571	712		581	772	576	456
mineral waters		984	539	718	685	628, 630	522
mining law				728, 731			
mispickel	716				773		
molybdenite	717				774		
monazite					772		
nickel				170	127	109	125
novaculite	716				772		
octahedrite		772					
opal	716						
peat	717				774		
petroleum	716				773		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
North Carolina phosphate rock		783	449	607	584, 772	592	
platinum	442, 717						
pottery clay	470				545		
precious stones			5, 439	595			
psilomelane	717				744		
pyrites	659, 717		505		772, 774		
pyrolusite	717			191	774		
pyrophyllite	660						
pyrrhotite	659						
quartz	490	724, 749, 753			772		
ruby	485						
rutile	492	765			772		
sagenite	491						
salt	717	840			773		
samarskite					772		
sandstone	715				772	545	374, 415
sapphire	485	734					
serpentine	716	776			772		
siderite	716				772		
silver	172, 717	312	200	104	58, 774	36	49
slate	717				774		415
sphalerite	717				774		
spodumene	488, 716				772		
staurolite		743					
steel	120			18	11	14	
structural materials						531	
succinite		780					
talc	660, 713, 715				769, 772		
tellurium	717				774		
tetradymite	717				774		
tetrahedrite	718				774		
tin		601			136, 773		
titanic acid ore					772		
tourmaline		745					
wad					774		
wheatstone	715				772		
zincblende	717				444		
zircon	487, 659	661, 741	393		772		
Norway, copper production			233	128	87	73	73
infusorial earth						578	
nickel	410						
silver		319					
Novaculite	492		433	589		5, 8, 10	460
imports			433	593	553	5	
in Arkansas	671, 492			589	701		
Georgia	677				722		
Indiana			435	592			
New Hampshire			434	590			
New York				591			
North Carolina	716				772		
Vermont				590			
prices			435	591			
production			435	4, 8, 10	4, 7, 553	5, 8, 10	6, 460
uses			436	589			
Nova Scotia, antimony		645					
coal	4		11	235	171, 189		
coke				436	435		
fire clay			414				
graphite				688			
grindstones				584			
gypsum		809	460		5	6	
iron ore industry	111						
manganese		554	554	198, 356		133	130
pig iron industry	111						
Obalski, J., on natural gas	496	772			501		
Obsidian	496, 769			597	706		
California							
Colorado		772					
New Mexico		772					
Texas	735				794		
Yellowstone National Park		772		597			
Ocher		925	526	708	677	618	508
imports		927	529	710	678	619	509
in Alabama				709	693		508
Arizona	761				697		
Arkansas	671						
California						618	
Canada						618	
Colorado							508
Georgia			528	709	729		508
Indiana					729		
Maine	689				737, 739		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Ocher in Maryland	692		527		742		508
Massachusetts	695				745	618	508
Mississippi	699						
Missouri	702				753		508
Nebraska	703				756		
New Hampshire	704				758		
New York							508
Ohio	719				776		
Pennsylvania			527	708	782	618	508
South Carolina	729				787		
Texas	735				799		
Utah	774				795		
Vermont	738		527		798	618	508
Virginia	741		527	709	802		508
West Virginia	745				806		
Wisconsin	746				807		508
Peruvian, Georgia				709			
prices				709	677	618	
production		7, 9, 10	6, 8	5, 7, 9	5, 677	618	508
red	769				706, 750		
yellow	769			708	702, 706		
Octahedrite		772					
Ohio alum	720	949			777		
bera grit	478			582			
blast furnaces	121						
bog iron ore	720				778		
brick	457	696			536, 539	562	
bromine		851	486	642	626	613	493
buhrstone	477, 719	712			776		
celestite	720				777		
cement		672, 678	406		527, 775	551	461
clay	718	697	414	569	540, 775	566	
coal	6, 33, 65, 103	12, 59, 172	11, 43, 83	230, 289	171, 2811	88, 206,	147, 235
coke	98, 130	152, 171	75, 93	378, 403	775	294	
coking coals		145			383, 407	395, 413	
copperas	607, 720				777		
drain tile		700		575			
earthenware		698					
encaustic tile		699					
fertilizers			469	625			
fire brick and clay	466, 718	697	414	569	540, 775	566	
flagging stone	718				775		
fluorspar	587				777		
galena	720				777		
gas-retort production		697					
glass-pots production		697					
gold	720				777		
graphite				686			
grindstone	479, 718	713	428	582	552, 775	545, 576	458
gypsum	527, 719	809	459	620	595, 775	6	405
hematite	719				776		
hollow tile		697					
iodine		854					
iron	119, 125, 720	252	182	18, 56	11	14	10, 17
ore		263, 275		61	46, 778		24
lime			412		533	556	
limestone	451, 719		412	540	516, 776	540	373, 417
limonite	719, 721			56	776, 778		
marble	451						
marl	524, 721				778		
metallic paint				711			510
millstones	477, 719	712			552, 776		
mineral waters		984	539	718	685	628, 630	522
mining law				729, 734			
natural gas		233, 242	156, 161, 172, 176	504	26, 464,	489	367
ocher	719				776		
peat	721				778		
petroleum	189, 719	215	146	458, 460	438, 451,	444, 459	292, 318
Portland cement					776		
potash and pearlsh					643		462
pottery clay	470	700					
quartz	720				777		
salt	532, 541, 719	836	479	628, 637	611, 618,	597, 604	482, 488
sand	720				776		
sandstone	451, 720			546, 582	521, 777	545	374, 415
analysis					777		416
sewer pipe		693, 701		576			
siderite					777		
shales					480		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Ohio steel	120		18, 184, 186	18	11	14	12
stoneware production		698					
strontia	720				777		
structural materials				531	510	532	
sulphur	578	864					
terra cotta		700					
white ware		699					
Oil. (See Petroleum.)							
Oilstones and whetstones	637, 677			590	701, 798	5	3, 460
Old Dominion Copper Company, Arizona		405				58	64
Omaha, Nebr., bluestone manufacture	297						
lead works	313					88	
structural materials				534	510	529	
Oneida salt springs, New York	537	830		632	614	600	485
onyx	768	757			519, 704		408
Öolitic limestone				541		541	
Opal	496	760			575, 577		
in Arizona	764				699		
California		760					
Colorado		760					
Georgia	677	760			722		
Nevada		760					
North Carolina	716						
Oregon						581	
Pennsylvania		760					
Texas	735				794		
mines, Mexico					575		
Orange mineral			296, 524	703			511
Oregon agate		757					
arrow points		727					
barytes					778		
blast furnaces	121						
borates	773				779		
burrstone	773						
calcite					778		
cement					530	553	
chalcopryrite					778		
chrysoprase		760					
cinnabar					778		
coal	6, 94, 773	12, 66	11, 45	230, 294	171, 288, 778 778	171, 206, 301	147, 240
copper pyrites					778		
diamond	484					581	
fire opal							
garnierite					778		
gold	173, 182	312	200	104	58, 778	36	49
quartz	490						
granite							374, 418
infusorial earth				588	554, 778		
iridium	444	581		222			
iron	129	252	182, 199	18	778	15	10, 17
ore		287			778		24, 40
jasper		758					
jet	773						
liguite	773						
limestone			412		778		373, 418
limonite					778		
magnetic iron ore	773				778		
pyrites					779		
marble							418
mica		911					
mineral waters		984	540	718	685	628, 630	522
mirabilite					778		
nickel	403, 773	539		171	127, 778	109	
platinum			367	222	142, 778		
priceite	773						
pyrrhotite					779		
quicksilver	387				125, 778	98	93
salt	550				778		
sandstone							374, 418
silver	172, 182	312	200	104	58	36	49
soda					778		
steel	120			18	11	15	
structural materials					510		
ulexite					779		
Oxford, Quebec, nickel	402						
Orpiment, Utah	774				795		
Orthoclase	724	382, 769			688, 782		
Orton, Edward, on gypsum in Ohio					596		
natural gas			176	504	479	490, 506	
Ostberg, P., on uses of aluminium			391				
Ouvarovite		740, 747					

	1882.	1883-'84	1885.	1886.	1887	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Ozocerite	609	955					
in California	609					6, 515	4, 6, 481
New Jersey		957					
Utah	609, 774	955				515	481
Wyoming		957			809		
uses						515	
Packard, R. L., on aluminum	445	658	390	220	138	160	110
Panther Creek, Pa., coal district	22	68	45				
Paraffin	207				795, 809		
Paris white		930	526	707	677	621	
Parker, E. W., on asphaltum							477
coal							145
Parrott, Mont., copper mines		385	216	118			
Rossmore, E., on menaccanite			441				
Paterson, N. J., structural materials				526			
Peale, A. C., on mineral waters		978	536	715	680	623	521
Peat, Illinois	679				727		
Indiana					729		
Massachusetts	693				743		
Minnesota	698				749		
Nebraska	703				756		
New Hampshire	705				759		
New York	710				767		
North Carolina	717				774		
Ohio	721				778		
Vermont	738				798		
Wisconsin	747				807		
Pectolite		775			561		
Pelhamine		776					
Peloux, Charles du, on nickel in New California.			299				
Pemberton, H., analyses of manganese ores.			342				
Pennsylvania, actinolite		765					
albite	725				783		
alum	606			681			
amethyst	491, 725	750			783		
andalusite		741					
anthracite	6, 7	12, 66, 104, 778	45	226, 295	290, 779	302, 329	146, 242
analyses		69					
distribution of output.		73	52	303	314	322	247
fields		105	226	297	296	302	
mines' condition.		75					
mining accidents.	107	127					
prices			55	308		180, 328	242
production		7, 10, 70	5, 8	7, 9, 295	6, 8	302	146, 242
shipments		70		299	294	323, 328	146, 242
shipping		73				327	
sizes		74, 129		307			248
apatite	725				783		
aquamarine	487						
asbestos	588, 721	913			779		
asbolite	725				783		
axinite		765					
azurite	721				779		
barytes	580, 725				783		
basanite		763					
beryl		740					
bituminous coal	6, 67, 130	12, 76	57	230, 314	171, 318, 780	332	146, 252
analyses		193					
prices		87				335	
production.	33, 67, 72	72, 82, 85	57	295, 321	321, 323	332, 335, 340	146, 252
reserves	68	78					
varieties		77					
bluestone							376, 420
bornite	725				783		
brick		696	415		536, 539	563	
brines					780		
bromine			486	642	626	613	493
bronzite		774					
burrstones		712	428	581			456
building stone			396	527			373, 418
cadmium sulphide					784		
calamine					783		
cassinite		769					
celestite	725				783		
cement		672	406		527	551	461
cerussite	721				779		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Pennsylvania, chalcedony		756					
chalcoite	725				783		
chalcopyrite	721				779		
chlorastrolite		774					
chrome iron ore	721	567			779		
chrysocolla	725	778			783		
chrysoptase		760					
coal. (See Anthracite and Bituminous.)							
cobalt		546					
coke		152, 175	77, 96	378, 408	383, 409	395, 414	
analyses			177, 194	408	413		
districts		145, 175, 194		408		415	
establishments		149		408		397	
manufacture experiments.		186					
ovens		150		408	388	400	
percentage yield of coal.		151, 187		387		405	
prices at Pittsburg production.	72	180, 196	97	409		182 4, 400, 415, 424 402	
value.		153		378			
copper	218, 231 721, 726				779, 784		
copperas	607						
corundum	477, 722				780		
crocidolite		735					
cuprite	725	775			783		
diaspore		738					
drain tile		700					
emerald nickel					785		
emery					780		
enstatite.		774					
epidote.		766					
essonite.		746					
feldspar	722, 729	933	523	701	780		
fertilizers			469	625			
fire brick and clay	465, 722	697	414	569	540, 780	566	
flagging stone	722				780		
fluorspar	725			692	784		
galena	723				780		
garnet	488, 725	746			784		
gold	725				784		
granite	723			537	514, 780	536	374, 418
graphite	590, 725			686	784		
greenockite	725				784		
hematite	723			52	780		40
hydrozincite	725				784		
idocrase		767					
ilvaite		768					
iron	119, 129 723	252	182	14, 22, 52	11	14, 23	10, 17
ore		263, 275		102	44		24, 40
analyses		270		55	44, 779		
pyrites	726				784		
jadecite	498						
jasper		762					
kaolin	723			573	781		
kyanite		748					
labradorite		769					
lead	721, 726				779		
lennilite		769					
lignite.					783		
lime	725	969			533	556	
limestone	451, 723				516	541	373, 420 421, 424
analyses							
limonite.	723				781		
magnesite	726				784		
magnetic iron ore	724			52	781		
pyrites	726				784		
malachite	724	778, 782					
manganese	726	551	342		784	124	
marble	451, 724				782		375, 427
marl.	724				782		
meerschaum		780					
melacnite	726				784		
metallic paint			529	711			510
mica	583, 726	908	518		784		
millerite	724				782		
millstones			428	581	552	576	456
mineral waters		984	540	718	685	628, 630	522
mining law				729, 759			

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Pennsylvania, molybdenite	726				784		
moonstone		770					
natural gas		233, 236, 243	155, 161	302	24, 464, 782	334, 481, 489	367
nickel	404, 726	537, 546			782, 785		124
ocher			527	708, 782			508
oil fields	188	214	135	442	441, 449	445	295
opal		760					
orthoclase	724				782		
ouvarovite		747					
petroleum	189, 724	214	130	442	438, 782	442	292, 295 312
production		221	135	445, 453		4, 442, 458	292
phosphate of lime					783		
prase		753					
psilomelane	726				784		
pyrites	726	769			784		
pyrolusite	726				784		
pyrrhotite	726				784		
quartz	724	749, 757			782		
rutile		765					
salt	532, 723	835			780		
sandstone	451, 724			546	782	545	374, 419 419
analysis							
sapphire		735					
serpentine	724	776			782		
siderite	725				782		
sienna			532	712			
silver						784	
slate	452, 725		398	713	522, 783	547	376, 424
smithsonite	726				784		
sphalerite	725				784		
spiegeleisen		263					
staurolite		743					
steel	120, 137		184	18	11, 27	14, 45	12
stoneware		698					
strontianite	582, 725				783		
structural materials				527	510	532	
sunstone	495	771					
talc	585, 725				783		
titanite		774					
tourmaline		745					
umber			532	713			
wad	726				784		
williamsite	497						
wulfenite	726				785		
zaratite	726				785		
zinc	360, 726	476			783		
zincblende	725				784		
zircon		661, 741					
Peridot	492	781	411	599, 604	735		
Peristerite		771			562		
Perm, Russia, copper	257						
Perovskite					702		
Perrenoud, G. F., on talc			534				
Perry, Nelson W., bibliography of iridium		588					
Perthite		771					
Peru, copper			233	128	88	73	73
iodine		856					
platinum		576					
Peters, E. D., jr., on mines and reduction works, Butte City, Mont.		374					
on nickel ores in Canada						110	
on the roasting of copper ores and furnace products		280					
Petersburg, Va., structural materials					511	535	
Petite Anse, La., rock salt	558	841	480	636	620	604	488
Petroleum, charters, refined oil						425	
exports		228				452, 472, 479	301
for burning brick					540		
geology	192						
history	186		130, 146, 148				
imports, Canada						472	
in Afghanistan		252				4	363
Alabama					702		
Arkansas				480		474	
Burmah		232				4, 442, 464	290, 292
California	189, 769	218	130, 148	440, 461	438, 452, 740	464	340

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Petroleum, in Canada	206	232	131	262, 440, 456	437, 456	43, 467	
China		232					
Colombia, United States of Colorado	211	216			438, 455, 710, 713	474 442, 464	292, 332
Egypt				478			
France	187						
Germany		232					
Illinois	679				727		292, 353
India		232					
Indiana	681				729	464	292, 349
Japan		232				474, 477	
Kansas	684				733		292, 355
Kentucky	189, 685	216	130, 147	461	452, 735	442, 463	292, 350
Louisiana	687				736		
Mexico		232					292, 361, 363
Missouri		220					365
New Mexico	211						292
New York	189, 710	214, 221	130	442, 445, 453	438, 447, 767	442, 448, 458	
New Zealand						473	
Ohio	189, 719	215	130, 146	458, 460	438, 451, 776	442, 459	289, 292, 318
Pennsylvania	189, 724, 729	214, 221	130, 142	442, 445, 453	438, 782	442, 446, 458	292, 295, 312
Roumania		232					
Russia	191	231	242	463, 470	458	478	
Scotland	187			484			
Sicily		232					
South America		232		486			
Spain		232					
Tennessee	733	220	130, 147	461	452, 791	442, 463	292
Texas	735	220		463	794		292, 359
Venezuela				486			
Virginia			146				
Washington			152				
West Virginia	189, 744	216	146	461	438, 451, 805	442, 463	292, 329
Wyoming	211, 759	217	130, 153	462	809	442, 466	363
inspectors, Canada				469			
localities where found	189			439	436	244	287
methods of producing	194					475	
origin	191						
pipe-line runs	204					447, 461	299
prices	203	224	137, 145	442, 448	438	450 472	
Canada							
New York				449	444		
pipe-line certificates		224		456	443, 450	450, 456	300
producers' association					8, 9	446	
production	XII, 200	2, 221	2, 131, 141, 150	3, 440, 470	6, 437	443	3, 6, 296
cost	198						
refining process	206			470			
shipments	201		135	446	442	448	
Canada					457	468	
New York		221	136	453	442, 447	449, 457	
Pennsylvania		221	135	453	442, 447	449, 457	
Russia, Baku				474	463	479	
Batoum					462		
specific gravity	205						
stocks	202	223	136, 145	447	442, 449	449, 457 468	293, 304, 319
value			131	441	43	4	
wells, cost of drilling	196			466		467, 476, 478	
Pewter		632					
Phenacite	487	617, 740	439		559	580	446
in Colorado	487	722, 740			710	580	
New Hampshire						581	
Philadelphia, Pa., bluestone manufacture coal market	297				177	180	153
structural materials				527	510	532	
Philip, E. B., on natural gas as an illu- minant			161, 174				
Phillips, Wm. B., on fertilizers in North America				611			
on mica in North Caro- lina					661		
Phinney, W. J., on the Indiana natural gas field						499	
Phoenicochroite in Arizona	764				699		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Phosphate of iron					806		
lead	764				699, 763, 787		
rock	504, 511, 517	783	444	607	584, 701, 720, 783	592	450
analyses	509	790, 799	449, 452	616	608		
exports			473	607			
imports		804	454, 458	607	583	591	450
In Alabama	798	783, 794, 803		618	694		
Arkansas			454		701		
Florida	675	783, 793	452	617	720	592	451
France			454				
North Carolina		783, 788	449	607		592	
South Carolina	504, 508, 517	783	444	607	584, 786	586	450
Spain			454				
mining methods	512, 516	790					
production	xiv, 517, 518	4, 784	3, 445	4, 608	6, 8, 580	5, 586, 590	4, 6, 450
shipments, South Carolina.	518	785	446	610	580	590	
Phosphatic marls	507, 512			619	772		
Phosphorus		540		676			
production				4, 676			
uses				676			
Phosphuranylite					668		
Pig iron	109, 127	248	182	1, 911	6, 19, 32	15, 23, 27, 30	10, 17, 21
classification	114						
imports			190	13	12	13, 20	
prices	142	251			14	16	
production	109, 122, 139	254	193	11	6, 14	12, 26	6, 10, 21
growth in the Southern States				33	22	24	
world's	108	257	194	22	19	29	
lead, New York City prices						83	
Pipe lines	204					447, 461	299
stone	498	778		747			446
Pitchblende	674, 752				712, 716		
Pittsburg, Kans., zinc works	347					93	
Pa., coal statistics	106	87	59		173, 201	183	
trade					179	183	156
coke district			106		416	182	
lead works	313						
structural materials				527			
Placer county, Cal., chromium	428						
Plaster of Paris (<i>See</i> Gypsum.)							
Platiniridium, California	769				706		
Platinum	442, 769	576	307	9, 222	142	165	143
exports		578	369	223	142	167	144
imports	444	578	368	223	143	167	144
in Arizona	764				699		
Australia		576					
Borneo		576					
Brazil		576					
California	442, 769	576			706		
Canada		577				165	
Colombia, United States of		576					
Colorado		576					
Georgia	442						
Hayti		576					
Idaho	442	576					
India		576					
New York	442						
New Zealand		577					
North Carolina	442, 717						
Oregon			367	222	142, 778		
Peru		576					
Ural Mountains, Russia		576	368	222	142	165	143
Virginia	442						
Wyoming			367				
ore analyses		577					
prices		578				166	144
production	16	3, 577, 580	3 7	2, 7, 9	2, 6, 9	3, 165	6, 143
sources				222		165	
uses		579		222			
Plumbago. (<i>See</i> Graphite.)							
Pocahontas, Va., coal and coke			69, 118	353			
Polybasite	751, 761, 774				697, 710		
Pope Valley quicksilver mine, California.	389	689		161	119		94

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Porcelain		690					
clay	471				806		
Porphyry	774				697		
Porter, J. B., on Alabama iron-ore district			85				
Portland cement, American	XIII	671	405, 407	556, 560	528	552	461
Maine, structural materials				520			
Oregon, coke		206					
structural materials					510		
Portugal antimony		645					
copper	254	356, 360,	237	133	93	73	73
manganese		367					
pyrites		555		201			130
tin ore		358, 367,		656	95		
pyrites		882					
tin ore		618					
Potash, foreign sources		967					
in fertilizers			465, 470				
glass making		967	556				
Potassium, bicarbonate		572	359	177	649		
bichromate					648	120	
bromide					647		
carbonate					643, 649		
chlorate					648		
chloride			465	624	637		
chromate					648		
ferricyanide					648		
ferrocyanide					648		
iodide					648		
nitrate					644, 796		
permanganate		557					
salts		816	465	624	628		
sulphate			465	625	643, 645		
Potomac marble, Maryland					742		
River cement					527	551	
Potters' clay	469, 659	676			5, 542,	6, 571	6
Pottery	471	689, 699	419	571	542	571	441
Pottsville, Pa., coal mining	107		46		728		
Prase		753			542		
Precious stones	XIV, 482	723	437	595	555	580	3, 6, 445
Prehnite	493						
Preston, John A., on Florida phosphates			452				
Pricelte	773			222	706		505
Prince, F., analyses of Minnesota Bessemer ores				75	266		
Procter, John R., on coking coals of Kentucky				400			
Proustite	751, 761,				697, 710,		
	770				723		
Providence, R. I., bluestone	297						
structural materials				523			
Prussia antimony		645					
copper	255		238	135			
lead	322	437	267				
manganese				201			
nickel	410	540					
salt		849					
silver	322						
zinc ore	357	481	278				
Psilomelane		382	318, 342				
Arizona	764				699		
Arkansas	171				701		
Great Britain				199			
Montana	755				754		
North Carolina	717			192	774		
Pennsylvania	726				784		
South Carolina					787		
Vermont	738				798		
Virginia	741				802		
Pumice stone	XIV, 480	10, 721	9, 433				
California	767	721	433		706		
imports		721	433				
Pumpelly, Raphael, on iron ore	111						
manganese deposits			347				
Purnell, Samuel, on coal		23					
Pyrrargyrite	498, 771				697, 795		
Pyrites	498	382, 617,	443, 501	604, 650,	95, 556	5, 8	4, 6, 518
		768, 877		669	609		
analyses			501	652			
arsenical			516		696, 714,		
auriferous	756, 770		516		753		
burning processes		890		651	724, 809		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Pyrites consumption of the world			510				
exports, Portugal		358, 367		656			
Spain		358, 364		655			
extraction of metals from		358	210	130	90		
foreign deposits		881	506	654			
imports	217	358, 886	211, 509	130		90, 610	
in Alabama	149, 670		506			695	
Alaska	760					696	
Arizona	761					697	
Arkansas	671					702	
California	769					706	
Canada	257	881	506	656		111	110
Colorado	498, 751	768				711	
Connecticut	673					715	
Dakota	754					717	
Georgia	677	880	506			722	
Germany		885					
Idaho	771					723	
Illinois	679					727	
Indiana	680					730	
Kansas	684					733	
Maine	689					739	
Maryland	692					742	
Massachusetts	693	878	503	654		743	
Minnesota	698					749	
Missouri	702					753	
Montana	755					754	
Nevada	772					757	
Newfoundland	257		507				
New Hampshire	230, 706	877	501	652		760	
New Jersey	708					762	
New Mexico	757					764	
New York	712	879	504			769	
North Carolina	659, 717		505			772	
Pennsylvania	726	768				784	
Portugal	254	882	507	656		95	
South Carolina	729					787	
Spain	253	882	233, 236,	654		93	
Tennessee	733		507			792	
Texas	735		506			794	
Utah	774					795	
Vermont	736	878	502			797	
Virginia	741	879	504	653		802	
Wisconsin	747					808	
Wyoming	758					809	
nickeliferous, analyses	401			712			
production		5, 781, 885, 889	4, 508	7, 657	6, 609	5, 584	4, 6, 518
Pyrochlore					668		
Pyrolusite	425	550, 970	304, 324, 352				
analyses	425	551					
in Alabama	669				695		
Arizona	762, 764				697, 699		
Arkansas	671				791, 702		
California	769				706		
Georgia		551			721		
Great Britain				199			
Idaho	771				724		
Maine	690				739		
Maryland	692				742		
Massachusetts	695				745		
Michigan				72			
Montana	755	382			755		
Nevada					757		
New Hampshire	706				760		
North Carolina	659, 717	552		191	774		
Pennsylvania	726				784		
South Carolina	729				787		
Tennessee					791		
Texas	736				794		
Utah	774				795		
Vermont	738		342		798		
Virginia	742		324		802		
Pyromorphite	702, 752, 764	382			699, 711, 753, 787		
Pyrope		746					
Pyroxene		382, 728		601			
Pyrrhotite		382	516			110	
Quartz	586	382		596, 604	556		446
aventurine		752					
crystals	490	724, 748			701		
gold	490	763					
in Alabama	670				695		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Quartz in Arizona.....	762				697		
Arkansas.....	171, 490	752			701		
California.....	490	749					
Colorado.....	490, 752	752		596	711		
Connecticut.....	674				714		
Dakota.....					718		
District of Columbia.....					719		
Illinois.....	678				726		
Indiana.....	680				729		
Iowa.....					728		
Maine.....	690	749			737, 739		
Maryland.....					740		
Massachusetts.....					743		
Mississippi.....	693	751			750		
Missouri.....	701	752			752		
New Hampshire.....	704				758		
New Jersey.....		752					
New York.....	710	748		596	767		
North Carolina.....	490	752			772		
Ohio.....	720				777		
Pennsylvania.....	724	752			782		
Rhode Island.....		728					
South Carolina.....					787		
Tennessee.....	733				792		
Vermont.....	738				798		
Virginia.....	743			596	803		
West Virginia.....	744				805		
Wisconsin.....	747				808		
Wyoming.....					809		
inclusions.....		753, 756			809		
production.....	XIV	781		604		584	446
rose.....	490	752			718		
smoky.....	XIV	751, 781		596, 604	556	584	448
Quebec, manganese.....	490					136	130
natural gas.....					501		
Queensland, Australia, tin ore.....		620					
Quicksilver.....	387	492	284	160	118	97, 103	94
census statistics.....							102
exports.....	392	500	294	167	124	104	108
foreign sources.....	392	496	290				
furnaces.....	395	507, 512					
imports.....		499	293	166	124	105	101
in California.....	387, 767	492	284	160	704	97	94
Oregon.....					125, 778	98	94
Utah.....					168		
prices.....	393	495, 497	287, 289	163, 165	121	102	98, 101
production.....	13, 16,	3, 6, 8,	2, 5, 7,	2, 7, 9,	2, 6, 8,	2, 98	2, 6, 94
in Austria.....	389	496, 501	285	161	123		
California.....	389, 393	492, 494,	284, 286,	167	120	2, 97, 100	103
Hungary.....		496	288			105	
Italy.....	392		293				
Oregon.....					125	98	
Spain.....	393	496				105	
Russia.....						105	
world.....	393	497			125		101
reduction at New Almaden, Cal.....		503		168			
shipments, San Francisco, Cal.....		500	289	166	124	104	100
vermillion.....		501	296	714	679	622	101
Raborg, Wm. A., on abrasive materials.....				581			
corundum.....				585			
graphite.....				686			
grindstones.....				582			
salt.....				628	611	597	482
Randol, J. B., statistics of quicksilver.....	389	493		167			100
Ransome process for cement.....				560	530		
Rath, G. von, on precious stones.....			442				
sulphur in Utah.....			495				
Raymond, R. W., on mining law.....		988					
the divining rod.....	610						
estimates of the gold and silver product.....	182						
Red lead.....	763	924	556	703	675	616	511
Reynoldsville-Walston, Pa., coke district.....			75, 108	416	418	423	
Rhenish provinces, Germany, zinc.....	356	485	277	159	117	96	92
Rhode Island, actinolite.....					785		
agate.....	727				785		
amethyst.....		750					
anthracite coal.....	7, 32	87					
arsenopyrite.....	727			2, 224	785		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Rhode Island, asbestos					785		
bog iron ore	727				785		
manganese	727				786		
bowenite	497						
brick					536, 539		
chalcedony	727				785		
chalcopyrite	727				785		
clay	727				785		
coal	6, 727	12, 87	11	2, 224	171, 351, 785, 785	171, 206, 361	
copper pyrites	727				785		
crocidolite		775			785		
dolomite			469	625	785		
fertilizers					785		
flagging stone	727				785		
galena	727				785		
garnet					785		
granite	727			537	513, 785	536	374, 427
graphite	727			225	672, 785	361	
hematite	727			43	785		
hornblende	491						
ilvaite		768			785		
iron	125, 133		184	42		14	
ore	120						
jasper		762			785		
limestone							373, 428
limonite	727				785		
magnetic iron ore	727			42	785		
manganese	727	551	342				
menaccanite			441				
mineral waters		984	540	718	685	628, 630	522
mispickel	727						
molybdenite	727				786		
octahedrite		772					
quartz		728, 749					
rhodonite		766					
sandstone	727						374, 428
serpentine	727				786		
sphalerite	727						
steel				17	11	14	
structural materials				523		533	
talc	727				786		
thetis hair stone	491						
wad	727				786		
whetstone	727				786		
Rhodochrosite	774	382					
Rhodonite	496, 755	382, 766	337		562, 755	582	
Richmond, Va., coal analyses					367		
trade	103						
structural materials						535	
Ricketts, L. D., petroleum wells of Wyoming.					466		
Ricolite							411
Rio Tinto, Spain, copper mines		356, 364	235, 508	128, 654	94		73
Rochester, N. Y., structural materials					510	530	
Rock crystal	489, 671		441		560, 702, 722		
salt analysis				360			
in Arkansas	171				702		
Kansas					608, 732	608	
Louisiana	564			636	736	604	
Michigan	696				746		
Nevada	543			638			
New York					765		
Texas					792		
Utah	774			639	795	605	
soap, California	767				704		
Rogers, H. D., on Ohio coal		59					
Rogersite in North Carolina					668		
Roofing tile		697	422	574	549		
Rose quartz	490				718		
Rothwell, R. P., on pyrites				650			
Rottenstone, imports		722					
Roumania petroleum		332					
Rubellite					560		
Ruby	485		439	601			
artificial				601			
in Burmah					572	582	
Dakota					718		
Georgia					722		
New Jersey	485						
North Carolina	485						
silver, Arizona	761						
Colorado	751						

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Ruby silver, Idaho.....	770						
Montana.....	755						
New Mexico.....	757						
Utah.....	774						
Ruffin, Edmond, the marl beds of South Carolina.....	511						
Russia chrome iron ore.....	428	571	358			120	
coal.....	5, 109	13	11	235	18, 189	28, 208	
copper.....	257		241	128	87		73
gold.....		319					
iridium.....		581					
iron ore.....	109		193		18		25
lead.....	323	434	270				
manganese.....		555		204	161	141	
mining law.....		1002					
natural gas, Baku district.....		243					
petroleum.....		232		463, 470	458	478	
pig iron.....	109		193				21
platinum.....		576	368	222	142	165	143
quicksilver.....						105	
silver.....		319					
steel.....				21	18		21
tin ore.....		619					
zinc.....			283				
Rutile.....	492, 674	382, 765	437	5, 8, 604	7, 556, 702, 772	584	6, 446
Sacramento, Cal., structural materials.....				535		522	
Sagenitic rutile.....	491	781	443	604	556	584	446
St. Joseph, Mo., structural materials.....						528	
St. Louis, Mo., coal market.....	103, 105					198	166
coke market.....						198	166
lead works.....	313						
structural materials.....				533		528	
St. Paul, Minn., structural materials.....				533		527	
coal trade.....						196	164
Salem, Mass., bluestone manufacture.....	297						
Salisbury district, Connecticut, iron ore.....			188	14, 42	16, 32, 42		
Salt.....	532	827	170, 474	629	611	597	482
analyses.....	564	849	479	636			
association, Michigan.....					613	599	
beds, Stassfurt, Germany.....					630		
cake, imports.....				640			
consumption, Pacific coast.....	542						
dairy.....					613	599	
epsom.....					699, 735, 810		
exports.....	551	850	484	641	625	610, 612	490
history.....	560						
imports.....	549, 551	850	481, 484	640	611, 623	610	489
in Arizona.....	550, 763	848	483		699		
Arkansas.....	671	843			702		
California.....	532, 547, 767	845	480	628	611, 622, 704	597, 605	482, 489
Colorado.....	541	843					
Dakota.....	541						
Idaho.....	550, 771	848	484		724		
Illinois.....	678	842		628	611, 725	597	482
Indiana.....	679	842		628	611, 728	597	482
Indian Territory.....					730		
Kansas.....	532, 683	843			622, 732	597, 607	482, 488
Kentucky.....	532, 684	842		628	611, 734	597	482
Louisiana.....	532, 686	841	480	628, 636	611, 620, 736	597, 604	482, 488
Michigan.....	532, 696	828	474	628	611, 746	597	482, 483
Minnesota.....					748		
Missouri.....	702	843			752		
Montana.....	541						
Nebraska.....	702	843			750		
Nevada.....	532, 543, 772	847	483	628, 638	611, 756	597	482
New Mexico.....	542, 744, 757	843			617, 763, 804		
New York.....	532, 709	830	476	632	611, 765	597	482, 484
North Carolina.....	717	840			773		
Ohio.....	532, 541, 719	836	479	628	611, 618, 776	597, 604	482, 488
Oregon.....	550				778		
Pennsylvania.....	532, 723	835			780		
Tennessee.....	733	842		628	611, 791	597	482
Texas.....	532, 734	842			792		
Utah.....	532, 549, 759	844	483	628, 639	611, 622, 795	597, 605	482, 489
Virginia.....	532, 740	840		628	611, 800	597	482

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Salt in West Virginia	532, 744, 759	839	479	628	611, 620, 804, 809	597, 604	482, 488
Wyoming	536	828	476	631	612	599	
inspection	539, 549	829		629	613	606	
prices	536, 551	827		628	614, 621	604	
production	xiv, 532	5, 827	4, 474	4, 628	6, 611	597	4, 6, 482
use in glass-making		966					
Salt-peter	597				644		
in Arkansas	671				702		
Illinois	679				727		
Indiana	681				730		
Kentucky	686				735		
Missouri	702				753		
Tennessee	733				791		
Texas	735				794		
Utah	775				796		
West Virginia	744				805		
Samarskite					668, 772		
San Antonio, Tex., structural materials					511		
Sand, glassmakers'		900	545				
Alabama					695		
Illinois	678				726		
Indiana					729		
Massachusetts	693				743		
Mississippi	699						
Missouri	701				752		
New York	710				767		
Ohio	720				777		
Pennsylvania	724				782		
South Carolina	729						
Tennessee	733						
Virginia					803		
West Virginia	744				805		
Wisconsin	747				808		
moulding					729		
Sandstone		664		546	520	544	374
flexible	676, 715				722, 786		
in Alabama	728						
Arizona	669				693		374, 377
Arkansas	764				700		374, 378
California	672				701		374, 378
Colorado	767	664		536	704	545	374, 382
Connecticut	451, 752			535	521, 711	544	374, 384
Dakota	451, 672			522	521, 714		374, 385
Florida	451				717		374, 429
Georgia				529			374, 386
Idaho	676						374, 388
Illinois	770				723	544	374, 388
Indiana	451, 678			532	726		
Iowa	451				729		374, 393
Kansas	451			534		514	374, 394
Kentucky	451, 684				733	514	374, 395
Louisiana	685			531	735		374, 396
Maine	687				736		
Maryland	688			520	737		
Massachusetts	691				740		374, 399
Michigan	451, 693				521, 748		374, 402
Minnesota	696			531, 582	746	544	374, 403
Mississippi	451, 697			532	748	544	374, 404
Missouri	699				750		
Montana	451, 701			533			374, 405
Nebraska							374, 408
Nevada	703				555		
New Hampshire					521		374, 409
New Jersey							374, 409
New Mexico	451, 706			547	761		376, 410
New York							374, 411
North Carolina	710			523, 546	767	544	374, 411
Ohio	715				772	545	374, 415
Oregon	451, 720			546, 582	521, 777	545	374, 415
Pennsylvania							374, 418
Rhode Island	451, 724			546	782	545	374, 419
South Carolina	727						374, 428
Dakota	728						
Tennessee							374, 429
Texas	732			529	790		374, 429
Utah	734			530	793		374, 431
Vermont	774				795		374, 432
Virginia	738				798		374, 432
Washington	742			529	802		374, 436
West Virginia	451						374, 437
	451, 744				521, 805		374, 437

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Sandstone in Wisconsin	451, 746			535	807	545	374, 438
Wyoming					809		374, 440
production				546	520	544	374
quarry methods	450				521	545	
tests				548			
uses							374, 375
Sandusky, Ohio, gypsum					597		
San Francisco, Cal., bluestone manuf- ture.	297						
coal	97, 102		16				168
manganese	424						
pig iron		287					
quicksilver		501		163			99
structural materials					508	523	
Sanidin in North Carolina					668		
San Juan Mountains, Colorado, tin ore	434						
San Luis Obispo, Cal., chrome iron ore	428					119	
Saponite	475, 767				704, 810		
Sapphire	485	733, 781	439, 443	604	556, 571	584	446
in Arizona	485				576		
Colorado	486						
Georgia	677				722		
Montana	485	736					
New Jersey	485, 708				762		
New Mexico	485						
North Carolina	485	734					
Pennsylvania		735					
Sardonyx, Colorado		757					
Satin spar		777					
Savannah, Ga., structural materials						523	
Saward, F. E., on anthracite coal trade		73		234			
Saxony bismuth		655					
lead	322						
nickel	406						
Scapolite, Massachusetts		773					
Schlauch, L. E., on structural materials			396				
Schmitz, E. J., on manganese			345				
Schneider, L., on tungsten			366				
Schönite, artificial, from kainite					642, 645		
Schorlomite		742					
Scranton, Pa., coal district	16, 107	67					
Scythe stones	739			591	553, 798		
Seattle, Wash., coal		90	15, 70				
Selenide of mercury, Utah	775				796		
Serpentine		775					
in Arkansas	672				703		
Colorado	753				713		
Delaware	675				719		
Georgia	677				722		
Maine	690	776					
Maryland	691	776			740		400
Massachusetts	695	776			745		
New Jersey	708	776			762		
New York	712	776			769		
North Carolina	716	776			772		
Pennsylvania	724	776			782		
Rhode Island	727				786		
Vermont	737				797		
Virginia	742				802		
Sewer pipe		693	423	576			
Shale oil		929		484			
Shaler, N. S., Rhode Island coal fields					351		
Shamokin, Pa., coal district	22		46, 53				
Sheafer, P. W., on anthracite		70					
Shepard, C. U., jr., on foreign phosphates			454				
Sicily petroleum		232					
sulphur	578	868	500		4		515
Siderite		382					
in Alabama	670				695		
Arizona	762				697		
Arkansas	679				703		
Connecticut	674				716		
Illinois	679				727		
Indiana	681				730		
Kansas	684				733		
Kentucky	685				735		
Maryland	693				741		
Massachusetts	695				745		
Michigan	697				747		
Missouri	702				753		
New Mexico	758				765		
New York	711				767		
North Carolina	716				772		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Siderite in Ohio.....	720				777		
Pennsylvania.....	725				782		
South Carolina.....	729				787		
Tennessee.....	732				790		
Vermont.....	738				799		
West Virginia.....	744				805		
Wyoming.....					810		
Sienna.....		928	532	712			
Silesia, Germany, zinc mines and works.....	356	482					
Silicified coral.....		758					92
wood.....	492	758, 781	443	604	556	584	446
Silliman, B., jr., on petroleum.....	187						
Silliman, B., sr., on petroleum.....	186						
Silurian iron ores.....	150						
Silva, A., on manganese mining.....			329				
Silver.....	172	312	200	104	58	40	47
bromide.....	772				756, 794		
chloride, Arizona.....	760				696		
California.....					707		
Colorado.....	749				707		
Dakota.....					716		
Idaho.....	770				722, 724		
Maine.....					738		
Montana.....	754				753		
New Mexico.....	756				762		
Utah.....	773				794		
Wyoming.....					808		
chlorobromide.....	750, 761				697, 709		
coinage.....					63	39	
consumed in the arts.....		319	206		63		
exports.....		321	207	108	62	40	
extraction.....	646	358	237				
imports.....		321	207		106, 108	62	40
mining, profits.....		318					
native.....	764, 770						
prices.....					695, 711		
production.....	172	312	200	106	62	38	
by States and Territories.....	172	312	200	104, 106	58	36	6, 49
of Alabama.....	176			105	59	37	49
Alaska.....	172, 177		200	105	59, 696	36	49
Argentine Republic.....		319					
Arizona.....	172, 182, 762	312, 315	200	104	59, 701	36	49
Australia.....		319					
Austria-Hungary.....		319					
Bolivia.....		319					
British Columbia.....		319					
California.....	172, 177, 182	312, 315	200	104	59	36	49
Canada.....		319					
Chile.....		319					
Colombia, United States of.....		319					
Colorado.....	172, 182	312, 315, 419	200	104	59		49
Dakota.....	172, 177	312	200	105	59, 717	36	49
France.....		320					
Georgia.....	172, 677	313	200	105	59, 722	36	49
Germany.....	322	319					
Idaho.....	172, 182, 750	312, 315	200	105	59, 723	36	49
Italy.....		319					
Japan.....		319					
Maine.....	172, 687	312	200	104	737	36	
Maryland.....					734		49
Mexico.....		319					
Michigan.....	176, 697			105	59, 746	37	49
Minnesota.....	698				749		
Montana.....	172, 182, 754	312, 315, 423	200	105	59, 755	36	49
Nevada.....	172, 182	312, 315, 418	200	105	59, 756	36	49
New Hampshire.....	176						
New Jersey.....	108				762		
New Mexico.....	172, 182, 756	312, 315		105	59	36	49
North Carolina.....	172, 713	312	200	105	59, 757, 774	36	49
Norway.....		319					
Oregon.....	172, 176, 182	312, 315	200	105	59	36	49
Pennsylvania.....	726				784		
Prussia.....	322						
Russia.....		319					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Silver production of South Carolina.....	172, 729	313	200	105	59, 788	36	49
Spain.....		319					
Sweden.....		319					
Tennessee.....	172, 734		200	105	59, 793	36	
Texas.....				105	59	37	49
Turkey.....		319					
Utah.....	172, 182, 738	312, 315, 417	200	105	59, 799	36	49
Vermont.....				105	59	37	
Virginia.....	172, 177, 743		200	105	59, 803	36	49
Washington.....	172	313	200	105	59, 804	36	49
Wisconsin.....	747						
Wyoming.....	176, 182		200	105	59, 809	36	49
ruby.....					697, 737, 754, 764		
telluride.....					710		
Slate.....	457		398, 532	549, 713	522	547	376
exports.....			400	551	523	548	
in Alabama.....					695		
Arkansas.....	672				525, 703		376, 379
California.....	457, 769				524, 704		376, 382
Colorado.....					524		
Dakota.....		603			718		
Georgia.....	452, 676				524, 721	550	376, 388
Maine.....	452, 688			519, 550	522, 737	547	376, 398
Maryland.....	452, 692			550	741		376, 399
Massachusetts.....	452, 693				743		
Michigan.....	696			550	522, 746	547	376, 403
Minnesota.....	697				749		
Nevada.....					757		
New Hampshire.....	706				760		
New Jersey.....	452, 707				761	547	376, 410
New York.....	452, 711			550	768		376, 414
North Carolina.....	717				774		415
Pennsylvania.....	452, 725		398	550	522, 783	547	376, 424
Tennessee.....	733			553	792	550	430
Texas.....	736				794		
Utah.....			399		524		376, 432
Vermont.....	452, 737			520, 550	522, 524,	547, 549	376, 434
Virginia.....	452, 742			550	522, 802	547	370, 436
pigment.....		7, 929		7, 713			6
prices.....		929	398	550	522	548	
production.....			6, 398	549	7, 522	547	376
Smallite.....	674, 702, 753	548			713		
Smelting furnaces.....	324, 409						
Smith, D. B., on coal receipts at Toledo, Ohio.....						190	
Smith, E. A., on Alabama coal.....	144						
iron ores.....	149	15					
marls.....	523						
Smith, T. G., on coal at Buffalo.....						186	
Smithsonite, Arizona.....	764				700		
Arkansas.....	672				703		
Illinois.....	679				727		
Iowa.....	682				732		
Kansas.....	683				733		
Maryland.....	692				741		
Missouri.....	701				752		
New Jersey.....	707				761		
Pennsylvania.....	726				784		
Tennessee.....	732				790		
Virginia.....	742				802		
Wisconsin.....	746				807		
Smock, John C., on buildingstone in New York.....					520		
ores, minerals, etc., in Jersey.....	665						
Smoky quartz.....	490	781	443	604	556		446
Snowshoe district, Pennsylvania, coal.....		184	60, 103		329		
Soapstone.....	xiv, 464	10	8				476
in Alabama.....					693		
Arizona.....	762				698		
Arkansas.....					703		
California.....	475, 767				704		
Connecticut.....					716		
Georgia.....					722		
Maryland.....	693				742		
New Hampshire.....	704						
North Carolina.....	713				769		
Rhode Island.....					786		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Soapstone in South Carolina	729				788		
Vermont	737						
Virginia	742						
Société des Metaux					67	6, 45	
Soda	xv, 601	964			699, 779		
analyses in Wyoming	601		551				
ash		963	550				
in glass-making		963	546				
Sodalite	498	773					
Sodium bichromate		572	178, 359				
carbonate	xv, 601				704, 756,		
metallic, Castner's process					809		
nitrate	599	966			651		
permanganate		557			657		
salts		964	231, 547	651	653		
sulphate	603, 759,	963			638, 706,		
	763, 772				757		
Soetbeer, Dr., on production of precious metals.	182						
Solvay process for sodium salts		964	231, 547		655		
South African diamond mines					563		
South Carolina, alum				681	786		
asbestos	588, 728	913					
bismuth		654					
bismuthite	728				786		
brick						563	
chalcopyrite	728				787		
clay	470, 728				786		
coal	729				787		
copper ores	729				787		
feldspar					787		
fertilizers, analyses	520		471	625	581, 593		
fire clay	466, 728				786		
galena	729				787		
gold	172, 728	312	200	105	59, 786	36	49
granite	728				515, 786	539	374, 428
graphite	729			686	787		
hematite	729				787		
iron ores	729			83	787		
itabirite	729				787		
itacolomite	728				786		
kaolin	728				545, 786		442
lead phosphate	729				787		
lignite	729				787		
limestone	728				786		373, 428
malachite	729				787		
manganese ores	424, 729	552		193	787	124, 130	127, 134
marble	505, 728				786		428
marl	523, 728				786		
mica		908			671		
mineral waters		984	540	718	685	628	522
ocher	729				787		
phosphate rock	508, 728	783	5, 144	7, 609	6, 580	586	449
pyrites	729	880			787		
pyrolusite	729				787		
quartz					787		
sand	729				787		
sandstone	728				786		
siderite	729				787		
silver	172, 176,	313	200	105	59, 788	36	49
	729						
structural materials						533	373, 428
talc	729				788		
whetstone					788		
zircon		741					
South Dakota, limestone							373, 428
Spain, antimony		645					
coal	5, 109	13	11	235		28, 208	
copper	249	356, 360,	234	133	93	73	73
		365					
		581					
iridium							
iron ore	109		98, 101	102			22
lead	322	434, 436	264				
manganese		555		201	155, 159		130
mining law		1001					
nickel ore	407						
petroleum		232					21
pig iron							
pyrites	253	882	507	654			
quicksilver	392	496				105	
silver		319					
steel	109						21
tin ore		618					
zinc		480, 400					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Spathic iron ore, Alabama	670				695		
Arizona	762				697		
Arkansas	672				703		
Connecticut	674				716		
Kansas	674				733		
Maryland					741		
Massachusetts	695				745		
North Carolina	717				774		
South Carolina	729				787		
Vermont	738				799		
Wyoming					810		
Specular iron ore, Colorado	751				710, 713		
Georgia	676				720		
Maryland	691				740		
Massachusetts	693				743		
Michigan	696				746		
Minnesota	697				747		
Missouri	700				751		
New Hampshire	705				759		
New York	709				766		
North Carolina	714				771		
Pennsylvania					781		
South Carolina	729				787		
Virginia	740				800		
Wisconsin	746				806		
Spelter (<i>see zinc</i>)							
Spenceville copper mines, California	217, 226				59		
Sphaerosiderite, Colorado	753				714		
New Mexico	758						
Sphalerite		382					
in Alabama	670				695		
Alaska					695		
Arizona	762				698		
Arkansas	672				701		
California	769				706		
Colorado	752				711		
Connecticut	674				716		
Dakota					717		
Idaho	770				723		
Illinois	679				727		
Indiana	681				730		
Iowa	682				731		
Kansas	683				733		
Kentucky	686				735		
Maine	688				737		
Maryland	692				741		
Massachusetts	695				745		
Minnesota	698				749		
Missouri	701				752		
Montana	755				755		
Nebraska	703						
New Hampshire	706				760		
New Jersey	708				762		
New Mexico	757				764		
New York	713				769		
North Carolina	717				774		
Pennsylvania	725				784		
Rhode Island	727						
Tennessee	732				791		
Utah	774				796		
Vermont	738				790		
Virginia	742				802		
Wisconsin	746				807		
Spiegeleisen	123	263, 560	187, 306	57			11, 14
Spilosite				599			
Spinel	486	737					
Spodumene	488, 716				738, 772	150	
Springfield, Mass., structural materials						526	
Sproull, H. S., on gypsum			458				
structural materials			395				
Standard Oil Company, operations	308						
Stanford, E. C. C., process for extracting iodine			489				
Stannite		593					
Stanton, C. P., on Arizona coal		18					
Stassfurt, Germany, potassium salts industry					630, 640		
Staurolite		742					
Steatite (<i>see Talc.</i>)							
Steel	109	254	160, 180, 186	12, 18	12, 161	12, 29	21
Bessemer consumption	125	254	180			12, 19	
exports	140		192			12	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Steel imports	139		190	12		13	
manganese		558			161		
melting by natural gas			160				
physical tests						118	
prices	141					16	13
production	125, 138	250, 256	181		13	12, 29	12
of Alabama	137			18	18	14	
Austria-Hungary	109	257		21	18	29	21
Belgium	109	257		21	18	29	21
California			186	18	11	15	12
Canada							21
China	111						
Colorado	120		186	18	11	15	
Connecticut	120		186		11	14	
Delaware				18		14	12
France	109	257		21	18	29	11, 21
Georgia						14	
Germany	109	257		21	18	29	21
Great Britain		257		21	18	29	16, 21
Illinois	119		186	18	11	14	12
Indiana				18	11	14	12
Iowa						14	
Italy	109	257		21	18	29	21
Kentucky			186	18	11	14	12
Luxemburg				21	18	29	21
Maine						14	
Maryland			186			14	12
Massachusetts	120		186	17	11	14	
Michigan			186	18	11	14	12
Missouri	120		186	18	11	14	12
New Hampshire	120		186			14	
New Jersey	120		186	18	11	14	12
New York	120		186	18	11	14	12
North Carolina				18		14	
Ohio	120		186	18	11	14	12
Oregon						15	
Pennsylvania	120		186	18	11	14	12
Rhode Island						14	
Russia	109	257		21	18	29	21
Spain	109	257		21	18	29	21
Sweden	109	257		21	18	29	21
Tennessee	119, 135		186	18	11	14	
Texas				18	11	14	
Vermont	120		186				
Virginia				18	11	14	12
Washington						15	
West Virginia			186	18	11	14	12
World	109	256		21	18	30	
Wisconsin				18	11	14	12
Wyoming				18	11	15	
summary						1	1
rails	127, 137	215, 255	181	13, 17, 20	11, 12	12, 21	
Stephanite	752, 762, 770				689, 712, 723, 738		
Stenbergite, Arizona	762				698		
Steubenville, Ohio, coke		171	93				
Stibnite, Arizona	764				700		
Arkansas	672				703		
California	769				704, 706		
Dakota					717		
Idaho	770				723		
Maine	690						
Nevada	772				757		
Utah	774				796		
Stone buildings, value	XIII		3, 396	536	3, 504	516	373
Stoneware, exports				580			444
general statistics		704					
manufacturing processes		685					
productions		698					
Stove linings		685					
Stowell, S. H., on petroleum	186		130				
Straits Settlements, tin ore	436						
Stream tin	434		593, 612		716	154	
Cornwall			593			153	
Dakota			612		716		
Ireland			615			153	
Idaho	434						
New South Wales			619				
Tasmania			621				
Wyoming			613				
Strikes, coal operatives	102	85	517, 528, 535, 536, 541	188	186	188	169
Stromeyerite	762				698, 712		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Strontia	582, 720, 769			699, 701	706, 777, 783		
Structural materials	450	662	395	517	503	516	3, 373
Stubbs, W. C., on the phosphates of Ala- bama.		794					
Stucco			462	620			465
Succinite	675, 708	780			719, 762		
Sudbury, Canada, nickel platinum			516	644 644	604	165	
Sulphur	578	864	494 513	644 644	604		515
estimation in pyrites cinders							
exports	579	872					515
extraction from ores		868					
imports	579	867	497	645	605	605	515
in Alaska		867					
California	578, 769	867		644	706		
Florida		864					
Idaho		864					
Italy		868					515
Kansas	684	864			733		
Louisiana	687	864	496	644	736		515
Nevada	578, 772	865		644	757		515
New Mexico		864					
New York		864					
Ohio		864					
Texas		864					
Utah	775	867	494	644	604, 796		515
Virginia	743	864			803		
Wyoming	759	864		644	810		
prices		868		647	604		
production	XIV, 578	5, 868	4, 500	4, 10	4, 8	5	4, 6, 515
recovery from alkali waste uses		876	500		607, 655		515
Sulphuric acid	578	876	515	650			
manufacture	578	359		651, 658, 671			
Sunstone	495	771, 781		604	556, 563	584	
Superior, Wis., coal trade							164
Swank, James M., on iron ore and its products. iron and steel indus- try of the United States.	108	257					
Sweden, coal	5, 109	13	11	235	189	28, 208	22
cobalt	405						
copper				128	87	73	73
gold		319					
iron	109		193	21			21
iron ore	109				18		22
lead		434					
manganese		555				142	130
nickel ores	405, 410						
silver		319					
steel	109						
tin ore		619					
Swineford, A. P., coal in Alaska on Lake Superior cop- per mines.	215					214	
Switzerland, asphaltum		937					479
Syenite, Arkansas					701		379
California	769				706		
Maine					737		
Massachusetts					743		
Sylvanite, Colorado					712		
Syracuse, N. Y., structural materials					510	531	
Tacoma, Wash., structural materials						535	
Talc	585		534				476
in Alabama	669						
Arizona	762, 764				698, 700		
Arkansas					703		
Connecticut	674				716		
Dakota					718		
Georgia	677		565		722		
Maine	689				738		
Maryland	693				742		
Massachusetts	695				745		
New Hampshire	704				758		
New Jersey	708				762		
New York	711		534		768		476
North Carolina	660, 715				772		
Pennsylvania	585, 725				783		
Rhode Island	727				786		
South Carolina	729				788		
Texas	736				794		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Talc in Vermont	737				797		
Virginia	742				802		
production	585		8			6	476
Tantalite, analysis of						151	
Tasmania, tin ore	436	621					
Taylor, F. W., on cobalt	421						
Tellurides, Arizona	762			648	698		
California	447			648			
Colorado	447, 748,			648	710, 754		
	751						
Nevada				648			
Montana	447						
Utah	447						
Virginia	447, 677,				707		
	743						
Tennessee, alum	732	949			791		
asphaltum	732				791	513	
azurite	730				788		
barytes	580, 730	922			788		
bitumen	732				791		
brick			415		536, 539	563, 565	
calamine	730				788		
cannel coal					357		
cement					529		461
cerussite	732				791		
chalcocite	730				788		
chalcopyrite	730				788		
charcoal	131						
clay	470, 730				788		
coal	6, 34, 72,	88, 154	11, 64,	34, 230	171, 352,	362	146, 269
	730		113		788		
analyses		198			354	366	
prices					357		
production	73			11, 341		176, 362	148, 269
value		88	11	11, 341		362	148, 269
coke		149, 152,	77, 111	342, 378,	383, 420	395, 400,	
		196		417		425	
analyses		151, 197		421			
copper ores	231, 730				788		
epsomite	732				791		
fire brick and clay	466, 732				791	570	
flagging stone	730				788		
fluorspar		776					
galena	730				789		
gold	172, 176,	312	200	105	59, 789	36	
	730						
granite	732				791		
gypsum	733				791		
hematite	731				789		40
iron	119, 129,	185, 252,	182	92	22	14, 23	10, 17
	133	278					
ores	667, 732	278			790		24, 40
pyrites	733				792		
lead ores	732				791		
lignite	733				791		
lime					533	533, 556	429
limestone	451, 731			529	789		373, 429
limonite	731				789, 790		
lithographic stone	595, 731	935		691	790		
magnesia	732						
magnesium sulphate					791		
magnetic iron ore	732				790		
malachite	732	778			790		
manganese ores	421, 733		344		791	124, 131	127, 135
marble	451, 732			545	518, 790	541, 543	375, 429
marl	524, 732				790		
melanconite	732				790		
metallic paint				711			510
millstones	732				790		
mineral waters		985	540	718	686	628	522
natural gas			161		492	510	
niter	733				791		
petroleum	733	220	130, 147	461	452, 791	442, 463	362
pyrites	733		506		792		
quartz	733				792		
salt	733	842			628	611, 791	597
salt peter					791		
sandstone	732				790		374, 429
silver	172, 176		200	105	59	36	
slate	733				792	550	430
smithsonite	732				790		
steel	117, 120,		184, 186	18		14	
	137						
structural materials				529		533	373, 429

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Tennessee, tetrahedrite					792		
zinc ores	367, 730, 732				790		
Terre pla'cs.		632, 637					
Terra alba	924		526	706	676	621	512
Terra cotta		652, 692, 700	422		719		
Tetradymite, Arizona	440				700		
Georgia	677				722		
North Carolina	717				774		
Virginia	743				803		
Tetrahedrite		382					
Alaska					695		
Arizona	762				698		
Arkansas	671				701		
Colorado	752				712		
Idaho	770				722		
Maine	689				738		
Massachusetts	695				745		
Montana	756				755		
New Mexico	757				764		
North Carolina	718				774		
Tennessee					792		
Utah	774				795		
Texas, agate	734	757			793		
alum	734	949			793		
amethyst	734	751			793		
asbestos	734				793		
asphaltum	734				793	513	477
blast furnaces	121						
bismuth ore	734				793		
bitumen	734				793		477
brick			415		536	563	
brines					792		
cement					527	551	461
chalcedony	734	757			793		
chalcocite	735				793		
clay	733				792		
coal	74, 733	12, 89	11, 67	230, 347	171, 357	171, 206, 367	147, 271
coke					421	307, 425	
copper		342		378, 421	793		
feldspar	735				793		
fire brick and clay	466, 735				541	566	
gadolinite						582	
galena	735				793		
garnet	735				793		
gold	735			105	59, 793	37	49
granite	735				793		374, 431
gypsum	526, 735	809			793		
hematite					794		40
ilmenite	735				793		
iron	129	252	182	18		14, 23	10, 17
ore	735				51, 794	51	24, 40
pyrites	735				794		
jasper	735	762			793		
kaolin				573	793		442
lead ore	735			140			
lignite	734				792	372	
lime			410		533	556	
limestone	734			530	793		373, 431
analysis							432
lithographic stone		935		691			519
magnetic iron ore	735				794		
manganese ores	736				794		
marble	735				794		
mineral waters		985	540	718	686	628	522
molybdenum	735				794		
niter	735				794		
obsidian	735				794		
ocher	735				794		
opal	735				794		
petroleum	285	320		463	794		292, 359
pyrite	735				794		
pyrolusite	736				794		
salt	532, 734	842			792		
sandstone	734				793		374, 431
silver	734			105	59, 793	37	49
slate	736				794		
steel	120		184	18	11	14	
structural materials				530	511	533	373, 431
sulphur		861	496				
talc	736				794		
titanic iron					793		
tourmaline	735				794		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Tharsis Sulphur and Copper Co.			236		94		
Thenardite, Arizona	764				700		
California	769				706		
Nevada	772				757		
Wyoming	759						
Thetis hair stone	491						
Thinolite	767, 772				704, 757		
Thompsonite	496	774, 781	443	604	556	584	446
Thulite					668		
Tiemannite, Utah	775				796		
Tile		681, 693,		574, 578			
hollow		704					
imports		682, 697					
Tin	434	707	370	578	549	573	
alloys		593, 629		214	134	144	119
exports	436	640	384	216	136	157	122, 123
Banca		622					
Billiton		622					
France		618					
Great Britain		619, 625					
New South Wales		620					
South America		625					
Tasmania		621					
foreign sources	436	615	377	215			121
imports	436	639	384	215	137	157	122
Great Britain		618, 625					
Japan		623					
South America		625					
Sweden		619					
mining, Harney Peak Co.						144	119
statistics, Great Britain		615					
prices			384	216	216	157	123
ore analyses		614	370			147, 154	
history		602, 611,					
635							
dressing, Cornwall			377				
exports, France		618					
New South Wales		620					
Queensland, Australia		621					
Russia		619					
South America		625					
Straits Settlements		622					121
Tasmania		621					
Victoria, Australia		620					
in Alabama	436, 667	601			693		
Australia	436						121
Austria		618					
Banca	436	594, 622					121
Billiton		594, 622					121
Burmah		623					
California	434, 438	614			136, 705		120
Colorado	768						
China	434				712		
Connecticut		633					
Cornwall	673	598			714		
Dakota	436	593, 615					
Finland	434	593, 602	370	214	134, 716		120
France		593					
Georgia		617					
Germany		601					
Idaho	434	618					
India		613					
Italy		623					
Japan		618					
Maine	434, 687	623					
Massachusetts		598			738		
Mexico		597, 694			744		
Missouri		623				436	
Montana		602					
New Hampshire	434	613					
New Jersey	705	597			759		
New South Wales		599					
New York		593, 619					
North Carolina		599					
Portugal		601			130, 773		
Queensland		618					
Russia		620					
South America		619					
Spain		625					
Straits of Malacca	436	618					
Straits Settlements		621					121
Sweden		619					
Tasmania	436	621					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Tin ore in Victoria, Australia	630						
Virginia	599		371	214	136, 803		121
West Virginia					136		
Wyoming	613				808	148	
origin	595						
production, Austria	618						
Banca	622						121
Billiton	622						121
Germany	618						
Great Britain	616						121
India	623						
Italy	618						
Japan	623						
Queensland, Australia	621						
Russia	619						
Spain	618						
Sweden	619						
Victoria	620						
treatment						154	
oxide imports			385	215			
physical properties	625						
plate and terne plate	637				12	22	
Plate Association	635						
plate imports	685		191	14, 215	137	13	122
industry, United States	634			214			
manufacture						20	
prices	635						
quantity of metal in	635						
value						13	
works	635						
powdered	626						
prices	637		384	216	137	158	
summary		3	3	2, 7			
world's output	XIII						121
Tincol, California	436				704		
Titanate of lime, Arkansas	767				702		
Titanic acid, Arkansas					701		
North Carolina					772		
iron ore, Minnesota					749		
New York	712				769		
Texas					793		
Wyoming					810		
Titaniferous magnetite analysis	149						
Titanite	498	774					
Toledo, Ohio, coal trade	103						159
structural materials					510	532	
Topaz	486	716, 737	440, 443	596, 604	556, 576	580	446
in Arizona	486						
Colorado	486	724, 737			712	580	
Connecticut	674				716		
Maine	486	738					
Massachusetts					743		
New Hampshire						581	
New Mexico	486						
Utah		738					
production		781				581	446
smoky	490						
Topeka, Kans., structural materials				531		535	
Torbernite					668		
Tourmaline	188	610, 617, 743	437, 443	595, 604	555, 560	582	446
in Dakota					718		
Maine	488	723, 743					
New York	488	745			769	582	
North Carolina		745			668		
Pennsylvania		745					
Texas	735				794		
production	488	781				584	
Trachyte	772				724, 756		
Tremolite		382					
Trenton limestone					481, 490		
Trilobites		727	143	604	555	584	446
Trinidad Coal and Coking Company		29	158				
asphaltum	605						478
Triphylite		618					
Tripolite, Georgia	677				722		
Indiana	681				720		
Maine					738		
Maryland	693				742		
Massachusetts					743		
New Hampshire	701				758		
New Jersey	705				762		
Virginia	743				803		
Wyoming					809		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Troilite, composition			517				
Trona	759, 769, 772				706, 756, 809		
Trumbull, Conn., wolfram	431						
Trumbull county, Ohio, coal			44	292		296	235
Tufa	767, 769, 774				704, 722, 768, 796, 805		
Tully, N. Y., salt wells							487
Tungstate of iron, California	769				707		
Tungsten	431	574	366	218			
in Connecticut		574					
Virginia		574					
ore analysis		575					
steel			366	218			
utilization	431						
Turkey chrome iron ore	428	571					
gold		318					
iron	111, 251						
ore exports		258					
lead		434					
manganese				205		142	130
silver		319					
umber				713			
Turner, G. M., on novaculite			433	589			
phosphorus				676			
Turquoise	493	767, 781	441	604	556, 562	582, 584	446
in Arizona	493	767			698, 703		
Colorado						582	
Nevada	493	768			757		
New Mexico	484, 493, 757	768			764	582	
Tuscarawas county, Ohio, coal			44	292		296	235
Tuscarora coal			20				
Ulexite	767, 772				707, 779		
Ultramarine		928	526	707	677	622	
Umbur		927	532	713		619	
imports		928		713	678	620	
in California	769				707		
Georgia					722		
Mississippi				713			
Pennsylvania			532	713			
Turkey				713			
Vermont				713			
Virginia	743				803		
prices				713		619	
Union Pacific Railway coal	87, 89	102	18, 22, 39, 72			390	185
Ural Mountains, Russia, platinum	444	576	368			165	143
Uraninite	674, 752	618			668, 712, 716		
Uranium	448				668, 718		
Utah alabaster	775				796		465
alum	775				796		
anglesite	773				794		
antimony	774	643			796		
arsenic, yellow sulphide					795		
arsenopyrite	773				794		
asbestos		913					
asphaltum					794	513	478
azurite	773				794		
barytes	733				794		
biotite	774						
bismuth ore	440, 773	654			796		
bituminous rock							478
blast furnaces	121						
brimstone	775				796		515
calcite	744, 773				794, 796		
cement rock						553	461
cerargyrite	773				794		
cerussite	773				795		
cervantite	774				796		
chalcopyrite	773				795		
chrysocholla	773				795		
cinnabar	774				796		
clays	773				795		
coal	6, 74, 773	12, 89, 154	11, 83	230, 350	171, 359, 795	68, 206, 374	147, 272
analyses		203			359	375	
production			68	352		171, 374	147, 272
coke		150, 202	77, 378			397, 441	
copper ores	228, 773, 794	329, 342	210	112	69, 795	59	60
production	216, 228	329	210	112	69	59	59

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Utah dolomite	773				795		
erubescite	773				795		
fahlerz					796		
galena	773				795		
geocerite	774				795		
gilsonite					795		
gold	172, 176, 182, 774	312	200	58, 104	59, 795	36	478 49
granite	774				795		374, 432
graphite	916						
Great Salt Lake, analysis		843					
gypsum	774	812			795		465
hematite	774				795		40
iron	129	252, 288	182				
ore	773	288			795		24, 40
pyrites					795		
kalinite	775				796		
kaolin	775				796		
lead	308	412, 416	248	142	103	86	80
ores					795	86	
molybdate					796		
production	308	412, 416	248	142	103	86	
works						86	
leadhillite	774						
lignite	774				795		
limestone	773				794		373, 432
limonite	774				795		
magnesian limestone	773				795		
magnetite	775				796		
malachite	774				795		
manganese	774				795		
marble	774			546	796, 519	543	375, 432
mercury selenide					796		
sulphide					796		
mica	774				796		
mineral waters		985	540		687	630	
wax	774				795	515	481
mlspickel	773				794		
molybdenite	774				795		
moss agate	491						
natural gas			161	515			
niter	775				796		
ocher	774				795		
orpiment	774				795		
ozocerite	609, 774	955				515	481 465
plaster of Paris	775				795		
polybasite	774						
porphyry	774				795		
pyrargyrite	774				793		
pyrites	774				795		
pyrolusite	774				795		
quicksilver				168			
rhodocrosite	774						
salt	532, 549, 774	844	483	628, 639	611, 622	597, 605	482, 489
salt peter	775				645, 796		
sandstone	774				795		374, 432
silver	172, 176, 182, 774	312	200	104	58, 794	36	49
slate			399		542		376, 432
sphalerite	774				796		
speiss	334						
steel	120						
stibnite	774				796		
sulphur	775	867	494	644	796		515
tellurium	447						
tetrahedrite	774				795		
tiemannite	775				796		
topaz		738					
tufa	774				796		
wulfenite	774				796		
zincblende					796		
Utica, N. Y., structural materials	174					531	
Valentine, J. J., gold and silver statistics	764	314	200, 202				
Vanadate of copper, Arizona	763				700		
lead, Arizona	449				699		
Vanadium	449						
Vancouver's Island, coal	5, 90						
iron ore	111						
Vanquelinite, Arizona	764				700		
Venezuela, copper	250	356, 360, 374	228, 232, 243	128, 139	88, 96	73	73
gold		319					
petroleum				436			

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Venetian reds							510
Ventilation in mines					235		
Verde antique marble, Vermont					797		
Verde salt, Arizona	764				700		
Vermilion	398	3, 501	531	2, 714		622	
imitation				713			
imports		502				622	
paint, Wyoming			531				
prices		501	296	714		622	
production	398	501	296			622	
Vermillion Lake, Minnesota, iron-ore mines.		267	188	75	16	17	35
Vermont, aquamarine	487						
arsenopyrite	737				798		
asbestos	737				798		
braunite	737				798		
brick						563	
chalcopyrite	736				796, 798		
chromic iron ore	569, 737				798		
clay	465, 736				797		
copper	216, 331,	329, 343	210	112	796	54	60
	736						
feldspar	737				798		
flagging stone	737				798		
galena	737				796, 798		
gold	737			105	59, 798	37	
granite	736				513, 797	536, 539	374, 433
graphite	737				798		
hematite	736			42	798		
infusorial earth	737				798		
iron	737			17	42		
ores	120				42, 709		
pyrites	736				797		
kaolin	469, 736						
kyanite		748					
lignite	738				798		
lime					533	556	433
limestone	451						373, 433
limonite	736				797		
magnetic iron ore	738				798		
malachite	736				797		
manganese ores	737	551	342		145, 798	124, 131	121, 135
marble	451, 736			541	518, 797	541	375, 433
marl	738				798		
metallic paint							510
mineral waters		985	540	719	686	629	522
mining law				728			
mispickel	737				798		
nickel	738						
novaculite				590	553		
ocher	738		527		798		508
oilstone	737				798		
peat					798		
pottery clay	469						
psilomelane	738				798		
pyrites	736	678	502		797		
pyrolusite	738				798		
quartz	738				798		
rhodonite		766					
sandstone	738				798		374, 433
scythestones	737				798		
serpentine	737				797		
siderite	738				799		
silver	738			105	59, 799	37	
slate	452, 737		398	520	522, 524,	547, 549	376, 434
					797		
					799		
sphalerite	738						
staurolite		743					
steel	137		184, 186		11		
structural materials				520		534	373, 433
talc	737				797		
umber				713			
verde antique marble					797		
wheatstone	737				798		
zaratite	738				799		
zincblende	738				799		
zircon		661					
Vicksburg, Miss., structural materials						528	
Victoria, Australia, antimony		646					
chrome iron ore						121	
Vfelle, Montagne Company, Belgium zinc works.		489					
Virginia, allanite		773			802		
alum shale					802		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Virginia. amethyst	491						
anthracite coal	7, 32						
apatite analysis		808					
arsenical iron pyrites					803		
arsenopyrite	742				803		
asbestos	588, 738	913			799		
barytes	580, 738	922	525		677, 799		513
bismuth		654					
bituminous coal (<i>see coal</i>).							
blast furnaces	121						
bornite	742				803		
brick production					536, 539	563	
buhrstones		712					456
building stone			397	529			373, 435
calamine	738				799		
calcareous marl					801		
cassiterite					803		
cement					527	551	461
works		672					
cerussite	738				799		
chalcocite	738				799		
chalcopyrite	739				799		
chrome iron ore	742	569			803		
clay	743	678			803		
coal	6, 34, 82,	12, 90,	11, 83	230, 352	171, 360,	380	146, 272
analyses	739	97, 205			799		
production	82	98		355	365		
production					361	171, 206,	
production						377	
coke	742	149, 152,	75, 82,	355, 378,	383, 421	395, 404,	
production		204	119	422		425	
production		152, 205	118	422		4, 400,	
production						426	
copper ores	231, 738,			653	799, 803		
production	741						
corundum		735					
diamonds	484	728					
dufrenite					803		
feldspar	742				803		
fire clay	742				803		
flagging stone	739				799		
fluorspar		777					
galena	739				800		
garnet		747				581	
gold	172, 176,	312	200	105	59, 800	36	49
production	739						
granite	740			537	514, 800	536	374, 435
graphite	590, 743			686	803		
greensand marl					801		
gypsum	526, 740	809	459		800		465
hematite	740			77	800		40
infusorial earth	743	721			803		
iron	119, 125	252	182, 185	24, 33, 77	11	14, 23	10, 17
ore	740	276		77	803		24, 40
kaolin	743				803		442
kyanite		748					
lead ores	738, 743	414			799, 803		
lime			410			556	436
limestone	451, 740				801		373, 436
limonite	740			80	801		519
lithographic stone							
magnetic iron ore	741, 743			78	801		
malachite	741	777			801		
manganese ores	424, 741	551	305, 307	17, 181,	144, 151,	123, 132	127, 135
production				193	802		
production				544	520, 801	544	375, 435
marble	451, 741				592, 801		
marl	523, 741				803		
massicot	743				801		
melaconite	741				801		
mica	743	908			660, 671,	614	
production					803		
microlite		772					
millstone	741				801		456
mineral waters		985	541	719	686	629	522
mining law				729			
mispickel	742				803		
moonstone	496	771					
natural coke					803		
gas			171	515			
ocher	741		527	709	802		508
petroleum			146				
platinum	442						
pottery clay	470						
psilomelane	741				802		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Virginia, pyrites.....	741	879	504	653	802		
pyrolusite.....	742				802		
pyrrhotite.....	743				803		
quartz.....	743	754			803		
quicksilver.....				168			
salt.....	532, 740	840		628	611, 800	597	482
sandstone.....	742				802		374, 436
serpentine.....	742				802		
silver.....	172, 176, 743		200	105	59, 803	36	49
slate.....	452, 742		398		522, 524, 802	547	376, 436
smithsonite.....	742				802		
specular iron ore.....					800		
sphalerite.....	742				802		
steel.....	120, 137		184	18	11	14	12
structural materials.....				529	511	535	373, 435
sulphur.....	743	864			803		
sandstone.....	495						
talc.....	742				802		
tellur-bismuth.....	447, 743				803		
tetradymite.....	743				803		
tin ore.....		599	371		136, 803		120
tripolite.....	743				803		
tungsten.....		574					
umber.....	743				803		
zinc.....	365						
ores.....	738, 742				799, 802		
Volborthite.....	764				700		
Volgerite.....	764				700		
Wad.....		382					
in Arizona.....	762						
Arkansas.....	672				703		
Maine.....	689				738		
New Hampshire.....					760		
New York.....	713				769		
North Carolina.....					774		
Pennsylvania.....	726				784		
Rhode Island.....	727				786		
Wages in coal mining.....	103	100, 137			186, 203		169
Walker, John A., on graphite.....	590	915					
Wallace nickel mine, Canada.....	403						
Wallaroo copper mine, South Australia.....	254						
Warrior coal fields, Alabama.....	36		86	236	156	211	173
Warsaw salt district, New York.....		830, 832		635	617	600, 603	486
Washington blast furnaces.....	121						
brick production.....						564	
calcite.....					803		
cerussite.....					804		
coal.....	6, 90, 95, 775	99	11, 83	230, 357	171, 367, 804	381	147, 275
production.....	96	12	11, 70	230, 359 362	368	171, 206, 381	148, 275
coke.....		149, 152, 206	77, 120	378, 423	383, 422 426	395, 400, 426	
galena.....					804		
gold.....	172, 176, 182	312	200	105	58, 804	36	49
granite.....							374, 437
infusorial earth.....				588			
iron.....	129, 148	252, 288	182	18	11	15	10, 17
ore.....	775						40
lead carbonate.....					804		
lignite.....	96, 775				804		
lime.....			412				437
limestone.....					803		373, 437
limonite.....	775				804		
marble.....					544		
mineral waters.....		985	541	719	686	629	522
petroleum.....			152				
plastic clay.....	775				804		
sandstone.....	451						374, 437
silver.....	172, 176, 182	313	200	105	59, 804	36	49
steel.....				18	11	15	
structural materials.....						535	373, 437
Watch jewels.....					573		
Weeks, Joseph D., on glass materials.....		958	544				
manganese.....			303	180	144	123	127
manufacture of coke.....		144		378	383	395	
natural gas.....				488	464	481	366
petroleum.....				439	436	442	287
Wells, Fargo & Co., on lead product in Utah.....				142	103	86	

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
West India petroleum		232					
West Virginia anthracite					804		
asphaltum					806		
barytes	605, 745	935			805		
blast furnaces	745						
brick	121				536		
brines					804		482, 488
bromine		851	487	642	804, 626, 648	613	493
cement		672					461
coal	6, 33, 83	12, 90, 142, 171	11, 83	230, 369	171, 373, 804	385	146, 277
analysis	84	208, 212		429		389, 432	
beds	83	90, 133					
mining in Kanawha Valley.		131					
production	84	98	71	370	375	171, 206, 386	
coke	83	145, 152, 207	77, 374	378, 424	383, 422	395, 427	
analysis		208, 210, 213		428	424, 430	439	
ovens		143, 150				398, 400, 436	
production	83	149, 208, 213	71, 122, 212	426	423	4, 400, 439	
dufrenite	745				806		
fire brick and clay	744				542, 804	566	
fluorspar	745			692	806		
gas coal		133		371			
grahamite	745				806		
graphite				686			
hematite	744				805		40
iodine		854					
iron	125, 135	252	182	32	11	14, 23	10, 17
ores	744	277		81	805		24, 34
lime	744		410				437
limestone	744				806		373, 437, 439
limonite	744				805		
manganese ores	424, 745				806		
marl					805		
mica					671		
mineral waters		985	541	719	686	630	522
milling law				729, 741			
natural gas		233, 243	156, 161, 173	504	26, 466, 484		367
niter	744				805		
ocher	745				806		
petroleum	189, 206, 744	216		461	438, 451, 805	4, 442, 463	292, 329
quartz	744				805		
salt	532, 539, 744	839	479	537, 628, 637	611, 620, 804	597, 604	482, 488
salt-peter	744				805		
sandstone	451, 744				521, 805		374, 438
siderite	744				805		
steel	120, 137		184	18	11	14	12
tin ore					136		
travertine					805		
tufa					805		
Westphalia, Germany, zinc	356						
Whetstones				589	553	5	460
in Dakota					718		
Indiana				592	729		460
North Carolina	715				712		
Rhode Island	727				786		
Scotland				594			
South Carolina	729				788		
Vermont	737			590	798		
Wisconsin	747						
White, George W., on structural materials.			396				
White, Prof. I. C., on the Kanawha, West Virginia coal field.		91, 93, 95					
White lead	XII	920	524	702	674	616	511
imports		921		703	675	617	511
manufacturers				702	674		
prices				703	674	616	
production				10, 702	2, 674	616	511
Whiting		931	526	707	677	621	512
Wilber, F. A., on apatite	521						
clays	465	676					
gypsum		809					
marls	522	808					

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Willemite	496, 707	773			700		
Williams, Albert, jr., on coal	764						
useful minerals of the United States.	664				688		
Williamsite	497						
Willis, Bailey, on coalfields of Washington.				357			
Wilmington, Del., structural materials				526			
Wilson, John N., lead ore, Sophia district.				147			
Winslow, Me., tin-ore mine		598					
Wire and wire-rope production				12			
Wisconsin agate		757					
amethyst		751					
asphaltum	747						
azurite	745				807		
barytes	747				807		
bitumen	747						
bog iron ore					807		
brick					536, 539	564	
catlimite		779					
cement		672			529	551	461
cerussite	747						
chalcedony		757					
chalcocite	747				807		
chalcopyrite	745				807		
clay	746				806		
coal, Milwaukee						193, 395	162
coke						397, 405	
copper	745, 747				807		
diamonds		732					
fire clay	407				806		
galena	745				806		
garnet	747						
gold	747						
granite	746				514, 806	536	374, 438
hematite	746				72	806, 857	40
iron	125, 133	252	185	18, 26	11	14, 23	10, 17
ore	747				806		30, 40
kaolin	471, 746				806		
lead	312, 747	414, 426		148			
lime					533	556	439
limestone	451, 746			535	516, 807	541	373, 439
limonite	746				807		
mag. etc iron ore					807		
malachite	746				807		
manganese				188	151	128	
manganiferous iron ore					151		
ma ble	451						
metallic paint				711			510
mica	747						
mineral waters		986	541	719	687	629	522
mining law				731			
natural gas			61				
ocher	746				807		508
peat	747				807		
porcelain clay					806		
potash and pearlash					643		
pyrites	747				808		
quartz	747	753			808		
sandstone	451, 746			535	807	545	374, 440
silver	747						
smithsonite	746				807		
sphalerite	746				807		
specular iron ore					806		
steel	120, 137		184	18	11	14	12
structural materials				535	511	535	373, 439
whetstones	747						
zinc	305			156			88
ores	746				807		
Witherite	686	382			735		
Wolfram	431, 769	618		218	707, 716, 718		
Wood coal, Alabama	669						
Massachusetts	695				744		
petrified, Dakota					718		
silicified, Colorado					711		
Wool, mineral	161						
Wulfenite, Arizona	762, 764				698, 709		
Massachusetts	695				745		
Pennsylvania	726				785		
Utah	774				796		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.	Pages.
Wyoming, alum.					809		
amphibolite	759						
anglesite					809		
aragonite					808		
argentite					809		
asbestos	759	913			809		514
asphaltum					809	513	
azurite					809		
barytes					809		
bismuthinite					809		
bitumen					809		
calcite					808		
cassiterite					808		
cerargyrite					808		
cerussite					808		
chalcocite	758				808		
chalcopyrite					808, 810		
chrysocolla	758				808, 810		
clay					810		
coal	6, 87	12, 100	11, 83	230, 374, 377	171, 380, 808	390	147, 280
analyses	86	101		375		391	
production	86, 89	101, 104	72	374		171, 206, 390, 393	280
coke manufacture		151					
copper ores	216, 229	329, 342	210	112	69, 76, 810	59	60
corundum					810		
dolomitic marble					808		
emery					810		
epsom salts					810		
feldspar					810		
fire clay	472						
flagging stone					808		
fluorspar	587						
galena					808		
glass sand					809		
gold	172, 176, 758	312	200	105	59, 808	36	49
granite					808		
graphite	590, 759	916					
gypsum	759				810		465
hematite	758				809		
ilmenite	759				810		
infusorial earth					809		
iron	120, 147	285	184	18	11	15	
ores	758	285			809	35	
kaolin					810		
kleberite					801		
lead ores					808		
lignite	758	100			808		373, 440
limestone					808, 810		
limonite					810		
lithographic stone					810		
magnesium sulphate					810		
magnetic iron ore					810		
malachite					809		
manganese ore					810		
marble					809		375, 440
dolomitic					808		
marl					810		
melanconite					810		
mica	583, 759	911	518		809		
millstone					810		
mineral soap					810		
waters		986	541		886	630	
wax					809		
mirabilite					809		
moss agate	491				810		
natural gas			161				
ozocerite		957			809		
petroleum	211, 759	217	130, 153	462	809	442, 466	363
plastic clay					810		
platnum			367				
pyrites	758				809		
quartz					809		374, 440
salt	541, 759	843			809		
sandstone					809		
saponite					810		
siderite					810		
silver ores	172, 176 182		200	105	58, 809	36	49
sodium carbonate			550		809		
sulphate	603, 759				809		

	1882.	1883-'84	1885.	1886.	1887.	1888.	1889-'90
	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>	<i>Pages.</i>
Wyoming, sulphur	759	864		645	810		
thenardite	759						
tin ore		613	370		808		
titanic iron ore					810		
tripolite					809		
trona	759				809		
vermillion			531				
zircon					810		
Yale, C. G., on borax							494
coal	2		576				
iron on Pacific coast		286	96				
mica			518				
mineral paints			532				
minor minerals of Pacific coast	662						
nickel in California			298				
Oregon				171			
sulphur			496				
Yellowstone National Park, agate		757					
amethyst		751					
geyserite		761					
obsidian		772		597			
Yttria ore					772		
Yttrgummite					668		
Zaratite, Maryland	693				742		
Pennsylvania	726				785		
Vermont	738				799		
Zinc	346	474	272	154	113	92	88
alloys		631					
carbonate in Arizona					700		
Arkansas					701, 703		
Illinois					727		
Iowa					732		
Kansas	733				733		
Maryland	365				741		
Missouri	368				752		
New Jersey	360				761		
Pennsylvania	726				784		
Tennessee					790		
Virginia	742				802		
Wisconsin	365				807		
exports	350	477	274	157	115	94	90
Great Britain		487					
Spain		490					
imports	349	477	274	157	115	93	90
Germany			279				
Great Britain		487					
metallurgy	384, 627, 657						
mines, Belgium		488					92
Kansas	371			156			88
Missouri	369			155			88
Silesia		482, 484					92
ore in Alabama					695		
Arizona	762				698		
Arkansas	672	476			701, 703		88
California	769				706		
Colorado	752				711, 714		
Connecticut	674				716		
Dakota					717		
Idaho	770				723		
Illinois	679				727		
Indiana	681				730		
Iowa	682				731		88
Kansas				156			88
Maine					737, 739		
Maryland	365				741		
Massachusetts	695				745		
Minnesota	698				749		
Missouri	701			155	752		88
Montana	755				755		
Nebraska	703						
New Hampshire	706				760		
New Jersey	360, 708						
New Mexico	757				764		88
New York	713				769		
North Carolina	717				774		
Pennsylvania	361, 725	476			784		
Tennessee	367, 732				791		
Utah					796		
Vermont	738				799		
Virginia	365, 742				802		
Wisconsin	746			156	807		88
oxide. (See Zinc white.)							
prices	351	478	275	158	116	94	91

INDEX.

	Page.		Page.
Abrasive materials, summary	3	Arizona gold	49
Africa copper	73	lead	80
Agate	446	contents of ores mined in ..	80
Alabama brown hematite	40	limestone	373, 378
coal	146, 172	sandstone	374, 378
mines, labor at	173	silver	49
gold	49	Arkansas antimony	141
iron ore	24	coal	147-174
iron-ore beds, geological formation of	28	analysis of	176
limestone	373, 377	market	175
metallic paint	510	transportation facilities ..	175
mineral waters	522	granite	374-378
ocher	508	limestone	373-378
petroleum	363	lithographic stone	519
pig iron	10, 11, 17	manganese	127-130
rank of, as producer of iron ore	35, 36	mineral waters	522
red hematite	39	sandstone	374-378
sandstone	374, 377	slate	376-379
silver	49	syenite	379
Alaska gold	49	zinc	88
silver	49	Arrow points	446
Algiers copper	73	Asbestos	514
Allouez copper mine	59	imports	514
Aluminum, by R. L. Packard	110	production 1880 to 1890 ..	6
alloys	115	Ash bed copper mine	59
and copper, strength of alloys	115	Asia copper	74
comparison with iron and copper	112	Asphaltum, by E. W. Parker	477
imports	118	imports	479
production 1880 to 1890	6	production 1880 to 1890 ..	6
steel, physical tests of	117	summary	4
summary	2	Trinidad	478
Amazonstone	446	Atlantic copper mine	59
Amethyst	446	Australia copper	74
Analysis of manganese from Corral Hollow, California	131	manganese	130
Anthracite	242, 446	Austria copper	73
distribution of	246	and Hungary pig iron	21
Antimony	141	steel	21
Arkansas	141	Austria zinc	92
imports	142	Average monthly prices iron and steel in United States	15
Montana	141	yearly prices iron and steel ..	15
Nevada	141	Ball clay	441
production, 1880 to 1890	6	Baltimore, Md., coal receipts	155
summary	2	shipments	155
Apatite, Canadian	451	Barium sulphate, imports	513
Argentine Republic copper	73	Barytes	513
Arizona copper	60	in Illinois	513
mines, report of progress	65	Missouri	513
cost of mining copper in	57	North Carolina	513
		Virginia	513
		summary	4
		Batesville district, Arkansas, manganese	130
		Belgium iron ore	22

	Page		Page
Belgium pig iron	21	Buffalo cement	461, 462
steel	21	coal clearances	158
Bellaire, Ohio, cement	461	receipts	158
Bellefontaine, Ohio, cement	462	trade	157
Belt copper mine	59	Buhrstones	456
Beryl	446	imports	456
Bessemer steel, Great Britain	16	Building stone, production, 1880 to 1890	6
ingots, production	14	summary	3
production compared		California, bituminous rock	477
with that of Great		borax	494
Britain	16	chromic iron ore	137
rails, production	14	coal	147, 178
Bichromate of potash, prices of	140	trade	168
Birkinbine, John, on iron ores	23	copper	60
Bituminous limestone pavements	480	gold	49
rock in California	477	granite	374, 380
Kentucky	478	gypsum	465, 466
Utah	478	lead contents of ores mined	
Bluestone	376	in	80
in New Jersey	376, 411	limestone	373, 383
New York	370, 412	manganese	127
Pennsylvania	376, 420	marble	375, 382
uses	377	metallic paint	510
Bolivia copper	73	mineral waters	522
Borax, by Charles G. Yale	494	nails	13
Borax in California	494	petroleum	292, 340, 346
Nevada	494	Portland cement	462
process of manufacture	502	rolled steel	12
production 1880 to 1890	6	salt	482, 489
reduction works	502	sandstone	374, 382
summary	4	silver	49
Bosnia manganese	130	slate	376, 382
Boston, Massachusetts, coal trade	153	tin	120
Brass exports	69	Calumet and Hecla copper mine	59, 60
imports	66	Canada iron ore	22
Bromine	493	pig iron	21
in Michigan	493	steel	21
Ohio	493	Canadian apatite	454
Pennsylvania	493	Cape of Good Hope copper	73
West Virginia	493	Carbonate ore in Alabama	33, 42
production, 1880 to 1890	6	Kentucky	40
summary	4	Maryland	42
Brown hematite in Alabama	40	New York	40
Colorado	40	Ohio	42
Connecticut	40	Pennsylvania	42
Delaware	40	West Virginia	42
Georgia	40	Casualties in Illinois coal mines	205
Idaho	40	Caswell, E. A., on prices of lead	83
Kentucky	40	Catlimite	416
Maine	40	Caucasus manganese	130
Maryland	40	Cement	461
Massachusetts	40	imports	462
Michigan	40	in Akron	461
Missouri	40	Buffalo	461
Montana	40	Fort Scott, Kansas	461
New Mexico	40	Georgia	461
New York	40	La Salle	461
Oregon	40	Lehigh Valley	461
Pennsylvania	40	Louisville	461
Tennessee	40	Mankato	461
Texas	40	Milwaukee	461
Utah	40	Missouri	461
Virginia	40	New Mexico	461
Washington	40	Ohio	461
West Virginia	40	Onondaga county, New York	461
Wisconsin	40	Rosendale	461

	Page.		Page.
Cement in Schoharie county, New York	461	Coal in Arkansas analysis of	176
South Riverside, California	463	transportation of	175
Texas	461	California	147, 178
Utica, Illinois	461	Colorado	147, 179
Virginia	461	Dakota	147
production, 1880 to 1890	6	Georgia	146, 194
Central copper mine	59	Idaho	147
Chateaugay iron ore	35	Illinois	195
Chattanooga cement	461	Indiana	205, 348
Chicago coal prices	162	Indian Territory	147, 207
shipments	160	analysis of	210
trade	160	Iowa	147, 215
Chile copper	73	Kansas	147, 217
manganese	130	Kentucky	146, 219
China clay	441	Maryland	221
imports	443	Michigan	146, 226
Chlorastrolite	446	Missouri	147, 226
Chromate and bichromate of potash		Montana	147, 228
imports	139	Nebraska	147, 231
Chromic acid imports	139	New Mexico	147, 231
iron ore	137	North Carolina	234
foreign sources	140	North Dakota	234
imports	139	Ohio	235
prices	140	Oregon	240
production, 1880 to		Pennsylvania	241
1890	6	Tennessee	146
summary	2	Texas	147, 271
Chrysoberyl	446	Utah	147, 272
Cincinnati coal receipts	165	Virginia	272
trade	165	Washington	147, 275
Clay imports	443	West Virginia	277
Cleveland, Ohio, coal trade	159	Wyoming	147, 280
Cliff copper mine	59	markets, Arkansas	175
Coal, by E. W. Parker	145	measures of Indian Territory	212
Coal and lignite, production of, in Ger-		mines, Alabama, labor at	173
many	21	Illinois, classification of	197
Coal, anthracite	242	mining, wages in	169
annual shipments	244	prices	162
average prices at Port		receipts, Baltimore	155
Richmond	154	Boston	153
distribution of	246	Buffalo	158
lake shipments from		Cincinnati, Ohio	165
Buffalo	157	Duluth, Minnesota	164
production 1880 to 1890	6	Kansas City, Missouri	166
bituminous, Illinois	146	Milwaukee	163
Indiana	146	Toledo, Ohio	160
Kentucky	146	shipments by Ohio river	156
Maryland	146	from Chicago	160
North Carolina	146	Erie	158
Ohio	146	Milwaukee	163
Oregon	147	summary	3
Pennsylvania	146, 252	trade at Baltimore	155
production, 1880 to		Boston	153
1890	6	Buffalo	157
Virginia	146	California	168
West Virginia	146	Chicago	160
clearances at Buffalo	158	Cincinnati	165
exports	149	Cleveland	159
fields of the United States	145	Duluth	164
foreign shipments of, from Balti-		Erie	158
more	155	Kansas City	166
imports	149	Louisville	165
at San Francisco	168	Milwaukee	162
Coal in Alabama	146, 172	Minneapolis	164
Arkansas	147, 174	Mobile	167

	Page.		Page.
Coal trade at New Orleans	167	Copper, by C. Kirchhoff	56
New York City	151	Adventure mine	59
Philadelphia	153	Allouez mine	59
Pittsburg	156	Ashbed mine	59
St. Louis	166	Atlantic mine	59
St. Paul	164	Belt mine	59
Superior, Wisconsin	164	British exports of	74
Toledo	159	Calumet and Hecla mine	59
Coal trade review	150	Central mine	59
Cobalt	124	Cliff mine	59
Cobalt oxide	124	Conglomerate mine	59
imports	125	exports	67, 68
production, 1880 to 1890	6	Evergreen Bluff mine	59
summary	2	exports from Great Britain	77
Colorado, analysis of manganiferous		Falls copper mine	59
iron ores in	133	Franklin mine	59
Colorado and New Mexico anthracite		Grand Portage mine	59
coal	146	Hancock mine	59
brown hematite	40	Huron mine	59
cement	462	imports	60, 61
coal	179	imports into France	77
copper	60	London	76
copper mines, report of prog-		Swansea	76
ress	60	in Argentine Republic	73
granite	374, 383	Africa	73, 74
gypsum	465, 466	Algiers	73
iron ore	24	Arizona	60
lead	80	Asia	74
contents of ores mined		Australa	74
in	80	Austria	73
limestone	373, 384	Bolivia	73
manganese	127, 131, 132	California	60
manganiferous ores in	133	Cape of Good Hope	73
marble	385	Chile	73
metallic paint	510	Corocoro	73
mineral waters	522	England, values of	73
nails	13	France	77
oher	508	Germany	73
oil fields, capital invested in	339	Great Britain	73
wages paid in producing	339	Hungary	73
petroleum	292, 332	Idaho	60
petroleum wells completed	337	Italy	73
pig iron	10, 17	Japan	74
rank of, as producer of iron		Maine	60
ore	35, 36	Middle States	60
red hematite	39	Missouri	60
sandstone	374, 384	Montana	60
analysis of	384	Nevada	60
silver	49	New Hampshire	60
statistics of oil tanks	338	New Mexico	60
Columbus cement	462	New Quebrada	73
Columnar section of the coal measures		Norway	73
of Indian Territory	212	Peru	73
Comparison of iron and steel activity		Russia	73
in 1890 and 1891	16	South America	73
Conglomerate copper mine	59	Southern States	60
Connecticut brown hematite	40	Spain and Portugal	73
granite	374, 385	Sweden	73
iron ore	24	Utah	60
limestone	373, 385	Venezuela	73
analysis of	386	Vermont	60
mineral waters	522	Wyoming	60
pig iron	10, 17	Isle Royal mine	59
rank of, as producer of iron		Kearsarge mine	59
ore	35, 36	Lake Superior	59, 60
sandstone	374, 385	Lake Superior, prices	71

	Page.		Page.
Copper, Mansfeld mine	73	Delaware and Maryland, rolled steel ..	12
markets	69	Delaware brown hematite	40
Mason and Barry mine	72	granite	374, 386
Mass mine	59	Denver, cement	462
mining, cost of	56, 57	Diamonds	446
Minnesota mine	59	Diopside	446
National mine	59	Duluth, coal trade	164
Nonesuch mine	59	receipts	164
Ogimamine	59	Earthenware exports	444
Osceola mine	59	imports	443
Peninsula mine	59	Eastern and Southern States, spelter ..	89
Pewabic mine	59	Eastern States, zinc	88
Phoenix mine	59	Emerald	446
Poderosa mine	73	Emery	457
Portuguesa mine	73	imports	457
prices	70	Erie, coal trade	158
production, 1880 to 1890	6	Europe, copper production of	74
production in Africa	74	England, values of copper in	73
Asla	74	Evergreen Bluff copper mine	59
Australia	74	Exports brass	69
Europe	74	British copper	74
North America	74	coal	149
South America	74	copper	67, 68
Quincy mine	59	copper from Great Britain	77
Ridge mine	59	earthenware	444
Rio Tinto mine	73	lead	86
St. Clair mine	59	lime	462
Sevilla mine	73	mineral waters	523
Sheldon and Columbia mine	59	nickel	126
Smelters	60	platinum	144
Summary	1	quicksilver	108
Tamarack mine	59	salt	490
Tharsis mine	73	stoneware	444
Wolverine mine	59	tin	122, 123
Cornwall iron ore	35	zinc	90
ore hills, Pennsylvania, pro-		Ferro-manganese, production of	11
duction of iron ore at	28, 29	Feldspar, production 1880 to 1890	6
Corocoro copper	73	Fertilizers, South Carolina	449
Corundum	457	Fibrous talc	476
production 1880 to 1890	6	production 1880 to 1890	6
Cost of copper at the Atlantic mine per		Fire-bricks imports	444
ton of rock treated	60	Fire-clay	441
Crown Point iron ore	35	Flint, Florida	386
Crucible steel ingots, production	14	production 1880 to 1890	6
Crude barytes, production 1880 to 1890 ..	6	Florida flint	386
Cryolite	473	limestone	373, 386
Cryolite imports	473	phosphates	451
Cuba manganese	130	sandstone	374, 386
Cumberland cement	461	Fluorspar	468
coal field, shipments from	225	metallurgical uses for	468
Cummings, U., on natural cement	461	production 1880 to 1890	6
Cut nails in California	13	summary	4
Colorado	13	Foreign copper producers	73
Illinois	13	tin mines	121
Indiana	13	Fort Scott cement	461
Kentucky	13	Fossil coral	446
Massachusetts	13	France and Spain zinc	92
Missouri	13	copper	77
New Jersey	13	iron ore	22
Ohio	13	manganese	130
Pennsylvania	13	pig iron	21
Virginia	13	steel	21
West Virginia	13	Franklin copper mine	59, 60
Wisconsin	13	Garnet	446
Dakota, Portland cement	462	Geology of the Choctaw coal field	298
Day, William C., on stone	373	Georgia brown hematite	40

	Page.		Page.
Georgia cement	461	Granite in Missouri.....	374, 405
coal	194	Montana	378, 408
bituminous	146	Nevada	374, 409
gold	49	New Hampshire	374, 409
granite	374, 386	New Jersey	374, 410
iron ore	24	New York	374, 411
industry	32	North Carolina	374, 414
brimstone	373, 388	Oregon	374, 418
manganese	127, 133	Pennsylvania	374, 418
marble	375, 387	Rhode Island	374, 427
analysis of	387	South Carolina	374, 428
mineral waters	522	South Dakota	374, 428
ocher	508	Texas	374, 431
pig iron	10, 11, 17	Utah	374, 432
rank of, as producer of iron ore	35, 36	Vermont	374, 433
red hematite	39	Virginia	374, 435
sandstone	374, 388	Washington	374, 437
silver	49	West Virginia	438
slate	376, 388	Wisconsin	374
Germany and Luxemburg iron ore	22	uses	374
pig iron	21	Graphite	507
steel	21	imports	507
Germany, coal and lignite	21	production, 1880 to 1890	6
copper	73	summary	5
pig iron	20	Great Britain—	
Gogebic iron-ore district	35	annual production of coal	20
Gold and silver, by William Kent	48	Bessemer steel	16
mines, wages paid	50	copper	73
summary	1	imports of copper into	75
world's production	52	iron ore	22
in Alabama	49	manganese	130
Alaska	49	pig iron	11, 18, 21
Arizona	49	steel	21
California	49	zinc	91
Colorado	49	Greece, manganese	130
Georgia	49	Grindstones	458
Idaho	49	imports	458
Maryland	49	production, 1880 to 1890	6
Michigan	49	summary	3
Montana	49	Ground feldspar	441
Nevada	49	Ground flint	441
New Mexico	49	Guano	451
North Carolina	49	Gypsum	465, 466
Oregon	49	imports	467
South Carolina	49	in California	465, 466
South Dakota	49	Colorado	465, 466
Texas	49	Iowa	465, 466
Utah	49	Kansas	465, 466
Virginia	49	Michigan	465, 466
Washington	49	New York	465, 466
Wyoming	49	Ohio	465, 466
production 1880 to 1890	6	South Dakota	465, 466
quartz, production 1880 to 1890	6	Utah	465, 466
Grand Portage copper mine	59	Virginia	465, 466
Granite	374	Wyoming	465, 466
in Arkansas	374, 378	production, 1880 to 1890	6
California	374, 380	summary	4
Colorado	374, 383	Hagerstown cement	461
Connecticut	374, 385	Hancock copper mine	59
Delaware	374, 386	cement	461
Georgia	374, 386	Hematite, red, production by States	39
Maine	374, 396	Hiddenite	446
Maryland	374, 398	Holland manganese	130
Massachusetts	374, 400	Hornblende in quartz	446
Minnesota	371, 404	Hungary copper	73

	Page.		Page.
Huron copper mine.....	59, 60	Imports, asbestos.....	514
Hydraulic cement—		asphaltum.....	479
Akron, New York.....	461	barium sulphate.....	513
Bellaire, Ohio.....	461	brass.....	66
Buffalo, New York.....	461	British copper.....	74
Chattanooga, Tennessee.....	461	buhrstones.....	456
Cumberland, Maryland.....	461	cement.....	462
Fort Scott, Missouri.....	461	china.....	443
Georgia.....	461	chromate and bichromate of	
Hagerstown, Maryland.....	461	potash.....	139
Hancock, Maryland.....	461	chrome ore.....	139
Illinois.....	461	chromic acid.....	139
Indiana.....	461	clay.....	443
Kansas.....	461	coal.....	149
Kansas City, Missouri.....	461	cobalt oxide.....	125
Kentucky.....	461	copper.....	60, 61
La Salle, Illinois.....	461	from United States in	
Mankato, Minnesota.....	461	England and France.....	76
Maryland.....	461	into Liverpool, Swan-	
Milwaukee, Wisconsin.....	461	sea, and London.....	76
Minnesota.....	461	into France.....	77
Missouri.....	461	Great Britain.....	75
New Lisbon, Ohio.....	461	cryolite.....	473
New York.....	461	earthenware.....	443
Onondago county, New York.....	461	emery.....	457
Pennsylvania.....	461	firebrick.....	414
Salt Lake City, Utah.....	461	graphite.....	507
Schoharie county, New York.....	461	grindstones.....	458
Tennessee.....	461	gypsum.....	467
Ulster county, New York.....	461	iron ore into Baltimore.....	44
Utah.....	461	Boston.....	44
Utica, Illinois.....	461	Buffalo Creek,	
Virginia.....	461	New York.....	44
West Virginia.....	461	Chicago.....	44
Wisconsin.....	461	Cuyahoga Co.....	44
Idaho, brown hematite.....	40	Detroit.....	44
copper.....	60	Perth Amboy.....	44
gold.....	49	Oswego.....	44
lead.....	80	Pensacola.....	44
limestone.....	373	Philadelphia.....	44
marble.....	375, 388	Pittsburg.....	44
sandstone.....	374, 388	Puget Sound.....	44
silver.....	49	San Diego.....	44
Illinois, barytes.....	513	San Francisco.....	44
bituminous coal.....	146	St. Louis.....	44
coal.....	195	Vermont dis-	
mines, casualties in.....	205	trict.....	44
classification of.....	197	lead.....	86
employés in.....	201	litharge.....	511
number of operat-		lithographic stone.....	520
ing days in.....	202	manganese.....	129
hydraulic cement.....	461	marble.....	375
limestone.....	373, 388	mercurial preparations.....	101
analysis of.....	390	mica.....	475
mineral waters.....	522	mineral waters.....	522
nails.....	13	wax.....	481
natural gas.....	367	nickel.....	126
petroleum.....	292, 353	ocher.....	509
pig iron.....	10, 17	Paris white.....	512
rolled steel.....	12	phosphates.....	450
salt.....	482	platinum.....	144
sandstone.....	374, 390	quicksilver.....	101
spelter.....	89	vermilion.....	101
steel rails.....	13	red lead.....	511
Imports, aluminum.....	118	salt.....	489
antimony.....	142	sulphur.....	515

	Page.		Page.
Imports, talc	476	Iron ore imports from Brazil	40
terra alba	512	British Colum-	
tin	122	bia	43
whetstones	460	Cuba	43
white lead	511	England	43
whiting	512	France	43
zinc	90	Germany	43
oxide	90	Greece	43
Indiana cement	461, 462	Italy	43
coal	205, 348	Labrador	43
bituminous	146	Manitoba	43
limestone	373, 390	Mexico	40
analysis of	392	Newfoundland	43
mineral waters	522	Northwest Ter-	
nails	13	ritory	43
natural gas	367	Ontario	43
petroleum	292	Portugal	43
well record	349	Quebec	43
pig iron	10, 17	Spain	43
rank of, as producer of iron		Turkey in Asia	43
ore	35, 36	in Alabama	24
rolled steel	12	Austria and Hungary	22
salt	482	Belgium	22
sandstone	374, 393	Canada	22
Indian red	510	Colorado	24
Indian Territory coal, analysis of	210	Connecticut	24
bituminous	147	Cornwall	35
Infusorial earth	459	France	22
production 1880 to		Georgia	24
1890	6	Germany and Luxumburg	22
Infusorial earth summary	5	Gogebic district	35
Iowa, coal	215	Great Britain	22
bituminous	147	Italy	22
gypsum	465, 466	Kentucky	24, 34
limestone	373, 393	Lake Champlain region	30, 35
mineral waters	522	Lake Superior region	35
sandstone	374, 394	Maine	24
zinc	88	Maryland	24, 34
Iron and steel	10	Marquette district	35
average monthly prices		Massachusetts	24
of	15	Menominee district	35
yearly prices of	15	Michigan	24
Industries of the United		Minnesota	24
States, by James M.		Missouri	24, 35
Swank	10	Montana	24
summary	1	New Jersey	24, 35
vessels built in the		New Mexico	24
United States	14	New York	24, 35
ore, by John Birkinbine	23	North Carolina	24, 34
and coal, the world's produc-		Ohio	24
tion of	22	Oregon	24
beds of Alabama, geological		Pennsylvania	24
formation of	28	Russia	22
carbonate, in Ohio	33	Spain	22
comparative production	35	Sweden	22
composition of, from Iron		Tennessee	24
Mountain, Missouri	47	Texas	24
districts, total production of	34	Utah	24
foreign receipts of	45	Vermilion district	35
from Wisconsin mines	31	Virginia	24
Great Britain's exports of	19	West Virginia	24, 34
imports	43	Wisconsin	24
from Africa	43	industry in Alabama	:7
from Cornwall Ore Hills,		Georgia	32
Pennsylvania	28	Michigan	26

	Page.		Page.
Iron ore industry in Minnesota	31	Lake Superior copper	60
Missouri	33	iron-ore region	35
New Jersey	32	Land plaster, Michigan	467
New York	29	La Salle, Illinois, cement	461
Ohio	33	Lawrence county, Pennsylvania, ce- ment	462
Pennsylvania	28	Lead, by C. Kirchhoff	78
Tennessee	32	contents in Arizona ores	80
Virginia	31	California ores	80
Wisconsin	30	Colorado ores	80
principal uses	23	Idaho ores	80
production by States	21, 26, 35, 36	Montana ores	80
of, at the Cornwall ore hills, Penn- sylvania	29	Nevada ores	80
shipments from Michigan mines	27	New Mexico ores	80
rails, production	14	ores mined in the Western States and Territories	80
rolled, production of compared with rolled steel	13	South Dakota ores	80
trade	16	Utah ores	80
Isle Royale copper mine	59	desilverizers, etc	60
Italy copper	73	exports	86
iron ore	22	highest and lowest prices of	83
manganese	130	imports	86
pig iron	21	in Arizona	80
steel	21	Colorado	80
Japan copper	74	Idaho	80
Jasper	446	Montana	80
Kansas bituminous coal	147	Nevada	80
coal	217	New Mexico	80
gypsum	465, 466	Utah	80
limestone	373, 394	market	82
analysis	394	prices of	83
mineral waters	522	production, 1880 to 1890	6
natural gas	367	summary	1
petroleum	292, 355	Lehigh Valley, Pennsylvania, cement	461
well record	358	Lime, exports	462
salt	482, 488	production, 1880 to 1890	6
sandstone	374, 395	Limestone	373
spelter	89	for iron flux, production, 1880 to 1890	6
zinc	88	in Alabama	373, 377
Kaolin	441	Arizona	373, 378
Kearsarge copper mine	59, 60	Arkansas	373, 378
Kentucky bituminous coal	146	California	373, 383
rock	478	analyses of	383
brown hematite	40	Colorado	373, 384
cement	461	Connecticut	373, 385, 386
coal	219	Florida	373, 386
iron ore	24, 34	Georgia	373, 388
limestone	373, 395	Idaho	373
mineral waters	522	Illinois	373, 388
nails	13	Indiana	373, 390
petroleum	292, 350	analysis of	392
petroleum well record	352	Iowa	373, 393
pig iron	10, 11, 17	Kansas	373, 394
rank of, as producer of iron ore	35, 36	analysis of	394
salt	482	Kentucky	373, 395
sandstone	374, 396	Maine	373, 398
Kent, William, on gold and silver	48	Maryland	373, 399
Kirchhoff, C., on copper	56	Massachusetts	373, 403
lead	78	Michigan	373, 403
zinc	88	Minnesota	373, 404
Kunz, George F., on precious stones	445	Missouri	406
Lake Champlain iron-ore region	30, 35	analysis of	373, 406
Lake copper, prices of	71	Montana	373, 408
		Nebraska	373, 408

	Page.		Page.
Limestone in New Jersey	373	Manganese, in New Brunswick	130
analysis of	410	New Zealand	130
New Mexico	373, 411	North Carolina	127, 134
New York	373, 413	Nova Scotia	130
Ohio	373, 417	Portugal	130
analysis of	417	Quebec	130
Oregon	373, 418	South Carolina	127, 134
Pennsylvania	373, 420	Spain	130
analyses of	421, 422	Sweden	130
423, 424		Tennessee	127, 135
Rhode Island	373, 428	Turkey	130
South Carolina	373, 428	Vermont	127, 135
South Dakota	373, 429	Virginia	127, 135
Tennessee	373, 429	ores	127, 129
Texas	373, 431	production, 1880 to 1890	6
analysis of	432	summary	2
Utah	373, 432	world's production of	129
Vermont	373, 433	Manganiferous iron ores	128, 129
Virginia	373, 436	ores, in Colorado	133
Washington	373	silver ores	128, 129
West Virginia	373, 437, 439	zinc ores	129
Wisconsin	373	Mankato, Minnesota, cement	461
analysis of	439	Mansfeld copper mine	73
Wyoming	373, 404	Marble	375
uses	374	imports	375
Litharge, imports	511	in California	375, 382
Lithographic stone	519	Colorado	385
Arkansas	519	Georgia	375, 387
imports	520	analysis of	387
Texas	519	Idaho	375, 388
Virginia	519	Maryland	375, 400
production, 1880 to		Massachusetts	375, 403
1890	6	Michigan	403
Louisiana salt	482, 488	New York	375, 414
Louisville, Ky., cement	461	North Carolina	415
coal trade	165	Oregon	418
Maine, brown hematite	40	Pennsylvania	375, 427
copper	60	South Carolina	428
granite	374, 396	Tennessee	375, 429
iron ore	24	Utah	432
limestone	373, 398	Vermont	375, 433
mineral waters	522	Virginia	375, 436
pig iron	10, 17	Wyoming	440
rank of, as producer of iron ore	35, 36	Marls	451
slate	376, 398	production, 1880 to 1890	6
Manganese, by Joseph D. Weeks	127	summary	4
from Corral Hollow, Cali-		Marquette iron-ore district	35
fornia, analysis of	131	Maryland brown hematite	40
imports	129	cement	461
in Arkansas	127, 130	coal	146, 221
Australia	130	gold	49
Batesville district, Ar-		granite	374, 398
kansas	130	iron ore	24, 34
Bosnia	130	limestone	373, 399
California	127, 131	marble	375, 400
Caucasus	130	mineral waters	522
Chile	130	ocher	508
Colorado	127, 132	pig iron	10, 11, 17
Cuba	130	rank of as producer of iron	
France	130	ore	35, 36
Georgia	127-133	sandstone	374, 399
Great Britain	130	serpentine, analysis of	400
Greece	130	silver	49
Holland	130	slate	376, 399
Italy	130	Mason and Barry copper mine	73
Nevada	127, 134	Massachusetts copper mine	59

	Page.		Page.
Massachusetts brown hematite	40	Mineral waters, imports	522
granite	374, 400	in Alabama	522
iron ore	24	Arkansas	522
limestone	373, 403	California	522
marble	375, 403	Colorado	522
mineral waters	522	Connecticut	522
nails	13	Georgia	522
ocher	508	Illinois	522
pig iron	10, 17	Indiana	522
rank of, as producer of		Iowa	522
iron ore	35, 36	Kansas	522
red granite, analysis of	401	Kentucky	522
sandstone	374, 402	Maine	522
analysis of	402	Maryland	522
Menominee iron-ore district	35	Massachusetts	522
Mercurial preparations, imports	101	Michigan	522
Merton, Henry R., & Co., on spelter		Mississippi	522
production of Europe	92	Missouri	522
Metallic paint	509	Nebraska	522
in Alabama	510	New Hampshire	522
California	510	New Mexico	522
Colorado	510	New York	522
New Jersey	510	North Carolina	522
New York	510	Ohio	522
Ohio	510	Oregon	522
Pennsylvania	510	Pennsylvania	522
Tennessee	510	Rhode Island	522
Vermont	510	South Carolina	522
Wisconsin	510	Tennessee	522
Mica	474	Texas	522
imports	475	Vermont	522
North Carolina	474	Virginia	522
production, 1880 to 1890	6	Washington	522
summary	4	West Virginia	522
Michigan bromine	493	Wisconsin	522
brown hematite	40	summary	4
coal	146, 226	Mineral wax imports	481
gold	49	Mining, cost of copper	56
gypsum	465, 466	Minneapolis coal trade	164
iron ore	24	Minnesota cement	461
land plaster	467	copper mine	59
limestone	373, 403	granite	374, 404
marble	403	iron ore	24
mineral waters	522	industry in	31
natural gas	367	limestone	373, 404
pig iron	10, 17	pig iron	17
rank of as producer of iron		pipestone	404
ore	35, 36	rank of, as producer of iron	
red hematite	39	ore	35, 36
salt	482, 483	red hematite	39
grades of	484	sandstone	374, 404
sandstone	374, 403	Mississippi mineral waters	522
silver	49	Missouri and Michigan rolled steel	12
slate	376, 403	barytes	513
Middle States, copper	60	bituminous coal	147
Millstones, production, 1880 to 1890	6	brown hematite	40
summary	3	cement	461
Milwaukee, cement	461	coal	226
coal receipts	163	copper	60
shipments	163	granite	374, 405
trade	162	iron ore	24, 35
Mineral paints	508	industry in	33
production, 1880 to 1890	6	limestone	373, 406
summary	4	mineral waters	522
Mineral waters, by A. C. Peale	521	nails	13
exports	523	ocher	508

	Page.		Page.
Missouri onyx.....	408	New Hampshire copper.....	60
petroleum.....	292, 361, 363	granite.....	374, 409
pig iron.....	10, 17	mineral waters.....	522
rank of, as producer of iron ore.....	35, 36	sandstone.....	374, 409
red hematite.....	39	New Jersey bluestone.....	370, 411
sandstone.....	374, 405	granite.....	374, 410
spelter.....	89	iron ore.....	24, 35
zinc.....	88	industry in.....	32
Mobile, coal trade at.....	187	limestone.....	373, 410
Montana antimony.....	141	analysis of.....	410
brown hematite.....	40	metallic paint.....	510
coal.....	228	nails.....	13
copper.....	60	pig iron.....	10, 17
cost of mining copper in.....	57	rank of, as producer of iron ore.....	35, 36
gold.....	49	red hematite.....	39
granite.....	374, 408	rolled steel.....	12
iron ore.....	24	sandstone.....	374, 410
lead.....	80	slate.....	376, 410
contents of ores mined in.....	80	New Lisbon, hydraulic cement.....	461
limestone.....	373, 403	New Mexico brown hematite.....	40
rank of, as producer of iron ore.....	35, 36	cement.....	461
red hematite.....	39	coal.....	231
sandstone.....	374, 408	copper.....	60
silver.....	49	gold.....	49
Moss agate.....	446	iron ore.....	24
Nails, cut and wire.....	13	lead.....	80
National copper mine.....	59	contents of ores mined in.....	80
Natural gas, by Joseph D. Weeks.....	366	limestone.....	373, 411
amount and value of coal displaced by.....	367	mineral waters.....	522
capital invested in.....	369	petroleum.....	365
consumption.....	366	ricolite.....	411
in Illinois.....	367	rank of, as producer of iron ore.....	35, 36
Indiana.....	367	red hematite.....	39
Kansas.....	367	sandstone.....	374, 411
Michigan.....	367	silver.....	49
New York.....	367	zinc.....	88
Ohio.....	367	New Orleans coal trade.....	167
Pennsylvania.....	367	New York mineral waters.....	522
pipe lines.....	368	New Quebrada copper.....	73
production 1880 to 1890.....	6	New York bluestone.....	376, 412
summary.....	3	brown hematite.....	40
value.....	366	cement.....	461, 462
West Virginia.....	367	coal trade.....	151
Nebraska coal.....	147, 231	granite.....	374, 411
limestone.....	373, 408	gypsum.....	465, 466
mineral waters.....	522	iron ore.....	24, 29
Nevada antimony.....	141	limestone.....	373, 413
borax.....	494	marble.....	375, 414
copper.....	60	metallic paint.....	510
gold.....	49	natural gas.....	367
granite.....	374, 409	ocher.....	508
lead.....	80	pig iron.....	10, 17
contents of ores mined in.....	80	rank of, as producer of iron ore.....	35, 36
manganese.....	127, 134	red hematite.....	39
salt.....	482	rolled steel.....	12
sandstone.....	374, 409	salt.....	482, 484
silver.....	49	sandstone.....	374, 411
New Brunswick manganese.....	130	slate.....	376, 414
Newbury, Prof. Spencer, B., on hy- draulic cement.....	461	New Zealand manganese.....	130
New England anthracite coal.....	146	Nickel.....	124
rolled steel.....	12	and cobalt.....	124

	Page.		Page.
Nickel, Canada	125	Onondaga county, New York cement ..	462
census statistics	125	salt district	485
exports	126	Onyx, Missouri	408
imports	126	Open-hearth steel ingots	14
Lancaster Gap, Pennsylvania	124	rails	14
Lovelocks, Nevada	124	Oregon brown hematite	40
Mine La Motte, Missouri	124	coal	147, 240
production, 1880 to 1890	6	gold	49
summary	2	granite	374, 418
Nonesuch copper mine	59	iron ore	24
North America, copper production of ..	74	limestone	373, 418
North Carolina barytes	513	marble	418
coal	146, 234	mineral waters	522
gold	49	pig iron	10, 17
granite	374, 414	rank of, as producer of iron ore ..	35, 36
iron ore	24, 34	red hematite	39
manganese	127, 134	sandstone	374, 418
marble	415	silver	49
mica	474	Osceola copper mine	59, 60
mineral waters	522	Ozocerite	481
pig iron	10, 11, 17	production 1880 to 1890	6
rank of, as producer of iron ore ..	35, 36	summary	4
sandstone	374, 415	Pacific Coast Borax Company	5
silver	49	Packard, R. L., on aluminum	110
slate	415	Parker, E. W., on asphaltum	477
North Dakota coal	234	on coal	145
Norway copper	73	Paris white	512
Novaculite, production, 1880 to 1890 ..	6	imports	512
Nova Scotia manganese	130	Peale, A. C., on mineral waters	521
Ocher	508	Peninsula copper mine	59
imports	508	Pennsylvania and New York petroleum ..	292, 312
in Alabama	508	Pennsylvania and New York petro-	314
Colorado	508	leum, capital invested	314
Georgia	508	Pennsylvania and New York petro-	313
Maryland	508	leum, value of wells	313
Massachusetts	508	Pennsylvania anthracite coal	146
Missouri	508	bituminous coal	146, 252
New York	508	bluestone	376, 420
Pennsylvania	508	bromine	493
Vermont	508	brown hematite	40
Virginia	508	cement	461, 462
Wisconsin	508	coal	241
Ogima copper mine	59	granite	374, 418
Ohio bituminous coal	146	iron ore	24
bromine	493	industry in	28
cement	461	limestone	373, 420
coal	235	limestone, analysis of	421, 422,
gypsum	465, 466	423, 424	375, 427
iron ore	24, 33	marble	510
limestone	373, 417	metallic paint	522
analysis	417	mineral waters	13
metallic paint	510	nails	367
mineral waters	522	natural gas	508
nails	13	ocher	295
natural gas	367	petroleum	10, 17
petroleum	292, 318	pig iron	35, 36
pig iron	10, 17	rank of, as producer of iron	39
Portland cement	462	ore	12
rank of as producer of iron ore ..	35, 36	red hematite	374, 419
rolled steel	12	rolled steel	419
salt	482, 488	sandstone	376, 424
sandstone	374, 415	analysis of	13
analysis	416	slate	14
wire nails	14	steel rails	14
Oilstones	460	wire nails	73
and whetstones, summary	3	Peru, copper	488
		Petite Anse salt mine	488

	Page.		Page.
Petroleum, by Joseph D. Weeks	287	Pig iron in Illinois	10, 17
Alabama	363	Indiana	10, 17
American, character and composition of	288	Italy	21
crude, stocks of	293	Kentucky	10, 11, 17
total product	290	Maine	10, 17
in California	290, 292, 340	Maryland	10, 11, 17
Colorado	292, 332	Massachusetts	10, 17
Illinois	292, 353	Michigan	10, 17
Indiana	292	Minnesota	17
Kansas	292	Missouri	10, 17
Kentucky	292, 350	New Jersey	10, 17
Lima district, Ohio	289, 323	New York	10, 17
Macksburg (Ohio) dis- trict	326	North Carolina	10, 11, 17
Mecca-Belden district	328	Ohio	10, 17
Missouri	292, 361	Oregon	10, 17
New Mexico	365	Pennsylvania	10, 17
Ohio	292, 318	Russia	21
wages	322	Spain	21
Pennsylvania	295	Sweden	21
Pennsylvania and New York	292	Tennessee	10, 11, 17
Pennsylvania and New York, shipments	303	Texas	11, 17
Tennessee	292	Virginia	10, 11, 17
Texas	292, 359	Washington	10, 17
West Virginia	292, 329	West Virginia	10, 11, 17
Wyoming	363	Wisconsin	10, 17
Ohio, capital invested	321	production 1880 to 1890	6
pipe-line certificate, prices	300	in Southern States	11
pipe-lines, Pennsylvania and New York	299	Pipestone	446
production, 1880 to 1890	6	Minnesota	404
statistics in California	346	Pittsburg, Pennsylvania, coal trade at	156
stocks	304	Platinum	143
Ohio	319	exports	144
West Virginia	329	imports	144
summary	3	prices	144
wages	294, 314	production 1880 to 1890	6
well record	311	Russia	143
Ohio	321	Ural mountains	143
Pewabic copper mine	59	Poderosa copper mines	73
Phenacite	446	Poland zinc	92
Philadelphia coal trade	153	Port Henry iron ore	35
Phoenix copper mine	59	Portland cement, Bellefontaine	462
Phosphates imports	450	Buffalo	461
in Florida	451	California	462
South Carolina	450	Colorado	462
production 1880 to 1890	6	Columbus	462
summary	4	Dakota	462
Pig iron	21	Denver	462
and steel, world's production of	21	Indiana	462
annual production of, for 81 years	10	Lawrence County, Pennsylvania	462
in Alabama	10, 11, 17	Lehigh County, Pennsylvania	462
Austria and Hungary	21	New York	462
Belgium	21	Ohio	462
Canada	21	Onondaga County,	461
Colorado	10, 17	New York	461
Connecticut	10, 17	Pennsylvania	462
France	21	prices	462
Georgia	10, 11, 17	San Diego	462
Germany and Luxembourg	20, 21	South Bend	461
Great Britain	18, 21	South Riverside, Cal- ifornia, tests of	464
		Yankton, Dak	462
		Portugal manganese	130
		Portuguesa copper mine	73

	Page.		Page.
Potomac River, cement.....	461	Red hematite in New Mexico.....	39
Potter, Prof. W. B., on analyses of Iron Mountain iron ore.....	46	New York.....	39
Potter's clay, production 1880 to 1890....	6	Oregon.....	39
Pottery.....	441	Pennsylvania.....	39
Precious stones, by George F. Kunz.....	445	Tennessee.....	39
production 1880 to 1890.....	6	Utah.....	39
summary.....	3	Virginia.....	39
Priceite, analysis of.....	505	Wisconsin.....	39
Prices quicksilver.....	104	production by States.....	39
Pyrites.....	518	Red lead imports.....	511
production 1880 to 1890.....	6	Rhine district and Belgium zinc.....	92
summary.....	4	Ricolite, New Mexico.....	411
Quartz.....	446	Ridge copper mine.....	59
Quebec manganese.....	130	Rhode Island granite.....	374, 427
Quicksilver.....	94	limestone.....	373-423
Abbott mine.....	95	mineral waters.....	522
Altoona mine.....	95	sandstone.....	374, 428
Bradford mine.....	95	Rio Tinto copper mine.....	73
California mine.....	95	Rolled iron in Alabama.....	12
Census statistics of.....	102	California.....	12
Cloverdale mine.....	95	Colorado.....	12
establishments, location and number of.....	102	Connecticut.....	12
expenditures in the produc- tion of.....	104	Delaware.....	12
exports.....	108	Georgia.....	12
exports and shipments of.....	100	Illinois.....	12
Great Eastern mine.....	95	Indiana.....	12
Great Western mine.....	95	Iowa.....	12
Guadalupe mine.....	95	Kentucky.....	12
highest and lowest prices of imports.....	101	Maine.....	12
movement of.....	100	Maryland.....	12
Napa Consolidated mine.....	95	Massachusetts.....	12
New Almaden mine.....	95	Michigan.....	12
New Idria mine.....	95	Minnesota.....	12
Oakland mine.....	95	Missouri.....	12
Oceanic mine.....	95	New Hampshire.....	12
Pope Valley mine.....	95	New Jersey.....	12
power used in mining and reduction.....	107	New York.....	12
prices.....	98, 104	Ohio.....	12
production 1880 to 1890.....	6	Pennsylvania.....	12
Redington mine.....	95	Rhode Island.....	12
St. John mine.....	95	Tennessee.....	12
Sulphur Bank mine.....	95	Virginia.....	12
summary.....	2	West Virginia.....	12
Sunderland mine.....	95	Wisconsin.....	12
value of production.....	107	Wyoming.....	12
vermilion imports.....	101	production.....	14
wages.....	104	steel in California.....	12
world's annual production.....	101	Delaware and Maryland.....	12
yield of from California ores.....	103	Illinois.....	12
Quincy copper mine.....	59	Indiana.....	12
Raborg, William A., on salt.....	482	Missouri and Michigan.....	12
Reaction in the American iron trade....	16	New England States.....	12
Red granite, Massachusetts, analysis of.....	401	New Jersey.....	12
Red hematite in Alabama.....	39	New York.....	12
Colorado.....	39	Ohio.....	12
Georgia.....	39	Pennsylvania.....	12
Michigan.....	39	Virginia.....	12
Minnesota.....	39	West Virginia and Ken- tucky.....	12
Missouri.....	39	Wisconsin.....	12
Montana.....	39	production.....	12, 14
New Jersey.....	39	Rosendale, New York, cement.....	461
		Russia copper.....	73
		iron ore.....	22
		pig iron.....	21
		platinum.....	143

	Page.		Page.
Russia steel.....	21	Sandstone in Oregon.....	374, 418
Rutile.....	446	Pennsylvania.....	374, 419
production, 1880 to 1890.....	6	analysis of.....	419
Sagenitic rutile.....	416	Rhode Island.....	374, 428
St. Clair copper mine.....	59	South Dakota.....	374, 429
St. Louis, coal receipts.....	166	Tennessee.....	374, 429
trade.....	166	Texas.....	374, 431
St. Paul, coal trade.....	164	Utah.....	43
Salt, by William A. Raborg.....	482	Vermont.....	374, 433
exports.....	490	Virginia.....	374, 436
by countries.....	592	Washington.....	374, 437
imports.....	489	West Virginia.....	374, 437
by customs districts.....	491	Wisconsin.....	374, 438
in California.....	482, 489	Wyoming.....	374, 440
Illinois.....	482	uses.....	374, 375
Indiana.....	482	San Francisco, coal imports at.....	168
Kansas.....	482, 488	Sapphire gems.....	446
Kentucky.....	482	Schoharie county, New York, cement.....	461
Louisiana.....	482, 488	Searles borax marsh.....	498
Michigan.....	482, 483	Serpentine, Maryland, analysis of.....	400
Nevada.....	482	Sevilla copper mine.....	73
New York.....	482, 484	Sheldon and Columbia copper mines.....	59
Ohio.....	482, 488	Silesia zinc.....	92
Onondaga district, New York.....	485	Silicified wood.....	446
Tennessee.....	482	Silver in Alabama.....	49
Utah.....	482, 489	Alaska.....	49
Virginia.....	482	Arizona.....	49
Warsaw district, New York.....	486	California.....	49
West Virginia.....	482, 488	Colorado.....	49
production, 1880 to 1890.....	6	Georgia.....	49
summary.....	4	Idaho.....	49
Salt Lake City cement.....	461	Maryland.....	49
Sand Coulee, Montana, coal, analyses of.....	229	Michigan.....	49
San Diego cement.....	462	Montana.....	49
Sandstone.....	374	Nevada.....	49
in Alabama.....	374, 377	New Mexico.....	49
Arizona.....	374, 378	North Carolina.....	49
Arkansas.....	374, 378	Oregon.....	49
California.....	374, 382	South Dakota.....	49
Colorado, analysis of.....	384	Texas.....	49
Colorado.....	374, 384	Utah.....	49
Connecticut.....	374, 385	Virginia.....	49
Florida.....	374, 386	Washington.....	49
Georgia.....	374, 388	Wyoming.....	49
Idaho.....	374, 388	Silver-producing mines, relative im- portance of.....	49
Illinois.....	374, 390	production 1880 to 1890.....	6
Indiana.....	393	Slate.....	376
Iowa.....	374, 391	ground as a pigment, production 1880 to 1890.....	6
Kansas.....	374, 395	in Arkansas.....	376, 379
Kentucky.....	374, 396	California.....	376, 382
Maryland.....	374, 399	Georgia.....	376, 388
Massachusetts.....	374, 402	Maine.....	376, 398
analysis of.....	402	Maryland.....	376, 399
Michigan.....	374, 403	Michigan.....	376, 403
Minnesota.....	374, 404	New Jersey.....	376, 410
Missouri.....	374, 405	New York.....	376, 414
Montana.....	374, 408	North Carolina.....	415
Nevada.....	374, 409	Pennsylvania.....	376, 424
New Hampshire.....	374, 409	Tennessee.....	430
New Jersey.....	374, 410	Utah.....	376, 432
New Mexico.....	374, 411	Vermont.....	376, 434
New York.....	374, 411	Virginia.....	376, 436
North Carolina.....	374, 415	uses.....	376
Ohio.....	374, 415	Smoky quartz.....	446
analysis.....	416		

	Page.		Page.
Soapstone	476	Sulphur production, 1880 to 1890	6
production 1880 to 1890	6	summary	4
summary	4	Summary	1
South America copper	73, 74	Superior, Wisconsin, coal trade at	161
South Bend, Indiana, cement	462	Swank, James M., on the iron and steel industries of the United States in 1889, 1890, and 1891	10
South Carolina gold	49	Sweden, copper	73
fertilizers	449	iron ore	22
granite	374, 428	manganese	130
limestone	373, 428	pig iron	21
manganese	127, 134	steel	21
marble	428	Syenite, Arkansas	379
phosphate rock	450	Talc, imports	476
silver	49	Tamarack copper mine	59
South Dakota, gold	49	Tennessee bituminous coal	146
granite	374, 428	brown hematite	40
gypsum	465, 466	cement	461
lead contents of ores mined in	80	iron ore	24, 32
limestone	373, 429	limestone	373, 429
recent developments of tin in	120	manganese	127, 135
sandstone	374, 429	marble	375, 429
silver	49	metallic paint	510
tin	120	petroleum	362
Southern States, copper	60	pig iron	10, 11, 17
production of pig iron in	11	mineral waters	522
zinc	88	rank of, as producer of iron ore	35, 36
Spain and Portugal copper	73	red hematite	39
iron ore	22	salt	482
manganese	130	sandstone	374, 429
pig iron	21	slate	430
steel	21	Terra alba imports	512
Spelter, census statistics of	88	Texas bituminous coal	147
in Eastern and Southern States	89	brown hematite	40
Illinois	89	cement	461
Kansas	89	coal	271
Missouri	89	gold	49
production	89	granite	374, 431
of Europe	92	iron ore	24
stocks of	89	limestone	373, 431
Spiegeleisen production	11, 14	analysis of	433
Steel	21	lithographic stone	519
in Austria and Hungary	21	mineral waters	522
Belgium	21	petroleum	292, 359
Canada	21	well record	360
France	21	pig iron	10, 11, 17
Germany and Luxemburg	21	rank of, as producer of iron ore	35, 36
Great Britain	21	sandstone	374, 431
Italy	21	silver	49
Russia	21	Tharsis copper mine	73
Spain	21	Thomsonite	446
Sweden	21	Tin	119
crude, production of	11	California	120
rails, Illinois	13	exports	122, 123
Pennsylvania	13	imports	122
production	13	mines, foreign	121
rolled, production of, compared with rolled iron	13	prices	123
Stone, by William C. Day	373	recent developments	120
Stoneware exports	444	in California	121
Structural materials, summary	3	South Dakota	120
Sulphur	515	Virginia	121
imports	515	South Dakota	120
		Temescal mine	119
		Virginia	120

	Page.		Page
Tin, world's supply of.....	121	Virginia, rank of, as a producer of iron	
Toledo, coal receipts at.....	160	ore.....	35, 36
trade at.....	159	recent developments of tin in.....	123
Topaz.....	446	red hematite.....	38
Tourmaline.....	446	rolled steel.....	12
Trilobites.....	446	salt.....	482
Trinidad asphaltum.....	478	sandstone.....	374, 436
pavements of.....	479	silver.....	49
Tully, N. Y., depth of salt wells at.....	487	slate.....	376, 433
rock salt and brine supply.....	486	tin.....	120
Turkey, manganese.....	130	Wages in coal mining.....	169
Turquoise.....	446	Warsaw salt district, New York.....	486
Ulster county, New York, cement.....	461	Washington, brown hematite.....	40
Utah, bituminous rock.....	478	coal.....	147, 275
brown hematite.....	40	gold.....	49
cement.....	461	granite.....	374, 437
coal.....	272	limestone.....	373
copper.....	60	mineral waters.....	522
gold.....	49	pig iron.....	10, 17
granite.....	374, 432	sandstone.....	374, 437
gypsum.....	465, 466	silver.....	49
iron ore.....	24	Weeks, Joseph D., on manganese.....	127
lead.....	80	natural gas.....	366
contents of ores mined in.....	80	petroleum.....	287
limestone.....	373, 432	Western Carolina Mica Company.....	474
marble.....	432	West Virginia, bromine.....	493
rank of, as producer of iron ore.....	35, 36	brown hematite.....	40
red hematite.....	39	cement.....	46
salt.....	482, 489	coal.....	146, 277
sandstone.....	374, 432	iron ore.....	24, 34
silver.....	49	limestone.....	373, 437, 439
slate.....	376, 432	mineral waters.....	522
Utica, Illinois, cement.....	461	nails.....	13
Venezuela copper.....	73	natural gas.....	367
Venetian red.....	510	petroleum.....	292, 329
Vermilion iron ore district.....	35	pig iron.....	10, 11, 17
Vermont copper.....	60	rank of, as producer of	
granite.....	374, 433	iron ore.....	35, 36
limestone.....	373, 433	salt.....	482, 488
manganese.....	127, 135	sandstone.....	374, 437
marble.....	375, 433	Whetstones.....	460
metallic paint.....	510	imports.....	460
mineral waters.....	522	White lead, imports.....	511
rank of, as producer of iron		Whiting.....	512
ore.....	35, 36	imports.....	512
sandstone.....	374, 433	Wire nails, Ohio.....	14
slate.....	376, 434	Pennsylvania.....	14
brown hematite.....	40	production.....	14
Virginia barytes.....	513	Wisconsin, brown hematite.....	40
bituminous coal.....	146	cement.....	461
cement.....	461	granite.....	438
coal.....	272	iron ore industry in.....	30
gold.....	49	iron ore mines, production	
granite.....	374, 435	from.....	31
gypsum.....	465, 466	limestone.....	373
iron ore.....	24	analysis of.....	439
iron ore, industry in.....	31	metallic paint.....	510
limestone.....	373, 436	mineral waters.....	522
lithographic stone.....	522	nails.....	13
manganese.....	127, 135	ocher.....	508
marble.....	375, 436	pig iron.....	10, 17
mineral waters.....	522	rank of, as producer of iron	
nails.....	13	ore.....	35, 36
ocher.....	508	red hematite.....	39
pig iron.....	10, 11, 17	rolled steel.....	12

	Page.		Page.
Wisconsin sandstone.....	374, 438	Yankton, South Dakota, Portland ce- ment.....	462
zinc.....	88	Zinc, by C. Kirchhoff.....	88
Wolverine copper mine.....	59	Arkansas.....	88
World's annual production, quicksilver	101	Austria.....	92
production of gold and silver		Eastern States.....	88
value of.....	54	exports.....	90
iron ore and		France and Spain.....	92
coal.....	22	Great Britain.....	92
manganese.....	129	imports.....	90
pig iron and		Iowa.....	88
steel.....	21	Kansas.....	88
supply of tin.....	121	Missouri.....	88
Wyoming, coal.....	280	New Mexico.....	88
copper.....	60	oxide, census statistics of.....	88
gold.....	49	imports.....	90
gypsum.....	465, 466	Poland.....	92
limestone.....	340, 373	prices of.....	91
marble.....	440	production, 1880 to 1890.....	6
petroleum.....	363	Rhine district and Belgium.....	92
wells, depth and		Silesia.....	92
flow of.....	364	Southern States.....	88
sandstone.....	374, 440	summary.....	1
silver.....	49	Wisconsin.....	88
Yale, Charles G., on borax.....	494	Zinc, white, production, 1880 to 1890.....	6









