


GEM STONES

The visual guide to more
than 130 gemstone varieties



Chrome Diopside

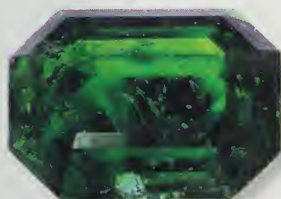

Amber



Kornerupine



Fluorite



Onyx



Pyrope




Precious Opal



Amethyst

Cally Hall



WITHDRAWN

No longer the property of the
Boston Public Library.
Sale of this material benefits the Library.



Digitized by the Internet Archive
in 2015

EYEWITNESS  HANDBOOKS

GEMSTONES





EYEWITNESS  HANDBOOKS

GEMSTONES

CALLY HALL



Photography by
HARRY TAYLOR
(Natural History Museum)

Editorial Consultant
JOSEPH J. PETERS





A DK PUBLISHING BOOK

Project Editor Alison Edmonds
Project Art Editor Alison Shackleton
Series Editor Jonathan Metcalf
Series Art Editor Spencer Holbrook
Production Controller Caroline Webber
U.S. Consultant Joseph J. Peters
U.S. Editor Charles A. Wills

First American Edition, 1994
6 8 10 9 7 5

Published in the United States by DK Publishing, Inc.
95 Madison Avenue, New York, NY 10016

Copyright © 1994 Dorling Kindersley Limited, London
Text copyright © 1994 Cally Hall

All rights reserved under International and Pan-American Copyright Conventions. No part of this publication may be reproduced, stored in a retrieval system, or transmitted in any form or by any means, electronic, photocopying, recording or otherwise, without the written permission of the copyright owners. Published in Great Britain by Dorling Kindersley Ltd. Distribution by Houghton Mifflin Company, Boston.

Library of Congress Cataloging-in-Publication Data

Hall, Caroline.

Gemstones / Caroline Hall.--1st American ed.

p. cm.-- (Eyewitness handbooks)

Includes index.

ISBN 1-56458-499-2 (hardcover): \$29.95 -- ISBN 1-56458-498-4 (flexibinding) \$17.95

1. Precious stones. 2. Gems. I. Title. II. Series

TS752.H218 1993

553.8--dc20

93-28348 CIP

Computer page makeup by Adam Moore

Text film output by The Right Type, Great Britain

Reproduced by Colourscan, Singapore

Printed and bound by Kyodo Printing Co., Singapore

CONTENTS

INTRODUCTION • 6

Author's Introduction 6

How this Book Works 9

What are Gemstones? 10

How Gemstones are Formed 12

Where Gemstones are Found 14

Physical Properties 16

Crystal Shapes 18

Optical Properties 20

Natural Inclusions 24

Faceting 26

Polishing, Carving, and Engraving 28

Gems Through the Ages 30

History and Folklore 32

Synthetic Gemstones 34

Imitation and Enhancement 36

Color Key 38



PRECIOUS METALS • 48



CUT STONES • 54

ORGANICS • 138

Table of Properties 150

Glossary 156

Index 158

Useful Addresses 160

Acknowledgments 160


AUTHOR'S INTRODUCTION

The mysterious appeal of gemstones, their exquisite colors and the play of light within them, would alone have made them precious to many, but their rarity, hardness, and durability have made them doubly valuable. The natural beauty, strength, and resilience of gems have inspired beliefs in their supernatural origins and magical powers, and stones that have survived the centuries have gathered a wealth of history and romance around them.

THERE ARE OVER 3,000 different minerals, but only about 50 are commonly used as gemstones. Others are cut for collectors of the unusual but are not suitable for wear because they are too soft and easily scratched. The number of minerals commonly used as gemstones constantly changes as new sources and varieties are found and fashions change. Over 130 gem species, including some exceptionally rare stones, are described in this book, illustrating the very wide range of naturally occurring gemstones.

WHAT IS A GEMSTONE?

To be regarded as a gemstone, a mineral (or occasionally an organic material) must be beautiful, most importantly in its color.

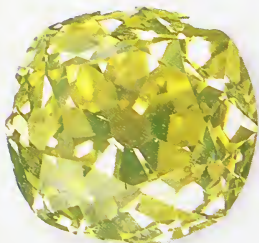

DIAMOND (BRILLIANT CUT)




STAR SAPPHIRE (CABOCHON)



RIVER PEARL
(UNCUT)



RUBY (STEP CUT)

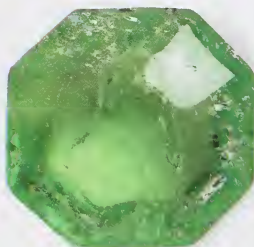

EMERALD
(OCTAGONAL CABOCHON)

FIVE MAJOR GEMSTONES

These five stones are the most highly prized. All except pearl have a particular cut that brings out their best qualities.




SORTING SAPPHIRES

Workers in Myanmar (Burma) sort through sapphires collected from river sediment. When cut, they epitomize the allure of gemstones.

A gemstone must also be durable – hard enough to survive constant use or handling without becoming scratched or damaged. Finally, it must be rare, because its very scarcity endows it with a greater market value.

THE SCIENCE OF GEMOLOGY

Gems are scientifically fascinating, too. Gemologists make a complete study of each stone they acquire, both as it is found in rocks and after it has been cut and polished. That is why the species entries in this book show the gem in its rough, natural state, perhaps still embedded in the host rock (or matrix),

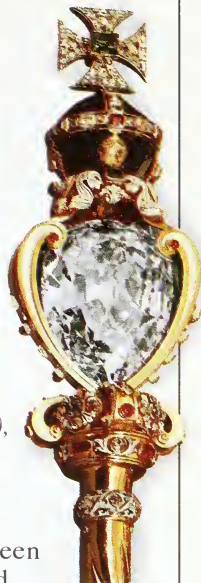

EMBLEMS OF POWER

The Cullinan I diamond (above), adorns the Royal Scepter of the British crown jewels (right).

as well as after it has been cut, polished, or carved. Many entries also feature a microphotograph that reveals the internal structure of the stone by magnifying it. In this world within a world the gemologist may turn detective, being able to distinguish between two similar species, or between a natural stone and a fake.

KINGS AND COMMONERS

Throughout the ages, gemstones have been seen as representations of wealth and power. Symbols of supremacy, from crowns to richly decorated robes, have traditionally been adorned with jewels. But



PRIVATE COLLECTION

The Mathews collection in London comprises 4 boxes of unmounted gems from all around the world (above), and a group of Colombian emeralds (right). The scope of this collection is unique, but many fine examples of cut and uncut gemstones are on public display in museums.



gemstones are not just for the wealthy or the scientifically minded: they can be appreciated by anyone, from the amateur gem-spotter to the enthusiast who enjoys their beauty and history. For this reason, the *Eyewitness Handbook of Gemstones* is not intended as a textbook but as a general introduction and an initial guide to identification.

COLLECTING GEMS

For many, the real satisfaction comes from actually owning gems. Most people cannot afford the more



MINING IN CAMBODIA

In many parts of the world, traditional methods and equipment are still employed for the collection of gemstones.

expensive stones, but anybody can collect a few minerals that, even if not gem quality, are still very attractive. You may even chance on a piece of jewelry in a local auction. No matter how modest your collection, it will give you hours of fascination and enjoyment.



A BOX OF JEWELS

In the 18th century, jeweled trinkets like this decorative box were very fashionable. A large citrine is in the center, surrounded by amethyst, agates, amazonite, garnet, and pearls.



FOSSICKING IN AUSTRALIA

Fossicking (foraging) for sapphires and opals is still possible in parts of Australia, as long as you first obtain a permit from the authorities. River beds and streams are the best locations.

HOW THIS BOOK WORKS

THIS BOOK is divided into three parts: precious metals, cut stones, and organics. Cut stones are arranged by crystal structure into seven groups (cubic, tetragonal, hexagonal, trigonal, orthorhombic,

monoclinic, and triclinic), but with a final section on amorphous gems. Within these sections, gem species are grouped with other species of a similar mineralogical type. The page below explains a typical entry.

crystal group to which gem belongs •

basic chemical composition of gem •

mean hardness of gem, measured on Mohs scale •

gem's common name, with mineral group in brackets (when appropriate)

gem's chief physical characteristics

where and how gem formed, and where it is found

additional information relevant to gem species or type

other color varieties and cuts shown to assist in identification

faceting styles and shapes popular for this gem

mean figure for specific gravity of gem


AMETHYST (QUARTZ)

Crystalline quartz in shades of purple, lilac, or mauve is called amethyst, a stone traditionally worn to guard against drunkenness and to instill a sober and serious mind. Amethyst is dichroic, showing a bluish or reddish purple tinge when viewed from different angles. Usually faceted as a mixed or step cut, amethyst has distinctive inclusions that look like tigerstripes, thumbprints, or feathers. Some amethyst is heat treated to change the color to yellow, producing citrine (see opposite). Crystals that are part citrine and part amethyst are called ametrine.

- **OCCURRENCE** Amethyst is found in alluvial deposits or in geodes. Some of the largest geodes containing amethyst are in Brazil. Amethyst from the Urals (Russia) has a reddish tinge; Canadian amethyst is violet. Other localities include Sri Lanka, India, Uruguay, Madagascar, the USA, Germany, Australia, Namibia, and Zambia.
- **REMARK** Poor quality material is often tumbled to make beads. If a stone is pale it may be set in a closed setting or have foil placed behind it to enhance the color. Amethyst has been imitated by glass and synthetic corundum.



TIE PIN
Amethyst jewelry was popular in the late 19th century. This handsome gold tie pin is adorned with an octagonal step-cut amethyst.



Characteristic tigerstripe inclusions are caused by parallel, liquid-filled canals.

• closeup photograph of inclusions in gem (if appropriate)

• example of jewelry or ornament included in some entries to illustrate use

• example of faceted gem, labeled with name of cut



OVAL MIXED CUT

color darkens toward tip of amethyst crystal

• annotation highlights key physical characteristics

• specimen of gem as it occurs naturally, often shown in host rock (matrix)



AMETHYST CRYSTAL SLICE

AMETHYST CRYSTALS ASSOCIATED WITH ROCK CRYSTAL



purple stone from Russia

polished, convex front

alternate colors due to twinning

HEXAGONAL MIXED CUT

slice cut perpendicular to length of crystal



Baguette



Bead



Mixed

SG 2.65

RI 1.54-1.55

DR 0.009

Luster Vitreous

• mean range of refractive values (singly refractive gems have one mean value only)

• mean value of birefracton (doubly refractive gems only)

• surface shine or "look" of gem

WHAT ARE GEMSTONES?

GEMSTONES are generally minerals that have been, or may be, fashioned to use for personal adornment. As a rule, they are beautiful, rare, and durable. Most are minerals: natural, inorganic materials with a fixed chemical composition and regular internal structure.

A few gems, like amber and pearl, come from plants or animals and are known as organics. Others, called synthetics, do not have a natural origin but are made in laboratories. Their physical properties are similar to those of natural gems, and they may be cut to imitate the real thing.

PRECIOUS METALS

The precious metals are gold, silver, and platinum. They are not true gemstones, but they are attractive and easily worked and have their own intrinsic value, often as settings for gems. Platinum is the rarest and the most valuable.





GOLD RING

GOLD NUGGET
(UNWORKED)

ORGANICS

Gem materials produced by living organisms are called organics. Their sources are as diverse as shellfish (which produce pearls), polyps (whose skeletal remains form coral), and the fossilized resin from trees (which makes amber). Ivory, jet, and shell are also organics. These materials are not stones and are not as durable as mineral gems. Instead of being faceted like mineral gems, they are usually polished or carved, or drilled and threaded as beads.



AMBER BEAD

AMBER BEAD

POLISHED STONE

Crystals may be rounded and polished naturally (like this emerald pebble, rolled in a stream) or ground mechanically.



NATURAL CRYSTAL

In its natural state, the mineral may be a prism, with clearly defined faces.




CUT STONES

Like the emerald shown here, almost all cut gems begin life in a crystalline form (see pp.18–19), embedded in a host rock known as the matrix. In this state, the stone is referred to as a rough. Many natural crystals are attractive enough to be displayed as they are. Others are faceted and polished to enhance their beauty (see pp.26–29), then set in a piece of jewelry or an ornament.

CABOCHON

A simple fashion for stones is to cut them en cabochon, producing a domed, highly polished surface.

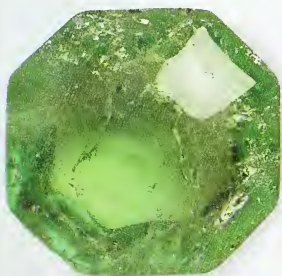

**IMITATION EMERALD
(GARNET ON GLASS)**



FACETED STONE

Most gemstones are cut to give them a number of flat surfaces, called facets. The facets absorb and reflect light, to magical effect.



IMITATIONS

Gemstones have been imitated throughout the ages. Many lesser stones have been used, as well as glass paste and other manmade materials. Composite stones, like the red garnet on green glass (above), are made of more than one piece.

JEWELRY

A piece of jewelry, usually one or several polished or faceted stones set in a mount of precious metal, is often the finished product.



SYNTHETICS

Manmade synthetic stones (see pp.34-35) are similar in chemical composition and optical properties to their natural equivalents. In the flux method, crystals are grown, then faceted (right).



**SYNTHETIC
CRYSTALS**




**SYNTHETIC
FACETED EMERALD**



HOW GEMSTONES ARE FORMED

GEMSTONES THAT HAVE a mineral origin are found in rocks or in gem gravels derived from these rocks. Rocks themselves are made up of one or more minerals and may be divided into three main types. The formation of these three types – igneous, sedimentary, or metamorphic – is a continuous process, described in terms of the rock cycle (shown right). Gem-quality minerals within these rocks may be easily accessible at the Earth's surface or lie buried deep beneath it. Others, separated from their host rock by erosion, are carried by rivers to lakes or the sea.

IGNEOUS ROCKS
form as molten rock solidifies, above or below ground. This erodes and is deposited as sediments.

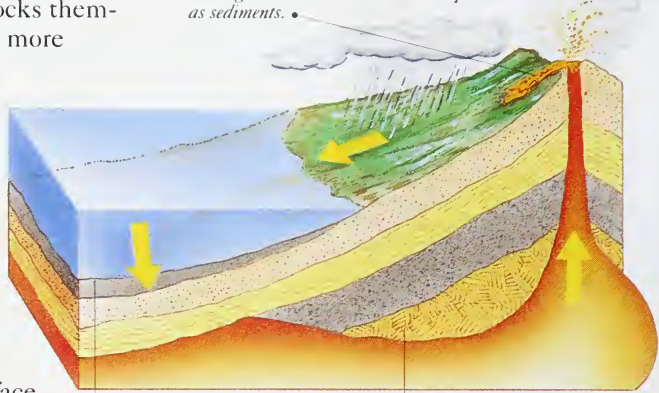

• **SEDIMENTARY ROCKS**
are formed from the accumulation and compression of eroded rock fragments. They may eventually be buried back below the surface.

• **METAMORPHIC ROCKS**
may be either sedimentary or igneous rocks whose character is fundamentally changed by heat and pressure.

peridot crystals form as lava cools



VOLCANIC BOMB FORMED FROM BASALTIC LAVA


IGNEOUS ROCKS

Igneous rocks have solidified from molten rock, which comes from deep beneath the Earth's surface. Some, called extrusive igneous rocks, are thrown out from volcanoes as lava, volcanic bombs (see left), or ash. Intrusive igneous rocks are those that solidify beneath the surface. Essentially, the slower a rock cools and solidifies, the larger the crystals – and therefore the gemstones – formed within it. Many large gemstone crystals form in a kind of intrusive igneous rock known as pegmatite.

METAMORPHIC ROCKS

Metamorphic rocks are either igneous or sedimentary rocks that have been changed by heat and pressure within the Earth to form new rocks with new minerals. As this happens, gemstones can grow within them. Garnets, for example, form in rocks called mica schists, which were once mudstones and clays. Marble, formed from limestone that has been subjected to intense pressure and high temperatures, may contain rubies.


kyanite and staurolite crystals form under high pressure

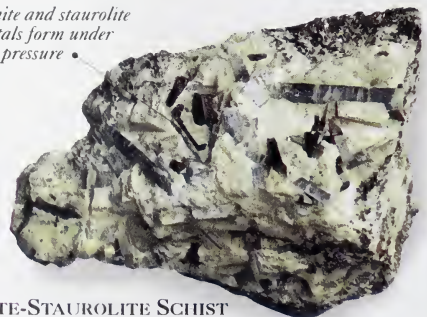

KYANITE-STAUROLITE SCHIST

SEDIMENTARY ROCKS

Sedimentary rocks are formed by the accumulation of rock fragments produced by weathering. In time, these fragments settle down and harden into rock once more. Sedimentary rocks are usually laid down in layers, and these may be shown as a feature in decorative stones. Most Australian opal occurs in sedimentary rocks; turquoise occurs mainly as veins in sedimentary rocks such as shale; halite and gypsum *are* sedimentary rocks.

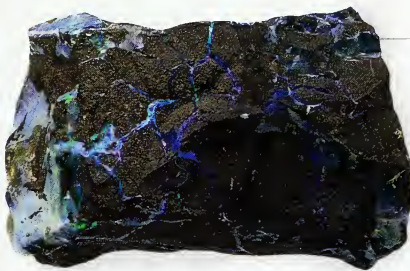

• blue-green opal in veins and fissures

AUSTRALIAN OPAL IN SEDIMENTARY ROCK

ORGANIC GEMS

Organic gems come from plants and animals. Natural pearls form around foreign bodies that have made their way inside the shells of marine or freshwater shellfish. Cultured pearls are produced artificially in large fisheries, many in the shallow waters off the shores of Japan and China. Shells treated as gems may come from animals as diverse as snails and turtles, living in the ocean, in fresh water, or on land. Coral is made up of the skeletons of tiny marine animals called coral polyps. Bone, or ivory from the teeth or tusks of mammals, may come from recently living animals or from fossils thousands of years old. Amber is fossilized tree resin, collected from soft sediments or the sea. Jet is fossilized wood, found in some sedimentary rocks.



TREASURE FROM THE SEA

The action of seawater has given this piece of amber (fossilized tree resin), washed up on a beach in Norfolk, England, a pitted and worn surface.



MODERN DIAMOND MINE IN BOTSWANA

Some gemstones are so valuable that large-scale mining, in which tons of rock may be extracted to collect tiny amounts of gemstone, are still viable.



ALLUVIAL MINING FOR SAPPHIRES

Small-scale mining with traditional methods and equipment, such as this in Sierra Leone, is still common in many countries.

WHERE GEMSTONES ARE FOUND

SOME GEM MINERALS, such as quartz and garnet, are found worldwide. Others, like diamonds and emeralds, are rarer, due to the more unusual geological conditions necessary for their formation. Even when a mineral is found worldwide, only a minute proportion may be of gem

quality. The main gem localities of the world are therefore those where gem-quality material occurs in sufficient quantity to make production economical.

DIAMONDS OF AFRICA

The kimberlite rocks of southern Africa are mined in a modern, large-scale way, producing vast quantities of diamonds for both industrial and gem use.



KEY TO SYMBOLS

DIAMOND	RUBY	SAPPHIRE	EMERALD
AQUAMARINE	CHRYSOBERYL	TOPAZ	TOURMALINE
PERIDOT	GARNET	PEARL	OPAL

TWELVE KEY GEMS

The 12 varieties of gemstone shown on this map represent some of the world's best-known gems. All are popular and highly prized, but some are far rarer than others.

PEARLS IN JAPAN

The shallow coastal waters of the Japanese islands offer ideal conditions for farming pearl oysters. Pearls are organic gems and therefore independent of geological conditions.



WORLD DISTRIBUTION

This map shows the main localities for 12 key gems. Each gem may of course occur in other places, but probably not in sufficient quantities to make its extraction economical. Some sites, although historically important, may now be worked out.



RUBIES IN MYANMAR

The rich mineral deposits of Mogok in Myanmar (Burma) have yielded some of the world's finest rubies, extracted by traditional methods. Sapphires are also mined here.

PHYSICAL PROPERTIES

THE PHYSICAL PROPERTIES of gemstones, their hardness, their specific gravity or density, and the way they break or “cleave,” depend on chemical bonding and the atomic structure within the stone. For example, diamond is

the hardest natural material known, and graphite is one of the softest, yet both are made of the same element, carbon. It is the way in which the carbon atoms are bonded together in diamond that gives it a greater hardness and resilience.



HARDNESS

One of the key qualities of a gemstone, hardness may be measured by how well a stone resists scratching. Every stone can be tested and classified using the Mohs scale of hardness (below), which gives every mineral a figure from one to ten. Intervals


between numbers on the scale are not equal, most obviously between nine and ten (see the Knoop scale, right). Hardness testing is destructive, however, and should be used on a gemstone only if other tests fail.

TESTERS

Each of these testing pencils is tipped with a Mohs mineral.

KNOOP SCALE

This scale shows the indentation caused by a diamond point when it meets the surface of a mineral. The 10 stages correspond to Mohs' points.



MOHS SCALE OF HARDNESS

The Mohs scale was devised by the German mineralogist Friedrich Mohs as a means of classifying the relative hardness of minerals. He took 10 common minerals and put them in order of “scratchability”: each one will scratch those below it on the scale but will be scratched by those above it.

MOHS' MINERALS




SPECIFIC GRAVITY

The specific gravity (SG) of a gem is an indication of its density. It is calculated by comparing the stone's weight with the weight of an equal volume of water. The greater a stone's specific gravity, the heavier it will feel. For example, a small cube of pyrite (SG 5.2) will feel heavier than a larger piece of fluorite with an SG of 3.18; and a ruby (SG 4.00) will feel heavier than an emerald (SG 2.71) of similar size.



FLUORITE

PYRITE



RELATIVE WEIGHTS
The smaller piece of pyrite (SG 5.2) feels heavier than the fluorite (SG 3.18), because it is more dense.

CLEAVAGE AND FRACTURE

Gemstones may break in two ways: they either cleave or they fracture. Which way they break depends on the internal atomic structure of the stone. Gems that cleave tend to break along planes of weak atomic bonding (cleavage planes). These planes are usually parallel, perpendicular, or diagonal to the crystal faces (as both planes and faces are directly related to the stone's atomic structure). A gemstone may have one or more directions of cleavage, which may be defined as perfect (almost perfectly smooth), distinct, or indistinct (examples are shown right). Gems with perfect cleavage include diamond, fluorite, spodumene, topaz, and calcite.

When a gemstone breaks along a surface that is *not* related to its internal atomic structure, it is said to fracture. Fracture surfaces are generally uneven, and each type has its own descriptive name, shown in the examples below and right.



BARITE

◁ PERFECT CLEAVAGE
Fragile barite has three directions of easy cleavage, giving smooth surfaces.




ALBITE

△ DISTINCT CLEAVAGE
Although not perfectly smooth, albite's cleavage surfaces can be clearly seen.



AQUAMARINE

◁ INDISTINCT CLEAVAGE
Cleavage direction is indistinct in aquamarine.

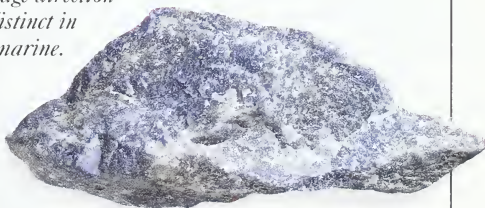

DUMORTIERITE


△ UNEVEN FRACTURE
An uneven fracture surface is typical of fine-grained or massive gems like dumortierite.

OBSIDIAN



△ CONCHOIDAL FRACTURE

The type most commonly found in gemstones, the name refers to the shell-like fracture surface.

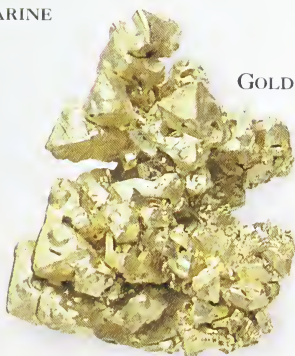

GOLD

△ HACKLY FRACTURE
Rough, uneven fracture surface is seen on the right of this gold specimen.

▷ SPLINTERY FRACTURE

Interlocking texture causes splintery fracture.



NEPHRITE

CRYSTAL SHAPES

some crystals form with a characteristic pyramidal end •

MOST MINERAL GEMSTONES are crystalline, with their atoms arranged in regular and symmetrical patterns, like a lattice; a few are amorphous, with no or only a weak crystal structure. Crystalline minerals may consist of a single crystal or of many in a group. Polycrystalline minerals are made up of many, usually small, crystals; in cryptocrystalline minerals, the crystals are too small to see without the aid of a microscope.

Crystalline minerals are made up of a number of flat surfaces called faces; the orientation of these faces defines the overall shape, which is known as the habit. Some minerals have a single, characteristic habit, such as pyramidal or prismatic; others may have several. A lump of crystalline mineral without a definite habit is called massive. Amorphous gemstones, like obsidian and tektites, have an irregular shape. Examples of common habits are shown right.

this natural glass cooled too fast for crystals to form




AMORPHOUS



PYRAMIDAL

rutile needles in this rock crystal have an acicular habit

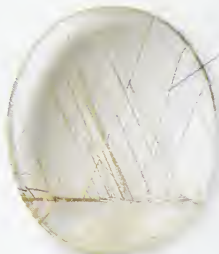

ACICULAR (NEEDLE-LIKE)

this crystal with six faces and flat ends is just one of many prismatic types •



PRISMATIC

TWINNING


Natural crystals are seldom perfect. Their growth is influenced by external factors such as temperature, pressure, space, and the medium in which they grow. One irregularity that may occur is known as twinning – when the internal structure of the crystal is repeated.

Twins grow together in a number of different ways.



TWINNED AMETHYST

• twinned crystals may show alternate colors

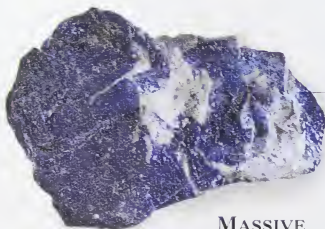

MASSIVE

• irregularly shaped mass with no apparent crystal habit

• crystal habit is branchlike



DENDRITIC

CRYSTAL SYSTEMS

Crystals are classified into seven different systems, according to the minimum symmetry of their faces. This depends on a crystal's axes of symmetry – imaginary lines (shown in black in the artworks on this page) around which a crystal may rotate and still show identical aspects. The number of times the same aspect may be seen – in one 360-degree rotation around an axis – defines that axis as twofold, threefold, etc., up to six.



PYRITE



CUBIC
Crystals in the cubic system (also known as the isometric system) have the highest symmetry, e.g., cubes, octahedra, and pentagonal dodecahedra. The minimum symmetry is four threefold axes.



HEXAGONAL/ TRIGONAL

These systems (thought by some to be one system) share the same axis of symmetry. Hexagonal crystals have six-fold symmetry; trigonal crystals threefold.



MILKY QUARTZ



TETRAGONAL

This system is defined by one fourfold axis. Typical crystal shapes include four-sided prisms and pyramids, trapezohedra, and eight-sided pyramids.



ZIRCON



MONOCLINIC

The monoclinic system has a minimum symmetry of one twofold axis. Prisms with basal pinacoids are common crystal shapes found in this system.



TOPAZ



ORTHORHOMBIC

The minimum symmetry of this system is three twofold axes. Typical crystal shapes are rhombic prisms and pyramids with basal pinacoids, and rhombic double pyramids.



BRAZILIANITE



TRICLINIC

Triclinic crystals have no axis of symmetry, so gemstones within this system are the least symmetrical.



AXINITE

OPTICAL PROPERTIES

COLOR IS THE MOST OBVIOUS visual feature of a gem, but in fact it is just one of many optical properties, all of which are dependent upon light. The individual crystalline structure of a gemstone (see pp.18–19) interacts with

light in a unique way and determines the optical properties of each gem species. Effects produced by light passing *through* a gem are described here; those produced by the *reflection* of light are described on pages 22–23.

WHAT MAKES COLOR?


The color of a gem depends largely on the way it absorbs light. White light is made up of the colors of the rainbow (spectral colors), and when it strikes a gem some spectral colors are “preferentially absorbed.” Those that are not absorbed pass through or are reflected back, giving the gem its color. Each gem in fact has a unique color “fingerprint” (known as its absorption spectrum), but this is visible only when viewed with a spectroscope (see p.38). To the naked eye, many gems look the same color.



SPLITTING LIGHT THROUGH A PRISM
The splitting of white light into its spectral colors is called dispersion. It gives gems their internal fire.

ALLOCHROMATIC GEMS

Allochromatic (“other-colored”) gems are colored by trace elements or other impurities that are not an essential part of their chemical composition. Corundum, for example, is colorless when pure, but impurities in it (usually a metal oxide) create the red stones we know as rubies, blue, green, and yellow sapphires, and orange-pink padparadscha. Allochromatic gems are often susceptible to color enhancement or change.

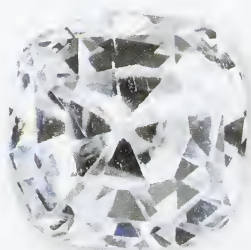

PURE CORUNDUM

RUBY (RED
CORUNDUM)




SAPPHIRE
(BLUE
CORUNDUM)

IDIOCHROMATIC GEMS

The color of idiochromatic (“self-colored”) gems comes from elements that are an essential part of their chemical composition. Thus idiochromatic gems generally have only one color or show only a narrow range of colors. Peridot, for example, is always green, because the color is derived from one of its essential constituents, iron.



PERIDOT



PERIDOT

MULTICOLORED GEMS

A crystal that consists of different-colored parts is called multicolored. It may be made up of two colors (bicolored), three (tricolored), or more. The color may be distributed unevenly within the crystal or in zones associated with growth. The many different varieties of tourmaline probably show the best examples of multicoloring, showing as many as 15 different colors or shades within a single crystal.



bicolored crystals can make attractive gemstones; junctions of color zones may be distinct (as here) or gradual

WATERMELON TOURMALINE


PLEOCHROIC GEMS

Gems that appear one color from one direction but that exhibit one or more other shades or colors if viewed from different directions are known as pleochroic. Amorphous or cubic stones show one color only; tetragonal, hexagonal, or trigonal stones show two colors (dichroic); orthorhombic, monoclinic, or triclinic stones may show three colors (trichroic).



IOLITE (BLUE ASPECT)

iolite is strongly pleochroic; colorless from one direction, blue when rotated 90 degrees

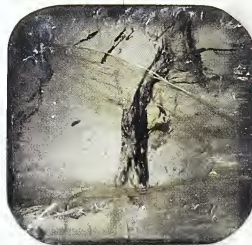

IOLITE (COLORLESS ASPECT)

REFRACTIVE INDEX (RI)

When a ray of light meets the surface of a polished gemstone, some light is reflected but most passes in. Because the gem has a different optical density from that of air, the light slows down and is bent from its original path (refracted). The amount of refraction within a gem is called its refractive index (RI) and, with the DR (below), can be used to help identify the stone.



calcite is highly birefractive, producing double images

CALCITE



SEEING DOUBLE
Zircon's back facets look doubled, due to strong double refraction (DR).

BIREFRACTION (DR)

When viewed through a refractometer (far right), cubic minerals like spinel are singly refractive, showing a single shadow edge; doubly refractive minerals like tourmaline split light rays in two, producing two shadow edges. The difference between the two gives the "birefractance" (DR).



SPINEL




TOURMALINE



LUSTER


The overall appearance of a gemstone, its luster, is determined by the way light is reflected from its surface. This is related to the degree of surface polish, which increases with the stone's hardness. Gemologists use a variety of terms to describe luster and its degree of intensity. "Splendent" means that the stone reflects light like a mirror; but if little light is reflected, the luster may be described as "earthy" or "dull." Stones with a luster comparable to diamond are described as "adamantine" and are the most desirable. Most transparent, faceted gems have a glasslike, "vitreous" luster; the precious metals have a metallic luster; and organic gems show a range, from "resinous" to "pearly" and "waxy." Some gemstone species vary in their luster: garnets, for example, range from the resinous hessonite garnet to the adamantine luster of demantoid garnet. Rough lazulite and howlite have a dull, earthy luster, which is vitreous after polishing.

hematite crystals, like pyrite and the precious metals, display metallic luster

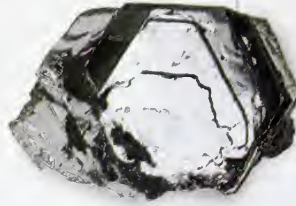

METALLIC LUSTER

hard and highly polished, the look of a diamond defines adamantine luster

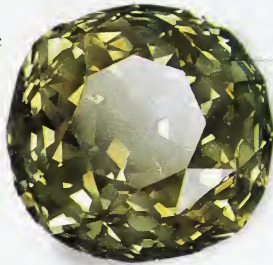


ADAMANTINE LUSTER

the glasslike luster of this ruby is the most common for cut stones



VITREOUS LUSTER

waxy luster is most commonly associated with turquoise

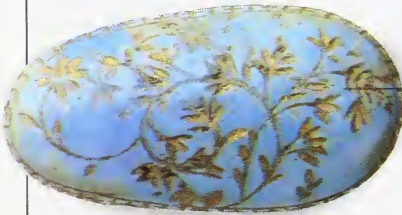

WAXY LUSTER

the greasy luster of this polished imperial jadeite is comparatively rare



GREASY LUSTER

organic gems, like this amber bead, may occur in a range of lusters, depending on the nature of the material



RESINOUS LUSTER

satin spar gypsum is commonly cited to describe silky luster



SILKY LUSTER

INTERFERENCE

Interference is an optical property caused by the reflection of light off structures within a gemstone. This internal reflection gives a play of color. In some stones it will produce the full range of the spectral colors; in others just one color may predominate. In opal, interference occurs because of the structure of the stone itself – spheres arranged in regular three-dimensional patterns. This produces the rainbow effect called iridescence, shown by a number of other gems such as hematite, labradorite, and iris quartz.


In moonstone feldspar, interference at the junctions of its internal layers (thin, alternating layers of different types of feldspar) produces a shimmering effect just below the surface of the stone, known as adularescence, opalescence, or a schiller (sheen).




moonstone feldspar exhibits a bluish white shimmer or sheen

ADULARESCEANCE


light reflected from labradorite gives a rainbow effect

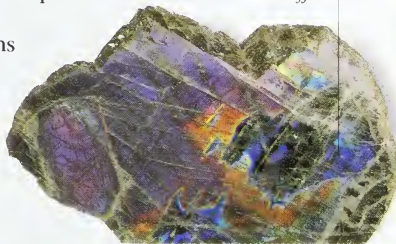

IRIDESCENCE



LIGHT LAYERS
Iridescence appears at layers within labradorite.

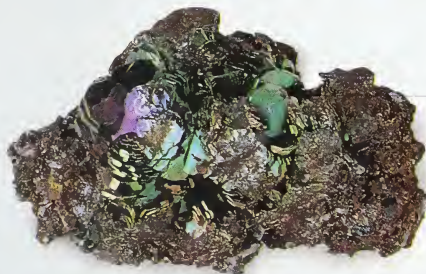

hematite shows a play of color

IRIDESCENCE



blue and green may predominate within opal

IRIDESCENCE

CAT'S-EYES AND STARS

When a gemstone is cut *en cabochon* (with a domed, polished surface), light reflecting from the stone's internal features, such as cavities or fibrous or needlelike inclusions (see pp.24–25), may create a cat's-eye effect (chatoyancy) or star stones (asterism). One set of parallel fibers gives rise to the cat's-eye effect; two sets of fibers produce a four-rayed star, three sets of fibers a six-rayed star, and so on.



SAPPHIRE STAR STONE

reflection from acicular (needle-like) rutile crystals gives a six-rayed star

parallel fibers within the stone produce the cat's-eye "flash"



CHRYSOBERYL CAT'S-EYE

NATURAL INCLUSIONS

INCLUSIONS ARE INTERNAL features of gems. They may be solids, liquids, or gases that the crystal enclosed as it grew, or cleavages, cracks, and fractures that filled (or partly filled) after the host material finished growing. Although

usually regarded as flaws, inclusions today are often seen as adding interest to a stone. They can also be invaluable in identifying a gem, because some are peculiar to a particular species, while others occur only in a particular locality.

FORMATION OF INCLUSIONS

Solid inclusions have usually formed before the host stone – the crystals of the host have grown around them and enclosed them. They may be distinct crystals or amorphous masses. Solids and liquid inclusions formed at the same time as the host are aligned to its atomic structure. For instance, the stars in star rubies and sapphires are caused by needlelike crystals of rutile, which formed parallel to the crystal faces at the same time as the host corundum crystals. Cavities filled or fractures healed after the formation of the host give inclusions that resemble feathers, insect wings, or fingerprints.



MICROSCOPE
A microscope that magnifies between 10 and 40 times is one of the most useful instruments for examining inclusions in gemstones.


• stone holder to allow viewing from any angle

DIAMOND WITH GARNET

Solid inclusions may be the same gem type as the host or different – like the garnet in this diamond.



PERIDOT "WATER LILY" (MAGNIFIED 30 TIMES)
Inclusions that look like water lily leaves are a typical feature of peridot from Arizona. Each inclusion consists of a central chromite crystal surrounded by liquid droplets.

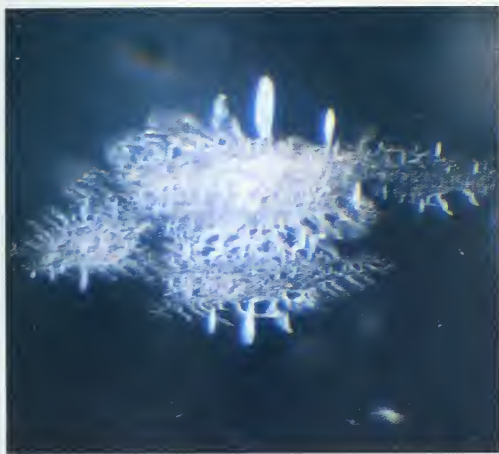

MOONSTONE "CENTIPEDES"

These insectlike inclusions (magnified 35 times) are a common feature of moonstone. In fact they are parallel cracks caused by strain.



INSECT IN AMBER

Insects are sometimes found trapped in amber, caught by the sticky resin as it was exuded. To create a natural effect, insects are sometimes added to imitation amber.




RUTILE NEEDLES

This carved rock crystal perfume bottle contains inclusions of needlelike rutile crystals. Tourmaline and gold are also found in rock crystal.



ALMANDINE GARNET (ABOVE)

Magnified 45 times, the gray patch on the left is a rounded apatite inclusion. The bright interference colors to the right are due to a zircon crystal.

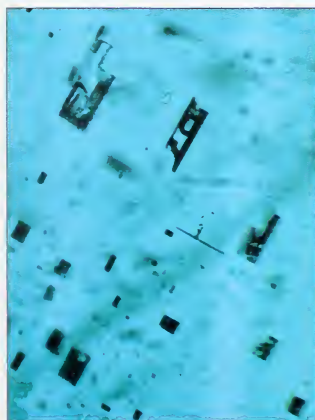

EMERALD (LEFT)

Rectangular cavities with tails (magnified 40 times) are sometimes found in natural Indian emeralds.

FACETING

THE MOST USUAL METHOD of fashioning a gem is to cut the surface into a number of flat faces, known as facets. This gives the stone its final shape, or cut. The gem cutter, or lapidary, tries to show the stone's best features, taking

into account its color, clarity, and weight. The lapidary may have to compromise to retain its weight and therefore value. The blue diagrams on the opposite page, which show the most popular cuts, are used throughout the book.

HOW A STONE IS FACETED

There are several stages in the cutting of a gemstone, each of which may be carried out by a different expert. In our example, a rough diamond crystal is fashioned into a brilliant cut. This is the most popular cut for this stone because


it maximizes the gem's naturally strong light dispersion. However, because each stone is a different shape, or has imperfections within it, or because retaining the weight is of paramount importance, the cut in its ideal form (the "make") may not be possible. Nevertheless, the essential aim is to make the diamond bright and sparkling, showing flashes of color called fire. To this end, the size, number, and angles of the facets are mathematically calculated. The rough crystal is sawn or cleaved to obtain a basic workable piece, then turned on a lathe against another diamond to give it a round shape. The facets are then cut and polished in stages, and the stone is given a final polish before mounting.



It maximizes the gem's naturally strong light dispersion. However, because each

• crown •

• bezel •

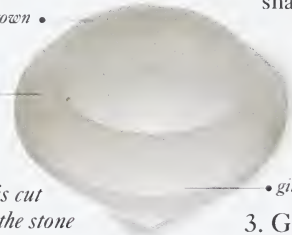

• girdle •

1. ROUGH

A rough diamond crystal is selected for faceting.

2. CUT

The top is cut off, and the stone rounded on a lathe by another diamond.

3. GRIND

The central flat table – is ground first, then the bezel facets.



• table •
• facet •



• bezel facet •

• upper girdle facet •

4. TOP AND BOTTOM

More facets are put on in groups and in sequence: the star facets and upper girdle facets on the crown; then the lower girdle facets and the culet on the pavilion (the underside).



• star facet •

5. FINISHING

A "brillianteer" then adds a further 24 facets above the girdle and 16 below.



6. MOUNTING

After a final polish, the stone is mounted in precious metal.

BRILLIANT CUTS

The brilliant cut is the most popular for diamonds and for many other stones, particularly colorless ones. It ensures that maximum light is reflected out through the front, giving brightness and fire.

Variations in the outline give the oval, the pear-shaped pendeloque, and the boat-shaped marquise or navette.



BRILLIANT-CUT
SAPPHIRE



ROUND



OVAL



RINGS OF FIRE


These gold rings from the house of Cartier are set with diamonds, sapphires, rubies, and emeralds, in a variety of cuts from brilliant to fancy.

STEP CUTS


The step cut (or trap cut) shows colored stones to advantage, having a rectangular or square table facet and girdle, with parallel rectangular facets. The corners of fragile gems may be removed, making octagonal stones – as, for example, in most emeralds.




OCTAGONAL STEP-CUT
SPESSARTINE




TABLE




SQUARE



OCTAGON



BAGUETTE



OVAL

MIXED CUTS

Mixed-cut stones are usually rounded in outline, with the crowns (above the girdle) cut as brilliants and the pavilions (below the girdle) step cut. Sapphires, rubies, and most transparent colored stones are cut in this style.



CUSHION



MIXED-CUT
PERIDOT



MIXED



FANCY-CUT
HELIODORE

FANCY CUTS

These have several possible outlines, such as triangular, kite-shaped, lozenge-shaped, pentagonal, or hexagonal. The cut may be used for rare gems, or to make the most of a flawed or irregularly shaped gem.



PENDELOQUE



MARQUISE



SCISSORS

POLISHING, CARVING, AND ENGRAVING

PRECIOUS METALS AND GEMS – usually massive, microcrystalline stones and organics – can be worked by polishing, carving, or engraving. Polishing is the oldest form of fashioning. Carving produces three-dimensional objects

by cutting them from a larger mass of material. Engraved images are made by scratching out lines or holes or by cutting away to leave a raised image. Carving and engraving require tools harder than the material being worked.

POLISHING

The shine given to the surface of a stone – by rubbing it either with grit or powder or against another stone – is its polish. Dark-colored gemstones and those that are translucent or opaque, for instance opal and turquoise, are often polished rather than faceted, as are organic gems. They may be polished as beads or as flat pieces to be used in inlay work, or cut *en cabochon* with a smooth, rounded surface and usually a highly polished, domed top and flat base.



PEBBLE POLISHER
Gem fragments of similar hardness may be turned into attractive pebbles (left) by tumbling in a drum containing abrasive grits and polishing powders (right).



MOTOR-DRIVEN TUMBLING DRUM FOR POLISHING



CARVING

Carving usually refers to the cutting of decorative objects from a larger mass. Stones as hard as 7 on the Mohs scale were carved in ancient Egypt, Babylonia, and China. Impure corundum (emery) was used for carving and engraving in India; nowadays a hand-held chisel or turning machine is used. Popular stones for carving include serpentine, Blue John, malachite, azurite, rhodonite, and rhodochrosite.

CHINESE CARVING

Carving of gemstones in China dates back to the Neolithic period. The most prized material was imported nephrite jade, and decorative objects like this model pagoda are still made.

ENGRAVING

Engraving usually refers to the decoration of the surface of a gemstone by the excavation (scratching out) of lines, holes, or trenches with a sharp instrument, known as a graver or turin. Cameos and intaglios are perhaps the most popular of all engraved objects. A cameo is a design (often a human profile) in flat relief, around which the background has been cut away. In an intaglio it is the subject, not the background, that is cut away, creating a negative image that may be used as a seal in clay or wax. Intaglios were particularly popular with the ancient Greeks and Romans and are still prized by collectors.



GOLD ENGRAVING

The surface of gold and other precious metals used in jewelry may be decorated with intricate patterns, using a hand-held chisel called a graver.

Engraved gemstones gained prominence in Europe in the Renaissance period. During the Elizabethan period in Britain cameo portraits were often given as gifts, particularly among the nobility. All through the ages, layered stones have been used for cameos or intaglios, with onyx and sardonyx particularly popular. Other gems suitable for engraving include rock crystal, amethyst, citrine, beryl, peridot, garnet, lapis lazuli, and hematite, as well as organic materials such as ivory and jet.



BEAD
Spherical gems such as pearls may be pierced and threaded as beads on necklaces.

CABOCHON
This simple cut is used to display colors and optical effects in opaque and translucent stones.



CARVING
The cameo symbol used in this book denotes both carvings and engravings.

POLISHED STONE
Decorative stones given a flat, polished surface may be used in ornaments and jewelry.

MODERN DESIGNS

This citrine prism, with its clean, architectural lines and exquisite engraving, demonstrates the flair and craftsmanship of modern designers. Its maker, Bernd Munsteiner, uses conventional cuts to create classic modern jewels akin to pieces of sculpture. Bernd Munsteiner is one of many artists working in Idar-Oberstein in Germany. Together with Hong Kong, Idar-Oberstein is considered to be one of the most important centers for carving and engraving gemstones today.



ENGRAVED CITRINE

GEMS THROUGH THE AGES

MANKIND'S FASCINATION with gemstones is as old as history itself. People everywhere, throughout the ages, have followed a natural instinct to collect things of beauty and value, and have used whatever gemstones they found locally – from shells to sapphires –

to adorn themselves. Today, there are more gem-producing areas than ever before, new stones are increasingly available, and jewelry designs continue to evolve. But the inherent attraction of gems – their beauty, durability, and rarity – remains the same.




QUARTZ BEADS

The pebbles in this necklace from Ghana were once used as a form of currency.

EARLY COLLECTORS

The earliest collectors found gems with no more equipment than a stick or shovel, a basket, and a sharp eye. Similar Stone Age tools found in the Mogok area of Myanmar show that rubies have been mined there for thousands of years – and the same methods of panning the stream with wicker baskets are used today. Evidence of more organized early mining – for example, abandoned mines and waste dumps – is found in the Urals of Russia, on the shores of the Mediterranean, in Cornwall, England, and in many other places worldwide.

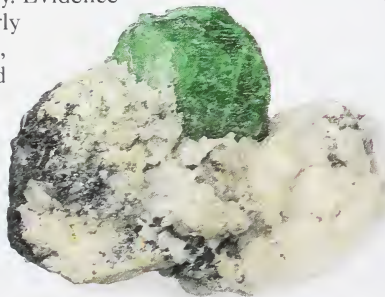


EMERALD IN LIMESTONE

Emerald has been sought after for many thousands of years. The earliest known mines date back to Egypt, 2000 BC.

FIRST USES

Gem materials were probably first used as much for their durability as their beauty. But beauty was not ignored, even then. For example, the Stone Age obsidian ax below has been wrought to be attractive as well as practical, and ancient civilizations did fashion gems purely for adornment. Although most were primitive in design, some were highly intricate, with painted surfaces. Down the ages, gems have also been offered as prestigious gifts, and their portability and intrinsic value gave them a natural use as currency.

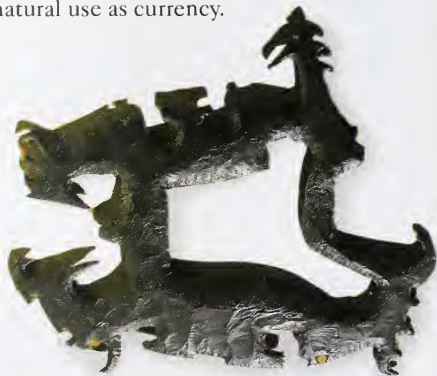

OBSIDIAN AX

A natural volcanic glass, obsidian could be fashioned into a razor-sharp tool or weapon.

ANCIENT JEWELRY

Little jewelry made before the 18th century survives. The best examples are probably those of ancient Egypt. Many of these pieces are gold set with gems such as turquoise, lapis lazuli, and carnelian. It shows the great skill of the Egyptian goldsmiths: the gold refined, annealed, and soldered; the gems fashioned – probably using silica sand, a technique also known to the ancient Chinese. The Romans went on to develop the polished stone rather than the setting. The art of the goldsmith and lapidary survived in the Dark Ages, though in medieval times gothic style was functional – mainly buckles, clasps, and rings.




MERMAN

In this typical 16th-century pendant, a pearl forms the torso, with diamonds and rubies set in gold around it.

UP TO THE PRESENT

With the discovery of the Americas in the 15th century, European trade in gemstones expanded, and 16th- and 17th-century jewelers could use gems from all over the world. With the rise of an affluent merchant class, jewelry became more widely owned and diamonds first became fashionable. In the 20th century, an increase in demand for affordable gems and the scarcity of the most valuable will doubtless continue the trend to use more varied gem species in jewelry.

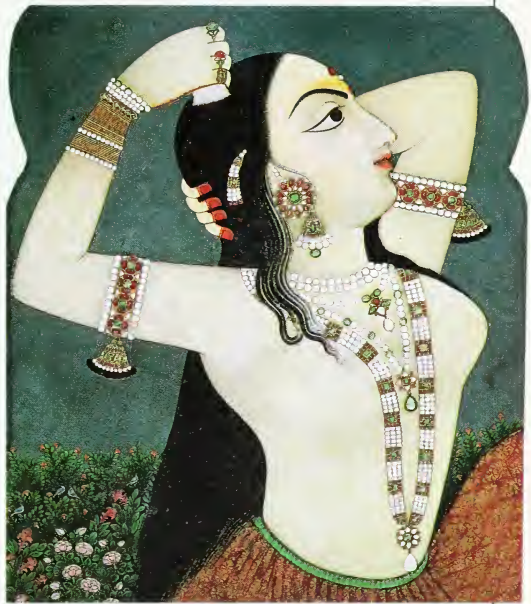

CLOTHED IN JEWELS

Civilizations through the ages have used jewelry for adornment. This late 18th-century miniature shows an Indian woman clothed in richly jeweled necklaces, earrings, bracelets, and amulets.



GEM-ENCRUSTED MODERN BROOCH

Jewelry has passed through many styles, from baroque in the 16th century and floral themes in the 17th, to Art Deco and beyond in the 20th.

HISTORY AND FOLKLORE

THERE ARE NUMEROUS myths and legends associated with gems. Some tell of cursed stones; others of stones with special powers of healing, or that protect or give good luck to the wearer. Some of the largest known diamonds have legends associated with them that have been told and retold over centuries, and many now lost are surrounded by tales of intrigue and murder. Some mines are thought to be cursed – probably rumors spread by the mine owners to keep unwanted prospectors away. In Myanmar (Burma), for instance, where all gemstones belonged to the monarch, the belief that anyone who took a stone from a mine would be cursed may have been deliberately cultivated to curb losses of a valuable national asset.

CRYSTAL GAZING

Since Greek and Roman times, balls of polished rock crystal have been used to see into the future. The difficulty of finding a flawless piece large enough to be polished adds to the mystique. The mystic gazes at the ball, lets the eyes go out of focus, and then interprets the misty “image.”

CRYSTAL BALL



PERUVIAN GOD

This 12th-century ceremonial knife from Peru is made from gold adorned with turquoise. The handle has been formed into the image of a deity.



DEATH MASK


This Aztec funeral mask adorned with turquoise may have speeded entry to the next world.



THUMB GUARD

This 17th-century ring, mounted with rubies and emeralds, was designed to protect an archer's thumb when releasing arrows.

rock crystal ball supported by Japanese dragons

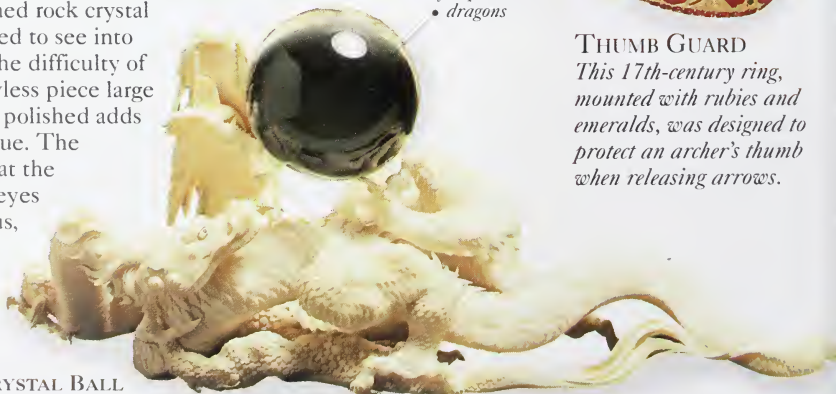

BIRTHSTONES

Certain gems have traditionally been associated with different months of the year and are thought lucky or important for people born under their influence. This probably stems from the ancient belief that gems came from the heavens. Many cultures associate gems with the signs of the zodiac, and others associate them with the months of the year. The selection varies from country to country, perhaps influenced by availability of gems, local traditions, or fashions. The custom of wearing birthstone jewelry started in 18th-century Poland and has since spread throughout the world. The most popular selection is shown at right.



JANUARY
(GARNET)

FEBRUARY
(AMETHYST)

MARCH
(AQUAMARINE)

APRIL
(DIAMOND)

MAY
(EMERALD)

JUNE
(PEARL)

JULY
(RUBY)

AUGUST
(PERIDOT)

SEPTEMBER
(SAPPHIRE)

OCTOBER
(OPAL)

NOVEMBER
(TOPAZ)

DECEMBER
(TURQUOISE)



SIGNS OF THE ZODIAC

This rock crystal is shaped with 12 pentagonal faces, each engraved with one of the signs of the zodiac.

CRYSTAL HEALING

Belief in the healing properties of gems has a very long history, as the rituals of medicine men in ancient tribes attest. Crystal healers today believe that each gem has the power to influence the health and well-being of a specific part of the body. The light reflected off stones placed on vital nerve points is thought to be absorbed by the body, supplying it with healing energy.



ROCK CRYSTAL

Prized for their beauty and clarity, rock crystals are often chosen for use in crystal healing.

CRYSTAL PENDANT

Gems worn close to the skin are believed to heal or protect.



SYNTHETIC GEMSTONES

SYNTHETIC GEMSTONES are made in laboratories or factories, not in rocks. They have virtually the same chemical composition and crystal structure as natural gemstones, so their optical and physical properties are very similar.

However, they can usually be identified by their distinctive inclusions. Many gems have been synthesized in the laboratory but only a few are produced commercially. These are generally used for industrial and scientific purposes.

MAKING A SYNTHETIC

Man has tried to replicate gemstones for thousands of years, but it was not until the late 1800s that any substantial success was achieved. In 1877, French chemist Edmond Frémy grew the first gem-quality crystals of reasonable size (see bottom right), and then around 1900 August Verneuil devised his technique to manufacture ruby. With a few modifications, the Verneuil flame-fusion method is still in use today. The powdered ingredients are dropped into a furnace and melt as they fall through a flame hotter than 3,630°F (2,000°C), fusing into liquid drops. These drip on to a pedestal and crystallize. As the pedestal is withdrawn, a long, cylindrical crystal, which is known as a *boule*, forms.



FLUX-MELT
SYNTHETIC EMERALD

FLUX-MELT TECHNIQUE

Pioneered by the French chemist Edmond Frémy, the flux-melt technique is still used to make emeralds. The powdered ingredients are melted and fused in a solvent (flux) in a crucible. The material must be kept at a very high temperature for months, before being left to cool very slowly.



FLAME-FUSION CORUNDUM
*Synthetic corundum manufactured by flame-fusion grows as a single mass called a *boule*. It has the same inner structure as a natural crystal and can be cut to shape.*

• pedestal on which *boule* forms




• corundum boules tend to split down their length



CORUNDUM
BOULES

• synthetic ruby crystals grown in a crucible

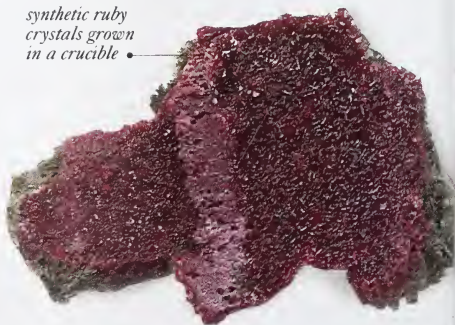

EDMOND FRÉMY

French chemist Edmond Frémy, the first to grow emerald crystals of a reasonable size, went on to grow ruby crystals by melting aluminum oxide and chromium in a crucible.

SHAPES AND COLORS

Because of the way they are made, synthetic gems may show subtle differences in shape and color that help distinguish them from their natural counterparts. For instance, corundum produced by flame fusion has curved growth lines rather than straight ones, because the ingredients have not mixed together fully. Some synthetic gems may also suffer from uneven color distribution. Flame-fusion spinel is manufactured to imitate gems such as ruby, sapphire, aquamarine, blue zircon, tourmaline, peridot, and chrysoberyl.




SYNTHETIC SPINEL
Synthetic spinel (above), colored red, may make a better imitation gem than flame-fusion ruby (left).

DISTINCTIVE INCLUSIONS


Synthetic gems have different inclusions from those of natural gems, so often the best way to tell them apart is to examine them with a loupe (below) or a microscope. Synthetic inclusions may be typical of a process, or of a synthetic gem species. For instance, in Verneuil rubies, gas bubbles have well-defined outlines; in flux-melt emeralds (right), characteristic veil and feather patterns form.



GILSON FLUX-MELT EMERALD

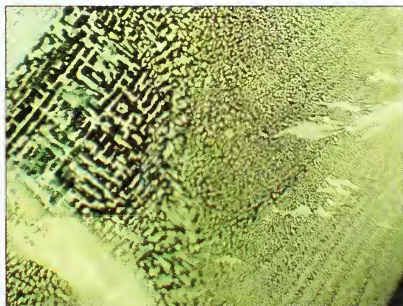


GILSON EMERALD INCLUSIONS
Synthetic emeralds from the French manufacturer Gilson have characteristic veil-like inclusions. The gems are made from poor-quality material by a flux-melt method.

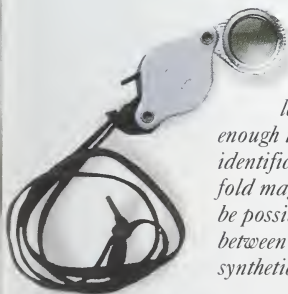


LOUPE
This hand-held lens is powerful enough to assist in gem identification. With its ten-fold magnification it may be possible to distinguish between natural and synthetic inclusions.

GILSON GEMS

Lapis lazuli, turquoise, and coral produced by the French manufacturer Gilson are similar to their natural counterparts but are not true synthetics because their optical and physical properties differ from the natural gems. Gilson lapis lazuli, for example, is more porous and has a lower specific gravity.



GILSON TURQUOISE



GILSON LAPIS LAZULI



GILSON CORAL

IMITATION AND ENHANCEMENT

IMITATION GEMS have the appearance of their natural counterparts, but their physical properties are different. They are intended to deceive. Manmade materials, such as glass and synthetic spinel, have been used to imitate many

different gems, but natural stones can also be modified to resemble more valuable gems. It is possible to enhance authentic gemstones by hiding cracks and flaws, or by using heat treatment or irradiation to improve their color.


GLASS IMITATIONS

Glass has been used for centuries to imitate gemstones. It can be made either transparent or opaque in almost any color, and, like many gems, it has a vitreous luster. At first sight, therefore, it may easily be mistaken for the real thing. However, it can usually be detected by its warmer feel and by the evidence of wear and tear that results from its greater softness. Chipped facets and internal swirls and bubbles are common. In addition, unlike most of the gems it imitates, glass is singly refractive.



GLASS "RUBY"

glass imitations often contain pronounced inclusions •

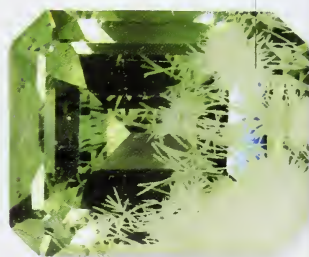


SNOWFLAKE INCLUSION IN GLASS

• glass can be made to imitate almost any transparent gem

OPAL IMITATIONS

Gemologists call the flashes of color in opal its "play of color," or iridescence. It is caused by the interference of light from the minute spheres of silica gel that make up the gem. This structure is imitated to great effect in opals made by the French manufacturer Gilson, although the difference can be seen in the mosaiclike margins of the patches of color (see p.135).

There are various other opal imitations, including stones made of polystyrene latex, or of different pieces assembled as one. In an opal doublet (two pieces) the top is natural precious opal, but the base is common (potch) opal, glass, or chalcedony. A triplet (three pieces) has an additional protective dome of rock crystal.

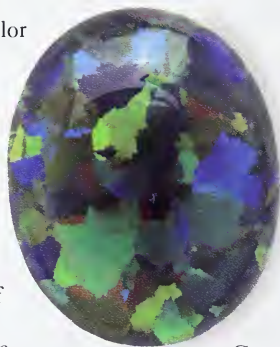


GILSON OPAL



POLYSTYRENE LATEX OPAL


SLOCUM STONES

American manufacturer John Slocum developed imitation opals with a good play of color, but they lack the silky, flat color patches of genuine opal and the structure looks crumpled when magnified.

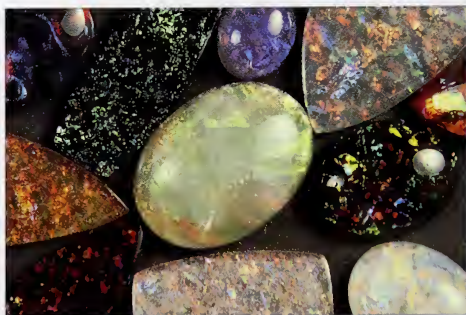

GARNET-TOPPED DOUBLET


One of the most common composite stones (stones made of more than one piece) is the garnet-topped doublet, or GTD. A thin section of natural garnet is cemented to a colored glass base, which gives the GTD its apparent color. The deception is most easily seen at the junction of the two layers, which may be obvious.



GTD JUNCTION
Changes in color and luster are visible where garnet and glass meet.


DIAMOND IMITATIONS

Many natural materials have been used to imitate diamond, but zircon is the most convincing. Synthetic imitations are popular, but each has its faults (right). Imitations can usually be detected by testing the heat conductivity of the stone.




YTTORIUM ALUMINUM GARNET (YAG)

• heavy, lacks fire



CUBIC ZIRCONIA

• softer, more fire



STRONTIUM TITANATE

• heavier than diamond

HEAT TREATMENT

Heating may enhance or change the color or clarity of some gems. Techniques range from throwing gems in a fire to "cook," to the use of sophisticated equipment. The outcome is certain for some gems (like aquamarine, which changes from green to blue), but less so for others.



BROWN ZIRCON HEATED TO BLUE

IRRADIATION

Gems may change color if exposed to radiation. This may come from radioactive elements within the Earth's crust or from artificial sources. Natural radiation may take millions of years to have an effect, while artificial irradiation may take only a few hours to change a gem's color. In some cases a gem will later revert to its original color or may fade with time. Many changes can be reversed or modified by heat treatment.



IRRADIATED, HEAT-TREATED TOPAZ

STAINING

Stains, dyes, or chemicals can alter the appearance of a gem, coating just the surface or changing the whole specimen. For staining to be effective, a stone must be porous or contain cracks and flaws through which the color can enter. Porous white howlite, for example, can be stained to imitate turquoise.



STAINED HOWLITE

OILING

Oils may enhance a gem's color and disguise fissures and blemishes. It is common to oil emeralds in order to fill their natural cracks and flaws.




OILED EMERALD

COLOR KEY

WHEN IDENTIFYING a gemstone, a gemologist will hold it, feel it, and examine it from all angles. This is done to assess the appearance of the stone by noting the color, the luster, and any other features. A hand-held loupe (see p.35) may be used to search for scratches and flaws on the surface that may give

an indication of hardness, while a search inside the stone may reveal characteristic inclusions. These features may be unique to one gem, but further tests may be necessary to identify synthetic or imitation stones. From this initial examination, however, the gemologist should know which tests to perform.

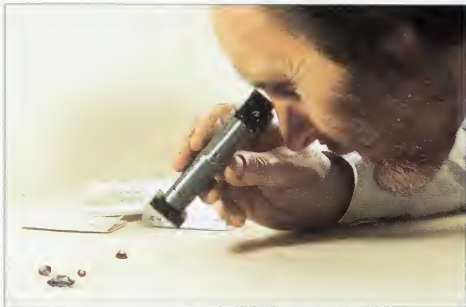

RUBY



ALMANDINE GARNET



RED GLASS

SPECTROSCOPE
Many gems appear the same color, but can be distinguished when viewed with a spectroscope (above). This reveals an absorption spectrum (left) that is unique to each gemstone (see p.21).

HOW THE COLOR KEY WORKS

This key puts all gems into one of seven color categories, though color varieties within some species may appear (or be listed, if not pictured in the book itself) in more than one. Each color category is divided into three sections: gems that are always that color, gems usually that color, and gems sometimes that color.

category heading



representative specimen

gem name

RUBY 94

page number of main entry

key identification features

Distinctive red color, hard

COLORLESS GEMSTONES

ALWAYS COLORLESS



HAMBERGITE 115
Perfect cleavage,
large birefracton



PHENAKITE 98
Silvery look
if well cut




ALBITE 130
Vitreous to
pearly luster



GOSHENITE 77
Spiky inclusions
common



BERYLLONITE 118
Lacks fire,
soft, brittle



ROCK CRYSTAL 81
*Vitreous luster,
transparent*



PETALITE 129
*Vitreous luster,
transparent*




DATOLITE 129
*Tinge of yellow,
green, or white*



ACHROITE 102
*Extremely
rare*


USUALLY COLORLESS



SHEELITE 70
*Very soft, good
fire, uncommon*




CELESTINE 105
*Soft, cut for
collectors only*



DIAMOND 54
*Adamantine
luster, good fire*




DANBURITE 110
*Yellow/pink tinge,
bright, lacks fire*



CERUSSITE 105
*Adamantine luster,
high density, soft*


SOMETIMES COLORLESS



DOLOMITE 99
*Soft, vitreous
to pearly luster*



EUCLASE 129
*Rare, black
mineral inclusions*



MOONSTONE 123
*Opalescence, blue
or white sheen*




**COLORLESS
ORTHOCLASE 122**
Three good cleavages



SCAPOLITE 71
*Rare, vitreous
luster*




FLUORITE 66
*Soft, lacks fire,
hematite inclusions*



ZIRCON 72
*Adamantine
luster, good fire*



SAPPHIRE 96
*Rare, high density,
extremely hard*




APATITE 79
Fairly soft

OTHER GEMS
ENSTATITE 111
GROSSULAR 61
TOPAZ 106

RED OR PINK

ALWAYS RED OR PINK




ROSE QUARTZ 83
Cloudy, distinctive pinkish color



KUNZITE 120
Strongly pleochroic, good cleavage



MORGANITE 78
Distinctive color, hard



THULITE 116
Distinctive color mix, massive



PINK GROSSULAR 60
Distinctive color, fine-grained, opaque




TUGTUPIE 74
Opaque, may be mottled, massive



RHODOCHROSITE 100
Fine-grained, banded; also clear faceted stones



RHODONITE 132
Black veins in massive material



RED BERYL 78
Extremely rare, seldom cut



RUBY 94
Distinctive red color, hard



ALMANDINE 59
Distinctive color, high luster




PYROPE 58
Distinctive color, inclusions rare



RUBELLITE 101
Pleochroic, cat's-eye cabochons

USUALLY RED OR PINK



TAAFFEITE 80
Extremely rare, fairly hard



SPESSARTINE 58
Lacelike inclusions, rare at gem quality

SOMETIMES RED OR PINK




JADEITE 124
Dimpled surface when polished



TOPAZ 106
Distinctive color, hard, high density



WATERMELON TOURMALINE 103
Distinctive colors



SAPPHIRE 97
High density, hard, pleochroic



CORAL 142
*Grain on surface,
soft, may fade*



SPINEL 64
*Hard, singly
refractive*




JASPER 92
*Distinctive
color, opaque*

OTHER GEMS


- ZIRCON 73
- RUTILE 71
- SMITHSONITE 99
- SCAPOLITE 71
- GARNET-TOPPED
DOUBLET 61

WHITE OR SILVER

ALWAYS WHITE OR SILVER




MILKY QUARTZ 85
*Distinctive milky
white color*



PLATINUM 52
*Metallic luster, high
density, opaque*




SILVER 50
*Metallic luster,
soft, opaque*



HOWLITE 128
*Very soft,
chalky, opaque*



IVORY 146
*Soft, growth
lines on surface*



MEERSCHAUM 119
*Chalky, opaque,
fine-grained, soft*




GYPSUM 128
*Silky to vitreous
luster, soft*

USUALLY WHITE OR SILVER



PEARL 138
*Pearly luster,
very soft*




SHELL 144
*Iridescent,
very soft*

SOMETIMES WHITE OR SILVER



CALCITE 98
*Soft, large
birefraction*



SERPENTINE 127
*Vitreous to greasy
luster, translucent*



NEPHRITE 125
*Tough interlocking
structure*

OTHER GEMS

- AGATE 88
- CORAL 142
- OPAL 134
- MOONSTONE 123

YELLOW TO BROWN GEMSTONES

ALWAYS YELLOW-BROWN



ANGLESITE 114
High density,
fragile, good fire



CITRINE 83
Distinctive
color




BRAZILIANITE 118
Fragile, brittle,
fairly soft, rare



SINHALITE 114
Pleochroic, large
birefracton



HELIODOR 77
Pleochroic, hard,
pastel shades




GOLD 48
Distinctive
color, soft




PADPARADSCHA 95
Distinctive orange-
pink color, hard



CARNELIAN 93
Translucent,
reddish brown



FIRE OPAL 134
Low density,
transparent



SARDONYX 90
Distinctive white
bands




HESSONITE 60
Granular
inclusions




SUNSTONE 130
Bright metallic
inclusions




HYPERSTHENE 112
Reddish iridescence,
fairly soft



DRAVITE 102
Pleochroic, showing two
shades of body color



CASSITERITE 70
High density,
good fire



TORTOISESHELL 144
Distinctive mottling
on surface



SMOKY QUARTZ 84
Distinctive grayish
brown color



EPIDOTE 121
Strongly pleochroic,
fragile, rarely cut

OTHER GEMS
TOPAZOLITE 107
PYRITE 63

USUALLY YELLOW-BROWN




AMBLYGONITE 132
Vitreous to pearly luster




YELLOW ORTHOCLASE 122
Fragile, cat's-eyes



VESUVIANITE 74
Pleochroic, vitreous to adamantine luster



SPHALERITE 63
Good fire, metallic to vitreous luster



TITANITE 121
Very good fire, pleochroic



AMBER 148
Very soft, resinous luster




AVENTURINE QUARTZ 85
Platy inclusions



AXINITE 133
Pleochroic, easily chipped



ENSTATITE 111
Fragile, distinctive absorption spectrum



STAUROLITE 117
Opaque, twinned crystals cross-shaped


SOMETIMES YELLOW-BROWN




RUTILE 71
Good fire, needle-like inclusions



PREHNITE 115
Usually cloudy and translucent



SCHEELITE 70
Fairly soft, good fire



CHATOYANT QUARTZ 86
Fibrous structure



MOSS AGATE 89
Translucent, mosslike pattern



ARAGONITE 104
Very soft, microcrystalline



SPESSARTINE 58
Hard, lacelike inclusions



BARITE 104
High density, very soft



CHRYSOBERYL 108
Hard, strongly pleochroic

OTHER GEMS


- DIAMOND 54
- DEMANTOID 62
- FLUORITE 66
- ZIRCON 72
- APATITE 79
- SAPPHIRE 96
- TOURMALINE 101
- TOPAZ 106
- KÖRNERUPINE 113

GREEN GEMSTONES

ALWAYS GREEN



CHRYSOCOLLA 126
*Distinctive color;
opaque, very soft*




EMERALD 75
*Distinctive color;
seldom flawless*




PERIDOT 113
*Distinctive oily
green color*




HIDDENITE 120
*Distinctive color;
pleochroic*



DIOPTASE 99
*Distinctive color;
large birefraction*




BLOODSTONE 93
*Opaque, red
spots*




UVAROVITE 59
*Distinctive color;
crystals fragile*



PRASE 92
*Translucent, dark
green color*




MALACHITE 126
*Characteristic bands
of color, soft*



MOLDAVITE 137
*Glassy, inclusions of
bubbles and swirls*




ALEXANDRITE 108
*Color changes,
pleochroic, high density*




ANDALUSITE 110
*Very strong
pleochroism*

USUALLY GREEN



SERPENTINE 127
*Vitreous to greasy
luster, fairly soft*



JADEITE 124
*Fine-grained,
may be dimpled*




DIOPSIDE 119
Large birefraction



DEMANTOID 62
*Asbestos inclusions,
adamantine luster*



AVENTURINE QUARTZ 85
*Platy inclusions,
vitreous luster*

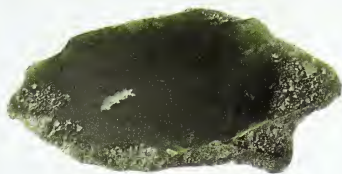


NEPHRITE 125
*Tough interlocking structure,
greasy to pearly luster*

OTHER GEMS
PREHNITE 115

SOMETIMES GREEN




MICROCLINE 123
*Distinctive blue-
green color*



AGATE 88
*Translucent,
distinct banding*



**WATERMELON
TOURMALINE 103**
Bicolored



DIAMOND 56
*Hardest natural
substance, good fire*




SAPPHIRE 96
*High density,
hard, pleochroic*




APATITE 79
*Distinctive
absorption spectrum*



ZIRCON 72
*Good fire, adamantine
to resinous luster*



**GROSSULAR
GARNET 61**
Vitreous luster



**GARNET-TOPPED
DOUBLET 61**
Two parts joined



ENSTATITE 111
*Distinctive
absorption spectrum*



KORNERUPINE 113
*Strongly pleochroic,
rare as gem quality*



SPHALERITE 63
*Very soft, good
fire, high density*

OTHER GEMS


- FLUORITE 66
- KYANITE 133
- TOURMALINE 103
- SMITHSONITE 99
- EUCLASE 129

BLUE OR VIOLET GEMSTONES

ALWAYS BLUE OR VIOLET



AQUAMARINE 76
*Tubular inclusions,
pleochroic*



LAZULITE 128
*Often
mottled*




HAÜYNE 68
*Small stones,
rarely cut*



TURQUOISE 131
*Distinctive color,
fragile*



INDICOLITE 101
*Strongly
pleochroic*



AZURITE 126
*Distinctive color,
fragile, soft*



LAPIS LAZULI 69
*Distinctive blue,
pyrite inclusions*



SODALITE 68
*Distinctive
blue color*



ZOISITE 116
*Strongly
pleochroic*



AMETHYST 82
*Tigerstripe
inclusions*

USUALLY BLUE OR VIOLET



SILLIMANITE 111
*Distinctly pleochroic,
good cleavage*



DUMORTIERITE 117
*Usually massive,
distinctive color*



BENITOITE 80
*Good fire,
birefractance*




IOLITE 112
*Strongly
pleochroic*



KYANITE 133
*Pleochroic,
brittle, flaky*

SOMETIMES BLUE OR VIOLET



FLUORITE 66
*Lacks fire, soft,
good cleavages*



TOPAZ 106
*Pleochroic, hard,
tearlike inclusions*



ZIRCON 72
*Good fire, adamant-
ine to resinous luster*



SMITHSONITE 99
*Distinctive
blue color*



SAPPHIRE 95
*High density,
hard, pleochroic*



SCAPOLITE 71
Cat's-eyes, fibrous inclusions



SPINEL 64
Hard, singly refractive




AXINITE 133
Pleochroic, brittle

OTHER GEMS

- APATITE 79
- AGATE (STAINED) 88
- HOWLITE (STAINED) 128
- DIAMOND 54
- EUCLASE 129
- CHRYSOBERYL 108
- GARNET-TOPPED DOUBLET 61

BLACK GEMSTONES

ALWAYS BLACK



HEMATITE 100
Metallic luster, opaque, iridescent



SCHORL 103
Opaque, vitreous luster




JET 140
Very soft, coal-like smell when warm

USUALLY BLACK



OBSIDIAN 136
Glassy, fairly hard, bubblelike inclusions

SOMETIMES BLACK



MELANITE 62
Adamantine to vitreous luster



DIAMOND 54
Adamantine luster, hard




TEKTITE 137
Glassy, cracks on surface



CORAL 142
Sensitive to heat, soft

IRIDESCENT GEMSTONES




OPAL 134
Iridescent colors, may dry and crack



FIRE AGATE 87
Iridescence resembles oily rings of color



LABRADORITE 130
Iridescence on dark body color



MOTHER-OF-PEARL 145
Blue and purple iridescence on surface

Crystal structure Cubic

Composition Gold

Hardness 2½

GOLD

The color of gold depends upon the amount and type of impurities it contains. Native gold is typically golden yellow, but in order to vary its color and increase its hardness for use in jewelry, gold may be alloyed with other metals. Silver, platinum, nickel, or zinc may be added to give a pale or white gold. Copper is added for rose or pink gold; iron for a tinge of blue. Gold purity is defined by the proportion of pure gold metal present, expressed as its carat (ct) value. The purity of gold used in jewelry varies from 9 carat (37½ percent or more pure gold), through 14, 18, and 22 carat, to 24 carat, which is pure gold. In many countries, gold jewelry is “hallmarked” to indicate its degree of purity.

- **OCCURRENCE** Gold is found in igneous rocks and in associated quartz veins, often in small quantities invisible to the naked eye. It is also concentrated in secondary “placer” deposits – as nuggets or grains in river sands and gravels. Gold may still be extracted from placer deposits by the traditional panning method, but modern commercial mining involves large earth-moving machinery and concentrated acids for processing the ore. The main gold-bearing rocks occur in Africa, California and Alaska, Canada, the former USSR, South America, and Australia.
- **REMARK** Gold has been used for coins, decoration, and jewelry for thousands of years. It is attractive and easily worked and wears well.



GOLD GRAINS



GOLD IN QUARTZ MATRIX

SG 19.30	RI None	DR None	Luster Metallic
----------	---------	---------	-----------------



• *crystalline nugget*

TIE PIN
This unusual piece of jewelry features a gold nugget set into a gold tie pin.



GOLD, DIAMONDS, AND PEARLS
This gold neckpiece is set with pink pearls and clusters of diamonds. Gold is a popular setting for precious stones as it is easy to fashion and is hard-wearing and resistant to acids and tarnishing.

groups of diamonds

natural pearl

GOLD BANGLE
This flexible bracelet is made from 18-carat rose and yellow gold.



GOLD MOLD
This ivy leaf motif was made by casting 18-carat gold in a wax mold.



softness of gold accommodates intricate working

• *hallmark*



GOLD BANGLE
The hallmark that shows the purity of worked gold is just visible on this delicate bangle. In this case, it indicates the gold is 18 carat.

square-cut demantoid garnet



GOLD RING
Gold is a popular and resilient material for rings. Here it is the setting for a green demantoid garnet.

Crystal structure Cubic	Composition Silver	Hardness 2½
-------------------------	--------------------	-------------

SILVER

Silver usually occurs in massive form as nuggets or grains, although it may also be found in wiry, dendritic (treelike) aggregates. When newly mined or recently polished, it has a characteristic bright, silver-white color and metallic luster. However, on exposure to oxygen in the air, a black layer of silver oxide readily forms, tarnishing the surface. Because of this, and the fact that it is too soft to be used in most jewelry in its pure or native form, silver is often alloyed with other metals or given a covering layer of gold. Electrum, an alloy of gold and silver in use since the time of the ancient Greeks, contains 20–25 percent silver. Sterling silver contains 92½ percent or more pure silver (and usually some copper), and Britannia silver has a silver content of 95 percent or more. Both alloys are used as standards to define silver content.


• **OCCURRENCE** Most silver is a by-product of lead mining and is often associated with copper. The main silver mining areas of the world are South America, the USA, Australia, and the former USSR. The greatest single producer of silver is probably Mexico, where silver has been mined for almost 500 years. The finest native silver, which occurs naturally in the shape of twisted wire, is from Kongsberg, Norway.



DENDRITIC SILVER CRYSTALS



POLISHED SLICE OF SILVER AND COPPER ORE

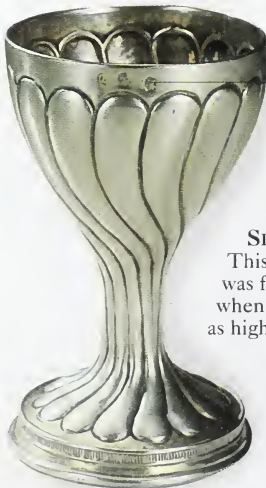

SILVER WINE CUP

This part-gilt silver cup was fashioned in 1493, when silver was valued as highly as gold.

• *crystals have wirelike habit*

• *dendritic silver from Kongsberg is renowned for its quality*



NATIVE SILVER FROM KONGSBERG, NORWAY

SG 10.50	RI None	DR None	Luster Metallic
----------	---------	---------	-----------------



• *rose gold*

TOWER BROOCHES
 These modern silver brooches, made by British silversmith V. Ambery-Smith, have additional decoration in rose and yellow gold.

• *silver*

• *yellow gold*

• *18-carat gold thread*



• *highly polished silver*

SILVER BRACELET
 This sterling silver bracelet also features 18-carat gold thread.

SILVER DISH
 Fashioned in 1973, this dish features a leaf motif border made from oxidized silver.



• *oxidation alters color of silver*



• *ornate carving*

WATCH CASE
 Because of its softness, silver is extremely popular for fine metalwork, as seen in this 18th-century watch.



• *silver lends a simple elegance to modern designs*

MODERN USES
 Silver is prized for ornamental items, such as these key rings. Today it is also used in electronics and photography.

Crystal structure Cubic

Composition Platinum


Hardness 4

PLATINUM

Platinum has been used for thousands of years, but it was not recognized as a chemical element until 1735. Of the three precious metals – gold, silver, and platinum – it is the rarest and the most valuable. Chemically inert and resistant to corrosion, platinum does not tarnish when exposed to the atmosphere, unlike silver. It is silvery gray, gray white, or white in color, opaque, and has a metallic luster. It is slightly more dense than pure gold and about twice as dense as silver. Early jewelers had difficulty achieving the 3,223°F (1,773°C) needed to melt platinum: it was not until the 1920s that the technology was developed sufficiently to work this precious metal.

• **OCCURRENCE** Platinum forms in igneous rocks, usually as ores in which the grains of platinum are often too minute to be seen with the naked eye. It may also occur in secondary “placer” deposits in river sands and gravels, and glacial deposits – usually as grains, more rarely as nuggets. The main occurrences of platinum have been in South Africa, Canada (Sudbury), the USA (Alaska), Russia (the River Perm and other rivers running down from the Urals), Australia, Colombia, and Peru.


• **REMARK** Although nuggets had been set in rings before 1920, most platinum jewelry dates from after this time. Soft and easy to carve, platinum is often fashioned into quite intricate designs.

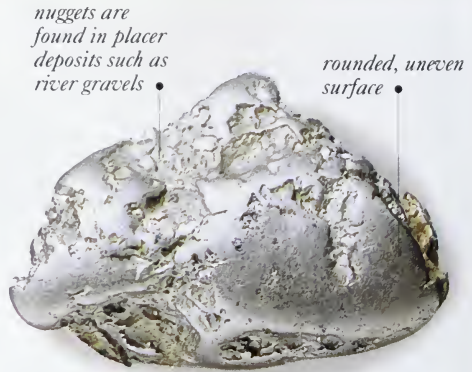

nuggets are found in placer deposits such as river gravels

rounded, uneven surface

PLATINUM NUGGET

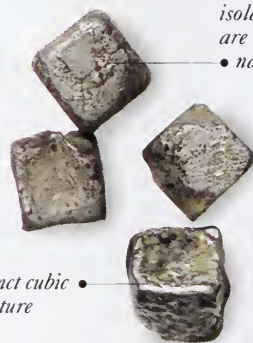

isolated crystals are rare in nature

distinct cubic structure


ISOLATED CRYSTALS



silvery color

grains are found in secondary deposits, rarely in the host rock

PLATINUM GRAINS

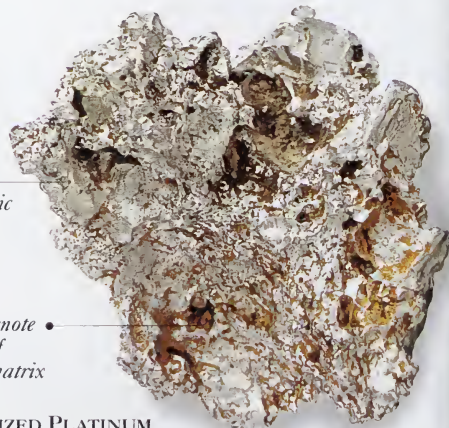

opaque, with metallic luster

cavities denote position of original matrix

CRYSTALLIZED PLATINUM

SG 21.40

RI None

DR None

Luster Metallic

RING AND EARRING SUITE

This modern suite is set with square-cut precious stones in all the colors of the rainbow.



• platinum setting



FILIGREE NECKLACE

Like gold and silver, platinum is quite a soft material, making it ideal for the sort of intricate working seen in this necklace. Unlike silver, platinum does not tarnish when exposed to the atmosphere.

• platinum filigree

MODERN BROOCH

Platinum is a popular and stylish material for modern jewelry.



• pendeloque-cut aquamarine

• diamonds



• diamond-set detail at back of necklace

• two hoops provide framework for design

NECKLACE WITH DIAMONDS

Platinum is a perfect, if very expensive, setting for cut diamonds, as the colors complement each other well.

• inlaid diamonds

• pendeloque-cut aquamarine



AQUAMARINE RING

Platinum provides a cool setting for this ice-blue pendeloque-cut aquamarine and its twenty diamonds.

Crystal structure Cubic	Composition Carbon	Hardness 10
----------------------------	-----------------------	----------------

DIAMOND

Diamond is the hardest mineral on Earth, and this, combined with its exceptional luster and brilliant fire, has made it the most highly prized of all gems. Pure, colorless diamond is the most popular, but other varieties – from yellow and brown to green, blue, pink, red, gray, and black – are also found, depending on the impurities present. Because of the uniform arrangement of their constituent carbon atoms, diamond crystals are well formed – usually octahedral with rounded edges and slightly convex faces. Their perfect cleavage facilitates the early stages of fashioning (see p.26), but they can be polished only by other diamonds.

- **OCCURRENCE** Diamond forms at high temperatures and pressures 50 miles (80 km) or more underground. When India and later Brazil were the main producers, most diamond came from secondary sources, such as river gravels. However, since the discovery of diamond in kimberlite rock in South Africa (around 1870), its extraction has involved processing vast quantities of rock. Australia is the main producer today; other localities include Ghana, Sierra Leone, Zaire, Botswana, Namibia, the former USSR, the USA, and Brazil.
- **REMARK** Diamonds are graded by the four C's: color, cut, clarity, and carat (weight).



• *colored diamonds, such as this yellowish green variety, are known as "fancy"*

BRILLIANT CUT



• *most diamonds are faceted as a brilliant cut, which brings out their natural fire*

• *pale pink stone*

BRILLIANT CUT



• *brilliant cut reflects as much light as possible out through front of stone*

BRILLIANT CUT



• *subtle gray-green color*


• *minimum light leakage through back facets*

BRILLIANT CUT



• *pink-red variety*


• *diamonds may be transparent to opaque*



• *green and black inclusions*

• *typical convex surfaces*

• *rounded edges*



• *adamantine luster*



FIVE UNPOLISHED DIAMOND CRYSTALS

SG 3.52	Ri 2.42	DR None	Luster Adamantine
---------	---------	---------	-------------------

LEAF DESIGN BRACELET

The extraordinary fire and luster of diamond produce an almost shimmering effect in this bracelet.

colorless, brilliant-cut diamonds

round, brilliant-cut diamonds

platinum ring

marquise-cut diamonds

CRESCENT BROOCH

Colorless diamonds are the most highly prized. In this brooch, many fine, brilliant-cut examples have been mounted in gold.

CLUSTER RING AND EARRINGS

Diamonds are popular for all jewelry, from the simplest to the most sophisticated, because of their hardness, superb luster, and spectacular fire.

diamond-studded earring

sugarlike surface texture

cubic habit uncommon

rough diamond with convex crystal faces

DIAMOND CRYSTALS

conglomerate of pebbles and mineral grains



Brilliant



Brilliant



Cushion



Old Mine (early Brilliant)






Pendeloque



Marquise

DIAMOND IN CONGLOMERATE MATRIX

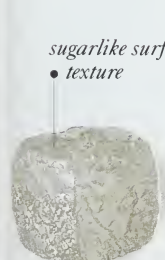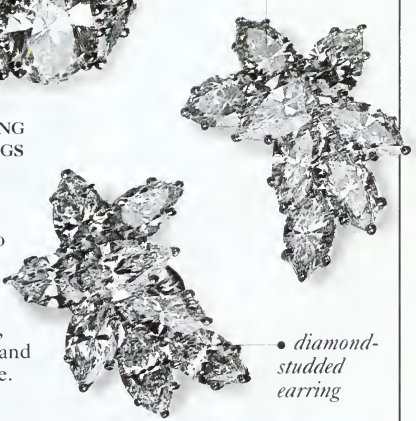

Crystal structure Cubic

Composition Carbon


Hardness 10



• different color varieties are caused by minute traces of other minerals


• unusual, semitranslucent, milky white stone

opaque, black "bort" variety derives color from graphite
• inclusions

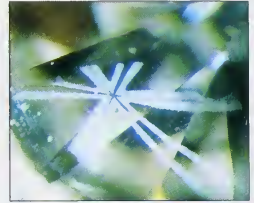

Inclusions in this diamond cause asterism in the form of a double six-rayed star.

BRILLIANT CUT

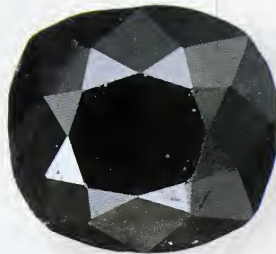

BRILLIANT-CUT BORT DIAMOND

colorless stone marred by black, carbon-filled
• inclusions

pinkish brown color •



BRILLIANT CUT




BRILLIANT CUT

dodecahedral (12-sided)
• habit




DIAMOND CRYSTAL

dark green color due to exposure to radioactive radium •

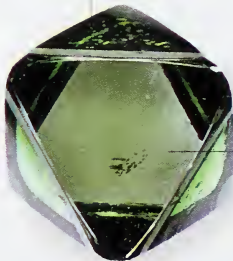

FANCY DIAMOND CRYSTAL

colorless diamond
• crystal

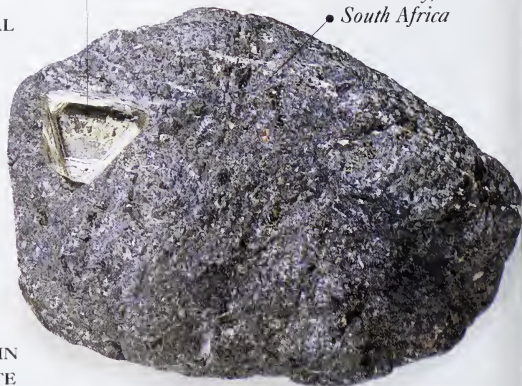

DIAMOND IN KIMBERLITE

volcanic, diamond-bearing kimberlite rock, first identified in Kimberley,
• South Africa

characteristic three-sided face, known
• as a trigon

SG 3.52

RI 2.42

DR None

Luster Adamantine

DIAMOND BROOCH
 Diamonds and emeralds set in gold make up this bird-shaped brooch, with pearls top and bottom.




BUTTERFLY BROOCH
 This glittering brooch, set with more than 150 diamonds, shows examples of round, square, drop, pendeloque, and fancy cuts.



YAG

GLASS

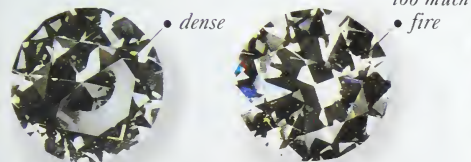

CUBIC ZIRCONIA

STRONTIUM TITANATE

DIAMOND IMITATIONS

Diamonds may be imitated by any colorless stone, by glass, and by manmade gems like YAG (yttrium aluminum garnet). None is an exact copy (see above).



Brilliant

Brilliant

Cushion



Old Mine (early Brilliant)

Pendeloque

Marquise

black bort occurs as rounded masses with radiating structure




FACETED BORT DIAMOND



CRYSTALLIZED BORT DIAMOND

massive habit

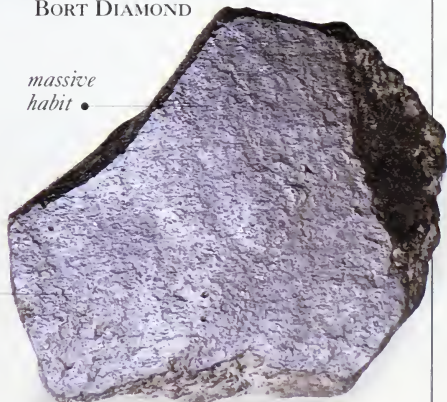

CARBONADO DIAMOND ROUGH

black diamond variety, often used industrially

damaged facet

over three-quarters of all mined diamonds are of industrial quality

Crystal structure Cubic	Composition Magnesium aluminum silicate	Hardness 7½
-------------------------	---	-------------

PYROPE (GARNET)

The blood red color of pyrope is due to its iron and chromium content. It rarely has inclusions, but when present they are rounded crystals or have irregular outlines. As with all garnets, pyrope has no cleavage, and fracture is subconchoidal to uneven.

• **OCCURRENCE** Pyrope is found in volcanic rock and alluvial deposits and may, along with certain other minerals, indicate the presence of diamond-bearing rocks. Localities include the USA

(Arizona), South Africa, Argentina, Australia, Brazil, Myanmar, Scotland, Switzerland, and Tanzania.

• **REMARK** Pyrope comes from the Greek *pyropos*, meaning fiery. Swiss and South African pyropes are lighter red than stones from Bohemia, where pyrope jewelry has been made for over 500 years.



Brilliant

Mixed



fiery red Bohemian pyrope

PYROPE CRYSTALS IN MATRIX



brilliant-cut crown

vitreous luster

OVAL BRILLIANT CUT

BOHEMIAN EARRINGS

Perfectly transparent, clear, uniformly colored crystals like these were popular for jewelry in the 18th and 19th centuries.

hornblende schist matrix

pyrope crystals



SG 3.80	RI 1.72–1.76	DR None	Luster Vitreous
---------	--------------	---------	-----------------

Crystal structure Cubic	Composition Manganese aluminum silicate	Hardness 7
-------------------------	---	------------

SPESSARTINE (GARNET)

Gem-quality spessartine is uncommon. It is bright orange when pure, but an increase in the iron content makes the stone darker orange to red. Inclusions are lace- or featherlike.

• **OCCURRENCE** Spessartine occurs in granitic pegmatites and alluvial deposits. It is found in Sri Lanka, Madagascar, Brazil, Sweden, Australia, Myanmar, and the USA; also Germany and Italy, but crystals there are too small to facet.

• **REMARK** Spessartine is named after the Spessart district of Bavaria, Germany. It can be confused with hessonite garnet or yellow topaz, but on close examination of inclusions it is distinguishable.



Brilliant

Step

Cabochon




CABOCHON

lacy inclusions

flat crystal face

SPESSARTINE CRYSTAL

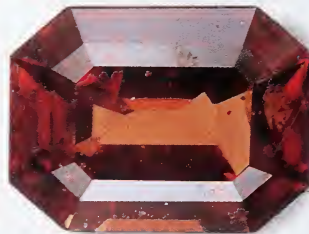

liquid inclusions

vitreous luster

OCTAGONAL STEP CUT



SG 4.16	RI 1.79–1.81	DR None	Luster Vitreous
---------	--------------	---------	-----------------

Crystal structure Cubic

Composition Iron aluminum silicate

Hardness 7½

ALMANDINE (GARNET)

Almandine is generally darker red than pyrope and may appear black, although pinkish red specimens are found. It is usually opaque or subtranslucent, but the rare transparent stones have high luster. Although dense, almandine is brittle, and facet edges chip. Many stones show characteristic inclusions, and four-rayed stars may be seen when the stones are cut *en cabochon*. The darker almandines are frequently cut as cabochons or used as abrasives in garnet paper. The underside of dark almandine is often hollowed out to let more light filter through the stone.

• **OCCURRENCE** Almandine is found in metamorphic rocks, such as garnet mica schist, and less frequently in granitic pegmatites. It has a worldwide occurrence.

• **REMARK** Slices of garnet have been used in windows in churches and temples, and legend has it that Noah suspended garnet in the ark in order to disperse light. Garnet was once said to cure melancholy and to warm the heart.



Cabochon




Mixed



• *brilliant cut enhances fiery red color*

ROUND BRILLIANT CUT



Needlelike crystals of rutile or hornblende are typical inclusions in almandine.



• *black mineral inclusions*



• *hollow back allows in more light*


CABOCHON



• *rounded almandine crystals*

• *granulite matrix*

• *cut shows triangular faces*

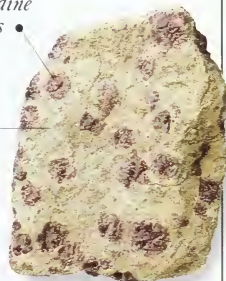

ALMANDINE CRYSTALS IN MATRIX

DROP EARRINGS
The pale pinkish red almandine garnets of these 18th-century earrings have been faceted in the rose cut and set in gold.

SG 4.00

RI 1.76–1.83

DR None

Luster Vitreous

Crystal structure Cubic

Composition Calcium chromium silicate

Hardness 7½


UVAROVITE (GARNET)

The attractive bright green color of uvarovite is due to the presence of chromium. The crystals are very fragile, with subconchoidal to uneven fracture.

• **OCCURRENCE** Uvarovite occurs in serpentine rocks. The best clear crystals are found in the Urals in Russia, lining cavities or rock fissures. Other sources are Finland, Turkey, and Italy.



Brilliant




UVAROVITE CRYSTAL

UVAROVITE CRYSTALS IN MATRIX

• *striations on crystal face*

• *uvarovite crystals*

• *skarn matrix*

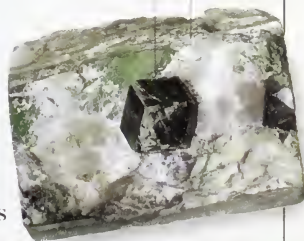

SG 3.77

RI 1.86–1.87

DR None

Luster Vitreous

Crystal structure Cubic	Composition Calcium aluminum silicate	Hardness 7½
-------------------------	---------------------------------------	-------------

HESSONITE (GROSSULAR GARNET)

Grossular garnets occur in a very wide range of colors, from colorless to black. Their name is derived from the first specimen ever found, a distinctive gooseberry green color (see opposite). The orange-brown color of hessonite grossular garnet is due to manganese and iron inclusions.

- **OCCURRENCE** The best hessonite garnets are found in Sri Lanka in metamorphic rocks or gem gravels and sands. In Madagascar, hessonite is often referred to as cinnamon stone. Other localities include Brazil, Canada, and Siberia (Russia), as well as the USA (Maine, California, and New Hampshire).
- **REMARK** Both the ancient Greeks and Romans made cameos, intaglios, and cabochons from hessonite, and faceted stones for jewelry.



OVAL MIXED CUT



OVAL MIXED CUT



ROUND MIXED CUT



Hessonite garnet has swirls of inclusions, giving it a honeylike appearance.

color due to manganese and iron

bright orange-brown hessonite crystals



HESSONITE CRYSTALS ON MATRIX



Brilliant



Mixed


SG 3.65	RI 1.73–1.75	DR None	Luster Vitreous to resinous
---------	--------------	---------	-----------------------------

Crystal structure Cubic	Composition Calcium aluminum silicate	Hardness 7
-------------------------	---------------------------------------	------------


PINK GROSSULAR (GARNET)

Pure grossular garnet is colorless, but impurities incorporated during its formation cause a wide range of colors. This pink variety results from the presence of iron.

- **OCCURRENCE** Pink grossular is found in Mexico, usually as a massive form in metamorphic rocks. Crystals are rare. It also occurs in South Africa.
- **REMARK** Pinkish grossular from Mexico may be known as rosolite.



GROSSULAR GARNET POLISHED SLAB

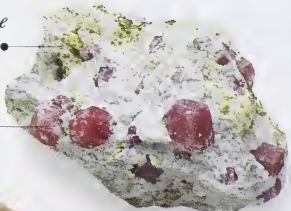


CRYSTALS IN MATRIX

limestone matrix

pink grossular crystals

pink and green banded material may be called Transvaal jade



Polished

SG 3.49	RI 1.69–1.73	DR None	Luster Vitreous
---------	--------------	---------	-----------------

Crystal structure Cubic	Composition Calcium aluminum silicate	Hardness 7
-------------------------	---------------------------------------	------------

GREEN GROSSULAR (GARNET)

There are two varieties of green grossular: one is found as transparent crystals, the other is massive. Massive green grossular from South Africa is called Transvaal jade, after its main source and because it resembles jade. It may contain black specks of the mineral magnetite. Since the 1960s, a transparent green grossular garnet, tsavorite, has been mined in Kenya. Massive green grossular is used as a decorative stone; tsavorite is faceted as a gem.

- **OCCURRENCE** Found in Canada, Sri Lanka, Pakistan, the former USSR, Tanzania, South Africa, and the USA. Kenya is the main source for tsavorite.
- **REMARK** The name "grossular" is derived from the botanical name of the gooseberry, *R. grossularia*. Massive grossular garnet of a gooseberry green color was first discovered in the former USSR. Since then it has also been found in Hungary and Italy.



chromium and vanadium create
• rich green color

BRILLIANT CUT



BEAD NECKLACE
Polished massive green grossular beads have a speckly appearance due to magnetite inclusions.



distinctive gooseberry
• color

MASSIVE POLISHED SLAB



groups of green grossular crystals
•

GREEN GROSSULAR CRYSTALS IN MATRIX



Brilliant



Bead



Polished

SG 3.49	RI 1.69–1.73	DR None	Luster Vitreous
---------	--------------	---------	-----------------

Crystal structure Variable	Composition Variable	Hardness Variable
----------------------------	----------------------	-------------------


GARNET-TOPPED DOUBLET

A doublet is a stone made of two separate pieces cemented together to create the appearance of a precious stone. Glass topped by red almandine garnet is the most common form, with green glass used to imitate emerald, blue to imitate sapphire. Once joined, the stone is faceted and polished.

- **REMARK** These stones were very popular in Britain and the rest of Europe in the Victorian era.



Brilliant




Brilliant



red almandine garnet cemented to
• green glass base

CUSHION-CUT DOUBLET

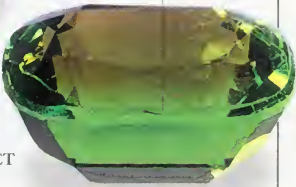

luster and color change at junction of stones
•

ALMANDINE GARNET ON GLASS BASE

SG Variable	RI Variable	DR None	Luster Variable
-------------	-------------	---------	-----------------


Crystal structure Cubic	Composition Calcium iron silicate	Hardness 6½
-------------------------	-----------------------------------	-------------

ANDRADITE GARNET


Garnets containing titanium and manganese are grouped as andradite garnet. The most valuable is demantoid, whose emerald green color is due to the presence of chromium. It has a higher dispersion than diamond and can be recognized by the characteristic "horsetails," which are fine, hairlike inclusions of asbestos. Topazolite, the yellow variety of andradite garnet, varies from pale to dark yellow. Only small crystals are found. Melanite is generally a black form, but can also be dark red.

• **OCCURRENCE** The best demantoid is found in the Urals in Russia and is associated with gold-bearing sands and metamorphic rocks. Other localities include northern Italy, Zaire, and Kenya. Topazolite crystals are found in the Swiss and Italian Alps in metamorphic rocks. Melanite is found in metamorphic rocks and volcanic lavas; fine crystals are found on the island of Elba (Italy) and in France and Germany.

high fire gives flashes of color



BRILLIANT-CUT DEMANTOID

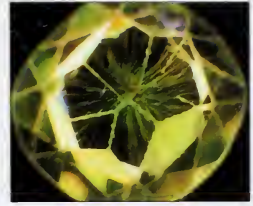

Demantoid garnet has inclusions of fine, hair-like asbestos fibers, known as "horsetails."

"horsetail" inclusions

typically worn facet edges due to softness of demantoid



MIXED-CUT DEMANTOID



BRILLIANT-CUT DEMANTOID


serpentine matrix



DEMANTOID GARNET CRYSTALS IN MATRIX


demantoid crystals

typically black, opaque stone



BRILLIANT-CUT MELANITE


crystal face has vitreous to metallic luster

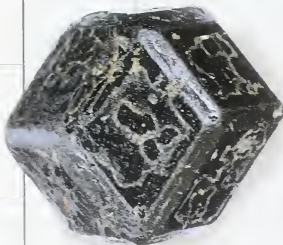

MELANITE CRYSTAL

serpentine rock

yellowish green crust of topazolite crystals

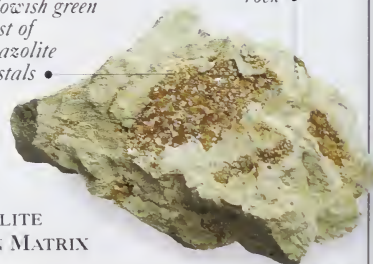

TOPAZOLITE CRYSTALS IN MATRIX



Brilliant

Brilliant

Mixed

SG 3.85	RI 1.85-1.89	DR None	Luster Vitreous to adamantine
---------	--------------	---------	-------------------------------


Crystal structure Cubic	Composition Iron sulfide	Hardness 6
-------------------------	--------------------------	------------

PYRITE

With its brassy yellow color, pyrite is often mistaken for gold (hence its other name, fool's gold). It occurs as cubes or as "pyritohedra," which have twelve faces, each with five edges. Pyrite has been used in jewelry for thousands of years, and examples from the ancient civilizations of the Greeks, Romans, and Incas have been found. Today it is used mainly in costume jewelry, but is brittle and requires careful cutting.

• **OCCURRENCE** Pyrite is found worldwide in igneous, metamorphic, and sedimentary rocks. Fine specimens come from Spain, Mexico, Peru, Italy, and France.

• **REMARK** The name comes from the Greek word *pyr*, meaning fire, since sparks are caused if pyrite is struck with a hammer.

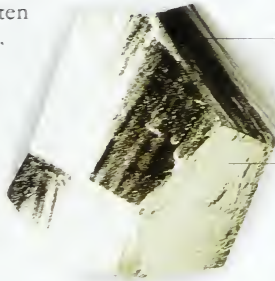

• striations may occur on crystal faces


• "pyritohedral" crystal has twelve faces

PYRITE CRYSTAL

cubic form has six square faces



PYRITE CRYSTAL



Cabochon

Polished

SG 4.90	RI None	DR None	Luster Metallic
---------	---------	---------	-----------------


Crystal structure Cubic	Composition Zinc sulfide	Hardness 3½
-------------------------	--------------------------	-------------

SPHALERITE

Sphalerite, also known as blende, is an important ore of zinc. It is usually very dark brown to black in color, but occasionally transparent, yellowish brown, or green stones are found that can be faceted. Since sphalerite is soft and has perfect cleavage, it is not suitable for jewelry, and is faceted for museums and collectors only.

• **OCCURRENCE** Sphalerite crystals are usually pseudo-octahedral in shape, forming in hydrothermal veins with other minerals, such as galena, quartz, pyrite, and calcite. Transparent, cuttable stones are found in Santander (Spain) and Mexico.

• **REMARK** In the past, sphalerite has often been confused with galena (lead sulfide), to which it is very similar.

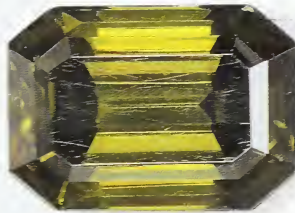


• back facets are doubled

OCTAGONAL STEP CUT

• worn facet edges


• high fire shows rainbow colors

• rich reddish brown crystals



BRILLIANT CUT

• vitreous luster

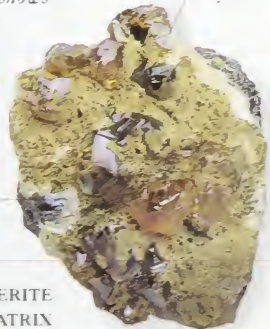

SPHALERITE CRYSTALS IN MATRIX



Brilliant

Brilliant

Mixed

SG 4.09	RI 2.36–2.37	DR None	Luster Metallic to vitreous
---------	--------------	---------	-----------------------------

Crystal structure Cubic	Composition Magnesium aluminum oxide	Hardness 8
-------------------------	--------------------------------------	------------

SPINEL

Spinel is found in a wide range of colors due to the presence of various impurities and is transparent to almost opaque. Red spinel colored by chromium and iron is the most popular, although for many years it was thought to be a variety of ruby. The orange-yellow or orange-red variety is called rubicelle (a diminutive of the French word for ruby). Blue spinel is colored by iron and less commonly by cobalt. Occasionally, inclusions of crystals such as magnetite or apatite may occur, and some Sri Lankan spinels may include zircon crystals surrounded by brown haloes. Star stones are rare, but when cut *en cabochon* may show 4-rayed or 6-rayed stars.

• **OCCURRENCE** Spinel occurs in granites and metamorphic rocks and is often found in association with corundum. Octahedral crystals and waterworn pebbles in a wide range of colors are found in the gem gravels of Myanmar, Sri Lanka, and Madagascar. Other localities include Afghanistan, Pakistan, Brazil, Australia, Sweden, Italy, Turkey, the former USSR, and the USA.

• **REMARK** Synthetic spinel has been manufactured since 1910. It has been used to imitate diamond or colored to imitate stones such as aquamarine and zircon. Blue synthetic spinel, colored by cobalt, has been used to imitate sapphire. The name may derive from the Latin word *spina*, meaning "little thorn," referring to the sharp points on some crystals.



• vitreous luster

• red stones originally known as Balas rubies

OCTAGONAL MIXED CUT



blood red stones sometimes known as ruby spinel •

OVAL BRILLIANT CUT



step cuts clearly visible •

pink stone from Myanmar •

OCTAGONAL STEP CUT

red color due to chromium and iron impurities



bright red color •

• waterworn fragments found in gem gravels of Sri Lanka

CRYSTALS AND FRAGMENTS



AGGREGATE OF SPINEL CRYSTALS

SG 3.60	RI 1.71-1.73	DR None	Luster Vitreous
---------	--------------	---------	-----------------



6-rayed star
brought out by
• cabochon cut

• asterism is
rare in spinel

STAR-STONE CABOCHON



brilliant-cut
• crown facets

• step-cut
pavilion
facets

CUSHION MIXED CUT



pinkish mauve
color •

• liquid-filled
inclusions

CUSHION MIXED CUT



pale pinkish
purple stone from
Sri Lanka •

OCTAGONAL STEP CUT

blue
gahnspinel
contains zinc •

gahnspinel is
named after
Swedish chemist
• J.G. Gahn



MIXED-CUT GAHNOSPINEL



pale pinkish
• mauve color

• synthetics have
been manufactured
since 1910

BRILLIANT-CUT
SYNTHETIC SPINEL

dark, zinc-rich
• spinel crystals



Brilliant



Brilliant



Cushion



Step



Cabochon



Mixed

quartz matrix •

SPINEL CRYSTALS
IN MATRIX



Crystal structure Cubic

Composition Calcium fluoride

Hardness 4

FLUORITE

Formerly called fluorspar, fluorite has limited use as a gemstone because it is relatively soft and therefore easily scratched. However, the wide range of colors (including yellow, blue, pink, purple, and green), the frequent incidence of more than one color in a single specimen, and zoning or patchy distribution of color make it an interesting stone. Despite its fragility and perfect octahedral cleavage, stones are faceted (usually for collectors) and can be polished very brightly. Cabochons of fluorite have been capped with rock crystal (see p.81) to protect them from scratches.

• **OCCURRENCE** Localities include Canada, the USA (where some of the largest crystals are found), South Africa, Thailand, Peru, Mexico, China, Poland, Hungary, Czechoslovakia, Norway, England, and Germany. Pink octahedral crystals are found in Switzerland. A purple- and yellow-banded variety called Blue John occurs in England.

• **REMARK** The ancient Egyptians used fluorite in statues and to carve scarabs, and the Chinese have used it in carvings for more than 300 years. In the 18th century, fluorite was powdered in water to relieve the symptoms of kidney disease.



bright golden
• yellow color

• stones are faceted for collectors only

OCTAGONAL STEP CUT


golden yellow cubic fluorite crystals •



iron ore matrix •

FLUORITE CRYSTALS IN MATRIX

twinned crystals •

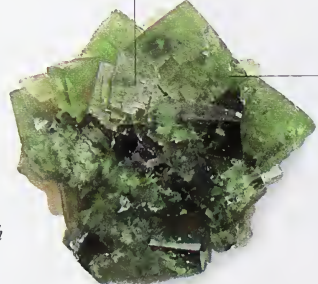

green cubic crystals •

FLUORITE CRYSTALS IN MATRIX



fluorite is soft and difficult to facet

• pale bluish green color

OCTAGONAL STEP CUT

black hematite inclusions •



colorless cubic crystals •

FLUORITE CRYSTALS IN MATRIX

fluorite may be mistaken for glass, feldspar, beryl, or quartz •



CUSHION FANCY CUT

SG 3.18

RI 1.43

DR None

Luster Vitreous

pale pink color

specks of black hematite



CUSHION STEP CUT

cubic fluorite crystals

tiny white quartz crystals




FLUORITE CRYSTALS IN MATRIX

cut stones may be highly polished and bright

mauve cubic fluorite crystals

white quartz crystals

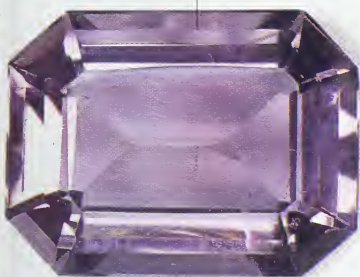

OCTAGONAL STEP CUT




FLUORITE CRYSTALS INTERGROWN WITH QUARTZ

yellow and purple banding

smooth cleavage surface

massive habit

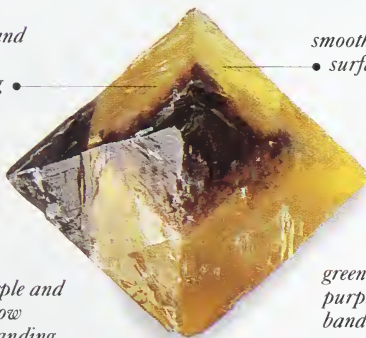

purple and yellow banding

green and purple banding



CLEAVED FLUORITE CRYSTAL

FLUORITE ROUGH

BLUE JOHN VASE
This attractive banded variety of fluorite has been carved since Roman times. The ancient Romans believed that drinking alcohol from a cup made of Blue John would allow the drinker to imbibe without becoming drunk.



Cushion



Step



Mixed



Cameo


Crystal structure Cubic	Composition Sodium aluminum silicate	Hardness 5½
-------------------------	--------------------------------------	-------------

SODALITE

Sodalite, whose name reflects its sodium content, is found in all shades of blue and is a major constituent of the rock lapis lazuli (opposite), so the two are easily confused. However, unlike lapis lazuli, sodalite very rarely contains brassy pyrite specks, and it has a lower specific gravity. Sodalite may contain white streaks of the mineral calcite, and can be carved for use in jewelry.

• **OCCURRENCE** Sodalite is usually found as masses in igneous rocks. Crystals are very rare, but twelve-sided crystals have been found in the lavas of the volcano Vesuvius in Italy, although they are too small to be used in jewelry. Other localities include Brazil, Canada, India, Namibia, and the USA.

• **REMARK** The most important commercial source of sodalite is Bancroft in Ontario, Canada. It was discovered during a royal visit by Princess Margaret of England. For this reason, sodalite from Bancroft is sometimes called Princess Blue.

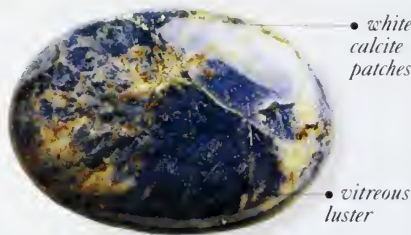

CABOCHON




OVAL BRILLIANT CUT



POLISHED SODALITE



SODALITE ROUGH



Cabochon

Cameo

SG 2.27	RI 1.48 (mean)	DR None	Luster Vitreous to greasy
---------	----------------	---------	---------------------------

Crystal structure Cubic	Composition Complex silicate	Hardness 6
-------------------------	------------------------------	------------


HAUYNE

Hauyne forms part of lapis lazuli (opposite). It is usually intergrown with other minerals and is seldom found as individual crystals. Hauyne has perfect cleavage, making cutting difficult, so it is faceted primarily for collectors.

• **OCCURRENCE** Hauyne is found as small, rounded grains in volcanic rocks. Ancient volcanoes of Germany and Morocco are the best known sources.



BRILLIANT CUT




patches of crystals form in matrix



Brilliant

HAUYNE CRYSTALS IN MATRIX

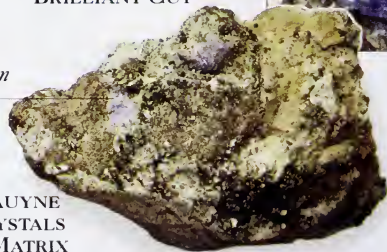

lilac hauyne crystals

matrix

SG 2.40	RI 1.50 (mean)	DR None	Luster Vitreous to greasy
---------	----------------	---------	---------------------------

Crystal structure Various

Composition Rock containing lazurite and other minerals

Hardness 5½

LAPIS LAZULI (LAZURITE)

Lapis lazuli is a blue rock made up of several different minerals, including lazurite, sodalite, hauyne, calcite, and pyrite. The composition and color of lapis lazuli varies, but it is the intense dark blue, with minor patches of white calcite and brassy yellow pyrite, that is considered to be the best quality.

• **OCCURRENCE** Lapis lazuli is usually found as boulders or within limestones.

The best quality lapis lazuli is from Afghanistan and has been used in many famous pieces, including the mask of Tutankhamen. Argentinian lapis lazuli is also of a high quality. A pale blue variety occurs in the former USSR and in Chile. Lapis lazuli from the USA is a darker shade of blue; Canadian specimens are lighter blue.

• **REMARK** Lapis lazuli has been worn in the belief that it will protect the wearer from evil. It has been imitated by stained jasper and by paste with inclusions of copper. Imitation lapis lazuli produced by Pierre Gilson in France has a composition very similar to natural lapis lazuli.

BEAD NECKLACE
Specks of pyrite and streaks of calcite are visible in these lapis lazuli beads.



BUDDHA CARVING
This carving is made from the highest quality lapis lazuli from Afghanistan.




• pale patches of calcite

brassy pyrite


main ingredient of imitation stone
• is lazurite

brassy pyrite
• specks




imitation stone
• softer than natural lapis lazuli

GILSON IMITATION CABOCHON

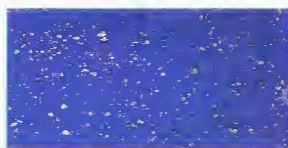

GILSON IMITATION SLAB

veins of brassy pyrite

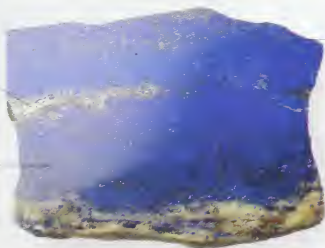


uneven fracture

blue color due to presence of lazurite

rock is sawn open and ground with grits to give flat surface

POLISHED LAPIS LAZULI SLAB

streaks of calcite

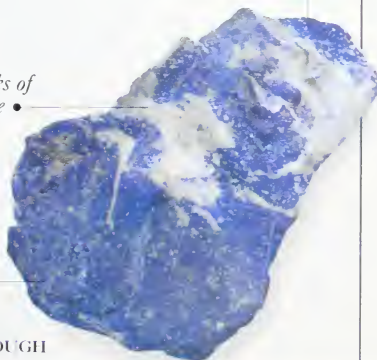

uneven fracture

LAPIS LAZULI ROUGH



Cabochon



Cameo



Polished

SG 2.80

RI 1.50 (mean)

DR None


Luster Vitreous to greasy

Crystal structure Tetragonal	Composition Calcium tungstate	Hardness 5
------------------------------	-------------------------------	------------

SCHEELITE

Scheelite is quite soft and is therefore faceted only for collectors of the unusual. It has high dispersion and good fire, and varies in color from a pale yellowish white to brown. Colorless synthetic scheelite is used to imitate diamond but can be distinguished by its birefractance. It may also be colored by trace metals in order to imitate other gemstones.

• **OCCURRENCE** Scheelite is found in pegmatites and metamorphic rocks. Very large crystals over 1 lb (0.5 kg) have been collected in Brazil, but generally, larger crystals are not sufficiently transparent to be faceted. Other localities include Australia, Italy, Switzerland, Sri Lanka, Finland, France, and England.

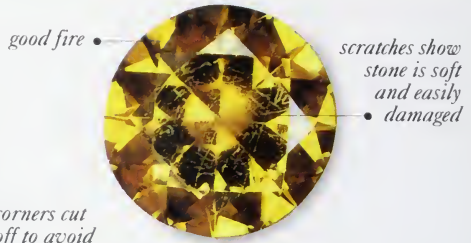

BRILLIANT CUT creamy yellow scheelite crystals



SQUARE STEP CUT

SCHEELITE CRYSTALS IN MATRIX



SG 6.10	RI 1.92-1.93	DR 0.017	Luster Vitreous to adamantine
---------	--------------	----------	-------------------------------


Crystal structure Tetragonal	Composition Tin oxide	Hardness 6½
------------------------------	-----------------------	-------------

CASSITERITE

Cassiterite is the principal ore of tin. It is usually recovered from mines as black opaque grains, which are of little use in jewelry. Crystals are generally short, stubby prisms, though transparent, reddish brown crystals with adamantine luster are sometimes found, and faceted for collectors. They could be confused with diamond, brown zircon, and titanite, but cassiterite has higher specific gravity and distinct dichroism.


• **OCCURRENCE** Cassiterite occurs in pegmatites and can be washed into alluvial deposits. Localities include the Malay Peninsula, England, Germany, Australia, Bolivia, Mexico, and Namibia.

• **REMARK** The name "cassiterite" comes from the Greek word, *kassiteros*, meaning tin.

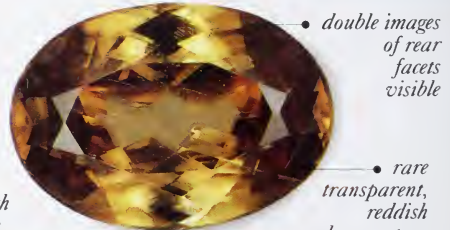


colorless stone with yellowish tinge

OVAL BRILLIANT CUT



opaque, short, prismatic crystals

ROUND BRILLIANT CUT

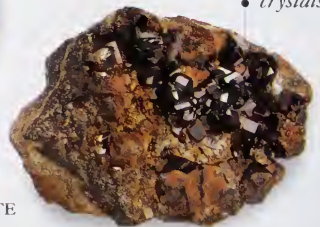

CASSITERITE CRYSTALS IN MATRIX



SG 6.95	RI 2.00-2.10	DR 0.100	Luster Adamantine
---------	--------------	----------	-------------------

Crystal structure Tetragonal	Composition Complex silicate	Hardness 6
------------------------------	------------------------------	------------


SCAPOLITE

Also called wernerite after the German geologist A.G. Werner, scapolite ranges in color from pink, purple, blue, yellow, and gray to colorless.

These colors reflect variations in composition, from sodium-rich to calcium-rich. Crystals are found as prisms that resemble sticks, giving rise to the name "scapolite," derived from the Greek words *scapos*, meaning rod, and *lithos*, meaning stone.

• **OCCURRENCE** Scapolite is found as crystals in pegmatites and in metamorphic rocks like mica schist and gneiss. It also occurs in massive form. Localities include Brazil, Myanmar, Canada, Kenya, and Madagascar.

• **REMARK** A cat's-eye effect can be seen in some pink and purple stones. Scapolite may easily be confused with amblygonite, chrysoberyl, and golden beryl.

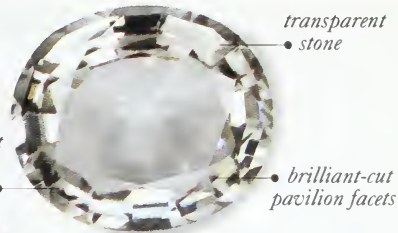

step-cut crown facets

transparent stone

brilliant-cut pavilion facets

MIXED CUT

variations in sodium and calcium in stone cause gray tinges



dark mineral inclusions

CABOCHON



massive yellowish rough

MASSIVE SCAPOLITE



pale yellow variety

STEP CUT



Brilliant



Step

SG 2.70	Rl 1.54-1.58	DR 0.020	Luster Vitreous
---------	--------------	----------	-----------------


Crystal structure Tetragonal	Composition Titanium oxide	Hardness 6
------------------------------	----------------------------	------------

RUTILE

Natural rutile has many times the fire shown by diamond, but it is masked by the red, brown, or black body color. The black material has been used in mourning jewelry, but rutile is most usually seen as rich, reddish brown, needlelike inclusions within quartz or within other stones, where the rutile crystals create a star effect by reflecting light.


• **OCCURRENCE** Igneous and metamorphic rocks and alluvial deposits in Australia, Brazil, the USA, Italy, Mexico, and Norway.

metallic, needlelike rutile inclusions

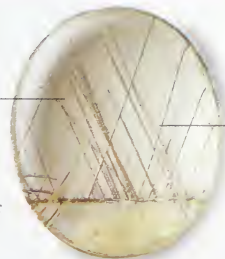

stone is known as sagenite when inclusions intersect at 60°

sprays of rutile inclusions



POLISHED QUARTZ

matrix covered by crystalline rutile

QUARTZ CABOCHON



RUTILE ROUGH



Baguette



Mixed

SG 4.25	Rl 2.62-2.90	DR 0.287	Luster Vitreous to metallic
---------	--------------	----------	-----------------------------

Crystal structure Tetragonal

Composition Zirconium silicate


Hardness 7½

ZIRCON

Zircon is most famous for its colorless stones, which closely resemble diamonds and have been used both intentionally and mistakenly in their place. Although colorless when pure, impurities will produce yellow, orange, blue, red, brown, and green varieties. Brown stones from Thailand, Vietnam, and Kampuchea are usually heat treated to change them into the colorless or blue stones popular in jewelry. Blue stones that revert to brown will regain the blue if reheated. Blue zircon reheated in the presence of oxygen will change to golden yellow. Zircon may be distinguished from diamond by its double refraction and by wear and tear on its facet edges. It has been imitated by both colorless glass and synthetic spinel. Some zircon contains radioactive thorium and uranium, which eventually break down the crystal structure. Decayed stones are known as "low" zircon, with a "metamict" structure; undamaged material is "high" zircon.

• **OCCURRENCE** Gem-quality crystals are usually found as pebbles in alluvial deposits. Sri Lanka has been a source of gem material for over 2,000 years; other localities include Myanmar, Thailand, Cambodia, Vietnam, Kampuchea, Australia, Brazil, Nigeria, Tanzania, and France.

• **REMARK** Zircon was believed to provide the wearer with wisdom, honor, and riches, and loss of luster was said to warn of danger. The name is from the Arabic *zargun*, which derives from the Persian for "gold color."

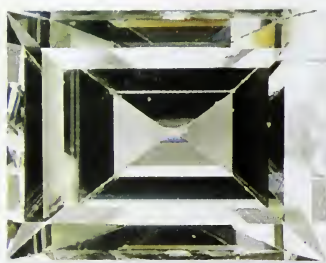

RECTANGULAR STEP CUT


• colorless zircon produced by heating reddish brown material



OVAL BRILLIANT CUT

green stones are often decayed
• "low" zircon

waterworn pebble with polished surface

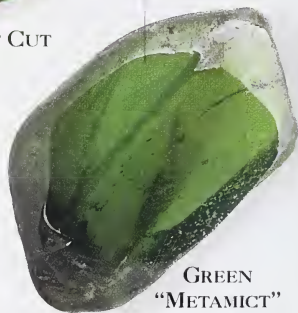

GREEN "METAMICT" PEBBLE

natural golden yellow color




OVAL MIXED CUT

zircon crystal



pegmatite matrix


dark biotite mica

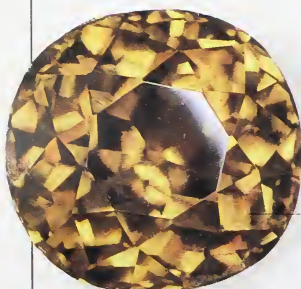

CUSHION BRILLIANT CUT

golden brown is most popular color for zircon jewelry

CRYSTALS IN MATRIX

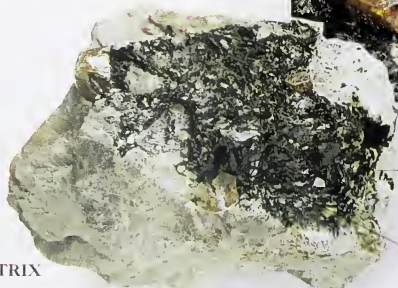

SG 4.69

RI 1.93-1.98

DR 0.059

Luster Resinous to adamantine



*doubling of
back facets*

*stone heat
treated to
achieve blue
color*

ROUND BRILLIANT CUT



*uneven color
distribution*


*yellowish
reflections*

*smooth
surface*

ROUND BRILLIANT CUT



**WATERWORN
PEBBLES**

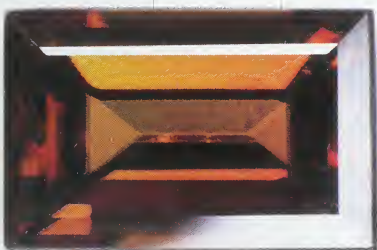

*doubling of
back facets*

*untreated reddish
brown color*

RECTANGULAR STEP CUT



*green zircon may
have "metamict"
structure*

*dark golden
brown stone*



**CUSHION
BRILLIANT CUT**

*double
pyramidal
ends*




*leaf green
mixed-cut
zircon*

ZIRCON RINGS

Its adamantine luster, strong birefractance, hardness, and vast color range make zircon an attractive stone when set in a ring. Unfortunately, its use is restricted by its brittle nature; cutting is difficult and the cut stone is easily damaged.



*yellow zircon
in center, flanked by
pale blue-violet stones*

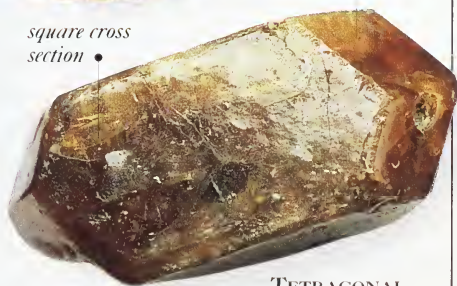

*square cross
section*

**TETRAGONAL
ZIRCON CRYSTAL**



Brilliant



Cushion



Zircon



Baguette



Mixed

Crystal structure Tetragonal	Composition Calcium aluminum silicate	Hardness 6½
------------------------------	---------------------------------------	-------------

VESUVIANITE

This mineral was first discovered on the Italian volcano Vesuvius as small, perfect crystals. Also called idocrase, it may be red, yellow, green, brown, or purple. It is seldom used in jewelry, but it may be cut for collectors. Crystals are usually thick prisms with a square cross section.

• **OCCURRENCE** There are several varieties: californite from California is green; rare blue cyprine is found in Norway; yellowish green xanthite is from New York; green wiluite crystals are from the former USSR. Other localities include Austria, Canada, Italy, and Switzerland.

• **REMARK** Vesuvianite may be confused with demantoid garnet, diopside, epidote, smoky quartz, tourmaline, zircon, and peridot.



Brilliant



Step




Mixed



CALIFORNITE CABOCHON



VESUVIANITE CRYSTAL

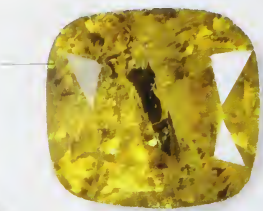

CUSHION CUT



VESUVIANITE CRYSTALS

SG 3.40	RI 1.70–1.75	DR 0.005	Luster Vitreous to adamantine
---------	--------------	----------	-------------------------------

Crystal structure Tetragonal	Composition Sodium aluminum beryllium silicate	Hardness 6
------------------------------	--	------------

TUGTUPITE

Tugtupite was first discovered in 1960 in Greenland, where it is carved for jewelry. Colors include dark red to bright pink and shades of orange. It may look mottled. When it is placed in the dark, the paler parts of the rock fade to white, but exposure to light restores the color.

• **OCCURRENCE** Tugtupite is found as massive opaque material in pegmatite veins. It also occurs in northern Russia.

• **REMARK** The name derives from its occurrence in Tugtup, Greenland, and means “reindeer stone.”



Cabochon



Cameo



Polished



POLISHED STONE



TUGTUPITE ROUGH

SG 2.40	RI 1.49–1.50	DR 0.006	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Hexagonal

Composition Beryllium aluminum silicate

Hardness 7½

EMERALD (BERYL)

Emerald derives its beautiful green color from the presence of chromium and vanadium. Emeralds are rarely flawless, so stones are often oiled to fill and disguise cracks, hide flaws, and enhance color. To minimize the loss of material, the step cut (also called the emerald cut) is commonly used, but ancient engravings are known, and cameos, intaglios, and beads can make the best of a flawed stone.

• **OCCURRENCE** Found in granites, pegmatites, and schists, as well as alluvial deposits, the finest emeralds are from Colombia. Other sources are Austria, India, Australia, Brazil, South Africa, Egypt, the USA, Norway, Pakistan, and Zimbabwe.

• **REMARK** Most emeralds used in historical jewelry were from Cleopatra's mines in Egypt, which now yield only poor-quality emeralds.



inclusions make stone look cloudy

PENDELOQUE




Tremolite inclusions may be found in emeralds as short rods or long fibers.



POLISHED PEBBLE

stone is semi-translucent


unusual domed front

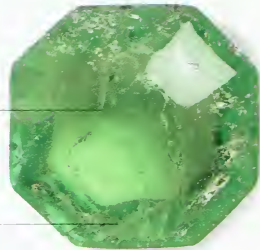


OCTAGONAL CABOCHON

group of inclusions

brilliant-cut crown facets
cracks and inclusions common in emerald

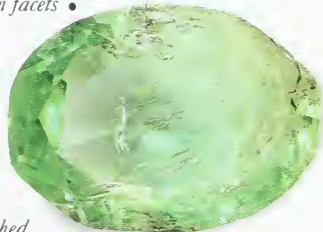

MIXED CUT



Synthetic emeralds have characteristic veil or wisp-like, liquid-filled inclusions.



good emerald-green color

SYNTHETIC PENDELOQUE



scratched prism face


HEXAGONAL CRYSTAL

prism has flat ends

crystals often found worn or etched
white calcite crystals




CRYSTAL IN MATRIX



Pendeloque



Step



Step



Cabochon

SG 2.71

RI 1.57–1.58

DR 0.006

Luster Vitreous

Crystal structure Hexagonal

Composition Beryllium aluminum silicate

Hardness 7½

AQUAMARINE (BERYL)


In the 19th century the preferred color for aquamarine was sea green, and indeed the name itself means seawater. Today the most valued colors are sky blue and dark blue. Aquamarine is dichroic, appearing blue or colorless as the stone is viewed from different angles.

Gem-quality aquamarine is found as hexagonal crystals, which may be up to 39 in (1 m) long and flawless, with striations along the length of the crystal. Aquamarine is often cut with the table facet parallel to the length of the crystal in order to emphasize the deepest coloration.

• **OCCURRENCE** The best of the gem-quality aquamarine is found in Brazil, where it occurs in pegmatites and alluvial deposits of gravel, locally called *cascalho*. Other localities include the Urals (Russia), Afghanistan, Pakistan, India, and, more recently exploited, Nigeria. A dark blue variety occurs in Madagascar.

• **REMARK** Almost all aquamarine on the market has been heat treated to enhance its color. Care must be taken not to overheat the stones, as they may become colorless.

untreated, sky blue stone

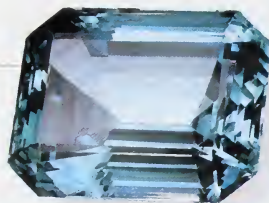

OCTAGONAL STEP CUT

cat's-eye effect visible on cabochon




CABOCHON

fibrous habit

step cut typical for aquamarine

heat treatment has lightened color

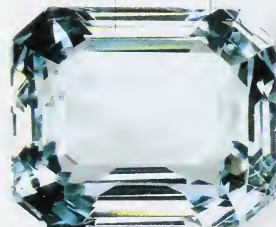


OCTAGONAL STEP CUT

untreated stone has greenish tinge



OCTAGONAL STEP CUT

many small facets

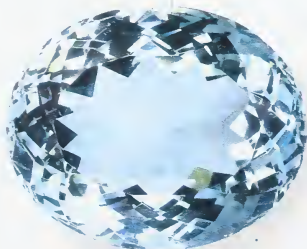

BRILLIANT CUT

poor-quality flawed stone



popular aquamarine color

crystal is too green and will require heat treatment



AQUAMARINE CRYSTALS



Brilliant



Step



Cabochon

SG 2.69

RI 1.57–1.58

DR 0.006

Luster Vitreous

Crystal structure Hexagonal	Composition Beryllium aluminum silicate	Hardness 7½
-----------------------------	---	-------------

HELIODOR (BERYL)

Heliodor, a yellow or golden yellow form of beryl, has always been linked with the sun. Gem-quality specimens are occasionally found, but more often inclusions of fine, slender tubes are present that are visible to the naked eye.

• **OCCURRENCE** Heliodor is found associated with aquamarine in granitic pegmatites. The finest quality stones are found in the Urals (Russia). Brazilian heliodor is often a pale yellow and is step cut to give depth of color. Heliodor from Madagascar is a finer color. Other localities include the Ukraine, Namibia, and the USA.

glowing, golden yellow color




SCISSORS CUT

heart-shaped cut keeps maximum possible weight



FANCY CUT

bevel-edged crystal with flat ends

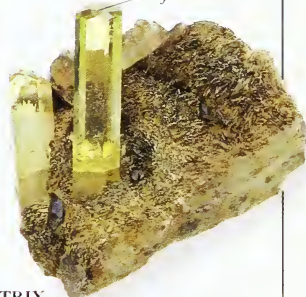

HELIODOR CRYSTALS IN MATRIX



Marquise



Table



Baguette

SG 2.80	Rl 1.57–1.58	DR 0.005	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Hexagonal	Composition Beryllium aluminum silicate	Hardness 7½
-----------------------------	---	-------------

GOSHENITE (BERYL)


Goshenite is the pure, colorless variety of beryl. It has been used to imitate diamond or emerald, by placing silver or green-colored metal foil behind a cut goshenite gemstone, then placing the stone in a closed setting so that the foil cannot be detected.

• **OCCURRENCE** Goshenite is named after Goshen, Massachusetts, where it was first found. Present localities include Canada, Brazil, and the former USSR.

• **REMARK** Pale and colorless beryl was once used for the lenses in spectacles, thus the German word for spectacles, *brille*, may have been derived from the word “beryl.”

stones are transparent

vitreous luster

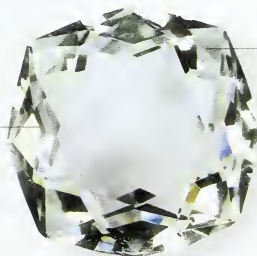


FANCY CUT

spiky inclusions are common



BRILLIANT CUT

crystals have hexagonal outline

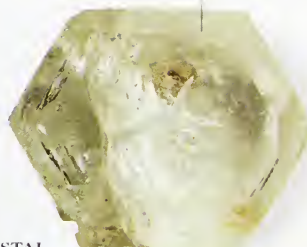

TABULAR CRYSTAL



Brilliant



Step



Mixed

SG 2.80	Rl 1.58–1.59	DR 0.008	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure	Hexagonal	Composition	Beryllium aluminum silicate	Hardness	7½
-------------------	-----------	-------------	-----------------------------	----------	----

MORGANITE (BERYL)

Colored by manganese impurities, the pink, rose, peach, and violet varieties of beryl are called morganite, after banker and gem enthusiast, J. Pierpoint Morgan.

Morganite tends to occur as short and stubby (tabular) prisms and is dichroic, showing either two shades of the body color or one shade and colorless.

• **OCCURRENCE** The first morganite to be described was a pale rose-colored specimen from California, where it occurred with tourmaline. Some of the finest morganite is from Madagascar; Brazil produces pure pink crystals, as well as some containing aquamarine and morganite in the same crystal. Other localities include Elba (Italy), Mozambique, Namibia, Zimbabwe, and (recently discovered) Pakistan.

• **REMARK** Stones with a yellow or orange tinge may be heat treated for a purer pink.



• typical pale pink color

• many small facets

• OVAL MIXED CUT


• vitreous luster



• BRILLIANT CUT



• DROP-SHAPED CUT

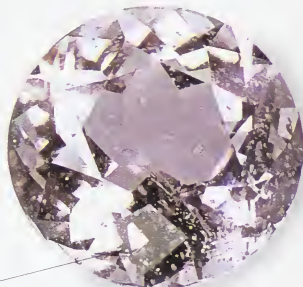

• ROUND BRILLIANT CUT


• pink color from manganese



• MORGANITE ROUGH



• Brilliant



• Step

• liquid-filled inclusions

SG	2.80	Ri	1.58–1.59	DR	0.008	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Hexagonal	Composition	Beryllium aluminum silicate	Hardness	7½
-------------------	-----------	-------------	-----------------------------	----------	----

RED BERYL

Very rare, and seldom seen as a cut stone, red beryl nonetheless has an unusually intense color, due to the presence of manganese.


• **OCCURRENCE** Found in rhyolites in the Thomas Mountains and Wah Wah Mountains in Utah.

• **REMARK** Red beryl is also called bixbite (not to be confused with bixbyite, a manganese iron oxide).



• Brilliant

• prismatic red beryl crystal

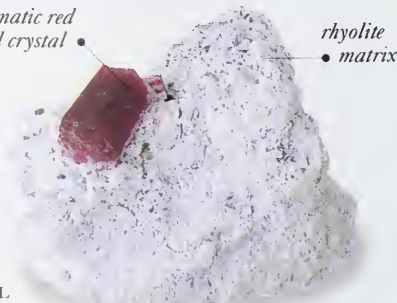

• rhyolite matrix

• CRYSTAL IN MATRIX

SG	2.80	Ri	1.58–1.59	DR	0.008	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure Hexagonal

Composition Calcium phosphate

Hardness 5

APATITE

With a value of only 5 on the Mohs scale of hardness, apatite is seldom faceted as a gemstone, except for collectors. However, when cut correctly, stones are bright with strong colors. Transparent to opaque, apatite occurs as colorless, yellow, blue, violet, or green hexagonal prisms or tabular crystals.

• **OCCURRENCE** Apatite is an abundant mineral found in many types of rock, but most gem-quality material is associated with pegmatites. Blue apatite from Myanmar is strongly dichroic, showing colorless or blue when viewed from different directions. Fibrous blue apatite from Myanmar and Sri Lanka may be cut *en cabochon* to show a cat's-eye. Chatoyant stones are also found in Brazil, along with yellow, blue, and green varieties. Other localities include the Kola Peninsula (Russia), Canada, East Africa, Sweden, Spain, and Mexico.

• **REMARK** Spanish apatite is often called "asparagus stone," because of its yellowish green color.



• blue-gray fibrous apatite

chipped facet edge, due to brittleness of stone

CAT'S-EYE CABOCHON



• black inclusions

ROUND BRILLIANT CUT




OCTAGONAL STEP CUT




• gray-green color

OCTAGONAL STEP CUT

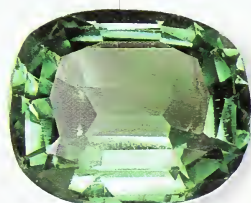

stones are opaque to transparent

CUSHION MIXED CUT

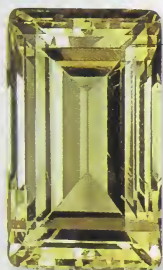

• cut stones are bright and strongly colored

RECTANGULAR STEP CUT



• pyramidal end

• yellow hexagonal prism

APATITE CRYSTAL

colorless apatite crystal



Baguette



Step



Step



Cabochon

quartz and gibertite matrix



APATITE CRYSTALS IN MATRIX

SG 3.20

RI 1.63-1.64

DR 0.003

Luster Vitreous

Crystal structure	Hexagonal	Composition	Beryllium magnesium aluminum oxide	Hardness	8
-------------------	-----------	-------------	------------------------------------	----------	---

TAAFFEITE

Taaffeite is very rare, and is unique in that it is the only gemstone not recognized as a new mineral species until it had been faceted. The first specimen (see right) was found by Count Taaffe in Ireland, in a jeweler's box of stones. It looked like spinel, had a pale mauve tinge, and was cushion cut, but was eventually found to be a new, doubly refractive (rather than singly refractive like spinel) mineral. Since then, more specimens have been found; these range in hue from red to blue to almost colorless.


- **OCCURRENCE** Taaffeite occurs in Sri Lanka, China, and the former USSR.
- **REMARK** No imitation taaffeites appear to exist.



• first specimen to be identified

• grayish mauve color


CUSHION CUT

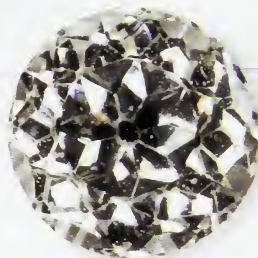

transparent stone

vitreous luster

semi-translucent pebble

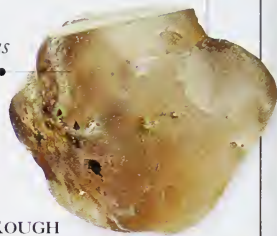

ROUND BRILLIANT CUT

TAAFFEITE ROUGH



Brilliant



Brilliant



Cushion

SG 3.61

RI 1.72-1.77

DR 0.004

Luster Vitreous

Crystal structure	Hexagonal	Composition	Barium titanium silicate	Hardness	6½
-------------------	-----------	-------------	--------------------------	----------	----

BENITOITE

The blue crystals of benitoite were discovered in 1906 by a mineral prospector who mistook them for sapphires. Crystals are shaped like flattened triangles and have a strong dispersion similar to diamond, but this is masked by the color. Dichroism is strong: the stone appears blue or colorless when viewed from different angles. Colorless crystals occur but are rarely faceted.

- **OCCURRENCE** Crystals occur in veins in blue schists. The sole source is in San Benito County, California, after which the stone is named.



pyramidal end

appears colorless at certain angles




BRILLIANT CUT

• unevenly distributed color

BRILLIANT CUT

conchoidal fracture

blue benitoite crystals

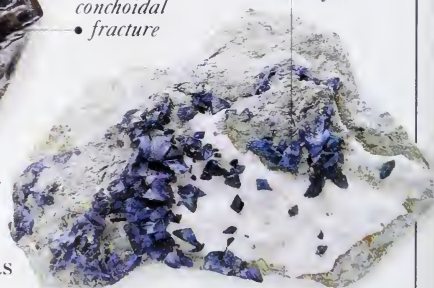

BENITOITE CRYSTAL FRAGMENT

BENITOITE CRYSTALS IN MATRIX



Brilliant



Brilliant



Cushion

SG 3.67

RI 1.76-1.80

DR 0.047

Luster Vitreous

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

ROCK CRYSTAL (QUARTZ)

Colorless and transparent, rock crystal is the most widely distributed variety of quartz, one of the most common minerals of the Earth's crust. The crystals are usually found as colorless hexagonal prisms, with pyramidal ends and striations perpendicular to their length; they are often twinned. Cleavage is poor and fracture conchoidal.

• **OCCURRENCE** Although found worldwide, the most important sources of rock crystal are in Brazil. Other localities include the Swiss and French Alps, where fine crystals occur, and Madagascar, the former USSR, and the USA.

• **REMARK** The name "quartz" comes from the Greek word *krystallos*, meaning ice, because it was thought that quartz was ice formed by the gods. Since the Middle Ages, crystal balls made of rock crystal have been used to predict the future. Today, rock crystal is used in lamps, lenses, and the manufacture of glass and precision instruments. Synthetic rock crystal has been produced since 1950 for use in watches.

POLISHED ROCK CRYSTAL

This flat disk of polished rock crystal has been engraved and set with an enameled monogram of blue, black, and gold.



transparent stone •

facet edges may wear on older stones •

ROUND BRILLIANT CUT

vitreous luster •



CUSHION BRILLIANT CUT

drilled hole •

carved grooves •



POLISHED BEAD

colorless through yellowish shading •

striations on prism faces •

hexagonal crystals •

pyramidal ends •



SINGLE CRYSTAL



CRYSTALS



Bead



Cameo



Brilliant



Step

SG 2.65

RI 1.54-1.55

DR 0.009

Luster Vitreous

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

AMETHYST (QUARTZ)

Crystalline quartz in shades of purple, lilac, or mauve is called amethyst, a stone traditionally worn to guard against drunkenness and to instill a sober and serious mind. Amethyst is dichroic, showing a bluish or reddish purple tinge when viewed from different angles. Usually faceted as a mixed or step cut, amethyst has distinctive inclusions that look like tigerstripes, thumbprints, or feathers. Some amethyst is heat treated to change the color to yellow, producing citrine (see opposite). Crystals that are part citrine and part amethyst are called ametrine.

- **OCCURRENCE** Amethyst is found in alluvial deposits or in geodes. Some of the largest geodes containing amethyst are in Brazil. Amethyst from the Urals (Russia) has a reddish tinge; Canadian amethyst is violet. Other localities include Sri Lanka, India, Uruguay, Madagascar, the USA, Germany, Australia, Namibia, and Zambia.
- **REMARK** Poor quality material is often tumbled to make beads. If a stone is pale it may be set in a closed setting or have foil placed behind it to enhance the color. Amethyst has been imitated by glass and synthetic corundum.



Characteristic tigerstripe inclusions are caused by parallel, liquid-filled canals.

TIE PIN

Amethyst jewelry was popular in the late 19th century. This handsome gold tie pin is adorned with an octagonal step-cut amethyst.



HEXAGONAL
MIXED CUT

purple stone
from Russia

polished,
convex
front

alternate colors
due to twinning



AMETHYST CRYSTAL SLICE

slice cut
perpendicular
to length of
crystal



OVAL MIXED CUT

typical
purplish
violet
color

color darkens
toward tip of
amethyst crystal



AMETHYST CRYSTALS
ASSOCIATED WITH
ROCK CRYSTAL



Baguette



Bead



Mixed

SG 2.65

RI 1.54–1.55

DR 0.009

Luster Vitreous

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

CITRINE (QUARTZ)

Citrine is the yellow or golden yellow variety of quartz. The yellow coloration, due to the presence of iron, is also responsible for the name, derived from the word *citrus*.

Natural citrine is usually a pale yellow, but rare; most citrine on the market is heat-treated amethyst (see opposite).

• **OCCURRENCE** Gem-quality citrine is extremely rare. The best material is found in Brazil, Spain, Madagascar, and the former USSR.

• **REMARK** Citrine has been used to imitate topaz (see pp.106–107) and was once called Brazilian topaz.

orange tinge often seen in citrine



MIXED CUT



MIXED CUT
PENDELOQUE

yellow color due to presence of iron

pyramidal end



CITRINE CRYSTAL



Brilliant



Pendeloque



Cabochon

SG 2.65

RI 1.54–1.55

DR 0.009

Luster Vitreous

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

ROSE QUARTZ

Pink or peach-colored quartz is called rose quartz and is mainly used in decorative carvings. Its color is thought to be due to the presence of small amounts of titanium.

Crystals of rose quartz are very rare; more usually, massive lumps are found, which can be carved or cut *en cabochon* or as beads. Transparent material is uncommon; it is usually cloudy or cracked, partly because it is so brittle. Rutile inclusions in rose quartz may produce a star effect when the stone is cut *en cabochon*.

• **OCCURRENCE** Rose quartz is found in pegmatites. The best material is from Madagascar, but Brazil produces a greater quantity. Other sites are the USA (Colorado), the former USSR, Scotland, and Spain.

ROSE QUARTZ SEAL

Intaglio seals such as this, made with an incised rather than a raised design, were very popular in ancient Rome.



rose quartz crystals



BRILLIANT CUT

pale pink stone from Madagascar

crystals are typically cloudy



ROSE QUARTZ
CRYSTALS



Bead



Mixed



Cameo

SG 2.65

RI 1.54–1.55

DR 0.009

Luster Vitreous

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

BROWN QUARTZ


Brown quartz includes crystalline quartz of a light brown or dark brown color, grayish brown "smoky" quartz, and the black variety called morion. Brown or smoky quartz from the Cairngorm Mountains of Scotland is called cairngorm. When irradiated, colorless quartz may change color to grayish brown, suggesting that brown quartz may have been formed by natural radiation within the ground. Brown quartz crystals are hexagonal prisms with pyramidal ends, in which inclusions of the mineral rutile may be present.

- **OCCURRENCE** Crystals weighing as much as 650 lb (300 kg) have been found in Brazil. Other localities include Madagascar, the Swiss Alps, the USA (Colorado), Australia, and Spain.
- **REMARK** Much of the smoky quartz on the market is in fact irradiated rock crystal. Brown quartz has been confused with andalusite, axinite, idocrase, and brown tourmaline.



• color may be due to natural irradiation

FANCY-CUT SMOKY QUARTZ

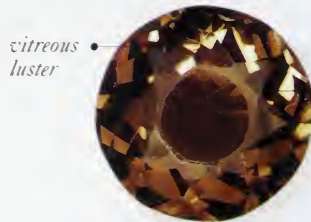

• vitreous luster

• characteristic grayish brown color

• pyramidal end

BRILLIANT-CUT SMOKY QUARTZ



SNUFF BOTTLE
Like most varieties of quartz, smoky quartz may be polished and fashioned in many ways. This snuff bottle, with red stopper and spoon, is of Chinese origin.

• opaque hexagonal prism

• horizontal striations on prism face



MORION CRYSTAL

• polishing of one facet makes interior visible

INTAGLIO SEAL

This incised intaglio was carved in smoky quartz and has been set in a polished octagon of obsidian, which is a natural volcanic glass. Intaglio seals were popular with the ancient Romans. This piece depicts a Roman wearing a helmet.

• incised image



WATERWORN CAIRNGORM PEBBLE



Mixed



Cameo

• smoky quartz intaglio

SG 2.65	RI 1.54-1.55	DR 0.009	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

AVENTURINE QUARTZ

This form of quartz contains inclusions of small crystals that reflect light and give a range of colors – depending on the nature of the inclusion. Green aventurine quartz has platy inclusions of green fuchsite mica; pyrite inclusions give a brown color; a greenish brown color may be due to the mineral goethite. Other inclusions result in bluish white, bluish green, or orange varieties.

- **OCCURRENCE** Aventurine quartz is found in Brazil, India, and Russia. Other localities include the USA, Japan, and Tanzania.
- **REMARK** Aventurine quartz has been confused with aventurine feldspar, amazonite, and jade. A simulant known as goldstone has been made to imitate both aventurine quartz and aventurine feldspar. It contains small triangles and hexagons of copper held in glass. With a 10x hand lens it should be possible to see the outlines of the copper spangles.



• brassy yellow mica inclusions


• oval orange-brown cabochon

CABOCHON




• fuchsite mica inclusions give green color

POLISHED SLAB

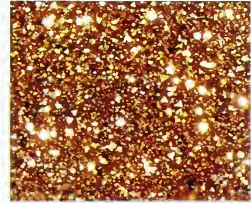


The copper inclusions in goldstone are visible with a 10x hand lens.

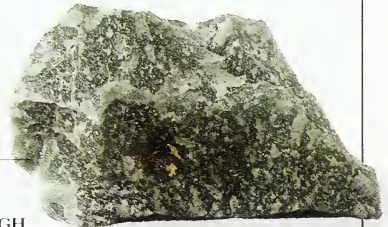

cryptocrystalline quartz with light-reflecting inclusions

AVENTURINE QUARTZ ROUGH

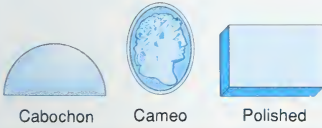

Cabochon

Cameo

Polished


SG 2.65	RI 1.54–1.55	DR 0.009	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

MILKY QUARTZ

This form of quartz derives its distinctive milky white or cream color from inclusions of gas and liquid bubbles. The degree of milkiness depends on the number and size of inclusions present. Crystals are hexagonal prisms with pyramidal ends.

- **OCCURRENCE** Very large crystals are found in Siberia. Other localities include Brazil, the European Alps, Madagascar, the USA, and Namibia.
- **REMARK** When polished or cut *en cabochon*, it may be confused with opal.

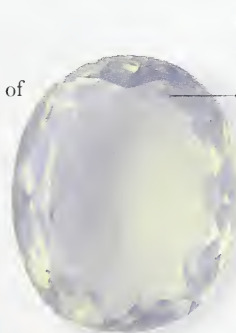

milkiness due to gas and liquid inclusions

OVAL CUSHION CUT



double pyramidal ends

HEXAGONAL CRYSTAL



Brilliant

Cameo

SG 2.65	RI 1.54–1.55	DR 0.009	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

CHATOYANT QUARTZ

The three varieties of quartz described here all have a fibrous structure, with inclusions of crocidolite (blue asbestos) that cause a cat's-eye effect known as chatoyancy. This effect is best seen when the stones are cut *en cabochon*. Each stone displays different colors according to the exact nature of the inclusions. The grayish yellow, semitranslucent appearance of quartz cat's-eye is due to inclusions of crocidolite "asbestos" and, less commonly, hornblende. It has a silky luster. "Tiger's-eye" is black, with iron oxide staining that gives yellow and golden brown stripes. "Hawk's-eye" forms when crocidolite changes to quartz, but the blue-gray or blue-green color of the original material remains.

• **OCCURRENCE** Quartz cat's-eye comes from Sri Lanka, India, and Brazil. The most important source of tiger's-eye is in South Africa, where it is found in thick slabs, together with the less common hawk's-eye. Chatoyant quartz is also found in Australia and the USA.

• **REMARK** Chatoyant quartz is always called quartz cat's-eye to avoid confusion with other chatoyant gems, particularly chrysoberyl.




HAWK'S-EYE CIGARETTE BOX

In this attractive ornament, made of polished slices of blue hawk's-eye, the wavy, fibrous nature of the original asbestos can be clearly seen. Partial oxidation has created a few yellow waves.



Bead



Cabochon




Polished



POLISHED
TIGER'S-EYE

wavy, fibrous
structure


markings resemble
tigerstripes

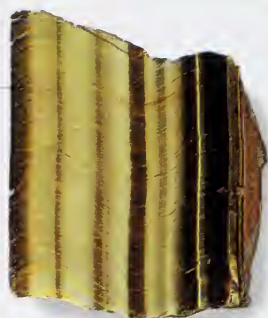

TIGER'S-EYE
POLISHED SLAB

yellow-brown
stripes due to iron
oxide staining

original blue color
and fibrous
structure retained

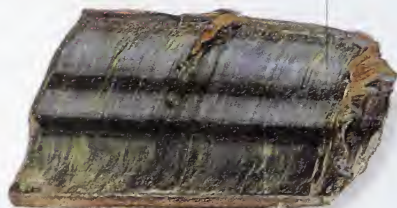

HAWK'S-EYE ROUGH

pale, almost
colorless
quartz




QUARTZ CAT'S-EYE CABOCHON

cabochon cut
brings out cat's-
eye effect

waterworn fragment
exhibits fibrous
structure

rough displays no
chatoyancy

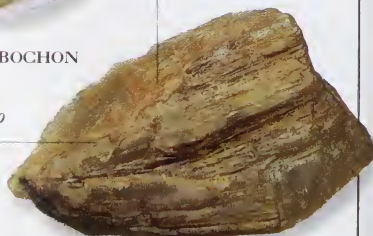

QUARTZ
CAT'S-EYE ROUGH

SG 2.65

RI 1.54-1.55

DR 0.009

Luster Vitreous

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

QUARTZ WITH INCLUSIONS

Quartz specimens with mineral inclusions are very common and make attractive gemstones. "Rutilated quartz" or "sagenite," popularly known as Venus-hair stone, is quartz with needlelike rutile crystals. These may be red, black, or brassy yellow and have a metallic luster. "Tourmalinated quartz" has inclusions of black tourmaline, which form prismatic or needlelike crystals. Opaque, metallic yellow inclusions of gold are found in specimens of "gold quartz." Inclusions of silver may also be found within quartz, often in branchlike dendrites, and are silvery gray or black, opaque, and metallic. The iron minerals, goethite and pyrite, are also found as inclusions. If cut *en cabochon*, quartz containing goethite may show the cat's-eye effect.

• **OCCURRENCE** Quartz with inclusions is found in Madagascar, Brazil, South Africa, India, Sri Lanka, Germany, and Switzerland.



Brilliant



Bead



Cabochon



Cameo



PERFUME BOTTLE
This piece of quartz contains distinctive inclusions of black, needlelike tourmaline crystals. It has been shaped, hollowed out, and polished to make a bottle.

• needlelike tourmaline inclusions

reddish brown rutile inclusions

hexagonal quartz prisms



RUTILATED QUARTZ CRYSTALS IN MATRIX

SG 2.65

RI 1.54–1.55

DR 0.009

Luster Vitreous

Crystal structure Trigonal

Composition Silicon dioxide

Hardness 7

FIRE AGATE (CHALCEDONY)

Fire agate belongs to the chalcedony family of microcrystalline quartzes. These stones are either solid colored or have bands or mosslike or dendritic inclusions (agates). The distinctive iridescent colors of fire agate are caused by layers of iron oxide within the quartz. This rainbow effect may be brought out by cutting *en cabochon*.

• **OCCURRENCE** Fire agate is found in the USA (Arizona) and Mexico.

• **REMARK** Iris quartz has a similar iridescence, but this is caused by internal cracks.



Bead



Cabochon



Mixed



Cameo




• iridescence brought out by cabochon cut

• iron oxide inclusions give "oily" effect

FIRE AGATE CABOCHON

rainbow colors

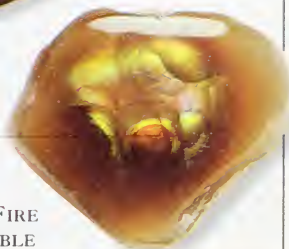

POLISHED FIRE AGATE PEBBLE

SG 2.61

RI 1.53–1.54

DR 0.004

Luster Vitreous

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

AGATE (CHALCEDONY)


Agates occur in nodular masses in rocks such as volcanic lavas. When split open, they reveal an amazing variety of colors and patterns and a distinct banding that distinguishes agate from other kinds of chalcedony (the compact, microcrystalline variety of quartz). Band colors are determined by the differing impurities present, although, since it is porous, agate is often dyed or stained to enhance the natural color. Agate also occurs in several distinct forms. Fortification agate has angularly arranged bands resembling an aerial view of a fortress. Moss agate (or mocha stone) is translucent and colorless, white or gray, with dark, moss- or treelike (dendritic) inclusions. It is usually cut as a thin slab or polished as ornaments, brooches, or pendants. Petrified wood is fossilized wood that has had its organic matter replaced by agate.

• **OCCURRENCE** Probably the most famous area for agates is Idar-Oberstein in Germany, where agate has been collected since 1548. Most agate now comes from the huge deposits in Uruguay and Brazil. Moss agate occurs in the Hindustan area of India; also China and the USA. The most famous petrified wood is found in the Petrified Forest in Arizona. Agates are also found in Mexico, Madagascar, Italy, Egypt, India, China, and Scotland.



angular and wavy agate banding • *white quartz crystals*

STAINED AND POLISHED OVAL

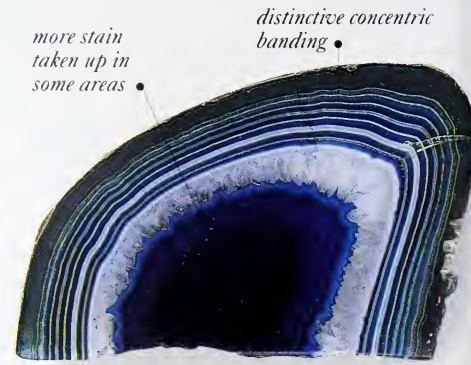

more stain taken up in some areas • *distinctive concentric banding*

STAINED AND POLISHED SLICE



parallel bands and patterns

POLISHED SLICE

• *agate is often collected and polished by enthusiasts*



agate forms in cavities in volcanic rocks

silica-rich fluids give color to bands


AGATE ROUGH

SG 2.61	RI 1.53-1.54	DR 0.004	Luster Vitreous
---------	--------------	----------	-----------------

black dendritic inclusions •

iron oxides and hydroxides form tree-like inclusions •

LANDSCAPE AGATE

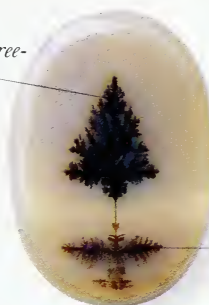

inclusions appear to create a scenic landscape •

pale cream background •



MOSS AGATE BROOCH STONE


green, mosslike inclusions •




white quartz crystals •

MOSS AGATE ROUGH

when magnified, bands in fortification agate resemble hill forts



colorless quartz crystals •

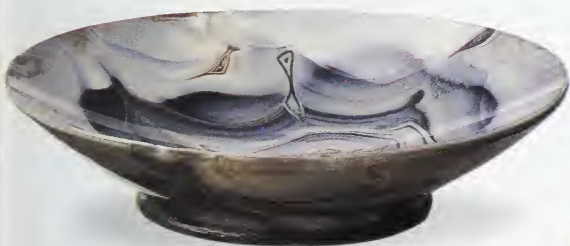

CARVED BOWL

Agate is a very popular stone for carving and polishing, although a piece as delicate as this bowl could be worked only by an expert lapidary. The parallel banding is typical of agate.



parallel but angular banding •


FORTIFICATION AGATE ROUGH



Cabochon



Cameo



Polished

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
-------------------------------	--------------------------------	---------------

ONYX, SARD, AND SARDONYX (CHALCEDONY)

Onyx, sard, and sardonyx are all varieties of the microcrystalline quartz, chalcedony. Onyx is similar to agate (see pp.88–89), but it has straight rather than curved bands. These may be brown and white or black and white. Sard is a brownish red variety, also similar to agate. Sardonyx, a blend of sard and onyx, has the straight white bands of onyx and the brownish red of sard. All three varieties are carved as small sculptures and intaglios, or they may be polished, tumbled, or cut as beads. They are renowned as excellent materials for inlay work. Since ancient Egyptian times, onyx has been stained to improve or change its color. Much onyx has been produced by soaking agate in a sugar solution, then heating it in sulfuric acid to carbonize the sugar particles. Sard may be imitated by saturating chalcedony with an iron solution.

- **OCCURRENCE** Found worldwide, they are formed by the deposition of silica in gas cavities in lavas, which results in the distinctive bands.
- **REMARK** Onyx seals were very popular with the Romans, who carved the pattern of the seal in negative relief to give a raised print. They often used stones with several layers, each of a different color, which were then individually carved to produce a different pattern in each layer.



FLOWER CAMEO
This cameo was worked from a single piece of onyx. The dark, opaque layer has been carved away in the shape of a flower to reveal the pale layer beneath.



STRAIGHT SEAL
The straight layers of onyx have been exposed to dramatic effect in this seal, an ornament popular with the Romans.




straight brown and white banding, characteristic of onyx


ONYX WITH WHITE OPAL

parallel bands of different colors

vitreous luster on some surfaces

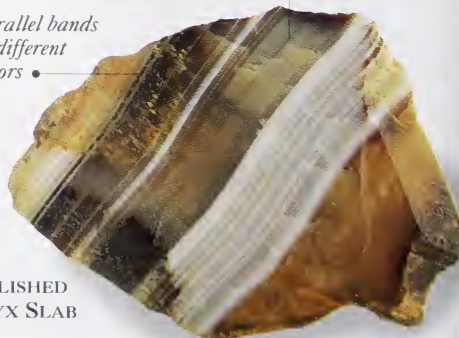

POLISHED ONYX SLAB



SG 2.61	Ri 1.53–1.54	DR 0.004	Luster Vitreous
---------	--------------	----------	-----------------



characteristic brownish red color

stone is translucent, with patchy color

OVAL POLISHED SARD

dark, semi-translucent stone with waterworn surface



SARD PEBBLE

pitted, partly waterworn surface



polished surface

SARD ROUGH

white and brownish red bands are characteristic of sardonyx



unbanded area is sard

unbanded chalcedony

sardonyx bands

POLISHED SARDONYX

SARDONYX CAMEO
In this intricately carved cameo, the pattern of a woman's head and winged dragon has been cut from three different layers - dark brown, white, and red-brown. A laurel garland is carved just inside the raised rim.



SARDONYX ROUGH

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

CHRYSOPRASE/PRASE (CHALCEDONY)

Used by both the Greeks and Romans as a decorative stone, chrysoprase, a translucent, apple green stone, is the most valued variety of chalcedony. The color, derived from the presence of nickel, may fade in sunlight, and stones may then be confused with fine jade (see pp.124–125).

• **OCCURRENCE** Mines in Poland and Czechoslovakia once produced very fine chrysoprase. However, since 1965, the best quality material has come from Queensland (Australia). Other localities are Brazil, California, the Urals (Russia), and Austria.

• **REMARK** Another green chalcedony, prase, has a more somber hue and is very rare.



PRASE CAMEO
Set in gold as an ornamental pin, this piece of fine green prase has been carved and polished into a classically styled cameo.



CHRYSOPRASE ROUGH

SG 2.61	RI 1.53–1.54	DR 0.004	Luster Vitreous to waxy
---------	--------------	----------	-------------------------


Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

JASPER (CHALCEDONY)

Jasper is a massive, fine-grained, opaque variety of chalcedony, believed to protect against sight defects and drought. It occurs in shades of brown, grayish blue, red, yellow, and green, and mixtures of these. "Orbicular" jasper has white or gray, eye-shaped patterns surrounded by red jasper. "Ribbon" jasper is striped and used in carvings, cameos, and intaglios, which show off its layered structure. Hornstone is a gray variety.

• **OCCURRENCE** Red jasper occurs in India and Venezuela; various colors occur in the USA, especially orbicular jasper in California; red and green ribbon jasper occurs in Russia. It also occurs in France and Germany.

stone may break easily at junction of stripes •

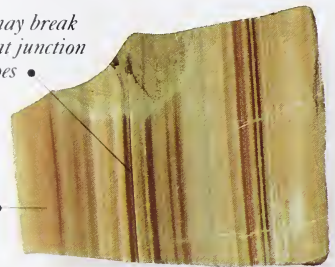


RIBBON JASPER FRAGMENT



mammillated habit •


iron oxide gives red coloring •

white quartz vein •

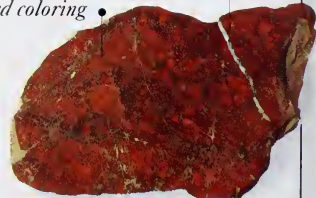

RED JASPER ROUGH

RED JASPER ROUGH



SG 2.61	RI 1.53–1.54	DR 0.004	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

CARNELIAN (CHALCEDONY)

Also called cornelian, this translucent, reddish orange variety of chalcedony was once thought to still the blood and calm the temper. Its various shades of red are due to the presence of iron oxide. Stones may be uniformly colored or faintly banded.


• **OCCURRENCE** The best carnelian is from India, where it is placed in the sun to change brown tints to red.

• **REMARK** Most carnelian on the market is stained chalcedony from Brazil or Uruguay.



• typical reddish orange stone from India

color bands formed by iron oxide impurities •

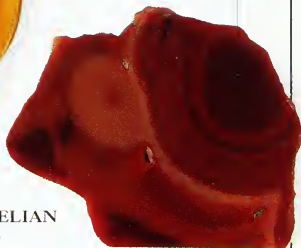

POLISHED STONE

POLISHED CARNELIAN FRAGMENT



Bead



Cabochon



Cameo

SG 2.61	Ri 1.53–1.54	DR 0.004	Luster Vitreous to waxy
---------	--------------	----------	-------------------------

Crystal structure Trigonal	Composition Silicon dioxide	Hardness 7
----------------------------	-----------------------------	------------

BLOODSTONE AND PLASMA (CHALCEDONY)

Bloodstone (also called heliotrope) and plasma are both opaque, green, spotted varieties of chalcedony, used for decorative carvings and cameos. The dark green of bloodstone is spotted with red because of the presence of iron oxides. These distinctive spots seem to resemble blood, giving the stone its name. Plasma is also green and may have yellowish spots.

• **OCCURRENCE** India is the primary source of bloodstone, but it also occurs in Brazil, China, Australia, and the USA. Plasma is mined in Zimbabwe.

• **REMARK** In the Middle Ages, bloodstone was attributed with special powers, as the spots were thought to be the blood of Jesus Christ. In Germany, hematite is also called bloodstone, so this variety is known as bluestone.




ROMAN GAMEO
The typical red spotting in dark green bloodstone appears as an almost solid mass in the high relief of this cameo.

• raised relief carved from red spotting


scattered red spots and veins •

polished material • often used as inlay

very deep • green

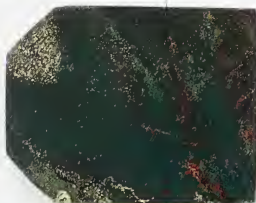

POLISHED BLOODSTONE SLAB

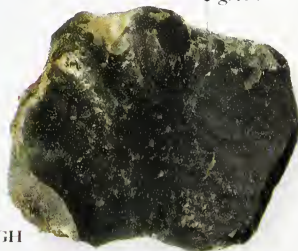

PLASMA ROUGH



Bead



Cameo



Polished

SG 2.61	Ri 1.53–1.54	DR 0.004	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal

Composition Aluminum oxide


Hardness 9

RUBY (CORUNDUM)

Ruby – the name given to red, gem-quality corundum – is one of the best gemstones for jewelry settings. Rubies may be any shade of red, from pinkish to purplish or brownish red, depending on the chromium and iron content of the stone. Frequent twinning of the crystals makes the material liable to fracture, yet ruby is a tough mineral, second only to diamond in hardness. Crystal prisms are hexagonal with tapering or flat ends. As the crystals grow, they form new layers, and, depending on the geological conditions and minerals present, color variations called zoning occur.

• **OCCURRENCE** Worldwide in igneous and metamorphic rocks, or as waterworn pebbles in alluvial deposits. The finest stones come from Myanmar; those from Thailand, the primary source, are brownish red; Afghanistan, Pakistan, and Vietnam yield bright red stones; those from India, the USA (North Carolina), Russia, Australia, and Norway are dark to opaque.

• **REMARK** In 1902, a Frenchman, Auguste Verneuil, produced a synthetic ruby crystal by exposing powdered aluminum oxide and coloring material to the flame of a blowtorch.

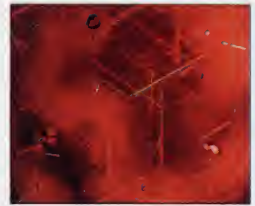

Rutile inclusions cause a silky appearance, which heat treatment will remove.

rubies were thought to ward off misfortune and ill health



• *mixed cut is typical for rubies*

CUSHION MIXED CUT

star effect seen in cabochons when rutile inclusions present



stone • weighs over 138 carats

ROSSER REEVES RUBY

manufactured by Verneuil method



STEP-CUT SYNTHETIC



Color zoning indicates the layers of growth in a crystal. They can be seen here as a series of concentric hexagons, which appear parallel to the prismatic crystal faces.

pinkish red crystal



RUBY CRYSTAL

purplish red coloration



CABOCHON

largest gem-quality crystals are from Myanmar



Brilliant



Step



Cabochon



Mixed

SG 4.00

RI 1.76–1.77

DR 0.008

Luster Vitreous

Crystal structure Trigonal

Composition Aluminum oxide

Hardness 9

SAPPHIRE (CORUNDUM)

All gem-quality corundum that is not red is called sapphire, yet this name is popularly associated with the color blue. Variation in color, due to iron and titanium impurities, spans many shades, but the most valuable is a clear, deep blue. Some stones, called "color-change sapphire," exhibit different shades of blue in artificial and natural light.

• **OCCURRENCE** Good-quality sapphire is found in Myanmar, Sri Lanka, and India. The best Indian sapphire is cornflower blue and is found in Kashmir, either in pegmatites or as waterworn pebbles in alluvial deposits. Sapphire from Thailand, Australia, and Nigeria is dark blue, and may appear nearly black. Montana produces sapphire of an attractive metallic blue. Other localities include Cambodia, Brazil, Kenya, Malawi, and Colombia.

• **REMARK** Synthetic sapphire production began in the late 19th century. Commercial quantities became available in the early 20th century.



• rutile inclusions create 6-rayed star effect in cabochons

STAR CABOCHON



CARVED BUDDHA
Since the Middle Ages, sapphire has symbolized the tranquility of the heavens, bestowing peace and amiability upon the wearer and suppressing wicked and impure thoughts.



pale blue Sri Lankan stone

BRILLIANT CUT



"Kashmir blue" crystals

sapphire crystal has intergrown with tourmaline

BLUE SAPPHIRE CRYSTAL



Brilliant



Cabochon



Cameo

SG 4.00

RI 1.76-1.77

DR 0.008

Luster Vitreous

Crystal structure Trigonal

Composition Aluminum oxide

Hardness 9

PADPARADSCHA (CORUNDUM)

Padparadscha is a very rare, pinkish orange sapphire. It is the only variety of corundum other than ruby that is given its own name, rather than being referred to as a sapphire of a particular color. The name derives from a Sinhalese word meaning "lotus blossom."

• **OCCURRENCE** Sri Lanka.

• **REMARK** Like all varieties of corundum, padparadscha is an excellent jewelry stone, second only to diamond in hardness.



characteristic pinkish orange color

vitreous luster

truncated heart shape



Mixed

MIXED CUT

SG 4.00

RI 1.76-1.77

DR 0.008

Luster Vitreous

Crystal structure Trigonal	Composition Aluminum oxide	Hardness 9
----------------------------	----------------------------	------------

COLORLESS SAPPHIRE (CORUNDUM)

The different colors found within members of the corundum group are due to small amounts of metal oxide impurities. Corundum without impurities (and therefore without color) is rare, but when found is classified as colorless sapphire. Stones made up of different colors, including colorless areas, are more common. Stones like these are generally oriented by the cutter so that the color is at the base. Then, when viewed from above, color fills the stone.

- **OCCURRENCE** Truly colorless sapphire is found in Sri Lanka. Cloudy or milky-colored sapphire is also found in Sri Lanka and referred to locally as *geuda*. Heat treatment of *geuda* produces blue sapphire, much of which is faceted and used in jewelry. Some Sri Lankan corundum shows red, blue, and colorless areas, which may be faceted or polished to give an interesting stone.
- **REMARK** Synthetic colorless corundum has been produced by the Verneuil method since about the 1920s and has been called diamondite.



cabochon shows 6-rayed star

near-colorless stone with grayish tinge

STAR-STONE CABOCHON



elongated cut

bubblelike inclusions

OVAL MIXED CUT



MIXED CUT

COLORLESS CRYSTAL

colorless sapphire is free from impurities

pyramidal end

pure, colorless stones are rare

twinned, prismatic crystal





Brilliant



Brilliant



Cabochon


SG 4.00	RI 1.76-1.77	DR 0.008	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Aluminum oxide	Hardness 9
----------------------------	----------------------------	------------


GREEN SAPPHIRE (CORUNDUM)

From medieval times until the end of the 19th century, green sapphire was known as "oriental peridot." Many sapphires that appear green actually consist of very fine alternating bands of blue and yellow sapphire, which may be visible under a microscope.

- **OCCURRENCE** Green sapphires are found in Thailand, Sri Lanka, and Australia (Queensland and New South Wales).



Brilliant



very dark green color

vitreous luster

CUSHION CUT

SG 4.00	RI 1.76-1.77	DR 0.008	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Aluminum oxide	Hardness 9
----------------------------	----------------------------	------------

PINK SAPPHIRE (CORUNDUM)

Pure pink sapphire is colored by very small quantities of chromium, and with increasing amounts of chromium it forms a continuous color range with ruby. Tiny amounts of iron may produce pink-orange stones called padparadscha (see p.95), or iron and titanium impurities together may make a purplish stone. Pink sapphires are often cut with a deep profile.

• **OCCURRENCE** Pink sapphires, from a very pale and delicate pink to a near-red, occur in Sri Lanka, Myanmar, and East Africa.

• **REMARK** Like rubies (see p.94), pink sapphires are believed to ward off ill health and misfortune. For the wearer to gain the benefit of the stone, however, it has been thought necessary for it to be worn directly on the skin. Therefore stones are cut so that, when set in a piece of jewelry, the back makes contact with the skin.



• pink color derives from chromium

• Sri Lankan stones range from pale pink to red

CUSHION MIXED CUT

stones may be worn next to the skin
• for maximum reputed benefit

striations on crystal face



OVAL MIXED CUT



PINK SAPPHIRE CRYSTAL



Brilliant

Cushion

Pendeloque

SG 4.00	RI 1.76-1.77	DR 0.008	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Aluminum oxide	Hardness 9
----------------------------	----------------------------	------------

YELLOW SAPPHIRE (CORUNDUM)

Until the end of the 19th century, yellow sapphire was known as "oriental topaz" (only blue corundum was called sapphire). Nevertheless, yellow and greenish yellow sapphires make unusual and attractive gemstones in their own right.

• **OCCURRENCE** In Queensland and New South Wales (Australia), a greenish yellow sapphire is found that may be faceted. Similar stones occur in Thailand and pure yellow stones in Sri Lanka, the USA (Montana), and East Africa.



• yellow sapphire, formerly known as oriental topaz

barrel-shaped crystal with tapering ends

CUSHION MIXED CUT



Brilliant

WATERWORN CRYSTAL



SG 4.00	RI 1.76-1.77	DR 0.008	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Calcium carbonate	Hardness 3
----------------------------	-------------------------------	------------

CALCITE

Common worldwide, calcite is the principal component of limestones and marbles and of most stalactites and stalagmites. It can also be found as large, transparent, colorless, complex crystals, or as prismatic crystals intergrown with other minerals. Because of its softness it is faceted only for the collector, but marbles and brown, banded calcite from limestone caves are used for both decoration and carving.


• **OCCURRENCE** Italy is famous for fine-quality marbles, particularly the creamy Carrara marble. Transparent, colorless rhombs are known as "Iceland spar"; a white fibrous variety, cut *en cabochon*, shows the cat's-eye effect. Pink and green crystals occur in the USA, Germany, and England.



Step



Polished

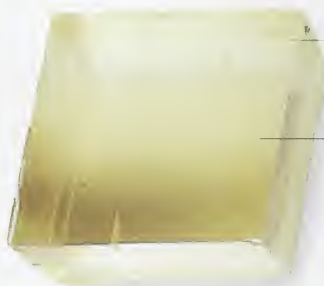

"ICELAND SPAR"
RHOMB

transparent,
colorless
crystals

• calcite crystals are highly birefractive

• vitreous luster on front, pearly luster at sides

• red tinge due to iron oxides



PRISMATIC
CALCITE CRYSTALS

SG 2.71	RI 1.48-1.66	DR 0.172	Luster Vitreous to pearly
---------	--------------	----------	---------------------------

Crystal structure Trigonal	Composition Beryllium silicate	Hardness 7½
----------------------------	--------------------------------	-------------

PHENAKITE

Phenakite is a rare mineral found as white or colorless tabular crystals or stubby prisms. Twinning is common and distinguishes it from rock crystal (see p.81), with which it is often confused (hence its name, derived from the Greek word for "cheat"). Transparent crystals are faceted for the collector and are hard and bright.

• **OCCURRENCE** Phenakite occurs in pegmatites, granites, and mica schists. The best crystals are found in Brazil, the Urals (Russia), and the USA (Colorado). Other localities include Italy, Sri Lanka, Zimbabwe, and Namibia.

• **REMARK** A pebble weighing 1.470 carats was found in Sri Lanka and faceted to a 569-carat oval and several smaller stones.



BRILLIANT CUT

• phenakite has silvery look when cut well


• vitreous luster



BRILLIANT CUT

• only transparent stones are faceted

• crystals have wedge-shaped ends

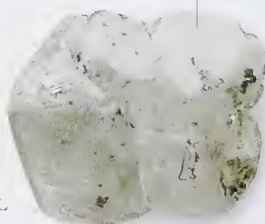

PHENAKITE CRYSTAL



Brilliant



Mixed

SG 2.96	RI 1.65-1.67	DR 0.015	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Hydrated copper silicate	Hardness 5
----------------------------	--------------------------------------	------------

DIOPTASE

Dioptase is a beautiful, vivid emerald green with a hint of blue. It has very high fire, but this is masked by its strong color, which may make stones translucent rather than transparent. Prized by the collector for its color, it is nonetheless rarely faceted, as stones are brittle and fragile, and too soft to be worn. It is sometimes confused with emerald.

• **OCCURRENCE** The best quality crystals are found in copper deposits in Russia, Namibia, Zaire, Chile, and the USA (Arizona).



Brilliant



Cabochon



DIOPTASE CRYSTALS

SG 3.31	Ri 1.67–1.72	DR 0.053	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Magnesium and calcium carbonate	Hardness 3½
----------------------------	---	-------------


DOLOMITE

Dolomite is found as colorless, white, pink, or yellow crystals, often with distinctive curved faces. Rarely faceted, because of its softness and perfect cleavage, its main use is in massive form, as a decorative stone.

• **OCCURRENCE** Found in limestones and marbles, the best crystals are from Italy, Switzerland, Germany, and the USA.



Step



Step



TWIN CRYSTAL



TWINNED DOLOMITE CRYSTALS IN MATRIX

SG 2.85	Ri 1.50–1.68	DR 0.179	Luster Vitreous to pearly
---------	--------------	----------	---------------------------

Crystal structure Trigonal	Composition Zinc carbonate	Hardness 5
----------------------------	----------------------------	------------


SMITHSONITE

Smithsonite is usually found as bluish green or green botryoidal masses or soft layers, which are polished and used as an ornamental stone (sometimes called bonamite). It may also be colored pink by cobalt or yellow by cadmium. Crystals may also be found, but are faceted for the collector only.

• **OCCURRENCE** Colorless crystals in Namibia and Zambia; blue-green masses in the USA, Spain, and Greece; yellow in the USA and Sardinia.



Cabochon

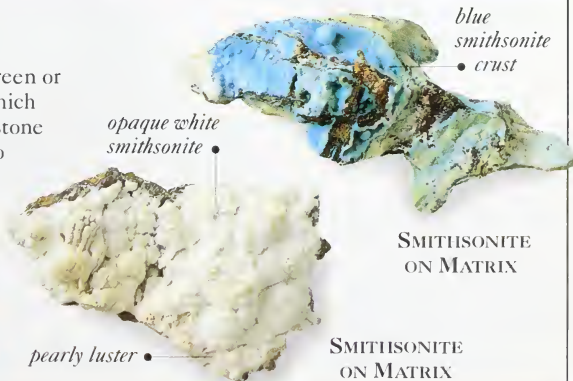

SG 4.35	Ri 1.62–1.85	DR 0.230	Luster Pearly
---------	--------------	----------	---------------

Crystal structure Trigonal	Composition Manganese carbonate	Hardness 4
----------------------------	---------------------------------	------------

RHODOCHROSITE

Rhodochrosite derives its pink color from manganese. Gem-quality crystals do occur and are cut for collectors, but the fine-grained, banded rock is more commonly used for decoration.

- **OCCURRENCE** Rhodochrosite occurs in veins associated with manganese, copper, silver, and lead deposits. Argentina has the oldest mines; its banded rhodochrosite is sometimes called "Inca rose." Today, the prime commercial sources are in the USA.



• *alternate pink and red bands*

• *polished cross section*



• *pinkish red crystals*



Bead Cabochon Cameo

BAILED RHODOCHROSITE

RHODOCHROSITE CRYSTALS IN MATRIX


SG 3.60	RI 1.60-1.80	DR 0.220	Luster Vitreous to pearly
---------	--------------	----------	---------------------------

Crystal structure Trigonal	Composition Iron oxide	Hardness 6½
----------------------------	------------------------	-------------


HEMATITE

Hematite usually occurs as massive, opaque material with a metallic luster, showing a blood red color when cut into thin slices. However, it can also occur as short, black, rhombohedral crystals and may have iridescent surfaces. When arranged like the petals of a flower, hematite is called an "iron rose." Shiny crystals may be called "specular" hematite, a name derived from their traditional use in mirrors.

- **OCCURRENCE** Main deposits are in igneous rocks around Lake Superior, Canada (Quebec), Brazil, Venezuela, and England. Iron roses are found in Switzerland and Brazil; cuttable material in England, Germany, and Elba.
- **REMARK** Powdered, it may be used as an artist's pigment or for polishing. In the past it was worn as protection against bleeding.

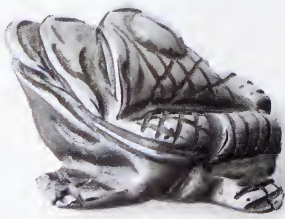


CARVED FROG
With a hardness of 6½, hematite is easily carved, but care must be taken to prevent scratching. This oriental-style frog has a gray metallic luster.

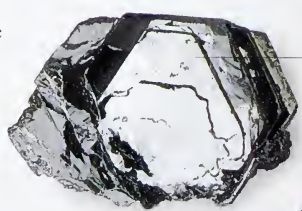

• *shiny crystals were once used as mirrors*

"SPECULAR" HEMATITE

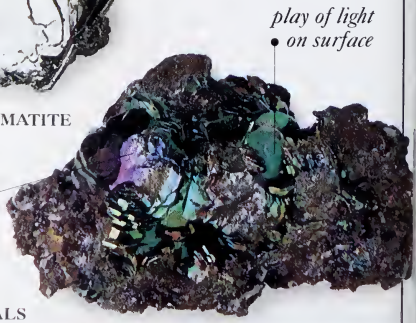

• *play of light on surface*

• *"iron rose" arrangement of crystals*

IRIDESCENT HEMATITE CRYSTALS



Bead Cabochon Cameo


SG 5.20	RI 2.94-3.22	DR 0.280	Luster Metallic
---------	--------------	----------	-----------------

Crystal structure	Trigonal	Composition	Complex borosilicate	Hardness	7½
-------------------	----------	-------------	----------------------	----------	----

RUBELLITE (TOURMALINE)

Members of the tourmaline family of minerals have the same basic crystal structure, but occur in many colors. Rubellite (from the Latin for red) is the name given to the pink or red variety, with ruby red stones the most highly prized. Rubellite crystals are striated, with a triangular cross section and a rounded outline. They may also occur with a fibrous habit, and show a cat's-eye when cut *en cabochon*.

- **OCCURRENCE** Russian pink and red tourmaline occurs in weathered granites. Other sites include Madagascar, the USA, Brazil, Myanmar, and East Africa.
- **REMARK** The specific gravity of tourmaline varies with color – dark red has a higher SG than pink.

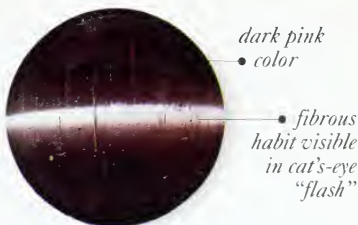

CABOCHON

rubellite crystals •

rock crystal •



RECTANGULAR STEP CUT



RUBELLITE CRYSTALS IN MATRIX



Pendeloque

Step

Cabochon

SG	3.06	RI	1.62–1.64	DR	0.018	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Trigonal	Composition	Complex borosilicate	Hardness	7½
-------------------	----------	-------------	----------------------	----------	----

INDICOLITE (TOURMALINE)

Dark blue tourmaline is called indicolite or, occasionally, indigolite. Indicolite is often heat treated to lighten its color and produce a more attractive stone.


- **OCCURRENCE** An important source for indicolite is Siberia (Russia), where it occurs in yellow clays formed from weathered granites. Fine, bright blue tourmaline has recently been found in Paraíba, Brazil. Other localities include Madagascar and the USA.
- **REMARK** A lilac to violet blue or reddish blue variety (first found in Russia) is known as siberite.

inky blue semi-transparent stone •



OVAL MIXED CUT

greenish blue transparent stone from Brazil •

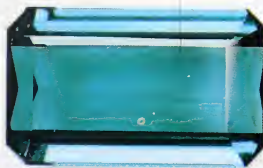


RECTANGULAR STEP CUT

fractured surface •
vertical striations •



INDICOLITE CRYSTAL



Step

Step

SG	3.06	RI	1.62–1.64	DR	0.018	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure Trigonal	Composition Complex borosilicate	Hardness 7½
----------------------------	----------------------------------	-------------

DRAVITE (TOURMALINE)

Dravite is a very dark-colored (usually brown) form of tourmaline, rich in magnesium. It is possible to lighten the color by heat treatment. Dravite shows strong dichroism and should therefore be cut with the table facet parallel to the length of the crystal, in order to show a lighter and more attractive color.

• **OCCURRENCE** Dravite can occur as single crystals or as parallel or radiating groups. Brown tourmaline and yellow tourmaline occur together in the gem gravels of Sri Lanka. It is also found in the USA, Canada, Mexico, Brazil, and Australia.

• **REMARK** The name "dravite" is derived from the district of Drave, in Austria.



golden brown
• color

• stones may be lightened by heat treatment

ROUND BRILLIANT CUT

orange-brown color •



CUSHION MIXED CUT

prismatic habit •



opaque, dark brown crystal •

CRYSTAL FRAGMENT



Brilliant



Brilliant



Cushion

SG 3.06	Ri 1.61-1.63	DR 0.018	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Complex borosilicate	Hardness 7½
----------------------------	----------------------------------	-------------

ACHROITE (TOURMALINE)

This particularly rare, colorless stone is a variety of elbaite, a member of the tourmaline group. It does not show the strong dichroism characteristic of most tourmaline varieties and therefore can be cut with the table facet either parallel or perpendicular to the length of the crystal. Colorless tourmaline may also be produced by applying heat to light pink tourmalines.

• **OCCURRENCE** Achroite occurs with colored tourmalines in the pegmatites of Madagascar and in the USA (Pala, California).


• **REMARK** Achroite is named after the Greek word *achroos*, meaning "without color."

transparent, colorless stone •




ROUND BRILLIANT CUT

girdle around "waist" of stone •

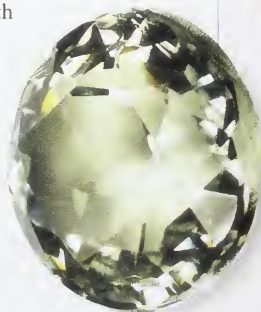

OVAL BRILLIANT CUT

fracture is conchoidal •



ACHROITE CRYSTAL



Brilliant



Brilliant



Mixed

SG 3.06	Ri 1.62-1.64	DR 0.018	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Complex borosilicate	Hardness 7½
----------------------------	----------------------------------	-------------

WATERMELON TOURMALINE

Tourmaline crystals with a pink center and a green rim, or vice versa, are called watermelon tourmaline, because their coloring is similar to the pink flesh and green rind of a watermelon. Many other tourmalines are made up of two or more colors, individual crystals containing up to 15 different colors or shades.

• **OCCURRENCE** Watermelon tourmaline is found in South Africa, Brazil, East Africa, and in many other localities.

• **REMARK** Parti- and multicolored tourmaline is carved or cut and polished to show off the different colors to best effect.



Baguette



Cabochon



TABLE CUT

• green and pink parts occur in single crystal

characteristic color zoning



CRYSTAL SECTION

SG 3.06	Ri 1.62–1.64	DR 0.018	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Complex borosilicate	Hardness 7½
----------------------------	----------------------------------	-------------

SCHORL (TOURMALINE)

Schorl is the black, iron-rich form of tourmaline and is very common. The opaque, prismatic crystals may be several yards in length.

• **OCCURRENCE** Found in pegmatites.

• **REMARK** During the Victorian era in Britain, black tourmaline was widely used for mourning jewelry, but today it has little, if any, value as a gemstone.



Brilliant



Mixed



SCHORL CRYSTAL

• broken, worn end

vertical striations

SG 3.06	Ri 1.62–1.67	DR 0.018	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Trigonal	Composition Complex borosilicate	Hardness 7½
----------------------------	----------------------------------	-------------

GREEN AND YELLOW TOURMALINE

Yellow-green is the most common of all tourmaline color varieties, but emerald green is much rarer and more valuable. Indeed, until the 18th century it was often confused with emerald.

• **OCCURRENCE** Emerald green stones are found in Brazil, Tanzania, and Namibia; fibrous yellow material occurs in Sri Lanka.



Brilliant



BRILLIANT CUT

semi-transparent stone

greenish yellow is most common color variety

SG 3.06	Ri 1.62–1.64	DR 0.018	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure	Orthorhombic	Composition	Calcium carbonate	Hardness	3½
-------------------	--------------	-------------	-------------------	----------	----

ARAGONITE

Aragonite is usually transparent or translucent and colorless or white when pure. Impurities may cause shades of yellow, blue, pink, or green to occur. It is found in many different habits: small, elongate, prismatic crystals form in radiating groups, and concretions and stalactites are also common. It has poor cleavage.

• **OCCURRENCE** Found mainly in sedimentary environments, aragonite may form as tufa (porous rock) in Czechoslovakia and Turkey. Other localities include Spain, France, the USA (Colorado), and Cumbria (England).



layering revealed in cut and polished section

STALACTITIC POLISHED SLAB




crystals growing out of matrix

crystals colorless when pure

CRYSTAL SPRAYS ON MATRIX



Bead



Polished


SG	2.94	RI	1.53–1.68	DR	0.155	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Orthorhombic	Composition	Barium sulfate	Hardness	3
-------------------	--------------	-------------	----------------	----------	---

BARITE

Barite occurs in a variety of colors, including colorless, white, yellow, and blue, but its softness, perfect cleavage, brittleness, and high density make it of little use as a gemstone, and it is cut for collectors only. Crystals vary a great deal and may be transparent to opaque, with a variety of habits from tabular to massive.

• **OCCURRENCE** Barite is commonly found in lead and silver mines. It also occurs in limestones, and may be deposited by hot springs. Crystals up to 40 in (1 m) in length have been found in Cumbria, Cornwall, and Derbyshire, in England. Other good localities include Czechoslovakia, Romania, Germany, the USA, and Italy.

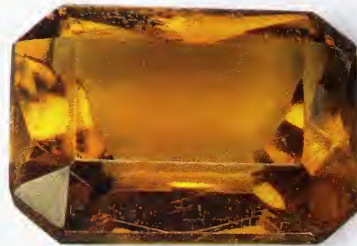

stones are faceted for collectors only

OCTAGONAL MIXED CUT

tabular, double-ended crystal



crystal layers build in concentric bands as stalagmite forms

STALAGMITE SECTION

stones are easily damaged

growth zones



BARITE CRYSTAL



Step



Mixed



Polished

SG	4.45	RI	1.63–1.65	DR	0.012	Luster	Vitreous to pearly
----	------	----	-----------	----	-------	--------	--------------------

Crystal structure	Orthorhombic	Composition	Strontium sulfate	Hardness	3½
-------------------	--------------	-------------	-------------------	----------	----


CELESTINE

Celestine is usually found as colorless, milky white, yellow, orange, or pale blue prismatic crystals, or in fine-grained masses. With a hardness of only 3½ on the Mohs scale and perfect cleavage, celestine is extremely fragile. It has been cut for the collector, however, and some fine specimens can be seen in museums.

• **OCCURRENCE** Celestine may occur with sandstones or limestones, in evaporite deposits, in pegmatites, in cavities in volcanic rocks, or with galena and sphalerite in mineral veins. Most of the material that is capable of being faceted is found in either Namibia or Madagascar. It is also found in Italy (including Sicily), England, Czechoslovakia, the USA, and Canada.



CELESTINE CRYSTAL

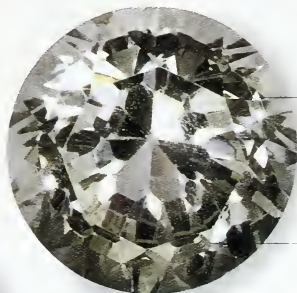

MIXED CUT

colorless celestine is the most common
• variety

cut stones are rare and
• lack fire

sulfur matrix •

transparent to semitranslucent colorless
• crystal

colorless celestine crystals •



CRYSTALS IN MATRIX

SG	3.98	RI	1.62–1.63	DR	0.010	Luster	Vitreous to pearly
----	------	----	-----------	----	-------	--------	--------------------

Crystal structure	Orthorhombic	Composition	Lead carbonate	Hardness	3½
-------------------	--------------	-------------	----------------	----------	----

CERUSSITE

Cerussite is usually colorless, but white, gray, and black specimens have been found. Its two most distinctive features are its high density and its adamantine luster. Crystals have a stubby tabular or elongate habit. Cerussite is attractive, but it is too soft to have much value as a gemstone and is cut for collectors only.

• **OCCURRENCE** Cerussite is usually found around lead ores. Large, clear, transparent, colorless, cuttable crystals have been found in Tsumeb (Namibia). Other localities include Austria, Australia, Czechoslovakia, the USA, Germany, Scotland, and Italy, including Sardinia.

• **REMARK** Sometimes confused with diamond and other colorless gems, it may be distinguishable by its higher density.



ROUND BRILLIANT CUT

• very pale gray color

worn facet edges
• due to softness

colorless, crystal "twin" •

surface formerly attached to matrix •

PRISMATIC CRYSTAL



SG	6.51	RI	1.80–2.08	DR	0.274	Luster	Adamantine
----	------	----	-----------	----	-------	--------	------------

Crystal structure Orthorhombic

Composition Aluminum fluorohydroxysilicate

Hardness 8

TOPAZ

Topaz occurs in a range of different colors: deep golden yellow topaz (sometimes called sherry topaz) and pink topaz are the most valuable; blue and green stones are also popular. Natural pink stones are rare – most pink topaz is heat treated yellow material. Much colorless topaz is irradiated and heat treated to a range of blues, some almost indistinguishable from aquamarine when seen with the naked eye. Some topaz has tear-shaped cavities, containing a gas bubble or several immiscible (nonmixing) liquids. Other inclusions such as cracks, streaks, and veils also occur. Prismatic topaz crystals have a characteristic lozenge-shaped cross section and striations parallel to their length. Topaz has one perfect cleavage.

• **OCCURRENCE** Topaz occurs in igneous rocks such as pegmatites, granites, and volcanic lavas. It may also be found in alluvial deposits as waterworn pebbles. Localities include Brazil, the USA, Sri Lanka, Myanmar, the former USSR, Australia, Tasmania, Pakistan, Mexico, Japan, and Africa. Brazil, Pakistan, and Russia are sources of pink topaz.

• **REMARK** In the 17th century the Braganza diamond (1,640 carats) in the Portuguese crown was thought to be the largest diamond ever found. This was never confirmed, and it is now believed to have been a colorless topaz. The name “topaz” is thought to be derived from the Sanskrit word *tapas*, meaning fire.



pale yellow
• topaz

• stones up to 35,000 carats have been faceted

OVAL MIXED CUT



pink color
• variety

• set in gold and worn around the neck, topaz is reputed to dispel bad omens, heal poor vision, and calm anger

OVAL STEP CUT

characteristic wedge-shaped ends



TRANSPARENT SHERRY-COLORED CRYSTAL



TOPAZ RING
A salmon pink, step-cut, eight-sided topaz, set in a gold ring.

FLOWER BROOCH

The heart of this flower-shaped brooch is a round, brilliant-cut topaz, surrounded by 36 sherry-colored topaz gems – some triangular, some diamond-shaped.

SG 3.54

RI 1.62–1.63

DR 0.010

Luster Vitreous

very pale
grayish green
color

stones are
typically
transparent



ELONGATED OVAL MIXED CUT



• 21,005-
carat
stone, once
the largest
gem ever
faceted

SQUARE CUSHION CUT
("THE BRAZILIAN PRINCESS")

blue topaz is
also popular

pale green
topaz crystal

• blue topaz
may be
produced by
heat treating
colorless
stones



OCTAGONAL STEP CUT



TOPAZ CRYSTAL
IN MATRIX

• pegmatite
rock

stone is partially
cut before being
heat treated to
• turn it blue

characteristic
tear-shaped
inclusions



PENDELOQUE CUT



Brilliant



Cushion



Pendeloque



Step



Step



Mixed



COLORLESS, PARTIALLY
FACETED PEBBLE

Crystal structure Orthorhombic

Composition Beryllium aluminum oxide

Hardness 8½

CHRYSOBERYL

Chrysoberyl occurs in a range of colors, from green, greenish yellow, and yellow to brown. It is a hard, durable stone, particularly suitable for use in jewelry. When cut well, gems are brilliant but lack fire. Two varieties, alexandrite and cat's-eye, have unique qualities of their own.

The very rare and valuable alexandrite changes from green in daylight to red, mauve, or brown under incandescent light. Synthetic chrysoberyl, synthetic corundum, and synthetic spinel have all been produced to imitate alexandrite's color change. Cat's-eye, when cut *en cabochon*, has a near-white line across a yellowish gray stone, due to canal- or featherlike fluid inclusions, or needlelike inclusions of rutile. The most highly prized cat's-eye color is a light golden brown, often with a shadow that gives a light and dark, "milk and honey" effect. Yellow chrysoberyl, popular in Portuguese jewelry of the 18th and 19th centuries, was also known as chrysolite.


• **OCCURRENCE** Although most has been mined out, the best chrysoberyl, including alexandrite, has been found in mica schists in the Urals (Russia). The largest faceted chrysoberyl from Russia weighs 66 carats. Large waterworn pebbles of various colors are found in the gem gravels of Sri Lanka. Chrysoberyl also occurs in Myanmar, Brazil, Zimbabwe, Tanzania, and Madagascar. Cat's-eye is found in Sri Lanka, Brazil, and China.

• **REMARK** The name chrysoberyl is from the Greek *chrysos*, meaning golden, and *beryllos*, which refers to the beryllium content. Known for thousands of years in Asia, it was highly valued for the protection it afforded from the "evil eye."



CUSHION MIXED CUT

golden brown color is highly prized

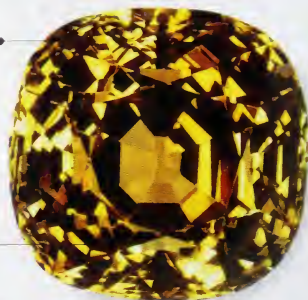

cut stones are brilliant but may lack fire

greenish yellow cabochon shows faint cat's-eye

CUSHION MIXED CUT



POLISHED CABOCHON

cat's-eye chrysoberyl has also been known as cymophane

typical wedge-shaped ends



FINGER RING

This very large ring, made of many cushion-cut chrysoberyl stones in a gold setting, is most probably of 18th-century Spanish origin. The chrysoberyl was collected from a vein running through chalk.



SPRAY OF CHRYSOBERYL CRYSTALS

SG 3.71

RI 1.74-1.75

DR 0.009

Luster Vitreous



alexandrite stones show a color change in
 • *incandescent light*

• *golden brown changes to red*

ALEXANDRITE MIXED CUT



alexandrite was found on the birthday of Tsar Alexander II and named after him

ALEXANDRITE CRYSTALS

• *intergrown crystals*

only chrysoberyl cat's-eye may be termed simply "cat's-eye"



cloudy blue flash in cat's-eye

• *cat's-eye effect*



dark brown stone with orange and red tinges


CAT'S-EYE DOUBLE CABOCHON

CAT'S-EYE CABOCHON

minute, tubelike inclusions produce chatoyancy



CAT'S-EYE DOUBLE CABOCHON

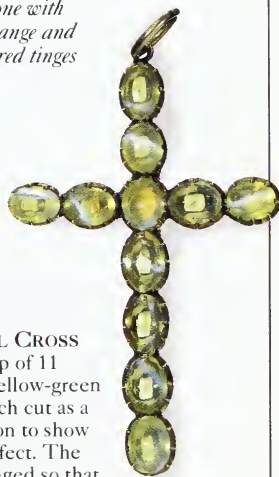

CHRYSOBERYL CROSS

A cross made up of 11 specimens of yellow-green chrysoberyl, each cut as a double cabochon to show the cat's-eye effect. The stones are arranged so that flashes are across the centers of the cabochons in a variety of positions.



Brilliant



Cushion



Cabochon



Mixed



VICTORIAN BROOCH

This exquisite brooch from the Victorian era in Britain is made up of greenish yellow, faceted chrysoberyls set in gold filigree. Its hardness and durability make chrysoberyl a particularly good stone for use in jewelry.

Crystal structure Orthorhombic	Composition Aluminum silicate	Hardness 7½
--------------------------------	-------------------------------	-------------

ANDALUSITE

Andalusite varies in color from a pale yellowish brown to a dark bottle green, dark brown, or the most popular greenish red. It has strong and distinctive pleochroism, so that, when turned, the same stone may appear yellow, green, and red. Large crystals may be vertically striated prisms with a square cross section and pyramidal ends, but these are rare. More usual are opaque, rodlike aggregates of crystals or waterworn pebbles. It is the pebbles that are usually cut as gemstones.


• **OCCURRENCE** Andalusite is usually found in pegmatites. Pebbles occur in the gem gravels of Sri Lanka and Brazil. Other localities include Spain, Canada, Russia, Australia, and the USA.

• **REMARK** An opaque, yellowish gray variety, chialstolite, occurs as long prisms, which make a cross when cut and polished.



• pleochroism creates flashes of yellow, green, and red

OCTAGONAL STEP CUT

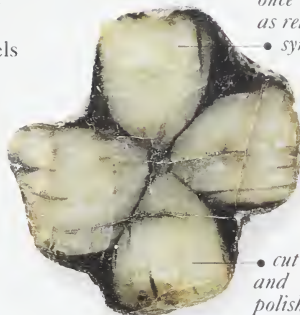

“cross” once used as religious symbol

CHIALSTOLITE CROSS SECTION



opaque crystals with rhombic cross section

ANDALUSITE CRYSTALS IN MATRIX



Brilliant



Baguette

SG 3.16	RI 1.63–1.64	DR 0.010	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Orthorhombic	Composition Calcium borosilicate	Hardness 7
--------------------------------	----------------------------------	------------

DANBURITE

Generally colorless, danburite crystals may also be yellow or pink. They form wedge-shaped prisms, similar to those of colorless topaz but may be distinguished by their cleavage (poor in danburite, perfect in topaz) and specific gravity (lower in danburite).

• **OCCURRENCE** First found in the town of Danbury, Connecticut. Gem-quality crystals occur in Myanmar, Mexico, Switzerland, Italy, and Japan.

stone from Myanmar has slight yellowish tinge

stones are bright but lack fire

characteristic wedge-shaped end



BRILLIANT CUT



Brilliant



Step



Mixed

WHITE DANBURITE CRYSTALS

SG 3.00	RI 1.63–1.64	DR 0.006	Luster Vitreous to greasy
---------	--------------	----------	---------------------------

Crystal structure	Orthorhombic	Composition	Magnesium iron silicate	Hardness	5½
-------------------	--------------	-------------	-------------------------	----------	----

ENSTATITE


Enstatite is one of the pyroxene family – a series of magnesium- to iron-rich silicates. Crystals occur as short prisms, but are rare: most gem-quality material is faceted from rolled pebbles. Cuttable enstatite varies in color from a gray- to yellowish green or olive green, to an iron-rich brownish green. A brilliant emerald green variety, colored by chromium, also occurs.

• **OCCURRENCE** Enstatite is often found with kimberlites in South Africa. Brownish green enstatite is found in Myanmar, Norway, and the USA (California). Some Sri Lankan and Indian enstatite is chatoyant. It also occurs in the USA, Switzerland, Greenland, Scotland, Japan, and the former USSR.

double cabochon cut shows cat's-eye effect




CAT'S-EYE CABOCHON

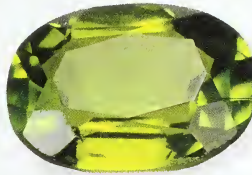


• *clear, yellowish green stone from South Africa*

OVAL MIXED CUT




Step



Cabochon

ENSTATITE ROUGH

massive, fibrous material

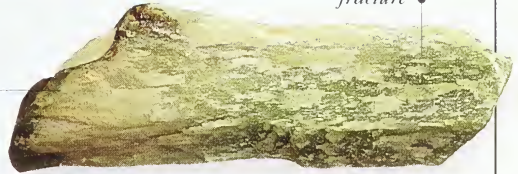

uneven fracture

SG	3.27	RI	1.66–1.67	DR	0.010	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Orthorhombic	Composition	Aluminum silicate	Hardness	7½
-------------------	--------------	-------------	-------------------	----------	----

SILLIMANITE

Sillimanite (named after Professor Silliman of Yale University) is blue to green with distinct pleochroism showing pale yellowish green, dark green, and blue from different angles. When crystals occur in long slender prisms in parallel groups, resembling fibers, the material is often called fibrolite.

• **OCCURRENCE** Sillimanite is found in metamorphic rocks and occasionally in pegmatites. Blue and violet stones are found in Myanmar; greenish gray stones in Sri Lanka; fibrolite in the USA (Idaho). Other sites are Czechoslovakia, India, Italy, Germany, and Brazil.

• *pale violet stone from Myanmar*




• *scissors-cut crown facets*

CUSHION MIXED CUT

long, slender crystals

perpendicular fibers



FIBROLITE CABOCHON



SILLIMANITE CRYSTALS IN MATRIX



Cushion



Cabochon

SG	3.25	RI	1.66–1.68	DR	0.019	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure Orthorhombic	Composition Iron magnesium silicate	Hardness 5½
--------------------------------	-------------------------------------	-------------

HYPERSTHENE


Hypersthene is an iron-rich pyroxene in the same series of minerals as enstatite (see p.111) and bronzite. It is distinguished by its reddish iridescence, which is due to platy inclusions of goethite and hematite. Often too dark to facet, it may be cut *en cabochon* instead to show the sparkling inclusions. Bronzite, a greenish brown variety with a bronzelike luster, is also a collector's stone – dark, slightly brittle, and not generally used in jewelry.

• **OCCURRENCE** Most gem hypersthene is found in India, Norway, Greenland, Germany, and the USA. Bronzite is found in Austria.



RECTANGULAR STEP CUT

colors range from green to grayish black • and brown

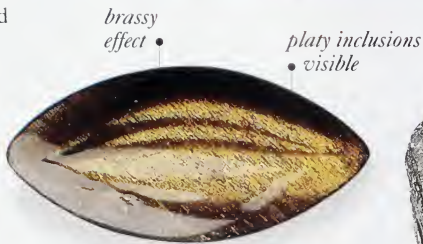

POLISHED BRONZITE

brassy effect •

platy inclusions • visible



opaque crystal fragment •



Cushion



Baguette

HYPERSTHENE ROUGH

SG 3.35	RI 1.65–1.67	DR 0.010	Luster Vitreous
---------	--------------	----------	-----------------


Crystal structure Orthorhombic	Composition Magnesium aluminum silicate	Hardness 7
--------------------------------	---	------------

IOLITE

Violet-blue iolite (also known as cordierite) has been called water sapphire because of its similarity to blue sapphire when cut. It can be recognized by its strong pleochroism, visible without equipment, which gives the gem its other name of dichroite. The best blue color is seen down the length of prismatic crystals; they may appear colorless when viewed across.

• **OCCURRENCE** Gem-quality iolite is found in alluvial deposits as small, transparent, waterworn pebbles in Sri Lanka, Myanmar, Madagascar, and India. Other localities include Namibia and Tanzania. Crystals are found in Germany, Norway, and Finland.

rich violet-blue tinge •

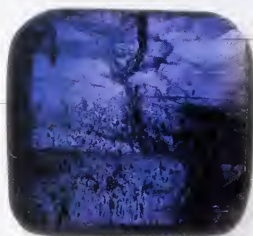

more intense color visible from front

paler color visible from this angle •

IOLITE CUBE – VIEW 1



IOLITE CUBE – VIEW 2

purplish blue crystal •



CRYSTAL IN MATRIX



Step



Cabochon



Mixed

SG 2.63	RI 1.53–1.55	DR 0.010	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Orthorhombic

Composition Magnesium aluminum borosilicate

Hardness 6½

KORNERUPINE


Although kornerupine was named in 1884, it was not until 1912 that gem-quality material was found. Even now it is uncommon and cut only for collectors. Strongly pleochroic, it appears green or reddish brown when viewed from different directions. To show the best color, it is cut with the table facet parallel to the length of the crystal.

• **OCCURRENCE** Localities include Madagascar, Sri Lanka, and East Africa, which also produces an emerald green variety. Cat's-eye gems are cut from Sri Lankan and East African stones.

• **REMARK** It has been confused with tourmaline and enstatite.



Cushion




Baguette



Step

distinctive grayish green color

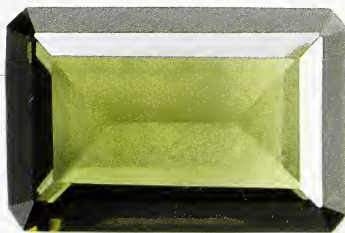


RECTANGULAR STEP CUT



MIXED CUT

• *kornerupine gems are rare and prized by collectors*

dark kornerupine crystals

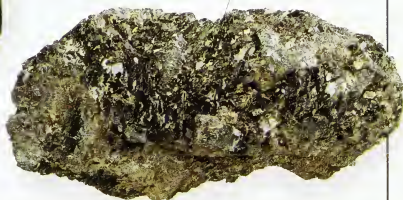

CRYSTALS IN MATRIX

SG 3.32

RI 1.66–1.68

DR 0.013

Luster Vitreous

Crystal structure Orthorhombic

Composition Magnesium iron silicate

Hardness 6½

PERIDOT

Gem-quality specimens of the mineral olivine are called peridot by gemologists. Peridot has an olive- or bottle green color that is due to the presence of iron, and a distinctive oily or greasy luster. It has a high birefractance, so doubling of the back facets can easily be seen in larger specimens when viewed from the front.

Good-quality crystals are very rare.

• **OCCURRENCE** Sources of peridot include St. John's Island (Egypt), China, Myanmar, Brazil, Norway, the USA (Arizona and Hawaii), Australia, and South Africa.

• **REMARK** The Crusaders brought peridot to Europe in the Middle Ages from St. John's Island in the Red Sea, where it had been mined for over 3,500 years.



• *green color due to iron*

distinctive bottle green color

OVAL MIXED CUT



OCTAGONAL MIXED CUT


peridot was often used in religious jewelry



CRYSTAL FRAGMENT



Pendeloque



Step



Cabochon

SG 3.34

RI 1.64–1.69

DR 0.036

Luster Vitreous to greasy

Crystal structure	Orthorhombic	Composition	Lead sulfate	Hardness	3
<h2>ANGLESITE</h2> <p>Anglesite is usually colorless or with a slight yellowish tinge but may also be found as gray, green, purple, brown, or black crystals (the black coloring is due to inclusions of galena). Crystals are heavy but as they are fragile and soft, with perfect cleavage, they are faceted for collectors only.</p> <ul style="list-style-type: none"> • OCCURRENCE Anglesite is formed by oxidation of galena (lead sulfide) and may be found in Anglesey in Wales (hence the name) and in the Leadhills district of Scotland. The best crystals are found in Tsumeb (Namibia) and Morocco. Other localities include Germany, the USA, and Sardinia. 					
 <p>• stones often have a slight yellowish tinge</p>		 <p>transparent anglesite crystal with pointed end</p> <p>galena matrix</p>			
<p>FANCY CUT</p> <p>ANGLESITE CRYSTALS IN MATRIX</p>		 <p>Step</p>			
SG	6.35	Rl	1.87–1.89	DR	0.017
				Luster	Waxy to adamantine


Crystal structure	Orthorhombic	Composition	Magnesium aluminum iron borate	Hardness	6½
<h2>SINHALITE</h2> <p>Until 1952, sinhalite was thought to be a brown variety of peridot, but on closer investigation it was found to be a completely new mineral. It varies from a pale yellowish brown to a dark greenish brown. Crystals have distinct pleochroism, showing pale brown, greenish brown, and dark brown when viewed from different directions. Occasionally, sinhalite has been faceted for the collector. Cut stones may be confused with peridot, chrysoberyl, and zircon.</p> <ul style="list-style-type: none"> • OCCURRENCE Most gem-quality sinhalite is found as rolled pebbles in the gem gravels of Sri Lanka. Crystals occur in Myanmar but are rare. Sinhalite is also found in the former USSR, and non-gem-quality material in the USA. • REMARK Sinhalite is named after <i>sinhala</i>, which is the Sanskrit name for Sri Lanka. 					
 <p>Step</p>		 <p>Mixed</p>			
 <p>• pale yellowish</p> <p>• brown stone</p> <p>• cut is slightly irregular to conserve weight</p>		 <p>double-ended, waterworn</p> <p>• prism</p>			
<p>CUSHION MIXED CUT</p> <p>CUSHION MIXED CUT</p>		 <p>dark yellow-brown</p>			
<p>SINHALITE CRYSTAL</p>					
SG	3.48	Rl	1.67–1.71	DR	0.038
				Luster	Vitreous

Crystal structure Orthorhombic	Composition Beryllium hydroxyborate	Hardness 7½
--------------------------------	-------------------------------------	-------------

HAMBERGITE

Hambergite, named after Axel Hamberg, the Swedish mineralogist, occurs as colorless to yellowish white crystals, but it is rare at gem quality. Brittle, with perfect cleavage, it is very fragile and suitable only for collectors. When cut, it looks like glass, but double images of the back facets may be seen through the table facet due to its high birefractance.


• **OCCURRENCE** Gem-quality hambergite is found in Kashmir (India), and also in Madagascar.

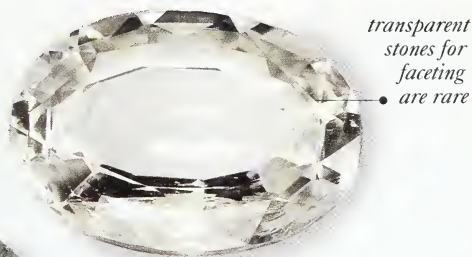

OVAL MIXED CUT

surface coloring from host rock

deep striations along length

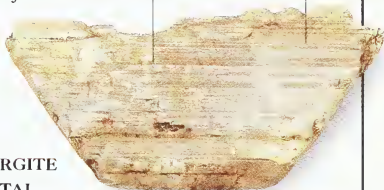

brown mineral inclusions

OVAL MIXED CUT HAMBERGITE CRYSTAL



Brilliant



Step

SG 2.35	RI 1.55–1.63	DR 0.072	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Orthorhombic	Composition Calcium aluminum hydroxysilicate	Hardness 6
--------------------------------	--	------------

PREHNITE

Often an oily green, prehnite may also range from pale yellowish to brown. Columnar or tabular crystals are rare: it occurs more usually as aggregates of barrel-shaped crystals or as botryoidal masses. Some pale yellowish brown prehnite is fibrous enough to be cut *en cabochon* and may show the cat's-eye effect.

• **OCCURRENCE** Prehnite is found in basaltic volcanic rocks, in intrusive igneous rocks, and in some metamorphic rocks. Pale green masses are found in Scotland; dark green or greenish brown masses in Australia; aggregates of crystals in France.

• **REMARK** Prehnite is named after Colonel von Prehn, who first introduced prehnite to Europe.




BRILLIANT-CUT STONES

stones are generally translucent




STEP CUT

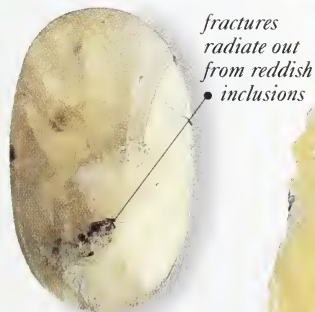

fractures radiate out from reddish inclusions

translucent crystals in botryoidal masses

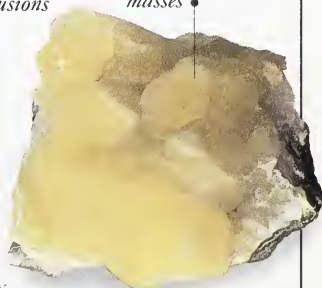

POLISHED FRAGMENT CRYSTALS ON MATRIX



Baguette



Step



Cabochon

SG 2.87	RI 1.61–1.64	DR 0.016	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Orthorhombic	Composition Calcium aluminum hydroxysilicate	Hardness 6½
--------------------------------	--	-------------

ZOISITE

Zoisite occurs in a number of varieties, the most sought after being tanzanite, a variety colored sapphire blue by the presence of vanadium. Tanzanite crystals have distinct pleochroism, showing either purple, blue, or slate gray, depending on the angle they are viewed from. There may also be a slight color change in incandescent light, when stones may appear more violet. A massive green variety of zoisite, containing rubies and occasionally dark hornblende inclusions, may be polished, carved, or tumbled to make ornaments or an attractive decorative stone. Thulite, a massive, pinkish red variety colored by manganese, is also polished or carved to make small ornaments. Tanzanite has been confused with sapphire, and thulite with rhodonite. Some heating of zoisite varieties may enhance their color.

• **OCCURRENCE** Tanzanite was first found in Tanzania (hence the name). Yellow and green zoisite occurs in Tanzania and Kenya. Thulite is found in Norway, Austria, western Australia, Italy, and in the USA (North Carolina).


• **REMARK** Discovered by Baron von Zois in the Sau-Alp mountains of Austria, zoisite was first called saualpite.



stone has been heat treated to enhance color

color varies from purple to blue due to pleochroism


TANZANITE MIXED CUT



pale bluish violet color

stones are soft and brittle

TANZANITE STEP CUT



tanzanite has perfect cleavage

violet-blue tanzanite crystal

TANZANITE CRYSTAL



polished zoisite is often used for decorative work

THULITE SLAB



pinkish red color due to manganese

THULITE CABOCHON



TANZANITE CRYSTAL IN MATRIX



massive habit

THULITE ROUGH

intergrown grayish white quartz



Step



Cabochon



Cameo

SG 3.35	RI 1.69–1.70	DR 0.010	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Orthorhombic	Composition Aluminum iron hydroxysilicate	Hardness 7
--------------------------------	---	------------

STAUROLITE

Opaque, cross-shaped staurolite “twins” are used in jewelry more often than the transparent stones, which are rare and cut only for collectors. “Cross stones,” as twins are called, have been used as amulets and in religious jewelry. Crystals are reddish brown to black, with distinct pleochroism.

• **OCCURRENCE** Staurolite occurs in Switzerland, Germany, the former USSR, the USA, Brazil, France, and Scotland.

cross shape formed by
• twinned crystals

short, black
staurolite
• crystals



opaque
• stone



CROSS STONE

CRYSTALS
IN MATRIX



Baguette



Step



Cameo

SG 3.72	RI 1.74–1.75	DR 0.013	Luster Vitreous
---------	--------------	----------	-----------------


Crystal structure Orthorhombic	Composition Aluminum iron borosilicate	Hardness 7
--------------------------------	--	------------

DUMORTIERITE

Dumortierite is best known in its massive form, which makes an attractive violet and blue decorative stone when polished. Reddish brown and red varieties also occur. Prismatic crystals larger than 1/2 in (1 mm) are very rare. Dumortierite is also found intergrown with rock crystal (colorless quartz) and is then called dumortierite quartz. This material is usually cut *en cabochon* or polished to make decorative stones.

• **OCCURRENCE** Most gem-quality material is found in Nevada. Other localities include France, Madagascar, Norway, Sri Lanka, Canada, Poland, Namibia, and Italy.

• **REMARK** Dumortierite was named after the French scientist M.E. Dumortier.

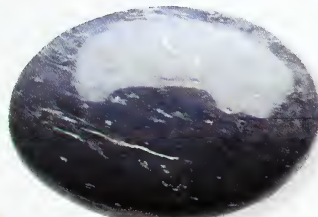


surface may
become pitted
when polished

DUMORTIERITE
QUARTZ CABOCHON

distinctive deep
blue color




CARVED BOTTLE
Hard but attractive, dumortierite is often polished and carved to make decorative objects, like this bottle adorned with the image of a bird.

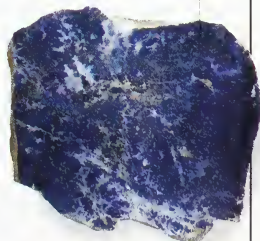

DUMORTIERITE
QUARTZ SLAB

splintery
surface

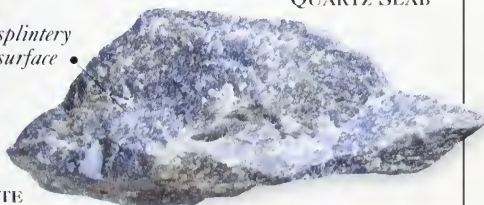

MASSIVE
DUMORTIERITE



Cabochon



Cameo



Polished

SG 3.28	RI 1.69–1.72	DR 0.037	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Monoclinic	Composition Sodium beryllium phosphate	Hardness 5½
-------------------------------------	---	--------------------

BERYLLONITE

Beryllonite crystals are colorless, white, or pale yellow, but its weak fire and low dispersion make it a dull gemstone. In addition, its softness, perfect cleavage, and brittle fracture make it fragile, although with care it may be faceted for collectors.

• **OCCURRENCE** Beryllonite is a pegmatite mineral found associated with the minerals phenakite and berylin in Maine. It is also found in Finland and Zimbabwe but remains a rare gem.

• **REMARK** Beryllonite is named after the beryllium content in its chemical composition. It has been confused with other colorless gemstones of low dispersion.



crystals are usually colorless
weak fire and low dispersion mean gems appear dull

CUSHION MIXED CUT




stones are soft and easily damaged

CUSHION MIXED CUT



cleavage planes visible

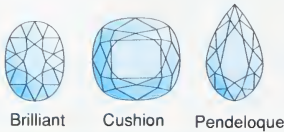

Brilliant

Cushion

Pendeloque

BERYLLONITE CRYSTAL

SG 2.83	RI 1.55–1.56	DR 0.009	Luster Vitreous
---------	--------------	----------	-----------------


Crystal structure Monoclinic	Composition Aluminum sodium hydroxyphosphate	Hardness 5½
-------------------------------------	---	--------------------

BRAZILIANITE

Brazilianite is a rare and unusual gemstone. Cut for collectors only, its yellow or yellowish green color is nonetheless striking. Crystals are fragile and brittle, with conchoidal fracture and perfect cleavage perpendicular to their length.

• **OCCURRENCE** The main localities are in Brazil, where crystals up to 6 in (15 cm) have been found. Smaller crystals have been mined in New Hampshire.

• **REMARK** Found in Minas Gerais in Brazil in 1944, brazilianite was first thought to be chrysoberyl, but closer examination revealed it to be a completely new mineral. It was named after the country in which it was found but has since been confused with chrysoberyl, beryl, and topaz.

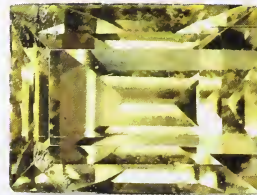

distinctive greenish yellow color

RECTANGULAR STEP CUT



stones chip and flake easily
yellow brazilianite crystals

apatite crystals



STEP CUT

GROUP OF CRYSTALS



Cushion

Pendeloque

Baguette

SG 2.99	RI 1.60–1.62	DR 0.021	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure **Monoclinic**

Composition **Calcium magnesium silicate**

Hardness **5½**

DIOPSIDE

Crystals of diopside may be colorless but are more usually bottle green, brownish green, or light green. The more iron-rich and magnesium-poor they are, the darker the color – almost to black. Very bright green diopside, colored by chromium, is known as chrome diopside. Violet-blue crystals, colored by manganese, have been found in Italy and the USA, and may be called violane. It is polished as beads when massive, cut for collectors when transparent, and cut *en cabochon* when fibrous.

• **OCCURRENCE** Gem-quality chrome diopside is found in Myanmar, Siberia (Russia), Pakistan, and South Africa. Other diopside localities include Austria, Brazil, Italy, the USA, Madagascar, Canada, and Sri Lanka. Dark green to black diopside, which shows a 4-rayed star when cut *en cabochon*, has been found in southern India since 1964.




RECTANGULAR STEP CUT

flaws are due to diopside's

- *fragility*

chrome diopside variety is bright

- *emerald green*



OCTAGONAL STEP CUT



Brilliant



Baguette



Step




Cabochon

dark green diopside crystals

-

DIOPSIDE IN MATRIX

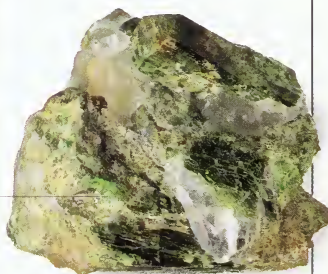

SG 3,29

RI 1.66–1.72

DR 0.029

Luster Vitreous

Crystal structure **Monoclinic**

Composition **Hydrated magnesium silicate**

Hardness **2½**

MEERSCHAUM

Meerschaum, also known as sepiolite, is a very fine-grained, soft, light rock. Found as compact, opaque masses with an earthy or chalky appearance, it may be white or gray with a yellowish or reddish tinge. Easily fashioned and often intricately carved, meerschaum is still used in Turkey for pipe bowls. With use, the smoke changes the white stone to an attractive yellow color.

• **OCCURRENCE** Today the most important source is Eskischehir in Turkey. Other localities include Czechoslovakia, Spain, Greece, and the USA.


• **REMARK** Light and porous enough to float on water, meerschaum derives its name from the German for “sea foam.”



BEAD NECKLACE
Soft and light, meerschaum is easy to carve into intricate objects, such as the individually worked beads on this delicate Turkish necklace.

dull, earthy luster

-

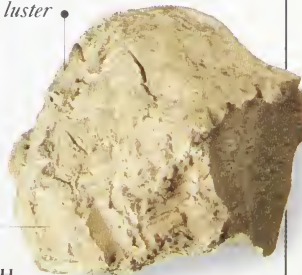

light, porous, creamy white meerschaum

-

MASSIVE ROUGH



Bead



Cameo

SG 1.50

RI 1.51–1.53

DR None

Luster Dull to greasy

Crystal structure **Monoclinic**

Composition **Lithium aluminum silicate**

Hardness **7**

SPODUMENE

Spodumene occurs in a range of colors, although the most common variety is yellowish gray. Two gem varieties – lilac-pink kunzite (colored by manganese) and bright emerald green hiddenite (colored by chromium) – are very popular with collectors, although perfect cleavage makes them fragile gemstones. Strong pleochroism is easily seen in gem material, showing colorless and two shades of the body color when viewed from different directions. Stones should always be cut to show the best color through the table facet. The pink color may fade with time, but some material is irradiated to intensify it.

• **OCCURRENCE** Spodumene was discovered in 1877 in Brazil, although it was not until 1879 that kunzite and hiddenite were recognized as different varieties of the same mineral. Spodumene is also found in Madagascar, Myanmar, the USA, Canada, the former USSR, Mexico, and Sweden.


• **REMARK** Lilac-pink kunzite is named after the gemologist G.F. Kunz, who first described it in 1902; hiddenite is named after W.E. Hidden, who discovered it in North Carolina in 1879.



lilac-pink color due to manganese

CUSHION-CUT KUNZITE


characteristic striations parallel to length



very pale green color

OCTAGONAL STEP CUT

KUNZITE CRYSTAL

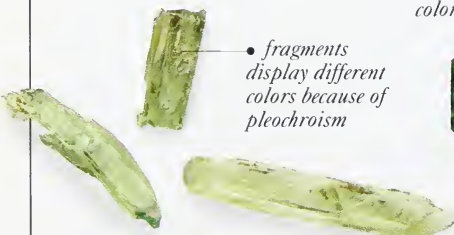


fragments display different colors because of pleochroism

emerald green color




STEP-CUT HIDDENITE

closeup of hiddenite crystals

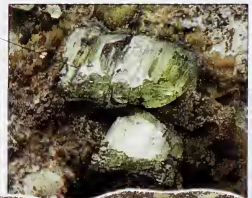

HIDDENITE CRYSTAL FRAGMENTS

gneiss matrix

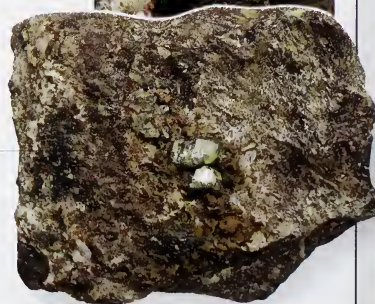


Brilliant



Pendeloque



Step



Step

HIDDENITE CRYSTALS IN MATRIX

SG 3.18

RI 1.66-1.67

DR 0.015

Luster Vitreous

Crystal structure Monoclinic


Composition Calcium aluminum iron hydroxysilicate

Hardness 6½

EPIDOTE

This fairly dense, fragile mineral has distinct cleavage and is rarely cut as a gemstone. Crystals are yellow, green, or dark brown columnar prisms, with faces finely striated parallel to the crystal's length. Pleochroism is strong, showing either yellow, green, or brown. Rock made up mainly of epidote may be polished or tumbled and sold as "anakite."

• **OCCURRENCE** Dark green crystals occur in the Austrian and French Alps. Epidote is also found in the former USSR, Italy, the island of Elba (Italy), Mozambique, and Mexico.

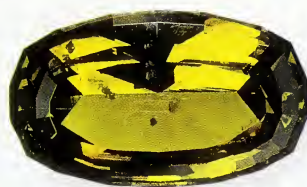

• stones are fragile and easily flawed

MIXED CUT

columnar epidote crystals



dark brown color

RECTANGULAR TABLE CUT

parallel striations



EPIDOTE CRYSTALS IN MATRIX



Cushion



Step

SG 3.40

Ri 1.74–1.78

DR 0.035

Luster Vitreous

Crystal structure Monoclinic

Composition Calcium titanium silicate


Hardness 5

TITANITE

Titanite, also known as sphene, is known for its very strong fire (its dispersion is higher than that of diamond) and rich colors, but it is seldom used in jewelry because it is too brittle and soft. Nevertheless, transparent yellow, green, or brown gem-quality material is cut for collectors. Titanite is strongly pleochroic (showing three different colors) and has high birefractance (seen as doubling of the back facets) and adamantine luster.

• **OCCURRENCE** Gem-quality titanite occurs in cavities in metamorphic rocks such as gneiss and schist and also in granite. Locations include Austria, Canada, Switzerland, Madagascar, Mexico, and Brazil.

doubling of back facets due to high birefractance



• high dispersion gives facets of varying colors

CUSHION MIXED CUT



TITANITE RING
Faceted stones, like this bright yellow brilliant cut set in gold, have high fire and rich colors.

characteristic wedge-shaped ends

twinned titanite crystals



TITANITE CRYSTALS IN MATRIX



Brilliant



Baguette



Mixed

SG 3.53

Ri 1.84–2.03

DR 0.120

Luster Adamantine

Crystal structure **Monoclinic**

Composition **Potassium aluminum silicate**

Hardness **6**

COLORLESS ORTHOCLASE

Orthoclase, an alkali feldspar, occurs in a range of colors, the most common being colorless.


Adularia, a colorless, transparent variety from Adular-Bergstock in Switzerland, has a bluish white "schiller," or sheen, called adularescence.

• **OCCURRENCE** Orthoclase feldspar occurs in intrusive igneous rocks and is one of the main constituents of granitic pegmatites. It is also found in metamorphic rocks such as schist and gneiss. Clear, colorless orthoclase occurs in Madagascar. Yellow and colorless cuttable material, cat's-eyes, and some star stones occur in the gem gravels of Sri Lanka and Myanmar.

• **REMARK** Feldspars are the most common rock-forming minerals at the Earth's surface. They are divided into two groups, the alkali feldspars and the plagioclase feldspars (see p.130). Orthoclase derives its name from the Greek for "break straight," a reference to its perfect cleavage at near 90 degrees.



Brilliant



Mixed

colorless, transparent stone




ADULARIA CUSHION CUT

internal cracks or flaws



ADULARIA CRYSTAL

white orthoclase crystals

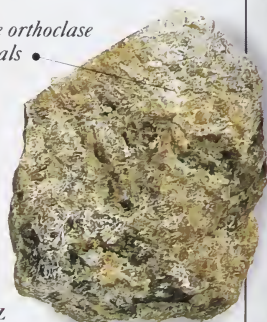

ORTHOCLASE WITH QUARTZ

SG 2.56

RI 1.51-1.54

DR 0.005

Luster Vitreous

Crystal structure **Monoclinic**

Composition **Potassium aluminum silicate**

Hardness **6**

YELLOW ORTHOCLASE

The yellow variety of orthoclase feldspar (see colorless orthoclase above) is usually faceted as a step cut because the stones are often fragile. The yellow color is due to the presence of iron.

Orthoclase crystals are columnar or tabular prisms, and are often twinned.

• **OCCURRENCE** The best yellow orthoclase is found in Madagascar in pegmatites, and may be faceted for the collector. Yellow orthoclase from Madagascar and Germany may be cut *en cabochon* to show the cat's-eye effect.


• **REMARK** Feldspars form in igneous and metamorphic rocks.

Which type is formed depends on the temperature it forms at and how it cools.



Step

step cut is most common, because of fragility of stone

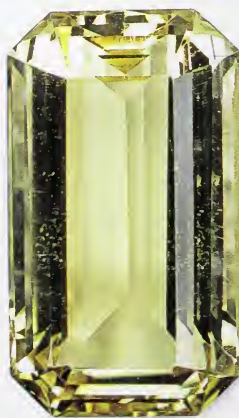

RECTANGULAR STEP CUT

crystals may be translucent to semitranslucent



CRYSTAL FRAGMENT

SG 2.56

RI 1.51-1.54

DR 0.005

Luster Vitreous

Crystal structure Monoclinic	Composition Potassium aluminum silicate	Hardness 6
-------------------------------------	--	-------------------

MOONSTONE (ORTHOCLASE)

Moonstone is the opalescent variety of orthoclase, with a blue or white sheen (or "schiller"), rather like the shine of the moon. This is caused by the reflection of light from the internal structure, made up of alternating layers of albite and orthoclase feldspar. Thin albite layers give an attractive blue; while thicker layers produce a white "schiller." Stones of large size and fine quality are rare.

• **OCCURRENCE** The best material is from Myanmar and Sri Lanka. Other localities include India, Madagascar, Brazil, the USA, Mexico, Tanzania, and the European Alps.



BLUE MOON
The moonstone in this finely detailed cameo has a distinct blue "schiller." Moon worshippers through the ages have used it in their jewelry.



CUSHION BRILLIANT CUT

pitted surface has frosted glass appearance



WATERWORN PEBBLE

SG 2.57	RI 1.52-1.53	DR 0.005	Luster Vitreous
---------	--------------	----------	-----------------


Crystal structure Triclinic	Composition Potassium aluminum silicate	Hardness 6
------------------------------------	--	-------------------

MICROCLINE

A form of alkali feldspar, microcline may be colorless, white, yellow, pink, red, gray, green, or blue-green. However, the semi-opaque, blue-green variety called amazonite (named after the Amazon River) is most commonly used in jewelry, and may be cut, usually *en cabochon*, up to almost any size. Its striking color is due to the presence of lead.

• **OCCURRENCE** The most important source of amazonite is India. Other localities include the USA, Canada, the former USSR, Madagascar, Tanzania, and Namibia.

• **REMARK** Although microcline has the same composition as orthoclase, its crystal structure is triclinic.

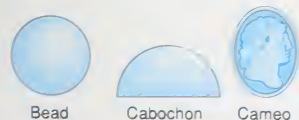

AMAZONITE SLAB



AMAZONITE CABOCHON


amazonite may be confused with jade or turquoise

characteristic blue-green color

some surfaces have silky luster

polished surface shows cleavage planes

blue, massive material

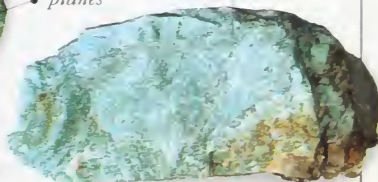

AMAZONITE ROUGH

SG 2.56	RI 1.52-1.53	DR 0.008	Luster Vitreous to silky
---------	--------------	----------	--------------------------

Crystal structure Monoclinic

Composition Sodium aluminum silicate

Hardness 7

JADEITE (JADE)

For centuries, jade was thought to be a single gemstone, but in 1863 two types were recognized: jadeite and nephrite. Nephrite (opposite) is more common, but both are tough, fine-grained rocks, suitable for carving. Jadeite, made up of interlocking, granular pyroxene crystals, occurs in a wide range of colors including green, lilac, white, pink, brown, red, blue, black, orange, and yellow. The most prized variety, imperial jade, is a rich emerald green, due to chromium. Jadeite commonly has a dimpled surface when polished.

• **OCCURRENCE** Jadeite is found in metamorphic rocks and as alluvial pebbles or boulders. Some boulders develop a brown skin from weathering, and this is often incorporated into carvings and worked pieces. The most important source of jade is Myanmar, which has supplied China with translucent imperial jade for over 200 years. Historically, Guatemala was an important source of jade, providing the material for the carvings of the Central American Indians. Jadeite also occurs in Japan and the USA (California).

• **REMARK** The Spanish *conquistadores* adopted the use of jadeite when they invaded Central America, and often wore amulets made from it. They called it *pedra de hijada* (loin stone) or *pedra de los riñones* (kidney stone), believing it prevented or cured hip and kidney complaints.

black inclusions •

characteristic
emerald green
• color

POLISHED IMPERIAL JADE

MEXICAN MASK

This opaque, mottled green mask was carved in Mexico, probably before 1753. Older jadeite carvings have a characteristic pitted surface; modern abrasives give a smoother finish.



massive habit •

mottled jadeite,
fashioned and
• polishedviolet color caused
by traces of iron •

JADEITE SPHERE



POLISHED SLAB



Bead



Cameo



Polished

SG 3.33

RI 1.66–1.68

DR 0.012

Luster Greasy to pearly

Crystal structure Monoclinic

Composition Calcium magnesium iron silicate

Hardness $6\frac{1}{2}$

NEPHRITE (JADE)

Nephrite, recognized as a separate type of jade since 1863 (see opposite), is found as aggregates of fibrous amphibole crystals. These form an interlocking structure tougher than steel, hence nephrite's popularity as a material for carving – first for weapons and later for ornaments. Colors vary from a dark green, iron-rich nephrite to a cream-colored, magnesium-rich variety. Nephrite jade may be homogeneous in color, blotchy, or banded.

• **OCCURRENCE** Nephrite jade has been carved by the Chinese for over 2,000 years, though the raw material was probably first imported from Turkestan, Central Asia, and later from Myanmar. Other localities include Siberia (dark green rocks, often with black spots), Russia (spinach-colored stones), and China. Nephrite jade is also found in various rocks in the North and South Islands of New Zealand (pieces carved in the 17th century include Maori clubs called *meres*). Other localities include Australia (black nephrite), the USA, Canada, Mexico, Brazil, Taiwan, Zimbabwe (dark green), Italy, Poland, Germany, and Switzerland.

• **REMARK** Nephrite may be confused with bowenite serpentine; it may be imitated by composite stones or dyed to improve color.


CHINESE CARVING

Nephrite jade has been carved in China for centuries and is tough enough to be worked into intricate designs. China is still one of the world's main jade-cutting centers.



DAGGER HANDLE

Because of its great strength, nephrite has been used since prehistoric times to make weapons. In fact, at one time it was known as "ax stone."

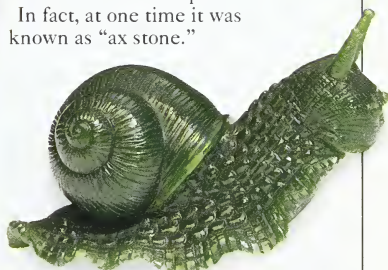

FABERGÉ SNAIL

The greasy luster of nephrite jade enhances this witty carving by the famous Russian jeweler, Fabergé.




color may
• be blotchy

tough,
interlocking
structure •

CHINESE CAMEL

The shape of the original boulder has been integrated into the design of this carving. Only one side of the boulder has been fashioned.

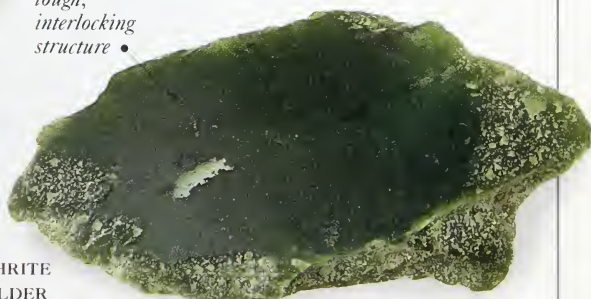

Bead



Cameo



Polished

NEPHRITE
BOULDER

SG 2.96

RI 1.61–1.63

DR 0.027

Luster Greasy to pearly

Crystal structure	Monoclinic	Composition	Copper hydroxycarbonate	Hardness	4
-------------------	------------	-------------	-------------------------	----------	---

MALACHITE

Malachite is usually found in opaque green masses, its color derived from copper. Crystals are too small for faceting, but the massive material is carved or polished in many ways to reveal the alternating bands of light and dark green. In the past, malachite was worn to ward off danger and illness.

• **OCCURRENCE** Malachite occurs in small quantities worldwide and in larger quantities in copper-mining areas. Zaire is the most important producer.



POLISHED MALACHITE

• concentric green to near-black banding

• common botryoidal habit



MALACHITE ROUGH


SG	3.80	RI	1.85 (mean)	DR	0.025	Luster	Vitreous to silky
----	------	----	-------------	----	-------	--------	-------------------

Crystal structure	Monoclinic	Composition	Hydrated copper silicate	Hardness	2
-------------------	------------	-------------	--------------------------	----------	---

CHRYSOCOLLA

Chrysocolla usually occurs as a bright green or bluish crust, or as compact, grapelike groups. Crystals intergrown with quartz or with opal are more commonly used in jewelry.


• **OCCURRENCE** Copper-mining areas, particularly Chile, the former USSR, and Zaire. "Eilat Stone" (intergrown with malachite and turquoise) reputedly came from King Solomon's mines.



POLISHED CHRYSOCOLLA

• brown patches of copper ore

• crystals are very small (micro-crystalline)

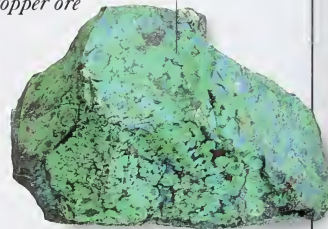

CHRYSOCOLLA ROUGH

SG	2.20	RI	1.57–1.63	DR	0.030	Luster	Greasy to vitreous
----	------	----	-----------	----	-------	--------	--------------------

Crystal structure	Monoclinic	Composition	Copper hydroxycarbonate	Hardness	3½
-------------------	------------	-------------	-------------------------	----------	----

AZURITE

Azurite is an azure blue copper mineral, occasionally found as prismatic crystals (rarely faceted), but more usually in massive form intergrown with malachite.

• **OCCURRENCE** Found particularly in copper-mining areas such as Australia, Chile, the former USSR, Africa, and China. Stones from Chessy, near Lyons in France, are called chessylite.



BANDED CHESSYLITE

• bands of green malachite

• polished stone

• dark blue azurite crystals



AZURITE CRYSTALS ON MATRIX

• green malachite


SG	3.77	RI	1.73–1.84	DR	0.110	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Monoclinic	Composition	Magnesium hydroxysilicate	Hardness	5
-------------------	------------	-------------	---------------------------	----------	---

SERPENTINE

The name serpentine refers to a group of predominantly green minerals that occur in masses of tiny intergrown crystals. The two main types used in jewelry are bowenite (translucent green or blue-green) and the rarer williamsite (translucent, oily green, veined or spotted with inclusions). They may be carved, engraved, or polished. Various marbles also contain serpentine veins.

• **OCCURRENCE** Bowenite is found in New Zealand, China, Afghanistan, South Africa, and the USA; Williamsite occurs in Italy, England, and China.

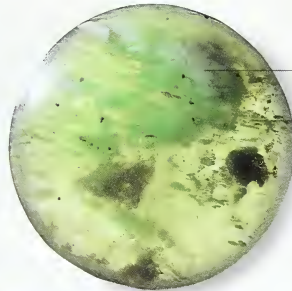


characteristic patches formed
• *by inclusions*

• *partly translucent*


rock composed of various serpentine
• *minerals*

WILLIAMSITE CABOCHON

• *lack of color due to thinness of slice*

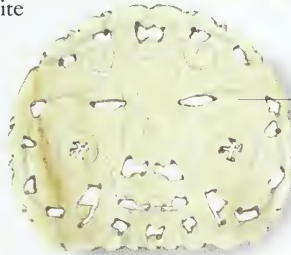

BOWENITE PENDANT

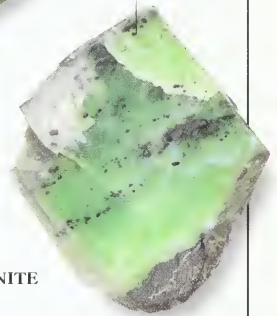

SERPENTINITE ROCK



Cameo



Polished


SG	2.60	RI	1.55–1.56	DR	0.001	Luster	Vitreous to greasy
----	------	----	-----------	----	-------	--------	--------------------

Crystal structure	Monoclinic	Composition	Hydrated zinc phosphate	Hardness	3½
-------------------	------------	-------------	-------------------------	----------	----

PHOSPHOPHYLLITE

This is one of the rarest of gemstones, and is highly prized by collectors. The crystals, which are prismatic or with a thick, tabular habit, range from colorless to deep bluish green, but the best specimens are a very delicate bluish green. Nevertheless, phosphophyllite is rarely cut, as the material is brittle and fragile, and large crystals are too valuable to be broken up.

• **OCCURRENCE** The finest crystals, and the only ones to be faceted, are from Bolivia. Other localities include Germany and the USA (New Hampshire).

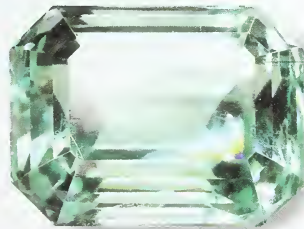

pale blue-green color is most
• *sought after*

cuttable material mainly from
• *Bolivia*

RECTANGULAR STEP CUT



STEP CUT


small fragments can
• *be faceted*

crystals crack
• *easily*



PHOSPHOPHYLLITE CRYSTALS

phosphophyllite
• *crystals*

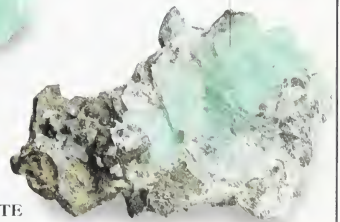

PHOSPHOPHYLLITE CRYSTALS ON PYRITE



Brilliant



Step


SG	3.10	RI	1.59–1.62	DR	0.021	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Monoclinic	Composition	Magnesium aluminum hydroxyphosphate	Hardness	5½
-------------------	------------	-------------	-------------------------------------	----------	----

LAZULITE

Crystals of lazulite are rare. Colors vary from a mottled pale blue to dark blue. Transparent stones are pleochroic, showing blue and colorless, but often lazulite is not transparent. Semi-translucent or opaque stones, found as small crystal fragments, may be polished, carved, or tumbled to make beads or decorative stones.

• **OCCURRENCE** Localities include the USA, Brazil, India, Sweden, Austria, Switzerland, Madagascar, and Angola.

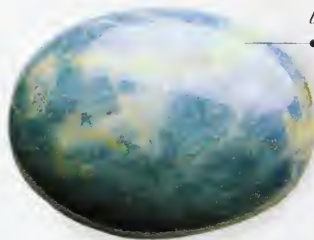

blue and white
• mottling


bipyramidal
lazulite
crystal •

POLISHED CABOCHON



Cabochon

LAZULITE
IN MATRIX

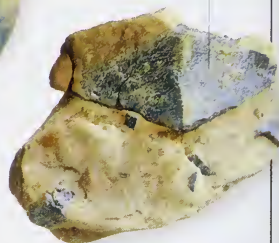

SG	3.10	Ri	1.61–1.64	DR	0.031	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------


Crystal structure	Monoclinic	Composition	Hydrated calcium borosilicate	Hardness	3½
-------------------	------------	-------------	-------------------------------	----------	----

HOWLITE

Howlite is a soft, light mineral with a chalky white color, commonly with black or brown veins. Crystals are occasionally found in groups. It is very porous and may be dyed to imitate other minerals, especially turquoise.

• **OCCURRENCE** Howlite has been found in large quantities in the USA (California).

• **REMARK** Though it is soft, howlite will withstand a polish and is occasionally used as a decorative stone.

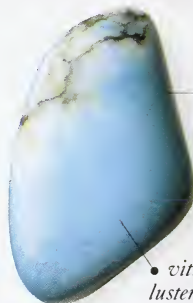

stained blue
to imitate
• turquoise

light, powdery,
• and porous



Bead

STAINED HOWLITE

• vitreous
luster



MASSIVE ROUGH

SG	2.58	Ri	1.58–1.59	DR	0.022	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Monoclinic	Composition	Hydrated calcium sulfate	Hardness	2
-------------------	------------	-------------	--------------------------	----------	---

GYPSUM

Several varieties of gypsum are used as decorative stones. The most important, alabaster, is found as fine-grained masses in pastel shades but is commonly stained in stronger colors. Selenite is colorless, occasionally cut for collectors, but is very soft. Satin spar is a fibrous variety, polished or cut *en cabochon*. Rose shapes (called "desert rose") also occur.

• **OCCURRENCE** Localities include Italy and England (alabaster); Italy, Mexico, the USA, and Chile (selenite).



cat's-eye
• effect

parallel
fibrous
structure •

• satin
luster

POLISHED
SATIN SPAR



Cabochon



SATIN SPAR ROUGH

SG	2.32	Ri	1.52–1.53	DR	0.010	Luster	Silky to vitreous
----	------	----	-----------	----	-------	--------	-------------------

Crystal structure **Monoclinic**Composition **Calcium hydroxyborosilicate**Hardness **5**


DATOLITE

Transparent, colorless crystals of datolite are cut for the collector only. A tinge of yellow, green, or white may also be present. More often, however, datolite occurs as a massive material, which may contain copper inclusions.

• **OCCURRENCE** Localities include Austria, Italy, Norway, the USA, Germany, and England. The main source of massive datolite with inclusions is the Lake Superior area of North America.

**Step**

crystals are cut for collectors only

**OCTAGONAL STEP CUT**

colorless, with tinge of yellow

**CRYSTAL**SG **2.95**RI **1.62–1.65**DR **0.044**Luster **Vitreous**Crystal structure **Monoclinic**Composition **Lithium aluminum silicate**Hardness **6**


PETALITE

Fine petalite is rare and fragile. For this reason it is only occasionally cut for the collector. Crystals are transparent, colorless, or white, occurring as tabular or columnar prisms with a glassy appearance. Massive petalite is more common, cut *en cabochon*.

• **OCCURRENCE** Elba (Italy), Brazil, Australia, Sweden, Finland, USA, Zimbabwe, and Namibia.

**Cushion**

fine stones are rare and fragile

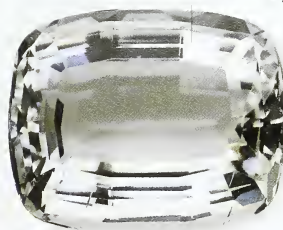**CUSHION MIXED CUT**


fibrous, massive material

**PETALITE ROUGH**SG **2.42**RI **1.50–1.51**DR **0.014**Luster **Vitreous to pearly**Crystal structure **Monoclinic**Composition **Beryllium aluminum hydroxysilicate**Hardness **7½**

EUCLASE

Euclase is a rare gem. The most attractive color is a pale aquamarine blue, but it also occurs in white, green, and colorless forms. Crystals are prismatic with a perfect cleavage, which means they are fragile and must be cut and handled with care.

• **OCCURRENCE** Euclase occurs mainly in pegmatites. Localities include Brazil, Tanzania, Zaire, Kenya, the former USSR, India, Zimbabwe, and the USA.

**Step****SQUARE STEP CUT**

black mineral inclusions



conchoidal fracture

PRISMATIC CRYSTALSG **3.10**RI **1.65–1.67**DR **0.019**Luster **Vitreous**

Crystal structure Triclinic	Composition Sodium calcium aluminosilicate	Hardness 6
--------------------------------	---	---------------

ALBITE

Albite is one of six species in the plagioclase feldspar series. Each species is defined by its albite and anorthite content: albite itself has the highest albite content. It is usually white, though gems are often colorless. Peristerite, an albite-oligoclase mix, has a blue sheen, like moonstone (see p.123).

• **OCCURRENCE**

The best specimens of peristerite are found in Canada.



Brilliant



Brilliant



MIXED CUT

ALBITE CRYSTALS

albite is usually colorless

cream-colored, opaque crystals



SG 2.64	RI 1.54–1.55	DR 0.009	Luster Vitreous to pearly
---------	--------------	----------	---------------------------

Crystal structure Triclinic	Composition Sodium calcium aluminosilicate	Hardness 6
--------------------------------	---	---------------

OLIGOCLASE

Oligoclase is a species of plagioclase feldspar (see above). The variety used in jewelry is called sunstone or, less commonly, aventurine feldspar. It has reflective inclusions of red, orange, or green platy crystals, which give it a metallic glitter. Sunstone may be faceted or carved, often as cabochons.

• **OCCURRENCE** Sunstone occurs in metamorphic and igneous rocks in Norway, the USA, India, the former USSR, and Canada.



Cabochon



SUNSTONE ROUGH

SUNSTONE PIN

The bright spangles in this cabochon, set as a tie pin, are caused by tiny inclusions of hematite.

hematite flakes produce sparkling parallel bands



SG 2.64	RI 1.54–1.55	DR 0.007	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure Triclinic	Composition Sodium calcium aluminosilicate	Hardness 6
--------------------------------	---	---------------

LABRADORITE

Labradorite is the plagioclase feldspar (see albite, above) that is most commonly faceted as a gemstone. It may be orange, yellow, colorless, or red, but the material that shows a play of color, or "schiller," is the most popular for use in jewelry.

• **OCCURRENCE** Occurs in metamorphic and igneous rocks in Labrador (Canada), Finland, Norway, and the former USSR.



Cabochon



Polished




CABOCHON

LABRADORITE ROUGH

play of color (schiller) seen on polished surface

interference of light at junctions of internal structures

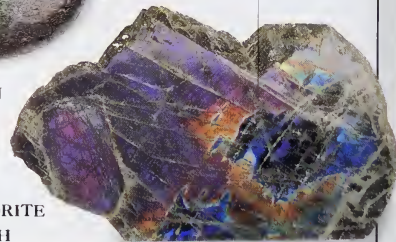

SG 2.70	RI 1.56–1.57	DR 0.010	Luster Vitreous
---------	--------------	----------	-----------------

Crystal structure **Triclinic**Composition **Hydrated copper aluminum phosphate**Hardness **6**

TURQUOISE


One of the first gemstones to be mined, turquoise has long been prized for its intense color, which varies from sky blue to green, depending on the quantities of iron and copper within it. Turquoise is commonly found in microcrystalline, massive form, usually as encrustations, in veins, or as nodules. It is opaque to semitranslucent, light and very fragile, with conchoidal fracture. Some material is very porous, leading to fading and cracking, so it may be impregnated with wax or resin to maintain its appearance.

• **OCCURRENCE** Sky blue turquoise from Iran is generally regarded as the most desirable, but in Tibet a greener variety is preferred. Localities in Mexico and the USA produce a greener, more porous material that tends to fade more quickly. Other localities include the former USSR, Chile, Australia, Turkestan, and Cornwall (England).

• **REMARK** Turquoise has been thought to warn the wearer of danger or illness by changing color. It has been imitated by stained howlite, fossil bone or tooth, limestone, chalcedony, glass, and enamel. In 1972, an imitation turquoise was produced in France by Gilson.

cut and polished as cabochon

laboratory-made stone has uniform color

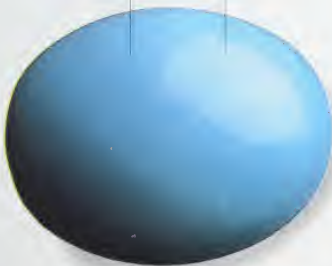

GILSON IMITATION



Bead



Cabochon



Cameo

GREEN FACE

This greenish blue turquoise stone has been carved in the image of a child's face, set in relief in a swivel ring.




PERSIAN BLUE


These two ornaments, engraved and inlaid with gold, are made from the finest sky blue turquoise, mined in Persia (now Iran) for over 3,000 years. The distinctive color is due to the presence of copper and traces of iron. Persian turquoise was introduced to Europe via Turkey – hence its name, derived from the word "Turkish."



pattern engraved and inlaid with gold

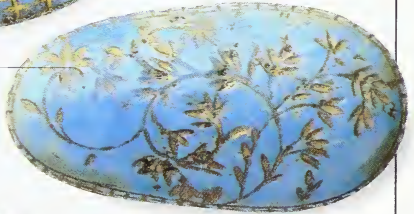

"spiderweb" turquoise has black veins

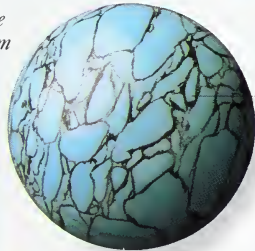


GILSON "SPIDERWEB" IMITATION

intense blue-green color

thin crust of turquoise

TURQUOISE IN MATRIX

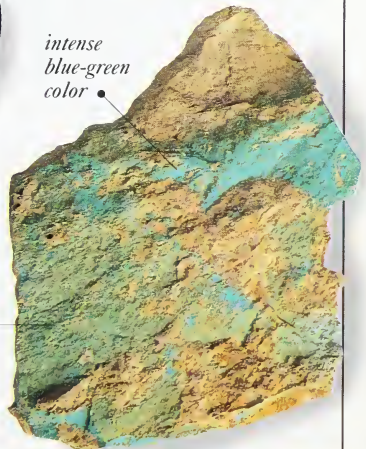

SG 2.80

RI 1.61–1.65

DR 0.040

Luster **Waxy to dull**

Crystal structure	Triclinic	Composition	Manganese silicate	Hardness	6
-------------------	-----------	-------------	--------------------	----------	---

RHODONITE

Rhodonite has a distinct pink or rose red color, although material containing black veins is more popular than a uniform pink. Massive rhodonite is usually opaque to translucent and is carved or cut as cabochons or beads. Transparent crystals are rare and fragile, but some have been cut for collectors.

• **OCCURRENCE** Both crystals and massive material have been found in the Urals (Russia), Sweden, and Australia. Other localities for fine-grained rhodonite include Brazil, Mexico, the USA, Canada, Italy, India, Madagascar, South Africa, Japan, New Zealand, and England.

• **REMARK** The name comes from *rhodos*, the Greek for "rose," referring to the distinct color.




black-veined stones are the most popular

characteristic pink-red color

OVAL CABOCHON

massive habit

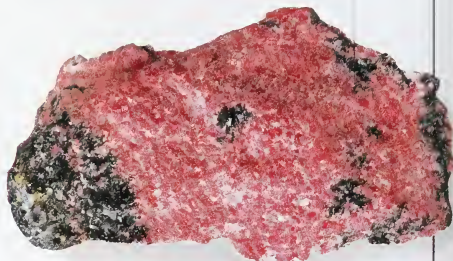

black areas rich in manganese

RHODONITE ROUGH



Bead



Cabochon



Cameo

SG	3.60	RI	1.71–1.73	DR	0.014	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Triclinic	Composition	Lithium aluminum hydroxyphosphate	Hardness	6
-------------------	-----------	-------------	-----------------------------------	----------	---

AMBLYGONITE

Amblygonite is found in a wide range of colors from white, pink, green, and blue to golden yellow and, more rarely, colorless. Large transparent to translucent crystals may occur, but as amblygonite is relatively soft, they are cut solely for collectors. Amblygonite is also found as cleavable or compact masses.

• **OCCURRENCE** Amblygonite is found in pegmatites. Brazil is the source of most gem-quality material, but it is also found in the USA. A pale mauve variety occurs in Namibia.

• **REMARK** Amblygonite has been confused with brazilianite and scapolite.



dark yellow color

stones are too soft to be popular for jewelry

OVAL BRILLIANT CUT


straw yellow color is most common



pale yellow color

perfect cleavage

OVAL BRILLIANT CUT

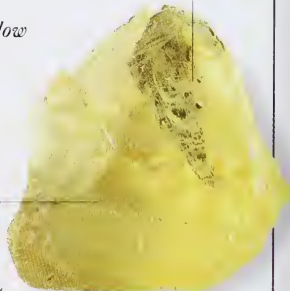

INCOMPLETE CRYSTAL



Brilliant



Brilliant



Mixed

SG	3.02	RI	1.57–1.60	DR	0.026	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Triclinic	Composition	Complex borosilicate	Hardness	7
-------------------	-----------	-------------	----------------------	----------	---


AXINITE

Axinite gets its name from its sharp-edged, axhead-shaped crystals. Although attractive and hard, they are brittle and rarely flawless and are faceted for collectors only. Brown is the most usual color, although it also occurs in honey yellow and plum purple varieties. A rare Tanzanian axinite is blue. Axinite is strongly pleochroic.

• **OCCURRENCE** Axinite is found in cavities in granite and in metamorphic rocks.


Localities include New Jersey, where the attractive honey yellow crystals are found, Mexico, Cornwall (England), France, and in the gem gravels of Sri Lanka.

• **REMARK** Darker axinite has been confused with smoky quartz.

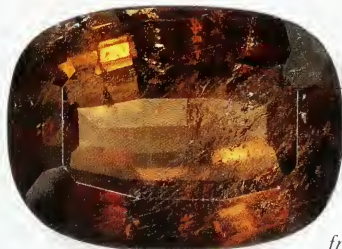

iron gives stone its rich brown color

OVAL STEP CUT



pale blue color due to low iron content

BRILLIANT CUT



fragile, sharp-edged crystals

AXINITE CRYSTALS



Brilliant

Brilliant

Mixed

SG	3.28	RI	1.67–1.70	DR	0.011	Luster	Vitreous
----	------	----	-----------	----	-------	--------	----------

Crystal structure	Triclinic	Composition	Aluminum silicate	Hardness	5 or 7
-------------------	-----------	-------------	-------------------	----------	--------

KYANITE

Gem-quality kyanite crystals are pale to deep blue or white, gray, or green. Color distribution in crystals may be uneven, with darker blue patches towards the interior.

• **OCCURRENCE** Kyanite is found in metamorphic gneiss and schist and in pegmatite veins through metamorphic rocks. It may be weathered out into alluvial deposits. Gem-quality crystals are found in Myanmar, Brazil, Kenya, and the European Alps. Alluvial deposits are found in India, Australia, and Kenya, and in parts of the USA.

• **REMARK** Kyanite crystals have two hardness values: they are softer parallel to the direction of cleavage and harder perpendicular to it.

cracks due to formation at high pressure

rich blue color




RECTANGULAR STEP CUT

uneven color distribution



CRYSTAL

staurolite crystals commonly occur with kyanite

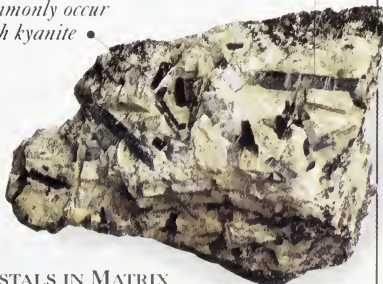

CRYSTALS IN MATRIX



Baguette

Step

Cabochon

SG	3.68	RI	1.71–1.73	DR	0.017	Luster	Vitreous to pearly
----	------	----	-----------	----	-------	--------	--------------------

Crystal structure	Amorphous	Composition	Hydrated silica gel	Hardness	6
-------------------	-----------	-------------	---------------------	----------	---

OPAL

Opal is a hardened silica gel, usually containing 5–10 percent water. It is therefore noncrystalline, unlike most other gemstones, and may eventually dry out and crack. There are two varieties: precious opal, which shows flashes of color (iridescence), depending on the angle of viewing; and common or “potch” opal, which is often opaque and displays no iridescence. The iridescence of precious opal is caused by the way the structure, a regular arrangement of tiny silica spheres, diffracts light – the larger the spheres, the greater the range of colors. Precious opal occurs in a number of color varieties, some of which are shown here.

• **OCCURRENCE** Opal fills cavities in sedimentary rocks or veins in igneous rocks. It forms stalagmites or stalactites and replaces organic material in fossil wood, shell, and bone. Australia has been the main producer of opals since the 19th century. Other localities include Czechoslovakia, the USA, Brazil, Mexico, and southern Africa.


• **REMARK** Opals have been imitated by Slocum stone, a tough, manmade glass, and, in 1973, Gilson made an imitation opal in the laboratory (see p.36).



• precious opal with dark background is called black opal

• cracks due to loss of original water content

BLACK PRECIOUS OPAL

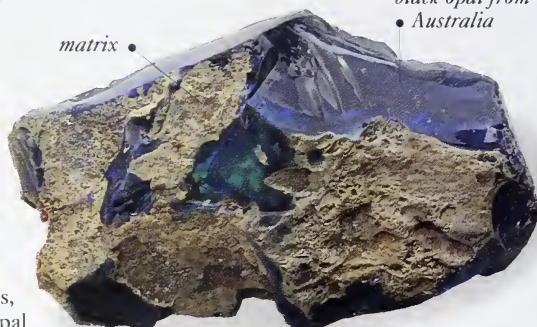

matrix

high-quality black opal from Australia

BLACK PRECIOUS OPAL IN MATRIX

good-quality stones are transparent, not milky



beautiful, rich orange body color gives fire opal its name

FIRE OPAL BRILLIANT



FIRE OPAL RING

Although many opals are cut *en cabochon*, this transparent fire opal has been faceted as an octagonal step cut and set in a gold ring.

volcanic rhyolite matrix

transparent fire opal



opaque white opal

OPAL IN MATRIX




SG 2.10

RI 1.37–1.47

DR None

Luster Vitreous

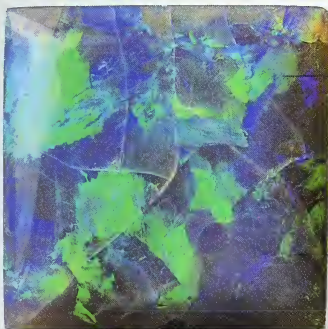

• iridescent flashes of green and blue

• convex front surface

POLISHED PRECIOUS OPAL


opal has filled cavity in host rock •



• iron nodule, split open to reveal opal


MATRIX OPAL

• shell is replaced by precious opal

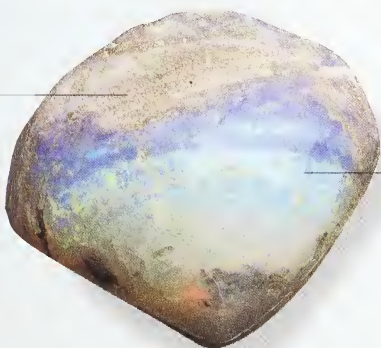

• play of color caused by diffraction of light off closely packed silica spheres

OPALIZED FOSSIL



Magnification reveals the mosaiclike structure of this Gilson imitation opal.




OPALS AND PEARLS
This exquisite gold cross, designed to be worn on a chain, is set with five precious white opals, cut *en cabochon*, and two pearls. The opals show flashes of red, blue, and green.



WHITE OPAL
Although soft and easily damaged, precious opal remains a popular stone for rings.

• mosaic pattern, visible under magnification (above), identifies stone as imitation

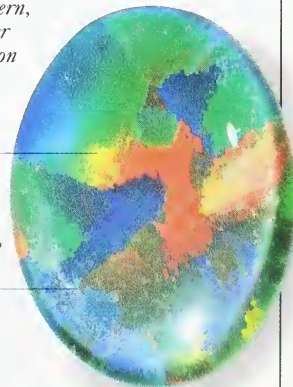

GILSON IMITATION OPAL

• stunning, bright colors




• manmade glass imitates play of color of natural opal

SLOCUM STONE



Step



Cabochon



Cameo

Crystal structure	Amorphous	Composition	Mainly silicon dioxide	Hardness	5
-------------------	-----------	-------------	------------------------	----------	---

OBSIDIAN

Obsidian is a natural glass. It is formed from volcanic lava that cooled too quickly for significant crystallization to occur. Hence it is amorphous, with no cleavage; fracture is conchoidal. Obsidian is usually black, but brown, gray, and, more rarely, red, blue, and green material is found. The color may be uniform, striped, or spotted. Some inclusions give obsidian a metallic sheen, while internal bubbles or crystals (called crystallites) produce a "snowflake" effect (called snowflake obsidian) or an iridescence seen as flashes of color.

• **OCCURRENCE** Obsidian is found in areas where there is or has been volcanic activity, such as Hawaii, Japan, and Java. Other localities include Iceland, Hungary, the Lipari Islands off Italy, the former USSR, Mexico, Ecuador, and Guatemala. Dark nodules found in Arizona and New Mexico are called "Apache tears."

• **REMARK** Obsidian has been used since prehistoric times for making tools, weapons, masks, mirrors, and jewelry. The very sharp shards of the natural glass have been fashioned as blades, arrowheads, and daggers. Today most obsidian jewelry comes from North and Central America.


characteristic dark color •

speckled effect caused by tiny gas bubbles •



OBSIDIAN CABOCHON

rare red obsidian •

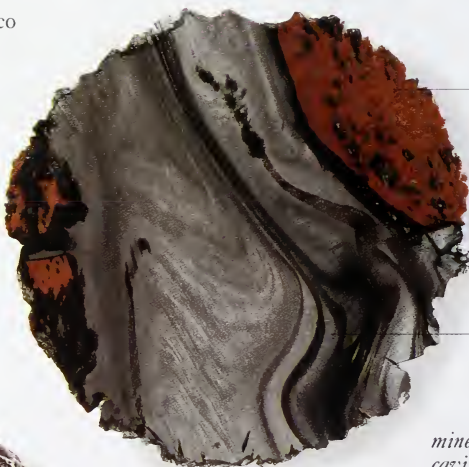

banding caused by solidification of flowing lava •

polished specimen has smooth, glassy surface •



APACHE TEARS



rough specimen has uneven surface •

mineral-lined cavities, called spherules •



OBSIDIAN ROUGH

amorphous black obsidian •



Cabochon



Polished

SG	2.35	RI	1.48–1.51	DR	None	Luster	Vitreous
----	------	----	-----------	----	------	--------	----------

Crystal structure Amorphous

Composition Mainly silicon dioxide

Hardness 5

TEKTITES


The first tektites were found in 1787 in the Moldau River in Czechoslovakia, hence their original name of "moldavites." Other color varieties of this natural glass have since been found in many different localities. Tektites are usually translucent and occur in a range of colors from green to brown. Their surfaces are usually uneven or rough, with a distinctive lumpy, jagged, or scarred texture. Tektites do not contain the crystallites found in obsidian (opposite). They may, however, have characteristic inclusions of round or torpedo-shaped bubbles or honeylike swirls.

• **OCCURRENCE** The Moldau River in Czechoslovakia is now the only known locality for green, transparent tektite. Tektites from Thailand have been carved as small, decorative objects worn in the belief that they give protection from evil.

• **REMARK** Several ideas have been put forward to explain the mysterious origin of tektites. One theory is that they came to Earth from outer space, melting as they passed through the atmosphere and thus forming their characteristic shape and surface texture. A second theory is that the impact of a large meteorite caused the surrounding rocks to melt and scatter, with cracks and scars then appearing as they cooled.

dark brown, semi-translucent stone •

dark stones are faceted only rarely •

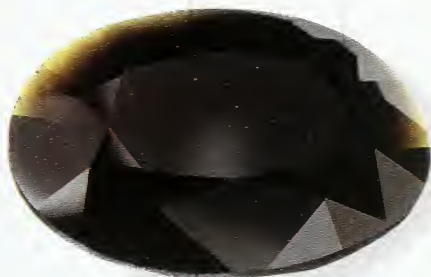

• OVAL BRILLIANT CUT

button shape caused by the way molten glass has cooled •



• TEKTITE ROUGH


surface shows cooling cracks •



• AUSTRALITE ROUGH

tektite varieties are named after their place of origin •

stone may be confused with diopside because of green color •

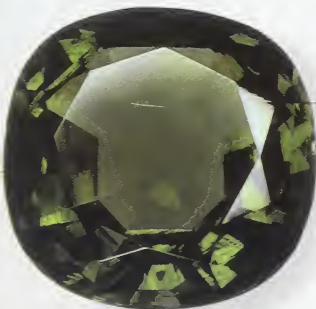

• MOLDAVITE BRILLIANT CUT

• green, transparent material is most suitable for faceting

distinctive craggy, uneven surface •



• MOLDAVITE ROUGH

translucent and transparent in parts •



Brilliant



Cushion



Bead

SG 2.40

RI 1.48–1.51

DR None

Luster Vitreous

Crystal structure Orthorhombic

Composition Calcium carbonate, conchiolin, and water

Hardness 3

PEARL

Pearls are formed in shellfish – especially oysters and mussels – as a natural defense against an irritant such as a piece of grit. Layers of aragonite, known as nacre, are secreted around the irritant and gradually build up to form the solid pearl. Light reflecting from these overlapping layers produces a characteristic iridescent luster, also known as the “orient of pearl.” An irritant is introduced to initiate the formation of a cultured pearl.

In a “nucleated” cultured pearl a small bead is used as the nucleus upon which the layers of nacre are secreted. Pearls vary in color from white, or white with a hint of color (often pink), to brown or black, depending on the type of mollusk and the water. They are sensitive to acids, dryness, and humidity, and so are less durable than many other gems.

• **OCCURRENCE** Natural pearls have been harvested from the Persian Gulf, the Gulf of Manaar (Indian Ocean), and the Red Sea for thousands of years. The coasts of Polynesia and Australia produce mainly cultured pearls. Both freshwater and saltwater pearls are cultivated in Japan and China.

Freshwater pearls occur in the rivers of Scotland, Ireland, France, Austria, Germany, and the USA (Mississippi).

• **REMARK** Pearls were once thought to be the tears of the gods.




pearls form as spheres when irritant is not attached to shell

NATURAL FRESHWATER PEARLS



shell of the pearl oyster (Pinctada maxima)

irregular shapes may develop if irritant is attached to shell



NATURAL FRESHWATER PEARLS

mother-of-pearl lining



SG 2.71

RI 1.53–1.68

DR Not applicable

Luster Pearly

A "BOMBAY BUNCH"

For hundreds of years, Bombay has been an important center for the buying and selling of pearls. To present them for selling, pearls are sorted by size, then strung into bunches on silk thread.

different sizes are included so that a complete necklace can be made from a "bunch"



silver-wire • tassels



Bead

pearl buddhas formed on casts placed inside shell



BUDDHA PEARLS

To produce miniature images of the Buddha, tiny casts were placed into the shell of this pearl mussel (*Cristaria plicata*). The mussel laid down nacreous layers over the casts, forming "blister" pearls. The pearls are later removed and the backs hidden in the mount or covered with mother-of-pearl.

JAPANESE CULTURE

This necklace, made by the Mikimoto company of Japan, uses saltwater cultured pearls. Japan leads the world in the production of cultured pearls, although they have been used by the Chinese for hundreds of years.

• cultured pearls have the same pearly luster as natural specimens



Crystal structure Amorphous

Composition Variety of lignite

Hardness 2½

JET

Jet is organic in origin. Like coal, it was formed from the remains of wood immersed in stagnant water millions of years ago, then compacted and fossilized by the pressures of burial. Jet is black or dark brown but may contain pyrite inclusions, which have a brassy color and metallic luster.

Jet takes a good polish and is often faceted. When burned or touched with a hot needle, it exudes the characteristic smell of coal.

• **OCCURRENCE** Evidence suggests that jet has been mined since about 1400 BC, and worked pieces of jet have been found in prehistoric burial mounds. During the Roman occupation of the British Isles, worked pieces of jet were shipped to Rome. Perhaps the most famous historical source is Whitby in Yorkshire, England, where much of the jet that was so popular for the mourning jewelry of the 19th century originated. During this time the mining and fashioning of jet provided the town with much of its income. Other localities include Spain, France, Germany, Poland, India, Turkey, the former USSR, China, and the USA.

• **REMARK** Jet was popular for mourning jewelry in the 19th century because of its somber color and modest appearance, and it has been traditionally fashioned into rosaries for monks. Jet has also been known as black amber, as it may induce an electric charge like that of amber when rubbed. Powdered jet added to water or wine was believed to have medicinal powers.

triangular facets •



DRILLED AND FACETED BEAD

surface cracks resulting from dehydration •

fine-grained, fragile specimen with rough, cracked surfaces •

dull, earthy luster before polishing •

gems made from jet take a good polish •



OVAL CABOCHON


opaque, with velvety luster •

uppermost surface is convex; back is flat •

faceting can add life to an otherwise dull gem •



ROSE CUT



Because jet is organic, it may dry out, causing the surface to crack.

SG 1.33

RI 1.64–1.68

DR Not applicable

Luster Velvety to waxy



BLACK ROSE

This piece of carved Whitby jet, with a finely wrought rose at the center, dates from the latter part of the 19th century.



VICTORIAN EARRINGS

Jet is light to wear, and so it is particularly suitable for earrings. It was very popular for mourning jewelry in Victorian England.



ammonite fossil

bivalve fossil

highly polished beads



FOSSIL-BEARING JET

The ammonite and bivalve fossils trapped in this jet specimen are evidence of its organic origin.

JET PENDANT

This exquisite pendant of a dove with a heart in its beak shows how well jet can be carved and polished.



TURKISH BEADS

This necklace from eastern Turkey is made from beads of polished and drilled jet. The high polish has given the beads an attractive luster.



Bead



Cameo



Polished

Crystal structure Trigonal

Composition Calcium carbonate or conchiolin

Hardness 3

CORAL

Coral is made up of the skeletal remains of marine animals called coral polyps. These tiny creatures live in colonies that form branching structures as they grow, eventually forming coral reefs and atolls. The surface of these coral "branches" has a distinctive pattern made by the original animals – either striped or like wood grain. Most corals – red, pink, white, and blue varieties – are made of calcium carbonate; black and golden corals are made of a hornlike substance called conchiolin. Red coral is the most valuable and has been used in jewelry for thousands of years. Dull at first, all coral has a vitreous luster when polished but is sensitive to heat and acids and may fade with wear. Coral may be imitated by porcelain, stained bone, glass, plastic, or rubber and gypsum mixtures.

• **OCCURRENCE** Most precious coral is found in warm waters. Japanese coral is red, pink, or white. Red and pink coral is also found on the Mediterranean and African coasts, the Red Sea, and the waters off Malaysia and Japan. Black and golden coral is found off the coasts of the West Indies, Australia, and the Pacific islands.

• **REMARK** Coral has been said to protect children, and parents may still give a gift of coral to their young children.



vivid red
• color

• high polish shows vitreous luster

RED CORAL CABOCHON



polished surface

cross section reveals intricate banded structure

RED CORAL SLICE



red coral from the Mediterranean

• distinctive "wood grain" pattern on surface of branches

RED CORAL

• branches form from coral polyp skeletons



RED CORAL CARVING

This piece of red coral (*Corallium rubrum*) from the Mediterranean has been carved to show a monkey climbing a blossoming tree.

SG 2.68

RI 1.49–1.66

DR Not applicable

Luster Dull to vitreous

distinctive pitted surface

Heliopora caerulea coral found in seas around Philippines

blue coral is often used to make beads



BLUE CORAL

highly polished surface

oval cabochon



BLACK CORAL CABOCHON

coral colonies naturally form branched, tree-like structures

black coral is made from hornlike conchiolin



BLACK CORAL

imitation slabs may be carved, polished, or fashioned as beads


polished bead manufactured by Gilson of France to imitate dark pink coral



IMITATION CORAL BEAD



IMITATION CORAL

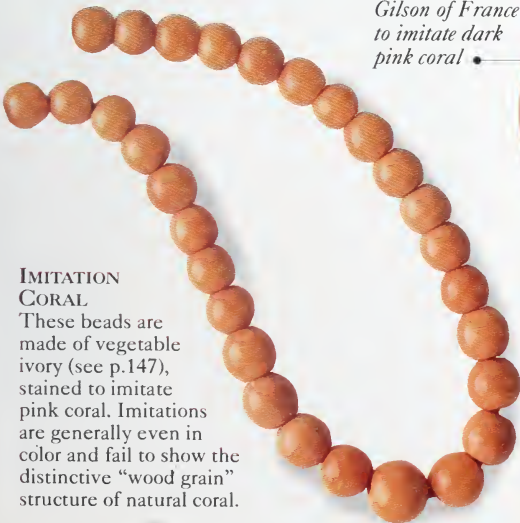


IMITATION CORAL

These beads are made of vegetable ivory (see p.147), stained to imitate pink coral. Imitations are generally even in color and fail to show the distinctive "wood grain" structure of natural coral.



Bead



Cabochon



Cameo

Crystal structure Various

Composition Calcium carbonate

Hardness 2½

SHELL

Shells come in a wide variety of sizes, shapes, and colors and may be fashioned into beads, buttons, jewelry, inlay, knife handles, snuff boxes, and other decorative items. Conch shells with pink and white layers may be carved into intricate and attractive cameos, as may helmet shells, which have white outer layers and golden brown or orange inner layers. The large pearl oysters (*Pinctada maxima* and *P. margaritifera*), abalones (paua), and topshells (Trochidae) are all prized for their iridescent (mother-of-pearl) shell linings. Tortoiseshell comes not from the tortoise but from the hard shell (carapace) of the Hawksbill Turtle. It has rich brown mottling or flamelike patterns on a warm, translucent, golden yellow background and is fashioned by warming the shell to flatten it and to scrape off the ridges. It is then polished and cut to shape.

- **OCCURRENCE** *Pinctada* oysters are found off northern Australia. Abalones are found off the coasts of the USA and paua shells off New Zealand. The Hawksbill Turtle is found in the warm waters of Indonesia and the West Indies.

- **REMARK** Tortoiseshell has now been largely replaced by plastic imitations.



TIGER COWRIE CAMEO

This Asian woman has been carved in a Tiger Cowrie shell (*Cypraea tigris*). The different colored layers have been cut away to create the effect of foreground and background.



• shell found on inshore sands of Indo-Pacific •

• surface layers cut away to leave image in high relief •

ROMAN CAMEO

This cameo has been carved into the shell of *Cassidae madagascarensis*. The detail is picked out in the upper layers of the shell.



bright pink interior may be used for inlay work •

SPIDER CONCH (LAMBIS LAMBIS)

SG 1.30

RI 1.53–1.69

DR Not applicable

Luster Dull to vitreous



HINGED BOX
The lid and base of this box show the distinctive coloring and patterning of tortoiseshell. Some light areas are transparent to semi-transparent; darker areas are opaque.



When magnified, spots can be seen in natural but not in imitation tortoiseshell.



HAIR COMB
This tortoiseshell comb shows attractive, almost fiery, patterns of yellow and brown, with darker patches.

distinctive rich brown mottling


iridescent colors are prized in many forms of jewelry and decorative items

ridges are scraped away during fashioning



TORTOISESHELL (CARAPACE OF HAWKSBILL TURTLE)

nacreous lining is used for jewelry and inlays

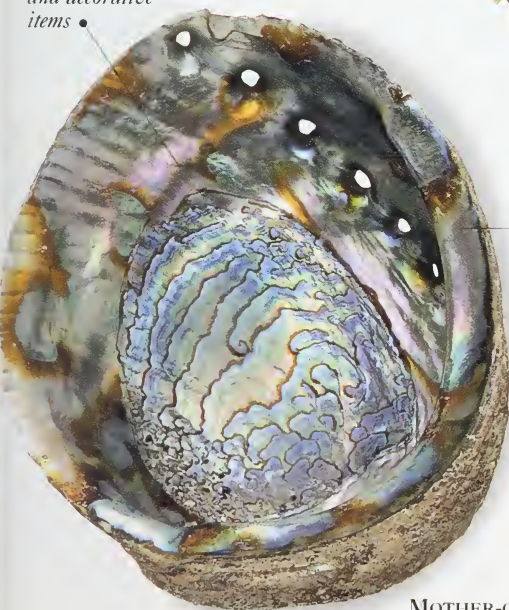

MOTHER-OF-PEARL SHELL



SHELL PILLBOX
The inlay in the lid of this pillbox has been fashioned from the layered, iridescent lining of a shell from the Haliotis family of shellfish.



Cabochon



Cameo



Polished

Crystal structure Amorphous

Composition Calcium hydroxyphosphate and organic

Hardness 2½

IVORY

Ivory has been prized for thousands of years for its rich, creamy color, its fine texture, and its ease of carving. Until quite recently it was a popular material for both jewelry and ornaments, but international restrictions on trading now help to protect the animals from which ivory is taken.

The teeth or tusks of mammals all have ivory as a constituent. Although usually associated with elephants, ivory from the Hippopotamus, Wild Boar, and Warthog is also used. Marine mammals such as the Sperm Whale, Walrus, Sea Lion, and Narwhal have ivory as well. Fossil ivory – from prehistoric animals such as mammoths, mastodons, or dinosaurs – can also be carved.

• **OCCURRENCE** African Elephants' ivory is the most highly valued, with a warm tint and little grain or mottling. Indian Elephants' ivory is a denser white, softer, and easier to work, but it yellows more easily. Ivory markets include Europe, Myanmar, and Indonesia.

• **REMARK** One piece of carved mammoth ivory found in France is estimated to be over 30,000 years old. In China and Japan ivory carving remains popular, even today. However, elsewhere, the use of ivory simulants – bone, horn, jasper, vegetable ivory, plastic, and resin – has been strongly encouraged in order to protect ivory-bearing animals.



INDIAN ELEPHANT IVORY

This intricately fashioned scene was probably carved from the tusk of an Indian Elephant, whose ivory is softer and whiter than the African Elephant's.



AFRICAN ELEPHANT IVORY

Made from warm, mellow African Elephant ivory, this Roman head is worked in the style popular in the 4th to 5th century BC.


thin canals containing nerve fibers



ELEPHANT IVORY CUP

Looking down into this cup, the crisscrossing, curving pattern unique to elephant ivory is visible.

distinctive curved growth lines

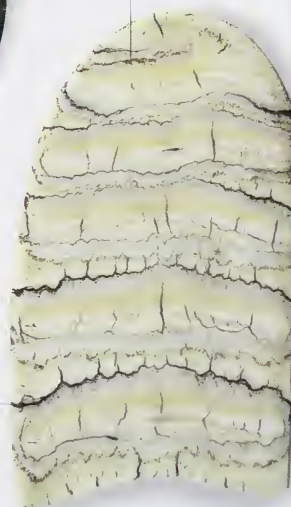

cut and polished molar tooth

POLISHED SECTION OF ELEPHANT TOOTH

SG 1.90

RI 1.53–1.54

DR Not applicable

Luster Dull to greasy



DRILLED BONE

Bone may be used as an ivory simulant. These two pieces have been worked as buttons or beads, with a plain back and carved front.


outer surface has yellowed with time

radial lines



SECTION OF HIPPOPOTAMUS TUSK

surface of Sperm Whale ivory yellows with age

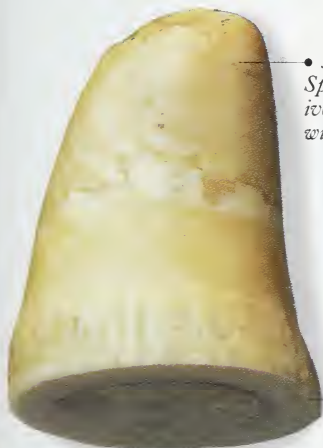

tough outer rim surrounds concentric inner structure

WALRUS IVORY
This necklace is made from stained walrus ivory. Ivory is porous and takes a dye readily.

green-stained beads are intended to imitate jade



PART OF WHALE TOOTH

VEGETABLE IVORY

This necklace is made of polished and drilled vegetable ivory beads, given a pale, artificial stain to imitate coral. Imitation ivory is now greatly encouraged, as more and more ivory-bearing animals face extinction.

beads stained pink to imitate coral



seed of the Doom Palm



hard, creamy white nut used to imitate elephant and other ivories



Bead



Cameo



Polished

VEGETABLE IVORY IN SHELL

Crystal structure	Amorphous	Composition	Mixture of organic plant resins	Hardness	2½
-------------------	-----------	-------------	---------------------------------	----------	----


AMBER

Amber is the fossilized resin of trees. Most amber is golden yellow to golden orange, but green, red, violet, and black amber has been found. Transparent to translucent, it usually occurs as nodules or small, irregularly shaped masses, often with a cracked and weathered surface. Amber may contain insects (and more rarely frogs, toads, and lizards), moss, lichen, or pine needles that were trapped millions of years ago while the resin was still sticky. Air bubbles may give amber a cloudy appearance, but heating in oil will clear this. When rubbed, amber produces a negative electrical charge that attracts dust. "Ambroid" is formed by heating and pressing together scraps of amber.

• **OCCURRENCE** The most famous deposits are in the Baltic region, particularly along the coasts of Poland and the former USSR. Baltic amber (known as succinite) washed from the seabed may reach as far as the coasts of England, Norway, and Denmark. Amber from Myanmar is called burmite; Sicilian amber is known as simetite. Other localities include the Dominican Republic, Mexico, France, Spain, Italy, Germany, Romania, Canada, Czechoslovakia, and the USA.

• **REMARK** Amber has had a number of medicinal uses attributed to it, but today it is used almost exclusively for jewelry. It has been imitated by plastic, glass, synthetic resin, and other natural resins, like copal.

characteristic golden orange color •

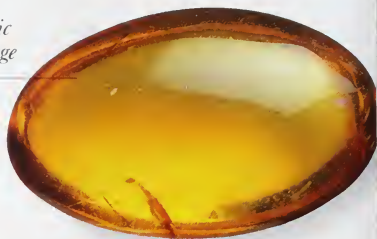

resinous luster •

transparent bead •



POLISHED BEADS

cracks produce spangling effect •

cracks may be caused by heat treatment •



POLISHED "SUN-SPANGLED" BEAD *weathered surface* •

cloudy, opaque area •

transparent area •



PARTLY POLISHED AMBER

pebble found washed up on beach •

BALTIC AMBER ROUGH



SG	1.08	RI	1.54–1.55	DR	Not applicable	Luster	Resinous
----	------	----	-----------	----	----------------	--------	----------

probably of Romano-British origin, around 1st century AD •



• golden yellow color

• river water has protected bead from drying out

ROMAN BEAD FOUND IN RIVER SILT


fly trapped in sticky resin, before fossilization •

amber may contain plants and insects, and occasionally • frogs or lizards



FLY IN AMBER

artificially colored brown, although a range of colors may be produced •

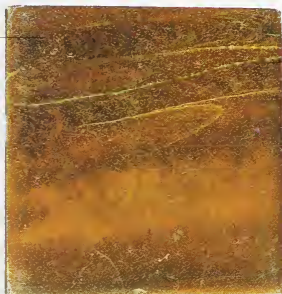

ambroid is made by warming and compressing small • pieces of amber

SQUARE AMBROID

BEAD NECKLACE
Some of the 31 drilled, cut, and polished amber beads that make up this necklace show signs of dehydration. This is a common problem with amber jewelry, which will dry out if left in the sun or worn in the heat of the day.

AMBER ORNAMENT

This Chinese ear ornament has been worked in the shape of a panda bear. The cracks are due to dehydration of the stone.



cracked • surface



Bead



Cabochon



Cameo



Polished

transparent beads have warm glow •



• *dehydrated bead*

• *numerous four-sided facets*

TABLE OF PROPERTIES

THIS TABLE INCLUDES all of the technical information for each gem species, arranged alphabetically by gem name. By so doing, it is intended to give the reader an at-a-glance reference to the more important physical and optical properties of each gem species.

The chemical composition of each gem is shown here by a formula, which includes all essential elements of that gem. Composition may vary slightly, depending on locality and conditions of formation. The physical properties of the gems – their hardness and specific gravity – are given as mean (average) values. Hardness is denoted by a figure from the Mohs scale of hardness, a scale used to classify the hardness of minerals relative to one another. The intervals between successive values are unequal, and an intermediate value such as 3½ denotes that the hardness is between 3 and 4, but it is not necessarily exactly halfway between. Hardness may vary slightly depending upon exact chemical content, so a mean figure is given here. The values for specific gravity (SG), which give an indication of the density of a gem, are also given as mean figures.

The optical properties of the gems are represented here by the refractive indices (RI) and the birefracton (DR).

They are related to crystal structure: a gem with cubic structure has a single value as its refractive index (RI); doubly refracting gems have two refractive indices (see p.21). Doubly refracting gems also have a value of birefracton (DR), found by using a refractometer. This figure is the difference between the highest and the lowest refractive indices. Physical and optical properties are continually reviewed as new minerals are discovered and new deposits exploited, so all figures given here are mean values, to be used as a guide only.

KEY TO CHEMICAL ELEMENTS IN THIS BOOK

Al	ALUMINUM	Mg	MAGNESIUM
Ag	SILVER	Mn	MANGANESE
Au	GOLD	Na	SODIUM
B	BORON	O	OXYGEN
Ba	BARIUM	P	PHOSPHORUS
Be	BERYLLIUM	Pb	LEAD
C	CARBON	Pt	PLATINUM
Ca	CALCIUM	S	SULFUR
Cl	CHLORINE	Si	SILICON
Cr	CHROMIUM	Sn	TIN
Cu	COPPER	Sr	STRONTIUM
F	FLUORINE	Ti	TITANIUM
Fe	IRON	W	TUNGSTEN
H	HYDROGEN	Zn	ZINC
K	POTASSIUM	Zr	ZIRCONIUM
Li	LITHIUM		

NAME & CHEMICAL COMPOSITION	STRUCTURE	HARDNESS	SG	RI	DR
ACHROITE (TOURMALINE) Na(Li,Al) ₃ Al ₆ (BO ₃) ₃ Si ₆ O ₁₈ (OH) ₄	Trigonal	7½	3.06	1.62–1.64	0.018
AGATE (CHALCEDONY) SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
ALBITE (Na,Ca)AlSi ₃ O ₈	Triclinic	6	2.64	1.54–1.55	0.009
ALMANDINE (GARNET) Fe ₃ Al ₂ (SiO ₄) ₃	Cubic	7½	4.00	1.76–1.83	None
AMBER mainly C ₁₀ H ₁₆ O	Amorphous	2½	1.08	1.54–1.55	N/A

NAME & CHEMICAL COMPOSITION	STRUCTURE	HARDNESS	SG	RI	DR
AMBLYGONITE $\text{LiAl}(\text{F,OH})\text{PO}_4$	Triclinic	6	3.02	1.57–1.60	0.026
AMETHYST (QUARTZ) SiO_2	Trigonal	7	2.65	1.54–1.55	0.009
ANDALUSITE Al_2SiO_5	Orthorhombic	7½	3.16	1.63–1.64	0.010
ANDRADITE GARNET $\text{Ca}_3\text{Fe}_2(\text{SiO}_4)_3$	Cubic	6½	3.85	1.85–1.89	None
ANGLESITE PbSO_4	Orthorhombic	3	6.35	1.87–1.89	0.017
APATITE $\text{Ca}(\text{F,Cl})\text{Ca}_4(\text{PO}_4)_3$	Hexagonal	5	3.20	1.63–1.64	0.003
AQUAMARINE (BERYL) $\text{Be}_3\text{Al}_2(\text{SiO}_3)_6$	Hexagonal	7½	2.69	1.57–1.58	0.006
ARAGONITE CaCO_3	Orthorhombic	3½	2.94	1.53–1.68	0.155
AVENTURINE QUARTZ SiO_2	Trigonal	7	2.65	1.54–1.55	0.009
AXINITE $\text{CaFeMgBaAl}_2\text{Si}_4\text{O}_{15}(\text{OH})$	Triclinic	7	3.28	1.67–1.70	0.011
AZURITE $\text{Cu}_3(\text{OH})_2(\text{CO}_3)_2$	Monoclinic	3½	3.77	1.73–1.84	0.110
BARITE BaSO_4	Orthorhombic	3	4.45	1.63–1.65	0.012
BENITOITE $\text{BaTiSi}_3\text{O}_9$	Hexagonal	6½	3.67	1.76–1.80	0.047
BERYLLONITE NaBePO_4	Monoclinic	5½	2.83	1.55–1.56	0.009
BLOODSTONE (CHALCEDONY) SiO_2	Trigonal	7	2.61	1.53–1.54	0.004
BRAZILIANITE $\text{Al}_3\text{Na}(\text{PO}_4)_2(\text{OH})_4$	Monoclinic	5½	2.99	1.60–1.62	0.021
BROWN QUARTZ (SMOKY QUARTZ) SiO_2	Trigonal	7	2.65	1.54–1.55	0.009
CALCITE CaCO_3	Trigonal	3	2.71	1.48–1.66	0.172
CARNELIAN (CHALCEDONY) SiO_2	Trigonal	7	2.61	1.53–1.54	0.004
CASSITERITE SnO_2	Tetragonal	6½	6.95	2.00–2.10	0.100
CELESTINE SrSO_4	Orthorhombic	3½	3.98	1.62–1.63	0.010
CERUSSITE PbCO_3	Orthorhombic	3½	6.51	1.80–2.08	0.274
CHALCEDONY SiO_2	Trigonal	7	2.61	1.53–1.54	0.004
CHATOYANT QUARTZ SiO_2	Trigonal	7	2.65	1.54–1.55	0.009
CHRYSOBERYL BeAl_2O_4	Orthorhombic	8½	3.71	1.74–1.75	0.009

NAME & CHEMICAL COMPOSITION	STRUCTURE	HARDNESS	SG	RI	DR
CHRYSOCOLLA (Cu,Al) ₂ H ₂ Si ₂ O ₃ (OH) ₄ nH ₂ O	Monoclinic	2	2.20	1.57–1.63	0.030
CHRYSOPRASE (CHALCEDONY) SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
CITRINE (QUARTZ) SiO ₂	Trigonal	7	2.65	1.54–1.55	0.009
CORAL CaCO ₃ (or C ₃ H ₄₈ N ₉ O ₁₁)	Trigonal	3	2.68	1.49–1.66	N/A
DANBURITE CaB ₂ (SiO ₄) ₂	Orthorhombic	7	3.00	1.63–1.64	0.006
DATOLITE Ca(B,OH)SiO ₄	Monoclinic	5	2.95	1.62–1.65	0.044
DIAMOND C	Cubic	10	3.52	2.42	None
DIOPSIDE CaMg(SiO ₃) ₂	Monoclinic	5½	3.29	1.66–1.72	0.029
DIOPTAISE CuOSiO ₂ H ₂ O	Trigonal	5	3.31	1.67–1.72	0.053
DOLOMITE CaMg(CO ₃) ₂	Trigonal	3½	2.85	1.50–1.68	0.179
DRAWITE (TOURMALINE) NaMg ₃ Al ₆ (BO ₃) ₃ Si ₆ O ₁₈ (OH) ₄	Trigonal	7½	3.06	1.61–1.63	0.018
DUMORTIERITE Al ₇ (BO ₃)(SiO ₄) ₃ O ₃	Orthorhombic	7	3.28	1.69–1.72	0.037
EMERALD (BERYL) Be ₃ Al ₂ (SiO ₃) ₆	Hexagonal	7½	2.71	1.57–1.58	0.006
ENSTATITE Mg ₂ Si ₂ O ₆	Orthorhombic	5½	3.27	1.66–1.67	0.010
EPIDOTE Ca ₂ (Al,Fe) ₃ (OH)(SiO ₄) ₃	Monoclinic	6½	3.40	1.74–1.78	0.035
EUCLASE Be(Al,OH)SiO ₄	Monoclinic	7½	3.10	1.65–1.67	0.019
FIRE AGATE (CHALCEDONY) SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
FLUORITE CaF ₂	Cubic	4	3.18	1.43	None
GOLD Au	Cubic	2½	19.30	None	None
GOSHENITE (BERYL) Be ₃ Al ₂ (SiO ₃) ₆	Hexagonal	7½	2.80	1.58–1.59	0.008
GROSSULAR (GARNET) Ca ₃ Al ₂ (SiO ₄) ₃	Cubic	7	3.49	1.69–1.73	None
GYPSUM CaSO ₄ ·2H ₂ O	Monoclinic	2	2.32	1.52–1.53	0.010
HAMBERGITE Be ₂ (OH)BO ₃	Orthorhombic	7½	2.35	1.55–1.63	0.072
HAUYNE (Na,Ca) ₄₋₈ Al ₆ Si ₆ (O,S) ₂₄ (SO ₄ Cl) ₁₋₂	Cubic	6	2.40	1.50 (mean)	None
HELIODOR (BERYL) Be ₃ Al ₂ (SiO ₃) ₆	Hexagonal	7½	2.80	1.57–1.58	0.005

NAME & CHEMICAL COMPOSITION	STRUCTURE	HARDNESS	SG	RI	DR
HEMATITE Fe_2O_3	Trigonal	6½	5.20	2.94–3.22	0.280
HESSONITE (GROSSULAR GARNET) $\text{Ca}_3\text{Al}_2(\text{SiO}_4)_3$	Cubic	7½	3.65	1.73–1.75	None
HOWLITE $\text{C}_2\text{B}_5\text{SiO}_9(\text{OH})_3$	Monoclinic	3½	2.58	1.58–1.59	0.022
HYPERSTHENE (Fe,Mg)SiO ₃	Orthorhombic	5½	3.35	1.65–1.67	0.010
INDICOLITE (TOURMALINE) $\text{Na}(\text{Li,Al})_3\text{Al}_6(\text{BO}_3)_3\text{Si}_6\text{O}_{18}(\text{OH})_4$	Trigonal	7½	3.06	1.62–1.64	0.018
IOLITE $\text{Mg}_2\text{Al}_4\text{Si}_3\text{O}_{18}$	Orthorhombic	7	2.63	1.53–1.55	0.010
IVORY $\text{Ca}_5(\text{PO}_4)_3(\text{OH})$ and organic material	Amorphous	2½	1.90	1.53–1.54	N/A
JADEITE (JADE) $\text{Na}(\text{Al,Fe})\text{Si}_2\text{O}_6$	Monoclinic	7	3.33	1.66–1.68	0.012
JASPER (CHALCEDONY) SiO_2	Trigonal	7	2.61	1.53–1.54	0.004
JET Lignite	Amorphous	2½	1.33	1.64–1.68	N/A
KORNERUPINE $\text{Mg}_4(\text{Al,Fe})_6(\text{Si,B})_4\text{O}_{21}(\text{OH})$	Orthorhombic	6½	3.32	1.66–1.68	0.013
KYANITE Al_2SiO_5	Triclinic	5 or 7	3.68	1.71–1.73	0.017
LABRADORITE (Na,Ca)(Al,Si) ₄ O ₈	Triclinic	6	2.70	1.56–1.57	0.010
LAPIS LAZULI (LAZURITE) $(\text{Na,Ca})_8(\text{Al,Si})_{12}\text{O}_{24}(\text{SO}_4)\text{Cl}_2(\text{OH})_2$	Various	5½	2.80	1.50 (mean)	None
LAZULITE $\text{MgAl}_2(\text{PO}_4)_2(\text{OH})_2$	Monoclinic	5½	3.10	1.61–1.64	0.031
MALACHITE $\text{Cu}_2(\text{OH})_2\text{CO}_3$	Monoclinic	4	3.80	1.85 (mean)	0.025
MEERSCHAUM $\text{Mg}_3\text{Si}_6\text{O}_{15}(\text{OH})_2 \cdot 6\text{H}_2\text{O}$	Monoclinic	2½	1.50	1.51–1.53	None
MICROCLINE KAlSi_3O_8	Triclinic	6	2.56	1.52–1.53	0.008
MILKY QUARTZ SiO_2	Trigonal	7	2.65	1.54–1.55	0.009
MOONSTONE (ORTHOCLASE) KAlSi_3O_8	Monoclinic	6	2.57	1.52–1.53	0.005
MORGANITE (BERYL) $\text{Be}_3\text{Al}_2(\text{SiO}_3)_6$	Hexagonal	7½	2.80	1.58–1.59	0.008
NEPHRITE (JADE) $\text{Ca}_2(\text{Mg,Fe})_5\text{Si}_3\text{O}_{22}(\text{OH})_2$	Monoclinic	6½	2.96	1.61–1.63	0.027
OBSDIAN Mainly SiO_2	Amorphous	5	2.35	1.48–1.51	None
OLIGOCLASE (Na,Ca)(Al,Si) ₄ O ₈	Triclinic	6	2.64	1.54–1.55	0.007
ONYX SiO_2	Trigonal	7	2.61	1.53–1.54	0.004

NAME & CHEMICAL COMPOSITION	STRUCTURE	HARDNESS	SG	RI	DR
OPAL SiO ₂ ·nH ₂ O	Amorphous	6	2.10	1.37–1.47	None
ORTHOCLASE KAlSi ₃ O ₈	Monoclinic	6	2.56	1.51–1.54	0.005
PADPARADSCHA (CORUNDUM) Al ₂ O ₃	Trigonal	9	4.00	1.76–1.77	0.008
PEARL CaCO ₃ ·C ₃ H ₁₈ N ₉ O ₁₁ ·nH ₂ O	Orthorhombic	3	2.71	1.53–1.68	N/A
PERIDOT (Mg,Fe) ₂ SiO ₄	Orthorhombic	6½	3.34	1.64–1.69	0.036
PETALITE Li ₂ OAl ₂ O ₃ ·8SiO ₂	Monoclinic	6	2.42	1.50–1.51	0.014
PHENAKITE Be ₂ SiO ₄	Trigonal	7½	2.96	1.65–1.67	0.015
PHOSPHOHYLLITE Zn ₂ (Fe,Mn)(PO ₄) ₂ ·4H ₂ O	Monoclinic	3½	3.10	1.59–1.62	0.021
PLASMA (CHALCEDONY) SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
PLATINUM Pt	Cubic	4	21.40	None	None
PRASE (CHALCEDONY) SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
PREHNITE Ca ₂ Al ₂ Si ₃ O ₁₀ (OH) ₂	Orthorhombic	6	2.87	1.61–1.64	0.016
PYRITE FeS ₂	Cubic	6	4.90	None	None
PYROPE (GARNET) Mg ₃ Al ₂ (SiO ₄) ₃	Cubic	7¼	3.80	1.72–1.76	None
RHODOCHROSITE MnCO ₃	Trigonal	4	3.60	1.60–1.80	0.220
RHODONITE (Mn,Fe,Mg,Ca)SiO ₃	Triclinic	6	3.60	1.71–1.73	0.014
ROCK CRYSTAL (QUARTZ) SiO ₂	Trigonal	7	2.65	1.54–1.55	0.009
ROSE QUARTZ SiO ₂	Trigonal	7	2.65	1.54–1.55	0.009
RUBELLITE (TOURMALINE) Na(Li,Al) ₃ Al ₆ (BO ₃) ₃ Si ₆ O ₁₈ (OH) ₄	Trigonal	7½	3.06	1.62–1.64	0.018
RUBY (CORUNDUM) Al ₂ O ₃	Trigonal	9	4.00	1.76–1.77	0.008
RUTILE TiO ₂	Tetragonal	6	4.25	2.62–2.90	0.287
SAPPHIRE (CORUNDUM) Al ₂ O ₃	Trigonal	9	4.00	1.76–1.77	0.008
SARD SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
SARDONYX (CHALCEDONY) SiO ₂	Trigonal	7	2.61	1.53–1.54	0.004
SCAPOLITE Na ₄ Al ₃ Si ₉ O ₂₄ Cl–Ca ₄ Al ₆ Si ₆ O ₂₄ (CO ₃ ,SO ₄)	Tetragonal	6	2.70	1.54–1.58	0.020

NAME & CHEMICAL COMPOSITION	STRUCTURE	HARDNESS	SG	RI	DR
SCHEELITE CaWO ₄	Tetragonal	5	6.10	1.92–1.93	0.017
SCHORL (TOURMALINE) NaFe ₃ Al ₆ (BO ₃) ₃ Si ₆ O ₁₈ (OH) ₄	Trigonal	7½	3.06	1.62–1.67	0.018
SERPENTINE Mg ₆ (OH) ₈ Si ₄ O ₁₀	Monoclinic	5	2.60	1.55–1.56	0.001
SHELL CaCO ₃ and C ₃₂ H ₄₈ N ₂ O ₁₁	Various	2½	1.30	1.53–1.59	N/A
SILLIMANITE Al ₂ SiO ₅	Orthorhombic	7½	3.25	1.66–1.68	0.019
SILVER Ag	Cubic	2½	10.50	None	None
SINHALITE Mg(Al,Fe)BO ₄	Orthorhombic	6½	3.48	1.67–1.71	0.038
SMITHSONITE ZnCO ₃	Trigonal	5	4.35	1.62–1.85	0.230
SODALITE 3NaAlSi ₃ O ₈ NaCl	Cubic	5½	2.27	1.48 (mean)	None
SPESSARTINE (GARNET) Mn ₃ Al ₂ (SiO ₄) ₃	Cubic	7	4.16	1.79–1.81	None
SPHALERITE (Zn,Fe)S	Cubic	3½	4.09	2.36–2.37	None
SPINEL MgAl ₂ O ₄	Cubic	8	3.60	1.71–1.73	None
SPODUMENE LiAl(SiO ₃) ₂	Monoclinic	7	3.18	1.66–1.67	0.015
STAUROLITE (Fe,Mg,Zn) ₂ Al ₉ (Si,Al) ₄ O ₂₂ (OH) ₂	Orthorhombic	7	3.72	1.74–1.75	0.013
TAAFEITE BeMg ₃ Al ₈ O ₁₆	Hexagonal	8	3.61	1.72–1.77	0.004
TEKTITES Mainly SiO ₂	Amorphous	5	2.40	1.48–1.51	None
TITANITE (SPHENE) CaTiSiO ₅	Monoclinic	5	3.53	1.84–2.03	0.120
TOPAZ Al ₂ (F,OH) ₂ SiO ₄	Orthorhombic	8	3.54	1.62–1.63	0.010
TUGTUPITE Na ₄ AlBeSi ₄ O ₁₂ Cl	Tetragonal	6	2.40	1.49–1.50	0.006
TURQUOISE CuAl ₆ (PO ₄) ₄ (OH) ₈ ·5H ₂ O	Triclinic	6	2.80	1.61–1.65	0.040
UVAROVITE (GARNET) Ca ₃ Cr ₂ (SiO ₄) ₃	Cubic	7½	3.77	1.86–1.87	None
VESUVIANITE (IDOCRASE) Ca ₆ Al(Al,OH)(SiO ₄) ₅	Tetragonal	6½	3.40	1.70–1.75	0.005
WATERMELON TOURMALINE Na(Li,Al) ₃ Al ₆ (BO ₃) ₃ Si ₆ O ₁₈ (OH) ₄	Trigonal	7½	3.06	1.62–1.64	0.018
ZIRCON ZrSiO ₄	Tetragonal	7½	4.69	1.93–1.98	0.059
ZOISITE Ca ₂ (Al,OH)Al ₂ (SiO ₄) ₃	Orthorhombic	6½	3.35	1.69–1.70	0.010

GLOSSARY

WORDS PRINTED in bold type have their own definition elsewhere in the glossary.

• **ABSORPTION SPECTRUM**

Pattern of dark lines or bands seen when a gem is viewed through a spectroscope.

• **ALLOCHROMATIC**

Refers to gems colored by impurities, without which the gem would be colorless.

• **ALLUVIAL DEPOSITS**

Concentrations of material that have been separated by weathering from the host rock, then deposited by rivers or streams.

• **AMORPHOUS**

Without a regular internal atomic structure or external shape.

• **ASSOCIATED MINERALS**

Minerals found growing together, though not necessarily intergrown.

• **ASTERISM**

Star effect seen on some stones when cut *en cabochon*.

• **BASAL PINACOID**

Feature relating to crystal symmetry. A **columnar** or **prismatic** crystal with flat ends may be referred to as having a basal pinacoid.

• **BIREFRACTION (DR)**

The difference between the highest and the lowest **refractive indices** in doubly refractive gems.

• **BOTRYOIDAL**

Shape similar to a bunch of grapes.

• **CABOCHON**

Gem cut and polished to have a domed upper surface. Such stones are said to be cut *en cabochon*.

• **CAMEO**

Design in low relief, around which the background has been cut away.

• **CARAT (CT)**

Unit of weight used for gems – a carat is one-fifth of a gram. It is also used to describe the purity of gold – pure gold is 24 carat.

• **CHATOYANCY**

The cat's-eye effect shown by some stones when cut *en cabochon*.

• **CLEAVAGE**

Breaking of a stone along lines of weakness related to the internal atomic structure. *See also* **Fracture**.

• **COLUMNAR**

Type of **habit** in which crystals form in the shape of columns (elongated prisms).

• **COMPOSITE STONE**

Stone assembled from several pieces, often to imitate a gem.

• **CONCHOIDAL FRACTURE**

Shell-like fracture. *See* **Fracture**.

• **CROWN**

Top part of a cut stone, above the **girdle**.

• **CRYPTOCRYSTALLINE**

Mineral structure in which crystals are so small they are not distinguishable with a microscope.

• **CRYSTAL**

Solid that has a definite internal atomic structure, producing a characteristic external shape and physical and optical properties.

• **CRYSTAL STRUCTURE**

Internal atomic structure of a crystal. All crystalline gems may be classified in one of seven groups, according to the symmetry of their structure: cubic, tetragonal, hexagonal, trigonal, orthorhombic, monoclinic, and triclinic.

• **CUT**

Term used to describe the way in which a stone is faceted. *See also* **Faceting**.

• **DICHROIC**

Refers to a gem that appears two different colors or shades when viewed from different directions.

• **DIFFRACTION**

The splitting of white light into its constituent spectral colors – the colors of the rainbow – when it passes through a hole or grating.

• **DISPERSION**

The splitting of white light into its constituent spectral colors – the rainbow colors – when it passes through inclined surfaces, such as those on a **prism** or faceted gem. Dispersion in gems is called fire.

• **DOUBLE REFRACTION (DR)**

Phenomenon in which each ray of light is split in two as it enters a noncubic **mineral**. Each ray travels at a different speed and has its own **refractive index**. *See also* **Birefraction**.

• **DOUBLET**

Composite stone made of two pieces cemented or glued together.

• **EVAPORITE DEPOSIT**

Sedimentary rock or **mineral** resulting from the evaporation of water from mineral-bearing fluids, usually seawater.

• **FACES**

Flat surfaces that make up the external shape of a crystal.

• **FACET**

Surface of a cut and polished gem.

• **FACETING**

Cutting and polishing of the surfaces of a **gemstone** into facets. The number and shape of the facets give the stone its style of cut.

• **FANCY CUT**

Name applied to a stone given an unconventional shape when cut.

• **FIRE**

See **Dispersion**.

• **FRACTURE**

Chipping or breaking of a stone in a way unconnected to the internal atomic structure. Because of this, fracture surfaces are usually uneven. *See also* **Cleavage**.

• **GEMSTONE**

Decorative material, usually a **mineral**, prized for some or all of the qualities of beauty, durability, and rarity. It is used synonymously with "gem" and "stone" throughout this book.

• **GEODE**

Cavity within a rock, in which crystals line the inner surface and grow toward the center.

• **GIRDLE**

Band around the widest part of a cut stone, where the **crown** meets the **pavilion**.

• **GRANITE**

Coarse-grained **igneous rock** comprising mainly quartz, feldspar, and mica.

• **HABIT**

Shape in which a crystal naturally occurs.

• **HARDNESS**

See **Mohs Scale of Hardness**.

• **HEAT TREATMENT**

Application of heat to a gem with the purpose of enhancing the color or clarity.

• **HYDROTHERMAL**

Refers to processes that involve the alteration or deposition of minerals by water heated by igneous activity.

• **IDIOCHROMATIC**

Describes gems whose color is due to elements that are an essential part of their chemical composition.

• **IGNEOUS ROCKS**

Rocks formed from erupted volcanic lava or solidified magma.

• **IMITATION GEMSTONE**

Material that has the outward appearance of the gem it is intended to imitate, but which has different physical properties. *See also Synthetic gemstone.*

• **INCLUSIONS**

Markings or foreign bodies found within a stone. Some can be used to identify a particular species.

• **INTAGLIO**

Design in which the subject is cut lower than the background.

• **INTERGROWN**

When two or more minerals grow together and become interlocked.

• **INTRUSIVE**

Igneous rock that has solidified within other rocks, below the Earth's surface.

• **IRIDESCENCE**

Reflection of light off internal features in a gem, giving rise to a rainbowlike play of colors.

• **LAPIDARY**

Craftsman who cuts and polishes gemstones.

• **LAVA**

Molten rock erupted from volcanoes. *See also Magma.*

• **LUSTER**

Shine or "look" of a gemstone due to reflection of light off the surface.

• **MAGMA**

Rock in a molten state below the Earth's surface. *See also Lava.*

• **MAMMILLATED**

Smooth, rounded shape.

• **MASSIVE**

Used to describe minerals that have an indefinite shape, or that consist of small crystals in masses.

• **MATRIX**

The rock in which a gem is found. Also known as host or parent rock.

• **METAMICT**

Refers to material that is breaking down from a crystalline to an amorphous state, due to the presence of radioactive elements.

• **METAMORPHIC ROCKS**

Rocks that have been changed by heat and/or pressure to form new rocks consisting of new minerals.

• **MICROCRYSTALLINE**

Mineral structure in which crystals are too small to be detected by the naked eye.

• **MINERALS**

Inorganic, naturally occurring materials with a constant chemical composition and regular internal atomic structure.

• **MIXED CUT**

Cut in which the facets above and below the girdle are styled in different ways – usually brilliant cut above and step cut below.

• **MOHS SCALE OF HARDNESS**

Measure of a mineral's hardness in relation to other minerals, based on its ability to resist scratching.

• **MULTICOLORED**

Used to describe single crystals made of different colored parts.

• **OPALESCECE**

Milky blue form of iridescence.

• **ORE**

Rock that contains metals capable of being extracted commercially.

• **ORGANIC GEM**

Gem made by or derived from living organisms.

• **PASTE**

Glass made to imitate gems.

• **PAVILION**

Lower part of a cut stone, below the girdle.

• **PEGMATITE**

An igneous rock formed as residual liquids from magma cool, often forming large crystals.

• **PLACER DEPOSIT**

Concentrated (secondary) deposit of minerals, usually in rivers or seas.

• **PLATY**

Habit characterized by flat, thin, platelike crystals.

• **PLEOCHROIC**

Term used to describe a gem that appears two or more different colors or shades when viewed from different directions.

• **POLYCRYSTALLINE**

Refers to a mineral made of many small crystals.

• **PRIMARY DEPOSIT**

Material still in its original rock. *See also Secondary deposit.*

• **PRISMATIC**

Habit in which parallel pairs of rectangular faces form prisms.

• **PSEUDOMORPH**

One mineral occurring in the crystal shape of another.

• **REFRACTION**

Bending of light as it passes from air into a different medium.

• **REFRACTIVE INDEX (RI)**

Measure of the slowing down and bending of light rays as they enter a gemstone. May be used to identify individual gem species.

• **REFRACTOMETER**

Apparatus used to measure the refractive indices of gems.

• **RHOMB**

Shape much like a skewed cube.

• **ROCK**

Material made up of one or more minerals.

• **ROUGH**

Term used to describe a rock or crystal still in its natural state, before faceting or polishing.

• **SCHILLER/SHEEN**

Form of iridescence.

• **SCHIST**

Metamorphic rock in which the crystals are in parallel arrangement.

• **SECONDARY DEPOSIT**

Gems or minerals that have been separated from their original rock and redeposited elsewhere. *See also Primary deposit.*

• **SEDIMENTARY ROCKS**

Rocks formed by the consolidation and hardening of rock fragments, organic remains, or other material.

• **SPECIES**

Used in this book to refer to individual gems that have distinct characteristics which may be defined and verified.

• **SPECIFIC GRAVITY (SG)**

Density, measured as the weight of the material compared with that of an equal volume of water.

• **SPECTROSCOPE**

Instrument used to view the absorption spectra of gemstones.

• **STEP CUT (OR TRAP CUT)**

Cut characterized by a rectangular table facet and girdle, with rectangular facets parallel to these.

• **STONE**

Term used for any gemstone.

• **STRIATION**

Parallel scratch, groove, or line.

• **SYMMETRY, AXIS OF**

Imaginary line through a crystal. If the crystal were rotated about its axis it would present an identical aspect two or more times in a rotation of 360 degrees.

• **SYNTHETIC GEMSTONE**

Laboratory-made stone whose chemical composition and optical properties are similar to those of its natural equivalent.

• **TABLE FACET**

Central facet on a gem's crown.

• **TRICHROIC**

Refers to a gem that appears three different colors or shades when viewed from different directions.

• **VITREOUS**

Glasslike (used to describe luster).

INDEX

A

achroite 102
 adularia 122
 agate 88
 alabaster 128
 albite 130
 alexandrite 108
 allochromatic gems 20
 almandine 59
 amazonite 123
 amber 148
 amblygonite 132
 amethyst 148
 amethyst 82
 ametrine 82
 andalusite 110
 andradite garnet 62
 anglesite 114
 apatite 79
 aquamarine 76
 aragonite 104
 asparagus stone 79
 australite 137
 aventurine quartz 85
 aventurine feldspar 130
 axinite 133
 azurite 126

B

barite 104
 benitoite 80
 beryl
 aquamarine 76
 bixbite 78
 emerald 75
 goshenite 77
 heliodor 77
 morganite 78
 red 78
 beryllonite 118
 birefracton 21
 birthstones 33
 bixbite 78
 blende 63
 bloodstone 93
 Blue John 67

boule 34
 bowenite 127
 brazilianite 118
 brown quartz 84
 bronzite 112
 burmite 148

C

cairngorm 84
 calcite 98
 californite 74
 carnelian 93
 carving 28
 cassiterite 70
 cat's-eye 108
 celestine 105
 cerussite 105
 chalcedony
 agate 88
 bloodstone 93
 carnelian 93
 chrysoprase 92
 cornelian 93
 fire agate 87
 fortification agate 88
 heliotrope 93
 jasper 92
 landscape agate 89
 moss agate 88
 onyx 90
 plasma 93
 prase 92
 sard 90
 sardonyx 90
 chatoyant quartz 86
 chessylite 126
 chiastolite 110
 chrome diopside 119
 chrysoberyl 108
 chrysocolla 126
 chrysoprase 92
 cinnamon stone 60

citrine 83
 cleavage 17
 color key 38
 colorless orthoclase 122
 colorless sapphire 96
 coral 142
 cordierite 112
 cornelian 93
 corundum
 colorless sapphire 96
 green sapphire 96
 padparadscha 95
 pink sapphire 97
 ruby 94
 sapphire 95
 yellow sapphire 97
 crystal shapes 18
 crystal systems 19
 cutting 10
 cymophane 108
 cyprine 74

D

danburite 110
 datolite 129
 demantoid garnet 62
 diamond 54
 dichroite 112
 diopside 119
 diopside 99
 dolomite 99
 dravite 102
 dumortierite 117
 dumortierite quartz 117

E

emerald 75
 engraving 29
 enstatite 111
 epidote 121
 euclase 129

F



faceting 26
 fibrolite 111
 fire agate 87
 fluorite 66
 fool's gold 63
 formation 12
 fortification agate 88
 fracture 17

G

gahnospinel 65
 garnet
 almandine 59
 andradite 62
 cinnamon stone 60
 demantoid 62
 green grossular 61
 hessonite 60
 pink grossular 60
 pyrope 58
 rosolite 60
 spessartine 58
 Transvaal jade 61
 tavorite 61
 uvarovite 59
 garnet-topped doublet 61
 gemology 7
 gems, collecting 8
 gemstones
 defined 10
 distribution 14
 folklore 32
 history 30
 Gilson gems 35
 gold 48
 goshenite 77
 green and yellow
 tourmaline 103
 green grossular 61
 green sapphire 96
 grossular garnet 60
 gypsum 128

H

hambergite 115
 hardness 16
 hayne 68
 hawk's-eye 86
 heat treatment 37
 heliodor 77
 heliotrope 93
 hematite 100
 hessonite 60
 hiddenite 120
 howlite 128
 hypersthene 112

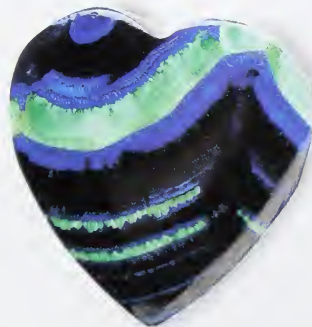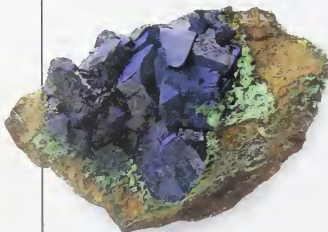

I
 idiochromatic gems 20
 idocrase 74
 igneous rocks 12
 imitation 36
 Inca rose 100
 inclusions 24
 indicolite 101
 indigolite 101
 interference 23
 iolite 112
 iron rose 100
 irradiation 37
 ivory 146

J
 jade
 jadeite 124
 nephrite 125
 jasper 92
 jet 140

K
 Knoop scale 16
 kornerupine 113
 kunzite 120
 kyanite 133

L
 labradorite 130
 landscape agate 89
 lapis lazuli 69
 lazulite 128
 loupe 35
 luster 22



MN
 malachite 126
 meerschaum 119
 metamorphic rocks 12
 microcline 123
 milky quartz 85
 mocha stone 88
 Mohs scale 16
 moldavite 137
 moonstone 123
 morganite 78
 moss agate 88
 multicolored 21
 nephrite 125

O
 obsidian 136
 oiling 37
 oligoclase 130
 onyx 90
 opal 134

optical properties 20
 organic gems 13
 orthoclase
 colorless 122
 moonstone 123
 yellow 122

P
 padparadscha 95
 pearl 138
 peridot 113
 peristerite 130
 petalite 129
 petrified wood 88
 phenakite 98
 phosphophyllite 127
 physical properties 16
 pink grossular 60
 pink sapphire 97
 plasma 93
 platinum 52
 pleochroic gems 21
 polishing 28
 prase 92
 prehnite 115
 pyrite 63
 pyrope 58

Q
 quartz
 amethyst 82
 aventurine 85
 brown 84
 cairngorm 84
 cat's-eye 86
 chatoyant 86
 hawk's-eye 86
 milky 85
 rainbow 87
 rock crystal 81
 rose 83
 rutilated 87
 sagenite 87
 smoky 84
 tiger's-eye 86
 tourmalinated 87
 with inclusions 87
 quartz cat's-eye 86

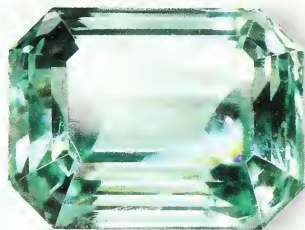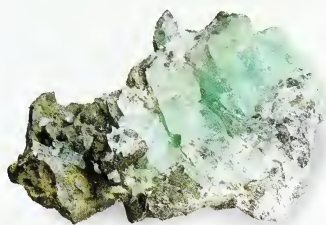

R
 rainbow quartz 87
 red beryl 78
 refractive index 21
 rhodochrosite 100
 rhodonite 132
 rock crystal 81
 rose quartz 83
 rosolite 60
 rubellite 101
 rubicelle 64
 ruby 94
 rutilated quartz 87
 rutile 71

S
 sagenite 87
 sapphire 95
 colorless 96
 green 96
 pink 97
 yellow 97
 sard 90
 sardonyx 90
 satin spar 128
 scapolite 71
 scheelite 70
 schorl 103
 sedimentary rocks 13
 selenite 128
 sepiolite 119
 serpentine 127
 shell 144
 siberite 101
 sillimanite 111
 silver 50
 simetite 148
 sinhalite 114
 Slocum stones 36
 smithsonite 99
 smoky quartz 84
 sodalite 68
 specific gravity 16
 spessartine 58
 sphalerite 63
 sphene 121
 spinel 64
 spodumene 120

staurolite 117
 succinite 148
 sunstone 130
 synthetic gems 34

T
 taaffeite 80
 tanzanite 116
 tektites 137
 thulite 116
 tiger's-eye 86
 titanite 121
 topaz 106
 tortoiseshell 144
 tourmalinated quartz 87
 tourmaline
 achroite 102
 dravite 102
 green and yellow 103
 indicolite 101
 indigolite 101
 rubellite 101
 schorl 103
 siberite 101
 watermelon 103
 Transvaal jade 61
 tsavorite 61
 tugtupite 74
 turquoise 131

UVW
 unakite 121
 uvarovite 59
 vesuvianite 74
 violane 119
 watermelon tourmaline 103
 wernerite 71
 williamsite 127
 wuluite 74

XYZ
 xanthite 74
 yellow orthoclase 122
 yellow sapphire 97
 zircon 72
 zoisite 116

USEFUL ADDRESSES

Gemological Institute of America
1660 Stewart Street, Santa Monica, CA 9040

Canadian Gemmologist Appraisers Association
PO Box 69024, Vancouver, BC, V3K 4W3

American Gem Trade Association
181 World Trade Center, 2050 Stemmons
Expressway, Dallas, TX 75207

Canadian Gemmological Association
21 Dundas Square, Suite 1209, Toronto, Ontario,
M5B 1B7

The Smithsonian Institution
Washington DC, 20560

Gemmological Association of Great Britain
27 Greville Street, London, EC1N 8SU

International Colored Gemstones Association
609 Fifth Avenue, New York,
NY 10017

The Gemmological Association of Australia
PO Box 1155, North Richmond, Victoria, 3121,
Australia

ACKNOWLEDGMENTS

The author would like to thank the Mineralogy Department curatorial team at the Natural History Museum (Alan Hart, David Smith, Peter Tandy, Henry Buckley, Andrew Clark) and the team leader Dr. Robert Symes for their help in getting gem specimens to Harry Taylor in the Photographic Department; my husband, Robert, and daughters, Alice and Emily, for giving me time to work quietly in my study, with only a few interruptions; Dr. Roger Harding, Alan Jobbins, Dr. Joseph Peters, and Christine Woodward for their expert help; and the team at Dorling Kindersley, especially Alison Edmonds, Alison Shackleton, Jonathan Metcalf, Mary-Clare Jeram, Lesley Malkin, and Lucinda Hawksley.

Dorling Kindersley would like to thank: Michael Allaby for compiling the index; Caroline Church for the endpapers; Neal Cobourne for the jacket design; Peter Bull for the rock cycle diagram 12 (tr); Janos Marffy for all additional artwork; Julia Pashley for picture research; Harry Taylor for his patience and co-operation during photography; Alastair Wardle for gem diagrams and the map on pp.14–15; Alison Edmonds for the loan of diamond jewelry for photography, 55 (cl); R. Keith Mitchell for the loan of taaffeite for photography 80 (t); Lesley Malkin and Constance Novis for additional editorial assistance; Peter Cross, Ann Thompson, and Kevin Ryan for additional design assistance.

All specially commissioned photography by Harry Taylor, except 11 (tr), 12 (cl), 13 (tr), 17 (bl & br), 18 (br), 19 (cl), 21 (cl), 26 (cutting a brilliant), 27 (br), 28 (tl & tr), 33 (tl, tr, bl, & br), 34 (tr, bl, & br), 35 (br), 36 (tl, cl & cr), 48 (e & bl), 50 (t & br), 55 (br), 57 (tl), 60 (br), 63 (tr & br), 67 (bl), 68 (cr), 69 (tr & br), 70 (cr & br), 71 (cl, cr, & br), 72 (cr), 74 (cl), 76 (bc), 77 (cl & cr), 78 (br), 81 (br), 82 (br), 83 (br), 85 (br), 87 (tc), 88 (bl & br), 92 (tr, tl, & bl), 93 (tr & c), 94 (br), 95 (cr & c), 98 (tr), 100 (br), 101 (tr), 104 (tr), 106 (br), 107 (cr), 109 (tr), 110 (br), 112 (br), 113 (br), 117 (bl), 120 (tl, tr, & cl), 124 (bl), 125 (tr, cl, bl, & br), 130 (cl, cr, & br), 134 (c), 135 (bc), 138 (br), 139 (l), 141 (cl), 142 (bl & br), 143 (tl), 145 (cl, cr, bl, & br), 148 (br) by Colin Keates; 30 (tr) by Dave King; and 144 (t, bl, & br) by Matthew Ward.

The publishers would also like to thank the following for permission to reproduce their photographs and illustrations:
Vicky Ambery-Smith 50 (tl); Asprey Ltd 31 (br),

49 (cl); Bridgeman Art Library 57 (tc); Cartier 27 (tr), 29 (tr); Crown Copyright (reproduced by permission of the Controller of Her Majesty's Stationery Office) 7 (tr); De Beers 13 (bl & br), 14 (cl); Garrard, the Crown Jewellers 49 (br), 55 (t); Andrew Farmer 28 (bl); Michael Holford 11 (r), 31 (tr), 32 (c & tr), 59 (tc), 106 (br); The Hutchison Library 8 (br); Alan Jobbins 6 (tr), 8 (c), 15 (tr & bl), 20 (cr), 24 (br), 25 (tl, cr, & br), 32 (cr), 35 (cr), 36 (tr & br), 37 (tr), 56 (tr), 59 (tr), 60 (tr), 62 (tr), 75 (tr & cl), 82 (tr), 86 (bl), 94 (tr & cl), 135 (cr & br), 140 (tr), 145 (tr); Bernd Munsteiner 2, 29 (br); The Natural History Museum 11 (bl), 13 (cr), 21 (br), 23 (tr), 24 (bl), 38 (tl); The Platinum Advisory Centre 26 (br), 53 (tl & br); Nicolas Sapieha 53 (tr); The Smithsonian Institution 76 (tr), 94 (cr), 107 (tr); Tiffany & Co 51 (tr & br), 55 (cr); The Victoria & Albert Museum 31 (cl), 32 (br), 125 (cr); Werner Forman Archive 30 (cr); The Worshipful Company of Goldsmiths 49 (tr), 50 (bl), 51 (bl & cr), 53 (bl).





BOSTON PUBLIC LIBRARY



3 9999 03542 018 9


Egleston Square Branch Library
2044 Columbus Avenue
Roxbury, MA 02119-1123

GAYLORD F

EYEWITNESS  HANDBOOKS

GEM STONES

A new generation of field guides, the *Eyewitness Handbooks* make identification of individual specimens sure, simple, and straightforward. Each volume includes hundreds of superb photographs combined with concise, informative descriptions of over 100 specimens. The *Eyewitness Handbook of Gemstones* is packed with more than 800 vivid full-color photographs. It is an invaluable resource for every enthusiast.

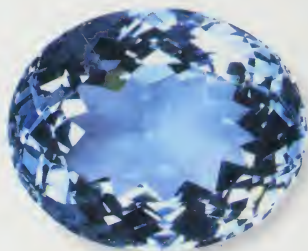

6-70040
Printed in Singapore



ISBN 1-56458-498-4



9 0000 >



9 781564 584984